


UNIVERSAL
LIBRARY

OU_172727

UNIVERSAL
LIBRARY

MINERALS AND THE MICROSCOPE

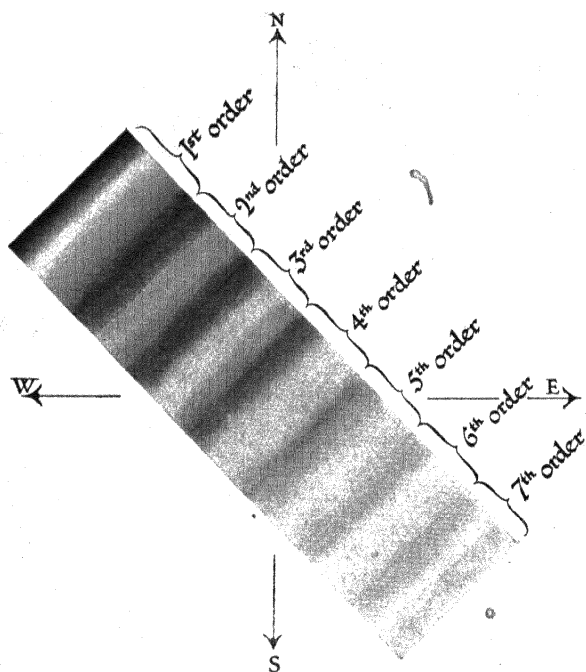

NEWTON'S SCALE.

The colours are seen when a wedge of quartz or gypsum is placed in an oblique position between crossed nicols.

The points of the compass illustrate the scheme adopted in order to indicate directions in the field of the microscope, it being assumed that the observer always faces north.

MINERALS AND THE MICROSCOPE

By

H. G. SMITH, A.R.C.S., B.Sc., F.G.S.

Head of the Department of Geology, East London College.

LONDON : THOMAS MURBY & CO., 1, FLEET LANE, E.C.
NEW YORK : D. VAN NOSTRAND CO., 25, PARK PLACE

First Printed, May, 1914.

Second Edition, November, 1919.

Reprinted with slight corrections, December, 1922.

Reprinted, December, 1927.

Third Edition, enlarged August, 1933.

MADE AND PRINTED IN
GREAT BRITAIN.

PREFACE TO THE THIRD EDITION

THE continued popularity of this book is evidence that it has responded to a demand by students. It is felt, however, that in consequence of increasing knowledge and the development of new ideas regarding Petrology, the second part of the work has become out of date. The whole of that section has therefore been re-written.

Theories are erected on the foundation of observation and experiment, and the ideal book would commence with a detailed description of the rocks, and conclude with an exposition of prevalent theories. In this case, however, the attempt is made to give material which will supplement the knowledge gained during the study of actual specimens and thin sections. If the student has made, or is making, some efforts along these lines, something like the ideal sequence is followed; and the hope is expressed that the method of treatment will give some life even to the study of inanimate materials like rocks.

H. G. SMITH.

June, 1933.

PREFACE

THE object of this book is to help the beginner over his initial difficulties in the study of petrology. Teaching experience extending over some years has convinced me that the difficulties met by the student are far greater than is commonly supposed by those who have forgotten their own early trials, or whose mental equipment was such as to enable them to escape the pitfalls waiting for their less fortunate fellows.

Even a series of lectures by a teacher of undoubted qualifications is not sufficient; the subject matter is so new to most students that very few are able to absorb the facts as rapidly as they are placed before them. It is felt that a good course of lectures and practical work requires amplification by a book whose aim is to smooth over difficulties of this kind.

Amplification of such a course, then, is the chief aim of this work. It is hoped, also, that those who are not able to attend a course of lectures may profit by the instruction contained herein. A point of primary importance, however, is that this book is not intended to serve as a substitute for the examination of thin sections.

The list of minerals described is far from being complete, but some care has been expended in the selection and arrangement of those dealt with, and

it is hoped that when a student has worked through them, he will be competent to, and desirous of, examining the minerals less commonly met with in thin section: •

The section on petrology is designed to bridge over the gap usually left by text books on the subject, and should be used in conjunction with such a book as Harker's *Petrology for Students*, or Hatch's *Text-book of Petrology*.

It has been found necessary to assume that students have a knowledge of elementary physics and of crystallography. The former may quite safely be assumed, but the latter assumption is probably more dangerous; a good and simple description of the subject, however, will be found in the latest edition of Rutley's *Mineralogy*, a book which will be found extremely useful in other respects. •

My thanks are due to the Rector of the Imperial College and to Professor Watts for permission to use the apparatus of the college in the preparation of the photographs reproduced in this book, also to my colleague, Mr. H. H. Read, for reading through the proofs and for many helpful suggestions.

H. G. SMITH.

April, 1914.

CONTENTS

	PAGE
OPTICAL PROPERTIES OF MINERALS	1-62
CHARACTERS OF MINERALS IN ORDINARY TRANSMITTED	
LIGHT	1-14
Colour	1
Form	4
Cleavage	5
Refractive Index	8
Alteration	12
Inclusions	13
Zoning	13
CHARACTERS OF MINERALS IN REFLECTED LIGHT ...	15
CHARACTERS OF MINERALS WITH THE LOWER NICOL	
INSERTED	16-26
Nature of Light	16
Double Refraction of Calcite	17
The Nicol	19
Pleochroism	22
Pleochroic Haloes	24
Twinkling	25
Crystallographic Summary	26
CHARACTERS OF MINERALS BETWEEN CROSSED NICOLS	27-50
Isotropism and Anisotropism	28
Extinction	28
Polarisation Colours	30
Birefringence	34
Newton's Scale	35
Twinning	37
Zoning	39
Anomalous Double Refraction	39
Aggregate Polarisation	40
Determination of Polarisation Colour	40
Sign of Dimetric Minerals	42
Optic Orientation of Trimetric Minerals	45

	PAGE
CHARACTERS OF MINERALS BETWEEN CROSSED NICOLS	
IN CONVERGENT LIGHT	51-62
Methods of obtaining an Interference Figure ...	51
Uniaxial and Biaxial Interference Figures... ..	52
Sign of Uniaxial Minerals ... •	56
Sign of Biaxial Minerals	58
Partial Interference Figures	59
DESCRIPTIONS OF COMMON ROCK-FORMING MINERALS	63-85
Forms of Silica	63
Felspars	64
Felspathoids	67
Micas	69
Other Micaceous Minerals	70
Pyroxenes	70
Amphiboles	72
Olivines	75
Serpentine	76
Apatite	77
Sphene	77
Garnets	78
Tourmaline	78
Topaz	79
Silicates of Alumina	80
Epidote	81
Zoisite	82
Calcite	82
Dolomite	83
Zeolites	83
Cordierite	83
Cassiterite	84
Zircon	84
Opaque Minerals	85
STUDY OF ROCKS	86-122
Igneous Rocks	86
Sedimentary Rocks	104
Metamorphic Rocks	114

LIST OF PLATES

	Newton's Scale in Colours	...	...	...	<i>Frontispiece</i>
					FACING PAGE
I	Six Interference Figures	...	...	...	52
II	Five examples of Quartz and Chalcedony	...	...	...	63
III	Six examples of Orthoclase Felspar	...	...	...	64
IV	Six examples of Plagioclase Felspars	...	...	...	65
V	Six examples of Felspathoids	...	...	...	67
VI	Six examples of Micas, etc.	...	...	...	69
VII	Six examples of Pyroxenes	...	...	...	71
VIII	Five examples of Amphiboles	...	...	...	73
IX	Two examples of Olivine	...	...	...	76
	One example of Serpentine	...	...	...	76
	One example of Sphene	...	...	...	76
	Two examples of Apatite	...	...	...	76
X	Two examples of Garnets	...	...	...	78
	Three examples of Tourmaline	...	...	...	78
XI	One example of Chialstolite	...	...	...	81
	One example of Kyanite	...	...	...	81
	Two examples of Epidote	...	...	...	81
XII	Two examples of Calcite	...	...	...	83
	One example of Dolomite	...	...	...	83
	One example of Zeolites	...	...	...	83
	One example of Cordierite	...	...	...	83
	One example of Cassiterite	...	...	...	83

DESCRIPTION OF A PETROLOGICAL MICROSCOPE


THE foot forms a support for the whole instrument, the pillar being attached to it by means of a joint which allows movement on a horizontal axis. The pillar supports the tube at its upper end, and the stage, RS, at the lower end; the adjustments, A_1 and A_2 , give rise to a movement of the tube with reference to the pillar so as to cause the objective, O, to approach or recede from the stage. O and O_1 are the two objectives; these have different magnifying powers, and either may readily be placed in line with the tube so as to come into use. The eyepiece, E, is a system of lenses fitting into the upper end of the tube; it brings the magnified image to a focus when the objective is properly adjusted.

RS, the rotating stage, supports the microscope slip, which is held in position by means of the two clips. The stage is graduated into degrees, and may be rotated through a known angle, the angle being read by means of a fixed point or a vernier attached to the pillar. The mirror, M, receives light from some source of illumination, and when placed at the proper angle, transmits the light along the axis of the instrument to the eye.

The polariser, P, is a Nicol's prism placed beneath the stage; it is capable of rotation on its own axis, and may be swung aside when not required. A, the analyser, is also a Nicol's prism which is capable of rotation; when required, it is swung into position above the eyepiece.

Additional fittings, the object of which is to produce interference figures, are B, the Bertrand lens, and C, the converging lens. The converging lens is placed between the polariser and the stage, the Bertrand lens in the tube above the objective. The latter consists of a converging lens of the required focal length; it may be mounted in a carrier, so as to enable it to slide in and out of the tube as required, or may be fitted in the lower end of a draw-tube. The illustration shows the tube cut away in order to indicate the position of this lens when in use.

S and S_1 are two slots, into which the wedge or mica plate may be inserted when determinations of " sign " are to be made.

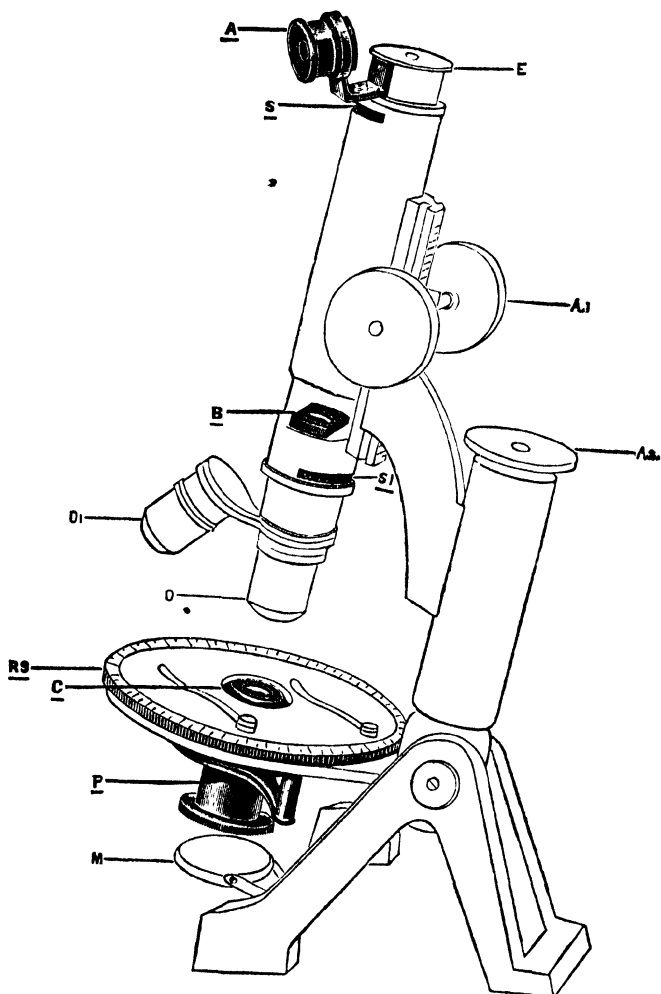

The above illustration shows at a glance the essential features of a Petrological Microscope by means of the letters underlined and the detail work. It will be found that the parts A, B, S, and S1 are differently situated in the microscopes supplied by various manufacturers.

OPTICAL PROPERTIES OF MINERALS

CHARACTERS OF MINERALS IN ORDINARY TRANSMITTED LIGHT


THE first examination of the section should be made with the one inch objective; both polariser and analyser being swung out of the axis of the instrument.

As a rule, it will be seen that the thin section is made up of several minerals, some transparent, others opaque. For the present we shall confine our attention*to the study of those minerals that transmit a certain amount of light; a method for the examination of opaque minerals will be described later.


Colour.—The light transmitted by the different minerals varies both in amount and kind; some minerals are almost opaque, others perfectly transparent. In some cases, the whole of the constituents of white light are allowed to pass through; these minerals are colourless. Other minerals, however, absorb some portion of the spectrum, with the result that the light reaching the eye has a certain colour—the colour complementary to that absorbed. This colour supplies us

with the first means of distinction between the rock-forming minerals.


The section will probably contain several fragments of any particular mineral, and the student will naturally expect that all these fragments will exhibit the same colour, or will agree in being colourless; but it must be realised that, while this may be the case, it is not necessarily so. Variation in the colour of the different fragments is intimately related to the crystal symmetry. Should the mineral in question crystallise in the cubic system, all the fragments present in the section will be either colourless or will transmit the same colour; a good example is the mineral garnet, the common varieties of which transmit a pink colour. On the other hand, biotite, crystallising in the monoclinic system, supplies us with an example of a mineral which varies in colour according to its orientation in the section. The different fragments occupy all possible positions in the rock from which the section is cut; consequently a section supplies numerous cases. Crystallographically, no two of these are identical, and each case has its own absorption. The result is that the different fragments of this mineral exhibit very different shades of brown. It will be seen that we must rely on other characters to demonstrate that such fragments are identical in composition. There are many cases, however, even in the same system, in which all sections of a coloured mineral have much the same shade; a good example is common augite. Again, the mineral muscovite, also crystallising in




1




2



3a




3b



4



5a




5b



7



8

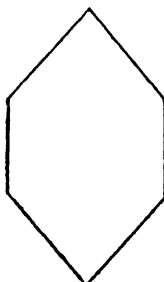

6



9

1. Augite.
Transverse section.

2. Hornblende.
Transverse section.

3a. Quartz—Basal section
3b. " Vertical "

4. Leucite.

5a. Nepheline—Basal section.
5b. " Vertical "

6. Olivine.

7. Tourmaline—Basal section.

8. Spinel.

9. Apatite—Basal section

the monoclinic system, is typically colourless in all its sections. The relationship of colour in thin section to crystal symmetry may be summarised as follows:—

Cubic system:—All sections of one mineral are colourless or exhibit the same colour.

Other systems:—The different sections are usually different in colour; but all may be colourless, or all may be similarly coloured.

Form.—The most useful rocks for microscopic investigation are those igneous rocks known as plutonic. These may be looked upon as aggregations of minerals which have crystallised from the fused state; and as the individual minerals have not all formed simultaneously, it will readily be understood that the first-formed minerals have had the best chance of developing that shape to which their own constitution would lead. The growth of the later-formed minerals has naturally been impeded by the first comers, and the one crystallising last of all has been compelled to fit itself into the space left by the earlier-formed crystals. It will be seen, then, that such rocks will show (1) minerals having their own form (idiomorphic); (2) minerals with their own form imperfectly developed; and (3) minerals whose form has no connection with their own constitution (allotriomorphic).

Further, even those minerals which are idiomorphic will show different outlines according to their position in the rock. The student will be able to form some idea as to the possibilities of variation in form by studying the case of a hexagonal prism

like a six-sided lead pencil. A longitudinal section would show a rectangle; a transverse section, a regular hexagon; an oblique section, as a rule, an irregular hexagon; the shape varying with the degree of obliquity. Other possibilities will occur to the intelligent student.

Having indicated the number of possible cases, we must warn the student that he will not often find perfectly idiomorphic constituents. When they do occur, however, they are extremely useful as a means of identification. Much more frequently he will find minerals giving merely indications of their form. The variations in form are so numerous that it is almost impossible to give summaries in terms of crystallography; it may, however, be stated that sections of cubic crystals are rarely elongated, while many sections of crystals with lower symmetry exhibit this character.


Cleavage.—Even a slight acquaintance with minerals as seen in hand specimen will be sufficient to enable the student to recall examples of minerals showing this tendency to break in definite planes. Calcite splits in three directions; in fact, it is almost impossible to break the mineral in any other direction. The common micas, muscovite and biotite, cleave in one direction with extreme facility; and gypsum also has one perfect cleavage. In thin section, these cleavages are seen as parallel straight lines. Minerals having more than one cleavage usually show more than one set of parallel cracks, those of the one set intersecting the others. The student must realise that these cleavages have a

definite crystallographic orientation; in the case of the micas, the one perfect cleavage is parallel to the basal pinacoid; the three cleavage directions of calcite are parallel to the faces of a rhombohedron. It must be understood also, that they are not necessarily parallel to faces actually present in the crystal; calcite, for example, rarely crystallises with the form of the rhombohedron to the faces of which its cleavages are parallel. The forms presented by calcite crystals are numerous and bewildering to the young student, but any one of these crystals may be cleaved in the three directions which are those of the faces of what is known as the fundamental rhombohedron. This constancy of cleavage direction for any mineral which shows cleavage at all, supplies another useful means of identification.

We find, however, a certain amount of variation in the different sections of any mineral. Micas, for instance, have one perfect cleavage; but in thin section we see many examples in which no cleavage is visible. The explanation is perfectly simple. Consider the analogous case of a book; the cleavage flakes of the mica correspond to the leaves of the book. Let the book rest flat on the table, and imagine it cut in vertical section; the cut surface would show a series of parallel lines produced by the intersection of the plane of section with the leaves. A horizontal section would not, however, show any cleavage, because it never cuts across a leaf. It is necessary to point out, however, that oblique sections do not always show cleavage. One

might expect that, as the horizontal section already considered is the only one not cutting across the cleavages, it would be the only one not showing the cracks in section. This is not the case. If we consider a series of sections varying from the perpendicular to the parallel, we find the cracks becoming less and less conspicuous, until, long before the parallel condition is reached, the cleavages become invisible.

We have considered the case of micas in some detail as they supply a very simple case, which serves as a peg on which to hang an important principle.

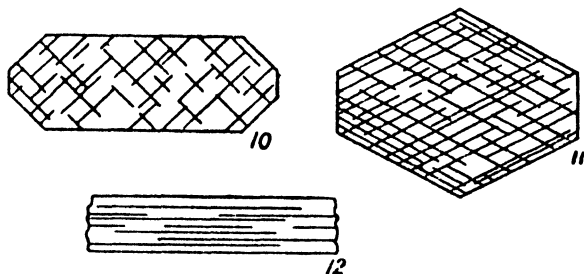

10. Augite.

11. Hornblende.

12. Biotite.

If we now pass on to the case of a mineral showing two cleavages, we have to consider, in addition to the presence of cleavage, the angle of inclination between the cleavages. Hornblende (monoclinic) is a common rock-forming mineral with two cleavage directions which are parallel to the prism faces.

A transverse section of four such faces would give a rhomb with angles of 125° and 55° ; and these, therefore, are the cleavage-angles typically exhibited by this mineral in thin section. A vertical section, however, shows one cleavage-direction only; the reason should be quite clear after a little consideration. Some difficulty is encountered by many students who fail to understand the value usually attached to a cleavage angle; it is quite true that the angles formed by the intersection of the cleavages, as seen in oblique sections, would vary with the degree of obliquity if they were visible. It should be remembered, however, that if section and cleavage are not inclined at or near a right angle, the cleavage cracks will not be visible; consequently, when the two cleavages of hornblende are seen in section, that section is approximately transverse, and the characteristic angles are exhibited. Augite is another monoclinic mineral with prismatic cleavages, but here they are almost at right angles; this difference in the cleavage angles is extremely important as a means of distinction between the two minerals.

Refractive Index.—For a full account of this property of solids and liquids, the student is referred to text books on Light; we shall here consider only those aspects which directly concern us.

A rock section is an extremely thin slab of rock which is sandwiched in between layers of a substance known as Canada balsam; this sandwich rests on a glass slip and is covered by another and much thinner slip of glass, but these may be

ignored. We are concerned here only with the substance in contact with the minerals making up the rock.

It is well known that colourless transparent substances are visible only when they differ in optical density (refractive index) from the fluid in which they are immersed; and the greater the difference between the two substances, the more conspicuous will be their limiting surfaces. An instructive experiment is to powder common glass and drop it in water. Better still, powder a fragment of the mineral cryolite and drop the powder in water; it is with the greatest difficulty that the mineral can be seen when immersed in the liquid, and one is inclined to believe that it has passed into solution. It is invisible, however, merely because the two substances, cryolite and water, have almost exactly the same refractive index.

We are now in a position to make a general statement. The visibility of a transparent solid depends on the difference in refractive index between it and the fluid in which it is immersed. Minerals in thin section may be considered to be embedded in a liquid—the Canada balsam. On examining the margins of the transparent minerals in section, we find, by working round the edges of the section where the minerals are in contact with Canada balsam, that some of the edges stand out conspicuously, while where other minerals come in contact with Canada balsam, the junction is comparatively inconspicuous. The minerals are in contact with the mounting medium

also on their upper and lower surfaces, and these supply us with additional information. In consequence of the method of preparation of thin sections, these surfaces are rough; they are grooved and pitted by the powders employed in the grinding. Those minerals differing in refractive index from that of the mounting medium show these rough surfaces when carefully focussed; on the other hand, those constituents approximating in refractive index to the Canada balsam always appear to be smooth in consequence of this approximation. Clearly, then, we have here a means of determining by mere inspection whether or not a particular mineral has a refractive index which is near to or distant from that of Canada balsam, 1.54.

But it is necessary to determine whether the refractive index of the mineral in question is higher or lower than that of Canada balsam; and a means of making this determination is supplied by BECKE'S TEST. Using the high power objective, focus carefully an edge of the mineral where it is in contact with the mounting medium, choosing an edge which is as clean as possible; if a small fragment of the mineral has become detached from the rest of the rock and thus lies surrounded by Canada balsam, it will supply the ideal conditions. Rack the tube up and down a little on each side of the position of focus, being careful not to push the objective through the slide, an accident which occasionally happens to the beginner. It will be seen that, when the fragment is slightly out of focus, it is surrounded by, or encloses, a ring of light, which

expands or contracts as the tube is alternately raised and lowered.

There are two cases. The refractive index of the mineral is (1) higher, and (2) lower, than that of Canada balsam, 1.54. It is convenient to consider only what happens when the objective is being raised. In the first case, when the mineral is denser than the mounting medium, the ring of light will contract; it will pass from the Canada balsam to the mineral. When the mineral is the less dense substance, the light passes from the mineral to the balsam.

In both cases, as the objective is raised, the light passes from the substance with the lower, to that with the higher refractive index. It is thus possible, by this test, to eliminate all those minerals which differ from the one under consideration in being higher or lower than Canada balsam in refractive index; and the method of elimination will sometimes be found extremely useful in making identifications. A concave mirror should always be used in making this test, and a diaphragm will be found useful in difficult cases. The existence of this more intense illumination depends on the property of total internal reflection, as the light impinges on a surface limiting a dense substance. In some cases it is possible by this method to compare the refractive indices of two minerals in contact, but the contact is not always sufficiently good to give results.

As examples of case 1, topaz, apatite, or olivine gives good results. Fluor, nosean, and leucite supply good examples of case 2.

When reference is made to "the refractive index" of a doubly refracting mineral, it must be understood that the mean refractive index is referred to, also, that that value has been obtained when using sodium light.

Alteration.—Orthoclase felspar supplies us with a good example of a mineral which is liable to decomposition on exposure to atmospheric conditions. If the rock from which the section has been cut is "fresh," this mineral is quite colourless and transparent; but when decomposed it has lost its transparency, and has become a mere aggregate of countless greyish semi-opaque particles of the hydrated mineral, kaolin. Some fragments are in an intermediate condition—altered merely in parts; the student should examine slides containing the mineral showing different degrees of alteration. The case of orthoclase is specially important because the tendency to decomposition is often useful in distinguishing this mineral from quartz, which it may strongly resemble.

Olivine, also, is unstable under atmospheric conditions, and is frequently seen more or less altered to the green mineral serpentine. The mode of alteration is very characteristic. Olivine, when fresh, is a colourless mineral, usually traversed by irregular cracks, and it is along these that the alteration product first develops. Later stages show that these "channels" of serpentine have become wider, the "islands" of fresh olivine have become smaller, and the last stage shows the mass of serpentine having the form of the olivine from

which it was derived. The serpentine is commonly associated with granules of black iron oxide, another product of the decomposition of the original olivine.

Biotite is another unstable mineral, the product in this case being the green mineral chlorite. Excellent examples showing different stages of alteration are obtainable in different sections, ranging from the fresh brown biotite to the pseudomorph in chlorite.

Inclusions.—In some few cases, minerals may be seen to contain inclusions of other substances which are useful in making identification. The best examples are seen in some specimens of leucite, which may show small fragments of other minerals (notably green augite) arranged in a ring. The student, however, must not expect all specimens of leucite to exhibit this character.

Other minerals contain inclusions, but the character is not often of service in distinguishing the mineral. Quartz may show liquid and gas inclusions, and orthoclase sometimes contains glass.

Zoning.—It is often found that a crystal is not uniformly coloured, but exhibits an arrangement of colour bands which are concentric with the exterior. Nosean, for example, is commonly distinguished by a well-marked brown periphery, although the centre is colourless. Tourmaline, brown garnets, and pyroxenes frequently show a succession of concentric rings of colour; this variety of zoning is known as colour-zoning. A similar structure,

already mentioned under the heading of inclusions, is exhibited by some minerals in consequence of their manner of arranging inclusions. Leucite is the most striking example; but a less conspicuous zoning by inclusions is sometimes seen in feldspars and pyroxenes.

Zoning is most commonly exhibited by the minerals which are grouped together as isomorphous, and no better example can be found than the Albite-Anorthite series of plagioclase feldspars. It is often found that the crystal is not homogeneous, but is built up of successive shells, each of which has a composition which is different from that of its neighbours; the crystal has commenced its growth as one member of the series, but has received additions of ever-varying composition. In consequence of this structure, the mineral being liable to decomposition and the several shells being unstable in different degrees, the weathering action has picked out the less stable layers and has emphasized the zonal nature. When the kaolinised layers have received a stain of iron oxide, as sometimes happens, the zoning becomes still more striking. But even when the feldspar is quite fresh, the zones are sometimes visible in consequence of the difference in refractive index between them. The colour-zoning of tourmaline, pyroxenes and garnets, is also to be attributed to an isomorphous relationship; it happens to be the case that the different members of the particular series are differently coloured.

CHARACTERS OF MINERALS IN REFLECTED LIGHT

HITHERTO we have considered only the case of minerals which, in section, transmit a certain amount of light; but some minerals, even in thin section, are quite opaque, and a special method of investigation is employed for their identification. The mirror must be tilted so that no light comes from below, the tube placed vertically, and the examination should be conducted near a window or other source of light, so as to allow of reflection from the upper surface of the slide. In these circumstances, magnetite shows a black metallic surface if fresh; it is associated with a red alteration product (hæmatite) if decomposed. Ilmenite (titanoferrite) if fresh, has also a black metallic appearance, but decomposition results in the formation of a whitish substance (leucoxene) which may be arranged in triangular areas; but this geometrical arrangement is not always seen. Iron pyrites shows a brass-yellow colour and metallic lustre.

This test may also be employed with advantage in the examination of some minerals which are not opaque; the distinction between quartz and felspar may sometimes be made advantageously by observing the mineral in question in reflected light. Any alteration of the felspar is easily seen by this method.

It should be remembered that in all the methods of examination to be described later, transmitted light is to be used.

CHARACTERS OF MINERALS WITH THE LOWER NICOL INSERTED

HAVING completed a survey of the characters employed in mineral identification when the microscope is used without either nicol, the attention of the student may be directed to the characters to be observed when the lower nicol (the polariser) is in position in the axis of the instrument, the upper nicol (the analyser) still being swung aside, as in the preceding section.

The Nature of Light.—In order to understand the phenomena, it is necessary first to realise some elementary facts as to the nature of light and the construction of the Nicol's prism.

As light may be transmitted through what is known as a vacuum, it is necessary to assume the existence of a substance pervading all space, by means of which the transmission is effected. This substance is known as the ether. It is quite certain that light is transmitted as a consequence of a series of vibrations which take place at right angles to the direction in which light is travelling, and the theory formerly accepted was that the ether particles themselves performed these vibrations to and fro without undergoing any movement along the line of propagation of the ray. The theory has now been considerably modified, and a theory of oscillation,

not of the particles themselves, but of their electrical condition, is now held to account for the facts more satisfactorily. But these oscillations or vibrations certainly do take place, and they take place at right angles to the direction of propagation of the light. A ray of ordinary light performs its vibrations in all directions possible subject to this limitation, that is, in all the directions perpendicular to the direction of transmission; but light which has passed through a nicol performs all its vibrations, not merely perpendicular to this direction, but parallel to a definite line which fulfils this condition. Such light, performing its vibrations in one plane only, is said to be polarised, and we have now to learn something about the construction of a "nicol" in order that we may realise the conditions of investigation.


The Double Refraction of Calcite.—The nicol is made of a clear variety of calcite known as Iceland Spar, a substance possessing to a remarkable degree the power of splitting a ray of entering light into two—the property we know as double refraction. The mineral has an extremely good cleavage in three directions, and, split along these cleavages, it yields a fragment of the form known as the rhombohedron. Light entering such a fragment perpendicularly to one of the cleavage planes is split into two rays, and, in consequence, any object viewed along such a perpendicular is doubled; two images reach the eye. The most satisfactory demonstration of this fact is obtained by resting the fragment on a sheet of white paper on which a small

blot of black ink has been made. Seen from above, such a spot is doubled. Now rotate the fragment. It is seen that one of the images remains stationary, while the path of the other is the circumference of a circle with the stationary image as centre. The stationary image behaves just as if the crystal were a slab of glass; it is therefore said to be produced by the ordinary ray. The ray producing the movable image, on the other hand, does not obey the ordinary laws of refraction. To anyone who has studied only singly refracting substances, its behaviour appears to be quite extraordinary, and it is therefore known as the extraordinary ray.

By looking at the surface obliquely, we can see that the ordinary image appears to occupy a higher position inside the fragment than does the extraordinary image. In other words, the density of the crystal for the ordinary ray is greater than for the extraordinary ray, or, the velocity of the extraordinary ray is greater than that of the ordinary ray. The fact that two such rays travelling in a doubly refracting crystal have different velocities, is extremely important to the student who wishes to understand what follows, and this experimental demonstration of the fact should help materially to fix the ideas.

We have seen, then, that a ray of light incident normally on a face of such a rhombohedron is split into two, each ray having its own path and a velocity which depends on the nature of the crystal. Still further information may be obtained if the two spots are examined through a nicol. The nicol

may, for the present, be considered as an instrument capable of transmitting only that light which vibrates in a direction known as the principal section—the line A.B. (Fig. 13). When the nicol is




13. The nicol seen from above.

rotated on a vertical axis, it is seen that the two spots appear and disappear alternately, and that a rotation of 90° is necessary to produce this alternation. Granting our assumption as to the direction of the vibrations transmitted by the nicol, it is easily demonstrated that each ray emerging from the cleavage fragment is polarised (performs its vibrations parallel to one line only), and that the two vibration directions, that of the ordinary ray and that of the extraordinary ray, are at right angles. Clearly, then, if it is possible to prevent the emergence of one of these rays from the Iceland spar, an efficient instrument for the production of polarised light may be obtained. Such an elimination is effected by the nicol. Before its operation can be understood, however, the student must realise what is meant by total internal reflection.

The Nicol.—A ray of light passing obliquely from one transparent substance to another, is refracted at the surface, the amount of refraction being proportional to the difference in optical density between the two substances. A ray passing from the less dense to the more dense substance is refracted towards the normal. Now, consider

what happens when a ray meets the surface from the more dense side, taking the case of glass and air. A ray such as B. C. D. (Fig. 14) passes from one substance to the other, but is refracted away from the normal—the angle of incidence is less than the angle of refraction. The angle of incidence for which the angle of refraction is 90° is of particular importance, and is known as the critical angle; when the angle of incidence is smaller, light passes to the rarer medium; when the angle of incidence is greater, no light emerges; it is reflected from the surface back into the denser medium. If then, two rays impinge on such a surface, with angles of incidence less and greater than the critical angle, one will pass to the rarer medium, the other will be totally reflected at the surface. The one succeeds in passing the surface, the other fails.

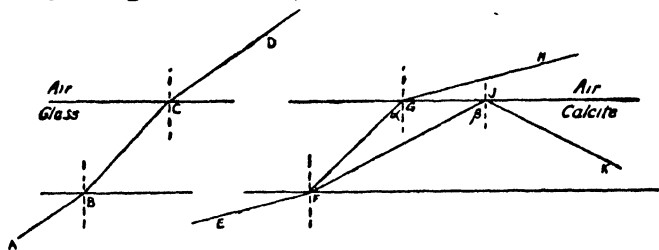


14. Refraction.


15. Refraction and total reflection.

Figure 15 represents the case of a doubly refracting substance where the entering ray, E. F., divides; one ray, E. F. G. H., emerges, because α is less than the critical angle; another ray, E. F. J. K., is totally reflected at J., because β is greater than the critical angle.

The student is now in a position to understand the principles on which a nicol is constructed.

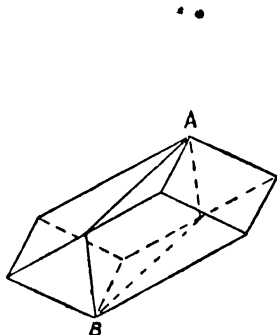

16. The film of Canada balsam within the nicol.

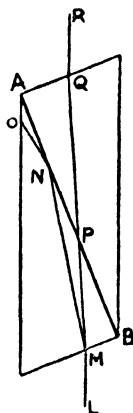

17. Separation of the two rays by the nicol.

An elongated cleavage rhombohedron of Iceland spar is cut into halves, as shown in Figure 16, and the two cut surfaces cemented together with Canada balsam; the two end faces are ground down so as to convert an angle of 71° to one of 68° . Figure 17 shows a section of the nicol where the plane of the paper is perpendicular to the film of Canada balsam A. B. with the vertical edges parallel to the axis of rotation when in position in the microscope. A ray of light entering at the lower surface is split into two. The ordinary ray is the more refracted, meets the film of balsam at N. with an angle of incidence greater than the critical angle, and is consequently


totally reflected to O, as the refractive index of the calcite for the ordinary ray is greater than that of the balsam (1.54). None of its light emerges at the upper surface of the nicol. •

The extraordinary ray is less refracted, and takes the path M.P.Q.R., penetrating the film of balsam at P., because the angle of incidence is less than the critical angle.

The vibrations of the extraordinary ray are executed in the plane of the paper; the emerging light is made up entirely of extraordinary rays; and, consequently, the desired end is achieved by this construction. Only plane polarised light is transmitted by the nicol. The vibration direction of this emerging light is the direction of the shorter diagonal of the end face as seen from above.


Pleochroism.—We are now in a position to consider the microscopic examination of thin sections when the lower nicol, the polariser, is in position in the axis of the instrument underneath the stage.

The light reaching the section has previously passed through the polariser, and is consequently performing its vibrations parallel to the principal section of that nicol, which, although the nicol is capable of rotation, we shall, for purposes of description, consider to be fixed in an E.W. direction. If now a section containing the mineral biotite is placed on the stage, and the stage rotated, it will be seen that the mineral changes colour from a pale brown to a dark brown,



18. Plan of the polariser in position.

and that a rotation of 90° is necessary in order to produce the maximum change.

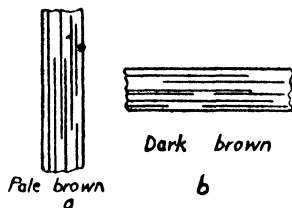

19. The pleochroism of biotite.

This property of certain minerals, exhibited very strikingly by biotite, of changing colour when thus examined, is known as pleochroism. It supplies us with an extremely valuable means of distinguishing many minerals with the polarising microscope.

The case of biotite will be easily understood if it is remembered that such a section is capable of transmitting light vibrations in two directions only. These two directions are at right angles, parallel and perpendicular to the cleavage direction. In position (a) Fig. 19, the whole of the light transmitted vibrates in one of these directions, and the mineral absorbs its minimum amount of light. In position (b), the whole of the light transmitted vibrates in the other of these directions, and the mineral absorbs its maximum amount of light. In an intermediate position, some light is transmitted vibrating in each of the two vibration directions, each direction absorbs its own amount of light, and consequently the transmitted light is intermediate in shade between the two pleochroism extremes.

Other common minerals affording good examples

of pleochroism are, hornblende (pale green to dark green or pale brown to dark brown); tourmaline (usually pale brown to dark brown); andalusite (colourless to pink); ægirine (usually a rich yellow to blue green). In all these cases the minerals are doubly refracting, and, as a rule, their sections have two rectangular vibration directions with different powers of absorption. It must be understood, however, that the strength of the pleochroism depends on the direction in which the section is cut; for instance, basal sections of biotite exhibit very feeble pleochroism, while basal sections of tourmaline are absolutely non-pleochroic. This crystallographic variation emphasizes the necessity for examining as many fragments of the mineral as are available in the slide before an identification is made.

Pleochroic Haloes.—Certain minerals, otherwise colourless in thin section, show curious circular brown areas, each of which contains at its centre an included fragment of some other mineral. These brown patches change colour when the section is rotated above the polariser; they are, in fact, pleochroic areas in an otherwise colourless section. It is quite certain that the including mineral has acquired this property in consequence of the presence of this minute inclusion. Several theories have been put forward to account for these pleochroic haloes, but it has now been satisfactorily proved that the development of colour around the inclusion is the result of the fact that such an inclusion is radio-active, and that its ejected

particles have produced an ionisation effect on the mineral in contact. Minerals showing these haloes are muscovite, cordierite, tourmaline, and biotite. The last two minerals are not colourless, even in thin section, but in their case the colour has been rendered more intense around the inclusion.

Twinkling.—A change which cannot be called pleochroism takes place when sections of the mineral calcite are rotated over the polariser. Calcite is doubly refracting, and consequently, most of its sections possess the two rectangular vibration directions for transmitted light. When the rotation takes place, the mineral shows, at one time, rough surface, well defined borders, and conspicuous cleavages; at another time, smooth surface, faintly defined borders, and inconspicuous cleavages. The change is from a mineral with a high refractive index to one with a low refractive index, and these extremes of relief are exhibited when the two vibration directions of the calcite in section come to be parallel in turn with the vibration direction of the light emerging from the polariser. This means that each of the two vibration directions has its own refractive index. A rapid rotation of the stage (or of the polariser beneath it) produces a rapid change of relief which cannot be better described than by the name of twinkling. This is quite different from pleochroism, which is essentially a change of colour, whereas the calcite remains quite colourless. Other minerals with a high double refraction show the same effect, not-

ably the other rhombohedral carbonates, but few other minerals show a conspicuous change of relief, though theoretically, all doubly refracting sections ought to show some such change. Only in a few cases, however, such as the one cited, is the change sufficiently great to be worthy of consideration in practice.

Crystallographic Summary.—It is a matter of some difficulty to tabulate the pleochroic properties of minerals crystallographically in such a way as to be of assistance to the student, but it may be stated quite definitely that the following sections are non-pleochroic:—

All colourless sections.

All sections of cubic minerals.

Basal sections of dimetric minerals.

Other sections may show pleochroism. Some show a striking change of colour, others merely a slight change; in still others the absorptive powers of the mineral for the two vibration directions are so nearly equal that even the most imaginative observer fails to notice any change of shade or colour.

CHARACTERS OF MINERALS BETWEEN CROSSED NICOLS

WHEN minerals are to be examined between crossed nicols, both analyser and polariser must be placed in the axis of the microscope, and, moreover, the two nicols must be rotated to such positions that, with an empty stage, no light reaches the eye. In order to simplify this adjustment each nicol is provided with a catch which indicates the correct position. It must be borne in mind by the beginner that if the two nicols are used, they *must* be in the crossed position, and neither may be rotated; rotation of the stage, however, is not only permissible, but essential. We have already seen that the light transmitted by the polariser vibrates only parallel to an E.W. line—the principal section. The analyser is similar to the polariser in all respects except that of position; its principal section is in a N.S. direction. The result of this “crossing” of the two nicols is that the emerging extraordinary ray of the polariser becomes the ordinary ray of the analyser, and is totally reflected from the film of balsam. With an empty stage, the polarised light from the lower nicol is allowed a free passage to the upper nicol, and, consequently, the whole of the light transmitted by the lower is stopped by the upper; the field is quite dark.

A plate of glass, or any other singly refracting substance placed upon the stage does not produce any alteration of this condition, the reason being that it has no power to change the vibration direction of the entering light. Canada balsam is another singly refracting substance, hence, we are quite certain that if any alteration is produced in the dark field when a microscope slide is placed on the stage, such alteration is due entirely to the minerals in the slide.

Isotropism and Anisotropism.—Some mineral sections have no power to produce any illumination; they are singly refracting and consequently are quite dark between crossed nicols. They remain in that condition during a complete rotation of the stage, and are said to be **ISOTROPIC**. All sections of minerals crystallising in the cubic system, and basal sections of minerals crystallising in either of the dimetric systems, are isotropic. All other sections are **ANISOTROPIC**, that is, they are alternately dark and illuminated when the stage is rotated.

Extinction.—It is found that anisotropic sections, for most positions of the stage, transmit light of a certain colour, but that, from time to time during rotation they become dark—they are said to extinguish; and if the angle of rotation is taken, it will be found that extinction takes place at intervals of 90° exactly. For instance, most sections of the mineral apatite (crystallising in the hexagonal system), which are elongated, colourless, have a high refractive index, and a basal cleavage,

MINERALS AND THE MICROSCOPE

Lines 7, 8 and 9 on page 29 should read :

The colour between crossed nicols is bright pink or green, and this extinguishes when the cleavage is N.S. or E.W. Both these cases show straight

when rotated between crossed nicols, show a colour which is grey; this is extinguished when the edges are N.S. or E.W. Another good example is supplied by the mineral muscovite. This usually shows no definite outline, but seen in ordinary light it is colourless, and shows a well-defined cleavage. The colour between crossed nicols is bright pink it is colourless, and shows a well-defined cleavage. is N.S. or E.W. Both these cases show straight extinction, that is, extinction takes place when some definite direction, edge or cleavage, is placed N.S. or E.W.

Other minerals, however, although they extinguish at intervals of 90° , do not extinguish in these positions, but at some other position during rotation. Most sections of the mineral augite, for instance (pale brown, high refractive index, and showing one or two good cleavages) extinguish when the edges of the fragment are not parallel to either of the rectangular cross-wires in the eye-piece of the microscope—placed N.S. and E.W. Such sections show oblique extinction, and it is sometimes useful to know the position at which extinction does take place. This angle of extinction is measured either from the N.S. or the E.W. cross-wire. In order to determine its value, the stage is first rotated until the mineral fragment is extinguished, when the angular position of the stage is read; the stage is then rotated until the crystal edge is parallel to one of the cross-wires, when the stage reading is again taken; the difference between the two readings gives the angle of extinction. It will

be seen, however, that this is only one of two possible values; the other value would have been obtained if rotation had brought the edge parallel to the other cross-wire. These two values are, of course, complementary, and it is usual to take the smaller value as the angle of extinction.

Polarisation Colours.—We may now proceed to consider the reasons why a section in one position gives a polarisation colour, and in another becomes extinguished. It has already been seen (1) that if light leaves the section vibrating as it entered (as it left the polariser) it must suffer elimination in the analyser; (2) that a doubly refracting section has two rectangular vibration directions which are the only possible directions of vibration in the section; (3) that extinction takes place at intervals of 90° .

If we suppose that the mineral section is in such a position on the stage that its two vibration directions coincide with the cross-wires, N.S. and E.W., the light emerging from the polariser will travel through the section vibrating exclusively along the E.W. vibration direction in the section, and will emerge from it still vibrating E.W., that is, in such a way as to be totally reflected by the analyser. A similar result must be obtained if the section is turned through 90° , for then the other vibration direction has come to lie E.W., and again total reflection is effected by the analyser. Such positions of the section, then, must secure extinction.

The reason for the production of polarisation colour when the vibration directions are not parallel

to the cross-wires, is not quite so simple; but it is not very difficult to obtain some idea as to the causes. It must be realised that the two vibration directions in the section are the only two possible for light penetrating the mineral, and also that while each vibration direction secures retardation of the light, the light which has vibrated in one of these directions has suffered a retardation which is not equal to that suffered by the other. Suppose that these directions make angles of 45° with the cross-wires. The light emerging from the polariser is vibrating E.W. On entering the section it divides; some vibrates N.E : S.W., the remainder N.W : S.E. The two rays travel up to the analyser, and although there must be some resolution of the two into N.S. and E.W. vibrations, the remainder reaches the analyser vibrating in other directions. • The essential point is that this light has traversed the section vibrating in different directions, and consequently there is a relative retardation. On entering the analyser, the vibration directions are reduced to two only : E.W. and N.S. The E.W. vibrations are totally reflected from the film of balsam, and it only remains to consider the N.S. vibrations. Some portion of the light has traversed the section vibrating N.E : S.W., the remainder has traversed the section vibrating N.W : S.E. That is, there are two rays vibrating in the same plane with a difference of phase, and this difference is comparable with the wave lengths of light. Clearly then, the conditions are such as to produce interference, for it is evident that for at

least one of the constituents of white light, the half wave length must divide into the relative retardation so as to give some odd whole number. Disregarding other kinds of interference, this particular kind must result in the elimination of the colour in question; the complementary colour (the polarisation colour) penetrates the analyser, and reaches the eye. The student will see that the polarisation colour depends entirely on the amount of the relative retardation effected between the two rays traversing the mineral section; this is quite unlike the case of pleochroism, which depends on the difference between the absorptive powers of the two vibration directions.

In considering the difference between the two retardations, it is necessary to take into account:—

- I. Thickness of section.
- II. Crystallographic orientation of section.
- III. Nature of mineral.

I. That the polarisation colour is dependent on the thickness of section in the case of anisotropic minerals, is beautifully demonstrated when a wedge-shaped fragment is placed between crossed nicols. Crystalline gypsum* is a suitable material for experiment. This mineral, which possesses a perfect clinopinacoidal cleavage, should be cleaved into a flake about one-sixteenth of an inch in thickness, and from this a small rectangle measuring about $1\text{ in.} \times \frac{1}{2}\text{ in.}$ should be cut with a knife, care being taken that the edges of the rectangle are parallel to the two vibration directions. This can be

* Quartz is equally useful.

done by drawing an E.W. or N.S. line on the flake when it is in extinction between crossed nicols. The rectangle should be cemented with Canada balsam near the end of a glass slip, half an inch in width, and carefully ground down so as to make one end as thin as possible, while retaining the full thickness at the other. When such a wedge is mounted and placed between crossed nicols in a N.E : S.W. or a N.W : S.E. position, it is seen to exhibit the succession of gorgeous colour-bands known as Newton's Scale. Every student should take an early opportunity of examining this scale,* as no amount of description will serve to give an adequate idea as to the nature of the colours. It will be necessary to refer repeatedly to this scale, but for the present we may look upon it simply as a complete proof that the particular polarisation colour produced depends on the thickness of the doubly refracting mineral through which the light has passed, the greater thickness effecting a greater relative retardation.

II. That equal thicknesses of the same doubly refracting mineral produce different polarisation colours when the sections have different crystallographic orientations, may be easily proved with almost any such mineral. Quartz supplies a very suitable case. If three sections are cut, say, parallel to the basal pinacoid, the rhombohedron, and the prism, ground down to the ordinary thickness, and mounted, they will show quite different colours between crossed nicols; the basal section is

* See frontispiece.

isotropic, the other two are anisotropic; the rhombohedral section polarising in grey, and the prismatic section in yellow. Barytes is another common mineral giving good results; the macropinacoidal section polarises in yellow, and the brachypinacoidal section in bright pink or green.

III. That the polarisation colour depends on the nature of the mineral may be demonstrated by mounting prismatic sections of quartz and calcite side by side. The quartz polarises in yellow, and the calcite in pale grey.

Birefringence.—All these polarisation colours in the case of anisotropic sections are due to the amount of relative retardation effected in the section—the difference between the velocities of the two rays travelling in the section, or, expressed differently, the difference between the two refractive indices, the retardation increasing, of course, with increase of thickness. Taking quartz as an example, we have seen that differently oriented sections produce different polarisation colours; if these colours are compared with those of Newton's scale, it will be seen that all three colours are found near the thin end of the wedge—low down in the scale; the yellow is the highest of the three, and this colour must be produced by that section of the mineral for which the difference of refractive indices is greatest. No other section of quartz will show polarisation colours higher in the scale than the yellow produced by the prismatic section; that is, such a section contains the two vibration

directions having the maximum velocity difference for the mineral. This difference is best expressed numerically as a difference between the two refractive indices. •

It may be demonstrated experimentally that when the light vibrates parallel to the *c* crystallographic axis of quartz, the refractive index is 1.553, and that when the vibrations take place at right angles to this direction, the refractive index is 1.544. The difference, .009, is clearly a measure of the strength of the double refraction for this particular mineral, and this value is the birefringence.

Every doubly refracting mineral agrees with quartz in this respect, that it has one particular section containing the two vibration directions giving the maximum and minimum velocities for the mineral. • Light vibrating in these directions has the maximum difference of refractive index for the mineral; the difference is the birefringence of that mineral, and, stated numerically, gives us some idea as to what polarisation colours the section of ordinary thickness is capable of producing.

Newton's Scale.—As it is often convenient to refer to these colours in terms of Newton's scale, it is necessary to examine this more closely. Examining these colours, beginning at the thin end of the wedge, we see that the first few colours are, dark grey, light grey, white, yellow, and red; these constitute what is known as the first order. The succeeding colours include at intervals, bands of

red or pink, the pink becoming paler and paler until it is indistinguishable from pale grey or white. These repeated bands supply a useful means of splitting up the scale into orders, each band terminating an order. It is difficult to state how many orders are exhibited by such a wedge, as, to some eyes, a colour high up in the scale may appear to be pink or green, while to others it is simply a white or grey. However, seven of these orders are distinctly visible; higher colours may be referred to as whites of a high order. No two orders exhibit quite the same colours, but only practice will enable the student to state definitely on examining mineral fragments between crossed nicols, to what order exactly the colour belongs. The first order colours are fairly characteristic; those of the second and third orders are the brightest in the scale; those of the higher orders become more and more pale. It is well for the student to realise that it is not advisable to use the words high and bright as synonyms; the higher colours in the scale are not bright.

An anisotropic section, colourless in ordinary light, shows when between crossed nicols a colour which is due entirely to interference; but the case of an anisotropic mineral section which absorbs some constituent of white light is not quite so simple. Muscovite, which is colourless in ordinary light, polarises in bright pinks and greens; biotite, with approximately the same birefringence, usually shows only a greyish brown. The reason for this is, of course, that biotite shows

interference colour and absorption colour simultaneously. Tourmaline and brown hornblende supply other examples of this masking of the polarisation colour; while brown sphene, whose polarisation colour is a high order grey, shows between crossed nicols a colour not noticeably different from the absorption colour. One can only say of such a section of sphene, that it is anisotropic.

A few minerals, placed between crossed nicols, show what are known as ultra-polarisation colours. These colours are not to be found in Newton's scale, and are shown only by a few minerals, all with a very low birefringence. Chlorite, a monoclinic micaceous mineral, and zoisite, an orthorhombic mineral allied to epidote, occasionally show these ultra-blues or ultra-browns. The most satisfactory explanation of these polarisation colours is that the section is isotropic for some colours and anisotropic for others.

Twinning.—The observant student has already noticed that while some mineral sections polarise and extinguish as a whole, differences of colour being easily explainable as the result of variations in thickness, some particular mineral fragment is divided into two areas, the dividing line being straight, and usually sharply defined. Of these two areas, one is in a position of extinction when the other is illuminated, and vice versa. Moreover, the polarisation colours of the two areas are unlike. Orthoclase felspar will often show this difference of extinction position and also of

polarisation colour, one area showing yellow and the other grey. These peculiarities are indicative of twinning, and often afford a useful means of distinction between different minerals. The reason for the different positions of extinction of the two areas is to be found in the fact that, as they have different crystallographic orientations, their rectangular vibration directions are not parallel, each to each. The reason for the difference of polarisation colour is to be found also in the fact that the two areas have different crystallographic orientations; they behave just as if they were two separate sections of the same mineral. This particular kind of twinning, resulting in the production of two such areas only, is known as simple twinning.

Another type of twinning is shown by sections of plagioclase feldspars such as labradorite. In this case there are not merely two such areas, but any number from three upwards in one crystal. When one of these fragments is examined between crossed nicols, it shows alternating black and illuminated ribbons when one set is in extinction. It is worth noting that alternate ribbons extinguish simultaneously. This particular type of twinning, of which labradorite has been taken as an example, is known as lamellar twinning.

The fact that twinning is exhibited commonly by some minerals and never in others, renders this particular character very useful in mineral identification. Simple twinning serves to distinguish

orthoclase felspar from quartz, and from plagioclase felspar—which shows lamellar twinning.

It is obvious that this test of twinning, the different positions of extinction, can only be observed in the case of anisotropic sections. This particular kind of evidence is not available in the case of minerals crystallising in the cubic system, and it is therefore a matter of some difficulty to prove the presence of twinning in sections of minerals having such a high degree of symmetry. Some indication, however, is sometimes given by a re-entrant angle, though this is not a satisfactory proof of twinning.

Zoning.—The zoning of such crystals as those belonging to the Albite-Anorthite series has already been mentioned, and it has been pointed out that this particular character may be observed in ordinary light in consequence of the fact that the different shells have unequal refractive indices and possibly different degrees of alteration. But this zoning is often quite inconspicuous until the examination is made between crossed nicols. As each zone has its own position of extinction, the structure is still more conspicuous in this condition of the microscope, notwithstanding the fact that the same crystal may show lamellar twinning. Pyroxenes also may exhibit zoning between crossed nicols, even in cases where such a character was invisible in ordinary light.

Anomalous Double Refraction.—It has been seen that all sections of minerals crystallising in the cubic system, ought, when examined between

crossed nicols, to be isotropic; but many sections of the mineral leucite (usually considered to crystallise in this system) show grey polarisation colours in intersecting ribbons.

The "anomaly" is that a cubic mineral is anisotropic, and that anomaly is bound to exist as long as we regard the mineral as belonging to this system. The mineral is not really a cubic mineral, but its crystals have a symmetry which is so nearly that of the trapezohedron, that it is a matter of some difficulty to place it elsewhere. Some sections of garnet exhibit similar anomalies.

Aggregate Polarisation.—This phenomenon of aggregate polarisation is seen in those cases where a mineral has been decomposed with the production of an aggregate of smaller, anisotropic fragments of some other mineral or minerals. The alteration product is made up of small fragments with all possible orientations, and consequently there is never complete extinction of the pseudomorph—a fact which occasionally troubles students. If such a pseudomorph be looked upon as a crowd of small individuals, the difficulty disappears.

Determination of Polarisation Colour.—Up to the present we have used the wedge merely to demonstrate the effects of variation in thickness of an anisotropic section. We have now to consider some other uses to which it may be put.

It has been suggested that, by practice, the student may acquire the ability to recognise the particular order in which any mineral fragment is

polarising, merely by inspection; but the wedge may be used to place the matter beyond doubt. In order to demonstrate the method, a fairly large fragment of a doubly refracting mineral in thin section should be placed between crossed nicols, and the stage rotated until it occupies one of the positions where the polarisation colour is at its brightest; the mounted wedge should then be inserted into the slot of the eye-piece until it occupies a position immediately above the fragment to be examined. In such circumstances the polarisation effect is due partly to the mineral on the stage, and partly to the wedge in the slot. There are two possible cases:—

- (1) The effect of the two is as the sum of two quantities having the same sign—the polarisation colours of the two are higher in the scale than either alone.
- (2) The effect of the two is as the sum of two quantities having unlike signs—the polarisation colours of the two are lower in the scale than either alone.

It is the second case that we require; a rotation of the stage through 90° will convert case (1) into case (2). Having obtained the required opposition between section and wedge, it will be seen that at some position in the latter, a black band takes the place of one of the colour-bands in the scale; the particular band of colour replaced by this compensation band is the polarisation colour of the mineral plate. If the mineral plate whose polarisa-

tion colour we set out to determine is the only fragment in the slide, or if it is at the edge of a rock section, the fact may be demonstrated by placing the section in such a position that it is only covered by one side of the wedge. On this side, the compensation band will be obtained; on the other, the ordinary scale will be exhibited; and the compensation band will be continuous across the wedge with the colour which is that exhibited by the section alone.

The test may be applied to any anisotropic section, though in the case of a small fragment, or one of irregular thickness, a little care is necessary in making the determination.


Sign of Dimetric Minerals.—We have already seen that a section of quartz cut parallel to the principal crystallographic axis c , polarised in yellow of the first order, the highest polarisation colour possible in sections of quartz of the standard thickness. All minerals crystallising in the hexagonal and tetragonal systems (dimetric) are similar in this respect, that, although the highest possible polarisation colour for any mineral is a function of the birefringence, they all exhibit their highest polarisation colour when cut in such a direction that the crystallographic axis c lies in the plane of section. This means that, for such a section, the difference in velocity of the two rays penetrating it, is at its maximum; and as such sections show straight extinction, the two vibration directions are respectively parallel to and perpendicular to the length of the crystal. These

particular directions, being the vibration directions of the rays with the two extremes of velocity for the crystal, are known as ether axes; that of the fastest ray is referred to as the X ether axis, and that of the slowest ray as the Z ether axis.

There are two cases:—

Where c coincides with Z, the double refraction is positive.

Where c coincides with X, the double refraction is negative.

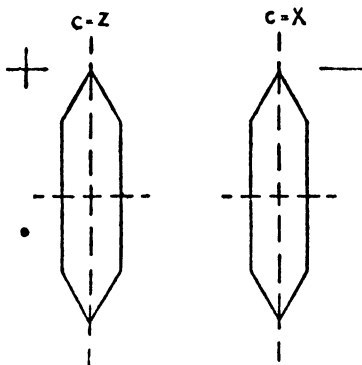

Dimetric crystals.
20. Positive. 21. Negative.

The wedge may be used to determine which of these two cases a particular vertical section of a dimetric mineral represents.

Before this can be done, however, it is necessary to learn something more about the wedge. We know that its two vibration directions are respectively parallel and perpendicular to the length, but we have not yet determined which of


these is "fast" and which "slow." In order to make this determination, we require a vertical section of a dimetric mineral whose sign is known. A small crystal of quartz meets our requirements admirably; it is well known that quartz is positive, therefore in a vertical section the length is the direction of slow vibration.

The section is placed on the stage between crossed nicols and brought to a position of maximum illumination, and the wedge inserted into the eye-piece slot. Opposition between crystal and wedge might be obtained with the crystal either N.E:S.W., or N.W:S.E. Suppose that opposition is obtained when the c axis is N.E:S.W., the length of the wedge being N.W:S.E. We know that c is slow, and that a is fast, and as opposition is taking place, the ray that came quickly through the quartz crystal comes slowly through the wedge, and vice versa. Therefore, the light vibrating parallel to the length of the wedge is penetrating slowly, the light vibrating perpendicular to the length is penetrating more rapidly.

We have thus determined the character of our wedge, and can speak of it as a slow wedge in terms of the kind of ray vibrating longitudinally. This fact having been determined, the knowledge thus obtained may be applied in order to determine the sign of any vertical section of a dimetric mineral

Apatite, for instance, is elongated along the axis c . A section parallel to c , tested with the wedge

between crossed nicols, is seen to give compensation with its length N.W : S.E.

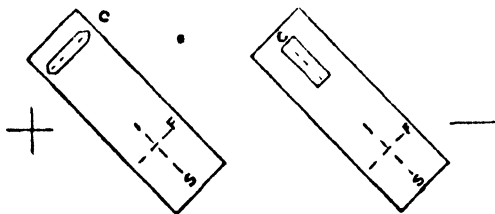

Positions of crystals giving compensation with the slow wedge.
22. Positive. 23. Negative.

As wedge and crystal must be in opposition, and as we know that the length of the wedge is "slow," then the length of the apatite must be "fast," $c = X$ and the sign is negative. The test may be applied to any vertical section of a dimetric mineral if we know the position of the crystallographic axis c in the section.

Optic Orientation of Trimetric Minerals.—It has been seen in the foregoing account of dimetric crystals—

- i. That in any anisotropic section there are two vibration directions which are perpendicular;
- ii. That the two rays penetrating such a section are propagated with different velocities;
- iii. That in a section containing the crystallographic axis c , the difference of velocity (indicated by the polarisation colour) is at a maximum;

- iv. That in such a section the vibration directions are respectively parallel to and perpendicular to the crystallographic axis c ;
- v. That the vibration directions giving extremes of velocity are known as ether axes;
- vi. That the sign of the double refraction may be determined by use of the wedge.

It will be seen that in a dimetric crystal there are many possible sections parallel to c , but all these have the same polarisation colours, and hence each contains two ether axes. We have to regard such a crystal as having, one ether axis coinciding with the crystallographic axis c , and an infinite number of other ether axes lying in a horizontal plane. In the case of the orthorhombic system, however, such is not the case. It is found that a section containing the a and c crystallographic axes (the brachypinacoid, 010) polarises in colours different from, and sometimes very much different from, those given by the section containing b and c (the macropinacoid 100). It is also found that the section perpendicular to c (the basal pinacoid, 001), is not isotropic.


Clearly there are some striking differences between the optical properties of a dimetric mineral and those of an orthorhombic mineral; the two ether axes X and Z , however, still coincide with two crystallographic axes, and it is our object to determine with which of the three crystallographic axes these ether axes coincide. The remaining crys-

tallographic axis, although it is merely the vibration direction of a ray which has some intermediate velocity (not necessarily a mean), is regarded as an ether axis, and is represented by the letter Y.

There are six possible cases within the system:—

1.	2.	3.	4.	5.	6.
$a=X$	$a=X$	$a=Y$	$a=Y$	$a=Z$	$a=Z$
$b=Y$	$b=Z$	$b=X$	$b=Z$	$b=X$	$b=Y$
$c=Z$	$c=Y$	$c=Z$	$c=X$	$c=Y$	$c=X$

The particular case represented by any orthorhombic crystal may be determined if we have three sections parallel to the three pinacoids. Barytes supplies us with a suitable case; fragments are fairly easy to prepare; it is important, however, that the sections should be as nearly as possible parallel to the three pinacoids.

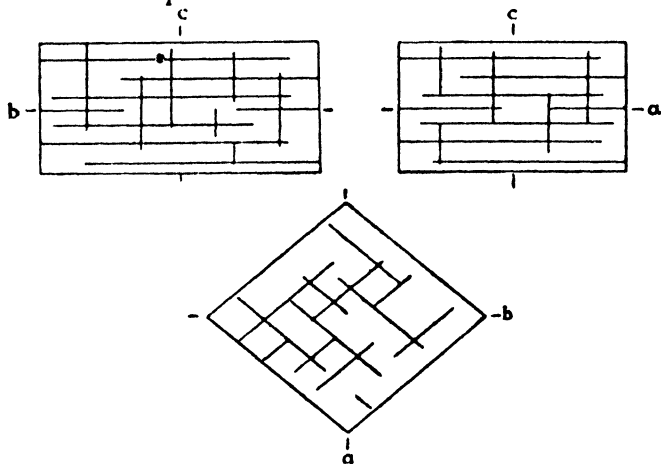

Pinacoidal sections of barytes.

24. Macropinacoid.

25. Brachypinacoid.

26. Basal pinacoid.

By determining the positions of extinction in the three sections, it is found that their vibration directions are, in Figures 24 and 25, parallel to the two cleavages (basal and prismatic, the former being the more perfect), and in Figure 26 that they bisect the cleavage angles; it is also found that they coincide with the crystallographic axes.

Each section should be taken in turn, rotated to a position of maximum illumination, and tested with the slow wedge, in two such positions if necessary, to find the position of compensation.

It is found that—

In section i., in position of compensation, *c* is parallel to the length of wedge. ∴ *c* is "faster" than *b*.

In section ii., in position of compensation, *c* is parallel to length of wedge. ∴ *c* is "faster" than *a*.

In section iii., in position of compensation, *b* is parallel to length of wedge. ∴ *b* is "faster" than *a*.

Hence it follows that—

$$\begin{array}{l} c > b > a \\ \& \quad a = Z \\ \quad \quad b = Y \\ \quad \quad c = X \end{array}$$

Careful testing with the wedge will demonstrate that, of the three sections, ii. shows the highest polarisation colours—a further proof that that is the section containing the ether axes with the maximum velocity difference, X and Z. Of the other two sections, iii. exhibits polarisation colours almost as

high as those of ii., very different from those of i.—a demonstration, if such be required, that the velocity of the ray vibrating in Y is not a mean between the two extremes.

The sign of double refraction cannot be obtained with certainty without the use of convergent polarised light.

The three ether axes, X, Y and Z, exist in all three trimetric systems, that is, the orthorhombic, monoclinic, and triclinic. In the last two systems, however, as the crystallographic axes are not, and as the ether axes are always, at right angles, the two kinds of axes cannot coincide. In the monoclinic system, the *b* crystallographic axis is coincident with one of the ether axes (X, Y, or Z), while the remaining two lie in the plane of symmetry. The situation of those two may be ascertained by measuring the extinction in a section parallel to the plane of symmetry (the clinopinacoid, 010). Neither of these ether axes necessarily coincides with either the crystallographic axis *a* or *c*.

The symmetry of the triclinic system being so low, it would be profitless to attempt a statement of optic orientation.

In the foregoing statement of optic orientation, we have considered only those sections containing two ether axes. Other sections have been ignored as introducing unnecessary difficulty at the present stage. It is quite evident that, as a section may take any direction whatever through a crystal, only a few of these will contain two ether axes; some will contain one only, while in the majority of cases the

section will not contain any. Nearly all these, however, are doubly refracting, and must therefore contain two vibration directions. A full statement of the case may be postponed for the present, but it may be pointed out that—

In sections containing two ether axes, vibration takes place parallel to them.

In sections containing one ether axis only, the vibration directions are respectively parallel to and perpendicular to this direction.

CHARACTERS OF MINERALS BETWEEN CROSSED NICOLS IN CONVERGENT LIGHT

IN considering the examination of transparent mineral plates, it has already been seen that there are three conditions of the microscope, all of which must be used in turn if we are to acquire a satisfactory amount of information in regard to the minerals in thin section. Even after this examination, it is not always possible to say with certainty that a particular mineral has been satisfactorily identified. The need for some further information is sometimes keenly felt. Convergent polarised light often supplies us with a means of acquiring the required information.

Methods of Obtaining an Interference Figure.—In fitting up the microscope, the instrument is first arranged as for use with parallel polarised light. The high power objective (usually $\frac{1}{4}$ in.) must be used. A system of converging lenses is fitted either beneath the stage or above the polariser, and a lens (the Bertrand lens) is placed in the tube of the microscope, either sliding in by means of a slot or fixed to the lower end of a draw tube. It is necessary to point out that some of these adjustments must be made with care, as the best results are not always obtained. Students should be quite sure that the nicols are in use and crossed, that the

mirror is adjusted to give the best possible illumination, that the Bertrand lens is in position, and that the converging lenses occupy their place between polariser and stage. ,


The effect may often be further improved by adjusting the objective and the converging system to the best advantage. The interference figure obtained in these circumstances with suitable sections of doubly refracting minerals is the best obtainable; but although the Bertrand lens is a necessity if determinations of sign are to be made, it is not absolutely necessary in order to obtain a view of the figure.

If all the adjustments here described, with the exception of the insertion of the Bertrand lens, have been effected, the figure may be focussed by means of an ordinary pocket lens held a little way (usually between 1 in. and 3 in.) above the eyepiece. The figure may also be observed without the Bertrand lens if the eyepiece also is removed.


It is sometimes useful to know the last two methods, because, although the figure obtained is not so large as that obtained with the Bertrand lens, it is perhaps rather more clear. In the following description, however, it will be assumed that the lens is in use.

Uniaxial and Biaxial Interference Figures.—The interference figure is seen when a suitable section of a doubly refracting mineral is examined in convergent light, and is one of two types. One of these is obtained when a basal section of a dimetric mineral is examined; the other when the section is


PLATE 1

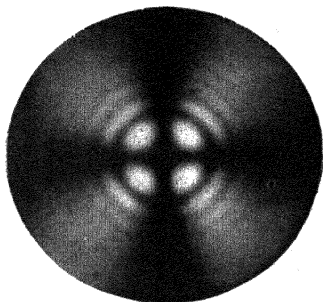


1.—Uniaxial interference figure.

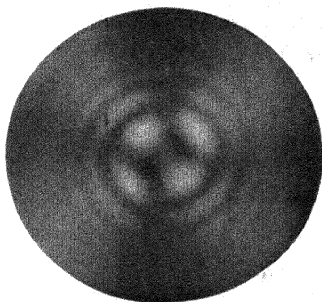


2.—Uniaxial interference figure.
Mica plate introduced.

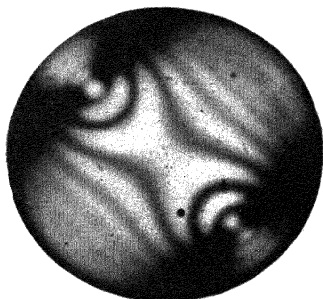


3.—Biaxial interference figure. Oblique position.

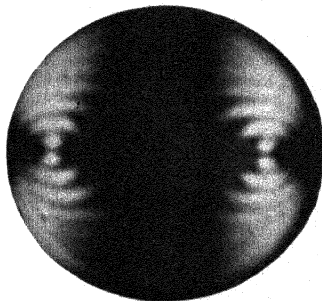

4.—Biaxial interference figure.
Straight position.

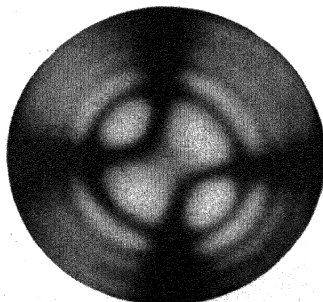

5.—Pseudo uniaxial interference figure.
Oblique position.

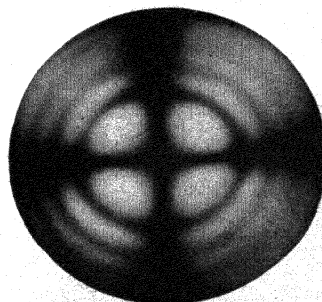


6.—Pseudo-uniaxial interference figure.
Straight position.

To face page 52.

cut from a trimetric mineral perpendicular to the X or Z ether axis.

It has been seen that, in general, when light is transmitted through a section of a doubly refracting mineral, it is split up into two rays having different velocities. There are sections of such minerals, however, perpendicular to which light is transmitted with one velocity only. These directions of propagation are known as optic axes. Dimetric crystals have one such direction, which coincides with the *c* crystallographic axis; they are hence referred to as *uniaxial*. Trimetric crystals have two such directions, and are consequently referred to as *biaxial*. It is always the case that these two optic axes lie in a plane which contains also the X

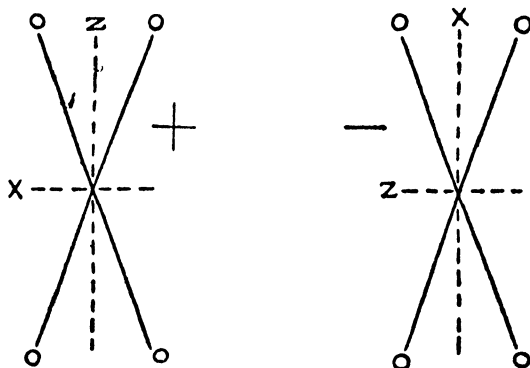

Optic axes and ether axes in biaxial crystals.
27. Positive. 28. Negative.

and Z ether axes, and that they are situated symmetrically with regard to them; that is, X and Z bisect the angles between the optic axes.

There are two cases—

- i. Z bisects the acute angle: double refraction positive.
- ii. X bisects the acute angle: double refraction negative.

In either case Y is perpendicular to the plane containing the optic axes (the optic axial plane) and is known as the optic normal.

The complete uniaxial interference figure is obtained when the section is perpendicular to the optic axis. It consists, as a rule, of a series of concentric circles which give Newton's scale of colours; the succession of colours when traced from the centre outwards is the same as that previously obtained with the wedge, commencing with the thin end. This system of rings is traversed by a black cross (N.S.: E.W.) the arms of which intersect at the centre. The figure remains unchanged as the stage is rotated.

The complete biaxial interference figure is obtained when the section is perpendicular to the acute bisectrix. It consists of a similar succession of colours, but in general in this case, they surround two centres. Travelling outwards from these centres it is seen that the two sets of rings fuse to form lemniscates, which ultimately give place to ellipses. The system of rings is traversed by black bands, but in this case there is a striking change as the stage is rotated. There is always a black band traversing each "eye"; the bands form a cross when the trace of the optic axial plane (the line joining the two eyes) is situated N.S. or E.W. When that

line is situated N.E : S.W. or N.W : S.E., the cross has split into hyperbolæ, one traversing each eye.

It is instructive to study the effects of variation in thickness in the case of minerals showing the two types of figure. This can be done conveniently in the case of minerals which have a good cleavage in the direction of section, such as the two micas, phlogopite and muscovite. Phlogopite is not an ideal case, but it is convenient; it shows a figure which is only approximately uniaxial, though the approximation is usually sufficiently close. A cleavage flake which is fairly thick should be selected and placed (unmounted) on the stage. If the section is thin enough to transmit the light, a uniaxial interference figure with several rings will be seen. Successive observations should be made on thinner and thinner flakes, and it will be seen that the number of rings in the field decreases until the final stage is reached with the innermost ring outside the field. The black cross, however, persists.

Muscovite supplies us with an almost perfect example of a biaxial interference figure. The process of examining progressively thinner flakes should be repeated, preferably with the figure in an oblique position. It is found that the rings expand around the eyes until even the innermost ring has given place to a lemniscate or an ellipse, or has even disappeared beyond the limits of the field. Here again the hyperbolæ persist throughout in the same position.

A similar change is observed if a series of minerals is examined in section (the sections should


be of a constant thickness) commencing with one having a high double refraction and proceeding to those with lower and lower double refraction. A similar expansion is observed analogous in the case of uniaxial minerals, to the thinning of biotite, and in the case of biaxial minerals to the thinning of muscovite.

An examination of a biaxial series also demonstrates the fact that in some cases the eyes come nearer together than in others; the distance between them being roughly a measure of the optic axial angle (the acute angle). This variation in the value of the optic axial angle would seem to suggest that there is no reason to suppose that there is any sharp distinction between uniaxial and biaxial minerals; the former may be regarded as a special case of the latter, where the optic axial angle has become so small as to be difficult to measure. Biotite or phlogopite is an example of a mineral which is certainly biaxial, because, as the stage is rotated, the black cross is seen to split up into hyperbolæ; but the optic axial angle is so small that the figure never shows two eyes even in thick sections.

Sign of Uniaxial Minerals.—It is not necessary that a mineral section which has been prepared specially to give an interference figure should have the same thickness as an ordinary rock section, in fact, it is only in the case of minerals with a very high double refraction that such a thin section gives the best results. As a rule, minerals in thin section, when examined in convergent polarised light, exhibit no coloured rings, but only a black

cross or hyperbolæ. Students must be prepared, then, to find that the figures to be examined will be very variable as to the number of coloured rings in the field. Even supposing the thickness to be constant, the number of rings in the field will, as has been seen, be dependent on the birefringence.

Fortunately, however, there is one method which can be used in order to determine the sign of any uniaxial mineral showing a complete figure. That method involves the use of a mica plate. This is a small rectangular flake of muscovite, usually cut in such a way that its slow vibration direction is parallel to the length of the rectangle. It should be mounted on a glass slip $\frac{1}{2}$ in. in width. The figure having been obtained, the mica plate should be inserted into the slot immediately above the objective. It has the effect of producing expansion in one pair of opposite quadrants, and contraction in the other pair. Where expansion takes place, two black spots appear near the centre of the field. There are two cases.

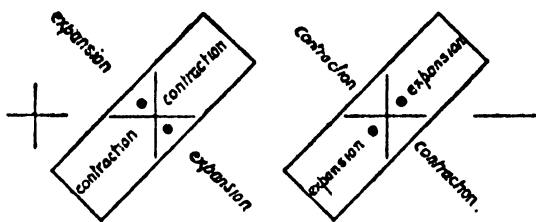

Sign of uniaxial minerals with mica plate.
29. Positive. 30. Negative.


When the double refraction is positive, a straight

line joining the two spots would lie perpendicular to the length of the plate, and when negative, parallel to the length.

The same method may be used in order to determine the sign of a biaxial mineral (such as biotite) with small optic axial angle.

Sign of Biaxial Minerals.—Having obtained the figure, the stage should be turned so that the trace of the optic axial plane occupies an oblique position (say N.E. : S.W.). The converging apparatus should be removed and the section examined in parallel polarised light by means of the low power objective. Testing with the wedge, the stage remaining in the same position, will give either compensation, or will raise the polarisation colours.

If compensation is obtained with the optic axial plane N.E. : S.W. using a slow wedge, then, as the length of the wedge is parallel to the optic normal, that direction must be the vibration direction of the faster ray, and the trace of the optic axial plane must be that of the slower; but the latter is the direction of the obtuse bisectrix, since the section is cut perpendicular to the acute bisectrix. Then Y (the optic normal) $>$ obtuse bisectrix, that is, the obtuse bisectrix $= Z$. The acute bisectrix must therefore be X , and the double refraction is negative.

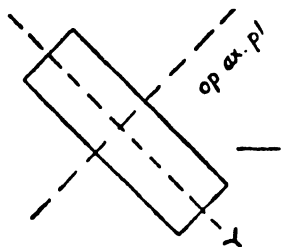

31. Compensation with a slow wedge for a negative biaxial crystal.

When the double refraction is positive, compensation is obtained when the slow wedge is inserted parallel to the trace of the optic axial plane.

It is possible to determine the sign of a mineral showing a biaxial figure without removing the converging apparatus. The wedge or mica plate should be inserted into the lower slot while the figure (with the optic axial plane N.W : S.E. or N.E : S.W.) is carefully observed. There will be one of two effects. Either the rings will become lemniscates or the lemniscates will become rings. In the first case opposition is taking place; in the second case, coincidence. The sign may be determined by a process of reasoning similar to that described for the preceding method.

Partial Interference Figures.—A complete uniaxial interference figure is given only by a section which is perpendicular to the vertical axis of a dimetric crystal (the optic axis); but as only a small minority of the fragments in a rock section are cut in that direction, it is desirable to have some method of determining the sign of double refraction of a mineral when the section has some other orientation.

The appearance of the partial interference figure depends largely on the obliquity of the section examined. In the case of a section which is almost perpendicular to the optic axis, the centre of the figure may be in the field of the microscope, but will not coincide with the centre of the field; rotation of the stage causes the centre of the figure to describe a circle concentric with that limiting the field. In


such a case the sign may be obtained by using a mica plate as with a complete figure.

A section departing still further from the position of that giving a complete figure may show only a portion of the system of rings on the margin of the field, or these may be entirely outside its limits, but in any case the arms of the black cross will sweep across the field as rotation takes place. The movement of these arms must be observed if the sign is to be determined.

Let it be supposed that the centre of the figure is somewhere outside the field away towards the N.E. On rotation of the stage in the clockwise direction, a horizontal arm sweeps across the field from N. to S., then a vertical arm from E. to W., then a horizontal arm from S. to N., and immediately before a complete rotation has taken place, a vertical arm from W. to E. The succession of events may be illustrated by holding two penholders at right angles to form a cross, resting a coin on the table, and, with the centre of the cross, describing a circle of greater diameter than that of the coin but concentric with it, so that the arms of the cross, while retaining their N.S. and E.W. directions, sweep in turn over the coin. It will be seen, then, that it is possible to locate the centre of the figure after a rotation of the stage has been completed.

The centre of the figure should be placed so that a straight line joining it with the centre of the field bisects one of the angles formed by the cross-wires, say to the N.E. Having got that in position, remove the converging apparatus and examine in

parallel polarised light between crossed nicols with the low power objective. Test with the slow wedge, on the assumption that the straight line joining the two centres (field and figure) is the vertical axis c .

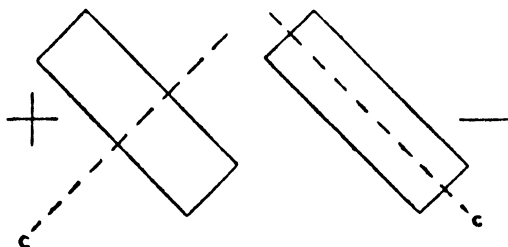

Compensation with a slow wedge and uniaxial crystals.

32. Positive.

33. Negative.

The wedge being inserted in a N.W.: S.E. direction, compensation in that position indicates positive double refraction, because $c=Z$. If compensation is obtained with the centre of the figure in the N.W.: S.E. line, the double refraction is negative, because $c=X$.

The sign of a mineral in section showing only a partial biaxial figure can only be obtained by means of more complex methods.

In applying the test of convergent polarised light to a doubly refracting mineral in thin section, the information desired is:—


- i. Is the mineral uniaxial or biaxial?
- ii. What is the sign of its double refraction?

One of the difficulties encountered is that the section is probably too thin to show anything of the coloured rings, but the "brushes" ought always to


be visible in a well-selected crystal. As a rule the fragment chosen should be the one giving the lowest polarisation colours. A black cross which remains unbroken on rotation, or vertical and horizontal brushes sweeping across the field, indicate a uniaxial mineral. A black cross breaking up into hyperbolæ, or a brush which at times occupies an oblique position in the field, indicates a biaxial mineral. It is worth noting that a section of a biaxial mineral, cut perpendicular to one of the optic axes, shows a system of concentric coloured circles traversed by only one black brush, the two ends of which, on rotation of the stage clockwise, follow the margins of the field in the anti-clockwise direction. The movements of that brush are of considerable importance in the examination of thin sections.

After the determination of the kind of figure, the sign of the double refraction should, be obtained. This may be done in all cases where a complete figure is exhibited, and in the case of a uniaxial mineral, even where only a partial figure is seen.

PLATE II

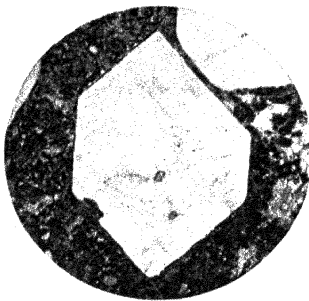

1.—Quartz. Ordinary Light. Vertical section. Showing form.

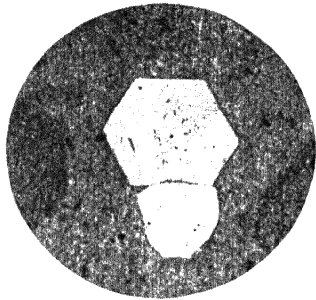


2.—Quartz. Ordinary Light. Basal section. Showing form.



3.—Quartz. Ordinary Light. Showing corrosion.



4.—Quartz. Ordinary Light. Showing corrosion.

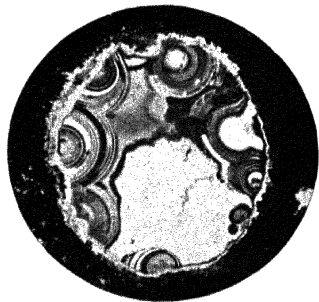

5.—Chalcedony in amygdale. Ordinary Light.

To face page 63.

DESCRIPTIONS OF COMMON ROCK-FORMING MINERALS

FORMS OF SILICA

Quartz.— SiO_2 . *Hexagonal. Birefringence positive.*

Colour.	None.
Form.	Commonly allotriomorphic, but occasionally showing hexagonal outlines.
Cleavage.	None.
Ref. Index.	1.55. A little higher than that of Canada balsam.
Alteration.	None.
Inclusions.	Minute liquid and gas inclusions sometimes seen with $\frac{1}{4}$ " objective.
Pol. Colours.	1st order. Basal sections isotropic.
Twinning.	Not seen.

It will be seen that the majority of the characters are negative; there is never any colour, cleavage, or alteration, twinning is not visible, there is rarely any form, and the refractive index is not such as to give any high relief. The absence of definite characters is the fact to be borne in mind by the student.

Tridymite SiO_2 . A rare variety of silica usually occurring as nests of scale-like crystals.

Chalcedony SiO_2 . A secondary form of silica found filling cavities. Usually in pale shades of brown, showing concentric arrangement. Between crossed nicols, shows a very characteristic aggregate polarisation, with black crosses due to radiating crystals.

Opal $\text{SiO}_2 \cdot n\text{H}_2\text{O}$. Also occurs filling interstices, and much like chalcedony in ordinary light, but distinguished by its isotropism between crossed nicols.

FELSPARS

Orthoclase.

Plagioclase.

Microcline.

Albite-Anorthite Series.

The common feldspars are silicates of aluminium with potassium, sodium, or calcium. Orthoclase feldspar crystallises in the monoclinic system; the plagioclase feldspars crystallise in the triclinic system. All possess cleavages parallel to 001 (basal pinacoid), and 010 (clinopinacoid or brachypinacoid).

Orthoclase.— KAlSi_3O_8 . *Monoclinic.*

<i>Twinning.</i>	<i>Manebach.</i>	<i>Twin plane</i>	001 (<i>basal pinacoid</i>).
	<i>Baveno.</i>	" "	021 (<i>clinodome</i>).
	<i>Carlsbad.</i>	" "	100 (<i>orthopinacoid</i>).
	"	<i>Comp.</i>	" 010 (<i>clinopinacoid</i>).

Birefringence negative.

Colour. None.

Form. Sometimes idiomorphic, when rectangular or hexagonal sections are shown. Often allotriomorphic.

Cleavage. In favourable sections two rectangular cleavages are seen, but some sections show one cleavage only; other sections show no cleavage.

Ref. Index. 1.52. Slightly less than, but very near to, that of Canada balsam.


Alteration. Often turbid in consequence of alteration, but may be quite or partially transparent.

Pol. Colours. 1st order; greys, white, and yellow.

Extinction. Commonly oblique, but sometimes straight.

Twinning. Absent or simple.

PLATE III

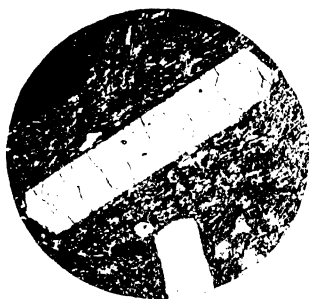

1.—Orthoclase. Ordinary Light.
Showing form.



2.—Orthoclase. Ordinary Light.
Showing form.



3.—Orthoclase. Crossed nicols.
Showing cleavages.



4.—Orthoclase. Ord. L. Showing altera-
tion and intergrowth with quartz.




5.—Orthoclase. Crossed nicols. Showing
Carlsbad twinning.




6.—Orthoclase. Crossed nicols. Showing
Baveno twinning.

To face page 61.


PLATE IV

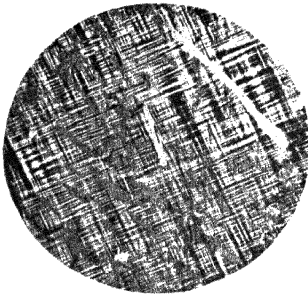


1.—Microcline. Crossed nicols. Showing cross-hatching.

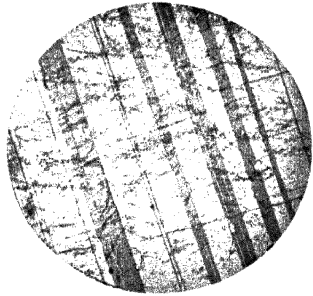


2.—Plagioclase, ab.-an. ser. Crossed nicols. Showing lamellar twinning.

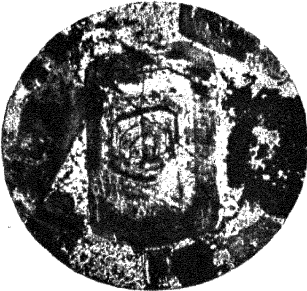

3.—Plagioclase, ab.-an. ser. Ordinary Light. Showing zoning by alteration.

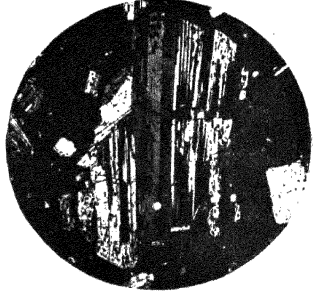


4.—Plagioclase, ab.-an. ser. Crossed nicols. Showing lamellar twinning.

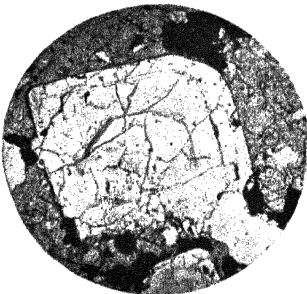

5.—Plagioclase, ab.-an. ser. Ord. L. Showing zoning by inclusions.

To face page 65.

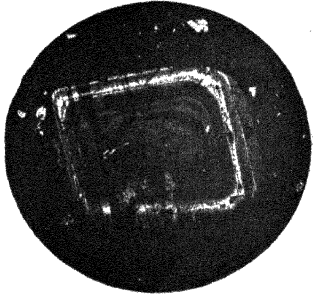

6.—The same. Crossed nicols. Showing zoning and lamellar twinning.

Microcline.— KAlSi_3O_8 . *Triclinic. Birefringence negative.*

This mineral cannot be distinguished in ordinary light from orthoclase, but between crossed nicols it shows lamellar twinning in two directions, the two sets often intersecting at angles approaching 90° . The pattern produced is that known as cross-hatching.

Albite-Anorthite Series.—*Triclinic. Twin plane 010 (brachypinacoid).*

The minerals in this series form an isomorphous group, with albite and anorthite at the two extremes. The members of the series cannot be said to have any well-defined individuality, as the several mineral names do not imply any definite composition.

The composition range of the several members of the series is illustrated below, where the albite molecule (Ab) $\text{NaAlSi}_3\text{O}_8$, and the anorthite molecule (An) $\text{CaAl}_2\text{Si}_2\text{O}_8$, are combined in the various proportions.


	Ab.	An.	Ref. Index.
Albite	10	0	1·53
	9	1	
Oligoclase	8	2	1·54
	7	3	
Andesine	6	4	1·55
	5	5	
Labradorite	4	6	1·56
	3	7	
Bytownite	2	8	1·57
	1	9	
Anorthite	0	10	1·58

An inspection of the above table will show that labradorite, for example, may have as little as 25% Ab. or as much as 50% Ab.

The members of this Ab. An. series are distinguished from orthoclase by the lamellar twinning seen when examined between crossed nicols. It is desirable also to distinguish between the different members of the series, but the distinction is a matter of some difficulty. The most commonly accepted method is based on the extinction angle, as measured from the twin striations, the extinction angle being greatest at the Anorthite end of the series. The beginner, however, is recommended to remain satisfied with having recognised the mineral as plagioclase felspar (Ab. An. series). He can later make himself familiar with the method of extinction or make use of the variation in refractive index. It will be seen that the refractive index of oligoclase is equal to that of Canada balsam. If the refractive index is less than 1.54 the felspar may be called albite; if greater than 1.54, the degree of relief may be used as a means of getting the approximate place of the felspar in the series.

Resemblances.—The distinction between orthoclase, microcline, and the Ab. An. series, is easily effected by a consideration of the kind of twinning. Quartz, however, is not always easy to distinguish from orthoclase. In difficult cases a careful search should be made for cleavage, alteration, and twinning. The presence of any one of these would eliminate quartz. The distinction may also be effected in convergent light; quartz is uniaxial, and orthoclase biaxial.


PLATE V

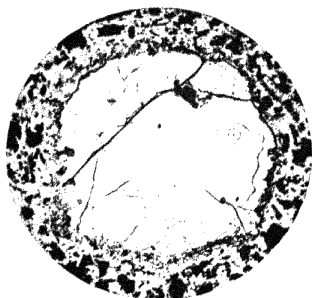


1.—Leucite. Ordinary Light. Showing form.




2.—The same. Crossed nicols. Showing cross-hatching.

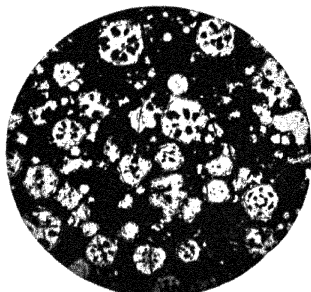


3.—Leucite. Ordinary Light. Showing inclusions.

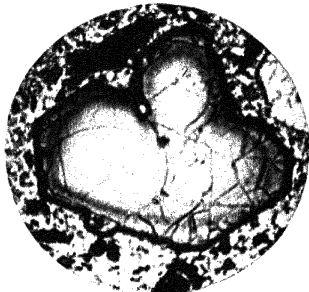

4.—Nosean. Ordinary Light. Showing zoning.

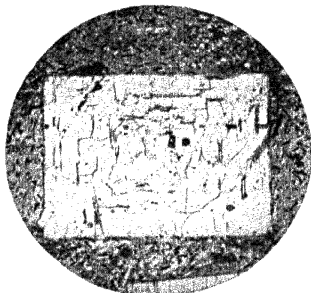

5.—Nepheline. Ordinary Light. Showing form of vertical section.

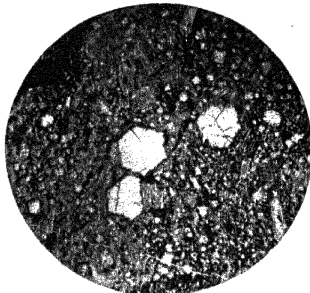

6.—Nepheline. Ordinary Light. Showing form of basal sections.

To face page 67.

FELSPATHOIDS

Leucite.— $\text{KAl}(\text{SiO}_3)_2$. Cubic (?).

- Colour.** None when fresh.
Form. Sometimes octagonal, but usually rounded.
Cleavage. None.
Ref. Index. 1.51. Sufficiently different from that of Canada balsam to have a fairly good relief.
Alteration. May be quite fresh, but occasionally turbid and pale brown through alteration.
Inclusions. Sometimes contains included fragments arranged radially or concentrically.
Pol. Colours. May be quite isotropic, but often polarises in dark greys and shows intersecting twin lamellæ resembling those of microcline.

Resemblances.—May be confused with microcline, but it has a better relief in ordinary light, and a lower double refraction. Form is also useful.

Nosean.—*Silicate and sulphate of sodium and aluminium.* Cubic. Cleavage 110 (Rhomb-dodecahedral).

- Colour.** None or brown.
Form. Very variable. Often irregular, but sometimes showing hexagonal outlines.
Cleavage. Occasionally, but not often, seen.
Ref. Index. 1.46. Has a good relief in consequence of its very low refractive index, but the common thick dark border is due to inclusions—not to refractive index.
Alteration. To aggregates of zeolites—producing turbidity.
Inclusions. Sometimes packed with dark brown inclusions, but often these are localised at the margins, giving a striking zoned appearance.
Pol. Colours. Isotropic when fresh, but showing aggregate polarisation when decomposed.

Hauyne.—*Composition similar to that of nosean but with calcium silicate and sulphate in addition.* Cubic.

Often very similar to Nosean in appearance, but more commonly has inclusions localised at the centre, and sometimes shows blue or green colour.

Nepheline.—*Composition* $\left\{ \begin{array}{l} m \text{ NaAlSiO}_4 \\ n \text{ KAl(SiO}_3)_2 \end{array} \right\}$ *Hexagonal. Cleavages prismatic and basal. Birefringence negative.*

Colour.	None when fresh, but brownish when altered.
Form.	Rectangular or hexagonal.
Cleavage.	Rarely seen.
Ref. Index.	1.54. Very nearly equal to that of Canada balsam.
Alteration.	May be fresh, but often found decomposed to radiating aggregates of small acicular crystals.
Pol. Colours.	Basal sections isotropic; other sections polarising in greys (1st order).
Extinction.	Straight.
Twinning.	None.


Resemblances.—May be distinguished from feldspars by its more common rectangular and hexagonal sections, its different type of alteration, its lower polarisation colours and isotropic sections, its straight extinction and the absence of twinning; also by examination in convergent light.

The allotriomorphic variety found in coarse-grained igneous rocks is known as *Elæolite*.

Sodalite.—*Silicate and chloride of sodium and aluminium. Cubic. Cleavage 110 (Rhomb-dodecahedral).*

Colour.	None.
Form.	Allotriomorphic.
Cleavage.	Not always seen, but may be found in more than one direction.
Ref. Index.	1.48. Approximating to, but less than, that of Canada balsam.
Alteration.	Occasionally turbid through decomposition, but usually clear.
Polarisation.	Isotropic.


PLATE VI

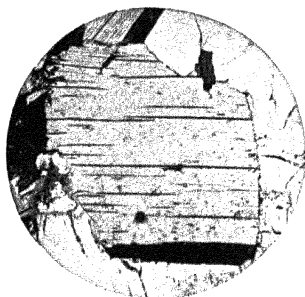


1.—Muscovite. Ord. L. Showing cleavage.




2.—Muscovite. Ord. L. Showing cleavage and intergrowth with biotite.

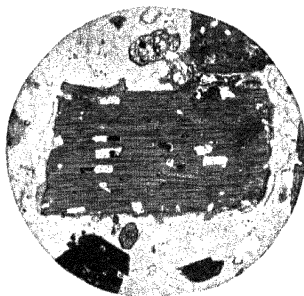

3.—Biotite. Ord. L. Showing form, cleavage and inclusions.

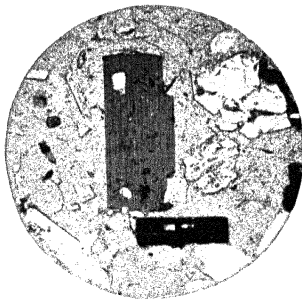

4.—Biotite. Pol. L. Showing pleochroism.

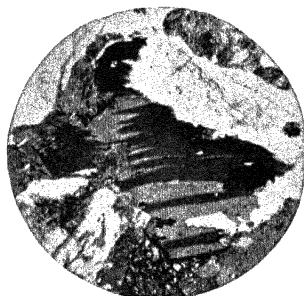

5.—Biotite. Ord. L. Showing partial alteration to Chlorite.



6.—Chlorite. Ord. L. Showing vermicular habit and occurrence in amygdale.

MICAS

Characterised by their perfect basal cleavage and pseudo-hexagonal symmetry. Muscovite and Biotite are selected as examples of the group.

Muscovite.—*Comp.* $H_2KA l_3(SiO_4)_3$. *Monoclinic.*
Cleavage 001. (*Basal*). *Birefringence negative.*

Colour. None.

Form. Allotriomorphic.

Cleavage. One direction of cleavage nearly always seen.

Ref. Index. 1.58. No very striking relief, but still evidently much different from Canada balsam.

Alteration. None.

Pleochroism. Since the mineral is colourless in thin section, there cannot be any pleochroism; but occasionally it is found that around minute inclusions the mineral is a pale brown, and these haloes are pleochroic.

Pol. Colours. Bright pinks and greens.

Extinction. Straight.

Twinning. None.

Resemblances.—Muscovite cannot be mistaken for any of the minerals previously described. Even ignoring other tests, the polarisation colours are sufficiently distinctive.

Biotite. — *Comp.* $(K,H)_2(Mg,Fe)_2(Al,Fe)_2(SiO_4)_3$.
Monoclinic. *Cleavage* 001 (*Basal*). *Birefringence negative.*

It has many characters in common with Muscovite, but differs in the following respects:—

Colour. Brown.

Alteration. Decomposes to a green product, Chlorite, which is sometimes pseudomorphous; but all stages in the alteration are to be seen.

Pleochroism. Strong: from pale brown to dark brown.

Pol. Colours. Commonly obscured by the absorption colour.

Resemblances.—The brown colour and pleochroism are sufficient to distinguish the mineral from any one of the preceding minerals.

OTHER MICACEOUS MINERALS

Chlorites.—*Basic silicates of iron, aluminium, and magnesium. Monoclinic. Cleavage 001 (Basal).*

Colour.	Green.
Form.	Usually as pseudomorphs after unstable ferromagnesian silicates which contained alumina; e.g., biotite. Sometimes in parallel or radiating aggregates; sometimes vermicular.
Cleavage.	In one direction only.
Ref. Index.	About 1.58.
Pleochroism.	Slight: pale green to darker green.
Pol. Colours.	1st order greys: often masked by absorption. Sometimes shows ultra-blues or ultra-browns.
Extinction.	Straight.

Chloritoids.—*Composition approximating to that of Chlorite. Monoclinic or Triclinic.*

Colour.	Indigo blue or greenish black.
Form.	Variable, but sometimes rectangular.
Cleavage.	One direction good: others obscure.
Ref. Index.	Variable, but always high.
Inclusions.	Abundant.
Pleochroism.	Usually from indigo blue to greenish yellow.
Pol. Colours.	1st order greys.
Extinction.	Usually oblique.
Twinning.	Common.

Resemblances.—Differ from Chlorites in having a high refractive index, often a curious indigo blue colour, and many inclusions. Pleochroism also is distinctive, usually from indigo blue to greenish yellow.


Talc.— $\text{H}_2\text{Mg}_3(\text{SiO}_3)_4$. *Monoclinic (?)*.

Very much like Muscovite, but has a slightly lower refractive index, 1.56, and a little higher birefringence.


PYROXENES

The pyroxenes fall into a fairly well-defined group of minerals with a tendency to form crystals

PLATE VII

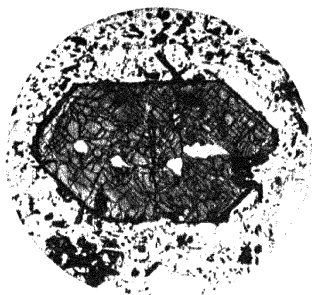


1.—Aegirine, transverse section. Ordinary Light. Showing form and cleavages.

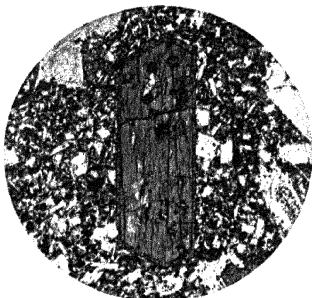


2.—Augite, vertical section. Ordinary Light. Showing form.



3.—Augite, vertical section. Ordinary Light. Showing form and zoning.

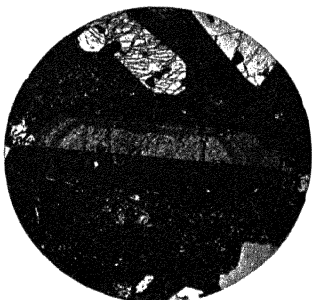

4.—Augite, trans. sect. Crossed nicols. Showing form, zoning and simple twinning.

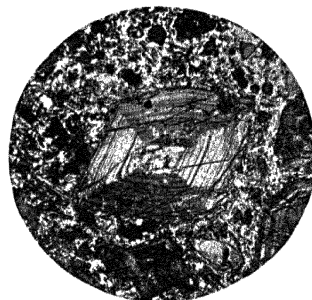

5.—Augite. Crossed nicols. Showing zoning and "hour-glass" structure.



6.—Enstatite, transverse section. Ordinary Light. Showing form and cleavages.

with eight vertical faces, four of these being prism faces meeting at angles which are approximately 90° . All of them have prismatic cleavages which intersect at the prism angle. Composition, variable.

Monoclinic Pyroxenes

Augite.—*Silicate of calcium, iron, magnesium and aluminium. Monoclinic. Cleavage 110 (Prismatic). Twin plane 100 (Orthopinacoid). Birefringence positive.*

Colour.	Brown.
Form.	Transverse sections sometimes octagonal.
Cleavage.	In transverse sections, two at right angles. Other sections may show one only, or even none.
Ref. Index.	1.72. The mineral has a good relief and the cleavages and other cracks are conspicuous.
Alteration.	Sometimes to green chlorite, occasionally to hornblende.
Pleochroism.	Typically none: but some varieties show feeble pleochroism.
Pol. Colours.	Bright colours, commonly 2nd and 3rd order.
Extinction.	Commonly oblique, but sometimes straight.
Twinning.	Simple and lamellar.

Diopside.—*Silicate of calcium, iron and magnesium.*

Differs from Augite only as regards colour—it is green instead of brown.

Aegirine.—*Silicate of sodium and iron.*

Sections of this pyroxene are also green, but, as the mineral is strongly pleochroic, the different fragments seen in ordinary light exhibit different shades of green, ranging from blue green to yellow green—two extremes which are seen when the mineral is examined with the aid of the polariser.

Diallage.—*Similar to augite in composition.*

Distinguished by the possession of an extra

cleavage (pinacoidal) and by a fibrous, woody appearance when seen in ordinary transmitted light—due to the parallel arrangement of platy inclusions (schillerization).

Orthorhombic Pyroxenes


These form an isomorphous series, with Enstatite, MgSiO_3 , birefringence positive, and Hypersthene (Mg,Fe) SiO_3 , birefringence negative, at the two extremes. It is usual to recognise an intermediate member of the series in Bronzite.

They differ from Augite in having a lower refractive index (enstatite 1.67 and hypersthene 1.70), and also in their polarisation. 1st order colours are common, but hypersthene occasionally shows 2nd order colours. There is a tendency for the octagonal outline of transverse sections to become regular. Hypersthene also shows a peculiar pleochroism — blue-green to reddish brown, and sometimes schillerization. Straight extinction is much more common than oblique extinction, the reverse of what is the case with the monoclinic pyroxenes.


AMPHIBOLES

As in the case of the pyroxenes, the amphiboles form an isomorphous series. In crystals of this group, however, only six vertical faces are usually found; the four prism faces meeting at angles of about 125° and 55° . The prismatic cleavages, of course, intersect at these angles. The amphiboles resemble the pyroxenes in many respects, not the least important being that of composition; and, in

PLATE VIII

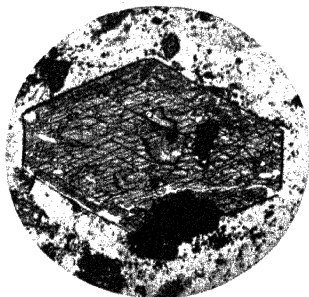


1.—Hornblende, transverse section. Ord. L.
Showing form and cleavages.

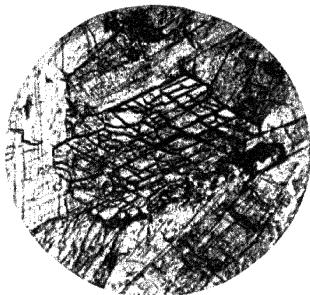


2.—Actinolite, transverse section. Ord. L.
Showing form and cleavages.



3.—Hornblende, vertical section. Ord. L.
Showing form and cleavage.

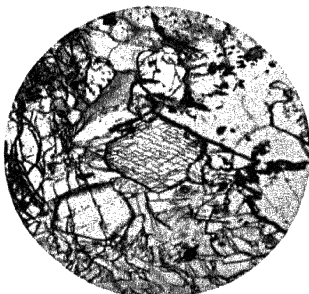

4.—Glaucophane, trans. sect. Ord. L.
Showing form and cleavages.

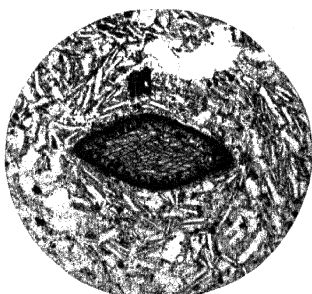

5.—Hornblende, trans. sect. Ord. L.
Showing alteration rim.

general, for any pyroxene, an amphibole can be found having the same empirical formula.

As there are many points of resemblance between the two groups, it is desirable to point out the characters by which we are enabled to distinguish between them; the most important are:—(1) the form, and (2) the cleavage angle.

Hornblende.—*Silicate of calcium, iron, magnesium, and aluminium. Monoclinic. Cleavage 110 (prismatic). Twin plane 100 (orthopinacoid). Birefringence negative.*

Colour.	Green or brown.
Form.	Transverse sections often show six-sided outline.
Cleavage.	Transverse sections show two intersecting at 125° .
Ref. Index.	1.65. Fairly good relief.
Alteration.	Not common, but occasionally pseudomorphed in magnetite or chlorite.
Pleochroism.	Strong: light to dark green, or light to dark brown.
Pol. Colours.	2nd order, but commonly masked by absorption colour.
Extinction.	Commonly slightly oblique; occasionally straight.
Twinning.	Occasional simple or lamellar twinning.

Actinolite.—*Silicate of calcium, iron and magnesium. Monoclinic.*

Distinguished from green hornblende by its paler green colour.

Tremolite.—*Silicate of calcium and magnesium. Monoclinic.*

Characterised by its entire freedom from colour.

Glaucophane.—*Silicate of sodium, aluminium, and magnesium. Monoclinic.*

Distinguished by its beautiful reddish or bluish-violet colour. In addition to either of these colours a pale greenish yellow is sometimes seen when the test for pleochroism is applied.

Anthophyllite.— $(\text{Mg}, \text{Fe})\text{SiO}_3$. *Orthorhombic.*

A rather rare mineral which is distinguished from Hornblende by the fact that nearly all sections show straight extinction.

Resemblances of Amphiboles.—It is not always easy to distinguish between pyroxene and amphibole; but in cases of difficulty a careful search should be made for a characteristic outline or cleavage angle.

The only other preceding minerals at all likely to be confused with amphiboles are the Micas. Sections of biotite sometimes resemble hornblende fairly closely; and the difficulty is not minimised by the fact that the two minerals are often found in the same slide. The following will be found useful in making the distinction between the two minerals.

Colour.—This test may be applied with advantage even though both minerals are pleochroic; the different fragments of the two minerals are not similarly coloured.

Form.—Transverse sections of hornblende are easily recognisable when well-formed; it is the elongated longitudinal sections which cause trouble.

Cleavage.—Transverse sections of hornblende again are easily distinguished from biotite by the possession of two cleavages meeting at 125° .

Ref. Index.—This test is useful, as biotite has the lower refractive index.

Pleochroism.—A useful test is found in the fact that biotite when showing the dark extreme of pleochroism, often exhibits a slightly mottled surface never seen in the case of hornblende.

Extinction.—Biotite always shows straight extinction; hornblende sometimes shows oblique extinction. Biotite, again, shows the mottled surface when in extinction.

Tremolite is sometimes difficult to distinguish from muscovite, but careful search should be made for the two cleavages and for oblique extinction, either of which will rule out muscovite.

OLIVINES

Olivine. — $(\text{Mg}, \text{Fe})_2\text{SiO}_4$. *Orthorhombic. Birefringence positive.*

Colour.	None when fresh, but often associated with green serpentine.
Form.	When idiomorphic, shows hexagons which are irregular, but symmetrical about two of the diameters.
Cleavage.	Rarely seen, but irregular cracks frequent.
Ref. Index.	1.68. Good relief.
Alteration.	Commonly altered to green serpentine and black iron oxide. Alteration commences along the cracks and margins; these gradually grow wider at the expense of the olivine until the final stage, a pseudomorph in serpentine, is reached.
Pol. Colours.	2nd and 3rd orders. Bright colours.
Twinning.	None.

Resemblances.—There is sometimes a difficulty in distinguishing between olivine and augite. Olivine may be distinguished by absence of colour, form (if idiomorphic), absence of cleavage, characteristic alteration.

Olivine is the intermediate member of an isomorphous group of minerals including :—

Forsterite—rich in magnesium. Mg_2SiO_4 .

Olivine—

Fayalite—rich in iron. Fe_2SiO_4 .

Forsterite is much like olivine, but decomposes to form a colourless serpentine.

Fayalite has a pale greenish colour and a slight pleochroism. Birefringence negative.

Serpentine.—*Hydrated silicate of magnesium and iron.*

It is easily recognised when associated with olivine or when a pseudomorph after well-formed crystals, but when it occurs as the bulk of large rock-masses, the sections present some difficulty to the beginner.


Colour. Usually pale green or yellow in colour, or may be almost colourless.

Pleochroism. Occasionally distinct, but usually very feeble

Pol. Colours. 1st order greys.

Resemblances.—Serpentine resembles Chalcedony to some extent, but has none of the radiating and concentric structure of that mineral. Chlorite may usually be distinguished by its cleavage or vermicular habit.

PLATE IX

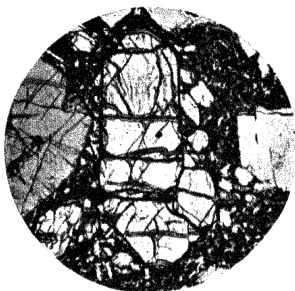

1.—Olivine. Ordinary Light. Showing form and alteration.




2.—Olivine. Ordinary Light. Showing form and more advanced alteration.




3.—Serpentine. Ordinary Light. Pseudomorph after Olivine.



4.—Sphene. Ordinary Light. Showing form and high refractive index.

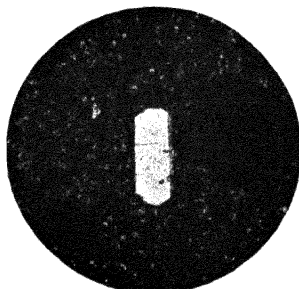

5.—Apatite, vertical section. Ord. L. Showing form and cleavage.

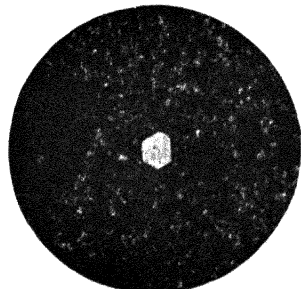

6.—Apatite, basal section. Ordinary Light. Showing form.

To face page 76.

Apatite.— $\text{Ca}(\text{F}, \text{Cl})\text{Ca}_4(\text{PO}_4)_3$. *Hexagonal. Cleavage Basal. Birefringence negative.*

Colour.	None.
Form.	Transverse sections regular hexagons, vertical sections lath-shaped.
Cleavage.	Occasionally seen in vertical sections.
Ref. Index.	1.64. Good relief.
Alteration.	None.
Pol. Colours.	1st order grey; basal sections isotropic.
Extinction.	Straight.
Twinning.	None.

Resemblances.—This mineral ought not to be mistaken for any of the foregoing; it is distinguished from nepheline by its refraction, and from olivine by its polarisation and form.

Spheue (Titanite).—*Silicate and titanate of calcium. Monoclinic. Twin plane 100 (orthopinacoid). Birefringence positive.*

Colour.	Yellowish-brown or greyish-brown.
Form.	Often lozenge-shaped—like an elongated ace of diamonds—but the form is not always well-developed.
Cleavage.	Rarely seen.
Ref. Index.	1.89. High relief and pitted surface.
Pleochroism.	Sometimes distinct, but usually feeble.
Pol. Colours.	High order greys. These, however, are so pale that the polarisation colour does not appear to be appreciably different from the absorption colour.
Twinning.	Not common, but sometimes simple twins are seen.

Resemblances.—When idiomorphic, no difficulty whatever is experienced, but other examples may exhibit some resemblance to augite. The differences of refraction and polarisation, however, should always serve to distinguish between them,

even when the obvious peculiarities of form are absent.

Garnets.— $R_3R''(SiO_4)_3$. *The Garnets form an isomorphous group of minerals which are here taken together for convenience. Each is a silicate of at least two metals, one divalent and one trivalent, the positive elements represented in the group being calcium, magnesium, iron, manganese, aluminium and chromium. Cubic.*


Colour.	Pink, colourless, or brown.
Form.	Commonly rounded, but occasionally polygonal.
Cleavage.	Rarely seen, but irregular cracks are common.
Ref. Index.	1.76 to 1.83. Good relief.
Alteration.	None.
Inclusions.	Sometimes present in abundance.
Pleochroism.	None.
Pol. Colours.	Isotropic in nearly all cases.

Resemblances.—The isotropism will usually serve to distinguish garnet from any of the other highly refracting minerals in the preceding list.


Tourmaline. — *Boro-silicate of aluminium, with magnesium, iron and alkali metals. Hexagonal. Birefringence negative.*

Colour.	Commonly brown, but may be yellow, green, blue, or colourless. Often the colour is irregular in its distribution, different portions of a single fragment being differently coloured.
Form.	Transverse sections triangular or hexagonal. Vertical sections elongated, and even sometimes acicular. Often in irregular masses.
Cleavage.	None; but an imperfect basal fracture is sometimes seen in vertical sections.
Ref. Index	1.63. Fairly good relief.


PLATE X

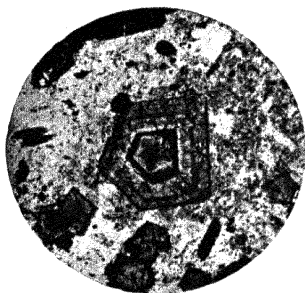


1.—Garnet (Melanite). Ordinary Light. Showing form and zoning

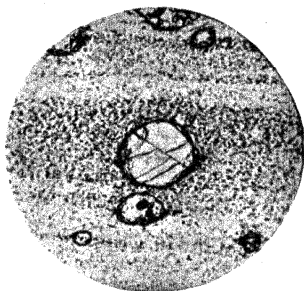


2.—Garnet. Ord. L. Showing rounded form and high refractive index.

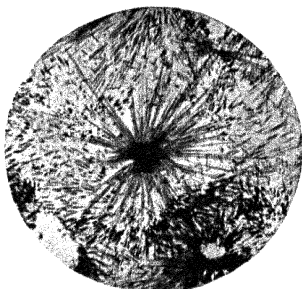

3.—Tourmaline. Ord. L. Showing acicular and radiating habit.

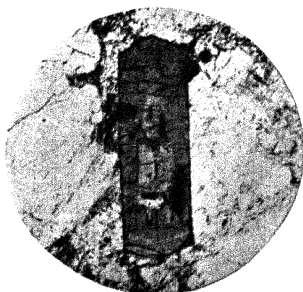

4.—Tourmaline, vert. section. Ordinary Light. Showing form.

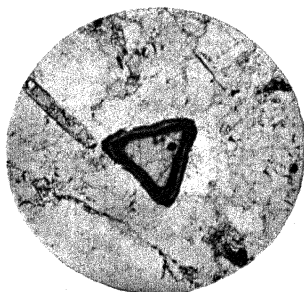

5.—Tourmaline, basal section. Ord. L. Showing form and zoning.

To face page 78.

- Alteration.** None.
- Pleochroism.** Vertical sections with colour are strongly pleochroic; oblique sections feebly pleochroic, and basal sections non-pleochroic. The possibility of the absence of pleochroism should be borne in mind when examining fragments whose orientation is not known. In well-formed vertical sections, it will be observed that when the length is arranged in a N.S. direction the maximum absorption is taking place.
- Pol. Colours.** 2nd order colours common; but when the absorption is strong, polarisation colours are obscured. Basal sections isotropic.
- Extinction.** Straight.
- Twinning.** None.

Resemblances.—When the crystals are small, vertical sections of brown tourmaline resemble biotite or hornblende; but either of these may be distinguished from tourmaline by an application of the pleochroism test. The dark extreme of tourmaline is seen when the length is N.S. The dark extreme of biotite or hornblende is seen when the length is E.W.

Topaz. — $(\text{AlF})_2\text{SiO}_4$. *Orthorhombic. Cleavage parallel to 001 (basal). Birefringence positive.*

- Colour.** None.
- Form.** Usually rounded or irregular.
- Cleavage.** Rarely seen.
- Ref. Index.** 1.62. Good relief.
- Alteration.** None.
- Pol. Colours.** 1st order.
- Twinning.** None.

Resemblances.—The characters of topaz are much like those of quartz, and some difficulty is experienced in making the distinction. An exhibi-

tion of cleavage settles the point at once in favour of topaz, but it is not often available; the most useful distinction is that of refractive index—a distinction which students should lose no time in endeavouring to appreciate. The minerals may also be distinguished in convergent light.

THE SILICATES OF ALUMINA

There are three important minerals coming in this group:—

Andalusite. *Orthorhombic.*

Sillimanite. *Orthorhombic.*

Kyanite. *Triclinic.*

Andalusite.— $\text{Al}(\text{AlO})\text{SiO}_4$. *Cleavage* 110 (*Prismatic*). *Birefringence negative.*

Colour. Pale pink to colourless.

Form. Usually in rounded grains, but occasionally showing rhomb-shaped or elongate sections.

Cleavage. Rarely seen.

Ref. Index. 1.64. Good relief.

Pleochroism. Pale pink or colourless.

Pol. Colours. 1st order greys.

Twinning. None.

Resemblances.—The mineral resembles apatite somewhat closely, but the pale pink colour and the form, together with the absence of isotropic sections, are useful means of distinction. Also distinguished by biaxial figure in convergent polarised light.


Chiastolite is a variety with characteristic inclusions.

Sillimanite.— Al_2SiO_5 . *Cleavage* 010 (*Brachypinacoid*). *Birefringence positive.*


Colour. None.

Form. Commonly acicular, but sometimes irregular.

PLATE XI

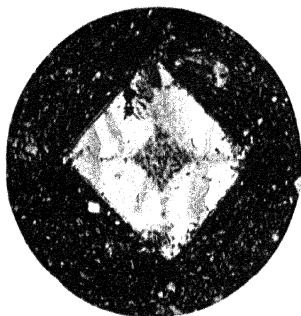

1.—Chialtolite, basal section. Ord. L.
Showing form and inclusions.

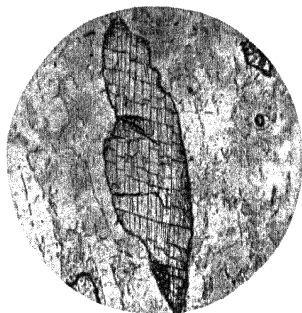

2.—Kyanite. Ord. L. Showing cleavages
and high refractive index.



3.—Epidote. Ordinary Light. Showing
form and cleavage.



4.—Epidote. Ordinary Light. Showing
occurrence in amygdale.

Cleavage. Rarely seen.
Ref. Index. 1.67. Good relief.
Pol. Colours. 1st and 2nd order.

Resemblances.—Distinguished from apatite by its higher polarisation colours, and by biaxial figure in convergent light.

Kyanite.— $(\text{AlO})_2\text{SiO}_3$. *Cleavage* 100 (*Macropinacoidal*) and 010 (*Brachypinacoidal*). *Birefringence negative*.

Colour. Pale blue or colourless.
Form. Irregular.
Cleavage. Usually well seen in one direction. Occasionally two are seen.
Ref. Index. 1.72. Good relief.
Pleochroism. Feeble—pale blue to colourless. May be absent.
Pol. Colours. 1st and 2nd order.

Resemblances. — The colour (if present), cleavage, and refractive index, are sufficient to distinguish the mineral from any other. Hauyne is sometimes blue, but the colour is almost the only point of resemblance. Glaucophane is distinguished by its lower refractive index and its peculiar colours and pleochroism.

Epidote.— $\text{Ca}_2(\text{AlOH})(\text{Al,Fe})_2(\text{SiO}_4)_3$. *Monoclinic*. *Cleavage* 001 (*Basal*). *Twinned on* 100 (*Orthopinacoid*). *Birefringence negative*.

Colour. Pale yellow green (pistachio green).
Form. Usually granular or irregular. Occasionally idiomorphic, with transverse sections exhibiting resemblances to those of hornblende.
Cleavage. In one direction, but not always seen.
Ref. Index. 1.76. Very good relief.
Pleochroism. Feeble: pale green to darker green.
Pol. Colours. 2nd and 3rd order. Very bright colours.
Twinning. Rarely seen.

Resemblances.—Epidote is distinguished from pyroxenes and amphiboles by its colour and higher refractive index; from sphene and garnet by its bright polarisation. Tourmaline is sometimes very similar in appearance when in irregular masses, but epidote may be distinguished by its peculiar colour, superior cleavage, higher refraction, or brighter polarisation; and in convergent light by its biaxial interference figure.

Zoisite. — $\text{Ca}_2(\text{AlOH})\text{Al}_2(\text{SiO}_4)_3$. *Orthorhombic. Cleavage* 010 (*Brachypinacoid*). *Birefringence positive.*

A mineral closely related to epidote in composition, but differing very widely from it microscopically.

Colour.	Usually none.
Form.	Variable.
Cleavage.	Rarely seen.
Ref. Index.	1.70.
Pol. Colours.	1st order grey or ultra-blue.

Resemblances.—Distinguished from apatite by absence of form, higher refractive index, or ultra-polarisation; also by its biaxial interference figure.


Calcite.— CaCO_3 . *Hexagonal. Cleavage Rhombohedral. Birefringence, negative.*

Colour.	None.
Form.	None.
Cleavage.	Good. In two or three directions.
Ref. Index.	1.57 approx.; but varies with the direction of section.
Alteration.	None.


PLATE XII




1.—Calcite, Ord. L. Showing cleavages and the occurrence in amygdule.

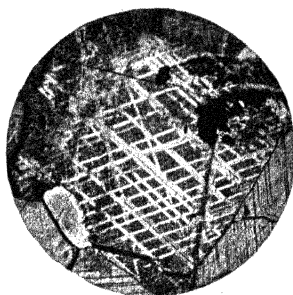

2.—Calcite, Crossed nicols. Showing lamellar twinning.

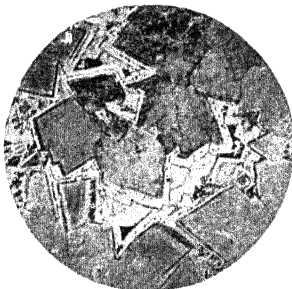


3.—Dolomite, Ordinary Light. Showing form and zoning.

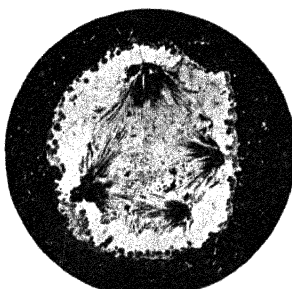

4.—Zeolites, Ord. L. Showing occurrence with vermicular chlorite in amygdule.



5.—Cordierite, Ordinary Light. Showing haloes round inclusions.

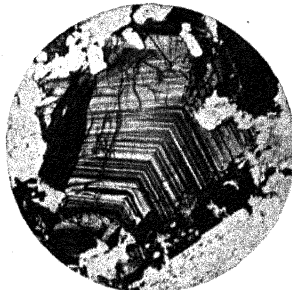

6.—Cassiterite, Ordinary Light. Showing zoning.

To face page 83.

- Pleochroism. None. But there is often a striking change of relief when the test is applied, the result of the high double refraction. This change, when the polariser or the stage is rotated rapidly, gives the effect known as twinkling.
- Pol. Colours. Pale pinks and greens or high order greys.
- Twinning. Lamellar.

Dolomite.— $\text{CaCO}_3\text{MgCO}_3$. *Hexagonal.*

Has many points of resemblance to calcite, but has crystals with a rhomb-shaped outline, and often well-marked colour zoning.

Zeolites.—*Hydrated silicates of aluminium with various alkalies and alkaline earths.*

The group known as Zeolites is a very large one, the different individuals differing greatly. As a rule, they are found filling cracks or cavities.

They are colourless, and have a refractive index near to that of Canada balsam. Two of the most important are ANALCIME (cubic) and NATROLITE (orthorhombic); the latter occurs as acicular crystals polarising in 1st order colours. Analcime may occur in cavities, possibly as a secondary mineral, but there is strong evidence in support of the idea that it (and zeolites in general) has crystallised as a normal igneous constituent.

Cordierite.—*Silicate of magnesium, iron, and aluminium. Orthorhombic. Cleavage 100, 010, & 001 (macro-, brachy-, and basal pinacoids). Birefringence negative.*

- Colour. None.
- Form. Usually allotriomorphic.
- Cleavage. Not conspicuous, but may often be seen.
- Ref. Index. 1.54. Almost equal to that of Canada balsam.

Alteration.	Commonly alters along cracks, forming turbid, pale greenish streaks.
Pleochroism.	None, save around minute inclusions, which often produce beautiful pleochroic haloes.
Pol. Colours.	1st order.
Twinning.	Occasionally seen. Simple, lamellar, or cyclic.

Resemblances.—May be distinguished from quartz and feldspars by the pleochroic haloes, which, although not necessarily conspicuous, may nearly always be found; also distinguished from quartz by its cleavages, twinning, and biaxial interference figure.

Cassiterite (Tinstone).— SnO_2 . *Tetragonal. Twinned on 101 (2nd order pyramid). Birefringence positive.*

Colour.	Brown.
Form.	Usually irregular or granular.
Cleavage.	None.
Ref. Index.	2.00. Very high relief.
Zoning.	Colour zoning common and well shown.
Pleochroism.	Feeble.
Pol. Colours.	High order greys, but usually masked by the body colour.
Twinning.	Simple twins common.

Zircon.— ZrSiO_4 . *Tetragonal. Twinned on 101 (2nd order pyramid). Birefringence positive.*

Very much like apatite, but distinguished by its higher ref. index (1.95), and by its polarisation colours. These latter are high order greys, with, in a few cases, pale pinks and greens of a high order. The distinction between the two minerals is not an easy one, as the greys of a high order may be very similar to those of the first order shown by apatite, but the distinction may be effected by the form of the cross sections and the sign of double refraction.

THE OPAQUE MINERALS

Magnetite.— FeOFe_2O_3 . *Cubic.*

Ilmenite.— FeTiO_3 . *Hexagonal.*

Pyrites.— FeS_2 . *Cubic.*

As these minerals are opaque, it will be seen that the only available method of examination is that by reflected light.

Pyrites, thus examined is seen to be brass yellow.

Magnetite and ilmenite are black when fresh, but when decomposed, the one can be distinguished from the other. The alteration product of magnetite is brown or yellow, that of titanoferrite is white, and its development has often taken place so as to form triangular geometrical patterns.

THE STUDY OF ROCKS

IGNEOUS ROCKS.—At different periods and in many areas great quantities of lava have been poured forth at the surface of the earth, and the rocks formed as a result of the cooling of these give us an idea as to the nature of some of the subterranean material, whether this came from a horizon within the crust or from beneath it. By far the most common of these rocks is basalt, which is a mixture of olivine, augite, and plagioclase felspar (about labradorite), together with a few other minerals in smaller quantities.

On account of the remarkable similarity between the basalts of different ages and different areas the opinion has, within recent years, been gaining ground that these flows were fed from a continuous layer underlying all continents and oceans; and that the continents, perhaps twenty miles thick, are floating in this substratum much as an iceberg floats in water.

From time to time, tensions develop in the continents, fissures originate and give an ascending passage-way to the liquid basalt which thus emerges at the surface by way of one of these or a series of them, more or less parallel. These effusions constitute fissure eruptions, but they differ in no essential from emission at volcanoes,

since the latter merely result in consequence of local plugging of a fissure. By such means, what was probably part of the basaltic substratum appears at the surface of the earth, and its very constant characters suggest that it reaches daylight in an unchanged condition as far as composition is concerned. If such a picture represents the facts, it is perhaps permissible to suppose that when the ascent through the crust ceases, there is left, frozen in this, a series of great wall-like masses of basalt rock extending from substratum to surface as dykes.

In other cases, however, the time factor enters; portions of the substratum ascending slowly within the crust and losing heat continuously to the adjacent country rocks. In such circumstances it is possible for certain chemical compounds to separate from the intrusive liquid, the magma, in the form of crystals. Among the earliest of these are olivine and augite; these are followed by lime-felspars, hornblende, and later, by biotite and alkali-felspars, together with quartz.

It will be obvious that if a mineral like olivine crystallises from such a magma, the residual liquid will have become poorer in iron and magnesium; indeed, if such crystallisation could continue (which is impossible) both these elements would then exist in the crystals, but not in the liquid. Crystallisation of one mineral, then, means separation of certain constituents from the liquid; it means also that the residual magma becomes relatively richer in those constituents not required by

the crystals; the liquid becomes progressively richer or progressively poorer, according to which of these we have in mind.

Such facts have been long appreciated, and it was customary for petrologists to speak of increasing acidity of the residuum, the idea being that a silica-rich liquid represented the final phase. It was Dr. N. L. Bowen who first showed that the essential increase was not in silica but in alkalis; that in the later stages the liquid becomes poorer in silica. He pictures the earlier minerals crystallising, and because they are heavier than the liquid, sinking; this sinking proceeding until prevented by increasing viscosity, until they have reached the bottom of the magma chamber, or until they are trapped in a meshwork of other crystals.

In such circumstances, if the liquid life of the reservoir is sufficiently long, we should expect the magma chamber to be stratified according to the order of crystallisation of the constituent minerals; we should also expect the last-formed crystals to occupy the uppermost part of the magma chamber. Moreover, we should expect the minerals there forming to be rich, not in silica, but in alkalis.

All this takes place well below the surface of the earth, hence the resulting rocks are known as plutonic; it takes place under conditions of slow cooling and therefore crystalline rocks are formed; hence the name holocrystalline applied to them. Clearly, any exposure of such rocks at the surface means that the overlying rocks have later been removed by denudation. In such a magma cham-

ber, where differentiation has proceeded to the limit, the plutonic rocks should be arranged in descending order, graduating one into the other, as follows :—

<i>Rocks.</i>	<i>Essential Minerals.</i>
Nepheline Syenite	Nepheline, Alkali feldspars.
Syenite	Alkali feldspars.
Granite	Alkali feldspars, quartz.
Diorite	Lime-soda feldspars.
Gabbro	Lime feldspars, olivine, augite.
Peridotite	Olivine, augite.

The particular variety of plutonic rock exposed at the surface to-day will depend on the extent to which denudation has proceeded. Thus, Bowen explains the difference between the plutonic rocks of the Rocky Mountain region and those of Montana, by suggesting that those of the former area (granites), represent deeper denudation than in the case of the latter, which are definitely richer in alkalis. •

But it must not be supposed that this complete stratification is always attained. The process is only allowed to proceed to the limit in the case of those reservoirs having a long liquid life. Freezing may take place at any stage and therefore the uppermost plutonic rock may be syenite, granite, diorite, or even gabbro if freezing supervenes at an early stage.

So far we have adopted Bowen's theory of crystal-differentiation, taking it as demonstrated that the work of gravity has been performed after the beginning of crystallisation.

It is possible, however, that differentiation was effected prior to crystallisation. Some liquids

form homogeneous mixtures at a high temperature, but if this is allowed to fall, the two liquids separate, the heavier below, and the lighter above. Thus, if such a procedure operates in the case of magmas, gravity stratification does not depend on sinking of crystals; moreover, the contact of two types of plutonic rock is likely to be sharper than under the conditions postulated by Bowen. Perhaps each is an important factor. In any case the result may be much the same as far as the broad outlines are concerned.

Professor R. A. Daly, perhaps the chief exponent of the theory of liquid immiscibility, points out an interesting consequence of progressive differentiation. He calls attention to small masses of diorite occurring in satellitic fashion around large granitic areas, and explains them by supposing that at an early stage of differentiation in the chamber, some of the magma was ejected from the upper part of it into the adjacent rocks. There it solidified rapidly (relatively) because of loss of heat to the cold rocks in contact; no further differentiation was possible and a diorite was formed. But in the parent magma chamber, the liquid life being longer, differentiation proceeded to a later stage, and granite was produced near the summit.

Another interesting phenomenon is explained by the same worker. In the case of some plutonic masses, the marginal portions are more basic (i.e. poorer in silica) than in the rest of the rock. Various suggestions have been put forward to account for this, but it is fairly certain that Daly's explana-

tion is the most satisfactory. A magma in an early stage of differentiation occupies a part of the earth's crust, freezing on the walls may be expected, and there is thus formed a fringe in which no further rearrangements can take place. In the central part of the chamber, however, loss of heat is much less rapid, gravity adjustments can be effected, and therefore, near the roof, a late phase will immediately underlie, and will be surrounded by, an earlier one. There are a few cases in which the margin is relatively acid (i.e. richer in silica), but in those cases the main mass is a nepheline syenite or allied rock, and this sort of thing is to be expected if the sequence of events already outlined, with alkali-rich rocks as the final phase, represents the facts.

The occurrence of dioritic satellites opens up some interesting speculations as to the sequence of these minor intrusions. It is not to be expected that a great magma chamber will be free from disturbance by earth movements during the whole period of crystallisation, and any squeeze is liable to result in transfer of some of the magma from the main chamber into the country rock. If we imagine this reservoir to be compressed at intervals before completion of crystallisation, intrusions from near the top of it will be progressively richer in alkalis. Consequently, if two such intrusions are found associated, we should expect the alkali-rich to be later than and possibly to cut the alkali-poor rock. The question is, however, a complicated one, because the area under consideration

may have received contributions from two adjacent batholithic chambers. Moreover, in a satellitic chamber the liquid life may be prolonged, differentiation of its partial magma may take place, and ejection of its liquid residuum may follow.

Another question, still unsolved, and of great importance, relates to the purity of the magma. It is quite certain that in some cases the igneous rock occupies a space which resulted in consequence of displacement of the pre-existing rocks, the magma having forced these aside or having occupied a chamber opened up by earth movements. A laccolite, for example, with a plane lower surface and a convex upper surface may very well result from emplacement of a magma which lifted up the superincumbent rocks. But, by definition, a laccolite has a floor of pre-existing rocks, and this floor is not always visible. Such a great granite mass as Dartmoor, for instance, may be a laccolite; but the floor is nowhere exposed and the mass may extend downward indefinitely; it may, in fact, be a batholith. Now, if this be the case, it is difficult to see how the magma could have come to occupy its present position by mere displacement. Hence Daly and others claim that the rocks that formerly existed there have been incorporated in the magma; they have been assimilated and the magma is no longer purely igneous in character. By this school it is contended that such assimilation of silica-rich material, and subsequent gravity adjustments, are necessary to produce the granitic differentiate.

To explain the existence of alkali-rich rocks like nepheline-syenites the assimilationists go a step further. They are impressed by the very common association of these intrusive rocks with limestone; they consider that calcareous fragments have been detached by the granitic magma and that reactions involving the using up of silica have taken place; that the magma has, in fact, been desilicated, with the result that silica-poor minerals like feldspathoids have originated. On these questions of the origin of granite and nepheline syenite then, the two schools of thought are definitely opposed. One derives all varieties by crystal sinking; the other demands assimilation of great masses of country rock. Each worker should keep both possibilities in mind, examine his rocks, and form his own conclusions. The controversy is not sterile; it has added enormously to the interest of problems in petrology, and mere rock description has been superseded by healthy speculation.

That portions of the country rocks are caught up by the magma admits of no doubt; these "xenoliths" are to be observed in numerous igneous intrusions. They, in many cases, are easily recognisable as such, being enclosed in the igneous rock without having suffered any appreciable change. In other cases, interchanges between magma and xenolith have taken place to such an extent that the latter is barely recognisable as such. That being so, the question at once arises as to how much of this incorporation, leaving no trace, has been effected. To that, of course, no satis-

factory answer is available. Dr. Harker was of the opinion that the magma was never hot enough to do the work, while Daly considered that it had taken place on a wholesale scale. Bowen, however, has shown that the importance of superheat was much exaggerated, and that this process of incorporation may take place to a considerable extent even though the temperature may never have been much higher than that at which crystallisation commenced. There is no possible doubt, then, that the intrusive igneous rocks we can examine in the field have lost their initial purity; they are to some extent modified as a result of the incorporation of portions of the pre-existing country rocks, and this modification ("contamination" of Professor Read) may or may not be recognisable when the rock is examined under the microscope or by means of chemical analysis.

But this migration from country rock to intrusion is not the only kind of transfer. It is quite certain that at different stages of cooling, material is exuded by the magma into the country rocks. The occurrence of many ore deposits, such as ores of copper, tin, and tungsten in the neighbourhood of igneous contacts, bears witness to the fact that solutions of various kinds have passed the junction and have laid down their burden in the country rocks, either in fissures or actually replacing pre-existing minerals. The cause of the precipitation in fissures is not always clear; but diminishing temperature away from the intrusion is one probable cause, decrease of pressure in the case of

ascending solutions is another. Conditions of chemical stability enter where solutions of magmatic origin encounter those of atmospheric origin and also where replacement (metasomasis) has taken place. Water has played an essential part in the transfer of this igneous material and it seems necessary to accept it as an integral part of the magma, although it is just possible that it may have been acquired by incorporation of water-bearing country rocks at an earlier stage of the magmatic history.

Water as a medium of transfer, does not, however, act alone. Gaseous emanations also are responsible for the manufacture of many ore deposits, particularly those of cassiterite and wolfram; the process is that known as pneumatolysis. Exudations of this kind seem to have taken place at high temperatures and probably, on the whole, precede those in which water is concerned, but no doubt their periods of emission overlap to some extent.

It should be borne in mind that the central parts of an intrusion remain liquid at a period when the marginal portions have become chilled, and therefore these solutions, in water or gas, travelling outwards from this liquid core, are compelled to traverse rock of igneous origin before reaching the country rocks, therefore precipitation may occur in the igneous rock already solidified, at the contact, or beyond. The particular point at which deposition takes place depends on a variety of causes, but naturally the high temperature

minerals will be laid down nearer the source of origin, those that can remain in solution at lower temperatures may be carried to some considerable distance before precipitation takes place and hence, their magmatic origin is not always obvious.

Transfer of igneous material by water or gas means, of course, that the volatile constituents can no longer be contained in their entirety by the magma. This result must follow as a consequence of crystallisation, because the amount of the latter is continually decreasing and there must come a time when the volatiles, which have not been abstracted to form crystals, become too voluminous for their more and more contracted quarters. It seems legitimate to expect, then, that metasomasis and pneumatolysis will commence soon after the beginning of crystallisation, and will continue as long as any liquid remains. Full data are wanting, but certainly much pneumatolytic activity takes place during or after the granitic stage. Tourmaline and topaz, rich in boron and fluorine respectively, are undoubtedly a consequence, in some instances, of this gaseous transfer, and they are frequently found replacing minerals of granite like orthoclase and biotite; likewise, beautiful pseudomorphs of cassiterite after feldspar are found in these rocks.

It may be taken as demonstrated, then, that neither the intrusion nor the country rock retains its original bulk composition; it is permissible for anyone however, to form his own opinion as to the extent to which such transfer has taken place in particular cases.

So far, we have considered the conditions under which intrusive igneous rocks are formed, the top of the basaltic wedge or magmatic chamber having failed to communicate with the earth's surface. But there is no fixed depth for the summit of such an intrusive body, and there must have been many cases in which communication with the light of day was effected, and the particular differentiation product developed at the time at that summit was ejected at the surface and formed an extrusive igneous rock. The composition of this volcanic rock will clearly depend on the particular stage of evolution reached in the chamber below. We thus may expect to find volcanic rocks comparable in composition with the plutonic rocks, the mineral content of which has been briefly indicated. There are, however, some conditions peculiar to igneous rocks formed above ground. In the first place, cooling at the surface is more rapid than it is underground, not because air is a better conductor than rock, but because convection ensures constant removal of heat from the cooling surface. Slow cooling facilitates crystallisation, therefore volcanic rocks tend to be non-crystalline or glassy. In the second place, escape of volatile constituents from the surface of a lava is much easier than it is in the case of an intrusive magma. Now it is safe to say that the presence of these volatiles facilitates the formation of crystals, and that their absence renders crystallisation difficult or impossible. For two reasons, therefore, extrusive igneous rocks should contrast with their intrusive counterparts

by being glassy instead of crystalline. On the whole, this expectation is justified, but there are, of course, some exceptional cases where crystals have grown in the surface flows after extrusion and where intrusive igneous rocks are glassy. Moreover, the volcanic rock may contain crystals of subterranean origin; this must be the case because extrusion is an incident which takes place during the period of crystallisation of the feeding magma and these must in certain cases be carried to the surface and will be found embedded in the material, glassy or otherwise, formed by solidification at the surface.

The lava after extrusion will, of course, flow down any slope on which it may rest, until further movement is rendered impossible by increasing viscosity. During this movement any contained elongated bodies, crystalline or otherwise, will be drawn out in the direction of flow and thus a fairly characteristic texture is developed in the rock; it must be remembered, however, that flow may, in certain circumstances, take place at depth and somewhat similar results be produced.

Another important peculiarity of extrusive rocks follows as a consequence of their mode of origin. The escaping gases cause bubbles to form at the surface; these form in great numbers and the gases burst through to the open air. The result is a vesicular or scoriaceous texture. Most of these vesicles are ellipsoidal in shape, the long axis indicating the direction of flow. The surface of the flow, then, may be expected to be glassy and to

exhibit scoriaceous texture; the central part of the flow may be glassy or crystalline. Any part of the flow, however, may contain crystals of subterranean origin.

In some cases (e.g. Antrim & Mull) such flows rest on plant remains which enable the date of the extrusion to be fixed with a fair amount of accuracy.

If the eruption was not effusive, but explosive, fragments of lava and other rocks were hurled violently upwards to come down later and form a deposit which, like an ordinary sediment, may enclose examples of the life of the period and enable the age to be determined by the fossil test. Such rocks are known as volcanic ash, tuff, or agglomerate. They will, of course, present evidence of clastic origin when examined with or without the aid of a microscope.

In considering the effusive rocks, it has to be remembered that the glassy state is unstable. Even old glasses made by man have in some instances made attempts at crystallisation, and those of igneous origin, particularly the older ones, frequently exhibit similar phenomena. Crystals formed under such conditions tend to be acicular and to be grouped radially about a point; they are most common in acid rocks, and are known as spherulites. The fact that flow bands frequently traverse them shows in those cases that the crystallisation is of later date. Also found in the glassy rocks are curved cracks known by the name "perlitic." Where crystallisation after solidification

(devitrification) has been considerable, it is sometimes difficult to recognise the fact that the rock was originally glassy; in such cases, the existence of perlitic structure may be distinctly useful in the attempt to work out the history of the rock.

As in the case of minor intrusions, elucidation of the history of a volcanic area is attended by considerable difficulty. Where one flow rests upon another it is clear that the upper one is the newer, but it is not always possible to get conclusive evidence of superposition. Assuming the truth of Bowen's sequence, that richer in alkalis should be the newer. But it is not certain that all the flows of one area came from the same reservoir and therefore this particular test is inapplicable. In any such area the sequence must be worked out by painstaking collection of evidence in the ground.

The orthodox classification of plutonic rocks according to composition may be indicated as follows:—

	Granite	Acid
66% SiO ₂ ————	Syenite	} Intermediate
	Diorite	
52% SiO ₂ ————	Gabbro	Basic

Thus, granite is that plutonic rock which is specially rich in silica, and therefore contains feldspars rich in the orthoclase or albite molecule, together with quartz; these are usually accompanied by one or both micas, and maybe, apatite and sphene. Gabbro is poor in silica and consists of a feldspar rich in the anorthite molecule together

with a pyroxene and usually, olivine; apatite and iron ore may be present. Of the two intermediate classes, syenite is rich in alkalies, while diorite is poor in them. In both cases, certain ferro-magnesian minerals like augite or/and hornblende are included; while biotite, apatite and sphene may be there, the latter mineral particularly in syenites. The chief minerals in these intermediate rocks, however, are the feldspars; syenite has orthoclase, microcline, or a soda-lime feldspar close to albite in composition; the feldspar of diorite ranges about andesine in composition although zoned examples are common, and of course, each zone has its own particular composition. But both syenite and diorite may contain a little quartz, thus indicating an approximation to the granitic end of the series. Now, if the tabular statement above represents the facts, a quartz syenite is a reasonable possibility, but a quartz diorite is absurd. Although there is much difference of opinion regarding rock nomenclature there are fairly common rocks which all petrologists call quartz-diorites. It therefore seems better to adopt a scheme such as that represented in diagram A. This method of grouping allows for the existence of types transitional between syenite and gabbro, gabbro and diorite, syenite and granite and granite and diorite, all of which undoubtedly exist. Again, there are a few rocks which seem to partake of the character of granite and gabbro or of syenite and diorite. A similar grouping may be adopted for those igneous rocks, usually found as dykes and sills (minor in-

trusions), which on the whole have a finer texture than the corresponding plutonics or contain their minerals embedded in a glassy matrix. They are usually referred to as hypabyssal (diagram B).

The corresponding volcanic rocks may be grouped in a similar way. Theoretically, these are the glassy rocks, and they do usually contain a certain amount of uncrystallised material; this is however usually very scarce in the case of basalts (see diagram C). If each of these three diagrams is drawn on a postcard and then superposed thus :

C
B
A

so that granite, quartz felsite, and rhyolite, form a vertical series, we get a scheme of classification, based on composition and texture, which is fairly satisfactory. Better still, regard the specimens as being stored in a building with three floors, four rooms on each.

According to this scheme, all plutonic rocks are on the ground floor, the hypabyssal rocks on the first floor and the volcanic rocks under the roof. Moreover, vertically above one another the rocks have approximately the same mineral composition.

There are, of course, many names given to different varieties of igneous rocks—names not mentioned in this brief summary—but it is believed that the scheme here suggested is fundamentally sound, and with this in mind, the student may proceed to the study of larger works and will find it a useful foundation.

A	Rich in Alkalies SYENITE Poor in Silica	Poor in Silica GABBRO Rich in Alkalies
	Rich in Silica GRANITE Poor in Alkalies	Poor in Alkalies DIORITE Rich in Silica
B	Rich in Alkalies FELSITE Poor in Silica	Poor in Silica DOLERITE Rich in Alkalies
	Rich in Silica QUARTZ FELSITE Poor in Alkalies	Poor in Alkalies PORPHYRITE Rich in Silica
C	Rich in Alkalies TRACHYTE Poor in Silica	Poor in Silica BASALT Rich in Alkalies
	Rich in Silica RHYOLITE Poor in Alkalies	Poor in Alkalies ANDESITE Rich in Silica

No claim to finality is implied ; a perfect scheme of classification will be based on complete knowledge of igneous processes, and it will be clear to those who have read the preceding pages that we are far from having attained that position.

SEDIMENTARY ROCKS. — The operations of denudation and deposition are so completely bound up with the appearances presented by these rocks that it is quite hopeless to attempt their study without a good knowledge of the processes. That knowledge will be assumed, and only the lines along which the examination of the rocks should proceed will be indicated.

As in the case of igneous rocks, hand-specimens should always be examined if available.

Arenaceous Rocks (pebbly and sandy).—In the attempt to elucidate the history of a conglomerate, thin sections of the pebbles may often be examined with profit ; because clearly such fragments are portions of rocks which formed the land surface at the time of accumulation of this particular deposit ; and the investigator, if he can, by lithological comparison, determine with certainty the rock-mass from which the pebble was derived, is able to obtain valuable information regarding the time at which deposition was effected. Thus, fragments of Shap granite are found in a conglomerate at the base of the Carboniferous Limestone. It follows that the intrusive rock is pre-Carboniferous in age ; it had even been “ unroofed ” before deposition of that limestone commenced. Conversely, if the age of the parent-

rock is known, information regarding the age of the deposit resulting from its erosion is available; and as the Shap granite is known to be of post-Silurian date, it follows that the conglomerate containing fragments derived from it is later still.

In recent years, much work has been done on sandy rocks, the same principles being applied; the constituent minerals are determined and attempts are made to visualise the nature of the rocks forming the old land surface from which the materials were denuded. First, sections of the sandstone should be made in the ordinary way. The minerals existing as grains should be identified, and the nature of the cementing material determined. The degree of rounding and angularity of the grains should be noted. As a result of the mode of formation of such rocks, there has usually been such a selection of mineral fragments that the bulk of these derived constituents is made up of minerals which are not decomposed by trituration in atmospheric waters; and as quartz is by far the most common of these, that mineral is the most conspicuous constituent. In those cases, however, where the accumulation of the detritus to form the deposit was not accompanied by much water action, less stable minerals had a chance of preserving their identity; and felspar grains are fairly abundant. Many such sections may be made and examined without the discovery of mineral grains other than those of quartz and felspar, but the amount of a rock constituting a thin section is very small, and any mineral which was

sufficiently stable under the conditions of the time might reasonably be expected to occur accompanying the quartz in the deposit. One object of the recent work is to discover the nature and amount of these less common minerals occurring as constituents of the sandstones.

The rock should be crushed and graded by placing the powder in the uppermost of a series of sieves, fitting one above the other, that with the smallest perforations being at the bottom, the sieves becoming coarser and coarser with ascent in the series. A little shaking will cause the fragments to separate into grades. A sample from each grade should be mounted in clove oil and examined under the microscope; it will then be clear which particular grade is most suitable for purposes of investigation.

The narrow end of an ordinary glass funnel should be fitted into a short rubber tube which should be closed by means of a spring clip. This funnel, supported in a suitable stand and nearly filled with bromoform (Sp. Gr. about 2.89) supplies the means of separating the minerals of the selected grade into two fractions, lighter and heavier. The whole of this grade is placed in the bromoform, stirred, and allowed to stand for a few minutes. Then the lower half of the bromoform is run into a basin, this being accomplished by opening the clip. The heavy liquid in this basin may then be decanted into the stock bottle via a filter placed in a funnel. The heavy mineral grains left behind may then be washed in benzene;

they will soon dry and can be mounted in clove oil or Canada balsam for examination. The lighter minerals are almost sure to be present in any thin section of the rock; it is these heavy minerals that are less common and therefore they should be collected and examined with some care. If necessary, magnetic or other methods may be used to split this heavy residue into smaller fractions.

The student who has become familiar with the appearance of these minerals as seen in thin sections will find some difficulties in the early stages for several reasons. As a result of crushing prior to grading some of the crystals will have been broken and therefore form may cease to be of any assistance even where the crystals were idiomorphic; the crushing also means that cleavable minerals will have split and will rest on the slide on a cleavage plane and therefore such planes will not be indicated by the parallel cracks previously found so useful in identification. The chief difficulty, however, is in regard to thickness. The grains will almost certainly have a greater diameter than the thickness of an ordinary thin section; moreover, however perfect the grading may have been, the different grains will vary in size. Therefore there is no definite standard of polarisation colour for a particular mineral, and some practice is required before the difficulty is overcome.

The following minerals are those most commonly found in these heavy residues:—

Anatase.—A tetragonal mineral. Colour blue or yellow. Often tabular owing to good development of the basal pina-

coid, but sometimes the pyramid is dominant. Refractive index very high, about 2.49. Between crossed nicols platy forms are isotropic; in convergent light shows a positive uniaxial figure.

Apatite.—Colourless. Occasionally as irregular grains, but most commonly as elongated crystals with well-defined prism edges. Refractive index about 1.60 and therefore has a fairly good relief. Usually clear and transparent. Birefringence, 0.004, is very low, and therefore always polarises in first order grey. Has straight extinction. With a slow wedge gives compensation when that is parallel to the direction of elongation.

Epидote.—Pale yellow green. Has a fairly good cleavage and fragments frequently rest on this. Refractive index about 1.73 and therefore relief is good. Pleochroism feeble. One of the two optic axes is approximately at right angles to the cleavage and therefore in convergent light a single eye is seen near the centre of the field; it is traversed by a single, almost straight, black band.

Garnet.—Usually pink or pale brown. Grains quite irregular in shape. Refractive index about 1.80 and therefore relief is good. No pleochroism. Isotropic.

Hornblende. — Colour green or brown. * Fragments usually rest on a prismatic cleavage. Refractive index about 1.65 and therefore with good relief. Pleochroic; vibration-direction giving maximum absorption slightly inclined to length of fragment. Extinction angle about 16°. In convergent light one of the optic axes emerges near the margin of the field.

Kyanite.—Generally colourless, but may be blue. Has three cleavages approximately at right angles; the fragment is usually elongated and probably rests on the best of the three cleavages. Clear and transparent. Refractive index about 1.72; good relief. Polarisation colours usually first order. Extinction about 30°. It happens that the acute bisectrix is approximately at right angles to the best cleavage and therefore the fragment shows a complete biaxial figure with negative birefringence.

Monazite. — A monoclinic mineral. Colour generally greenish yellow with brownish patches. Usually as rounded grains bounded above and below by cleavage. Refractive index high, about 1.80. Not pleochroic. Polarisation

colours high. In convergent light shows a positive biaxial figure with a small optic axial angle.

Muscovite.—Colourless. Fragments rest on the perfect cleavage. Refractive index about 1.59; fairly good relief. Clear and transparent. Between crossed nicols difficulty is encountered because the polarisation colours (first order) are much lower than those usually shown in thin section. The acute bisectrix is approximately at right angles to the cleavage and therefore the fragment shows a complete biaxial figure. Birefringence negative.

Rutile. — A tetragonal mineral. Colour a very dark brown, almost opaque (with the condenser inserted the mineral shows a rich brown of medium shade). May be as rounded grains or as elongated crystals. Refractive index very high, about 2.62 and therefore relief is conspicuous. Pleochroism rather weak, maximum absorption with the elongation E.W., i.e., for longitudinal vibrations. Extinction straight.

Staurolite.—An orthorhombic mineral. Colour brown. No cleavage and therefore the fragments are quite irregular in shape. Refractive index about 1.74; good relief. Usually clear and transparent, but may be cloudy as a result of abundant small inclusions. Pleochroism feeble. A biaxial figure with a positive sign is sometimes, but not often, seen.

Topaz.—Colourless. May be rounded or may rest on the basal cleavage. Refractive index about 1.62; relief good. Clear and transparent. Cleavage flakes always show low polarisation colours. In convergent light a positive biaxial figure occupies the centre of the field.

Tourmaline.—Colour variable, but commonly brown. May be as elongated crystals resting on a prism face, may be rounded. May rest on a basal cleavage. In certain cases, e.g., when colour is strong and the crystal axis lies parallel to the glass slip, pleochroism is intense, maximum absorption taking place for transverse vibrations. A fragment resting on the basal cleavage will not show pleochroism. Between crossed nicols, prisms extinguish in the straight position. Basal sections are isotropic and give in convergent light a uniaxial negative figure.

Zircon.—A tetragonal mineral. Colourless. Usually as elongated crystals with well-defined terminations; may

be as rounded grains. Refractive index high, about 1.93; relief good. Usually clear and transparent. Between crossed nicols shows high polarisation and straight extinction.

(NOTE.—In all cases when getting the interference figure with mineral grains, use the third method indicated on p. 52; remove both Bertrand lens and the eyepiece.)

Magnetite and **Ilmenite**, both opaque, black, and metallic, are common. When fresh, are difficult to distinguish, but magnetite is liable to change to red iron oxide, while ilmenite may acquire a whitish colour as a result of change to leucoxene.

In the above descriptions it is assumed that the mineral grains are mounted in Canada balsam or clove oil, each of which has a refractive index about 1.54. Some idea as to the refractive index of the mineral, just as in the case of thin sections, may be obtained by inspection of the relief exhibited by it. The Becke method may be used to give additional information in this connection, but the shape of the grains is not as a rule suitable for this purpose, what is known as the shadow method gives more satisfactory results. To apply this test, keeping the eye fixed on a particular fragment, slide some opaque object immediately underneath the stage. The field will, of course, be partially darkened, but the observer should concentrate his attention on the edge of the grain. A black shadow will appear *on* one side of this, the side near to or remote from that from which the opaque object is introduced. If the shadow appears on the "near" side, the refractive index of the mineral is higher than that of the liquid; if it appears on the "off" side, it is less.

The two cases figured are drawn on the assump-

tion that the opaque object (a finger is suitable) comes in from the right.



Mineral > liquid. Mineral < liquid.

A combination of the inspection and the shadow methods gives the observer some idea as to the refractive index of the mineral under investigation, and the mineral should then be mounted in a liquid having a value something near that estimated for the grain. The following liquids will be found useful :—

Chloroform	...	...	...	...	1·45
Olive oil	...	...	...	...	1·47
Castor oil	...	...	...	...	1·48
Xylol	...	...	...	...	1·49
Oil of cedar wood	...	...	...	...	1·51
Monochlor benzol	...	...	...	...	1·53
Oil of Cloves	...	...	...	...	1·54
Brom-toluene	...	...	...	...	1·55
Dimethylaniline	...	...	...	...	1·56
Orthotoluidine	...	...	...	...	1·57
Cinnamon oil	...	...	...	...	1·59
Cassia oil	...	...	...	...	1·60
Iodobenzene	...	...	...	...	1·62
Monobromnaphthalene	...	...	...	...	1·66
Methylene Iodide	...	...	...	...	1·74

By applying the shadow test, and proceeding by trial and error, the refractive index of the mineral may be found with a close approach to accuracy if the fragment is immersed successively in liquids more and more closely approximating to that of itself. The observations should be made with a low power objective in a room having a temperature of about 60° F.

It will be seen in some cases, that instead of resulting in a definite shadow, insertion of the finger produces colour fringes; these always indicate a close approximation between the values of mineral and liquid. They result from the fact that the liquid has much the stronger dispersion. In difficult cases, it is advisable to perform the experiment by the light of a sodium flame instead of in daylight.

Argillaceous Rocks. — Slates and shales are usually so fine-grained that even the microscope fails to reveal much as to their mineral composition. Some examples, however, seem to show that their constituents are similar to those of arenaceous rocks, the fragments merely having been ground down to much smaller dimensions. Crystals of pyrite, of fairly large size in some instances, cannot be regarded as derived fragments; they must have acquired their present characters as a result of changes since deposition of the sediment.

Calcareous Rocks.—As a rule, these are the result of accumulation of fragments of organic origin, although some of them, such as stalactite and travertine, are formed simply by deposition from solution. Oolitic limestones are probably also inorganic in origin, the calcium carbonate of the oolite having been deposited in successive layers around a nucleus. Calcite makes up the bulk of such rocks and may easily be recognised as such by the twinkling effect observed when the section is examined over a rotated polariser, and by the absence of crystal form. The organisms of

which the rocks may be largely built are often clearly recognisable. Foraminifera such as *Globigerina*, *Nummulites*, also various corals and crinoids, are important limestone builders.

Some calcareous rocks consist entirely of dolomite, a mass of mutually interfering rhomb-shaped crystals, some of which may be sufficiently well-formed to give material assistance in identification. Such rocks were originally ordinary limestones; they have since been bathed in water containing magnesium salts and have suffered metasomasis. All stages of the change may be observed, some oolitic limestones showing perfectly formed rhombs of dolomite. The tendency is towards destruction of organic structures, but there are some cases where oolites are still visible even though the process of dolomitisation is complete. Other dolomitic limestones, not pure dolomites, were probably deposited as the mixed carbonates from the waters of desert areas. In some examples there has been re-sorting of the two carbonates as a result of the work of underground waters; this has given rise to the existence of concretionary structures. So far, the microscope has not added greatly to our knowledge of such rocks.

Siliceous Rocks.—In some examples the material accumulated as a deposit of the remains of organisms with siliceous skeletons, sometimes sufficiently well-preserved to be identified. The most common are radiolaria and sponges, and the rock is known as chert. Good examples of beds of

sponge chert are to be seen forming part of the Lower Greensand of Surrey, notably at Leith Hill and Tilburstow Hill. In other cases, as in flint, the rock is a silicified limestone, having resulted in consequence of the process of metasomatic replacement. Sometimes oolitic limestone has been silicified without destruction of the texture.

Carbonaceous Rocks.—A few of the Carboniferous coals exhibit the remains of spores and spore cases of the plants of that period. Other plant tissues are occasionally revealed by this method of investigation.

The distinction between sedimentary and igneous rocks, as seen under the microscope, is not always easy. The two classes overlap as tuffs, which are volcanic in origin, but are formed as a consequence of sedimentation; they may include fossils and are bedded. It must be borne in mind that the material of volcanic origin may form the whole of the sediment or it may be a very small percentage of the whole. Moreover, material originally volcanic in origin may be obtained second-hand if the area being denuded to supply the sediment is made of igneous rocks. True bedding is exhibited by such rocks; but flow structure of some lavas, notably rhyolites, simulates bedding very closely in some instances.

METAMORPHIC ROCKS. — Some of these rocks were originally igneous in origin, others were sediments, but in either case they have acquired distinctive new characters in consequence of the application of heat or pressure or both. In

some cases the rock mass we call metamorphic is of composite origin, being made up partly of igneous, partly of sedimentary material.

When a magma is intruded into a series of sediments, heat is supplied to these, and their constituents come to be re-arranged. A siliceous sandstone becomes a quartzite, a shale or slate develops crystalline minerals like andalusite or chiastolite, a limestone becomes a marble, a dolomitic limestone with some siliceous content becomes a crystalline limestone containing silicates like tremolite or diopside. Now the growth of new crystals in such a metamorphic rock means a local change of composition and this of necessity means that certain chemical compounds have migrated from one part of the rock to another, although the bulk composition of the rock mass remains constant. As suggested, such changes may be due to the action of heat alone, assisted perhaps by the action of water originally present in the country rocks.

But it has previously been seen in dealing with intrusive igneous rocks that exchanges across the contact are to be expected and it is extraordinarily difficult to be quite sure in any particular case that such exchange has not taken place, that nothing has been added and nothing taken away. Perhaps the best example of simple heat metamorphism is the case of the dolomitic Cambrian limestone of the North-West Highlands described by Sir Jethro Teall, but even there we can only say that the changes can be explained without

postulating the introduction of any foreign material. In other cases it is quite certain that limestones have been considerably enriched in silica and other constituents near the contact with the intrusion. Where an intrusion has cross-cutting relations with regard to the strike of the country rocks, it is sometimes possible to trace a particular bed into the metamorphic aureole, to collect samples at intervals and to make investigations regarding the changes observed at various distances from the contact. Something may be done in that way if exposures are sufficiently abundant to enable the observer to be quite sure that he is keeping on the same horizon, but there is no guarantee that the bed originally had a constant lithology.

We have to be prepared then for the possibility that in the case of some of the minerals found in a metamorphic aureole, material has been added by the igneous rock.

Similar considerations apply where the junction is extremely complex. In the case of a fissile sediment the protrusions of magma may take the form of numerous small sills, so small that an ordinary hand-specimen may include several of them. If there has been recrystallisation of the sedimentary layers and two-way migrations at the contacts, elucidation of the history presents complicated, if pretty, problems.

Striking changes of a rock may be due to pressure as was shown by Teall in his study of the Scourie dyke. He traced this dolerite dyke into a

belt of earth movement, found that the augite became hornblende and that a parallel arrangement of constituents, foliation, was developed.

Again, it is well known that some of the older rocks of the earth's crust have been buried repeatedly by newer sediments; they have undergone movements of depression and uplift. During a period of subsidence, sedimentation taking place at the same time, such old rocks were passing to regions of higher temperature; the pressure to which they were subjected was also increasing. Such circumstances undoubtedly favour the development of crystalline characters, and any differences of lithology between the successive beds might justifiably be expected to result in parallel layers of crystalline minerals, each layer having the mineral composition dictated by the nature of the original sediment.

The processes concerned in metamorphism, then, involve the action of heat, supplied by contact with an intrusion or by descent within the earth's crust; of pressure, resulting as a consequence of burial beneath later sediments, or by that kind of pressure, shearing, which involves differential movement of the constituents; and by that of a complicated kind of intrusion known as *lit-par-lit* injection, which means the development of a composite rock.

In all these cases there is a tendency towards the arrangement of the constituent minerals in layers. Initial differences of composition of the several beds are preserved whether metamorphism is by

contact or is the more widespread kind (regional) due to sinking of considerable areas. These differences may even be emphasized as a result of migration, across the bedding, of material to feed the growing crystals. Where metamorphism is by contact, any material invading the bedded rocks may be expected to follow the lamination and to effect deposition along those planes, thus emphasizing the differences between the horizons. Shearing produces a somewhat similar result, the planes of differential movement becoming planes of foliation. Pebbles in conglomerates and phenocrysts in igneous rocks have one dimension diminished and the others (in the planes of foliation) increased. This process may be assisted by the presence of water, solution taking place at points of maximum pressure and deposition in places protected by the presence of the resistant body. In this way are developed eye-shaped masses giving what is known as augen structure. Foliation will obviously be produced in the cases where minute igneous intrusions have followed parallel planes of weakness in the initial rock.

Metamorphic rocks are, then, characterised as a rule by foliation, but there are examples in which this structure is too coarse to show in an ordinary hand-specimen.

The metamorphic character is often betrayed also by the nature of the constituent minerals. Those specially characteristic of these rocks are :—chiastolite, sillimanite, kyanite, cordierite, tremolite, actinolite, glaucophane, forsterite, talc, zoisite, and garnets.

All stages of crystallisation are found, the particular one reached being dependent on the nature of the original rock and the amount of change it has undergone.

The most important metamorphic rocks are :—

Gneiss. — Holocrystalline, coarsely foliated, feldspar abundant. They are characterised as granite-gneiss, diorite-gneiss, etc., according to the plutonic rock they most closely resemble and by the metamorphism of which they may have been derived. The “eyes” of an augen-gneiss are possibly relics of original porphyritic crystals.

Schist.—Holocrystalline, conspicuously foliated, poor in feldspar, foliation less coarse than in gneiss. They are named mica-schist, hornblende-schist, chlorite-schist, talc-schist, quartz-schist, etc., emphasis being laid on some conspicuous mineral.

Some rocks originally argillaceous, and which have not been raised to any very high temperature, are known as chistolite slate, phyllite, and spotted slate.

Crystalline Limestones. — Consist to a greater or less extent of crystalline calcite. In many cases the metamorphism seems to have consisted of changes involving re-arrangement of materials already present. Thus, a pure limestone gives crystalline limestone (marble); a limestone with scattered fragments of silica becomes a marble with lime silicates: a dolomitic limestone with scattered silica becomes a crystalline limestone with silicates like tremolite or diopside. In this latter case the process is known as dedolomitisation. There are other cases in which the occurrence of great masses of iron-garnet compels belief in transfer from igneous sources.

In the study of contact metamorphism in any particular area, if the intrusive body has a fairly definite margin, the obvious procedure is to make a series of traverses at right angles to the contact, collecting and examining the rocks exposed; each traverse to extend to such a distance that it has become clear that the country rock is definitely igneous or sedimentary in character without any

alteration that might be due to the presence of the intrusion. The degree of metamorphism should diminish with increasing distance from the contact. It should be borne in' mind, however, that the nearest point in the igneous mass is not necessarily the nearest point exposed; if the upper surface of the intrusion has an irregular form the nearest point may be along a vertical line from the position of observation. In order to acquire the necessary knowledge regarding the changes due to metamorphism, all the unmetamorphosed rocks in the area should be studied; they are the raw materials. Whether the original rocks are igneous or sedimentary they should be mapped. It might be thought that metamorphism would have no effect on igneous rocks, but it has to be remembered that these may have been weathered before intrusion of the particular mass whose metamorphic effects are the particular object of study, and these products of weathering, formed at low temperatures, have been heated by the intrusion. Moreover, not all minerals formed during igneous action were crystallised at high temperatures; some of them, particularly those of vesicles in lavas, although igneous in origin are essentially low temperature minerals and they may become recrystallised under the influence of the intrusive rock.

If it is possible to explain the existence of all the minerals in the aureole without having recourse to the theory of igneous emanations, the study is comparatively simple. It will be clear, however,

that familiarity with the nature of the original rocks and with the compositions of the minerals in the aureole is essential. A possible complication is the existence of tongues (apophyses) of igneous rock extending from the main intrusion into the aureole.

In some cases intrusion was effected into an area occupied by rocks which had been metamorphosed at some earlier period; the study is then a matter of considerable difficulty.

Elucidation of the history of an area of regionally metamorphosed rocks involves the necessity of determining to what extent the changes were due to depression of the area, shearing, and litle injection. Difficulties in the way of determination of the nature of the original rocks may be great or small, depending on the amount of metamorphism. In some cases it is clear that the rock was originally a conglomerate or a grit or a porphyritic intrusive rock; in others there are mere suggestions of original structures—the palimpsest structure of Sederholm.

Whatever theories may be advanced by the investigator, and these must develop in the course of the work, all relevant facts should be recorded, not merely those which support the particular theory adopted.

SUGGESTIONS FOR FURTHER READING.

- N. L. Bowen.—*The Evolution of the Igneous Rocks.* Humphrey Milford, 1928.
R. A. Daly.—*Igneous Rocks & their Origin.* McGraw-Hill Co., 1914.

- A. Harker.—Petrology for Students. Camb. Univ. Press.
—— The Natural History of Igneous Rocks. Methuen, 1909.
—— Metamorphism. Methuen, 1932.
- F. H. Hatch & A. K. Wells.—The Petrology of the Igneous Rocks. Allen & Unwin, 1926.
- A. Holmes.—The Nomenclature of Petrology. Murby & Co., 1928.
- A. Johannsen.—A Descriptive Petrography of the Igneous Rocks. Camb. Univ. Press. Vol. I. 1931. Vol. II. 1932.
- S. J. Shand.—Eruptive Rocks. Murby & Co., 1927.
- J. J. H. Teall.—British Petrography. Dulau, 1888.
- N. H. & A. N. Winchell.—Elements of Optical Mineralogy. Chapman & Hall. Part I., 1922. Part II., 1927. Part III., 1929.

INDEX

The numbers in heavy type are those of pages where a description of the Minerals is to be found.

- Absorption, 23
- Acid igneous rocks, 100
- Acid margins, 91
- Actinolite, 73, 118
- Ægirine, 24, 71
- Agglomerate, 99
- Aggregate polarisation, 40
- Albite, 65
- Albite-Anorthite series, 14, 39, 65
- Alkali feldspars, 87, 89
- Allotriomorphism, 4
- Alteration, 12
- Amphiboles, 72
- Analcime, 83
- Anatase, 107
- Andalusite, 24, 84
- Andesine, 65
- Andesite, 103
- Anisotropism, 28
- Anomalous double refraction, 39
- Anorthite, 69
- Anthophyllite, 74
- Apatite, 3, 11, 28, 44, 77, 108
- Apophyses, 121
- Arenaceous rocks, 104
- Argillaceous rocks, 112
- Assimilation, 92
- Augen gneiss, 119
- Augen structure, 118
- Augite, 2, 3, 7, 13, 29, 71, 86, 87, 89
- Barytes, 34
- Basalt, 86, 103
- Basic igneous rocks, 100
- Basic margins, 90
- Batholith, 92
- Batholithic chambers, 92
- Baveno twin, 64
- Becke's test, 10, 110
- Bertrand lens, 51, 52
- Biaxial interference figure 52
- Biotite, 2, 5, 7, 13, 22, 23, 25, 36, 56, 58, 69, 87
- Birefringence, 34
- Bronzite, 72
- Bytownite, 65
- Calcareous rocks, 112
- Calcite, 5, 6, 17, 20, 22, 34, 82, 112
- Carbonaceous rocks, 114
- Carlsbad twin, 64
- Cassiterite, 88, 96
- Chalcedony, 63
- Change of relief, 25
- Chert, 114
- Chiastolite, 80, 118
- Chiastolite slate, 119
- Chlorite, 13, 37, 70
- Chlorite schist, 119
- Chloritoid, 70
- Cleavage, 5
- Cleavage angle, 8
- Colour, 1
- Colour zoning, 13
- Compensation band, 41
- Contamination, 94
- Contact metamorphism, 118
- Cordierite, 25, 83, 118
- Critical angle, 20
- Crossed nicols, 27
- Cryolite, 9
- Crystalline limestone, 119
- Crystal differentiation, 89
- Crystal sinking, 88
- Dedolomitisation, 119
- Desilication, 93
- Devitrification, 100
- Diallage, 71
- Differentiation, 89
- Diopside, 71
- Diorite, 19, 100, 103
- Dioritic satellites, 90
- Dolerite, 103
- Dolomite, 113
- Dolomitic limestone, 113
- Dolomitisation, 113
- Double refraction, 17, 25
- Elæolite, 68
- Enstatite, 72
- Epidote, 81, 108
- Either axes, 43, 46
- Extinction, 28
- Extinction angle, 29
- Extraordinary ray, 18, 27
- Extrusive igneous rocks, 97
- Fayalite, 76
- Felsite, 103
- Feldspathoids, 67, 93
- Feldspar, 14, 15, 64
- Fissure eruptions, 86
- Flint, 114
- Flow structure, 98
- Fluor, 11
- Foliation, 117
- Form, 4
- Forsterite, 76, 118
- Gabbro, 89, 100, 103
- Garnet, 2, 13, 14, 40, 78, 108, 118
- Glassy Rocks, 97
- Glaucophane, 73, 118
- Gneiss, 119
- Granite, 89, 90, 100, 103
- Gypsum, 5
- Hæmatite, 15
- Haüyne, 67
- Holocrystalline rocks, 88
- Hornblende, 3, 7, 24, 37, 73, 87, 108
- Hornblende schist, 119
- Hypabyssal igneous rocks, 102
- Hypersthene, 72
- Iceland spar, 17
- Idiomorphism, 4
- Igneous rocks, 87
- Ilmenite, 15, 85, 110
- Inclusions, 13
- Interference, 32
- Intermediate igneous rocks, 100
- Isomorphism, 14
- Isotropism, 28

- Kaolin, 12
 Kyanite, 81, 108, 118
 Labradorite, 33, 65, 66, 86
 Laccolite, 92
 Lamellar twinning, 38
 Leucite, 3, 11, 13, 40, 67
 Leucoxene, 15
 Light, 18
 Lime felspar, 87, 89
 Lime-soda felspar, 89
 Liquid immiscibility, 90
 Lit-par-lit injection, 117
 Magma, 87
 Magnetite, 15, 85, 110
 Manebach twin, 64
 Marble, 119
 Metamorphic aureole, 116
 Metamorphic rocks, 114
 Metasomasis, 95, 96
 Mica, 5, 6, 69
 Mica plate, 57
 Mica schist, 119
 Microcline, 65
 Minor intrusions, 91
 Monazite, 108
 Muscovite, 2, 5, 29, 36, 55, 57, 69, 109
 Natrolite, 83
 Nepheline, 3, 68, 89
 Nepheline syenite, 89, 91, 93,
 Newton's scale, 33, 34, 35
 Nicol, 19, 21
 Non-pleochroic sections, 26
 Nosean, 11, 13, 67
 Oblique extinction, 29
 Oligoclase, 65, 66
 Olivine, 3, 11, 12, 75, 86, 87, 89
 Oolitic limestone, 112
 Opal, 63
 Opaque minerals, 15, 85
 Optic axes, 53
 Optic axial angle, 53
 Optic orientation, 43, 45, 49
 Ordinary ray, 18, 27
 Orthoclase, 12, 13, 37, 64
 Palimpsest structure, 121
 Partial interference figures, 59
 Peridotite, 89
 Perlites, 99
 Phyllite, 119
 Plagioclase feldspars, 14, 38, 65, 86
 Pleochroic haloes, 24
 Pleochroic sections, 26
 Pleochroism, 22
 Plutonic rocks, 88
 Pneumatolysis, 95, 96
 Polarisation, 17, 30, 35, 40
 Porphyrite, 103
 Principal section, 19
 Pseudomorphism, 13, 40, 96
 Pyrites, 15, 85
 Pyroxenes, 14, 39, 70
 Quartz, 5, 12, 13, 15, 33, 34, 39, 44, 63,
 87, 89
 Quartz diorite, 101
 Quartz felsite, 102, 103
 Quartz schist, 119
 Quartz syenite, 101
 Refraction, 20
 Refractive index, 10, 14, 111
 Regional metamorphism, 118
 Relative retardation, 31, 33
 Replacement, 95
 Residual magma, 87
 Rhyolite, 103
 Rutile, 109
 Schist, 119
 Scoriaceous texture, 98
 Scourie dyke, 116
 Sedimentary rocks, 104
 Serpentine, 12, 80
 Shadow method, 110
 Shearing, 118
 Sign of double refraction, 40, 56, 57
 Siliceous rocks, 113
 Sillimanite, 80, 118
 Simple twinning, 38
 Single refraction, 28
 Sodalite, 68
 Sphene, 3, 37, 77
 Spherulites, 99
 Spotted slate, 119
 Stalactite, 112
 Staurolite, 109
 Straight extinction, 29
 Superheat, 94
 Syenite, 89, 100, 103
 Talc, 70, 118
 Talc schist, 119
 Tinstone, 84
 Titanite, 3, 37, 77
 Titanoferrite, 15
 Topaz, 11, 79, 95, 109
 Total reflection, 20
 Tourmaline, 3, 13, 14, 24, 25, 37, 78,
 96, 109
 Trachyte, 103
 Travertine, 112
 Tremolite, 73, 118
 Tridymite, 63
 Tuff, 99
 Twinkling, 25
 Twinning, 37
 Two-way migration, 116
 Ultra polarisation, 37
 Uniaxial interference figures,
 Vesicular texture, 98
 Vibration directions, 23, 24, 25, 30, 31,
 34, 50
 Volatiles, 96, 97
 Volcanic ash, 99
 Volcanic rocks, 97, 102
 Volcanoes, 86
 Wedge, 33, 41, 44, 58, 61
 Xenoliths, 93
 Zeolites, 83
 Zircon, 84, 109
 Zoisite, 37, 82, 118
 Zoning, 15, 41

MICROSCOPE SLIDES

To illustrate

“MINERALS AND THE MICROSCOPE”

SECTIONS OF SELECTED UNIAXIAL AND BIAXIAL MINERALS.

Cut in appropriate directions to give interference figures. Also sections to illustrate refractive index, polarisation, and extinction.

TO SHOW NEWTON'S SCALE AND FOR DETERMINATION OF

Sign: *Wedge of Quartz* From 15/- upwards

* *When ordering a quartz wedge please give size of slot in the microscope for which it is required.*

FOR DETERMINATION OF SIGN: *Mica plate*..... 4/0

ORDINARY LIGHT.

1. Three minerals mounted together to show difference of refractive index (*Quartz, Fluor, Topaz*)..... 3/0

PARALLEL POLARISED LIGHT.

2. Straight extinction (*small quartz crystals*)..... 1/6
3. Oblique extinction (*cleavage flake of Gypsum*) 1/6

INTERFERENCE FIGURES.

4. Uniaxial + (*Quartz*) 3/0
5. " — (*Tourmaline*) 3/0
6. Biaxial + (*Topaz*) 3/0
7. " — (*Muscovite*)... 2/0

SPECIAL INTERFERENCE FIGURES.

8. Smaller optic axial angle (*Aragonite*) 3/0
9. Partial biaxial (*Epidote*) 3/0
10. Pseudo uniaxial (*Phlogopite*) 2/0

EFFECTS OF VARYING THICKNESSES.

11. Biaxial (*Muscovite*)..... 3/0
12. Pseudo-uniaxial (*Phlogopite*) 3/0

Sections of Uniaxial Crystals: Sections cut at any required inclination to the optic axis.

Sections of Biaxial Crystals: Sections cut at right angles to the optic axial plane at any required inclination to the acute bisectrix.

COLLECTION OF 150 THIN SECTIONS

The list given in the next two pages includes 53 slides (indicated by asterisks) illustrating "Minerals and the Microscope."

Geological Supplies Department:

THOMAS MURBY & CO., 1, Fleet Lane, Ludgate Circus, London, E.C.4

150 THIN SECTIONS. A representative collection of first-class slides carefully selected for the study of petrology. 2/6 per slide.

IGNEOUS ROCKS.

- 1 *Microcline granite, *Rubislaw Quarries, Aberdeen.*
- 2 Biotite granite (Adamellite), *Shap, Westmorland.*
- 3 *Biotite granite, *Cheesewring Hill, Cornwall.*
- 4 Leinster granite, *Killiney, Co. Dublin.*
- 5 Coarse Leinster granite, *Three Rock Mt., Co. Dublin.*
- 6 Tourmaline granite, *Troon, Cornwall.*
- 7 *Tourmaline granite (Luxullianite), *Luxulyan, Cornwall.*
- 8 *Biotite - hornblende - granite, *Dalbeattie, Scotland.*
- 9 Augite granite, *Boosberg, Vosges, France.*
- 10 Basic secretion in granite, *Shap, Westmorland.*
- 11 Greisen, *Grainsgill, Cumberland.*
- 12 Pegmatite, *W. of Cripple Creek, Colorado.*
- 13 Augite syenite (Laurvigite), *Laurvig, Norway.*
- 14 Nepheline syenite (Foyaite), *Sierra de Monchique, Portugal.*
- 15 Nepheline syenite (Ditroite), *Ditro, Transylvania.*
- 16 *Hornblende syenite, *Plauen'scher Grund, Dresden.*
- 17 *Augite syenite (Olivine monzonite), *Kentallen, Scotland.*
- 18 Monzonite, *Monzoni, Tyrol.*
- 19 Quartz-enstatite-diorite, *Penmaen-mawr, Wales.*
- 20 Diorite, *Vosges, France.*
- 21 Quartz diorite, *St. Sampson's, Guernsey.*
- 22 *Hornblende-biotite-diorite, *Guernsey, Iroctolite, Coverack, Cornwall.*
- 23 Anorthosite, *Lewis, Essex Co., New York.*
- 25 Essexite, *Lennoxtown, Glasgow.*
- 26 Norite, *Auchenbradie Quarry, Aberdeen.*
- 27 Kimberlite, *Murfreesboro, Arkansas, U.S.A.*
- 28 Teschenite, *Inchcolm, Firth of Forth.*
- 29 *Dunite, *Mt. Dun, New Zealand.*
- 30 Lherzollite, *Arguenos, France.*
- 31 Cortlandtite, *Syracuse, New York.*
- 32 Pyroxenite (Bronzite), *N Carolina, U.S.A.*
- 33 *Augite picrite, *Inchcolm, Firth of Forth.*
- 34 *Serpentine, *Banff, Scotland.*
- 35 *Hypersthene gabbro (Hyperite), *Maud Junction, Aberdeen.*
- 36 *Gabbro, *Carrock Fell, Cumberland.*
- 37 Hypersthene gabbro, *St. Sampson's, Guernsey.*
- 38 Saussuritic gabbro, *Lendalfoot, Ayrshire.*
- 39 *Granophyre, *Mourne Mts, Ireland.*
- 40 Augite granophyre, *Carrock Fell, Cumberland.*
- 41 *Riebeckite eurite, *Ailsa Craig, Firth of Clyde.*
- 42 *Aplite, *Long Downs, Falmouth, Cornwall.*
- 43 Aplite, *Ennerdale, Cumberland.*
- 44 Spodumene-bearing elvan, *Co. Dublin.*
- 45 Mylonised elvan, *Co. Dublin.*
- 46 *Quartz porphyry, *Armboth Dyke, Thirlmere, Cumberland.*
- 47 Quartz porphyry, *Vosges, France.*
- 48 Quartz felsite, *St. John's Vale, Cumberland.*
- 49 Orthophyre, *Mid-Eildons, Nr. Melrose, Scotland.*
- 50 Keratophyre, *Kuabon, Wales.*
- 51 Porphyrite, *Eycott Hill, Cumberland.*
- 52 Andesite porphyry, *Newton, Mass, U.S.A.*
- 53 *Hornblende porphyrite, *Colvend, Dalbeattie.*
- 54 Bostonite, *Essex Co., New York.*
- 55 Solvsbergite, *Solvsberget, Norway.*
- 56 *Dolerite, *Clee Hill, Ludlow.*
- 57 *Dolerite, *Craiglochart, Edinburgh.*
- 58 Dolerite, *Pouk Hill, Walsall.*
- 59 Nepheline dolerite (Nephelinite), *Lobau, Saxony.*
- 60 Tachylitic edge of dolerite sill, *Dippin, Arran.*
- 61 Diabase (Gimlet Rock), *Pwllheli, Wales.*
- 62 Lugarite, *Lugar, Ayrshire.*
- 63 Mica-lamprophyre (Minette), *Sale Fell, Cumberland.*
- 64 Mica - lamprophyre (Minette), *Franklin Furnace, New Jersey, U.S.A.*
- 65 Limburgite, *Limburg, Kassertuhl.*
- 66 Alnoite (Mellinite basalt), *Spiegel River Valley, Cape Colony.*
- 67 Vogesite, *Glen Catacol, Arran.*
- 68 Vogesite, *Andlautal, Vosges Mts.*
- 69 *Eclogite, *Eppenreuth, Bavaria.*
- 70 *Spherulitic obsidian, *Isle of Lypart, Sicily.*
- 71 Obsidian, *Millard Co., Utah.*
- 72 *Pitchstone with microliths, *Corrie-Arran.*
- 73 Porphyritic pitchstone, *Corriegills, Arran.*
- 74 Pumice, *Millard Co., Utah, U.S.A.*
- 75 Rhyolite (Lea Rock), *Wellington, Salop.*
- 76 Spherulitic rhyolite, *Cloughmore, Co. Antrim.*
- 77 *Spherulitic rhyolite, *Long Sled-dale, Cumberland.*
- 78 Rhyolite showing fluidal structure, *Ballymena, Co. Antrim.*
- 79 Trachyte, *San Leonardo, Etna.*
- 80 Augite trachyte, *Peppercraig Hills, Haddington, Scotland.*
- 81 *Trachyte with sanidine, *Drachengfels, Siebenbrige.*

* See reference at foot of previous page.

Geological Supplies Department:

THOMAS MURBY & CO., 1, Fleet Lane, Ludgate Circus, London, E.C.4

THIN SECTIONS—continued.

- | | |
|--|---|
| <p>82 *Hypersthene andesite, <i>Dumyat, Stirling</i></p> <p>83 Biotite andesite, <i>Craigowerhouse, Auchtermuchty, Fife</i></p> <p>84 Hornblende andesite, <i>Glen Coe Pass, Argyllshire</i></p> <p>85 *Hornblende andesite, <i>Monarch, Chaffee Co., Colorado, U.S.A.</i></p> <p>86 *Hornblende andesite, <i>Mt Shasta, California</i></p> <p>87 *Hornblende andesite, <i>Wolkenberg, The Rhine</i></p> <p>88 Dacite, <i>Chemnitz, Saxony</i></p> <p>89 Variolitic basalt, <i>Weston-super-Mare, Somerset</i></p> <p>90 Glassy basalt, <i>Darmstadt, Germany</i></p> <p>91 *Porphyritic olivine basalt, <i>Arthur's Seat, Edinburgh</i></p> <p>92 Amygdaloidal basalt, <i>High Tor, Matlock</i></p> | <p>93 Phonolite, <i>Beacon Hill, Crispale Creek, Colorado</i></p> <p>94 *Nosean phonolite, <i>Wolf Rock, Cornwall</i></p> <p>95 *Leucite tephrite with hauyne, <i>Tavolato, Rome</i></p> <p>96 *Leucitophyre, <i>Rieden, Esfel.</i></p> <p>97 Epidosite, <i>Stornoway, Lewis, Scotland</i></p> <p>98 Melaphyre, <i>Vosges, France</i></p> <p>99 Kenyte, <i>Cape Roys, Ross Island, Antarctic</i></p> <p>100 Palagonite, <i>Tan-y-Craig, Wales</i></p> <p>101 Spilitic (Pillow lava), <i>Mulhous Island, The Lizard, Cornwall</i></p> <p>102 Volcanic agglomerate, <i>Arthur's Seat, Edinburgh</i></p> <p>103 *Calcareous tuff, <i>Goblin Combe, Weston-super-Mare</i></p> <p>104 Volcanic Ash, <i>Ison's Haunch, Arthur's Seat, Edinburgh</i></p> |
|--|---|

METAMORPHIC ROCKS.

- | | |
|--|--|
| <p>105 *Mica-schist with garnets, <i>Zaptau, Germany</i></p> <p>106 Mica-schist with tourmaline, <i>Ballycomus, Co. Antrim, Ireland</i></p> <p>107 Graphite - mica-schist, <i>McDowell Co., North Carolina, U.S.A.</i></p> <p>108 Talc schist, <i>St. Lawrence Co., New York, U.S.A.</i></p> <p>109 *Chlorite schist, <i>W. of Fortsoy, Banff, Scotland</i> [Dublin]</p> <p>110 Andalusite schist, <i>Killiney, Co. Wick</i></p> <p>111 *Actinolite schist, <i>Garron Point, Banff</i></p> <p>112 Hornblende schist, <i>Tregurthey, Cornwall</i></p> <p>113 *Glaucophane schist, <i>Nocchie, Susa, Italy</i></p> <p>114 *Cordierite - andalusite - gneiss, <i>Schinnokoppe, Riesengebirge</i></p> <p>115 Sillimanite - garnet - gneiss, <i>Nr. Hague, Warren Co., New York</i></p> | <p>116 *Kyanite granulite, <i>Rohrsdorf, Saxony</i></p> <p>117 Hornstone, <i>Charnwood Forest, Leicester</i></p> <p>118 *Ottrelite slate, <i>Ottrel, Belgium</i></p> <p>119 *Chistolite slate, <i>Skiddaw, Cumberland</i></p> <p>120 Clay slate, <i>Penrhyn Quarries, Nr. Bangor, Wales</i></p> <p>121 Clay slate, <i>Ballachulish, Argyllshire, Scotland</i></p> <p>122 Mylonite (crushed slate), <i>Balmacara, Skye</i></p> <p>123 *Crystalline limestone, <i>Carrara, Italy</i></p> <p>124 Garnetiferous greenstone, <i>Cam-bourne, Cornwall</i></p> <p>125 Greenstone with axinite, <i>Carrickdu, St. Ives, Cornwall</i></p> <p>126 Epidiorite, <i>Kennack, Cornwall</i></p> <p>127 Epidote bearing rock, <i>Shap, Westmorland</i></p> |
|--|--|

SEDIMENTARY ROCKS.

- | | |
|--|--|
| <p>128 *Normal quartzite, <i>Hartshill, Nuneaton, Warwickshire</i></p> <p>129 Torridon sandstone, <i>Assynt, Sutherland</i></p> <p>130 *Permian sandstone, <i>Grange Hill, West Kirby, Cheshire</i></p> <p>131 Glaucinite sandstone, <i>Hollybush Hill, Malvern</i></p> <p>132 *Glaucinite sandstone, <i>Upper Greensand, Swanage, Dorset</i></p> <p>133 Keuper sandstone, <i>Basement beds, Nr. Liverpool</i></p> <p>134 Millstone Grit, <i>Dunford Bridge, Yorkshire</i></p> <p>135 *Ferruginous sandstone, <i>Portland, Conn., U.S.A.</i></p> <p>136 Barytiferous sandstone, <i>Tegg's Nose, Nr. Macclesfield, Cheshire</i></p> <p>137 Ganister sandstone, <i>Lower Coal Measures, Bolton, Lancs.</i></p> <p>138 Serpula limestone, <i>Upper Greensand, Worbarrow Bay, Dorset</i></p> | <p>139 *Foraminiferal limestone, <i>Castleton, Derbyshire</i></p> <p>140 *Nummulitic limestone, <i>The Pyramids, Ghizeh, Egypt</i></p> <p>141 *Globigener limestone, <i>Athens, Cyprus</i></p> <p>142 Pisolitic limestone, <i>Colwall Copse, Malvern Hills</i> [Bath]</p> <p>143 *Oolite, <i>Upper Portland Beds</i></p> <p>144 *Normal Chalk, <i>Portrush</i></p> <p>145 *Dolomite, <i>Lummaton Quarry, Torquay</i></p> <p>146 Dolomite, <i>Little Falls, New York</i></p> <p>147 *Silicified oolite, <i>State College, Penn., U.S.A.</i></p> <p>148 Silicified oolite, <i>Centre Co., Penn., U.S.A.</i></p> <p>149 Oolitic ironstones, <i>Low Main Coal, Derbyshire</i></p> <p>150 Banded chert, <i>Upper Greensand, Great Haldon, Devon</i></p> |
|--|--|

Geological Supplies Department:

THOMAS MURBY & CO., 1, Fleet Lane, Ludgate Circus, London, E.C.4

MURBY'S BOOKS IN SCIENCE

SUMMARISED LIST SEPTEMBER, 1938

Books published since January, '36
and forthcoming books marked

Imported (agency) books marked † are subject
to variations in price owing to fluctuations in exchange

Postages are given for the guidance of the bookseller and the purchaser

THOMAS MURBY & CO., 1 FLEET LANE, LONDON, E.C.4
Telegrams. Murbyology, Cent, London, Cables. Murbyology, London, Telephone: Central 4821

AN INTRODUCTION TO GEOLOGY.

By A. E. TRUEMAN, D.Sc , F.G.S.

Professor of Geology in the University of Glasgow

Illustrated with 133 line drawings

4s. net Postage 4d.

This outline of Geology has been prepared primarily for use in schools. It covers the syllabus proposed for school courses by the British Association Committee on the Teaching of Geology. It is suitable for candidates preparing for the First School Certificate in Geology or for the Higher Certificate with Geology as a subsidiary subject. It deals in an elementary way with the whole range of the subject. Those sections in which pupils can make their own observations are emphasised.

The aim of the author has been to awaken an interest in simple geological phenomena and in their relation to human life, to show something of the history of the changes affecting scenery and land forms, and particularly to build up a time-scale so that the conception of a sequence of events can be followed.

CHAP.

CONTENTS.

- I. THE STUDY OF ONE'S SURROUNDINGS. Field work, introductory ideas about rocks and minerals, origin of valleys, soils, etc.
- II. WEATHERING, Ground Water
- III. THE GEOLOGICAL WORK OF RIVERS AND STREAMS
- IV. THE GEOLOGICAL WORK OF ICE.
- V. COASTS, SEAS AND OCEANS
- VI. THE COMMON MINERALS. A simple introduction to chemical composition and crystal form. Only about twenty common minerals are mentioned.
- VII. THE SEDIMENTARY ROCKS.
- VIII. THE ARRANGEMENT OF THE SEDIMENTARY ROCKS. I (Stratification, Dip and Outcrop)
- IX. THE ARRANGEMENT OF THE SEDIMENTARY ROCKS. II. (Folds, Faults, Unconformity)
- X. IGNEOUS ROCKS. Volcanoes. Metamorphic Rocks.
- XI. FOSSILS AND THEIR USES. The main groups are described in general terms and few generic names are introduced.
- XII. THE ROCKS OF BRITAIN. A short account of historical geology with some reference to the scenery produced by different formations.
- XIII. FURTHER ASPECTS OF PHYSIOGRAPHY. (River systems, peneplains, and other topics which are best understood in relation to historical geology.)
- XIV. EARTHQUAKES. EARTH MOVEMENTS. THE INNER EARTH.
- XV. SOME USES OF GEOLOGY.
- XVI. GEOLOGY IN THE FIELD. The book ends, as it begins, with an emphasis on field work. Various suggestions are made for observations which can be made in almost all areas.

Some reference is made to books for further reading and to suitable maps. Questions and suggestions for practical work follow each chapter.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

HANDBOOK OF THE GEOLOGY OF GREAT BRITAIN. Edited by J. W. EVANS, C.B.E., D.Sc., F.R.S., and C. J. STUBBLEFIELD, Ph.D. Contributors P. G. H. Boswell, D.Sc., A. Morley Davies, D.Sc., C. Davison, Sc.D., H. Dewey, J. W. Evans, C.B.E., D.Sc., F.R.S., E. J. Garwood, Sc.D., F.R.S., J. W. Gregory, D.Sc., F.R.S., A. Harker, F.R.S., O. T. Jones, D.Sc., F.R.S., P. F. Kendall, D.Sc., F.R.S., J. Parkinson, Sc.D., G. H. Plymen, Ph.D., Linsdall Richardson, F.R.S.E., G. Slater, D.Sc., H. C. Versey, D.Sc., W. W. Watts, Sc.D., F.R.S., W. B. Wright, Sc.D. "The book represents an authoritative conspectus of the present state of our knowledge of British Stratigraphy." xii + 556 pp., 24 Tables, 67 Figures. Full Bibliographies and Index. **24s. net.** Postage foreign 1s 2d. inland 7d.

STUDENT'S ISSUE of the above with same contents, bound in brown cloth, ink lettering, **20s. net.**

HANDBOOK OF THE GEOLOGY OF IRELAND. By the late PROFESSOR GRENVILLE A. J. COLE, D.Sc., F.R.S., M.R.I.A., Director of the Geological Survey of Ireland and T. HALLISSY, B.A., M.R.I.A., of the Geological Survey of Ireland **8s. 6d. net** postage 5d.

AN INTRODUCTION TO STRATIGRAPHY (British Isles). By L. DUDLEY STAMP, B.A., D.Sc., A.K.C., F.G.S. Second edition revised throughout and enlarged. **10s. net.** Postage inland 6d., abroad 7d.

● **THE DORSET COAST: A Geological Guide** By G. M. DAVIES, M.Sc., F.G.S. Cloth **6s. net.** In two parts (paper covers), Part I., Western Section, **2s. 6d. net.** Part II., Central and Eastern Sections, **3s. 6d. net.** Postage: Bound 4d., Parts 2d.

GEOLOGICAL SECTIONS OF PARTS OF THE DORSET COAST. By G. M. DAVIES, M.Sc., F.G.S. (i.) Cliff Sections from Pinhay Bay to Burton Cliff (ii) Vertical Section of the Jurassic Rocks of S.W. Dorset. (iii) Section through Black Ven 50 sets of three diagrams, **13s. 6d.** 25 sets, **7s.** Single sets, **4d.**

● **THE GEOLOGY OF LONDON AND SOUTH-EAST ENGLAND.** By G. M. DAVIES, M.Sc., F.G.S. Well illustrated with text figures and half-tone plates. *In preparation.*

UNDERGROUND SOUTH-EASTERN ENGLAND. A Three-Dimensional Map of the Weald, London Basin and Chiltern Hills. By L. J. CHUBB, M.Sc., F.G.S. In coloured sheets to be made up. **12s. 6d. net.** Binding equipment 2s. Made up **35s.** Postage Sheets, inland 6d., abroad 10d. Made up, inland 6d., abroad 10d.

THE IGNEOUS ROCKS OF THE MOUNTSORREL DISTRICT. By E. E. LOWE, B.Sc., Ph.D. **6s. 6d. net,** postage 3d.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

Regional Geology

MAP OF THE BRITISH ISLES with Geological Boundaries. For students to colour 2d. each, postage 1d. 1s. 3d. per doz., 14s. per gross, postage extra.

GEOLOGICAL MAP OF THE BRITISH ISLES. In 10 colours. Natural Scale 1 : 3,500,000. 2½d., postage 1d.

LOCAL GEOLOGY. A Guide to Sources of Information on the Geology of the British Isles. By A. MORLEY DAVIES., D Sc., F.R.G.S., F.G.S. 2nd Edition revised 1927. 1s net, postage 1d.

● **GEOLOGY OF CHINA.** By J. S. LEE, D.Sc., Professor of Geology in the Peking University. The book deals with the physical geography, stratigraphy and tectonics of China, with a discussion on wider problems of continental movement. Numerous maps, diagrams and half-tone illustrations of fossils and land-forms. *In the press.*

● **LEXICON DE STRATIGRAPHIE. VOL. I. : AFRICA.** Compiled by a Commission appointed by the XVth International Geological Congress. 31s. 6d. Postage : inland 6d , foreign 9d.

● **GEOLOGY OF S.W. ECUADOR.** By Dr G. SHEPPARD, State Geologist of the Republic of Ecuador, with a Chapter on the Tertiary Larger Foraminifera of Ecuador by Dr. T. WAYLAND VAUGHAN. Deals with the Physical Geography and Stratigraphy of the area; and with the Petroleum Geology. 25s. net. Postage : inland 6d , foreign 7d.

● † **GEOLOGY OF THE TAMPICO REGION, MEXICO.** By JOHN M. MUIR. 300 pp , 15 half-tone plates, 41 line drawings, 9 tables. 19s. 6d.

● † **GULF COAST OIL FIELDS.** A Symposium on Gulf Coast Cenozoic. By 52 authors. Chiefly papers reprinted from the *Bulletin of the American Association of Petroleum Geologists*. 1,100+ pp., 292 figs, 19 half-tone plates. Present price 18s. 6d. Postage : inland 8d., foreign 1s. 4d.

MIOCENE STRATIGRAPHY OF CALIFORNIA By ROBERT M. KLEINPELL. Upwards of 300 pages, 22 plates of fossil figures, 14 line drawings, 20 tables and charts. \$5. Present price 22s. 6d. *In the Autumn* This is a publication of the American Association of Petroleum Geologists.

† **THE GEOLOGY OF VENEZUELA AND TRINIDAD.** By RALPH ALEXANDER LIDDLE. xxix. + 552 pp 709 illustrations , 24 sections and maps, \$7.50. Present price 33s. 6d. Postage : inland 7d , foreign 1s. 3d.

† **THE STRUCTURAL EVOLUTION of SOUTHERN CALIFORNIA.** By H. D. READ and J. S. HOLLISTER. \$2. Present price 9s. The coloured map (24in x 31in.) may be had separately. 50 cents. (2s. 6d), postage 6d., map 2d.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

Regional Geology

- † **GEOLOGICAL MAP OF THE WORLD.** Edited by FRANZ BEYSCHLAG. With the co-operation of the Prussian Geological Survey. Twelve Sheets, average scale of 1:15,000,000, with colour key on a separate sheet. The present price of the entire map of 12 sheets, and sheet of explanations of conventional signs, is **£10 10s.** Postage extra. Supplied only in complete set.
- † **GEOLOGIE DE LA MÉDITERRANÉE OCCIDENTALE.** Published under the direction of Prof. J. MARCET RIBA.
- Vol. I. 1929-30. **Le XIVe Congrès Géologique International et les excursions dans les Pays Catalans.** xlv + 252 pp. **£1 12s.**
- Vol. II. 1930-32. **Communications faites sur la Région Catalans à l'occasion des Excursions du Congrès** Nos. 1-48. 575 pp. **50s.**
- Vol. III. 1930-37. **Etudes sur la Minéralogie et la Géologie de la Région Catalane.** 382 pp. **65s.**
- Vol. IV. **Les Chaînes Bétique et Subbétiques.** 312 pp. **50s.**
- Vol. V. **Les Chaînes Nord Africaines.** 136 pp. **32s.**
- † **Bibliographie Général du Congrès Géologique International (XIVe Session, Espagne).** 1s 6d
- † **Bibliographie Géologique du L'Espagne** 2s. 6d. net.
- † **Montserrat.** Esquisse physiographique illustrée. 1s. 6d.
- † **Region Volcanique d'Olot.** 5s.
- † **Regio Volcanica Catalana.** 3s.
-

Palæontology

- AN INTRODUCTION TO PALÆONTOLOGY.** By A. MORLEY DAVIES, A.R.C.S., D.Sc., F.G.S., Assistant Professor of Palæontology, Imperial College of Science. Now **10s. 6d.** net, postage 5d.
- TYPE AMMONITES.** By S. S. BUCKMAN. Published in 72 parts, of which some are now out of print. **9s.** per part.
- **TERTIARY FAUNAS.** A text-book for Oilfield Palæontologists and Students of Geology. By A. MORLEY DAVIES, A.R.C.S., D.Sc. F.G.S. *Vol. II., THE SEQUENCE OF TERTIARY FAUNAS.* 15s. net. Postage: inland 6d., foreign 8d. *Vol. I., THE COMPOSITION OF TERTIARY FAUNAS.* 22s. 6d. net. Post: inland 6d., abroad 10d.
- **EVOLUTION AND ITS MODERN CRITICS.** By A. MORLEY DAVIES, D.Sc. Designed primarily as a reply to Mr. Dewar, the author of *Difficulties of the Evolution Theory*. In England of late years the literary disbelievers have become more assertive, encouraged by the rejection of the theory by two or three qualified biologists. **7s 6d.** net, postage 5d.
- THE DINOSAURS.** A Short History of a Great Group of Extinct Reptiles. By W. E. SWINTON, Ph.D., F.G.S., F.R.S.E. of the Department of Geology, British Museum (Natural History). Fully illustrated. **15s.** net Postage: inland 6d., foreign 8d.
-

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

METHODS IN GEOLOGICAL SURVEYING. By DR. E. GREENLY and Dr HOWEL WILLIAMS. 17s. 6d. net. Postage inland 6d., foreign 10d

DIP AND STRIKE PROBLEMS, mathematically surveyed By KENNETH W. EARLE, D.Sc., F.G.S. Deals with the trigonometrical, geometrical and graphical solution of such problems as are likely to confront the practical and mining geologist in the field 12s. 6d. net, postage 5d.

● **A SERIES OF ELEMENTARY EXERCISES UPON GEOLOGICAL MAPS.** By JOHN I. PLATT, M.Sc., F.G.S. 2nd Edition (*revised and enlarged*). 1s. 6d., postage 3d

SINGLE MAPS. The following exercises are available in single sheets Nos 2, 4, 6, 7, 8, 12, 13, 17, 19, 22, 24 and 26. Prices 9d. a dozen for any map of which less than a gross is ordered, 8s. a gross for any one map of which a gross or more is ordered

SIMPLE GEOLOGICAL STRUCTURES. A Series of Notes and Map-Exercises. By JOHN I. PLATT, M.Sc., F.G.S., and JOHN CHALLINOR, M.A., F.G.S. 3s. 6d. net, postage 3d

NOTES ON GEOLOGICAL MAP READING. By A. HARKER, LL.D., F.R.S., F.G.S., with 40 illustrations. 3s. 6d. net, postage 3d.

PROFILE SHEETS, for drawing sections from Contour Maps, 1d. each, 10 for 6d., postage 1½d., 100 for 4s. 6d., postage 6d.

Crystallography

ELEMENTARY CRYSTALLOGRAPHY By J. W. EVANS, D.Sc., F.R.S., F.G.S., and G. MACDONALD DAVIES, M.Sc., F.G.S. 7s. 6d. postage 4d.

PATTERNS FOR THE CONSTRUCTION OF 36 CRYSTAL MODELS REPRESENTING ACTUAL MINERALS. Designed by F. SMITHSON, Ph.D., F.G.S. 4s. net, postage 2d., cards for mounting 1s., mounted 7s. 6d., postage 3d. Models made up 32s.

CRYSTALLOGRAPHIC NETS for constructing 41 models representing simple forms. With instructions 3s. net, postage 1d.; on card ready for making into models, 7s. 6d. net, made-up, price 23s.

GRAPHICAL AND TABULAR METHODS IN CRYSTALLOGRAPHY. By T. V. BARKER, 14s. net, postage 5d.

THE STUDY OF CRYSTALS. A general Introduction. By T. V. BARKER. 8s. 6d. net, postage 6d.

SYSTEMATIC CRYSTALLOGRAPHY. An Essay on Crystal Description, Classification and Identification. By T. V. BARKER, 7s. 6d. net, postage 6d.
Stereographic Nets. 24 sheets. 3s.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

Mineralogy and Petrology

- **RUTLEY'S MINERALOGY.** 23rd edition. Revised and enlarged. By H. H. READ, A.R.C.S., D.Sc., Herdman Professor of Geology in the University of Liverpool. Many illustrations have been redrawn and a large number added. The value of the book as an introduction to Mineralogy for the student of Geology or Mining is greatly increased. 8s. net, postage 6d.
- A HISTORY OF THE THEORY OF ORE DEPOSITS, with a Chapter on the Rise of Petrology** By THOMAS CROOK, 10s. 6d. net, postage 6d.
- ORE DEPOSITS OF MAGMATIC ORIGIN: Their Genesis and Natural Classification.** By Prof PAUL NIGGLI. Translated by Dr. H. C. BOYDELL, M.I.M.M. Revised and supplemented by Dr. Niggli and Dr. R. L. Parker 9s. 6d. net, postage 6d.
- MINERALS AND THE MICROSCOPE.** An introduction to the study of Petrology. By H. G. SMITH, A.R.C.S., B.Sc., F.G.S., THIRD EDITION with the section on Petrology re-written and enlarged. Plates and text figures. 5s. net, postage 4d.
- THE DETERMINATION OF MINERALS UNDER THE MICROSCOPE.** By JOHN W. EVANS, C.B.E., D.Sc., F.R.S., F.G.S., Coloured plate and many line drawings 7s. 6d. net, postage 4d.
- THE DETERMINATION OF THE FELDSPARS IN THIN SECTION.** By DR. K. CHUDOBA Translated by Dr. W. Q. KENNEDY. Cloth 6s. 6d. net., paper 4s. 6d. net, postage 4d.
- DIAMOND: A DESCRIPTIVE TREATISE** By J. R. SUTTON, M.A., Sc.D. Gives results of observations made during 35 years or so on South African diamond 111 illustrations. 15s. net, postage 5d.
- OPAL: The Gem of the Never Never** By T. C. WOLLASTON, 14 plates (3 beautiful reproductions in colour). Part I., Australia's National Gem, Part II., On the Trail of the Opal, Part III., Sketches of Opal Field Characters 10s. 6d. net, postage 5d.
- THE NOMENCLATURE OF PETROLOGY.** By ARTHUR HOLMES, D.Sc., A.R.C.S., D.I.C., F.G.S., Professor of Geology, Durham. 2nd and cheaper Edition. 7s. 6d. net, postage 5d.
- PETROGRAPHIC METHODS AND CALCULATIONS.** By Prof. ARTHUR HOLMES, D.Sc., A.R.C.S., D.I.C., F.G.S. Second impression. 15s. net Postage inland 6d., foreign 10d.
- DR. HOLMES' FORM FOR THE CALCULATION OF THE NORM OR STANDARD MINERAL COMPOSITION.** 12 Forms. 1s. 9d. net, postage 2d.
- METHODS IN PRACTICAL PETROLOGY.** By H. B. MILNER, B.A., F.G.S., and G. M. PART, B.A., F.G.S. Hints on the Preparation and Examination of Rock Slices. Illustrated. 3s. 6d. net, post. 3d.
- THE STUDY OF ROCKS.** By Prof. S. J. SHAND. An account of the Petrology of Eruptive, Sedimentary and Metamorphic rocks for students who have already made a beginning with elementary geology. 6s. net, postage 5d.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

ERUPTIVE ROCKS. Their Genesis, Composition, Classification and their Relation to Ore Deposits. By Professor S. J. SHAND. 44 illustrations. 20s. net. Postage: inland 6d., foreign 9d.

INSTRUCTIONS FOR USING THE QUANTITATIVE MINERALOGICAL CLASSIFICATION OF ERUPTIVE ROCKS. By Prof. S. J. SHAND 1s. 3d. net, postage 1d. Explains the application of the classification proposed in *Eruptive Rocks*.

† ASSIMILATION AND PETROGENESIS. Separation of Ores from Magmas. By Prof. J. STANSFIELD. (Valley Publishing Co., Urbana.) \$4.50 net. Present price 18s. 6d., postage 6d.

LIMESTONES. Their Origins, Distribution and Uses. By F. J. NORTH, D.Sc., F.G.S., Keeper in the Department of Geology. National Museum of Wales. 16s net. Postage. inland 6d., foreign 10d.

ON THE MINERALOGY OF SEDIMENTARY ROCKS. A Series of Essays and a Bibliography. By Professor P. G. H. BOSWELL, O.B.E., D.Sc., F.R.S., M Inst M M., A.R.C.S., D.I.C., 21s. net. Postage: inland 6d, foreign 9d.

CARD INDEX OF ABSTRACTS. Reprinted from the above. Over 1,000 abstracts, on one side of the paper, for card index 10s. 6d. net, postage 4d.

● **SEDIMENTARY PETROGRAPHY.** By HENRY B. MILNER, M.A., D.I.C., F.G.S., M.Inst.P.T In the press. Probably Autumn.

ALLUVIAL PROSPECTING. The Technical Investigation of Economic Alluvial Minerals By C. RAEBURN, D.Sc., F.G.S., Geological Survey of Nigeria, and HENRY B. MILNER, M.A. (Cantab.), D.I.C., F.G.S., M Inst.P.T. Foreword by J D. FALCONER, M A., D.Sc., F.G.S., F.R.G.S., late Director of the Geological Survey of Nigeria. 36s. net. Postage. inland 6d., foreign 1s.

● **REGIONAL PETROLOGY OF THE SOUTHERN NORTH SEA.** By J. A. BAAK Gives the results of the mineralogical examinations of more than 1,000 samples from the floor of the North Sea. 8s. 6d. net, postage 4d.

● **SILICATE ANALYSIS: A Manual for Geologists and Chemists, with Chapters on Check Calculations and Geo-Chemical Data.** By A. W. GROVES, D.Sc., Ph.D., D.I.C., F.G.S. Foreword by Prof. ARTHUR HOLMES. 12s. 6d. Postage: inland 6d., foreign 7d.

● **† METASOMATISCHE PROBLEME** (In German). (Mount Isa, Rammelsberg, Meggen, Mansfeld und Kunstliche Verdrangung). By Dr. IR. C. SCHOUTEN. 148 pages, 20 plates with 174 photo-micrographs and 3 figures in text. Price 8s. 6d. net.

THE STONES OF LONDON. By J. VINCENT ELSDEN, D.Sc., F.G.S., and J. ALLEN HOWE, O B.E., B.Sc, F.G.S., M.I.M.M. A Guide to the stones used in London. 1s 3d. paper, postage 8d.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

- **AN INTRODUCTION TO GEOLOGY.** By A. E. TRUEMAN, D.Sc., F.G.S., Professor of Geology in the University of Glasgow. This book covers the syllabus proposed for school courses by the British Association Committee on the Teaching of Geology. 4s. net, postage 4d.

- **EARTH-LORE: Geology without Jargon** By Professor S. J. SHAND, D.Sc., F.G.S. A broad survey of geology for the general reader, 2nd Edition. Revised and enlarged 16 plates, 33 text figures. Now 3s. 6d. net, postage 4d
The sales of this book in U.S.A. and Canada are in the hands of E. P. Dutton Company, Inc., N.Y.

GEOLOGICAL MODELS. By FRANK SMITHSON, Ph.D., F.G.S.
Particulars of made up Models, etc., on application.

BLOCK MODELS. Patterns for Construction and Notes.

1st SERIES (Faulting, Folding, etc.), 12 models. 1s. 6d. net, postage 1d.

2nd SERIES (Igneous Phenomena, etc.); 14 models. 1s. 6d. net, postage 1d.

SIMPLE RELIEF MODELS. Patterns. 5s. 6d net, postage 5d.

Brochures for Teachers of Geography by Dr. L. Dudley Stamp.
Descriptive two collections (of 30 specimens in each).

NOTES ON COMMON ROCKS 6d. net, postage ½d.

NOTES ON SOME ECONOMIC MINERALS AND ROCKS. 6d. net, postage ½d. *Reprinting.*

A GEOLOGICAL CHART. By COL. F. G. TALBOT. Suitable for hanging in the Class Room Gives in clear and simple form the main outlines of geological history. 1s. 4d. net, postage 2d.

† **OUTLINES OF GLACIAL GEOLOGY.** By F. T. THWAITE., University of Wisconsin. (Photo-Lithoprint of Typewritten Manuscript, 1934) 115 pp., with 89 Figures. 12s. 6d. net, postage 6d *New edition now ready.*

MEMO-MAPS. Small blank maps for use with geological and other collections for recording geographical distribution, and for other uses 25 of one kind, 6d net, postage 1d., 1,000 15s.
World Western Europe, British Isles, England and Wales (with county boundaries), Scotland (with county boundaries), Asia, India, Africa, North America, South America, Australia

LOCAL GEOGRAPHY. By C. G. BEASLEY, B.A. 1s. net, postage 1d.
The ideal guide for Schools undertaking Regional Surveys.

THE RIVER SEVERN FROM SOURCE TO MOUTH. By M. LANCHESTER. Starting at the peat bog in which the Severn rises, the authoress tramped the whole distance to the river-mouth. 58 sketches and map. 2s. 6d. net, postage 4d.

USEFUL ASPECTS OF GEOLOGY: An Introduction to Geological Science for Engineers, Mining Men and all interested in the Mineral Industries. By Professor S. J. SHAND, 2nd Edition, revised and extended. 6s. net, postage 4d

A PRACTICAL HANDBOOK OF WATER SUPPLY. By F. DIXEY, D.Sc., F.G.S., Director of the Geological Survey, Nyasaland. A handbook describing the geological and other aspects of water supply. 21s. net. Postage inland 6d, foreign 1s.

Alluvial Prospecting By C. RAEBURN, D.Sc., and H. B. MILNER, M.A. See p. 8.

● **↑GEOLOGY OF NATURAL GAS: A Symposium.** Edited by HENRY A. LEV. xii. + 1227 pp. Numerous illustrations \$6.00. Present price 25s. 6d net. Postage inland 8d, abroad 1s. 4d. Consists of thirty-eight papers prepared by forty-seven authors.

● **↑COMPREHENSIVE INDEX OF THE PUBLICATIONS OF THE AMERICAN ASSOCIATION OF PETROLEUM GEOLOGISTS** from 1917-1936, covering the *Bulletin* and other A.A.P.G. Publications 392 pages double col 13s. 6d Postage. inland 7d, abroad 10d

Also for the General Reader

↑AUTOBIOGRAPHY OF EARTH. By T. H. BRADLEY. A light and interesting account of the Earth's history, written by a man with a genuine gift for vivid description. A sustained sense of drama dominates the book. The impressionist illustrations are in keeping with the author's style. \$3.00. Present price 15s. Postage. inland 6d., abroad 8d.

● **A HAND THROUGH TIME; Memories — Romantic and Geological; Studies in the Arts and Religion; and the grounds of Confidence in Immortality.** By EDWARD GREENLY. Liberally illustrated. In two volumes. 18s net. Postage inland 8d, foreign 1s. 6d.

This book tells of a Victorian girlhood and boyhood, of 36 years of a happy married life, of work on the Geological Survey, and gives sketches of the greatest geologists of the period. It deals also with the literary, political, and religious interests of the author and his wife, and closes with the author's confidence in immortality.

THE POETRY OF GEOLOGY. By KENNETH KNIGHT HALLOWES, M.A. Consists of an essay on the Poetry of Geological Science and thirty poems by the author. 6s. net, postage 3d.

OTHER BOOKS of interest to the general reader

Useful Aspects of Geology. By Professor Shand. (p. 10), **Earth Lore.** By Professor Shand (p. 9), **The Dinosaurs** By Dr. W. E. Swinton. (p. 5); **Limestones.** By Dr. F. J. North. (p. 8), **Opal.** By T. C. Wollaston. (p. 7); **Evolution and its Modern Critics.** By Dr. A. M. Davies. (p. 5).

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

Geological Terminology

GERMAN-ENGLISH GEOLOGICAL TERMINOLOGY. By W. R. JONES, D.Sc., F.G.S., M.I.M.M., and Dr. A. CISSARZ. An introduction to German and English terms used in Geology. 12s. 6d. net. Postage. inland 6d., foreign 7d.

The above is uniform with the *German-English Terminologies* in *Chemistry, Botany and Physics*. See pp 14 and 16.

The Nomenclature of Petrology. By Prof. A. Holmes. See p 7.

A FRENCH-ENGLISH VOCABULARY IN GEOLOGY AND PHYSICAL GEOGRAPHY. By G. MACDONALD DAVIES, M.Sc., F.G.S. 6s. net, postage 3d.

Seismology

● **GREAT EARTHQUAKES** By C. DAVISON, Sc.D., F.G.S. Describes and records scientific data of the world's great earthquakes; the Lisbon Earthquake of 1755 to the Hawkes Bay (New Zealand) Earthquake of 1931. (The Great Japanese Earthquake (1923) is not described here, having been described in an earlier volume) 17s. 6d. Postage. inland 6d., foreign 7d.

THE JAPANESE EARTHQUAKE OF 1923. By C. DAVISON, Sc.D., F.G.S. Describes the great Japanese disaster and deals with this earthquake as an event in the history of the earth. 40 diagrams. 7s. 6d. net, postage 6d.

● **STUDIES IN THE PERIODICITY OF EARTHQUAKES.** By C. DAVISON, Sc.D., F.G.S. The author has revised and considerably extended his studies on the periodicity of earthquakes 13s. 6d. net, postage 4d.

Geology—Periodicals

† **ANNOTATED BIBLIOGRAPHY OF ECONOMIC GEOLOGY.** For all subjects bearing on Economic Geology. \$5.00 per year.

† **ECONOMIC GEOLOGY.** Annual Subscription \$5.75

† **INDEX OF "ECONOMIC GEOLOGY."** A ten-volume index, covering volumes XXI-XXX \$2 10. Present price 9s

† **BULLETIN OF THE AMERICAN ASSOCIATION OF PETROLEUM GEOLOGISTS.** Monthly. Subscription \$15 40 per annum.

Soil Science—Bi-monthly

SOILS AND FERTILIZERS. A periodical issued every two months, incorporating the *Monthly Letters* of the Imperial Bureau of Soil Science, about 400 abstracts of newly published methods, and *Summaries of Recent Reports*—Nos 1 to 3 ready. Subscription rate, (foreign) ordinary edition, 25s. per annum; single copies British and foreign, 5s.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

SOIL SCIENCE

- **MOTHER EARTH.** Letters on Soil, addressed to Prof. R. G. STAPLEDON, C.B.E., M.A., by Prof. G. W. ROBINSON, Sc.D., Author of *Soils*. This book sets forth in terms intelligible to the general reader modern views on the soil 5s. 6d. net. Postage 5d.
- **SOILS. Their Origin, Constitution and Classification.** An Introduction to Pedology. By G. W. ROBINSON, Sc.D., Professor of Agricultural Chemistry in the University College of N. Wales, Bangor. *Second edition revised, 1936. Reprinted 1938.* 20s. net. Postage: inland 6d., foreign 9d.
- **SOIL ANALYSIS A Handbook of Physical and Chemical Methods.** By C. H. WRIGHT, M.A., F.I.C., former Senior Agricultural Chemist, Nigeria. *Second edition. In preparation.*
- ‡ **THE GREAT SOIL GROUPS OF THE WORLD, AND THEIR DEVELOPMENT.** By Prof. Dr. K. D. GLINKA, Director of the Agricultural Institute, Leningrad. Translation by C. F. MARBUR, 235 pp., Mimeographed 1928 33.25. Present price 15s. Postage: inland 6d., foreign 8d.
- **THE CYCLE OF WEATHERING.** By Prof. B. B. POLYNOV, of the Dokuchaiev Soil Institute, Moscow, corresponding member of the Academy of Sciences. U.S.S.R. Translated by Dr. ALEXANDER MUIR, of the Macaulay Institute of Soil Research, Aberdeen. 10s. 6d. net. Postage: inland 6d., foreign 3d.
- THE KATAMORPHISM OF IGNEOUS ROCKS UNDER HUMID TROPICAL CONDITIONS.** By the late Prof. SIR J. B. HARRISON (late Director of Science and Agriculture, Government Analyst and Geologist, British Guiana). Foreword by SIR J. E. RUSSELL. Preface by Prof. F. HARDY 79 pp. 5s. net. An important work on rock weathering and soil formation.
- **THE PRINCIPLES OF SOIL SCIENCE.** By Professor A. A. J. DE' SIGMOND, Professor of Agricultural Technology, University of Technical Sciences, Budapest. English edition. 22s. 6d. net. Postage: inland 6d., abroad 10d.
- **SOILS OF THE LUSITANO-IBERIAN PENINSULA.** By Prof. EMILE H. DEL VILLAR. In Spanish and English (English translation by Prof. G. W. ROBINSON). Price 40s. for countries outside Spain. Postage inland 6d., abroad 1/- . *The map in 17 colours to accompany this volume will be ready shortly.*
- **A PROVISIONAL SOIL MAP OF EAST AFRICA** (Kenya, Uganda, Tanganyika, and Zanzibar) with memoir by G. MILNE. 5s. Postage 3d.
- **INTERNATIONAL SOIL MAP OF EUROPE, 1:2,500,000.** The present price of the map is: (a) not mounted, 12 sheets, £10, (b) as a wall map mounted on linen with rods and rings, £12. Postage extra.
This map, produced by the International Society of Soil Science, is a development of the smaller scale map published in 1927. The new map is based entirely on actual field surveys, and has a more detailed nomenclature.

Thomas Murby & Co. 1, Fleet Lane, Ludgate Circus, London, E.C.4

BIBLIOGRAPHY OF SOIL SCIENCE, FERTILIZERS AND GENERAL AGRONOMY 1931-1934. Over 6,000 references to papers, bulletins and reports published throughout the world. Entries carefully classified according to Universal Decimal System of Classification. Compiled by the IMPERIAL BUREAU OF SOIL SCIENCE. 504 pp. Cloth, 25s. net.

BIBLIOGRAPHY OF SOIL SCIENCE FERTILIZERS, AND GENERAL AGRONOMY, 1934-1937. Contains 7,500 references to papers published during period and embraces every subject directly or remotely connected with the soil. There is an author index of 4,500 names. 556 pp. Price 25s. net.

TECHNICAL COMMUNICATIONS OF THE IMPERIAL BUREAU OF SOIL SCIENCE : Nos. 24—33. 2s., No. 34, 2s. 6d.

No. 24, Laterite and Laterite Soils, No. 26, The Dispersion of Soils in Mechanical Analysis, No. 27, Land Amelioration in Germany, No. 28, Soil Erosion (By T. Eden), No. 29, Soil, Vegetation and Climate, No. 30, The Determination of Exchangeable Bases in Soils; No. 33, Organic Manures (By S. H. Jenkins, Ph.D., F.I.C.), ● No. 34, Tropical Soils in relation to Tropical Crops, ● No. 35, The Design and Analysis of Factorial Experiments (By F. Yates, M.A.), 5s., ● No. 36, Erosion and Soil Conservation (By G. V. Jacks and R. C. Whyte), 5s., No. 37, Soil Structure (By Dr. E. W. Russell) 2s. Ready Particulars of Nos 7 to 23 on application.

TRANSACTIONS OF THE THIRD INTERNATIONAL CONGRESS OF SOIL SCIENCE (1935), held at Oxford, July 30th to August 7th. Subjects dealt with: Soil Physics, Soil Chemistry, Soil Microbiology; Soil Fertility; Soil Genesis, Morphology and Cartography, Soil Technology.

Vol. I—COMMISSION PAPERS 440 pp. In paper covers.
To members of the International Society of Soil Science, 23s. net. To non-members, 28s. net.

Vol. II—PLENARY SESSION PAPERS AND PRESIDENTIAL ADDRESS 200 pp. In paper covers.
To members, 11s. net. To non-members, 13s. net.

● Vol. III—PLENARY AND COMMISSION PAPERS, DISCUSSIONS, COMMISSION AND OTHER REPORTS. 290 pp. In paper covers.

To members, 16s. net. To non-members, 19s. net

Postage: inland 8d., foreign 1s. 4d

†PROCEEDINGS OF THE SECOND INTERNATIONAL CONGRESS OF SOIL SCIENCE, Leningrad (Moscow, U.S.S.R., 1930).

VOL. I—Soil Physics (1932)	Pp. xxxi + 304	13s.
" II.—Soil Chemistry (1933).	Pp. xxiv + 225	8s. 6d.
" III—Soil Biology. (1932)	Pp. xix + 303	13s.
" IV.—Soil Fertility (1932)	Pp. xviii + 264	13s.
" V—Classification, Geography and Cartography of Soils. (1932).	Pp. xxiii + 424	17s.
" VI.—Application of Soil Science to Agricultural Technology. (1932).	Pp. xxii + 320	13s.
" VII—General Plenary Sessions, Excursions		8s. 6d.

Fuller particulars of the above and of other publications of the Soviet Section of the International Society of Soil Science will be sent on application.
Postage approx. inland 6d., foreign 9d., per vol.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

- **THE SOILS OF PALESTINE.** By Dr. A. REIFENBERG *Now Ready.*
14s. Postage 4d.

**GUIDE-BOOK FOR THE EXCURSION ROUND BRITAIN OF
THE THIRD INTERNATIONAL CONGRESS OF SOIL
SCIENCE, 1935.** iv. + 74 pp. 2s. 6d. net.

† **ADDITIONAL PUBLICATIONS OF THE SOVIET SECTION
OF THE INTERNATIONAL SOCIETY OF SOIL SCIENCE.**
Pedology in USSR, 1935, 7s. Soil Microbiology in the USSR, 1933, 7s.
Bodenfruchtbarkeit und Anwendung der Dünger in der UdSSR., 1933, 8s.
Bodenchemie in der UdSSR, 1934, 4s. 6d. The Problem of Soil Structure,
1933, 4s. 6d. Problemes de la Physique du Sol, 1934, 8s. Classification
Geography and Cartography of Soil in USSR. (awaiting price).

† **POTASH DEFICIENCY SYMPTOMS** By Prof. OSCAR ECKSTEIN,
ALBERT BRUNO and J. W. TURRENTINO In German, French
and English. 55 plates in colour, 41 figures 8s. Postage .
inland 6d., foreign 10d. *Out of print. New edition in preparation.*

- **AGRICULTURAL ANALYSIS:** A Handbook of Methods excluding
those for Soils By C. H. WRIGHT, M.A., F.I.C., Author of
Soil Analysis. Gives the working details of the methods of
analysis of fertilisers, feeding stuffs, milk, milk products, insecti-
cides and fungicides. For advanced students and agricultural
chemists. 16s. net. Postage : inland 6d , foreign 8d.

- **AN OUTLINE OF FORESTRY.** By THOMAS THOMSON, M.Sc.,
Head of the Department of Forestry, University College of
N. Wales, Bangor, and R. M. K. JERRAM, M.C., Late Indian
Forest Service, Assistant Lecturer in Forestry, University College
of N. Wales. Deals with : (i) Forest Policy, (ii) Forest Bionomics,
(iii) Forest Economics, (iv) Forest Management. *In the press.*

BIOLOGY

- **GERMAN-ENGLISH BOTANICAL TERMINOLOGY.** By Dr
E. & Prof. H. ASHBY, Dr. H. RICHTER and Dr. BÄRNER
A concise account of Botany in parallel texts of German and
English *Probably ready in Autumn.*

- **GERMAN-ENGLISH ZOOLOGICAL TERMINOLOGY.** By T. L.
GREEN, B.Sc., A.R.C.S., and J. M. WATSON, A.R.C.S., and
Dr. HEINZ GRAUPNER *In preparation*

THE WOAD PLANT AND ITS DYE. By J. B. HURRY, M.A.,
M.D. 360 pages, 2 coloured plate and numerous other plates and
text figures 21s net Postage : inland 6d , foreign 9d.

PSYCHOLOGY

- **WHEN TEMPERAMENTS CLASH.** A Study of the Components
of Human Temperaments By MURDO MACKENZIE, 7s. 6d net
Postage 5d.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

LAND UTILISATION and Regional Survey

MAPS OF THE UTILISATION SURVEY OF GREAT BRITAIN.

Prepared by the Land Utilisation Survey under the Directorship of Dr. L. DUDLEY STAMP, B.A., F.G.S., from a field survey. Prices. Flat and unmounted, 4s. net (post free, 4s. 3d.). Mounted on linen and folded in covers, 5s. net (post free, 5s. 2d.). Set of first 12 sheets, unmounted, 36s. net (post free, 36s. 6d.) mounted 45s. net.

ONE-INCH MAPS

ENGLAND AND WALES.—No. 7 Newcastle-on-Tyne, 11 Durham and Sunderland, 12 Keswick and Ambleside, 29 Preston, Southport and Blackpool, 30 Blackburn, 35 Liverpool and Birkenhead, 36 Bolton and Manchester, 37 Barnsley, 43 Chester, 44 Northwich and Macclesfield, 46 The Dukeries, 54 Nottingham, 55 Grantham, 56 Boston, 57 Fakenham, 58 Cromer, 62 Burton and Walsall, 63 Leicester, 64 Peterborough, 65 Wisbech, 66 Swaffham, 67 Norwich and Great Yarmouth, 72 Birmingham, 76 Thetford, 77 Lowestoft and Waveney Valley, 81 Worcester, 82 Stratford-on-Avon, 84 Bedford, 87 Ipswich, 88 St David's and Cardigan, 95 Luton, 96 Hettford and Bishop's Stortford, 99 Pembroke and Tenby, 100 Llanelli, 101 Swansea and Aberdare, 102 Newport, 103 Stroud and Chepstow, 105 Watford and N.W. London, 107 N.E. London and Epping Forest, 108 Southend-on-Sea, 109 Pontypridd and Barry, 112 Marlborough, 113 Reading and Newbury, 114 Windsor, 115 S.E. London and Sevenoaks, 117 East Kent, 120 Bridgwater, 123 Winchester, 132 Portsmouth and Southampton, 133 Chichester and Worthing, 134 Brighton and Eastbourne, 141 Bournemouth and Swanage, 142 Isle of Wight, 146 Land's End and Lizard.

● JUST PUBLISHED.—No. 22 Pickering, 31 Leeds, 39 Market Rasen, 52 Stoke, 61 Wolverhampton, 85 Cambridge, 124 Guildford.

SCOTLAND.—No. 4 South Mainland—Shetland Isles, 12 Wick, 45 Aberdeen, 53 Sound of Mull, 59 Iona and Colonsay, 60 North Jura and Firth of Lorne, 68 Firth of Forth, 74 Edinburgh.

IN THE PRESS.—No. 16 Saltburn, 33 Hull, 116 Chatham, 125 Tunbridge Wells.

SCHEDULED FOR PUBLICATION.—No. 38 Doncaster, 86 Bury St Edmunds, 97 and 98 Colchester and Harwich, 105 Oxford, 110 Cardiff, 126 Wexham of Kent, 135 Hastings, 138 Exeter and Dartmoor. **SCOTLAND**—No. 72 Glasgow, 73 Falkirk and Motherwell.

An Outline Description of the First Twelve Sheets. By L. D. STAMP and E. C. WILLATTS. With illustrations and coloured specimen map, 1s., postage 1d.

Wall Maps on Linen:—London (4 sheets) 25s., with rollers 28s., Norfolk (4 sheets) 25s., with rollers 28s., Mull (3 sheets) 18s., with rollers 21s.

We are prepared to supply at a few days' notice any of the wall maps in folded and dissected style at the same price as on cloth with rollers. These are likely to prove attractive to those who wish to carry their maps around with them.

THE LAND OF BRITAIN Final Report of the Survey. **ENGLAND**—Part 78, **Berkshire**, 2s. 6d., postage 5d., Part 53, **Rutland**, 2s., postage 3d., Part 69, **Lincolnshire**—(Parts of Holland) 2s. 6d., postage 5d., Part 70, **Norfolk**, 4s., postage 6d., Part 79, **Middlesex and London**, 4s., postage 5d., Part 86, **Somerset**, 4s., postage 5d. **SCOTLAND**—Part 1, **Ayrshire**, 2s. 6d., postage 5d.; Part 2, **Moray and Nairn**, 2s., postage 3d.

● **ATLAS OF CROYDON AND DISTRICT** Prepared by the Croydon Natural History and Scientific Society. Editor, C. C. Fagg, F.G.S. First Issue (loose leaf binder and several maps). 12s. 6d. net. Postage. inland 7d., foreign 1/4.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

CHEMISTRY AND PHYSICS

CHEMICAL CALCULATIONS: THEIR THEORY AND PRACTICE.

By A. KING, M.Sc., and Dr. J. S. ANDERSON, both of the Chemistry Department of the Imperial College of Science and Technology, South Kensington. For first year students in Universities and for higher classes in Schools. 4s. 6d. net, post. 4d.

- **INORGANIC PREPARATIONS.** By A. KING, M.Sc., A.R.C.S., D.I.C. A logical arrangement of experiments with sufficient theoretical matter for the student to correlate theory with practice. Detailed directions for about 190 preparations, and about an equal number briefly sketched. 5s. 6d. net, postage 4d.

- **SILICATE ANALYSIS: A Manual for Geologists and Chemists, with Chapters on Check Calculations and Geo-Chemical Data.** By A. W. GROVES, D.Sc., Ph.D., D.I.C., F.G.S. Foreword by Prof. ARTHUR HOLMES. 12s. 6d. Postage: inland 6d., foreign 7d.

GERMAN-ENGLISH CHEMICAL TERMINOLOGY. By A. KING M.Sc., and Dr. H. FROMHERZ. An introduction to Chemistry in English and German. In Murby's German-English Terminologies. 12s. 6d. net. Postage: inland 6d., foreign 7d.
The sale of this book in U S A. and Canada is in the hands of D. Van Nostrand Company (Inc.), New York.

- **GERMAN-ENGLISH PHYSICS TERMINOLOGY.** By E. R. FRANZ, B.Sc., Hons. (London) A.L.A., with the collaboration of Dr. VON AUWERS. *In preparation.*

TRILINEAR COÖRDINATE PAPER. For use in plotting three variables, in petrology, chemistry, physics, etc. Each side 20 cms., divided into 100 parts, every fifth line heavy. Price, 10 sheets for 1s. 3d., 20 2s. 6d., 50 4s. 6d.

HOBBS' ARITHMETIC OF ELECTRICAL MEASUREMENTS. Revised and Edited by A. RISDON PALMER, B.Sc., B.A., Head of the Matriculation Department, the Polytechnic, W. 9th Reprint of the 16th Edition With answers. 2s. net, postage 2d.

In each chapter a brief explanation is followed by fully worked examples, and numerous well selected examples for the student to work

MAGNETIC MEASUREMENTS AND EXPERIMENTS By A. RISDON PALMER, B.Sc., B.A. With answers. 2s. net, postage 2d. *Second reprint.*

Each chapter contains a set of experiments, arranged to reduce a duplication of apparatus as far as possible (or graphical questions), a short account of the theory to supplement the class lesson, some fully worked examples, and a set of carefully graduated exercises

ELECTRICAL EXPERIMENTS. By A. RISDON PALMER, B.Sc., B.A. 2s. net, postage 2d. *Third reprint in the press.*

A course of Experimental Electricity for one or two years. Details are given as to apparatus and the method of procedure, and the setting out of results.

Thomas Murby & Co., 1, Fleet Lane, Ludgate Circus, London, E.C.4

