UNIVERSAL
LIBRARY
OU_214217
UNIVERSAL
LIBRARY

2114217

A TREATISE ON CHEMISTRY

MACMILLAN AND CO., LIMITED
LONDON BOMBAY CALCUTTA
MELBOURNE MADRAS

THE MACMILLAN COMPANY
NEW YORK BOSTON CHICAGO
DALLAS SAN FRANCISCO

THE MACMILLAN CO. OF CANADA, LTD
TORONTO

A

TREATISE ON CHEMISTRY

THE RIGHT HONOURABLE SIR H E ROSCOE, F R S
AMI
C SCHORLEMMER, F R S

VOLUME l l

THE METALS

PART II

" *Chymia, alias Alchemia et Spagirica, est ars corpora vel mixta vel composita, vel aggregata etiam in principia sua resolvendi aut ex principiis in talia combinandi."—STAHL, 1723.*

NEW EDITION COMPLETELY REVISED BY
B MOUAT JONES AND OTHERS

MACMILLAN AND CO, LIMITED
ST MARTIN'S STREET, LONDON
1923

COPYRIGHT

Frist Edition printed 1878
Reprinted, 1879, Second Edition, 1883 , *Reprinted,* 1887, 1893
Third Edition,1897, Fourth Edition, 1907, Fifth Edition, *1913*
Sixth Edition, 1923

PRINTED IN GREAT BRITAIN

THE FOLLOWING ARE THE CHIEF CONTRACTIONS EMPLOYED IN THIS VOLUME

ABBREVIATED TITLE	*JOURNAT*
Amer Chem J	American Chemical Journal
Amer J Set	American Journal of Science
Analyst	The Analyst
Annalen	Justus Liebiir's Annalen der Chemio
Ann Physik	Annalen dei Physik
Ann Chim Phys	Annates do Chinue et do Physique
Ann Mines	Annales des MUNES
Arch Neerland	Aichives Neerlanduses des Science exactes et naturelles
Arch Pharm	Aichiv dei Pharmazie
Atti R Accad Lineei Per	Atti della Real Accadomia del Lineer
Brochem Zert	Benchte der deutschen CHEMISHEN Gesellschaft
Brit Assoc Reports	Biochemist he Zeutschrift
Bull Acad roy Belg	Reports of the British Association
Bull Geol Soc Amer	Academic royale do Belgique Bulletin de in Classe des Scuncos
Bull Soe ehun	Bulletin of the Geological Society of America
Chem Cent	Bulletin de la SOCIETE chimique de Pins
Chem Neus	Chemisches Centialblatt
Chem Zert	Chemical News
Compt rend	Chemikal Zeitung
Gaz"	Comptes rendus hebdomadanes des Stances de l'Academic des Sciences
Geol Mag	Gazette chimica atahana
Jahrb Mm	Geological Magazine
J Amer Chem Soc	Neues Jahrbuch fur Mineralogu, Geologie und Palaeontology
J Chim phys	Journal of the Amciican Chemical Society
J Iron Steel Inst	Journal de Chimic physique
J Pharm	Journal of the Iron and Steel Institute
J Physical Chem	Journal do Pharmacie
J pr Chem	Journal of Physical Chemistry
J Boy Agric Soc	Journal fur praktische Chemie
J Russ, Phys Chem Soc	Journal of the Royal Agucultuial Society
J Soc Chem Ind	Journal of the Physical and Chemical Society of Russia
Journ Chem Soc	Journal of the Society of Chemical Industry
Landw Versuths Stat	Journal of the Chemical Society
Mem Manch Phil Soc	Die landwutschifthchen Versuchs Stationen
Mm Mag	Memoirs and Proceedings of the Manchester Literary and Philosophical Society
Monatsh	Mineralogical Magazine
Pfluger's Archiv	Monatshette fur Chemic und verwandte Therle anderer Wissenschaften
Pharm J	Archiv fur die gesammte Physiologic des Menschen und der Thiere
Phil Mag ,	Pharmaceutical Journal
	Philosophical Magazine

CONTRACTIONS EMPLOYED IN THIS VOLUME

ABBREVIATED Titiles	JOURNAL
Phil Trans	Philosophical Transactions of the Royal Society
Pogg Ann	Poggendorft's Annales der Physik und dei Chemie
Proc Chem Soc	Proceedings of the Chemical Society
Proc K Akad W elensch Amsterdam	Koninkhjke Akademie van Wetenschappen to Amsterdam Proceedings [English Version]
Proc Roy Soc	Proceedings of the Royal Society
Proc Roy Soc Edin	Proceedings of the Royal Society of Edmbu gh
Quart J Geol Soc	Quarterly Journal of the Geological Society
Rec hav chim	Recueil des travaux chimiques des Pays Bis et de la Belgique
Silzungshir K Akad Wass Berlin	Sitzungsbenchte der komghch preussischen Akadeime dir Wissenschaften zu Berlin
Zeit anal Chem	Zeitschrift fur analytische Chemie
Zait angeu Chem	Zeitschuft fur angewandte Chemic
Zeit anarg Chan	Zeitschrift fur anorganische Chemie
Zeit Chem	Zeitsehrift fur Chemie
Zed Kektrochem	Zeitschrift fur Ekktrochcmic
Zed Krysf Man	Zeitschuft fur Kiystallogiaphic und Miner alogic
Zed physikal Chem	Zeitschuft fur physikahschi Chemic , Stochic metrie und Verwandtschaftslehre
Zed Physiol Chem	Hoppe Seylers Zeitschuft fur physiologischo Chemie

CONTENTS

	PAGE
GROUP IV	831
THE TITANIUM GROUP	833
TITANIUM	833
ZIRCONIUM	849
HAFNIUM	858
THORIUM	859
THE GERMANIUM GROUP	868
GERMANIUM	868
TIN	872
LEAD	902
GROUP V	942
THE VANADIUM GROUP	943
VANADIUM	943
CORUMBIUM	973
TANTAIUM	990
THE ANHMONY GROUP	997
ANHMONY	997
BISMUIH	1031
GROUP VI	1050
CHROMIUM	1051
MOLYBDENUM	1096
Tungsten	1124
URANIUM	1149
GROUP VII	1170
MANGANESE	1171
GROUP VIII	1208
THE IRON GROUP	1209
IRON	1210
COBALT	1329
NICKEL	1355
THE RUTHENIUM GROUP	1388
RUTHENIUM	1388
RHODIUM	1398
PALLADIUM	1406
THE PLATINUM GROUP	1422
OSMIUM	1423
IRIDIUM	1438
PLAIINUM	1450

PAGE

THE RADIOACTIVE ELEMENTS 1490

PHENOMENA OF RADIOACTIVITY 1502
THE PRODUCTS OF RADIOACTIVE CHANGE 1511
RADIUM 1515
ACTINIUM 1526
THORIUM 1527
URANIUM 1528
ATOMIC STRUCTURE 1532

INDEX 1541

CHEMISTRY

THE METALS *{continued)*

GROUP IV

Sub-group (a)	*Sub-group (b)*
Carbon	Silicon
Titanium	Germanium
Zircomum	Tin
(Cerium)	Lead
Hafnium	
Thorium	

374 In this group there is no well-defined division of the elements composing it into two distinct sub-groups, such as is noticeable in the others of the first seven groups, and the differences observable between the members of the odd and even series are only of minor importance

Cerium probably belongs to this group, but as its chemistry is so intimately connected with that of the other members of the group of rare earth metals it has been described among them

The first two members of this group, carbon and silicon, have already been described among the non-metallic elements Both exist in the amorphous and crystalline states, silicon melting only at a very high temperature, whilst carbon has not yet been melted, although it volatilises at the highest attainable temperatures The remaining elements all have metallic properties, and, with the exception of tin and lead, possess high melting points, in the compact state they undergo at most a surface oxidation in the air at the ordinary temperature, but when Strongly heated readily combine with oxygen, and, except in the case of lead, the oxide formed in presence of an excess of oxygen is the *dioxide* The dioxides of the members having the lower atomic weights, including those of carbon and silicon, behave chiefly as acid-forming oxides, but they become more basic as the atomic weight of the element increases These oxides correspond in each case with a series of salts in which

the element is tetravalent, and, except in the case *of* lead, this series includes the most important compounds Lead in its most characteristic compounds is divalent, and, as is so frequently the case with elements having a high atomic weight, it presents many resemblances to the elements having the next lowest and next highest atomic weights, viz, thallium and bismuth

A very characteristic series of double salts with the alkali hahdes is yielded by the tetrahalogen derivatives of most of these elements, the double fluorides, which have the general formula $M^{I}_{2}M^{IV}F_{6}$, being the most important In the case of silicon, titamum, germanium, zirconium, and tin, these compounds are isomorphous, but this appears not to be the case with the thorium compound The corresponding salt of lead has not been prepared, but an acid salt, PbF_{4},3KF,HF, exists, which is isomorphous with the analogous tin salt, SnF_{4},3KF,HF

Carbon is distinguished from all other elements by the property possessed by its atoms of uniting together m open or closed chains, forming nuclei, which may contain as many as sixty atoms, and which, in combination with the other elements, give rise to the immense number of carbon compounds The same property is observable to a much smaller extentinsilicon, but not in the other members of the group In addition to the typical elements, carbon and silicon, only germanium, tin, and lead,i *e*, the members of the " odd " series, yield organometalhc derivatives

THE TITANIUM GROUP.

TITANIUM Ti = 481 At No 22

375 The Rev William Gregor [1]in1789 discovered a new metal contained in the mineral menachanite or ilmenite, occurring in Cornwall In 1795 Klaproth investigated the composition of the mineral rutile, and discoveredinit a new metal to which he gave the name of titanium In a subsequent investigation of ilmenite,in1797, he found that the metal which that mineral contained was titanium Klaproth found that rutile consisted mainly of titamum dioxide, but he did not succeed in obtaining the oxide in the pure state, this having been first accomplished by Rose in 1821

Titanium, though not an abundant element, is very widely

[1] *Crell Ann ,1791.*

distnbuted It is not found in the metallic state, but occurs as the dioxide, TiO_2,in three minerals, rutile, brookite, and anatase, which possess different crystalline forms, in combination with ferrous and ferric oxides in titanic iron ore or ilmenite, $FeTiO_3$, and with lime and oxide of iron in perofskite, $(Ca,Fe)TiO_3$, as well as in titanite or sphene, $CaTiSiO_5$, schorlomite, $Ca(Ti,Fe)SiO_5$, and keilnauite, $CaYt(Ti,Al,Fe)SiO_5$ Magnetic iron ore also frequently contains larger or smaller quantities of titanium which finds its way into many blast-furnace slags and pig-irons Titanium occurs in small quantity in several other minerals, and traces have been foundintrap and basalt, in many amphiboles and micas, and in garnet, hence it occurs in most fertile soilsin quantities between 0 3 and 0 6 per cent, [1] i nmany clays, and likewiseincertain mineral waters It has been found in human and ox flesh and bone,[2] and occurs in the ashes of all plants [3] in quantities up to 0 27 per cent ,[4] andinmany peats [5] Its presence has been detectedincertain meteorites, and it forms an important constituent of the solar atmosphere

Preparation of Metallic Titanium —Metallic titanium is difficult to obtain in the pure condition, the usual methods for the reduction of the oxide, such as heating with metallic sodium and magnesium, yield products which still contain considerable quantities of titanium monoxide, and the product obtained by the action of sodium on halogen derivatives of titanium also usually contains small quantities of the monoxide, formed by the action of the moisture present, and of the nitride, obtained by the direct union of the metal with nitrogen, which it is almost impossible completely to exclude Owing to the extreme readiness with which titanium and nitrogen combine at high temperatures, and to the metallic appearance of the nitride, this compound was mistaken by the earlier investigators for the metal itself, as was also the compound which it forms with carbon and nitrogen, now known as titanium cyanomtnde

Moissan fused carbon with an excess of titanium dioxide at a very high temperature in the electric furnace Three distinct layers were found in the solidified product, the uppermost consisting of titanium contaimng about 5 per cent of carbon, the second of the nitride, and the third of titanium monoxide

[1] **Geilmann,** *J Landw* **, 1920, 68, 107**
[2] **Baskerville,** *J Amer Chem Soc* **, 1899, 21, 1099**
[3] **Wait,** *J Amer Chem Soc,* **1896, 18, 402, Lippmann,** *Ber,* **1897, 30, 3037**
[4] **Gerimann,** *J Landw* **, 1920, 88, 107**
[5] **Baskerville,** *J Amer Chem Soc* **, 1899, 21, 402**

The top layer was heated again with an excess of titanium dioxide, the quantity of carbon was reduced to 2 per cent, and the product was from from nitrogen and silicon [1]

Nilson and Pettersson,[2] by acting on titamum tetrachloride with sodiuminan air-tight cylinder of mild steel at a red heat prepared metallic titanium in yellow scales, whicn had frequently a bluish surface colour These, however, still contained a considerable quantity of oxygen, probably as the monoxide A still less pure product is obtained by heating potassium titanofluonde with sodium A very much purer product has been obtained by heating titanium oxideinan evacuated iron vessel with calcium shavings [3]

Metallic titanium has been prepared by Stahler and Bachran [4] by heating the dichlonde in a current of hydrogen to 1100°, when the reaction $2TiCl_2 = TiCl_4 + Ti$ takes place A method of preparing titamum of 99 7 per cent purity has been described by Podszus[5] The method consists in placing a mixture of sodium and titamum tetrachloride in a steel bomb filled with hydrogen or carbon dioxide and containing a number of polished steel balls The bomb is closed by a powerful screw and sealed with molten lead The bomb being closed, the whole is rotated at 200° for 20-40 hours to produce an intimate mixture The reaction is started by heating the bomb strongly for a few minutes When the reaction is complete the bomb is cooled from the top downwards The product is titamum in the foim of minute crystals which are highly reactive

Titanium is a brittle, grey metal, which is hard enough to scratch steel and quartz It has a density 4 87 and melts at 1795°. It is stable in the air at the ordinary temperature, but burns brilliantly in oxygen at 610° Titanium combines with nitrogen with extreme readiness, in this respect resembling boron and magnesium, the reaction commences at about 800°, and the mtiide is also formed together with the oxide when the metal burns in the air

Titanium combines with the halogens when heated to form the tetrahalides, with chlorine the action takes place at 350°, with bromine at 360° and with iodine at 400° It dissolves slowly in dilute sulphuric acid andinconcentrated hydrochloric acid, with liberation of hydrogen and formation of violet salts It is

[1] Moissan, *Compt rend* , 1855, **120,** 290 [2] *Zert physikal Chem,* 1887, 1, 25
[3] Wedekind, *Annalen,* 1913, 395, 149 [4] *Ber* , 1911, 44, 2907
[5] *Zeit anorg Chem* , 1917, **99,** 123

converted into titanic acid by nitric acid and aqua regia and decomposes steam at 700-800° Moissan [1] has distilled the metal

in the elec

the metal condensinginsmall crystals

Metallic titarium in the form of its alloys is used in the steel industry Steel to which a small quantity of titanium has been added is improved in tensile strength and is largely used on the American railways and for bridge construction

TITANIUM COMPOUNDS

TITANIUM AND OXYGEN

376 Titanium combines with oxygen to form a number of oxides, the most important being

Titanium monoxide, TiO
Titamum sesqiuoxide, Ti_20_3
Titamum dioxide, TiO_2
Titanium peroxide, TiO_3

Titanium Monoxide, TiO, is obtainedinthe form of black, prismatic crystals by heating the dioxide strongly in the electric furnace,[2] and is also formed, together with magnesium titanate, when titanium dioxide is heated with the requisite quantity of magnesium powder [3]

$$2TiO_2 + Mg = TiO + MgTiO_3$$

The hydroxide, $Ti(OH)_2$, is formed as a black precipitate when an alkali hydroxide is added to a solution of titanium dichloride It is readily oxidised in air to hydrated titanium dioxide

Titanium Sesquioxide, Ti_2O_3, is obtained by strongly igniting titanium dioxide in a current of hydrogen and allowing the product to cool in the gas The same oxide may also be obtained as a copper-coloured, lustrous, crystalline mass, together with the trichloride and oxychloride of titanium, by passing a mixture of hydrogen and the vapour of titanium tetrachloride over white-hot titanium dioxide It is not attacked by nitric or hydrochloric acids, but sulphuric acid dissolves it with formation of a violet solution (Ebelmen)

The *hydrated sesquioxide* is formed by digesting a solution of titanic acid in hydrochloric acid with metallic copper at 20-40°, the solution attains a violet-blue colour, and when poured into

[1] *Compt rend* , 1906, **142,** 673 [2] Moissan, *Compt rend* , 1892, **115,** 1034
[3] Winkler, *Ber* , 1890, 23, 2658

aqueous ammonia yields a dark brown precipitate of titanous hydroxide (Fuchs) The hydroxide is formed also when a solution of the trichlonae is precipitated by alkalis

When titanium sesquioxide is shaken with milk of lime in the presence of oxygen it is oxidised to the dioxide - More oxygen is absorbed than is necessary for this change, whilst hydrogen peroxide is formed in amount corresponding to the whole of the oxygen absorbed Water must therefore take part in the reaction, and the phenomenon is probably a case of autoxidation (see Vol I, p 253) In the same way, when the sesquioxide is oxidised by a solution of chromic acidinthe presence of potassium iodide, or by potassium permanganateinthe presence of tartaric acid, titanic acid is formed, and at the same time oxidation of the potassium iodide or tartaric acid is brought about [1]

Titanium Dioxide, TiO_2, is tnmorphous, occurring as three different minerals, rutile, anatase, and brookite Rutile crystallises in tetragonal prisms, having a specific gravity of 4 18-4 25, isomorphous with those of tin dioxide or cassitente, and possessing an adamantine lustre and a brown or reddish colour Anatase crystallises in a totally different form of the tetragonal system, has a specific gravity of 3 82-3 95, and a brown or black colour Brookite crystallises in flat, rhombic prisms and has a specific gravity of 4 12-4 23

Amorphous titanium dioxide is obtained by the decomposition of aqueous titanium chloride by ammonia, the precipitate being washed, dried, and lgmted, or it may be directly prepared from rutile or titanic iron ore In order to prepare the pure oxide from rutile, the finely-powdered mineral is fused with three times its weight of potassium carbonate, the solidified mass powdered and dissolved, in a platinum vessel, in dilute hydrofluoric acid, potassium titanofluonde being thus formed and the ferric oxide left free from titanium The mass is then heated with sufficient water to dissolve the whole of the titanium double salt, the liquid boiled, and filtered hot On cooling, the mass of the titanofluonde crystallises out, and this, after washing with cold water, may be purified by recrystallisation The titanofluonde is then dissolvedinhot water and the titanium precipitated by ammoma as titanic hydroxide containing ammonia, which on ignition yields pure titanium dioxide (Wohler) Pure titanic oxide may also be obtained from titanic ore in a similar manner, or by fusing it with potassium bisulphate, or by

[1] **Manchot and Ritcher, *Ber* , 1906, 39, 320, 488**

igniting it, in a mixture of chlorine and hydrochloric acid when ferric chloride is volatilised (Friedel and Guerin)

$$2FeTiO_3 + 4HC1 + Cl_2 = 2FeCl_3 + 2TiO_2 + 2H_20$$

Amorphous titanium dioxide is a white, tasteless powder which when gently heated has a lemon-yellow colour, and when strongly ignited* appears brown It has a specific gravity of from 3 89 to 3 95, and when very strongly heated this rises to 4 25

When it is heated with microcosmic salt (Ebelmen) or with borax (G Rose) for some time to a white heat, fine crystals of rutile are obtained, which have a specific gravity of 4 26 Crystalline titanium dioxide can also be obtained by passing the gases obtained by decomposing molten potassium titanofluonde with hydrogen chloride through a hot platinum tube into which a current of moist air and hydrogen is also passed In this way Hautefeuille [1] has shown that by treatment at a temperature not exceeding the boiling point of cadmium (778°), anatase is produced, the crystals of which have a specific gravity of 3 7 to 3 9, at a temperature of about 1,000°, steel-blue coloured rhombic crystals of brookite are obtained, which have a specific gravity of 4 1, and closely resemble the natural crystals from Miask At still higher temperatures again, rutile is produced, so that this last is the only form which is stable at a high temperature, andinan acid or moist atmosphere [2]

At the temperature of the oxy-hydrogen flame titanium dioxide fuses, forming a thin liquid, which solidifies to a confused crystalline mass

In its chemical properties titanium dioxide closely resembles the corresponding silicon dioxide, behaving as an acid anhydride It is insolubleinwater, hydrochlouc acid, and dilute sulphuric acid, although it dissolves when digested for some time with hot concentrated sulphuric acid The amorphous oxide dissolves on fusion with alkalis or alkali carbonates, unless it has been strongly lgnited, forming the titanates, and also dissolves slowly in fused potassium hydrogen sulphate, yielding a clear mass which dissolves perfectlyinwarm water When this solution is boiled, the hydrated dioxide is precipitated Titanium dioxide corresponds to the most important series of titanium salts in which the metal is tetravalent

Titanic Acid and the Titanates —As is the case with the analo-

[1] ***Ann Chim Phys*** **, 1865, [4], 4, 129**
[2] **Fnedel and Guerin, *Bull Soc chim* , 1874, 22, 482**

gous silicic acid, several hydrates of varying composition are known There appears to be little doubt that the hydrates *orthotitanic acid*,, $T(OH)_4$, and *metatitanic acid,* $TiO(OH)_2$, exist, but in addition others have been prepared containing quantities of water intermediate between the amounts required for these two formulae, and also with less than that required by the latter formula These may possibly be the hydrates corresponding to the complex titanic acids, but they have not been obtained of sufficiently definite composition to enable this to be ascertained

Orthotitanic Acid, $Ti(OH)_4$, is obtained by adding an alkali to a cold hydrochloric acid solution of a titanate, and forms a voluminous white precipitate which is soluble in dilute hydrochloric acid and sulphuric acid, and loses water on drying, forming other hydrates When heated it is converted into the anhydride, the reaction being accompanied by evolution of light When allowed to remain under water it is gradually converted into metatitanic acid [1]

Metatitanic Acid, $TiO(OH)_2$, is obtained by boiling a solution of orthotitanic acid in hydrochloric acid, or by the action of nitre acid of specific gravity 1 25 on titanium It is insoluble in acids except concentrated sulphuric acid When heated it is converted into the anhydride without emission of light

The other hydrates also are frequently spoken of as " ortho " or " meta " acids, according as they are soluble or insoluble in dilute acids

By the dialysis of a hydrochloric acid solution of orthotitanic acid, Graham obtained a solution of colloidal titanic acid, and von der Pfordten has also obtained the acid as a colourless jelly [2]

Potassium Titanate, K_2TiO_3, is formed as a yellow, fibrous mass when the dioxide is fused with potassium carbonate On boiling titanic acid with caustic potash and evaporating the solution, colourless, readily soluble prisms of $K_2TrO_3,4H_2O$ are deposited When a hydrochloric acid solution of titanic acid is precipitated with potassium carbonate, an amorphous precipitate of potassium trititanate, $K_2Ti_3O_7,2H_2O$, is thrown down, and this in presence of hydrochloric acid is converted into a hexatitanate, $K_2Ti_6O_{13},2H_2O$ The fused anhydrous normal salt, when treated with water in excess, also yields a trititanate, $K_2Ti_3O_{7,}3H_2O$, as a fine crystalline powder

When sodium carbonate and titanium dioxide are fused the

[1] Wagner, *Ber* , 1888, 21, 960
[2] *Annalen,* 1887, **237,** 213

three *sodium, titanates,*[1] $Na_8Ti_5O_{14}$, $Na_2Ti_3O_7$, and Na_2TiO_3, are obtained, of these, $Na_8Ti_5O_{24}$ crystallises in forms resembling augite and has a refractive index greater than 1 74

Calcium Titanate, Ca TiO_3—This occurs in the Urals, in the valley of Zermatt in Switzerland, and at Magnet Cove, Arkansas, as the mineral perofskite, which contains in addition 1 to 6 per cent of ferrous oxide, as well as traces of manganese and magnesium It forms rhombic crystals having a metallic or adamantine lustre, a yellow or iron-black colour, and a specific gravity of 4 0 The crystals can be artificially obtained by fusing a mixture of potassium carbonate and titanium dioxide with a large excess of calcium carbonate [2]

Calcium Titanosikcate, $CaTiSiO_5$, is found as titanite or sphene in brown, green, or black monochnic crystals, having an adamantine or resinous lustre and a specific gravity of 3 4 to 3·56, occurring imbedded in granite, gneiss, mica-schist, and granular limestone Titanite can be obtained artificially by fusing calcium chloride with titanium dioxide and silica The mineral guarinite has the same composition as titanite, and is found in tetragonal crystals, having a specific gravity of 3 487, in small cavitiesina greyish trachyte at Monte Somma

Ilmenite, or Titanic bon Ore, $FeTrO_3$—This mineral, the one in which titanium was first discovered, occurs tolerably widely distributed, and crystallises in black, hexagonal crystals One of its most important localities is Krageroe, in Norway Fine crystals are also found in Warwick Co , New York, and vast deposits occur at Bay St Paul, in Canada It is frequently found in the finely-divided state as sand on the shores of the Mersey opposite Liverpool, in New Zealand, and elsewhere Its specific gravity ranges from 4 5 to 5, and its composition is a variable one It was thought to be an isomorphous mixture of the sesquioxides of titanium and iron, but is now regarded as a derivative of titanium dioxide Many llmenites contain magnesia,[3] and the formula has sometimes been written as (Fe,Mg)O,TiO2

Geikielite, a rare mineral from Ceylon, is a ferro-magnesian titanate containing a high proportion of magnesia [4]

Titanium Tnoxide, or *Titanium Peroxide,* TiO_3, is obtained by dropping titanium chloride into dilute alcohol and adding a

[1] Niggh, *Zeit anorg Ckem* , 1916, **98, 241** [2] *Ibid*
3 Penfield **and** Foote, *Amer J Set,* 1897, [4], **4, 108**
[4] Cro**ok and Jones,** *Mineralogical Magazine,* **1906,14, 160**

large excess of hydrogen peroxide to the solution Ammonia, ammonium carbonate, or potash is then added, and after a time a bright yellow protipitate separates out 'The precipitate consists of a hydrate of titanium trioxide, $TiO_3,3H_2O$, winch retains water and salts very persistently, and dissolves in hydrochloric acid with evolution of a little chlorine and formation of a vellowish-red solution [1]

When titanium trioxide is treated at O° with hydrogen peroxide and potash and alcohol are then added, crystals of *potassium peroxide hypertitanate*, $K_2O_4,TiO3,K_2O_2,10H_2O$, separate out, whilst if soda is usedinplace of potash the compound formed has the composition $(Na_2O_2)_4,Ti_2O_7,10H_2O$ These substances are stable at 0°, but lose oxygen at ordinary temperatures [2]

TITANIUM AND THE HALOGENS

377 *Titanium Trifluonde*, TiF_3, is obtained as an insoluble violet powder by igniting potassium titanofluonde in a current of hydrogen and treating the product .with hot water It is also formed when the potassium titanofluonde is reduced in aqueous solution by zinc and hydrochloric acid or sodium amalgam It combines with ammonium fluoride, forming the double salts $(NH_4)_2TiF_5$ and $(NH_4)_3TiF_6$

Titanium Tetrafluoride, TiF_4, is obtained by the action of fluorine on warm, finely-powdered titanium, or of anhydrous hydrofluoric acid on titanium tetrachloride at 100-120°, or on powdered titanium at a red heat,[3] and also by the action of liquid anhydrous hydrofluoric acid on the tetrachloride[4] It may also be prepared by heating barium titanofluonde to a red heat[5] It is a white solid at the ordinary temperature, boils at 284°, and has the specific gravity 2 798 at 27 5°, whilst its vapour destiny at 444° corresponds with the formula TiF_4 It is very hygroscopic and dissolves in water to a clear solution, which on evaporation deposits crystals of $TiF_4,2H_20$ With dry ammonia, it forms the compound $TiF_4,2NH_3$, which sublimes without decomposition and is soluble in water Titanium tetrafluoride is decomposed by hot sulphuric acid with formation of the dioxide

[1] **Classen, *Ber* , 1888, 21, 370**
[2] **Melikoff and Pissarjewsky, *Ber* , 1898, 31, 678**
[3] **Ruff and Ipsen, *Ber* , 1903, 36, 1777**
[4] **Ruff and Plato, *Ber* , 1904, 37, 673** [5] **Emich, *Manatsh* , 1904, 26 1907**

When titanium dioxide is dissolved in hydrofluoric acid a syrupy liquid is obtained, which probably contains *hydrogen titanofluonde,* H_2TiF_6 The *titanofluondes* are isomorphous with the sihcofluonrides, zirconofluondes, and stannifluondes

Potassium Titanofluonde or *Potassium Fluotitanate,* K_2TiF_6 — This salt may be prepared by the action of potassium hydrogen fluoride on a solution of titanium dioxide in excess of concentrated hydrofluoric acid It crystallises in small, lustrous leaflets, which may be recrystallised without change from hydrofluoric acid[1] The hydrated salt, K_2TiF_6,H_2O, is prepared either by adding potash to aqueous hydrogen titanofluonde (Berzehus), or, according to Wohler, by fusing titanium dioxide in a platinum crucible with twice its weight of potassium carbonate and dissolving the fused and pulverised mass in a platinum dish in the requisite quantity of dilute hydrofluoric acid The potassium salt then crystallises outinshimng scales closely resembling those of boric acid and belonging to the monochnic system (Mangnac), they may be dried between filter paper and recrystallised from boiling water It loses its water at 100° and melts without decomposition at a white heat The anhydrous salt may be obtained from the hydrated salt by recrystallisation from concentrated hydrofluoric acid (Marchetti) When a warm solution of potassium titanofluonde is treated with hydrogen peroxide, *potassium tUanoperoxyfluoride,* $TiO2F_2,2KF$, is formed[2]

Sodium Titanofluonde, Na_2TiF_6, is obtained in a similar manner to the preceding salt in hexagonal prisms most probably isomorphous with sodium silicofluoride (Mangnac) A solution containing an excess of hydrofluoric acid deposits small, glistening, rhombic crystals having the composition $Na_2TiF_6,NaHF_2$

Ammonium Titanqfluorite, $(NH_4)_2TiF_6$ —This salt was obtained by Berzehus, in rhombohedra isomorphous with the corresponding tin compound, by neutralising hydrogen titanofluonde with ammonia Anothei salt of composition

$$(NH_4)_2TiF_6,NH_4F$$

separates in tetragonal crystals from a solution of the preceding saltinan excess of ammonium fluoride

Titanium Bichloride, $TiCl_2$, was obtained by Fnedel and Gu£nn[3] by passing dry hydrogen at a dull red heat over titanium trichloride This compound is a very hygroscopic light brown

[1] Marchetti, *Zeit anorg Chem* , 1895,**10, 66**
[2] Piccini, *Zeit anorg Chem* , **1895, 10, 438**
[3] 4nn ***Chim Phys* , 1876, [5], 7,24 Stahler and Bachran, *Ber* ,1911,44,2906**

powder, which can be volatilised in hydrogen at a red heat without fusion It burns like tinder on exposure to air, giving off fumes of titanium tetrachiroide and leaving a residue of titanium dioxide It hisses when thrown into water, evolving hvdrogen and yielding a yellow liquid

Titanium Trichloride, $TiCl_3$—When the vapour of titanium tetrachloride mixed with hydrogen is passed through a red-hot tube, dark violet scales of the trichloride are deposited (Ebelmen) It may also be obtained by heating titanium tetrachlorideina closed tube with molecular silver at 180-200°

$$TiCl_4 + Ag = T1Cl3 + AgCl$$

If the mixture thus obtained is heated more strongly, the reverse action takes place (Fnedel and Guenn) Titanium trichloride has also been obtained by the electrolytic reduction of a solution of titanium tetrachloride in dilute hydrochloric acid, violet crystals of the composition $TiCl_3,6H_20$ being deposited when the resulting liquid is either evaporatedin*vacuo* or saturated at 0° with dry hydrochlouc acid [1]

Titanium trichloride is non-volatile, and on heating decomposes into the dichlonde and tetrachloride When heated in the air, thick vapours of titanium tetrachloride are emitted and titanium dioxide is left behind It readily deliquesces on exposure to moist air and dissolves in water with evolution of heat, yielding a reddish-violet solution

Titanium trichloride is a powerful reducing agent Thus when boiled with aqueous sulphurous acid, sulphur separates out, whilst nitric acid and the nitrates are reduced by it to ammonia (Knecht), and the salts of gold, silver, and mercury to the metals Standard solutions of titanium trichloride have been used in volumetric analysis for the estimation of ferric iron and also for the analysis of a number of colouring matters [2]

Double compounds of titanium trichloride with the chlorides of rubidium and caesium have been prepared,[3] having the compositions $TiCl_3,2RbCl,H_2O$ and $TiCl_3,2CsCl,H_2O$

Titanium Tetrachloride, $TiCl_4$—Metallic titanium does not combine with chlorine at the ordinary temperature, but when heated to 350° it burns in the gas with brilliancy, forming the

iPohdon, *Zert anorg Chem* , 1899, 19, 306, Stahler, *Ber,* 1904, 37, 4405, Spence and Son, German Pate t, 154642

[2] Knecht, *Ber* , 1908, 36, 166, Knecht and Hibbert, *ibid* , 1903, 36, 1549, 1905, 38, 3318, 1907, 40, 3819, 1910, 43, 3455

[3] Stahler, *Ber* , 1904, 37, 4405

tetrachloride (Wohler) According to Fnedel and Guerin, titanium dioxide is converted in presence of chlorine at a white heat into titanium tetrachloride, oxygen being evolved The tetrachloride is readily obtained by passing dry chlorine over a heated mixture of titanium dioxide and carbon, whilst it is also formed, together with carbonic oxide and hydrogen chloride, when chloroform or carbon tetrachloride vapour is passed over heated titanium dioxide [1]

It may also be obtained by heating powdered ferrotitanium in a current of chlorine or by treating ferrotitanium with hydrochloric acid to dissolve out most of the iron, and heating the dried residue of titanic oxide with carbonina stream of chlorine [2] It is a mobile, transparent, colourless liquid, having a specific gravity of 1 7604 at 0° (Pierre) It freezes [3] at -23°, and boils at 136 4° (134 8°, Emich), its vapour having the normal specific gravity of 6 836 (Dumas) It possesses a penetrating acid odour, and emits dense white fumes on exposure to air

Titanium tetrachloride is decomposed by an excess of water with formation of titanic acid, which remains dissolved in the aqueous hydrochloric acid simultaneously formed By careful addition of water it is possible to replace the chlorine atoms one by one by hydroxyl, yielding the compounds $TiCl_3(OH)$, $TiCl_2(OH)_2$, and $TiCl(OH)_3$, whilst an excess of water conveits it into $Ti(OH)_4$

Titanium tetrachloride yields a large number of crystalline compounds with other chlorides analogous to those formed by stannic chloride [4] When dry ammonia gas is passed over titanium tetrachlonde it is rapidly absorbed, and a very hygroscopic powder, $TiCl_4,4NH_3$, is formed which when ignited yields a yellow sublimate of $TiCl_4,3NH_4Cl$ Other compounds with ammonia [5] have been prepared of the formulae $TiCl_4,6NH_3$ and $TiCl_4,8NH_3$, these are solid bodies which lose ammonia readily in air and on extracting with liquid ammoma yield ammonium chloride and a dark yellow substance, *titanamide,* $Ti(NH_2)_4$

Titanium tetrachloride dissolves in concentrated hydrochloric acid to form a yellow solution containing *chloro-htanic acid,*

[1] **Renz, *Ber* , 1906, 39, 249**

[2] **Vigouroux and Arnvant, *Bull Soc chtm* , 1907, [4], 1, 19**

[3] **Emich, *Monatsh* , 1904, 25, 907**

[4] **Sce Rosenheim, and Schutte, *Zeit anorg Chem,* 1901, 26, 239, Ruff and Ipsen, *Ber* , 1903, 36, 1777**

[5] **Stahler, *Ber,* 1905, 38, 2619 See also Rosenheim and Schutte, *Zeit anorg Chem* , 1901, 26, 239**

H_2TiCl_6,[1] and when this solution is treated with the theoretical quantity of ammonium chloride yellow crystals of ammonium chlorotitanate separate

Titanium Oxychloride, $Ti_2O_2Cl_2$, is obtained, together with the trichloride, when a mixture of hydrogen and the vapour of titanium tetrachloride is passed over the ignited dioxide It forms reddish-brown, translucent crystals, which burn when heated in the air with formation of the dioxide and the tetrachloride (Friedel and Guerin) Other oxychlorides also have been prepared

Titanium Tnbromide, $TiBr_3,6H_2O$, is obtained in unstable, deliquescent, violet-coloured crystals when a solution of titanium tetrabromide in hydrobromic acid is electrolysed, and the liquid then saturated with hydrobromic acid gas [2]

Titanium Tetrabromide, $TiBr_4$, is obtained when hydrobromic acid is passed over the heated chloride[3] as an amber-yellow, hygroscopic, finely crystalline mass which has a specific gravity of 2 6, melts at 39°, and boils at 230° [4]

It is readily hydrolysed by water, forming oxybromides, $TiBr_3OH$ and $2TiBr(OH)_3,2H_2O$ It combines directly with ammonia, forming the compound $TiBr_4,8NH_3$ It dissolves in hydrobromic acid to form a blood-red solution which contains *bromotitanic acid,* H_2TiBr_6 When treated with ammonium chloride, the ammonium salt of this acid, $(NH_4)_2TiBr_6,2H_2O$, separates in dark red crystals

Titanium Di-iodide, TiI_2,[5] is prepared by heating the tetralodide in a current of hydrogen and mercury vapour It is a black compound which forms non-volatile, hygroscopic leaflets of density 4 3 It is decomposed by water and is solubleinboiling hydrochloric acid to form a blue solution

Titanium Tn-iodide, $TiI_3,6H_2O$ —Deliquescent, violet crystals of this composition are formed by the electrolytic reduction of a solution of the tetra-iodide in hydnodic acid [6]

Titanium Tetra-iodide, TiI_4, is produced when iodine vapour is passed over heated titanium (Weber), also when dry hydnodic acid is passed into titanium tetrachloride, which is gradually

[1] Kowalewsky, *Zert anorg Chem* , 1900, 26, 189 Rosenheim and Schutte, *Zeit anorg Chem* , 1901, 26, 239

[2] Stahler, *Ber* , 1904, 37, 4405

[3] Thorpe, *Journ Chem Soc* , 1885, 47, 126

[4] Duppa, *Proc Roy Soc* , 1857, 8, 42

[5] Defacqz and Copaux, *Bull Soc chim* , 1908, [3], 899

[6] Stahler, *Ber,* 1904, 37, 4405

heated up to its boiling point The small quantity of free iodine giving a violet tinge may be removed by three or four distillations in a stream of hydrogen (Hautefeuille) A third process consists in passing the vapour of titanium tetrachloride mixed with hydrogen and iodine vapour through a tube heated to redness •Titanium tetra-rodide forms a brittle mass having a reddish-brown colour and metallic lustre It melts at 150° to a yellowish-brown liquid, which solidifies on cooling in fine octahedral crystals It distils without decomposition at a temperature slightly above 360°, giving rise to orange-coloured vapours The specific gravity of its vapour at 440° has the normal value of 18 054 It fumes strongly in the air and dissolves readily in water

TITANIUM AND SULPHUR

378 Titanium combines with sulphur to form the sulphides, TiS_2, Ti_2S_3, and TiS, corresponding to the oxides of the metal

Titanium Bisulphide, TiS_2, is obtained by passing a mixture of titanium tetrachloride vapour and sulphuretted hydrogen through an ignited tube, and forms large brass-yellow, lustrous scales, closely resembling mosaic gold It burns when ignited in the air, yielding titanium dioxide and sulphur dioxide

Titanium Sesquisulphide, Ti_2S_3, is formed by passing a mixture of moist sulphuretted hydrogen and carbon disulphide vapour over titanium dioxide heated to bright redness,[1] or by igniting the disulphide in a current of an indifferent gas,[2] it forms a greenish-black or grey powder It is stable towards dilute solutions of acids and alkalis, but forms green solutions of unknown composition in concentrated sulphunc and nitric acids

Titanium Monosulphide, TiS, is prepared by heating either of the foregoing compounds in a current of hydrogen and is a lustrous substance resembling bismuth

Titanous Sulphate, $TiS0_4$, is formed when metallic titanium is dissolved in sulphuric acid and the solution evaporated to dryness

Titanium Sesquisulphate, $Ti_2(SO_4)_3,8H_2O$, is obtained by dissolving the metal in dilute sulphuric acid The violet solution on concentration assumes a fine blue lustre and deposits small tufts of crystals (Glatzel)[3] By repeated evaporationin*vacuo* of a solution of t

[1] Thorpe, *Journ Chem SOC ,* **1885, 47, 491**
[2] **von der Pfordten,** *Annalen,* **1886,** 234, **290**
[3] **Compare Stahler, *Ber* , 1905, 38, 2619**

acid, violet crystals of the composition $3Ti_2(SO_4)_3,H_2SO_4,25H_2O$ are obtained, and the same compound is formed also by the electrolysis of a solution of titanium tetrachloride in concentrated sulphuric acid This substance forms a violet solution in water, and on repeated evaporation with concentrated sulphuric acid in absence of air, yields the anhydrous sesquisulpbate as an insoluble, green, crystalline powder (Stahler) Titanium sesquisulphate is decomposed by heat into sulphur dioxide, sulphur tnoxide, and titanium dioxide It forms an alum with caesium sulphate, $Cs_2SO_4,Tr_2(SO_4)_3,24H_2O$, which crystallises in cubes, and a similar alum with rubidium sulphate,[1] whilst a double sulphate, $Ti_2(SO_4)_3,Na_2SO_4,5H_2O$, has also been prepared[2] The violet acid salt forms with rubidium and ammonium sulphates the compounds $3Ti_2(SO_4)_3,Rb_2SO_4,24H_2O$ and

$$3Ti_2(SO_4)_{35}(NH_4)_2SO_4,18H_2O \text{ (Stahler)}$$

Normal Titanium Disulphate, $Ti(SO_4)_2,3H_2O$, is formed by the oxidation of the sesquisulphate with nitric acid, and on evaporation remains as a transparent, yellowish, deliquescent, amorphous mass The sulphate forms double salts, such as $K_2SO_4,Ti(SO_4)_2,3H_2O$, $Ti(SO_4)_2,CaSO_4$, etc[3]

Basic Titanium Sulphate, $(TiO)SO_4$, is obtained as a hard white mass by dissolving dry titanic acid in boiling sulphuric acid and evaporating,[4] whilst crystals of $(TiO)SO_4,5H_2O$ are obtained by boiling titanic acid with alcoholic sulphuric acid and evaporating[5] Several other basic sulphates have been prepared[6] by heating titanium dioxide with sulphuric acid in sealed tubes at different temperatures

TITANIUM AND NITROGEN

379 Titanium is one of the elements which very readily combine with mtrogen, and two compounds of these two elements are known

Titanium Mononitnde, TiN, is obtained by heating titanium dioxide very strongly in the electric furnace in presence of mtrogen A better method[7] is to heat titanium dioxide in a

[1] **Piccini, *Gazz* , 1895, 25, [2], 542, *Zeit anorg Chem* , 1898,17, 355**
[2] **Spence and Son, German Patent, 149602 (1904)**
[3] **Weinland and Kuhl, *Zert anorg Chem* , 1907, 64, 253**
[4] **Merz, *J pr Chem* , 1866, 99, 157**
[5] **Rosenheim and Schutte, *Zert anorg Chem* , 1901, 26, 239**
[6] **Blondel, *Bull Soc chim* , 1899, [3], 21, 262** [7] **Ruff, *Ber* , 1909, 42, 900**

porcelain boat for six hours at 1400-1500° in a stream of ammonia It is a bronze-yellow mass which has a specific gravity of 5 18 and is hard enough to scratch rubies and cut diamonds[1]

Titanium Nitride, Ti_3N_4 —When the compound $TiCl_4,4NH_3$ is heated a copper coloured compound is obtained,[2] which was regarded as the element until Wohler,[3] showed that it contained mtrogen and gave it the formula Ti_3N_4 Wohler also prepared a dark blue compound with a coppery sheen to which he gave the formula TiN_2 It has been shown by Schneider[4] that the former substance contains oxygen and the latter does not exist The tetranitride has been prepared by Ruff and Treidel[5] as follows The compound $TiBr_4,8NII_3$ is washed with liquid ammonia to form an orange-coloured substance of the approximate composition $2Ti(NH_2)_4,TiBr_4,8NH_3$ The compound is then treated with a solution of an equivalent amount of potassamide in liquid ammonia, when monopotassium titanium di-imide, Ti(NH)NK, and titanic nitride are formed The nitude has a brown colour and is decomposed by water into ammonia, and by heat into TiN and nitrogen

TITANIUM AND CARBON

380 *Titanium Carbide,* TiC, is prepared by fusing titanium dioxide with an excess of carbon, or with calcium carbide in the electric furnace, and is thus obtained as a mass having a crystalline fracture, and a specific gravity of 4 25, it is not attacked by hydrochloric acid, is only slowly dissolved by aqua regia, and does not decompose steam at 700° In other respects it resembles metallic titanium, but burns more readily in oxygen[6]

Steel-grey crystals of titanium carbide have been obtained from cast iron prepared from titaniferous ores[7] Titanium carbide is used for making arc lamp electrodes

Titanium Cyanonitride—When iron ores contaimng titanium are reduced in the blast-furnace small bulhant copper-coloured cubes, which are hard enough to scratch glass and are almost infusible, are found in cavities both of the slag and of the metal A mass containing as much as 80 lb has been found in a single

[1] Moissan, *Compt rend* , 1895, **120,** 290
[2] Liebig, *Pogg Ann* , 1830, **21,** 259
[3] *Annalen,* 1850, 73, 34 [4] *Zeit amorg Chem* , 1895, 8, 81
[5] Ruff and Trerdel, *Ber* , 1912, 45, 1364
[6] Moissan, *Compt rend* , 1895,**120,** 290, 1897,**125,** 839
[7] Sh mer, *Chem News* , 1887, **55,** 156

blast-furnace in the Harz This substance was examined by Wollaston in 1822 and believed by him to be metallic titanium, [1] but Wohler in 1848 showed that it contained nitrogen and cyanogen, and gave to it the formula $Ti(CN)_2,3Ti_3N_2$ He likewise obtained it artificially [2] by heating a .nixture of ferrocyanide of potassium and titanium dioxide in a well-closed crucible at a temperature sufficient to melt nickel Titanium cyanonitride can also be prepared by heating to whiteness a mixture of titanium dioxide and charcoal in a tube of gas carbon in a stream of dry nitrogen (Deville and Wohler) [3] A third method of preparation is to fuse potassium cyanide in the vapour of titanium tetrachloride (Wohler) It has a specific gravity of 5 28, and is attacked only by a mixture of nitric and hydrofluoric acids When ignited in a current of steam it is decomposed as follows

$$Tr(GN)_{2J}3Tr_3N_2 + 20H_2O = 2HCN + TrO_2 + 6NH_3 + 10H_2$$

Chlorine also decomposes this substance at a red heat, titanium tetrachloride and a volatile sublimate consisting of a compound of titanium tetrachloride and cyanogen chloride being formed When fused with potash ammonia is given off, potassium titanate being produced

DETECTION AND ESTIMATION OF TITANIUM

381 Titanium is distinguished from tin inasmuch as its oxides are not reduced to the metallic state when heated on charcoal before the blowpipe With microcosmic salt titanium dioxide yields a colourless bead in the outer flame, but m the inner flame the bead is yellow whilst hot and assumes a violet colour on cooling According to Riley, the delicacy of this reaction is increased by melting metallic zinc in the microcosmic bead heated on charcoal, a distinct coloration being then obtained when the zinc is burnt away, even with minute quantities of titamum When fused in the microcosmic bead with addition of a small quantity of an iron salt in the reducing flame, a bright-red bead is obtained Titarium compounds do not colour the gas-flame, but both the spark and the arc spectrum show an enormous number of bright lines, chiefly in the blue and green, which have been carefally mapped by Thalen and others

[1] *Phil Trans* , **1823, 113, 17** [2] *Annalen,* 1850, **73,** 34, **74, 212**
[3] *Ibid* , **1857,103,** 230

Metallic zine placed in a hydrochloric acid solution of titanic acid evolves hydrogen and the liquid assumes a violet-blue colour, a dark violet precipitate is formed if the solution be not too dilute, and this gradually turns white by oxidation The violet-blue solution when diluted with water assumes a rose-colour, and this reaction serves for the detection of small quantities of titanium Sodium throsulphate when boiled with a nearly neutral solution of a titanate precipitates the whole of the titanic acid, and this reaction serves as a means of separating titanium from iron and the metals of the group

In order to remove silica, when present, the mixture is evaporated with hydrofluoric acid, the silicon being expelled as silicon tetrafluoride

Titanium is always estimated gravimetncally in the form of titanium dioxide, this being thrown down from its solutions in acids by ammonia, or by saturating with sulphur dioxide and boiling Titanium may also be estimated volumetncally by reducing titanirum dioxide to titanium sesquioxide by means of zine in an acid solution and subsequently oxidising with standard permanganate

Atomic Weight of Titanium —The atomic weight of titanium was first determined by Rose [1] in 1829 by decomposing titanium tetrachloride with water, weighing the titanic acid formed and estimating the chlorine in the filtrate, the number found being 47 72 A redetermination was made in 1885 by Thorpe,[2] who analysed pure titanium tetrachloride and tetrabromide, the amount of silver required for complete precipitation of the halogen, the amount of silver halide formed, and the quantity of titanium dioxide yielded by each being ascertained, the average of the results of the six series of experiments gave the number 48 1, which is at present (1922) adopted

ZIRCONIUM Zr = 90 6 At No 40

382 In 1789 Klaproth found a new earth in the mineral zircon, to which he gave the name of zirconia He discovered in 1795 that the same earth was contained in hyacinth, a mineral found in Ceylon, and he thus ascertained the truth of Werner's previous supposition that these two minerals were identical Zircon and hyacinth possess the formula $ZrSrO_4$, and are more or less coloured by ferric oxide Zirconium is found in a few other rare minerals,

[1] *Pogg Ann* , 1829, 15, 145 [2] *Journ Chem Soc* , 1885, 47, 108

and occurs in appreciable quantities in Norwegian granite, with thoria and several of the rare earths[1]

The metal zircomum was first obtained by Berzelms in the form of an iron-grey powder by heating potassium zirconofluonde with potassium The metal can also be obtained, according to Troost, by passing the vapour of zircomum dhlonde, $ZrCl_4$, over heated sodium The ignited amorphous metallic powder thus obtained is so finely divided that it passes through the pores of filter paper, but it assumes a metallic lustre under the burmsher The amorphous metal may also be prepared by heating zirconia with magnesium powder,[2] and thus prepared it has a velvet-black appearance like wood charcoal

Wedekind[3] has obtained a metal containing 99 09 per cent of zirconium He heats an intimate mixture of $Zr0_2$ and calcium shavings in an evacuated iron vessel When the reaction is completed the contents of the tube are treated successively with water, acetic acid, dilute hydrochloric acid, and water, all the operations being conducted in absence of air The residual powder is then washed with acetone and dried *in vacuo* at 250-300°, finally, at a temperature of 800-1000°, the powder sinters, but does not melt, it exhibits a mirror-hke brilliancy on polishing Zirconium of 99 3 per cent purity has been obtained by the action of sodium on potassium zirconofluoride by the same method[4] as that described for titanium *(q v)*

Crystallised zirconium was first obtained by heating potassium zirconofluoride with aluminium at the temperature of melting non, it is, however, best prepared by heating zircoma in the electric furnace with an insufficient quantity of carbon for its complete reduction, and is thus obtained as a metallic button containing some zirconia but free from carbon and nitrogen It may also be obtained by heating the carbide with zircoma in a similar manner,[5] or by heating potassium zirconofluonde with magnesium in the electric furnace [6]

Crystallised zirconium forms broad, apparently monochnic,

[1] Phipson, *Chem News,* 189G, 73, 145 See also Marden and Rich, *Bur Mines Bull,* 19.21,186

[2] Phipson, *Compt rend,* 1865, 61, 745, *Chem Newt,* 1906, 93, 119, Winkler, *Ber ,* 1890, 23, 2604

[3] *Annalen,* 1913, 395, 149, compare also Weiss and Neumann, *Zeit anorg Chem ,* 1910, 65, 248

[4] Podzsus, *Zed anorg Chem,* 1917, 99, 123 See also Marden and Rich, *J lnd Eng Chem ,* 1920,12, 651

[5] Moissan, *Compt rend ,* 1893,116, 1222, Troost, *ibid ,* 1428

[6] Wedekind, *Zett Elektrochem ,* 1904, 10, 331

plates, has a specific gravity of 4 08 at $15^{0},^{1}$ and is hard enough to scratch glass and rubres It is only very slowly oxidised in the air even at a white heat, but burns in the oxy-hydrogen flame, and yields the tetrachloride when heated to dull redness in chlorine or hydrogen chloride It is also dissolved by caustic potash with evolution of hydrogen It is only slowly attacked by acids, with the exception of hydrofluoric, even on heating, but is rapidly oxidised by aqua regra The amorphous metal readily takes fire in the air on warming

ZIRCONIUM COMPOUNDS

383 *Zirconium Oxide or Zirconia,* ZrO_2 —In order to prepare this oxide zircon is ignited and then quenched in water The powdered mineral is mixed with three to four times its weight of acid potassium fluoride, and gently heated in a platinum vessel until all moisture has been driven off The platinum crucible is then placed in a Hessian one, and both are well covered and exposed for two hours to the strongest heat of a wind furnace The porcelain-like mass thus obtained is boiled with water containing hydrofluoric acid, and the insoluble potassium silico-fluonde filtered off On cooling the solution, crystals of potassium zirconofluonde are deposited, and these are purified by recrystal-hsation The pure salt is then heated with sulphuric acid until all the hydrofluoric acid is driven off, the residue is dissolved in water, and the zirconia precipitated in the cold by ammonia [2]

In order to avoid the use of hydrofluoric acid, the very finely powdered zircon may be treated as follows It is first fused with hydrogen potassium sulphate and the fused mass repeatedly boiled out with water containing sulphuric acid, when a residue of basic zirconium sulphate, $4Zr0_2,3SO_3,14H_2O$, is obtained, which is next fused with caustic soda in a silver basin This is then lixiviated with water, the residual zirconia, which contains soda, washed with hot water and dissolved in hot concentrated sulphuric acid, the solution filtered and precipitated with ammonia [3] The precipitate thus obtained consists of zirconium hydroxide, which readily parts with its water on heating When heated at 140-200° it has the composition ZrO_2,H_2O, and is known as zircomc acid A hydrated oxide containing less water than this is obtained by repeatedly boiling zirconium oxychlonde

[1] **Meyer,** ***Monatsh*** **, 1899, 20, 793** [2] **Homberger,** ***Annalen,*** **1876, 181, 232**
[3] **Franz,** ***Ber,*** **1870,3,58**

with water and drying the precipitate at 100°, this has been called metazirconic aqjd[1] According to van Bemmelen,[2] however, these substances arerprobably not true hydroxides, ,but colloidal zircoma, containing water in the form of a hydrogel The hydroxide is slightly soluble in water, and colours yellow turmeric paper brown When precipitated and washed in the cold, it is easily soluble in dilute acids, if, however, it be precipitated from a hot solution, or washed with boiling water, it is soluble only in concentrated acids When heated to incipient redness it is converted into zircoma with evolution of heat The oxide thus obtained has the specific gravity[3] 5 489, and is only slightly soluble even in hydrofluoric acid, but dissolves on heating in a mixture of two parts of sulphuric acid and one part of water An hydroxide of the formula $Zr_5O_8(OH)_7$, which gives rise to a chloride, $Zr_5O_8Cl_4,22H_2O$, and a sulphate, $Zr_5O_8(SO_2)_2,xHI_2O_4$, has been described by Rodd[4]

Zircoma can be obtained in the crystalline state in the form of tetragonal prisms isomorphous with cassitente and rutile and having a specific gravity of 5 71[5] For this purpose, the amorphous oxide is fused with borax in a porcelain furnace, the fused residue being boiled out with sulphuric acid

Pure zirconra melts at 3000°, and the fused product has a specific gravity 5 89 The linear coefficient of expansion is 0 00000084, nearly the same as that of fused quartz

Zirconira is employed in the preparation of rods for the Nernst electric lamp Crucibles, etc , can be made by mixing zircoma with 10 per cent of magnesia Crucibles made from zircoma mixed with 1-3 per cent of yttria[6] do not soften until 2400° Platinum can be melted in such crucibles with the oxy-hydrogen flame Quartz can also be melted without destroying the crucible[7]

Zircoma, like the dioxides of the other metals of this group, acts as an acid-forming oxide, and yields salts corresponding to the metasihcates and metatitanates

Sodium Zirconate, Na_2ZrO_3, obtained by fusing the oxide with sodium carbonate, forms a crystalline mass which is de-

[1] Ruer, *Zert anorg Chern* , 1905, 43, 282
[2] *Zert anorg Chern* , 1906, 49, 125
[3] Venable and Belden, *J Amer Chem Soc* , 1898, 20, 273
[4] *Journ Chem Soc* , 1917, 111, 396
[5] Nordenskrold, *Pogg Ann* , 1861,114, 612
[6] Ruff and Lauschke, *Zert anorg Chem* , 1916, 97, 73
[7] Weiss and Lehmann, *Zeit anorg Chem,* 1909,65,178

composed by water with separation of zirconia When heated with an excess of sodium carbonate to whiteness the salt Na_4ZrO_4 is produced This is again decomposed by water with formation of hexagonal tablets paving the composition $Na_2Zr_8O_{17},12H_2O$ = $Na_2O,8Zr0_2,12H_2O$

Zirconrium Sesquioxide[1] Zr_2O_3, is prepared as a green powder by the combustion of zirconium hydride On ignition in air, it is converted into the dioxide

Zirconium Peroxide, $Zr_2O_5,9H_2O$, is obtained as a white powder when hydrogen peroxide is added to a solution of zirconium sulphate Under certain conditions a hydrated oxide, $ZrO_3,5H_2O$, is formed,[2] and this when treated with excess of hydrogen peroxide and an alkali hydroxide is stated to form the alkali salts of *perzirconic acid,*[3] $H_4Zr_2O_{11}$

Zirconium and Hydrogen —When zircoma is heated with magnesium powder in a current of hydrogen the latter is absorbed, the product containing zircomum hydride, ZrH_2, together with zirconia and perhaps a lower oxide[4] The hydride is also formed when hydrogen acts on the metal at a red heat [5] It burns in the air to form the sesquroxide

Zirconium Fluoride, ZrF_4, is obtained by heating zircoma with acid ammonium fluoride The residual mass is easily soluble in water containing hydrofluoric acid, and crystallises in glistening, triclnic tablets having the composition $ZrF_4,3H_2O$

According to Chauvenet, the hydrate, $ZrF_4,3H_2O$, is really $ZrOF_2,2HF,2H_2O$, for on heating to 140° water is lost and $ZrOF_2,2HF$ left, whilst at higher temperatures the compound $ZrOF_2$, is formed [6] The anhydrous compound sublimes and forms small, highly refractive prisms with a density 4 433 It dissolves slightly in water, and when the solution is warmed, zircomum hydroxide is precipitated It combines with liquid ammonia to form $5ZrF_2,2NH_3$

Zirconium fluoride forms a series of double salts with other fluorides which are isomorphous with the corresponding silicofluondes, titanifluondes, and stannifluorides

Potassium Zirconofluonde, K_2ZrF_6, is obtained by igniting

[1] Weiss and Neumann, *Zert anorg Chem* , 1909, **65,** 248
[2] Bailey, *Journ Chem Soc* , 1886, 49, 481
[3] Pissarjewsky, *J Buss Phys Chem Soc* , 1900, 32, 609
[4] Winkind, *Ber* , 1891, 24, 888
[5] Wedekind, *Ann* , 1913, **305,** 149, Weiss and Neumann, *Zed anorg Chem* , 1910,65,248
* *Compt rend,* **1917,164,** 727

zircon with acid potassium fluoride or by pouring a solution of potassium fluoride into an excess of zirconium fluoride solution. It crystallises in shall, acute, rhombic prisms, and dissolves at 2° in 128, at 15° in 71, and at 100° in 4 parts of water

When zirconium hydroxide is dissolved in the smallest quantity of hydrofluoric acid and the liquid is poured into a conoentrated solution of neutral potassium fluoride, the salt K_2ZrF_6,KF is precipitated, and crystallises from boiling water in fine needles

If sodium fluoride and zirconium fluoride are mixed in any proportion, the salt $Na_2ZrF_6,4NaF$ is produced It forms small, monoclinic crystals which dissolve in 258 parts of water at 18°, and at 100° in about 60 parts of water

Ammonium salts, corresponding to the salts of potassium, and other double fluorides,[1] are known

Zirconium Chloride, $ZrCl_4$, is obtained by passing chlorine gas over a heated mixture of zircoma and charcoal, by the action of chlorine or hydrogen chloride on the heated metal, when it is obtained as a white, crystalline sublimate by heating the dioxide with phosphorus pentachlonde at 190° in a sealed tube, and best of all by heating the dioxide in a stream of chlorine and carbon tetrachloride at 800° It may be recrystalliesd from hydrochloric acid, but it is doubtful whether it has ever been obtained in this way free from the oxychlonde Zirconium chloride forms with ammonia the compounds[2] $ZrCl_4,8NH_3$ and $ZrCl_4,3NH_3$ On addition of water to the chloride heat is evolved, and zirconium oxychloride, $ZrOCl_2$, is formed, which remains dissolved in the acid solution The same compound is obtained by dissolving zirconium hydroxide in dilute hydrochloric acid, and on evaporation crystallises out in prismatic needles belonging to the tetragonal system, and having the composition $ZrOCl_2,8H_2O$[3] These are readily soluble in water, have an astringent taste, and when heated to 50° lose water, forming more basic oxychlondes, whilst by treatment with concentrated hydrochloric acid crystals of $ZrOCl_2,6H_2O$ and $ZrOCl_2,3F_2O$ have been obtained[4]

Zirconium Bromide, $ZrBr_4$, is prepared in a similar way to the chloride, and forms a white, crystalline powder which is easily

[1] See also Wells and Foote, *Zeit anorg Ghent,* 1895, 16, 434, *Amer J Sci* , 1897, 3, 461

[2] Stahler and Denk, *Ber* , 1905, 38, 2611 Compare Matthews, *J Amer Chem Soc* , 1898, 20, 815

[3] Weibull, *Ber* , 1887, 20,1394

[4] Venable and Baskerville, *J Amer Chem Soc* , 1898, 20, 321,

volatilised at the temperature of the gas flame In contact with moist air or water it forms zirconium oxybromide, $ZrOBr_2$, which crystallises in needles, and may also be prepared by evaporating a solut on of the hydroxide in hydrobromic acid, when $ZrOBr_2,8H_2O$ separates out[1] With ammonia,[2] zirconium bromide gives the compounds $ZrBr_4,4NH_3$ and $ZrBr_4,10NH_3$ A number of oxybromides of the same types as the oxychlondes are known

Zirconium Iodide, ZrI_4, is obtained by passing hydrogen iodide over zirconium or the carbide at a bright red heat According to Dennis and Spencer,[3] it is a white, crystalline body which is insoluble in water and acids, Stahler and Denk,[4] however, state that it dissolves in water and acids, the aqueous solution depositing colourless crystals of the *oxyzodide,* $ZrOI_2,8H_2O$

Zirconium Sulphide—-When metallic zirconium and sulphur are heated together in a current of hydrogen they combine with evolution of heat to form a cmnamon-brown powder, which assumes a metallic lustre under the burnisher This is not attacked by most of the dilute acids, but dissolves slowly in aqua regia and readily in hydrofluoric acid When fused with potash, zirconia and potassium sulphide are formed

Zirconium Sulphate, $Zr(SO_4)_2$, is obtained by dissolving the oxide or hydroxide in sulphuric acid, evaporating, and heating nearly to redness It is a white mass which dissolves slowly but completely in cold, and quickly in hot water Hydrated crystals are obtained by concentrating a solution which contains free acid, and these swell up on heating, like alum The salt decomposes at a red heat, leaving a residue of pure zircorina The behaviour of zirconium sulphate in solution[5] is best represented by the formula $(ZrO)SO_4,H_2SO_4$, whilst the crystalline hydrated salt is $(ZrO)SO_4,H_2SO_4,3H_2O$, and not $Zr(SO_4)_2,4H_2O$, as was formerly thought If its solution be saturated with zirconium hydroxide a basic salt, $Zr(SO_4)_2,ZrO_2$ or $(ZrO)SO_4$, is formed, and this is obtained on evaporation as a hydrated mass If the normal salt be precipitated with alcohol an insoluble salt, $Zr(SO_4)_2,2ZrO_2$, is thrown down A large number of similar

[1] **Rosenheim and Frank,** ***Ber*** **, 1907, 40, 803**

[2] **Matthews,** ***J Amer Chem Soc,*** **1898, 20, 839, Stahler and Denk,** ***Ber,*** **1905,38,2611**

[3] ***J Amer Chem Soc,*** **1896,18, 673**

[4] ***Ber,*** **1904, 37, 1137**

[5] **Ruer,** ***Zert anorg Chem,*** **1904, 42, 187, Ruer and Levin bid1905 46, 440, Rosenheim and Frank,** ***Ber,*** **1907, 40, 8C**

basic sulphates have been described by Chauvenet[1] and Rodd[2]

Zirconium and Narogen —The nitride, Zr_2N_3, is pbtained by heating zirconium chloride to redness in a current of dry ammonia,[3] and also by heating zirconia and magnesium in a loosely-covered crucible[4] It is a brownish-green, crystalline powder which oxidises with incandescence when gently heated in air (Wedekmd) A nitride of the formula Zr_3N_8 is formed when the compound $ZrCl_4,8NH_3$ is heated to redness in nitrogen (Matthews) Bruere and Chauvenet[5] are unable to obtain the compound Zr_3N_8, but always obtain Z_3N_4, on heating ammoma derivatives of zirconium chloride

Zirconium Nitrate, $Zr(NO_3)_4$, is obtained as a yellow, gummy mass by dissolving the hydroxide in nitric acid and evaporating at a moderate heat If the solution be evaporated *in vacuo* over caustic soda and phosphorus pentoxide, extremely hygroscopic crystals of $Zr(NO_3)_4,5H_2O$ separate out[6] The existence of normal zirconium nitrate has been questioned by Chauvenet,[7] who finds that the concentration of a solution of this salt always leads to the loss of nitric acid and the separation of the basic salts, $ZrO(NO_3)_2,2H_2O$, at ordinary temperatures, and $ZrO(NO_3)_2,3\ 5H_2O$, at temperatures below 10° A number of other basic nitrates also exist

Zirconium Boride, Zr_3B_4, has been prepared by heating in the electric furnace a mixture of zirconium and boron,[8] it forms a steel-grey mass, consisting of microscopic crystals, and has the specific gravity 3 7

Zirconium Carbides—Zirconium combines with carbon to form two carbides having the composition ZrC_2 and ZrC The *dicarbide* is obtamed by heating zircoma with an excess of carbon in the electric furnace and has a metallic appearance and brilliant fracture, and is not decomposed by water even on heating The *monocarbide* is prepared in a similar manner, but the mixture of zirconia and carbon is placed in a carbon tube closed at one end, which is then heated in the electric furnace.

[1] *Compt rend* , 1917,**164,** 864, 946, **165,** 25, 1918,**167,** 24, 126
[2] *Journ Chem Soc* , 1917, **111,** 396
[3] Matthews, *J Amer Chem Soc* , 1898, 20, 840
[4] Wedekind, *Zert anorg Chem,* 1905, **45,** 385
[5] *Compt rend,* 1918V**167,** 201
[6] Rosenheim and Frank, *Ber* , 1907, 40, 803
[7] Chauvenet and Nicolle, *Compt rend,* 1918,**166,** 781, 821,
[8] Tucker and Moody, *Journ Chem Soc* , J 902, 81, 14

It has a grey colour and metallic lustre, and is hard enough to scratch quartz It is permanent in the air and is not decomposed by water, but burns brilliantly in oxygen [1]

Zirconium Silicids $ZrSI_2$—This compound is obtained by heating a mixture of potassium zirconofluoride, aluminium, sulphur, and sard, the whole being covered with a layer of magnesium powder [2] It forms small steel-grey crystals having the specific gravity 4 88 at 22°

Silicates of Zuconium—Of these, zircon or hyacinth, $ZrSrO_4$, is the most important It occurs in crystalline rocks, especially in granular limestone, schist, gneiss, syenite, and granite The chief localities are in alluvial sands in Ceylon, the Urals, in the Isle of Harris, in Greenland, in the gold districts of Australia, and in many places in North America Zircon crystallises in tetragonal prisms and pyramids (Fig 182), having an adamantine lustre, they are colourless in the pure state Usually, however, zircon is coloured red or yellow by ferric oxide The colourless and smoke-coloured varieties are termed jargon This variety exhibits a peculiar absorption spectrum, from which Sorby concluded that it contained a new element, to this he gave the name of jargonium, but subsequently he found that these lines were caused by the presence of uranium oxide An artificial jargon yielded a similar spectrum, though neither uranium nor zirconium compounds do so[3]

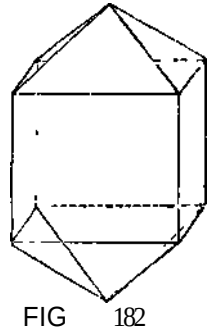

FIG 182

DETECTION AND ESTIMATION OF ZIRCONIUM

384 The reactions of the zirconium salts are very similar to those of the metals contained in cente and gadohnite A reaction of zirconium by which it is distinguished from the cerium metals is the formation of a basic potassium zircomum sulphate, insoluble in water and hydrochloric acid This salt is obtained by adding a hot solution of potassium sulphate to a concentrated solution of a zirconium salt This reaction also serves to separate zirconium from titanium, tantalum, and columbium Another method of separating zirconium from the metals of the

[1] Moissan, *Compt rend,* 1893,**116,** 1222, 1896,**122,** 651
[2] Honigschmid, *Compt rend,* 1906,**143,** 224.
[3] *Chem News,* 1870, **21,** 73

cerium and iron groups is to boil the solution 'with sodium throsulphate, when zirconium alone is precipitated as the throsulphate, this on washing and heating leaves a residue of zirconia

Titanic acid and thoria are also precipitated together with the zirconia by sodium throsulphate In order to separate these, ammonium oxalate is added to the hydrochloric acid solution, when the thoria is thrown down Ammonrum carbonate is now added to the filtered liquid, when, in the presence of the oxalate, only titanic acid is precipitated, the zirconia remaining in solution (Hermann) Zirconrum can readily be separated from iron, titanium, etc , by means of hydrogen peroxide, this precipitates it quantitatively from solutions of the sulphate as the hydrated peroxide (Bailey)

The spectrum of zirconium has been mapped by Thalen, and contains characteristic lines in the red and blue

Atomic Weight of Zirconium —The first accurate determination of the atomic weight of zirconrum was that of Mangnac,[1] who from the analysis of potassium zirconofluoride obtained the number 90 03 Bailey,[2] from the weight of zirconra yielded by a known quantity of pure zirconium sulphate, found the number 90 65, whilst Venables,[3] who estimated the zircoma obtained by heating the oxychlonde, $ZrOCl_2,3H_20$, found the number 90 78 A more recent determination made by the nephelometric method from the ratio 4Ag $ZrCl_4$ gives the value 91 76[4] The atomic weight now (1922) adopted is 90 6

HAFNIUM. At No 72

Thomsen in 1895 and Bury[5] in 1921 suggested on chemical grounds that the missing element immediately preceding tantalum in the periodic system should be a tetravalent homologue of zircomum Bohr has drawn the same conclusion from his theory of atomic structure (p 79) These views have now received considerable confirmation from the recently reported discovery by Coster and Hevesy,[6] using the method of *X-ray* spectroscopy (p 72), of a new element, of atomic number 72, in numerous zirconium minerals, in one of which it appears to be present to the extent of at least 1 per cent " It seems to

[1] ***Ann Chim Phys*, 1860, [3], 60, 257**
[2] ***Proc Roy Soc* , 1890, 46, 74** [3] ***J Amer Chem Soc* , 1898, 20, 119**
[4] **Venables and Bell, *J Amer Chem Soc* , 1917, 39, 1598**
5 / *Amer Chem Soc* , 1921, 43, 1602
[6] ***Nature*, 1923,113, 79**

be very probable that ordinary zirconium contains at least from 0 01 to 0 1 pes cent of the new element Especially the latter circumstance proves that the element 72 is chemically homologous to zirco num Experiments are in progress to isolate the new element and to determine its chemical properties For the new element we propose the name Hafnium (Hafniae = Copenhagen) "

The atomic weight of this element may be expected to be in the neighbourhood of 178

This discovery throws doubt on the claim of Urbain's rare-earth element, Celtium (p 829), to the position 72, though Dauvillier[1] has recently supported this claim by means of X-ray spectroscopy

THORIUM Th = 2324 At No 90

385 In the year 1815 Berzehus believed that he had found in several Swedish minerals a new earth to which he gave the name of thoria, but on further examination the substance turned out to be basic phosphate of yttrium On the other hand, in 1828,[2] he discovered a distinct earth in a mineral from the island of Lovon, in Norway, now termed thorite, and to this the name of thoria was given, as it agreed in many of its properties with the substance previously so named Besides being found in thorite, this substance was discovered in other rare minerals, thus by Wohler in pyrochlor, by Bergman and others in orangite, and by Karsten in monazite, a phosphate of cerium and lanthanum which contains 4-18 per cent of thoria Another source of thoria is the mineral euximite from Arendal, in which this earth was discovered by Mosander and Chydemus, and it has also been found in Norwegian granite[3] More recently it has been discovered in a mineral called thonanite occurring in Ceylon, which contains 70-80 per cent of thona, along with 11-15 per cent (UO_2 + UO_3), 2-3 per cent of lead, and varying amounts of metals of the cerium and ytterbium group and SiO_2 and CaO[4] It also contains helium, and when heated to redness evolves 9 c c of this gas per 1 gram[5]

[1] *Compt renl,* 1992, **174,** 1347
[2] *Poqg Ann* , 1829, 16, 385
[3] Phipson, *Chem News,* 1896, 73, 145
[4] Dunstan, *Nature,* 1904, 69, 510, Dunstan and Blake, *Proc Roy Soc,* 1905, 76, [-4 J, 253, Dunstan and Jones, *Proc Boy Soc* , 1906, **77,** [4], 646
[5] Ramsay, *J Chim Phys* , 1905, 3, 617

The following table gives the composition of some of these minerals [1]

Thorite from Lovon		Thorranite		Monazite from Ilmengebirge	
SrO_2	19 31	ThO_2	78 86	P_2O_5	28 50
ThO_2	58 91	UO_2	6 03	ThO_2	17 95
UO_3	1.64	UO_3	9 07	SnO_2	210
Fe_2O_3	3 46	$Ce0_2$		Ce_2O_3	26 00
Mn_2O_3	2 43	La_2O_3	1 02	La_2O_3	23 40
CuO	2 62	Di_2O_3		MnO	186
MgO	0 36	PbO	2 59	CaO	168
K_2O	O15	Fe_2O_3	O 46		
Na_2O	O 11l	CaO	113		10149
PbO	0 82	He	0 39		
SnO_2	0 01	P_2O_6	trace		
$A1_2O_3$	0 06	Insol in			
H_2O	9 66				
	99 54		99 75		

Thorium occurs also in other minerals containing the metals of the cerium group, as gadoniite and orthite In one of these minerals Bahr believed he had found another new metal, to which he gave the name wasium, but he afterwards convinced himself that this substance is identical with thorium [2]

Doubts have been put forward as to the individuality of thorium, and Baskerville,[3] from experiments on the fractional distillation of the chloride in a current of chlorine, concludes that it contains two other elements to which he gives the names berzelium and carolnium The work of other investigators, however, does not confirm this result, but points to the uniform nature of thorium [4]

At the present time thorium compounds are prepared on the manufacturing scale, as they form the chief constituent of the mantles employed for the Welsbach incandescent gas-burner, they are put on the market chiefly in the form of crude thorium nitrate which contains also the nitrates of zirconium and the cerite earths Thorite is the most convenient raw material, but is not found in sufficient quantity, and the crude material mostly employed is the Brazilian or American monazite sand,

[1] See Schilling, *Zeit angew Chem*, 1902, 15, 921, where a *resume* of the analyses of orangite and thorite is given [2] *Annalen*, 1864, 132, 227

[3] Baskerville, *J Amer Chem Soc*, 1901, 23, 761, 1904, 26, 922, *Ber*, 1905, 38, 1444 See also Brauner, *Proc Chem Soc* , 1901,17, 67

[4] Meyer and Gumprey, *Ber*, 1905, 38, 817, Eberhard, *ibid* , 826.

which has been formed by disintegration of the rock containing the mineral monazite*

Although the process adopted for the preparation on a large scale of thorium nitrate for the incandescent mantle industry is kept secret, the following is a general outline The powdered monazite sand either from Brazil or Carolina is moderately heated with concentrated sulphuric acid in cast-iron pans When the reaction is finished the partially solidified product is dissolved in cold water It is important that at this stage the solution be kept strongly acid, otherwise the phosphates of the metals will be deposited The undissolved residue of quartz, ferrotitanmm, zircon, magnetic oxide of iron, etc , is separated by decantation The solution is now fractionally neutralised with magnesia Owing to thorium phosphate being the least soluble of the phosphates, the first fraction consists mainly of this

The crude phosphate is dissolved in concentrated hydrochloric acid, oxalic acid added, when the thorium is precipitated as oxalate, together with small quantities of cerium and ytterbium metals The well washed precipitate is then treated with warm sodium carbonate solution The thorium goes into solution with traces of ytterbium metals, but the cerium remains undissolved as the double carbonate By treatment with alkali hydroxide the hydroxide is precipitated, or the oxalate is reprecipitated by means of hydrochloric acid In order to remove traces of impurities the oxalate or hydroxide is converted into sulphate with sulphuric acid and the sulphate purified by being several times recrystalhsed, the salt $Th(S0_4)_2,8H_20$ crystallising out In order to prepare the nitrate this salt is boiled with ammonia, by which means the hydroxide is produced This is well washed, and dissolved in nitric acid The solution is evaporated to dryness, and heated on the water-bath until on ignition it is found to contain 48 to 49 per cent of ThO_2, representing the nitrate with practically $4H_2O$ [1]

Metallic thorium is obtained by heating potassium thorium chloride with sodium in an iron cylinder Thus prepared, it forms microscopic hexagonal tablets, having the colour of nickel, and giving a silver-white streak It has also been prepared by the action of sodium vapour on the vapour of certain volatile organic compounds of thorium such as the acetylacetonate [2]

[1] Boehm, *Chemische Industrie*, 1906, 29, Nos 17-19, Dieseldorff, *ibid*, 1900,29,411

[2] Siemens and Halske, German Patent, 133959, 1900 See also Moissan and Honigschmid, *Ann Chim Phys* , 1906, [8], 8, 182

According to von Bolton,[1] thorium melts at 1450°, whilst Wartenberg[2] gives 1700° as the melting, point At ordinary temperatures the specific heat is 0 02787 It has a specific gravity of 11 0 (Nilson), and 11 32, but after heating and rolling 12 16 (v Bolton), and takes fire when heated in the air, burning with a bright flame, it dissolves with difficulty in hydrochloric acid, and is not attacked by aqueous alkalis, but is readily soluble in aqua regra,[3] with nitric acid it first dissolves rapidly, but soon becomes passive At 450° thorium combines with chlorine, bromine, iodine, and sulphur, with incandescence, at 650° it combines with hydrogen and introgen respectively to form the hydride and nitride Thorium is slightly more electropositive than magnesium, it forms alloys with copper, aluminium, zirconium, tungsten, and nickel In the case of nickel an intermetallic compound, Th_2Ni, has been isolated Thorium possesses the property of radioactivity, and this will be discussed in the chapter on this subject

COMPOUNDS OF THORIUM

386 *Thorium Dioxide* or *Thoria,* ThO_2, is obtained from thorite or orangite by heating the powdered mineral with a slight excess of sulphuric acid and a little water, the dried mass is powdered, heated to remove excess of sulphuric acid, and the residue carefully dissolved in six to seven parts of ice-cold water The solution is filtered from silica, and heated to the boiling point with ammonia The precipitated hydroxides are washed by decantation, dissolved in hydrochloric acid and precipitated with oxalic acid, the precipitate well washed by decantation, and ignited The thoria thus obtained still contains ceria, yttria, and a little manganese To obtain pure thoria the product is again dissolved in sulphuric acid, the excess of sulphuric acid removed by careful heating, the powdered salt dissolved in ice-cold water, and the temperature of the solution allowed to rise gradually to 20° A hydrated sulphate of thorium then separates out as an insoluble precipitate, the other metals remaimng in solution, and by repeating the process several times the thorium sulphate may be obtained perfectly pure It is then precipitated by ammonia and the hydroxide thus obtained ignited[4]

[1] *Zeit Elektrochem* , 1908,14, 809 [2] *Ibid,* 1909,16, 33
[3] Nilson, *Ber,* 1882,15, 2519, 2537, 1883, 16, 153
[4] Kruss and Nilson, *Ber,* 1887, 20, 1665

Pure thoria is a snow-white powder, which may be obtained in tetragonal crystals, isomorphous with those of cassiterite and rutile, by heating the amorphous powder with borax in a porcelain furnace They possess a specific gravity of 10 2, and dissolve in sulphuric acid only on long-continued boiling As already mentioned, thoria forms the chief constituent of the Welsbach incandescent mantles, the other and smaller constituents consisting of more basic oxides, that of cerium being usually employed (see p 815)

Meta-thorium Oxide is obtained by igniting the oxalate, and its peculiar deportment with volatile acids explains the fact that Bahr believed this to be the oxide of a new metal It was considered to be Th_3O_5, but has been found to have the empirical formula ThO_2, and, according to Wyrouboff and Verneml,[1] is a polymerised form of thorium dioxide If it be treated with hydrochloric acid or nitric acid no apparent action takes place, but if the excess of acid be evaporated on the water-bath, a brownish, semi-tiansparent residue is left, and this dissolves in water to form a translucent, opalescent liquid which appears milk-white in reflected light, and yields a precipitate with acids This is due to the fact that the oxide forms salts with these acids without loss of water, and these are soluble in water but not in the acids, and are therefore precipitated again by addition of the acids to the solution If the solution be treated with ammonia and the precipitate dried at 100°, a compound having the composition $Th_4O_7(OH)$ is obtained and this is insoluble in acids[2]

Thorium Peroxide, Th_2O_7 —This unstable compound is produced when hydrogen peroxide is added to the sulphate or acetate, and then excess of ammonia added[3] It forms a gelatinous precipitate which on keeping slowly gives up oxygen, being converted into ThO_3[4]

Thorium Hydride, ThH_4, is obtained by heating thorium to a dull red heat in hydrogen[5] It is not acted upon by water, but dissolves in hydrochloric acid with evolution of hydrogen When heated in air, it decomposes with the evolution of hydrogen At 390° it has a dissociation pressure of one atmosphere

[1] *Compt rend*, 1898, **127,** 863, *Zeit anorg Chem*, 1901, 28, 90, *Ann Chim Phys*, 1905, [8], 6, 441 See also Stevens, *Zeit anorg Chem*, 1901, 27,41

[2] Cieve, *Bull Soc chim*, 1874, **21,** 115

[3] Wyrouboff and Verneuil, *Ann Chim Phys* , 1906, [8], 6, 441

[4] Pjssarjewski, *Zeit angew Chem* , 1902, **31,** 359

[5] Matignon and Delepine, *Compt rend* , 1901,**132,** 36

387 *Salts of Thorium*—The salts of thorium are colourless, and when soluble possess a strongly astringent taste

Thorium Fluotids ThF_4, is obtained by the addition of hydrofluoric acid or a fluoride to a solution of a thorium salt as a gelatinous precipitate which passes into a heavy white powder, $ThF_4,8H_2O$, which loses 4 molecules of water in a vacuum and produces $ThF_4,4H_2O$ At 110° in a current of hydrogen the hydrate, $ThF_4,2H_2O$, is formed, whilst at 250° the whole of the hydrates yield the basic fluoride, $Th(OH)F_3,H_2O$ The oxyfluonde, $ThOF_2$, is formed when $ThF_4,4H_2O$ is heated at 800° in a current of hydrogen fluoride, or by igniting thorium sihcofluonde in a current of hydrogen The same powder is produced by the action of hydrofluoric acid on thona The anhydrous product is obtained by leading hydrogen fluoride over anhydrous thorium chloride or bromide heated to 350-400° [1]

Potassium Thorojluoride, $K_2ThF_6,4H_2O$, is obtained by boiling the hydroxide with potassium fluoride and hydrofluoric acid, in the form of a heavy, black powder When a solution of the chloride is precipitated with acid potassium fluoride the compound $K_2ThF_6,4ThF_4,H_2O$ is thrown down Other double fluorides with potassium fluoride are known, but as they are all insoluble in water and hydrofluoric acid, it is uncertain whether they are definite compounds or mixtures [2]

Thorium Chloride, $ThCl_4$—This is obtained by heating the oxide mixed with carbon in a current of chlorine, by heating a mixture of the dioxide and phosphorus pentachloride in an evacuated tube, by heating the dioxide at a red heat in a current of carbon monoxide and chlorine, vapour of carbon tetrachloride, chlorine and sulphur monochloride, or phosgene It has the specific gravity 4 59, melts at 820° (Moissan and Martinsen),[3] and sublimes in white, shining tablets, its vapour density being 12 42, corresponding to the above formula It deliquesces on exposure to the air, and its solution may be obtained by dissolving the hydroxide in hydrochloric acid The anhydrous chloride combines readily with ammonia to form a series of compounds with 4, 6,7,12, and 18 molecules of ammonia These compounds are all formed by the direct action of either gaseous or liquid ammonia on the anhydrous chloride and on keeping lose ammonia and form the compound $ThCl_4,4NH_3$ This latter compound is stable up to 120°, at 250° it is converted into the *tetra-amide,*

[1] Chauvenet, *Compt rend,* 1908, **146,** 489
[2] Rosenheim, Samter, and Pavidsohn, *Zeit anorg Chem,* 1903, 36, 424
[3] *Compt rend,* 1905,**140,** 1510

$Th(NH_2)_4$, and at a red heat into the *di-imide*,[1] $Th(NH)_2$ The strongly concentrated solution solidifies to a fibrous, crystalline mass which on heating emits hydrogen chloride It forms hydrates with 2, 4, 7,8, and 9 molecules of water, whilst a number of oxy- and hydroxy-chlondes have been described[2] It forms with the chlorides of the alkali metals easily soluble double salts, as $KCl,2ThCl_4,18H_2O$

Thorium forms a bromide and an iodide which are similar in their behaviour to the chloride

Thorium Sulphide, ThS_2 —The metal burns in sulphur vapour with great brilliancy, forming a yellow powder which exhibits a metallic lustre under the burnisher, and has probably the above composition (Berzelms) It has been prepared pure by passing dried hydrogen sulphide over thorium sulphate at a low red heat It is a yellow powder which inflames spontaneously in the air[3] When carbon disulphide vapour is passed over thorium dioxide heated to redness it yields the *oxysulphide,* ThOS, as a light brown substance[4]

Thorium Sulphate, $Th(S0_4)_2$, is obtained by dissolving the oxide in hot concentrated sulphuric acid, or by rubbing up powdered thorite or orangite to a paste with sulphuric acid, and heating the mixture to 500° until all the excess of sulphuric acid is driven off The mass is then treated with cold water and boiled, a crystalline precipitate remains, and this may be purified by repeated solution in cold water and reprecipitation by boiling If the solution be allowed to evaporate at the ordinary temperature, transparent monochnic crystals of $Th(S0_4)_2,9H_20$ are deposited, whereas above 43° a hydrate with $4H_2O$ is formed Other hydrates with 2, 6, and 8 molecules of water are known[5] Thorium sulphate forms double salts with the sulphates of the alkali metals, $Th(SO_4)_2,2K_2SO_4,2H_2O$ crystallises in regular prisms, which are easily soluble in water but do not dissolve in a solution of potassium sulphate Thorium sulphate forms a number of basic sulphates, and combines with pyridine, quinolme, phenylhydrazine, and diethylamine to form well crystallised derivatives

[1] Chainenet, *Compt rend,* **1910, 151,** 387, *Ann Chim Phys,* **1911,** [8], **23,** 275

[2] Rosenheim and Schilling, *Ber* , 1900, 33, 977, Rosenheim, Samter, and Pavidsohn, *Zeit anorg Chem* , 1903, 35, 424, Krusg, *ibid,* 1897, 14, 361

[3] Hauser, *Zeit anorg Chem* , 1907, 53, 74 Compare also Duboni, *Compt rend,* 1908, **146,** 815

[4] Kruss, *Zeit anorg Chem* , 1894, 6, **49**

[5] Roozeboom, *Zert physikal Chem,* 1890, 5, **198**

Thorium and Nitrogen—A nitride, Th_3N_4, is formed[1] when metallic thorium is heated in a current of nitrogen, and when the carbide is heated. in ammonia or the di-imide in either ammonia or nitrogen,[2] whilst a nitride of the same composition is obtained by reducing the dioxide with magnesium or aluminium in an atmopshere of nitrogen[3] The latter compound however, differs from the former in that it is not decomposed by water

Thorium Nitrate, $Th(NO_3)_4$,$12H_2O$, is a very soluble salt crystallising in large, deliquescent tablets Nitrates have also been obtained crystallising with $6H_2O$ and $5H_2O$,[4] and many double salts with other mtrates are known[5] Complex compounds with antipyrme, pyridine, qumolme, and diethylamme have also been prepared

The *phosphate* is insoluble both m water and phosphoric acid

Thorium Sondes, ThB_4 and ThB_6, have been prepared by heating thorium dioxide with amorphous boron in the electric furnace[6]

Thorium Carbide, ThC_2, is prepared by heating thona with sugar charcoal in the electric furnace, and forms a crystalline mass which is only slightly affected by concentrated acids but readily dissolves in dilute acids and is decomposed by water with evolution of a mixture of methane, ethylene, acetylene, and hydrogen[7]

Thorium Sihcide, $ThSi_2$, is obtained by heating a mixture of the double fluoride of potassium and thorium, potassium silicofluonde, and powdered aluminium at 1200°, or by heating silicon with thona in the electric furnace[8] It forms tetragonal plates of specific gravity 7 96

Thorium Carbonates —No normal metacarbonate, $Th(CO_3)_2$, of thorium has been obtained, but the *ortho-carbonate,* $ThC0_4$, is known This compound is obtained by treating thorium hydroxide with caibon dioxide under a pressure of 30-40 atmospheres At ordinary pressures a basic carbonate, $Th(OH)_4C0_3$, is obtained When ammonium carbonate solution is added to solutions of thorium salts precipitates of basic carbonates are

[1] Matignon and Del(Spme, *Compt rend,* **1901,132,** 36

[2] Chauvenet, *Ann Chim Phys* , 1911, [8], **23,** 425

[3] Kohlschutter, *Annalen,* 1901, **317,** 158 Compare Matignon and Deltpine, *Ann Chim Phys* , 1907, [8], 10, 130

[4] Fuhse, *Zert angew Chem* , 1897, 4, 115

[5] Meyer and Jacoby, *Zeit anorg Chem* , 1901, 27, 359

[6] Bmet du Jassonneix, *Compt rend* , 1905, **141,** 191

[7] Moissan, *Compt rend,* 1896, **122,** 573 see also Moissan and Ftard, *Ann Chim Phys* , 1897, [7], **12,** 427

[8] Homgsohmid, *Compt rend,* 1906, **142,** 280

obtained These dissolve in excess of alkali carbonates and yield solutions from which crystalline double carbonates of the type $3Na_2C0_3Th(C03)2,12H_2O$ may be separated Thorium carbonate forms a double carbonate with thallium carbonate of the formula $Th(C0_3)_2,3Th_2CO_3$

DETECTION AND ESTIMATION OF THORIUM

388 The compounds of this metal give no characteristic blowpipe or flame reaction The alkalis and ammonium sulphide precipitate from its solutions the hydroxide insoluble in excess, and the carbonates give rise to a precipitate of a basic carbonate, which dissolves in an excess of the reagent Ammonia produces no precipitate in this solution as it does in the corresponding one containing zirconium Another characteristic property of thorium is its reaction with potassium sulphate, and especially the fact that the thiosulphate is thrown down from thorium solutions on addition of potassium thiosulphate, a reaction by which this metal may be separated from the metals of the cerium group In order to separate it from titanium, columbium, and tantalum, ammonium oxalate is added to the solution, when the thonum alone is precipitated, if, however, an excess of ammonium oxalate be used the thorium oxalate dissolves Thorium can be separated from zirconium by throwing down both metals as oxalates by ammonium oxalate, and then adding an excess of oxalic acid, when the zirconium oxalate dissolves completely, leaving behind the oxalate of thorium Thoimm is estimated as the oxide, obtained by igniting the precipitated hydroxide

The Atomic Weight of thorium was determined by several chemists without concordant results Thus Berzelms[1] found 235 5, and Delafontame[2] 229 7 as the mean of several well-agreeing analyses of the sulphate Cleve, by the same method, obtained the number 232 6, whilst analyses of the oxalate yielded him the number 232 2 On the other hand, Kruss and Nilson, by analysing the carefully purified sulphate, obtained as a mean of several consistent experiments,[3] the number 232 4, which is now (1922) adopted

[1] *Pogg Ann* , 1829, 16, 385 [2] *Arch Sci phys nat*, 18b3,18, 343
[3] *Ber* , 1887, 20, 1665 Compare Meyer and GuAiperz, *Ber* , 1005, 38, 817

THE GERMANIUM GROUP.

GERMANIUM Ge = 72 5 At No 32

389 This element was discovered in 1886 by Winkler in the course of an investigation of a new silver mineral found at Freiberg in 1885, and termed argyrodite, $GeS_2,4Ag_2S$ The preliminary investigation led him to suppose that the new element would occupy the vacant place between antimony and bismuth in the periodic classification,[1] but further examination showed that the new element was tetravalent, and identical with the ekasilicon predicted by Mendeleev The close agreement between the predicted properties of the element and its compounds and those actually observed by Winkler, has already been mentioned (p 70)

Germanium is an extremely rare element argyrodite and canfieldite,[2] a mineral of similar composition from Bolivia, contain 6—7 per cent of the metal, but these are both rare Traces of germanium have been found in several minerals, particularly in zinc blendes, the richest source of the element now known being retort residues from the smelting of zinc from certain localities It is separated by a process depending on the volatility of the tetrachloride, 100 grams of the impure zinc oxide are dissolved in 200 c c of concentrated hydrochloric acid On distillation m the presence of chlorine, or some other oxidising agent which prevents arsenic from volatilising, the distillate which passes over between 121° and 140° contains all the germamum [3]

Metallic germanium is best obtained by the reduction of germanium dioxide with carbon at a full red heat The semi-crystalline regulus is washed with water to remove carbon, and fused with a little borax It is thus obtained as a greyish-white, brittle, lustrous metal, which frequently crystallises in octahedra,[4] has a specific gravity of 5 469, melts about 960°, and is not markedly volatile at 1350° It oxidises at a high temperature, is insoluble in hydrochloric acid, but dissolves in aqua

[1] *Ber* , 188b, 19, 210 [2] Penfield, *Amer J Sci* , 1893, [3], 46, 107
[8] Buchanan, *J Ind Eng Chem* , 1917, 9, 661 See also Dennis and Papish, *J Amer Chem Soc* , 1921, 43, 2131
* See Kolkmeijer, *Proc K Akad Wetensch Amsterdam,* 1922,25, 125

regia, and is converted by nitric acid into the dioxide It combines directly witji the halogens

COMPOUNDS OF GERMANIUM

390 Germanum forms two oxides, germanium dioxide, $Ge0_2$, and germanium monoxide, GeO

Germanium Dioxide, $Ge0_2$, the most important of these, is obtained from argyrodite as follows the powdered mineral, mixed with nitre and potassium carbonate, is introduced in small quantities at a time into a red-hot Hessian crucible On cooling, two layers are obtained, the upper one, which contains all the germanium, is powdered, extracted with water, the solution treated with sulphuric acid, and evaporated to dryness The acid residue dissolves in cold water, but almost all the germanium is deposited as oxide on standing, the remainder is precipitated as sulphide and converted into oxide by heating with nitric acid To purify the crude oxide, it is dissolved m hydrofluoric acid, and potassium fluoride added, potassium fluogermanate separates out, and is converted into a soluble thio-salt by fusion with potassium carbonate and sulphur, this* being decomposed by sulphuric acid, and the germanium precipitated as sulphide with sulphuretted hydrogen The sulphide, mixed with a little sulphuric acid and heated, yields a mixture of sulphide and oxide, which is conveited into the pure oxide by roasting and treating with nitric acid Thus prepared, it forms a dense, white powder, somewhat soluble in water, 1 part of the dioxide dissolving in 247 1 parts of water at 20°, and m 95 3 parts at 100°, the solution on evaporation deposits microscopic rhombic crystals Germanium dioxide has acid properties, but also dissolves m acids, it is readily reduced by carbon, sodium, and magnesium

No germamum hydroxide of definite composition has been prepared, but a colloidal hydrate is obtained by decomposing an alkaline solution of the dioxide with carbon dioxide

Germanous Oxide, GeO, is obtained by heating the dioxide with a small quantity of magnesium, or by heating the hydroxide, it forms a greyish-black powder The corresponding *hydroxide* $Ge(OH)_2$, is obtained as a yellow or yellowish-red precipitate by the action of alkalis on germanium dichlonde or germamum chloroform, and is soluble in excess of the alkali Hantzsch[1] has shown that when this excess is neutralised with hydrochloric acid, some germanous hydroxide remains in solution

[1] *Zeit anorg Chem,* 1902, 30, 289

From the conductivity of this solution and also of the alkaline solution, and from measurements of the rate at which the alkaline solution saponifies chyl acetate, he concludes that germanous hydroxide in aqueous solution is a weak monobasic acid of the same type as formic acid, and has the constitution HGeO OH, whilst in alkaline solution the salt HGeO ONa is present In aqueous solution part of the hydroxide is also present in the form $Ge(OH)_2$

Germanium Hydride, GeH_4, is formed when the tetrachloride is reduced with sodium amalgam The hydrogen evolved burns with a bluish-red flame which deposits a mirror on a cold porcelain surface A mirror may also be obtained in the same way as in Marsh's arsenic test, and on heating in air is converted into the white dioxide The hydrogen evolved as above gives a black precipitate with silver nitrate, and this on treatment with nitric acid gives germanium dioxide [1]

Germanium Tetrajluoride, GeF_4, has not been prepared in the anhydrous state, but large crystals containing three molecules of water are obtained by concentrating a solution of the dioxide in hydrofluoric acid It combines with hydrofluoric acid to form *fluogermanic acid,* which has not been prepared pure, its *potassium* salt, K_2GeF_6, is prepaied by adding potassium fluoride to a solution of the dioxide in hydrofluoric acid, and forms hexagonal crystals, isomorplious with those of ammonium silicofluonde which are sparingly soluble in cold, but readily m hot water

Germanium Tetrachloride, $GeCl_4$, is obtained by the direct union of germanium and chlorine, but is best prepared by heating the metal or the sulphide with mercuric chloride, it is a thin, colourless liquid, which fumes in the air, has a specific gravity of 1 887 at 18°, and boils at 86 5° [2] It is slowly decomposed by water with formation of hydrated germanium dioxide

Germanium Chloroform, $GeHCl_3$ —When germanium is heated in a current of hydrogen chloride it becomes red hot, and a distillate is obtained which, after exposure to the an, separates into two layers The heavier of these consists of germanium chloroform, which is a colourless, fuming liquid, boiling at 75°. The lighter layer is *germanium oxychloride,* $GeOCl_2$, which is also a colourless liquid, but is less mobile than germanium

[1] Voegelen, *Zeit anorg Chem* , 1902, 30, 325 See also Paneth, Matthies, and **Schmidt** Hebbel, *Ber* , **1922, 55,** ***[B],*** 775, 2615, Muller and Smith, *J Amer Chem Soc* , **1922, 44, 1909,** Schenck, *Rec trav chim* , **1922, 41, 569**

[2] **Dennis and** Hance, ***J*** *Amer Chem Soc* , **1922, 44, 299**

chloroform, aoes not fume in the air, and boils considerably above 100° *Germanwm dichloride,* $GeCl_2$, is also known, it is a colourless, fuming liquid

Germanium Disulfide, GeS_2 —Thip *z* impound, which is the most characteristic of the germanium derivatives, is prepared by the action of sulphuretted hydrogen on a solution of germanium dioxide, or by the addition of an excess of a mineral acid to a solution of an alkali thiogermanate, sulphuretted hydrogen being passed through the solution to complete the precipitation It is a white powder, only wetted with difficulty by water It is appreciably soluble, 1 part dissplvmg in 221 9 parts of cold water, it also readily dissolves in ammonium sulphide The throgermanates are obtained by fusing germanium derivatives with an alkali carbonate and sulphur [1]

Germanium Monosulphide, GeS, is obtained by carefully heating the disulphide in a current of hydrogen, and forms thin plates having a greyish-black colour and an almost metallic lustre The reduction easily proceeds further, with formation of metallic germanium When dissolved in alkalis and reprecrpitated by acid, it forms brown flakes soluble in hot concentrated hydrochloric acid with evolution of hydrogen sulphide [2]

DETECTION AND ESTIMATION OF GERMANIUM

391 Germanium salts impart no colour to the Bunsen flame, but the spark spectrum exhibits a number of bright lines, especially in the blue and violet regions, the following among others having been measured 6021, 5893, 5131, 4814, 4743, 4685, 4261, 4179 It is most readily recognised by the precipitation in strongly acid solution of a white sulphide, which is readily soluble in alkalis or ammonium sulphide, and slightly soluble in water this compound is also the most suitable yet known for its gravimetric estimation When an aqueous Solution of hydrofluoric acid containing any germanium compound is saturated with solid potassium chloride, a giey, gelatinous precipitate of potassium fluogermanate is formed

Atomic Weight of Germanium —By the analysis of pure germanium chloride, Winkler, in 1886, found the atomic weight to be 72 5 More recently, Muller, by conversion of potassium fluogermanate to potassium chloride, has obtained the number 72 42 [3]

[1] *J pr Chem* , 1886, [2], 34, 182, 1887, [2], 36, 177
[2] *Ber* , 1888, 21, 131 [3] *J Amer Chem Soc* , 1921, 43, 1085

TIN (Sannum) Sn=118 7 At No 50.

392 This metal was known in early times It is very uncertain whether the word " be*dil* " in the Old Testament, which is translated by the Greek word **κασσίτερος,** and by the Latin *stannum,* was originally used to designate tin It is likewise doubtful whether the metal which the Phoenicians are said to have brought from the Cassiterides, the exact locality of which was unknown to Herodotus, was really tin Possibly the Greek word is connected with the Arabic " kasdir," which signifies tin It is, however, certain that at the beginning of our era the word was used to specify tin, for Pliny states that *cassiteron* and *'plumbum candidum* are the same, and he adds that it is more expensive than *plumbum nigrum* (lead), he moreover states that it serves for soldering the latter metal, and that it is obtained from the Cassitendes in the Atlantic Ocean That the Cassitendes really were the British Islands appears more than probable, for after Caesar's conquest tin was carried from the Cornish mines through Gaul, by way of Marseilles to Italy,[1] and Diodorus Siculus mentions that the inhabitants carry the tin to a certain island called Iktis, lying on the coast of Britain " During low water the intermediate space is left dry, and they then carry over abundance of tin to this place in their carts " There can be little doubt that the Iktis of Diodorus is St Michael's Mount, in Mount's Bay, in Cornwall, for up to the present day a causeway exists, flooded at high water, but dry at low water, across which the inhabitants are in the habit of carrying goods to and from the mainland The names by which Pliny designates tin and lead seem, however, to show that he did not consider these as distinct metals, but rather as varieties of one metal, and he adds, " Sequitur naturae plumbi cujus duo genera, nigrum atque candidum " The word *stannum,* which at a later period became the general designation for tin, also occurs in Pliny's works, though it appears certain that by this word he did not signify tin, but rather any mixture of metals which contains lead In the works of the Latin Geber the most important properties of tin are mentioned, such as the peculiar crackling sound which the metal emits when bent, as well as the fact that it forms brittle alloys Tin was terr ed Hermes by the early Greek alchemists, but about A *D* 500 it received the name of Zeus or Jupiter, and

[1] G Smith, *The Cassitendes* London, 1863

to it the sign 4. was given, owing to the above-mentioned property of forming brittle alloys it was, however, sometimes termed *diabolus metallorum*

Tin has been found) in small quantities m Siberia, Guiana, and Bolivia in the native state, together with metallic gold, though the metallic tin from the last-named locality may, according to Forbes, possibly have been an artificial product It has also been found in small tablets in bismuthite from Mexico

The chief ore of tin is cassiterite, or tinstone, a more or less pure form of the dioxide, SnO_2 Less frequently it is found as tin pyrites, Cu_4SnS_4,$(Fe,Zn)_2SnS_4$, and occasionally as silicate It also occurs in small quantity in certain eprdotes, as well as in columbites, tantalites, and other similar minerals Various mineral waters contain traces of tin, and this metal has also been detected in certain meteoric masses

393 *The Metallurgy of Tin* [1]—Almost all commercial tin is obtained from tinstone, which is found in veins traversing the older crystalline and schistose rocks, and also as *stream tin* in water-worn nodules amongst the detritus of the same rocks Tin ore is not, however, very widely distributed, only occurring in large quantities in a few localities The oldest and best known tin mines from which tin has continuously been obtained, probably from the time of the Phoenicians up to the present, are those of Cornwall The ore there occurs in the granite and in the metamorphic schistose rock, and is found especially rich in the killas, a metamorphic clay slate, and in the line of junction of this with granite It is found in veins or lodes, in beds or flats, and in ramifications of small veins or " stock-werke," and these tin veins usually run in Cornwall in an easterly or westerly direction The following minerals are frequently found together with tinstone wolfram, apatite, topaz, mica, tourmaline, arsenical pyrites, etc

Tin mines exist, though on a much smaller scale than in Cornwall, in other parts of Europe, as in Saxony, Bohemia, Russia, Sweden, France, and in the Spanish province of Galicia Very large deposits of tin ores are, however, found in other quarters of the globe The principal producers of tin ore are, at the present time, the Malay Peninsula, Bolivia, the *Dat'* Islands of Banca and Bilhton, Australia and Tasmania, Yunn in China, and Nigeria All these prodifce more tin ore than

[1] See also *Metallurgy of Tin* Henry Louis McGraw **Hill Book Company, 1911**

Cornwall Tin has also been found in Mexico, South Africa, Japan, Siam and Burma

Tin ores may be smelted in shaft furnaces or in reverberatory furnaces, but as the ores obtained are generally very poor, containing only from 1 to 2 per cent of tin, preliminary operations of dressing or concentration are always necessary, and as considerable losses are experienced in these operations, much attention is being given to the direct treatment of tin-bearing material, and many suggestions have been put forward These, however, are not in a sufficiently advanced state to be considered in detail

The process adopted in Cornwall for the reduction of the metal is a simple one The ore, after being stamped, is washed to free it as much as possible from gangue, and is then roasted in calcining furnaces for the purpose of driving off the sulphur and arsenic contained in the arsenical and ordinary pyrites, if these be present

The vapours from these revolving calcining furnaces are led into chambers in which the arserious oxide condenses The construction of an Oxland and Hocking's revolving calciner is shown in Fig 183 This consists of a long cylinder lined with firebrick and placed in an inclined position The fire (H) IS placed at the lower end (A), whilst the upper end is in connection with chambers in which the arsenious oxide condenses The ore is dried on the top of these chambers, which are made of iron plate, and then brought by means of the hopper (h) into the cylinder, the roasted ore falling down into the space (F) This then undergoes a second washing in order to remove the ferric oxide and other oxidised materials, and if copper or bismuth be present, is treated with dilute sulphuric or hydrochloric acid for its removal After these operations the roasted ore is found to contain from 60 to 70 per cent of tin It sometimes happens that the tin ore is mixed with more or less wolfram, $(Fe,Mn)WO_4$, and as this mineral possesses a high specific gravity it cannot be removed from the tm ore by washing In order to remove this impurity, the presence of which in the smelting operations would prove injurious to the quality of the tin obtained, the ore is passed through some form of magnetic separator which extracts the wolfram and allows the tinstone to pass on The spared tin ore, or *black tin,* is then mixed with one-fifth part so weight of anthracite and the mixture sprinkled with some water m order to prevent the finely divided ore from being blown by the draught into the flues The construction of the reverberatory. furnace is shown in Figs 184 and 185 the charge is introduced

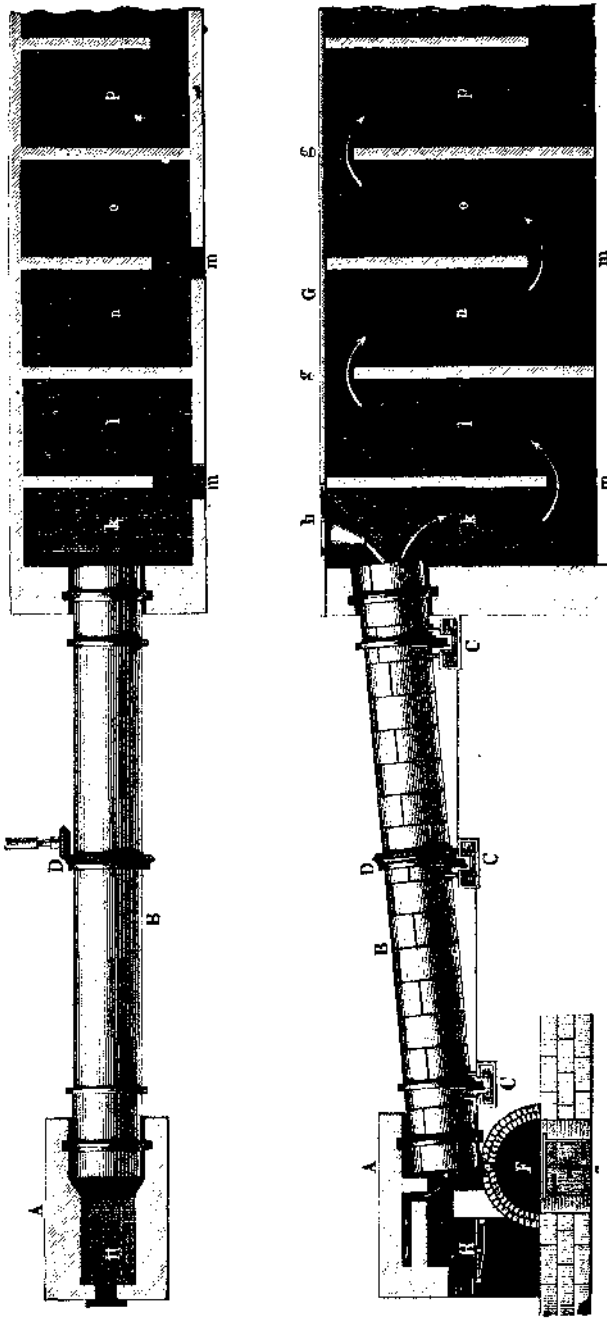

FIG. 183.

by the door (B) on to the hearth (A), and then worked through the door (E) The temperature of the furnace is gradually raised for five hours, the charge then repeatedly stirred, and at the

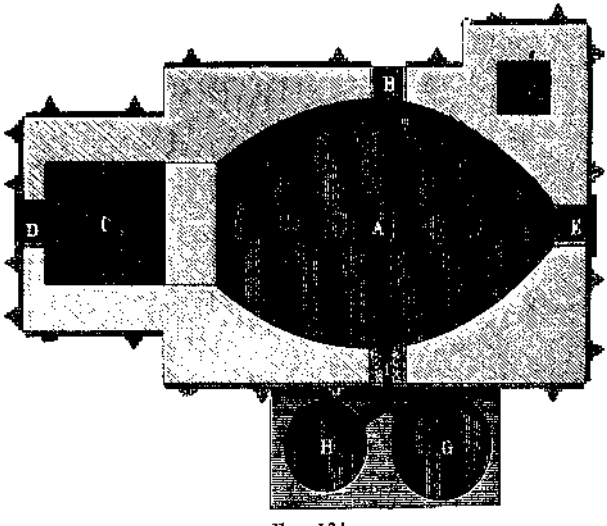

FIG. 184.

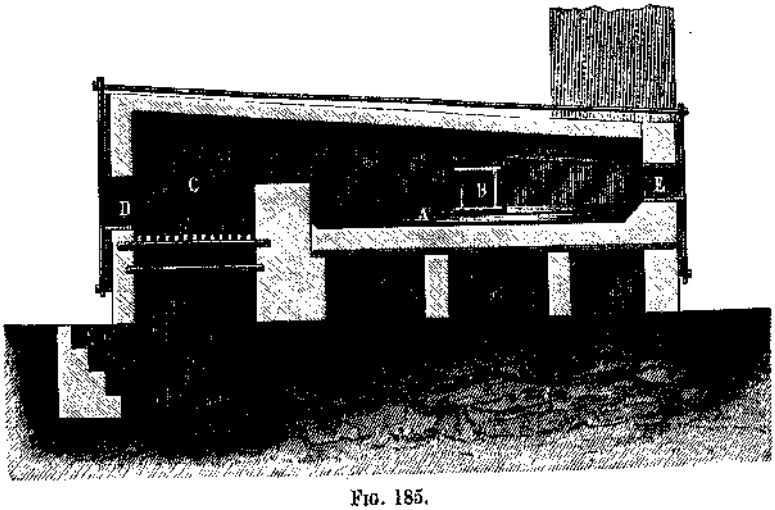

FIG. 185.

expiration of six hours the reduced metal is tapped and allowed to run from the lower part of the hearth through the hole (f) into the vessel (G) The impure tin thus obtained is then cast into moulds, and these are refined by the process of *liquation* This is effected by placing the ingots in another similar reverberatory

furnace which is gradually heated, so that the pure, more easily fusible tin first melts and runs into a cast-iron vessel (H) placed below, whilst the less fusible alloy of tin with iron and arsenic remains on the hearth A fire is placed under the vessel (H) IN order to keep the metal liquid, and this is then stirred up with a pole of green dense wood The length of this operation depends upon the quality of the metal which it is desired to obtain, and may last from one to several hours The dross which separates during the process of refining, and the " hard-head," or residue which remains on the hearth, both of which contain large quantities of tin, are afterwards worked up In order to prepare *gram tin,* the tin is heated until the metal becomes brittle and crystalline, it is then broken up by a hammer, or allowed to fall from a considerable height

The slags formed duung the smelting operations generally contain sufficient tin to be worth extraction This tin may exist as prills of metal or in chemical combination The metallic portion is often separated by crushing and washing, or by allowing the slag to stand in a molten condition for some hours, when the metallic tin settles to the bottom Slags containing tin in the combined condition are re-smelted with dross and other residues and strong bases at high temperatures in shaft or reverberatory furnaces

394 *Separation of Tin from Tin Scrap, etc*—Tin issepar
from tin scrap and tin can waste by means of any
The tin waste is washed in an alkaline bath to remove
rinsed in water, then heated in a furnace to remove solder, ar
then treated in iron cylinders with chlorine, the cylinders being kept cool [1] The tin chloride thus formed is put on the market, and the steel scrap, which contains less than 0 1 per cent tin, is hydraulically pressed into briquettes, and smelted in open-hearth furnaces

The electrolytic process formerly used, in which sodium hydrate was the electrolyte, proved expensive, as it required highly paid labour, expensive electric current, and gave as a product a tin mud of inferior quality, which required further smelting treatment to convert it into marketable tin

The total amount of tin produced in 1919 was about 113,893 tons[2]

395 *Properties and Uses of Tin* —Tin as a white, brightly

[1] ***Ost Zert Berg u Hutt Wesen,* 1909, 57, 103**
[2] ***Mineral Industry,* 1919, 28, 665**

lustrous metal, which melts at 232° (Heycock and Neville), boils under atmospheric pressure at about 2270° (Greenwood),[1] and has a specific gr vity at 13° of 7 293 (Matthressen) Its specific heat is 0 05363 at 0°, 0 05549 at 54°, and 0 05690 at 97 6° (Griffiths) [2] Its atomic heat is therefore 6 37—6 76 Its average compressibility between 100 and 500 megabars is O 000,001,7 (Richards and Stull) [3] It is harder than lead, but softer than gold It exhibits a fibrous fracture, and when bent emits a peculiar crackling sound caused by the friction of the crystalline particles Tin can be easily rolled or hammered out to foil, and at a temperature of 100° it may be drawn into wire, which, however, possesses but slight tenacity, at 200° it becomes so brittle that it may be powdered A sample of Banca tin which was exposed at St Peteisburg to a very low temperature during the winter of 1867-8, fell to granular, ciystalline pieces or to a coarse powder This alteration is due to the fact that tin, like sulphur, exists in more than one form, dependent upon the temperature, the stable form below 18° being the grey powder or " grey tin " At ordinary temperatures common white tin is in a metastable condition, but the change to the stable grey tin takes place with extreme slowness The rate of change may, however, be accelerated by lowering the temperature, the maximum velocity being reached at --50° This alteration was known to Aristotle, who speaks of tin as " melting " when kept at low temperatures [4] Betr 18° ana 194° the stable form of tin is tetragonal, whilst nis temperature it is rhombic [5] If zinc be brought into solution of tin chloride the metal separates out in the form of fine crystalline dendrites, and this deposit, known as the tin-tree (Arbor Jovis), was first prepared by Ilsemann in 1786 When tin is melted and then allowed partially to solidify, the liquid portion being poured off, needle-shaped prismatic or tabular crystals of the metal remain behind Another mode of obtaining crystalline tin is to decompose tin chloride by a weak electric current, when the metal is deposited in tetragonal prisms and pyramids Fine crystals of tin can also be obtained when water

[1] *Proc Roy Soc* , 1909, 82, [-4], 396
[2] *Ibid,* 1913, 88, *[A],* 549
[3] *Pub Carn Inst,* 76, 1907
[4] Cohen and van Eyk, *Zed physikal Chem* , 1899, 30, 601, Hasslinger, *Monatsh,* 1908, 29, 787, Cohen, *Zed physikal Chem,* 1908, 63, 625, 1909, 68, 214
[5] Findlay, *The Phase Rule,* p 39 (Longmans), Cohen and Goldschmidt, *Zeit anorg Chem* , 1904, 60, 225, Janecke, *Zed physikal Chem* , 1915, 90, 313

containing zinc dust in suspension is gradually added to a solution of tin chloride

Metallic tin remains bright in dry or moist air at the ordinary temperature, but whcm melted it gradually oxidises, forming a greyish-white skin on the surface, which consists of a mixture of tin and stannous oxide and is gradually oxidised to the dioxide It is dissolved by dilute, and more rapidly by concentrated hydrochlouc acid, with evolution of hydrogen and formation of stannous chloride, it dissolves also in aqua regra and in hot concentrated sulphuric acid, and is converted by somewhat diluted nitric acid into metastannic acid It dissolves also in aqueous solutions of the alkalis, with formation of salts of metastannic acid and evolution of hydrogen

Tin is used for a large number of purposes, for the piepara-tion of vessels for household and technical use, for the manufac-ture of tinfoil, for tinmng copper and iron, and especially for preparing the alloys of tin Tinned copper vessels were em-ployed by the ancients, for we find them described by Pliny, and the same author also mentions as a well-known fact that in the process of tinning, the weight of copper articles increases but slightly, and he adds that the substance termed stannum is employed for this purpose

Copper- and brass-ware can readily be tinned by dipping the vessel into the molten metal In order to cover the interior of a vessel with a coating of tin, it is heated and some molten tin poured in, which is then well divided over the surface by rubbing with rags In order to prevent the oxidation of the metal, a small quantity of resin or sal-ammoniac is added Agricola was the first to mention the process of tinning iron It appears, however, that at that time it was only slightly employed The process is usually supposed to have been discovered m Bohemia in 1620, coming into use in England and France about 100 years later In the modern process of preparing the common tin plate, an important industry in South Wales, mild steel plates, after being annealed, rolled and " pickled " in weak acid solutions, are dipped in a bath of molten tin On the surface of this is a layer of zinc chloride which acts as a flux, and the plates have to pass through this before they reach the tin In the bath they pass under a partition and emerge through a layer of hot grease, which floats on the surface of the tin and is separated from the flux by the partition The plates pass between rollers to remove the excess of tin, and are then polished

ALLOYS OF TIN

396 Several of these alloys are largely employed in the arts Tin and lead may be mixed in any proportion, and the alloys are harder and tougher, but more readily fusible than either of the two metals For this reason they are employed is solders The following table gives the composition of some of the different lead and tin alloys

	Common Pewter	Solder		
		Fine	Common	Coat se
Tin	4	2	1	1
Lead		1	1	2

In practice, a certain amount of antimony is often used to replace some of the tin in these alloys [1]

Bronze is the name given to any alloy consisting chiefly of copper and tin, although other elements are frequently added to impart particular properties

The alloys corresponding in composition to the formulae $SnCu_3$ and $SnCu_4$ are definite chemical compounds, and are the only ones of the series which remain homogeneous after melting, a certain amount of liquation taking place in all the others The hardness of these alloys increases as the proportion of copper is increased from pure tin to 35 per cent of copper, from 35 per cent to 73 per cent of copper the alloys are extremely brittle, and beyond 73 per cent of copper, the hardness diminishes as the copper is increased The effect of heat on some of the copper-tin alloys is remarkable, for whilst steel is hardened by quenching in water, these alloys are hardened by slow cooling and when quenched in water they lose their bnttleness and become malleable

Gun-metal usually contains 9 parts of copper to 1 of tin, and has a yellow colour This alloy also serves for the preparation of bronze medals

Speculum-metal is composed of 1 part of tin to 2 parts of copper melted together, with, frequently, addition of a small quantity of arsenic It possesses a steel-grey colour, is very brittle, and takes a very high polish

Bell-metal possesses a varying composition It generally consists of from 4 to 5 parts of copper to 1 of tin It has a yellowish-grey colour, and readily melts to form a thin liquid It has a finely granular structure, is hard, brittle, and very

[1] See Bannister and Tabor, *Journ Inst Metals,* 1909, 2, 58

ANALYSES OF ALLOYS OF TIN

	I	II	III	IV	V	VI	VII	VIII	IX	X	XI	XII	XIII	XIV
Cu	9174	67	73 94	82	84 25	87 89	84 53	85 9	70 30	89 43	89 78	88 77	89 34	84 20
Sn	8 26	33	2167	17	15 64	10 58	6 82	14 1	24 53	8 17	916	9 25	7 50	3 05
Pb	—	—	119	—	—	—	8 65	—	5 20	105	133	0 71	121	0 75
Fe	—	—	017	1	trace	0 27		—	—	0 34	—	—	—	—
Zn											0 35	128	161	1155
Ni	—	—	2 11	trace	—	—	—		—	0 19	—	—	—	—

I English gun-metal
II Speculum metal used m construction of Lord Rosse's large telescope
III Bell cast in 1670 in Darmstadt
IV Chinese gong
V Egyptian bronze com of the reign of Ptolemy IX
VI Attic bronze com
VII Roman bronze com of Justinian
VIII Gaulish axe
IX Celtic arrow head
X Bronze statue of sixteenth century from Augsburg
XI Statue of Germanicus, cast in Berlin in 1824
XII Thorwaldsen's Shepherd, cast in Berlin in 1825
XIII Statue of Bacchus in Berlin, 1830
XIV Statue of Lessing in Brunswick

sonorous The Chinese gongs and tom-toms are cast at a very high temperature, and then quickly brought under the hammer, in consequence the loy becomes very dense

The preceding table gives the compositior of some of the alloys described above

Phosphor-bronze—The addition of phosphorus to lronze imparts to it a character of greater hardness, elasticity, and toughness This material is obtained by melting copper with tin phosphide, sometimes with a small addition of lead It contains from 0 25 to 2 5 per cent of phosphorus, and from 5 to 15 per cent of tin, and is largely used, especially that containing from 7 to 8 per cent of tin, for portions of machinery for which hardness and toughness are important properties The alloy containing more tin has been employed for bell-metal Its valuable properties are connected with the fact that copper forms a homogeneous alloy with tin phosphide, the presence of phosphorus preventing the oxides from dissolving and thus impairing the qualities of the metal

Tin Amalgam—Tm readily combines with mercury with lowering of temperature The amalgam may be formed more quickly when mercury is poured into molten tin, and, according to the quantity of mercury added, the amalgam is either liquid, or forms a granular or crystalline mass When mercury is made the negative pole in a solution of tin dichloride, fine ciystals of the amalgam are obtained containing from 44 to 51 per cent of tin (Joule) Tin amalgam was formerly largely used for silvering mirrors, but now has almost entirely been superseded by the use of silver

It is not certain when tin amalgam was first employed for manufacturing minors, inasmuch as, during the middle ages, the processes used in the preparation of mirrors were kept secret It is, however, clear that before amalgam was used, a surface of metallic lead was employed for obtaining a mirror as early as the thirteenth century, when such murors were common These were curved, and were prepared, as Beckman described in his *History of Inventions,* from large glass globes, into the interior of which a mixture of resin, molten lead, and sulphide of antimony was introduced, the fluid mass being brought over the surface until it was all covered with a thin film The globe was then cut into pieces, and the mirrors thus obtained were often employed as ornaments A guild of glass-mirror makers existed at Nuremberg in the year 1373, whether they made mirrors according to

the above process is doubtful, but they, as well as French workmen, sold products of their art in the Venetian market up to the year 1500 The use of amalgam for coating mirrors is first mentioned by Kunkel, who recommends for the purpose an amalgam of 2 parts of quicksilver, 1 part of marcasite (bismuth), ½ part of tin, and ½ part of lead

COMPOUNDS OF TIN

TTN AND OXYGEN

397 The fact that tin readily forms a calx was observed at an early period Pelletier was the first, in the year 1792, to show that tin combines in two proportions with oxygen, forming two series of salts This investigation was continued by Proust, but for a long time considerable doubt existed as to the number of the oxidation products of the metal Berzelius in 1812 assumed that there were three oxides, SnO, Sn_2O_3, and SnO_2, on the grounds that when the metal is oxidised by nitric acid the highest oxide thus prepared possesses a totally different chemical character from that obtained by precipitation with alkalis from a solution of the salts of tin The subsequent investigations of Davy, Gay-Lussac, and Berzelius himself have proved that only the first and last of these oxides exist A peroxide, SnO_3, has also been prepared

Tin Monoxide or *Stannous Oxide,* SnO —This oxide may be prepared in a variety of ways In the first place, it is obtained as an olive-coloured powder when stannous oxalate is ignited out of contact with air Secondly, it may be prepared by adding a solution of potassium carbonate to one of tin dichlonde, when a white precipitate having the composition $Sn_2O(OH)_2$ is thrown down This readily absorbs oxygen from the air, but if it be washed in absence of air and dried in a stream of carbon dioxide, the monoxide remains behind as a black powder Stannous oxide is also obtained when the pure dichloride is mixed with sodium carbonate, the mass heated until it has become black, and then lixiviated If the hydrated oxide be boiled with a dilute solution of caustic potash, the anhydrous oxide is obtained as a crystalline powder, the crystals consisting of combinations of the cube and dodecahedron It may also be obtained in the crystalline state by digesting a nearly saturated solution of the hydrated oxide in acetic acid at a temperature of 56°.

According to Hantzsch,[1] the hydroxide, SnO_2H_2, is precipitated when caustic soda is added to a solution of stannous chloride in the absence of air *It* dissolves in excess of the reagent, and, like germanous hydroxide, acts as a weak monobasic acid, the solution containing sodium stannite, H SnO ON

Stannous oxide readily takes fire when heated in the air, and dissolves in acids with formation of stannous salts, to which it corresponds These are, however, more readily obtained by the action of acids upon the metal, and possess an unpleasant metallic taste, redden litmus, owing to hydrolysis, readily absorb oxygen, and serve as powerful reducing agents

Tin Dioxide or *Stannic Oxide,* SnO_2, occurs in nature as tinstone, or cassitente, crystallising in the tetragonal system (Fig 186), and possessing an adamantine lustre The ciystals are seldom colourless, being generally tinted brown or black from the presence of the oxides of manganese and iron *Stream-tin* is found in water-worn nodules, and *Wood-tin* in reniform, fibrous masses When tin is heated nearly to its boiling point in the air, it burns with a luminous, white flame, and the dioxide which is thus formed in a state of fine division was formerly known as f*lores jovis* If fused in the presence of air, the surface of the metal soon becomes covered with a grey pellicle, which then passes into a grey powder known as f*lores stanni,* consisting of a mixture of finely-divided metal with the oxide, the mixture, on continued ignition, is wholly converted into stannic oxide The dioxide is also obtained on treating tin with nitric acid, when a violent oxidation occurs The hydrated white powder thus formed yields the dioxide on washing and igniting If a solution of stannic chloride be precipitated with ammonia, a gelatinous precipitate is obtained which can be completely washed only with difficulty If, however, it be heated with a concentrated solution of an alkali sulphate, a dense precipitate is thrown down, and this can be easily washed and yields the pure dioxide on ignition An amorphous, white or straw-coloured powder is then obtained, which is quite insoluble in water and possesses a specific gravity of 6 71 On heating it changes colour, becoming lemon-yellow and then brown, but it assumes its original tint on cooling

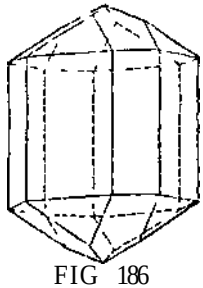

FIG 186

[1] *Zeit anorg Chem* , **1902, 30, 289 , see also Bury and Partington,** *Journ Chem Soc* , **1922,121, 1998**

The dioxide may also be obtained by the electrolysis of a solution of potassium or sodium chloride, a tin plate being used as anode, and one of platinum as cathode [1]

By heating amorphous stannic oxide in a current of hydrogen chloride it may be obtained in microscopic crystals which have the form of cflssitente and a specific gravity of 6 72 (Deville) [2] The formation of crystalline stannic oxide has been observed in fusing the dross collected on the hearth of a gun-metal furnace, the crystals being hard, brittle, four-sided prisms [3] Stannic oxide can be fused only at a very high temperature, according to Cusack [4] 1127° It is not volatile, nor is it attacked by concentrated acids, with the exception of sulphuric acid

Stannic Hydroxides—Two stannic hydroxides are known, which have the same composition, H_2SnO_3, but different chemical properties Berzelms,[5] who discovered the second form, introduced the term " isomerism " to designate this hitherto unknown phenomenon They are both weak acids, but react differently with other acids, and form different salts with alkalis, from which they can be precipitated unchanged by the addition of acids they are distinguished by the names *stannic* and *metastannic* or a- and *ft-stannic acids*

Berzelms showed that they are both in the same stage of oxidation The difference is not due to their water content, for this is variable, depending on how they are dried, and the difference between the two forms persists through the varying degrees of hydration Two views have been held as to the cause of the difference The older is that the ß-form is a polymer of a-stannic acid the method of preparation of the a-acid, and the composition of its salts, make it probable that the molecule contains only one atom of tin, and that it has the simple formula H_2SnO_3 the work of Fiemy [6] and Engel [7] on the salts and oxychlondes derived from ß-stannic acid indicate that its molecule contains five atoms of tin, and that it can be given the formula $H_2Sn_5O_n,4H_2O$ On the other hand, Mecklenburg [8] has produced evidence that the two forms are both colloidal hydrates, differing only in the size of their particles, while no clear line of demarcation can be drawn between the two forms, the a-acid

[1] **Lorenz,** ***Ze it anorg Chem*** **, 1896,12, 436**
[2] ***Compt rend,*** **1861, 53, 161** [3] **Abel,** ***Journ Chem Soc*** **, 1858, 119**
[4] ***Proc Royal Irish Acad*** **, 1897, 4, 399** [5] ***Annalen,*** **1817, [2], 5, 149**
[6] ***Ann Chim Phys,*** **1848, [3J, 23, 385**
[7] ***Compt rend,*** **1897, 124, 765, 1897, 126, 464, 651, 709**
[8] ***Zeit anorg Chem,*** **1909,64,368, 1912,74,207, 1914,84, 121 See also Collins and Wood,** ***Journ Chem Soc*** **, 1922, 121, 441**

consists of the relatively small particles and the ß-acid of the larger ones

Berzehus, Engel, and others have described a third form, *payastannic acid* This is not an isomer of the *a*- and ß-forms, since it has a different water content from either of the others when dried under similar conditions It has the composition $H_2Sn_5O_n,2H_2O$, and is obviously related closely to metastannic acid, and has been regarded as an internal anhydride of it, according to Kleinschmidt,[1] however, it is identical with it

Stannic acid or a-stannic acid is obtained as a white, hydrated precipitate by the action of calcium carbonate or alkali on a solution of a stannic salt, or by the action of an acid on a stannate Its water content depends on how it has been dried, rapidly dried by suction and pressure it has the composition $Sn0_2,4H_2O$ or $H_2[Sn(OH)_6]$, dried slowly in the air at room temperature, it has the composition $Sn0_2,2H_2O$ or H_4SnO_4, dried in a vacuum over sulphuric acid it has the composition SnO_2,H_2O or II_2SnO_3, but it is doubtful if these are definite hydrates The final product on heating is anhydrous stannic oxide The fleshly precipitated hydroxide, while still moist, dissolves slightly in water, to which it imparts an acid reaction, and is readily soluble in dilute acids, forming stannic salts, and in alkalis to foim stannates It is partially transformed to the ß-form on drying or on standing in contact with water, especially on heating

The Stannates —Only one orthostannate, cobalt orthostannate, Co_2SnO_4, has as yet been prepared It has been obtained by Hedvall[2] by fusing cobaltous and stannic oxides with potassium chloride and dissolving out the excess stannic oxide with hydrochloric acid

The stannates of the other metals, when formed by fusion, have the formula $M^1{}_2SnO_3$, but when formed from solution have the formula $M^1{}_2SnO_3,3H_2O$ Bellucci and Parravano[3] argue that these are derivatives of hexahydroxy-stannic acid, $H_2[Sn(OH)_6]$, the three molecules of water are water of constitution, not water of crystallisation, since they are often not expelled by long heating at 100° All the stannates examined, namely, those of sodium, potassium, lead, silver, calcium, strontium, and barium, contain three molecules of water, the potassium salt is isomoiphous with the potassium salts of hexahydroxy-plumbic acid, $H_2[Pb(OH)_6]$, and the far more stable hexahydroxy-platmic acid, $H_2[Pt(OH)_6]$,

[1] *Monatsh* , 1918, 39, 149 [2] *Arkiv Kem Min Geol*, 1914, 5, No 18, 1
[3] *Zeit anorg Chem*, 1905, 45, 142

they are analogous to the hexachlorostannates, $H_2[SnCl_6]$, and an intermediate acid, $H_2[Cl_3Sn(OH)_3]$, exists

The alkali stannates alone are soluble m water, and can be obtained as measurable crystals, stannates of the other metals are obtained as l-isoluble precipitates by double decomposition

Potassium Stannafe, K_2SnO_3, is obtained by fusing the dioxide with potash, or by dissolving the hydrated oxide in potash-lye The solution yields on evaporation over sulphuric acid colourless, glistening, rhombic prisms of $K_2[Sn(OH)_6]$, which have an alkaline taste and are readily soluble in water Metallic copper brought into contact with the solution becomes covered with a bright coating of tin

Sodium Stannate, Na_2SnO_3, is prepared on a large scale and employed extensively in calico-printing under the name of *preparing salts* It is obtained either by fusing the finely powdered or levigated tinstone with caustic soda, dissolving the mass in water to remove any ore that may be unacted upon, and evaporating the solution, or by heating tin with caustic soda and Chih saltpetre On evaporating the solution, crystals of $Na_2SnO_3{,}3H_2O$, or $Na_2[Sn(OII)_6]$, are obtained, which are more soluble in cold than m hot water A tolerably concentrated solution of the salt which contains no caustic soda deposits on cooling fine prisms of the composition $Na_2SnO_3{,}10H_2O$, and these effloresce on exposure to air

Metastannic Acid and the Metastannates—In his *Reflections on the Hypothesis of Alkali and Acidum,*[1] published in 1670, Boyle remarks that aqua-foitis eats up or destroys more tin than it dissolves On the other hand, he elsewhere[2] mentions that a solution of tin in aqua-fortis readily becomes gelatinous Kunkel, who also studied the action of nitric acid on tin, mentions in his *Laboratonum Chymieum* that tin can only be dissolved when it is added in small quantities to an acid, and that heat must be altogether avoided, because white calx of tin is thrown down when the acid is hot The explanation of these different statements is to be found in the facts that when the metal is treated with weak nitric acid it forms either stannous or stannic nitrate, according to the degree of concentration of the acid, and that the latter salt easily decomposes with separation of a gelatinous stannic acid, whilst, on the other hand, when tin is acted upon by strong nitric acid it is violently attacked with evolution of

[1] Boyle, *Op* 4, 284
[2] " Experiments and Considerations Concerning Colours "

heat and formation of an insoluble white powder consisting of a mixture of a- and ß-stanmc acids, Klemschmidt, however, maintains that it ß-stannyl nitrate, $Sn_5O_9(NO_3)_2,4H_2O$, and that this is readily hydrolysed to ß-stannic acid by washing with water Metastannic acid is also prepared by the addition of acids to metastannates, or by their hydrolysis in dilute solution, by the hydrolysis of ß-stannyl chloride, by the spontaneous change of a-stannic acid, and by the slow spontaneous hydrolysis of stannic salts and stannates Engel finds that it has the composition $SnO,2H_2O$ or $H_2Sn_5O_{11},9H_2O$ when it is dried in the air, and SnO_2,H_2O or $H_2Sn_5O_n,4H_2O$ when it is dried in a vacuum over sulphuric acid According to van Bemmelen,[1] however, it always contains less water than the a-form when the two forms are treated similarly, and no definite hydrate exists The final product on heating is stannic oxide

The freshly precipitated hydroxide reddens litmus paper, and is distinguished from a-stanNIc acid, inasmuch as it is altogether insoluble in nitric acid, and swells up but does not dissolve in strong sulphuric acid, forming the easily hydrolysed compound ß-stannyl sulphate, $Sn_5O_9SO_4\ 4H_2O$ (Klemschmidt) Hydrochloric acid produces a compound, meta- or ß-stannyl chloride, which is soluble in water but insoluble in hydrochloric acid, and Which Engel found to have the formula $Sn_5O_9Cl_2,4H_2O$ Numerous similar hydrated oxychlorides have been described

Metastannates are produced by the action of alkalis on metastannic acid or on solutions of its chlonde the best known is sodium metastannate, which is slightly soluble in water but insoluble in excess of alkali Fremy and Klemschmidt find it can be represented by the formula $Na_2Sn_6O_{11},4H_2O$ Other metastannates of greater complexity have been described

It is doubtful if any of these derivatives of the stannic hydroxides, except the easily crystallisable stannic salts and the stannates, are real compounds, their composition depends to a large extent on the method of preparation, and they are all readily hydrolysable Mecklenburg has shown that the reaction between ß-stannic acid and phosphoric acid is a typical adsorption effect The composition of the product varies with the concentration of the phosphoric acid in tire solution according to the usual law that holds when true chemical combination does not occur, but an adsorbed layer is formed on the surface of any very finely divided substance It is probable that all the meta-

[1] *Ber* , 1880,13, 1466

stannates, metastannyl chlorides, and other compounds with acids are adsorption phenomena Solutions of metastannyl chloride are not true solutions, but colloidal

Parastannic acid was discovered by Berzehus, who called it ß-stannic acid, lunce then this name has been applied to meta-stannic acid It has been studied by Engel, and is formed when metastannic acid is heated in water at 100° Its reactions are almost identical with those of ß-stannic acid, but it contains two less molecules of water in its composition

	Dried in air	Dried in a vacuum	Potassium salt	Chloride
Metastannic acid	$H_2Sn_{,}.O_{11},9H_2O$	$H_2Sn_5O_{11},4H_2O$	$K_2Sn_5O_{11},4H_2O$	$Sn_5O,Cl_2,4H,O$
Parastannic acid	$H_2Sn_5O_n,7H_2O$	$H_2Sn_5O_{11}2H_2O$	$K_3Sn_5O_{11},2$ or $3H_2O$	$Sn_5O,Cl_2,2H,O$

Colloidal or *Soluble Stannic Acid* was obtained by Graham [x] by the dialysis of a mixture of tin tetrachloride and alkali, or of sodium stannate and hydrochloric acid, the gelatinous mass which is first formed gradually dissolving The liquid is converted on heating into colloidal metastannic acid Traces of hydrochloric acid or of a salt bring about gelatmisation in both solutions

Tin Peroxide, SnO_3 —This oxide is known only in the hydrated condition, and is prepared by the addition of barium peroxide to a solution of stannous chloride containing hydrochloric acid The barium chloride is removed by dialysis, and the colloidal solution is evaporated A white mass having the formula $H_2Sn_2O_7$ or $2SnO_3,H_2O$ remains behind [2]

When stannic hydroxide is heated with hydrogen peroxide at 70°, and the mixture is desiccated, a *perstannic acid,* $HSnO_4,2H_2O$, is obtained, and this on heating at 100° yields the acid $H_2Sn_2O_7,3H_2O$ Potassium and sodium stannates when similarly treated form salts coi responding to these acids [3]

When concentrated alkali stannate solutions are electrolysed at low temperatures and with low current densities, perstannates are formed, owing to anodic oxidation [4]

STANNOUS COMPOUNDS

398 *Tin Diflaoride* or *Stannous Fluoride,* SnF_2, is obtained by dissolving the hydrated monoxide m hydrofluoric acid On evaporation in absence of air this compound is obtained in the form of small, white, monochnic tablets

[1] ***Phil Trans*** **, 1861,151, 213** [2] **Spring, *Bull Soc chim* , 1889, [3], 1, 180**
[3] **Tanatar, *Ber* , 1905, 38, 1184** [4] **Coppadoro, *Gazz* , 1908, 88, 1, 489**

Tin Dichloride or *Stannous Chloride,* $SnCl_2$, is obtained on the large scale by dissolving tin in hydrochloric acid On evaporating the solution and cooling, crystals of hydrated stannous chloride, $SnCl_2,2H_2O$, known in commercr as *Tin Salt,* separate out in transparent, monoclmic prisms which melt in their water of crystallisation at 40°, and on cooling again yield *ss* crystalline mass They have a specific gravity of 2 71, and dissolve at the ordinary temperature m 0 37 part of water When more strongly heated they partially decompose with evolution of hydrogen chloride, but when dried in a vacuum over sulphuric acid they lose their water The anhydrous salt, which may also be obtained by heating tin in hydrogen chloride, or with the requisite amount of corrosive sublimate, is a transparent mass having a fatty lustre and conchoidal fracture It fuses at 250° to form an oily liquid which boils at 606° Its vapour at low temperatures has a density always less than that required by the formula Sn_2Cl_4, but at a high temperature the value becomes constant, agreeing with $SnCl_2$,[1] whilst the freezing point of urethane is lowered by dissolving stannous chloride in it by an amount corresponding to the formula $SnCl_2$ [2] The hydrated salt dissolves in a small quantity of water with lowering of temperature, forming a clear liquid which, when diluted with much water, becomes turbid, a basic chloride, $2Sn(OH)Cl,H_2O$, being precipitated, this again dissolves on the addition of acids The same precipitate is formed when the clear solution is exposed to the action of the air

$$6SnCl_2 + 2H_2O + O_2 == 2SnCl_4 + 4Sn(OH)Cl$$

Stannous chloride is soluble in alcohol and in ether[3] It combines with ammonia to form compounds which vary in composition according to the temperature of reaction [4] When cooled in a freezing mixture, a yellow compound, $SnCl_2,2NH_3$, is formed, which blackens on exposure to light, and is decomposed by moisture into stannous oxide and ammomum chloride At ordinary temperatures, a mixture of $SnCl_2,2NH_3$ and $SnCl_2,NH_3$ results, whilst at 100° $SnCl_2,NH_3$ only is formed At 120—300°, the compound $3SnCl_2)2NH_3$ is formed as a brownish-red, crystalline mass, which is the most stable of the three compounds

Tin Dibromtde or *Stannous Bromide,* $SnBr_2$, is obtained when

[1] Blitz and V Meyer, *Ber* , 1888, 21, 22
[2] Castoro, *Gazz* , 1898, 28, n, 317
[3] de Jong, *Zeit anorg Chem* , 1902, 41, 596
[4] Sofianopoulos, *Compt rend,* **1911,**152, 865

tin is heated in hydrogen bromide or distilled with mercuric bromide It forms a light yellow, translucent mass fusing at 215 5°, and is soluble in water A solution of this compound is obtained by acting "with hot aqueous hydrobromic acid upon metallic tin

Tin Di-iodide or *Stannous Iodide,* SnI_2, is best obtained by adding a small excess of iodide of potassium to a warm concentrated solution of stannous chloride It crystallises in yellowish-red needles which dissolve only slightly in water, though readily in warm solutions of the chlorides and iodides of the alkali metals, and also in dilute hydrochloric acid It melts at 316°, solidifying to a crystalline mass which liquefies at a higher temperature When heated in absence of air it is obtained in the form of a red, crystalline mass, yielding a scarlet powder On treatment with dry ammonia, a yellow compound having the formula $SnI_2,2NH_3$ is formed [1] If a saturated solution of stannous iodide in hydriodic acid be cooled to 0°, pale yellow needles of *todostannic acid,* $HSnI_3$, are deposited These are very unstable and readily decompose, forming stannous iodide [2]

The fluoride, chloride, bromide, and iodide combine with the corresponding halide compounds of the alkali metals and with those of the metals of the alkaline earths to form crystalline double salts

Tin Monosidphide or *Stannous Sulphide,* SnS, is obtained by heating together the metal and sulphur Thin tin foil takes fire spontaneously when brought into sulphur vapour "When thus obtained, it is a lead-grey, tough, crystalline mass, which melts at a higher temperature than the metal When a solution of stannous chloride is saturated with sulphuretted hydrogen, a brown hydrated precipitate is obtained, which on drying becomes black This is scarcely soluble in ammonium sulphide, but dissolves on the addition of sulphur, and is also soluble in the polysulphides of the alkali metals, the stannous sulphide being first converted by the sulphur into stannic sulphide, which then dissolves, forming ammonium thiostannate When the dried precipitate is added to fused stannous chloride and the melted mass treated on cooling with dilute hydrochloric acid, stannous sulphide is obtained in metallic, glistening, crystalline scales, having a specific gravity of 4 973 The crystalline variety may also be obtained by heating the amorphous sulphide in the

[1] Ephraim and Schmidt, *Ber* , 1909, 42, 3856
[2] Young, *J Amer Chem Soc* , 1897, 19, 851

electric furnace [1] Amorphous tin sulphide dissolves readily in hot hydrochlpric acid, whilst the crystallised substance dissolves less readily

Stannous Sulphate, $SnSO_4$ is formed by dissolving the metal or the hydrated oxide in dilute sulphuric acid On evaporation in a vacuum, microscopic, granular crystals are obtained which are only a little more soluble in hot than in cold water The solution readily deposits a basic salt

Stannous Nitrate, $Sn(NO_3)_2$—This salt is obtained by the action of very dilute nitric acid on the metal, ammonium nitrate being simultaneously produced

$$4Sn + IOHNO3 = 4Sn(NO_3)_2 + NH_4NO_3 + 3H_2O$$

STANNIC COMPOUNDS

399 *Tin Hydride* —If an alloy of tin and magnesium, the composition of which corresponds to the formula Mg_2Sn, is dissolved in hydrochloric acid, the hydrogen evolved contains small amounts of a volatile hydride of tin This is condensed by liquid au, and can be re-evaporated without decomposition On passing through a heated tube, it is decomposed, with the formation of a characteristic tin mirror [2]

Tin Tetrafluoride or *Stannic Fluoride,* SnF_4, is obtained as a hygroscopic, white, crystalline substance by the action of anhydrous hydrofluoric acid on stanmc chloride [3] It boils at 705°, subliming below this temperature, and has the specific gravity 4 78 at 19° An aqueous solution of the fluoride may be obtained by dissolving the hydrated dioxide in hydrofluoric acid, the solution coagulates on boiling, and decomposes on evaporation with evolution of hydrogen fluoride Gaseous ammonia combines with tin tetrafluoride at 43°, forming a white compound, SnF_4,NH_3, which loses very little ammonia even at 400°[4] When the fluoride and ammonia are heated together in a sealed tube at 120—130°, $SnF_4,2NH_3$ is formed Both these compounds are soluble in ammonia

Liquid hydrogen sulphide decomposes the fluoride in a sealed tube, thus $SnF_4 + 2H_2S = SnS_2 + 4HF$

Chlorine compounds of phosphorus bring about an exchange

[1] Mourlot, *Compt rend* , 1897, **124,** 768
[2] Paneth and Furth, *Ber-*, 1919, 52, *[B]*, 2020 See also Paneth and others, *Ber* , 1922, 55, $[B]_9$ 769, 775
[3] Ruff and Plato, *Ber* , 1904, 37, 673
[4] Wolter, *Chem Zeit,* 1912, 36, 165

of chlorine and fluorine, and metals react violently with the fluoride, liberating tin

It combines with other fluorides, forming a characteristic series of double salts, the *stannifluorides,* which mostly crystallise well and are isomorphous with the corresponding double fluorides of silicon, titanium, germanium, and zirconium [x]

Potassium Stannifluoride, K_2SnF_6,H_2O, is obtained by neutralising hydrofluoric acid with potassium stannate, or by treating stannic chloride with a cold solution of potassium fluoride [2]

It crystallises in thin, nacreous tablets or in rhombic pyramids which are much more soluble in hot than in cold water When the solution contains an excess of hydrofluoric acid, the salt K_2SnF_6,HKF_2 is deposited in monoclmic prisms

The stannifluondes of sodium, ammonium, calcium, and magnesium are also crystalline soluble salts

Tin Tetrachloride or *Stannic Chloride,* $SnCl_4$, was first mentioned by Libavms in 1605, who obtained it by distilling tin or its amalgam with excess of corrosive sublimate It was termed by him *Spmtus argenti vivi sublimati,* but afterwards it received the name *Spintus fumans Libavn* For its preparation, the process originally proposed by Libavius may be employed, or chlorine may be passed over tin foil, tm-plate scrap (p 877), or fused tin placed m a retort When the stream of chlorine is quick, and especially if the gas-delivery tube dips into the molten metal, an evolution of light and heat is observed It may also be prepared by passing chloroform vapour over the heated dioxide [3]

Tin tetrachloride is a colourless, thin, fuming liquid, which solidifies at — 33°, has a specific gravity of 2 234 at 15°, and boils at 113 9°,[4] forming a colourless vapour having the normal specific gravity of 9 1997 (Dumas) At the boiling point it dissolves rhombic sulphur, yellow phosphorus, and iodine, and can be mixed in all proportions with bromine and carbon disulphide When mixed with turpentine so much heat is evolved that the hydrocarbon takes fire Its property of fuming in the air depends on the fact that it absorbs atmospheric moisture In 1770, Demachy observed that it solidified when brought into contact with one-third of its weight of water to form a crystalline mass termed *butter of tin* Several distinct hydrates soluble in

[1] **Mangnac,** *Ann des Mines,* **1859, [5], 15, 221**
[2] **Emich,** *Monatsh* **, 1904, 26, 907** [3] **Renz,** *Ber,* **1906, 39, 249**
[4] **Thorpe,** *Journ Chem Soc* **, 1880, 37, 331**

water may be produced, according to the quantity of water which is added Thus the compound $SnCl_4,3H_2O$ is formed by exposing the anhydlous chloride to the action of moist air, or by the evaporation of its aqueous solution This hydrate crystallises in monoclinic needles which melt at 80°, and on cooling again solidify to a crystalline mass A second hydrate, having the composition $SnCl_4,5H_2O$, is obtained by the addition of a sufhcient quantity of water to the anhydrous chloride, or by the gentle evaporation of the aqueous solution It is deposited in opaque, acute, monoclinic prisms, which melt at a low temperature and again solidfy to a crystalline mass Lastly, large transparent, monoclinic crystals of the hydrate $SnCl_4,8II_2O$ are deposited m the cold from a dilute solution On boiling a dilute aqueous solution of tin tetrachloride, stannic hydroxide is formed, in very dilute solutions this precipitate forms on standing

Tin tetrachloride is employed by dyers as a valuable mordant Drebbel in Holland is said to have made the discovery that by help of this salt a permanent red dye can be obtained from cochineal Dyers were formerly in the habit of prepaung this mordant, known by the old names of tin-composition, physic, or dyer's spints, by dissolving tin, together with salammoniac or common salt, in nitric acid, or by dissolving tin in aqua regia, whence the solution was formerly termed nitromunate of tin It is usual now for dyers to employ the crystalline pentahydrate, $SnCl_4,5H_2O$, which is a commercial product known as *oxymuriate of tin* It is also largely employed for weighting silk

Anhydrous stannic chloride combines with ammonia to form a solid mass having the composition $SnCl_4(NH_3)_4$, which can be sublimed and is soluble in water without decomposition[1] It can be obtained in crystals by evaporating the aqueous solution over sulphuric acid, but if it be allowed to stand for some days, or if the liquid be warmed, stannic hydroxide separates out in a gelatinous form Tin tetrachloride combines also with many other chlorides to form crystalline compounds,[2] such as $SnCl_4,2SCl_4$ This is obtained by the action of chlorine on tin disulphide, and forms large, yellow crystals, which melt at a summer temperature, and decompose above 40°, with evolution of chlorine If dry nitrous fumes are led into a solution of stannic chloride, the compound $SnCl_4,N_2O_3$ is deposited as a

[1] Persoz, *Aan Chim Phys* , 1830, 44, 322
[2] H Rose, *Pogg Ann* , 1837, 42, 517

yellow, amorphous mass, and if this be sublimed or if the dry vapours from aqua regia be passed into the chloride, the compound $SnCl_4,2NOCl$ is produced, which crystallises in bright, shining octahedra If a solution of stannic chloride in chloroform be used, a white precipitate of $SnOCl_2,3SnCl_4,N_20_5$ is obtained, and this on heating yields a white sublimate of $SnCl_4,4NOCl$ [x] Stanmc chloride also combines with phosphorus pentachlonde to form the compound $SnCl_4,PCl_6$, which sublimes in glistening, colourless crystals, but when kept even in closed vessels falls to an amorphous powder It has a peculiar, extremely pungent smell, and fumes strongly in the air The compound $SnCl_4,POCl_3$ forms crystals which melt at 58°, and can be distilled at 180° without decomposition This compound fumes strongly in the air, and is at once decomposed by contact with water [2]

Like the fluoride, stannic chloride readily yields a series of double salts known as the *stannichlondes*, which present a similarity to the platinichlorides, but are less stable than the latter salts [3] The free acid, H_2SnCl_6, is obtained in thin plates containing $6H_20$ by saturating the pentahydrate, $SnCl_4,5H_20$, with hydiochlonc acid gas at 28° and cooling to 0°.[4]

Ammonium Stannichloride, $(NH_4)_2SnCl_6$, separates as a crystalline powder when solutions of the two salts are mixed, and crystallises from dilute solution in small, regular octahedra It dissolves at the ordinary temperature in 3 parts of water Its concentrated solution can be boiled without decomposition, but when diluted tin hydroxide separates out It was formerly much used by calico-pimters under the name of *pink salt,* from its power of acting as a mordant for madder-red colours, but its use has been almost entirely superseded by the crystalline pentahydrated stannic chloride

Tin Tetrabromide or *Stannic Bromide*, $SnBr_4$—Tin and bromine unite together with evolution of light and heat The bromide is best prepared by adding bromine very slowly to strips of tin, the temperature being kept between 35° and 59° [5] It is a white, crystalline mass, which fumes strongly on exposure to air and is easily soluble in water It melts at 33° and boils at

i Thomas, *Compt rend* , 1896, **122,** 32

[2] Casselmann, *Annalen*, 1852, 83, 257

[3] von Biron, *J Buss Phys Chem Soc* , 1904, **31,** 489, Bcllucci and Parravano, *Atti B Accad Linceu* 1904, [4], **13,** n, 307, von Biron, *J Buss Phys Chem Soc*, 1905, 37, 963, 994, 1036

[4] Engel, *Compt rend* , 188b, **103,** 213, Seubert, *Ber* , 1887, 20, 793

[5] Lorenz, *Zert anorg Chem*, 1895, 9, 365

201° The specific gravity of the liquid is 3 349 at 35°, and its vapour density is 7 92 [1] It is easily soluble in cold water, forming a colourless liquid from which the hydroxide is deposited slowly at the ordinary temperature and quickly on boiling It yields crystalline *stanmbromides* with the alkali bromiues

Tin Tetraiodide, SnI_4—When tin and iodine are heated together, combination commences at 50°, and at a higher temperature heat and light are emitted In order to prepare this compound, tin filings are first moistened with carbon disulphide, and then iodine is gradually added It crystallises in red octahedra, melting at 146° and having a specific gravity of 4 696 Tin tetraiodide boils at 295°, but sublimes at as low a temperature as 180° in yellowish-red needles, very similar in form to those of ammonium chloride It is soluble in carbon disulphide, absolute alcohol, ether, chloroform, or benzene, with water it forms hydnodic acid and stannic oxide

If ammonia be led into a solution of tin tetraiodide in carbon disulphide, and at the same time the solvent be allowed to evaporate, a white substance, $SnI_4,8NH_3$, is formed This is also formed by passing ammonia over the tetraiodide [2]

Tin Disulphide or *Stannic Sulphide,* SnS_2—This compound, crystallising in six-sided tablets or in gold-coloured, translucent scales having a specific gravity of 4 425, is used as a bronze powder for the purpose of bronzing articles of gypsum, wood, etc, and is known in commerce as mosaic gold The discovery of this compound is usually ascribed to Kunkel He does indeed speak of a sublimation of sulphide of tin and sal-ammomac, but expresses himself so vaguely that it is impossible to recognise this compound from his description It was well known in the eighteenth century under the names of *mosaic gold, aurum mosaicum,* or *musivum* It was then prepared as at the present day by subliming a mixture of tin amalgam, sulphur, and ammonium chloride, and as it was supposed to contain mercury it was often employed as a mercurial medicine Peter Woulfe in 1771 showed that it did not contain mercury, and described other methods for its production, according to which it is still prepared Thus, for instance, it is obtained in the form of a fine pigment by heating 18 parts of tin amalgam, containing 6 parts of mercury, with 6 parts of ammonium chloride and 7 parts of sulphur, when ammonium chloride, mercuric chloride,

[1] **Carnelley and O'Shea,** *Journ Chem Soc* **, 1878, 33, 55**
[2] **Ephraim and Schmidt,** *Ber,* **1909, 42, 3856**

and stannous chloride sublime, and stannic sulphide remains behind in the form of .golden-yellow scales It is likewise prepared by heating tin monosulphide with 8 parts of mercuric chloride, or subhming tin filings with ammonium chloride and sulphur, and according to several other receipts given by Woulfe [1] Pelletier believed mosaic gold to be a compound of sulphur with the highest oxidation product of tin, and Proust, who found that it could be obtained by heating stannous chloride or tin monoxide with sulphur, supposed it to be a compound of tin, sulphur, and a small quantity of oxygen The exact composition was ascertained by J Davy and Berzelius in the year 1812 The formation of mosaic gold from tin, sulphur, and ammonium chloride appears to take place according to the following equations (Gmelin)

(I) $Sn + 4NH_4C1 = (NH_4Cl)_2SnCl_2 + H_2 + 2NH_3$
(II) $2(NH_4Cl)_2SnCl_2 + S_2 = SnS_2 + 2NH_4C1 + (NH_4Cl)_2SnCl_4$

When heated, a portion sublimes without decomposition, but the greater part is resolved into sulphur and monosulphide It is not attacked by hydrochloric or nitric acid, but readily dissolves in aqua regia, as well as in caustic potash, when potassium stannate and potassium thiostannate are formed If sulphuretted hydrogen be led into a solution of the tetrachloride a yellow precipitate is obtained This consists of a mixture of tin disulphide and tin dioxide, and is readily soluble in the sulphides of the alkali metals, when the *thiostannates* are formed

Thiostannic Acid—When dilute hydrochloric acid is added to a solution of thiostannate, a yellow precipitate is obtained, which on drying forms an almost black powder possessing a brown streak and wax-like lustre, and having the composition H_2SnS_3 When heated in absence of air it yields the golden-yellow disulphide [2]

Potassium Thiostannate, $K_2SnS_3,3H_20$, is prepared by boiling a concentrated solution of potassium sulphide with the necessary quantities of sulphur and tin, it crystallises in colourless prisms By a similar process, the *sodium salt*, $Na_2SnS_3,2H_20$, is obtained in yellow, vitreous, regular octahedra [3] When sodium sulphide is fused with tin monosulphide and sulphur, a black, crystalline mass is obtained, yielding a dark-coloured solution, which on concentration at a low temperature yields

[1] *Phil Trans*, 1771, 61, 114 [2] Kuhn, *Annalen*, 1852, 84, 110
[3] Ditte, *Compt rend*, 1882, 95, 641

colourless crystals resembling gypsum, and having the formula $Na_4SnS_4,12H_20$

Ammonium thioWannate is formed by dissolving the sulphides in yellow ammonium sulphide, and may be precipitated by alcohol m unstable yellow tablets of the composition[1] $(NH_4)_2SnS_3,3H_20$

When mosaic gold is fused with iodine in absence of air, a crystalline mass of SnS_2I_4 is obtained, and this can be sublimed, or recrystalhsed from solution in carbon disulphide It is decomposed by water into stannic oxide, sulphur, and hydnodic acid

Stannic Oxysulphide, Sn_2OS_3,UH_2O—This compound is obtained by allowing precipitated stannic sulphide to remain in contact with ammonia, filtering and acidifying the filtrate, or by digesting the sulphide with ammonium carbonate and acidifying the filtered solution It is a white mass which is soluble in ammonia and gradually becomes yellow on keeping[2]

Stannic Sulphate, $Sn(SO_4)_2$—As already mentioned, tin dioxide dissolves in concentrated sulphuric acid, and from the solution two crystalline bodies may be obtained having the empirical formulae $SnO_2,2H_2SO_4$ and SnO_2,H_2SO_4, which may be regarded as the normal sulphate, $Sn(SO_4)_2,2H_2O$, and the basic sulphate, $Sn(SO_4)_2,SnO_2,2H_2O$ Both of these are decomposed by water with separation of stannic oxide

On mixing solutions of stannic acid in sulphuric acid, and calcium sulphate in sulphuric acid, and concentrating, regularly formed, colourless cubes are obtained of $Sn(SO_4)_2,CaSO_4,3H_2O$, similar salts are obtained with barium, strontium, and lead sulphates[3]

Stannic Nitrate, $Sn(NO_3)_4$, is obtained as a white powder by the action of 70 per cent nitnc acid on tin, but must be quickly removed, as it is rapidly converted into the hydrated dioxide It is a white substance which is stable in presence of concentrated nitric acid at 90°, but is immediately decomposed at 100°[4] It dissolves in water, but the solution is almost immediately decomposed with separation of hydrated stannic oxide

Potassium Ammono-stannate, $K_2[Sn(NH_2)_6]$, is produced by the action of potassamide on stannic iodide in liquid ammonia,[5]

[1] **Stanek, *Zeit anorg Chem*, 1898, 17, 117**

[2] **Schmidt, *Ber*, 1894, 27, 2739 See also *Chem Centr*, 1907, l, 397**

[3] **Weinland and Kuhl, *Ber*, 1906,39, 2951 See also *Zeit anorg Chem*, 1907, 64, 259**

[4] **Montemartmi, *Gazz*, 1892, 22, 384**

[5] **Fitzgerald, *J Amer Chem Soc*, 1907, 29, 1693**

a reaction entirely analogous to the production of stannates by the action of alkalis in aqueous solution

$$6KNH_2 + SnI_4 = K_2[Sn(NH_2)_6] + 4KI$$
$$6KCLI + SnI_4 = K_2[Sn(OH)_6] + 4KI$$

If this is heated at 145°, it loses three molecules of ammonia, which is analogous to the behaviour of potassium stannate tnhydrate

$$K_2[Sn(NH_2)_6] = K_2Sn(NH)_3 + 3NH_3$$
$$K_2[Sn(OH)_6] - K_2Sn0_3 + 3H_20$$

No more ammonia can be driven off by heating for several hours at 316°

Tin and Phosphorus—When finely-divided tin is heated in the vapour of phosphorus, a silver-white, very brittle mass, having the composition SnP, is obtained This has a specific gravity of 6 56, and dissolves readily in hydrochloric acid, but is not attacked by nitric acid When phosphorus is thrown on to the surface of molten tin, combination also takes place The compound containing the largest quantity of phosphorus which can thus be obtained has a silver-white colour, is not very brittle, and may be cut with a knife, it appears to possess the composition Sn_3P_2 (Pelletier)[1] If spongy tin, obtained by precipitating a tin salt with zinc, be brought into contact with such a quantity of phosphoius that one atom of the latter be present to nine atoms of the metal, a phosphide having the composition Sn_9P is obtained The same compound is foimed whenever any of the other phosphides containing more phosphorus is heated This is a coarse, crystalline mass, which has the appearance of cast zine It melts at 370°, and is used for the preparation of phosphor-bronze

Stannic Pyrophosphate is obtained by the action of phosphoric acid on stannic acid, and is insoluble in water and in nitric acid This reaction is employed for the separation of phosphoric acid from other bodies For this purpose a known quantity of tin foil is added to the nitric acid solution of the body under investigation, when the whole of the phosphoric acid remains behind with the metastannic acid

[1] Sec also Stead, *J Soc Chem Ind* , 1897,16, 200, 309, and Johbois, *Compt rend*, 1909, 148, 630

DETECTION AND ESTIMATION OF TlN

400 When a small quantity of a tin compound is held in the reducing flame on charcoal, a malleable lead of metal is obtained, which easily dissolves in hot hydrochloric acid This solution gives with a small quantity of mercuric chloride a white precipitate which becomes grey on boiling

$$(I)\quad SnCl_2 + 2HgCl_2 = SnCl_4 + Hg_2Cl_2$$
$$(II)\quad SnCl_2 + Hg_2Cl_2 = SnCl_4 + 2Hg$$

If one of the metallic globules be fused in a borax bead slightly tinted with cupric oxide and heated in the reducing flame, the bead will become of a red tint, due to the formation of cuprous oxide

Stannous salts yield a brown precipitate of stannous sulphide with sulphuretted hydrogen, which dissolves in ammonium sulphide containing polysulphides, the solution, on addition of an acid, deposits stannic sulphide Ammonia and caustic alkalis give a white precipitate of stannous hydroxide, which is soluble in excess of the latter reagents Stannous chloride gives a blue coloration with ammomum molybdate, and in this way 1 part of tin as stannous chloride may be detected in 1,500,000 parts of solution[1]

Stannic salts yield a yellow precipitate of stannic sulphide with sulphuretted hydrogen, readily soluble in ammomum sulphide, and alkalis precipitate stanmc hydroxide, which dissolves in an excess of the precipitant

Zinc precipitates metallic tin from solutions of the tin salts in the form of glistening scales, or in a spongy or arborescent mass The tin salts do not impart any colour to the non-luminous gas-flame, but the spark spectrum of the chloride exhibits two characteristic lines having wave-lengths of 4526 and 5631 (Lecoq de Boisbaudran) These same lines are seen together with others in the spark spectrum of the metal, the most brilliant of the tin lines being as follows (Thalen) 6452, 5798, 5631, 5588, 5563, 4526

In the processes of qualitative analysis tin is obtained together with those metals which are precipitated by sulphuretted hydrogen in an acid solution To separate tin from these the

[1] Longstaff, *Chem News.* 1899, 80, 282, Rogers, *J Amer Chem Soc* , 1900, 22, 220

well-washed precipitate is treated with yellow ammonium sulphide, filtered, and the filtrate acidified with cold dilute hydrochloric acid The precipitate may contain, beside stannic sulphide, the sulphides of arsenic and antimony After it has been well washed with water, it is digested with solid ammonium carbonate to dissolve the sulphide of arsenic The residue is then dissolved in concentrated boiling hydrochloric acid, the solution boiled with metallic copper, and the liquid tested for stannous chloride with mercuric chloride (see also under Antimony).

Tin may be estimated as the oxide If the metal or one of its alloys be under examination, it is oxidised with pure, tolerably strong nitric acid, and the well-washed residue ignited From solution it is precipitated with ammonia as the hydroxide, but if it be present in the form of stannous salt it must be first oxidised with chlorine or hydrochloric acid and potassium chlorate The precipitate obtained by ammonia is then dissolved in the smallest quantity of hydrochloric acid and heated with a concentrated solution of sodium sulphate, when the hydroxide is again precipitated, and this is not gelatinous, and may therefore be easily washed (Lowenthal) When tin sulphide is obtained in the separation of tin from the other metals, it can be gradually converted into stannic oxide by gentle roasting and subsequent ignition

Tin is frequently estimated by volumetric methods, the processes depending on the oxidation of stannous chloride to stannic chloride by means of standard solutions of ferric chloride or iodine

The electrolytic method has been employed for estimating tin as the metal, the process being carried out in the presence of ammonium oxalate or some other organic salt[1] It may be deposited also from solutions in ammonium sulphide

Atomic Weight of Tin—The early determinations of the atomic weight of tin were made by oxidising the metal to the dioxide, but the numbers obtained varied considerably Thus Berzehus[2] found the number 117 65, and Mulder and Vlaanderen[3] 116 3, whilst a later determination by the last named gave the higher value 11816 Dumas[4] by the same method obtained the number 118 06 Bongartz and Classen[5] employed

[1] Engels, *Ber*, 1895, 28, 3182, Hollard, *Compt rend*, 1897, **124,** 1451, Fischer, *Ber*, 1903, 36, 2348, etc.

[2] *Pogg Ann*, 1826, 8, 177 [3] *J pr Chem*, 1849, 49, 35

[4] *Ann Chem Pharm*, 1860, **113,** 26 [5] *Ber*, 1888, **21,** 2900

four different methods, namely, the oxidation of pure tin with nitric acid, and the electrolysis of potassium stannichlonde, ammonium stanmcmoride, and stanmc bromide The average of the most trustworthy experiments gave the number 119 0 Briscoe,[1] by analysis of the tetrachloride, obtained the number 118 7, which is now (1922) adopted[2] This number has been confirmed by Baxter and Starkweather,[3] by electrolysis of stannic chloride, and by Krepelka,[4] by analysis of the tetrabromide

L E A D (Plumbum) Pb = 207 20 At No 82

401 The first mention of lead occurs in the well-known passage in the Book of Job, Chap X I X , and it is mentioned also in the Book of Numbers, Chap X X X I , as a portion of the spoil taken from the Midianites It is found under the name of opheret, derived from the word aphar, signifying to have a grey appearance In the oldest Greek translations of the Old Testament the word occurs, and this as well as the word undoubtedly refers to lead It appears that no exact distinction was drawn between the metals lead and tin during the time of the Israelites, but we find that Pliny points out a distinction between these two metals, inasmuch as he gives the name of *plumbum nigrum* to lead, whilst tin is designated as *plumbum candidum* (p 872) Lead was known to the ancient Egyptians, as lead plates have been found in the Temple of Barneses I I I

It has already been stated that the seven metals known to the ancients were supposed to be in some way connected with the seven heavenly bodies which were then known to belong to our solar system Dull, heavy lead was apportioned to Saturn, and this metal is designated in the writings of the alchemists by the sign

Lead is seldom found in the free state in nature Native lead does, however, occur in small quantities in certain lead ores, and in volcamc tufa The oxides of lead are found in the form of rare minerals, the yellow oxide, PbO, and the red oxide or red lead, Pb_3O_4 The commonest ore of lead is galena or lead sulphide, PbS, this is very widely distributed, generally occurring together with quaitz, calc-spar, fluor-spar, and heavy-spar, in the older as well as in the more recent strata, and in almost every

[1] *Journ Chem Soc* , 1915, **107,** 63

[2] Aston, *Nature,* 1922, **109,** 813, has shown that there are eight isotopes of tin of atomic weights, 120, 118, 116, 124, 119, **117,** 122, 121

[3] *J Amer Chem Soc* , 1920, 42, 905 [4] *Ibid* , 925

part of the world Thus in Cornwall it occurs in veins in the coarse argillaceous schist, provmcially termed killas, in Derbyshire, Cumberland, Northumberland, and Yorkshire, it is found in mountain lin estonvi, in Cardiganshire and Montgomeryshire it occurs in the Lower Silurian, and the chief deposits in the United States likewise occur in the same formation Again, at Sala in Sweden, it is found in granular limestone, and in Freiberg in a schistose gneiss, older than the carboniferous system Enormous quantities of galena, closely associated with zinc blende, occur in the Broken Hill deposits of Australia, in Burma, Bhodesia, etc Sulphide of lead also occurs in combination with the sulphides of antimony and copper in the minerals zmckenite, $PbSb_2S_4$, and bournomte, $CuPbSbS_3$ In addition to these ores, lead carbonate occurs as the mineral cerussite, $PbCO_3$, found in some localities, as in the neighbourhood of Aix-la-Chapelle and of Santander in Spain, in sufficient quantity to be worked It is also found in the lead mines of Cornwall and Devonshire, in Yorkshire, at Leadhills in Scotland, and at Seven Churches in County Wicklow Other naturally occurring compounds of lead are the basic chloride, occurring as the minerals matlockite, Pb_2Cl_2O, and mendipite, $Pb_3Cl_2O_2$, and the sulphate of lead or anglesite, $PbSO_4$, found associated with galena and carbonate of lead at Leadhills and in other localities Again, we have a basic sulphate called lanarkite, $PbO,PbSO_4$, leadhilhte, $PbSO_4,3PbCO_3$, phosgemte, $PbCl_2,PbC0_3$, stolzite or lead tungstate, $PbW0_4$, wulfemte or lead molybdate, $PbMo0_4$, crocoisite or lead chromate, $PbCr0_4$, pyromorphite or lead phosphato-chlonde, $3Pb_3P_20_8,PbCl_2$, mimetesite or lead chloro-arsenate, $3Pb_3As_20_8,PbCl_2$, as well as compounds of lead with the rarer elements, such as selenium, tellunum, selenic acid, vanadic acid, etc

By far the greater quantity of the total lead brought into the maikets of the world is derived from galena

402 *Smelting of Lead*—Lead is an easily reducible metal requiring but simple processes for its production, and it was produced in England during the Roman occupation m a variety of localities Numerous pigs of Roman lead have been found bearing Latin inscriptions Whether lead was reduced in England before this period appears doubtful, the remains of rude furnaces in which lead ore was smelted in early times are, however, found in Derbyshire and elsewhere, and are termed *boles* by the inhabitants In these furnaces the heat

was not urged by an artificial blast of air, but piles of stone were built on the western brow of some eminence so as to employ the natural currents of air on mountainous places A mixture of ore and charcoal was introduced into the interior of these furnaces, the lead being run out at the bottom after the operation

The form of furnace next employed was the *ore-hearth,* a small, rectangular blast-furnace blown by bellows worked by means of a water wheel [1] Modifications of this furnace are still in use in certain localities

About the middle of the eighteenth century lead smelting in reverberatory furnaces appears to have been introduced into England from Flintshire, where it was in use in the year 1698

Three distinct processes are employed for lead smelting The first of these, known as the *air reduction process* (Percy), is employed when the ore consists mainly of galena, and is free from silica and the sulphides of other metals The second, or *carbon reduction process,* is employed for less pure ores and consists m the roasting of the ore and the subsequent reduction of the lead oxide by carbonaceous matter The third process is known as the *precipitation process,* the reduction of the lead being effected by metallic iron, this is chiefly practised in France, Germany, Spain, and North America, where the ore contains other metals, such as copper, antimony, and arsenic It is however, to be remembered that two or even three of the above processes are often worked in the same furnace with the same charge of ore

In the *air reduction process* the galena is roasted in a reverberatory furnace until a portion of the sulphide is converted into oxide and sulphate, the temperature is then raised, when metallic lead is formed together with sulphur dioxide The following reactions are usually given as representing the interaction of the unaltered lead sulphide with the oxide and sulphate

$$2PbO + PbS = 3Pb + SO_2$$
$$PbSO_4 + PbS = 2Pb + 2SO_2$$

In presence of an excess of sulphur dioxide, however, lead is partially reconverted into sulphide and sulphate [2]

$$2Pb + 2SO_2 = PbS + PbSO_4$$

[1] **See H L Pattinson, " Description of Lead Smelting in the North of England "** ***Transactions of the Natural History Society of Northumberland, Durham, and Newcastle on Tyne,*** **vol 2, part I , also J J Brown, jun , " Lead Smelting in the Ore Hearth,"** ***Trans Am Inst Min Eng,*** **1911, 42, 402**

[2] **Jenkins and Smith,** ***Proc Chem Soc*** **, 1897,13,104, Schenck and Rassbach,** ***Ber,*** **1907, 40, 2185, 2947**

The reverberatory furnaces used for the English process of lead smelting are of two kinds, the Flintshne furnace and the flowing furnace The difference between these is that in the first the slag is aked out in pasty lumps, whereas in the flowing furnace the slag is tapped out in the molten state and termed run-slag The reaction which takes place during the early stages of reduction is identical in both cases, but, in the flowing furnace, metallic iron is added to assist in the reduction of sulphide of lead

Fig 187 shows the constiuction of the Flintshire furnace The usual charge of are is 20 cwt This is introduced by means of a hopper (T) in the arch of the furnace The hearth of the furnace (B) is hollowed out as shown in the figure to permit

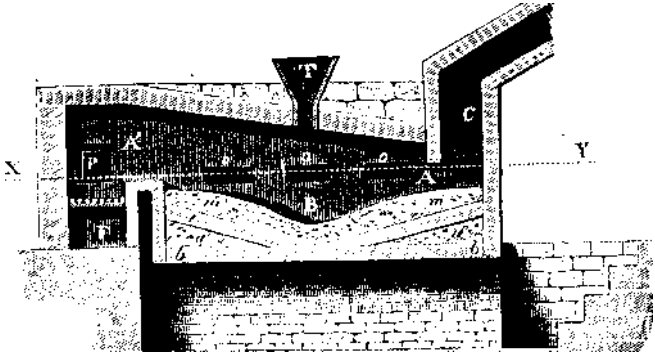

Eig 1ST.

the lead to flow through a tapping hole into an iron pot placed in front of the furnace The charge is evenly spread over the surface and gently heated, the are being well rabbled at intervals, and the tempeiatuie carefully regulated by opening or closing the various doors, so as to maintain the mass as hot as is possible without causing it to clot together, a portion of the sulphide is oxidised to oxide and sulphate, and the mass thus prepared for the following stage of the operation During this part of the process the skimmings from the lead run off from the previous operation, which consist chiefly of lead containing a little sulphide, are added, and are quickly acted on by the lead oxide and sulphate with formation of metallic lead, which is run off from the tap-hole and contains more silver than the subsequent portions of the metal After about two hours the temperature is raised to a bright red heat, the metal being formed in quantity, whilst

from time to time, in addition to stirring the mass, a small quantity of lime is added to stiffen the unreduced portion This part of the process extends over an hour, and then for three-quarters of an hour the temperature is further raised and an additional small quantity of lime added, which besides lessening the fusibility of the mass also liberates any lead oxide which may have combined with the silica, and allows it to be reduced by the lead sulphide Finally, the furnace is raised for three-quarters of an hour to the highest attainable temperature and a sufficient quantity of lime added partially to solidify the slag, which is raked out, and the lead run off from the tap-hole in the usual manner

The *grey slag* obtained may contain as much as 40 per cent of lead, and is further worked up in the slag-hearth, which is a small shaft furnace, or may be mixed in with the charge for the larger blast furnaces

Reduction of Lead in Blast Furnaces —This is the method now most generally adopted, as it is suitable for any class of ore and the percentage of lead may be much lower than that necessary for the other methods, whilst the presence of silica to a certain extent is not disadvantageous For ores such as those which occur in the Harz, where the galena is mixed with iron and copper pyrites, zinc blende, fahl-ore, bournonite, and zinckenite, the blast furnace method gives the best results, and this is suitable also for the reduction of the oxides or carbonates of lead The process for sulphide ores consists first in roasting to get rid of sulphur and then smelting the roasted ore with fluxes and reducing agents in the blast furnace The roasting was formerly effected in heaps, in shaft furnaces or reverberatory furnaces, the latter being worked by hand or mechanically

Several new methods of roasting galena have been introduced, in which the ore is mixed with lime, gypsum, oxide of iron or other material, damped and fed on to a small fire in a converter-shaped vessel, through which air is blown,[1] or fed on to some type of sintering machine such as is used in the various Dwight-Lloyd[2] processes for down-draft roasting The chief advantage of these processes lies in the fact that the product obtained is very suitable for blast-furnace treatinent, but

[1] *Mineral Industry,* 1905, 14, 402, see also " Lead Smelting and Refining," by W R Ingalls, published by the *Engineering and Mining Journal,* 1906, for " The Theory of Blast Roasting of Galena," see Bannister, *Trans Inst Min and Met,* 1912, 21, 346

[2] *Report of Seventh Internal Cong App Chem,* 1909, III, *A,* 20

besides this the cost is less, the losses of metal are less, and the production of fine material is greatly reduced

The blast furnace mostly used for lead and silver-lead smelting

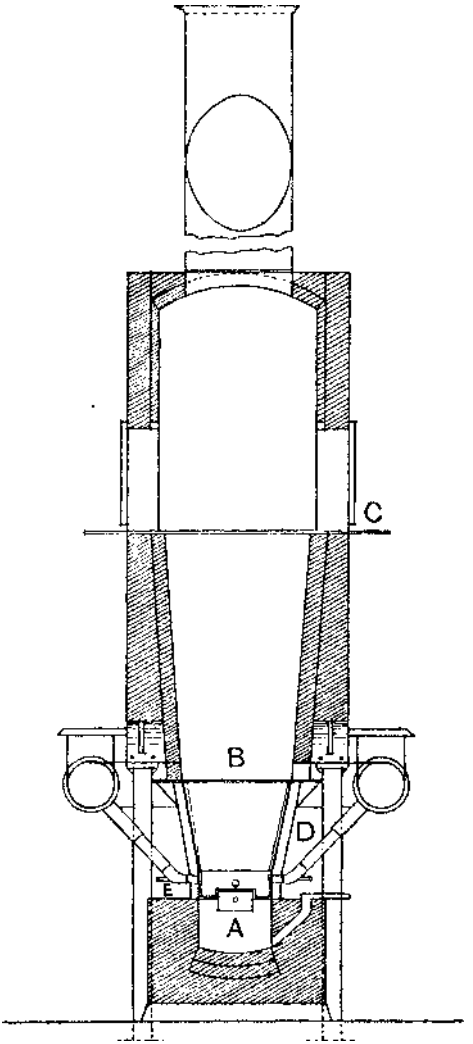

Fig. 188,

is rectangular in plan, about 44 inches wide and 144 inches long inside at the tuyere level Fig 188 is a section of such a furnace, which comprises a crucible portion (A), a- shaft (B), extending from the crucible to the feed-floor (0), and a stack from

the feed-floor upwards The furnaces are water-jacketed about the lower portion or bosh of the shaft, these jackets being made of cast iron or of stee, and through them water circulates continually These jackets are shown at D, and through the side jackets the tuyeres (E) pass into the furnace The shaft above these jackets is lined with firebrick, although in the newer furnaces the water jackets are carried to the top

An Arents syphon tap is often fitted to the crucible portion of these furnaces for continuously drawing off the lead When the ores contain copper the roasting is not carried so far, a certain amount of sulphur being left in the ore to combine with the copper for the formation of a cupriferous matte, and in this case a certain amount of unaltered lead sulphide will always be present in the matte The furnace charge consists of a mixture of roasted ore, carbonaceous fuel, generally coke or a mixture of coke and charcoal, old slags and fluxes The fluxes most used are ferruginous ores, often carrying silver or gold, which is collected partly in the lead and partly in the matte if this be also formed, ferruginous slags containing an excess of ferrous oxide, and sometimes lime or limestone The slag should contain between 30 and 35 per cent of ferrous oxide, between 10 and 30 per cent of lime, and between 30 and 50 per cent of silica The lead present in the form of oxide is reduced partly by the carbon monoxide in the gases and partly by solid carbon, that present as sulphide, by iron, generally formed by reduction of the oxide of iron present in the charge Any silicate present is reduced by the action of carbon in the presence of ferrous oxide or lime, and any lead sulphate present is reduced by reaction with sulphide, or is converted into sulphide by the action of carbon and this sulphide reduced by metallic iron

Softening of Lead —The lead produced in these processes is hard, owing to the presence of small quantities of antimony, arsemc, copper, zinc, iron, tin, bismuth, and sulphur, and it is necessary to remove these in order to render the lead marketable Silver is also generally present and is removed by special processes, which are described later, and which enable the silver to be recovered It is also necessary to remove impurities before desilvensation, as copper, antimony and arsenic interfere with the Pattinson process, and these, together with nickel and cobalt, interfere with Parkes's process

For the purpose of removing the impurities, the lead is melted in a reverberatory furnace at a low temperature Copper

forms an alloy with some of the lead which is less fusible than lead itself and this separates out as a scum on the molten lead and may be removed, all the other commonly occurring impurities except bismuth are more readily oxidised than lead and are oxidised in the furnace together with a portion of the lead, the mixed oxides forming a dross on the surface which is removed from time to time Bismuth cannot be got rid of in this manner, but it is concentrated with the silver in the Pattinson process for desilvensation The hearths of modern reverberatory furnaces for the softening of hard lead consist of wrought iron pans lined with two thicknesses of firebrick and are often water-jacketed at the sides to dimniish the corrosive action of the oxides formed on the material composing the hearth

Condensation of Lead Fume —During the smelting processes a large amount of lead fume is carried away in suspension in the waste gases from the furnaces, and many devices have been introduced for condensing and collecting these fumes, for subsequent treatinent In many works the arrangement consists merely in having very long flues between the furnaces and the chimney, the amount of condensation depending on the length of the flue In other works more complete condensation is effected by arrangements for lowering the velocity of the gases, by first passing the exit gases through large chambers containing baffle plates, and then through iron flues cooled by the air Other methods for condensing the fume consist of using a water spray or causing the gases to pass through layers of water on their way to the chimney " Bag houses " are largely used for the condensation of lead fume, in the use of these, the cooled gases are forced through canvas or twill bags on their way to the chimney Electrostatic methods of precipitating the fume have been introduced into some works

403 *Desilvensation*—Ordinary lead obtained by any of the above-mentioned processes always contains silver, and a very considerable proportion of the silver which now comes into the market is obtained from argentiferous galena In former times the only process by which this silver could be extracted was cupellation, by which the whole of the lead is oxidised, whilst metallic silver remains behind The oxide has then to be again leduced to metallic lead It is, however, generally admitted that the process of cupellation cannot be economically carried on in the case of lead which contains less than 150 oz. of silver to the ton, and consequently, as very large quantities of

lead are brought into the market containing smaller quantities than this, a large portion of this silver was lost until Hugh Lee Pattinson in the year 1833 obtained a patent for an improved method of separating silver from lead, which soon came into general use and by which large quantities of silver are now extracted from lead

This method depends upon the fact that if lead containing a small quantity of silver be melted, and the melted mass allowed to cool, a point is reached at which pure lead begins to crystallise out If the crystals of lead which are thus formed be then withdrawn from the remainder of the metal, and this process continued until the greater part of the lead has been separated, it is found that the liquid which remains contains most of the silver In order to render this process economical the lead requires to be repeatedly crystallised in a series of iron pots, the lead rich in silver gradually accumulating towards one end of the series, whilst the desilvensed or market lead is obtained at the other end

The melted lead is first thoroughly skimmed, then the fire is withdrawn and the lead allowed to cool, care being taken to break off and mix with the liquid mass any portion that may solidify on the sides of the pot When the temperature reaches a certain point small crystals of lead begin to form, and at this point the whole mass of metal is continually stirred with an iron rod, whereby the crystals sink to the bottom of the pot and accumulate in considerable quantity A perforated ladle is now introduced by means of which the crystals are removed The operation is thus earned on in successive stages until two-thirds or even seven-eighths of the original lead is removed from the pot By this means in an actual working 846 cwt of original lead was separated into 36 cwt of nch lead containing 160 to 170 oz of silver per ton, and 810 cwt of poor lead containing 7 to 10 dwt of silver per ton The silver is then extracted from the rich lead by the process of cupellation (p 461)

A modification of the Pattinson process, known as the Luce-Rozan process, is now frequently adopted in place of the original method For this only two pots are necessary, viz , an upper or melting pot, and a lower or crystallising pot The former holds about 7, and the latter about 21 tons

The mode of working the plant is as follows[1] The crystallising pot may be supposed to contain 14 tons of lead

[1] Cookson, *Trans Newcastle Chem Soc*, 1878

crystals from a previous operation, and the melting pot 7 tons of lead of similar silver content, already melted, a moderate fire is set away in the fire-grate of the crystallising pot, and the contents of the melting pot skimmed of their dross, the hot lead from the latter is then run on the warm crystals in the crystallising pot, and with the aid of the moderate fire already referred to, the whole contents of this pot (now 21 tons) are rapidly melted and brought into a working condition, when the charge is carefully skimmed, the melting pot is at the same time charged with 7 tons of lead from a previous operation containing one-half the amount of silver in the lead then being worked up, as this will be the assay of the crystals resulting from the operation about to be performed in the crystallising pot The fire under the latter is then drawn, and steam at fifty to fifty-five pounds pressure per square inch admitted and distributed evenly by means of a baffle plate To hasten the cooling and consequent crystallisation, thin strearms of water are allowed to run on to the surface of the lead, the crystallisation being more perfect than in the old Pattinson process As soon as two-thirds of the lead has crystallised out, the rich liquid lead is tapped off, the crystals being retained in the pot by means of perforated plates The liquid lead is run into moulds and awaits its turn for further treatinent The proportion of silver in the crystals is thus reduced to one-half, whilst that in the liquid run off is doubled, and this process of recrystallising is repeated as in Pattinson's process, until the ciystals are sufficiently poor in silver not to require further treatinent, and the rich lead is worked up until its silver content is of the standaid fit for cupellation

This process has the advantage over that of Pattinson that a great saving is effected in fuel and the cost of labour, and also that, except in the case of very hard lead, no further softening process is necessary The original outlay and expenses for repairs are, however, considerably greater

Another process for desilvensing lead is known as Parkes's or Karsten's zinc process Molten lead and zinc do not mix in all proportions, lead being capable of taking only 1 6 per cent of zinc, whilst zinc takes only 1 2 per cent of lead, and Karsten, in 1842, concluded from experiments which he made on the subject that lead gives up all the silver which it contains if melted with zinc, but he did not apply this conclusion to practical metallurgy In the year 1850 Alexander Parkes, of Birmingham,

patented a process for extracting silver from lead by the above-mentioned reaction For a ton of lead containing 14 oz of silver, 22 4 lb of sinc are needed and a proportionate amount if more silver be present The alloy of zinc and silver rises to the surface during cooling, and when it solidifies it is withdrawn by means of a perforated ladle In order to remove the small quantity of zinc which is dissolved in the lead, the mixture is heated to dull redness and steam blown through, the zinc being thereby oxidised, whilst the main portion of the lead remains behind in the maiketable state The zinc-silver alloy is first heated to a temperature slightly above the melting point of lead to liquate as much of the latter as possible, and the residue is heated with carbon in a crucible retort, whereby the zinc is distilled off and collected, the residual rich silver-lead alloy being cupelled in the usual manner

Gold and copper, which sometimes occur in market lead, can be separated from it in the same way, inasmuch as these metals alloy with zinc even more readily than does silver, and this process has been satisfactorily carried out in England by Baker A similar method is employed in the Harz, the lead is there melted with 0 16 per cent of zinc, and the alloy is obtained as a scum on the surface, having the composition

Pb	Zn	Cu	Ag
89 46	5 78	4 52	0 243

On a second addition an alloy having the following composition is obtained [1]

Pb	Zn	Cu	Ag
9105	5 21	3 50	0 238

Market lead almost always contains traces of antimony, copper, and iron, and occasionally of zinc, nickel, and bismuth, whilst the silver which it contains varies from 1 part in 40,000 to 1 part in 200,000, but since the introduction of the method of desilvensmg by zinc and purification by steam the purity of the commercial lead has very much increased

Elect ro-refimng of Lead[2]—Various attempts have been made from time to time to refine lead by an electrolytic process, but until Betts invented his process in 1901, no great success was attained In this process, the electrolyte consists of lead

[1] Rammelsberg, *Ber Entw Chem Ind* , 935

[2] Sec *Lead Refining by Electrolysis,* by *A* G Betts (John Wiley & Sons, 1908)

fluosihcate solution, the anodes are cast of the crude lead and the cathodes of pure lead In order to obtain solid deposits of lead, the use of addition agents to the electrolyte is necessary, and in the process gelatine is mostly used, in the proportion of 1 part of geiatine to 5,000 parts of solution The impurities remain in the anode slime, and pure lead is deposited at the cathode, as shown by the following table

	Cu	Bi	As	Sb	Ag	Pb
Crude lead	1 40	014	7 4	4 0	0 64	87 14
Pure lead	0 001	0 0022	0 0025	0 0017		
Anode slime	9 3	0 52	44 58	25 32	4 7	10 3

The following table shows the production of lead in 1919, by the chief lead-producing countries in metric tons [1]

Australasia	82,732 tons
Belgium	4,157 „
Canada	19,566 „
France	10,928 „
Germany	50,700 „
India	19,090 „
Italy	16,264 „
Mexico	70,229 „
Spain	99,912 „
United Kingdom	13,100 „
United States	385,682 „

404 Chemically pure lead is prepared according to Stas[2] as follows —A solution of acetate of lead is heated in a leaden vessel in contact with thin sheet lead to a temperature of from 40° to 50° in order to precipitate silver and copper The filtrate is then poured into pure, very dilute sulphuric acid, and the lead sulphate formed carefully washed with a solution of ammonium carbonate and ammonia, and thus converted into lead carbonate A portion of this is then converted into lead oxide by carefully heating in a platinum basin, whilst to the remaining portion pure dilute nitric acid is added in such quantity that a portion of the carbonate remains undissolved The oxide of lead is then added to the boiling solution of the nitrate in order to precipitate traces of iron, and the filtered solution poured into one of pure ammonium carbonate The

[1] Imperial Mineral Resources Bureau, Statistical Summary, 1921
[2] *Bull Acad toy Belg*, 1860, 10, 205

precipitated lead carbonate is then reduced by means of potassium cyanide, and the metal thus formed fused a second time with the cyanide, when it assumes in the molten state a convex surface like mercury

Lead, purified by Stas's method, has been distilled in a vacuum at about 1200° in quartz vessels by Lambert and Cullis[1], before the admission of air it has a brilliant metallic lustre

Properties and Uses of Lead —Cohen and others have shown that lead probably exists in two allotropic forms, this has been confirmed by Janecke, who finds a transition point at about 60° by the study of temperature-pressure curves [2]

Lead can easily be crystallised in the form of regular octahedra by melting, allowing the molten metal partially to solidify, and pouring off the portion which is still liquid Similar crystals are obtained by the electrolytic decomposition of solutions of lead salts, using a strong current, but with weak cunents plates belonging probably to the monoclmic system are formed It is also deposited at the cathode by the electrolysis of dilute sulphuric acid with lead electrodes, sometimes in the spongy form consisting of microscopic needles, and sometimes in plates [3] Similar crystals to these separate out in bright, shining, arborescent forms, known as the lead tree, if a piece of zinc be hung up in a solution of lead acetate Lead has a specific gravity of 11 254, or, after it has been poured into water, of 11 363 On hammering it cracks and becomes lighter, but if it be pressed it attains a specific gravity of 11 388 Richards and Wadsworth found that lead, purified by recrystallisation of the acetate and the chloride, prepared by electrolysis and fused in pure charcoal vessels in an atinosphere of hydrogen, has a density of 11 337 at 20° [4] Its atomic heat is 3 06 at — 250°, 4 48 at — 236°, and 5 70 at — 188° (Kamerlingh Onnes and Keesom[5]), at higher temperatures it increases more slowly and Dulong and Petit's law is obeyed Thus, at — 73° it is 6 13, at 0° 6 31, at 136° 6 61 Its average compressibility between 100 and 500 megabars is 0 000,002,2 (Richards and Stull) [6] It is soft and tough, may be cut with a knife, and leaves a streak upon

[1] *Journ Chem Soc,* 1915, **107,** 210
[2] *Zeit physihal Chem,* 1915, **90,** 313
[3] Elbs and Rixon, *Zeit Elektrochem* , 1903, 9, 265, Haber, *Zeit anorg Chem* , 1898, 16, 438 See also Hughes, *J Phys cal Chem* , 1922, 26, 316
[4] *J Amer Chem Soc,* 1916, 38, 221
[5] *Verilag K Akad Wetenschappen,* 1914, 23, 792
[6] *Pub Cam Inst,* **1907, 76**

paper It can easily be rolled out to thin foil, but it cannot be drawn out into fine wire The presence of antimony, zinc, bismuth, arsemc, and silver increases the bnttleness of lead Lead belongs to the class of white metals, though it has a decidedly bluish-grey tint indicated by the expression lead-grey A freshly cut surface possesses a bright lustre, which, however, soon becomes dull from superficial oxidation By the electrolysis of lead nitrate Wohler obtained a deposit on the negative pole of crystallised leaflets of lead possessing a red colour like that of copper These did not dissolve in dilute acids, whilst they were soluble in hot nitric acid, and, on dissolving, the colour resembled that of copper to the last moment[1] Lead melts at 327°, and boils under atinospheric pressure at about 1525° (Greenwood)[2] Its vapour density has been measured at 1870° by von Wartenberg ,[3] its molecular weight has been measured by the depression of freezing-point method in mercury solution by Kamsay[4] from both results it is found to be monatomic

Lead has been obtained in the colloidal form by reducing a solution of the dichlonde with hydrazine hydrate in the cold[5]

Metallic lead is largely employed in the arts for a great variety of purposes on account of its softness and pliability, its low melting point, the difficulty with which it undergoes oxidation at ordinary temperatures, and the fact that it withstands the action of water and of many acids better than most of the common metals

The most important alloys of lead are those which it forms with tin, which have been described under that metal (p 880)

COMPOUNDS OF LEAD

LEAD AND OXYGEN

405 Lead forms five compounds with oxygen

Lead suboxide, Pb_20,
Lead monoxide, PbO,
Lead sesquioxide, Pb_20_3,
Red lead, Pb_30_4,
Lead dioxide, $Pb0_2$.

[1] *Ann Chem Pharm Suppl,* 1863, 2, 135
[2] *Proc Roy Soc* , 1909, **82,** *[A],* 1580
[3] *Zert anorg Chem,* **1908,** 56, **320**
[4] *Zert physikal Chem,* **1889,** 3, 359
[5] Gutbxer, *Zett anorg Chem,* **1902, 31, 448.**

The most important of these is the strongly basic monoxide, which corresponds of the chief series of salts, in which lead is divalent The dioxide acts as a weak basic oxide towards strong acids, as an acidic oxide to strong bases, and also behaves in many respects as a peroxide The sesquioxide and red lead are probably salts formed by the combination of the basic monoxide and the acidic dioxide (p 918)

Lead Monoxide, PbO —This compound was known to the ancients, as it is formed when lead is heated in contact with the air, and is, therefore, produced in various metallurgical processes The different forms of this compound were, however, regarded as different substances, giving rise to the names *plumbum ustum, scoria plumbi, scoria argenti, galena, XiOdpyvpos,* etc When lead is heated to its point of volatilisation in the air, it takes fire and burns with a white light, yielding this oxide, which formerly received the name of flowers of lead or *flores plumbi* Lead, when heated in the air, becomes covered with a grey film, and if the surface be continually renewed, becomes wholly converted into lead-ash, a yellowish-grey, pulverulent mixture of metallic lead and yellow monoxide, which, if heated in the air for a longer time, is wholly converted into the latter This yellow oxide is termed *massicot,* whilst the other form of lead monoxide, termed *litharge,* is obtained at a temperature at which the oxide fuses, solidifying to a scaly, shining mass sometimes yellowish, sometimes inclined to red

Crystallised oxide of lead also occurs in nature as a mineral found near Vera Cruz (Noggerath) The crystals may be artificially obtained by allowing litharge to cool slowly, it forms rhombic octahedra, which are sometimes also found as a deposit in the lead furnaces (Mitscherlich), and red, tetragonal crystals may also be obtained (Geuther) Lead oxide possesses a colour varying from lemon-yellow to reddish-yellow, and on heating assumes a brownish-red tint Its specific gravity at 4° is 9 36 (Joule and Playfair) It is reduced to the metallic state by carbonic oxide at 100°, by hydrogen at 310°, and by carbon[1] in an atinosphere of nitrogen at 550° Litharge is largely used in the arts, especially for the manufacture of flint glass, and as a glaze for earthenware, it is used also for the preparation of red lead, lead acetate, lead nitrate, white lead, lead plaster, and drying oils Commercial litharge contains carbon dioxide and water absorbed from the air, but they may be removed by

[1] Doeltz and Graumann, *Metallurgie,* 1907, 4, 420

ignition Not infrequently it contains small quantities of iron oxide and copper oxide, the latter easily removable by ammoma

Basic Lead Hydroxide, $Pb_2O(OH)_2$—This substance is obtained as a white precipitate by the action of air and water free from carbonic acid upon the metal, or is thrown down as a white precipitate on the addition of ammonia or a fixed alkali to a lead salt, this, however, dissolves in a large excess of the reagent and the solution contains a *plumhte,* H PbO OR, in which the normal hydroxide acts as a weak monobasic acid * The basic hydroxide is obtained in colourless, tetragonal crystals by exposing a cold solution of lead monoxide in caustic potash to the air, the carbon dioxide in the latter converting the caustic potash into potassium carbonate

The compound $Pb_3O_2(OH)_2$ is formed according to Payen as follows —100 parts of a solution of basic acetate of lead, $Pb_30_2(C_2H_30_2)_2$, saturated at 16°, are added to 50 volumes of cold water which has previously been well boiled a mixture of 20 parts of ammonia and 30 parts of boiled water is then added, and the solution allowed to stand at 25-30°, when the above hydroxide separates out in glittering octahedra

At 130° lead hydroxide loses a portion, and at 145° the whole, of its water, being then converted into lead oxide The hydroxides of lead as well as the oxide turn moistened red litinus paper blue, as they are somewhat soluble in water They act as strong bases but also combine with certain basic oxides Thus when lead oxide is fused with the alkalis, alkaline earths, and other metallic oxides, a glass is formed, and, in consequence of this, lead oxide attacks clay crucibles It dissolves also in caustic potash and soda as well as in lime and baryta water, yielding yellow liquids The calcium compound is slightly soluble in water, and crystallises in white needles on cooling

Lead Suboxide, Pb_2O, is formed when lead oxalate is heated in an atinosphere free from oxygen to a temperature below 300° (Dulong)

$$2PbC_20_4 = Pb_20 + CO + 3C0_2,$$

or when lead oxide is reduced by CO at 300° [2] It is a black, velvety powder of specific gravity 8 342 at 18° (Tammann),[3] which, when heated in absence of air, or treated with caustic

[1] Hantzsch, *Zert anorg Chem,* **1902, 30, 289**
[2] **Brislee,** *Journ Chem Soc ,* **1908, 93, 164**
[3] ***Zert anorg*** *'Chem,* **1901, 27, 304**

soda or acids, is decomposed into the metal and the monoxide When lead is melted in the air the surface becomes covered first with a grey film, which, according to Berzelms, consists of the suboxide The suboxide has by some been considered to be an intimate mixture of finely-divided lead and the monoxide Against this view, however, is to be placed the fact that mercury does not dissolve metallic lead from this grey powder, whilst a solution of sugar, which readily dissolves lead monoxide, does not take up any from this substance After heating, dilute acetic acid or a solution of sugar does dissolve out lead oxide, whilst metallic lead remains behind in the coherent state Cold 10 per cent sodium hydroxide decomposes it, forming sodium plumbite and metallic lead

A whole series of monovalent lead salts has recently been described by Denham [1] By the action of methyl iodide, bromide, and chloride on the suboxide, the corresponding subhalide, Pbl, PbBr, or PbCl was obtained They are sparingly soluble The subacetate, $PbC_2H_30_2$, and the subsulphate, Pb_2S0_4, are produced by the action of acetic anhydride and methyl sulphate on the suboxide

Lead Sesqmoxide, Pb_2O_3, is formed when a solution of sodium hypochlorite is carefully added to a cold caustic potash solution of lead oxide (Wmkelblech), or when a solution of red lead in acetic acid is precipitated by very dilute ammonia The action of potassium plumbite on potassium plumbate produces a precipitate of hydrated lead sesquioxide of composition $Pb_2O_3,3H_20$ or $Pb[Pb(OH)_6]$ [2] It is a reddish-yellow, amorphous powder which does not part with the whole of its water at 150° It is decomposed by acids into the monoxide and dioxide, and is, therefore, considered to be a compound of these two, $PbO,Pb0_2$, and may be termed *lead metaplumbate*

Red Lead or *Minium,* Pb_3O_4 —This compound was described by Pliny, under the name of *minium,* but it was at that time not sufficiently distinguished from cinnabar and the red sulphide of arsenic Dioscondes, however, mentions that it can be prepared from white lead " *cerussa, si coquatur rufescit* ", and Geber says " *plumbum aduntur et Jit minium* "

Eed lead is usually prepared by carefully heating very finely-divided pure massicot or white lead For this purpose the oxide is heated for about twenty-four hours either on the flat hearth

[1] ***Journ Chem Soc*** **, 1917, 111, 29, 1918,113, 249, 1919,115, 109**
[2] **Bellucci and Parravano,** ***Zat anorg Chem,*** **1906, 60, 107**

of a reverberatory furnace, or in .barrel-shaped vessels open at both ends, the mass bfemg frequently stirred and the heat not allowed to rise above dull redness (about 400°) The brightness and beauty of the colour depend much on the care spent on the roasting, as these properties are influenced especially by the particular molecular condition of the material, and this is produced only at a given temperature

Red lead is a scarlet, crystalline, granular powder, which, on heating, first assumes a finer red colour and afterwards turns violet, and lastly black, but on cooling regains its original tint When more strongly heated, at about 470^0,[1] it loses oxygen and is converted into the monoxide Its specific gravity varies from 8 6 to 9 1 Commercial red lead frequently contains the yellow oxide, litharge, mixed with it, which may be extracted by repeatedly digesting with a solution of lead acetate Red lead is largely used as a pamt and also in the preparation of flint glass For both these purposes it is necessary that it should be as free as possible from iron, and in this case it is not infrequently prepared from white lead Red lead is also adulterated with oxide of iron, red bole, powdered heavy spar, and brick dust These substances remain undissolved when red lead is digested in warm dilute nitric acid to which a little sugar has been added, whilst the red lead is dissolved completely Boiling hydrochloric acid extracts sesquioxide of iron from the impure oxide with formation of lead chloride and liberation of chlorine Like the sesquioxide, it is decomposed by acids into the monoxide or a corresponding salt, and the dioxide, and is therefore regarded as a compound of two molecules of the former and one of the latter, $2PbO,PbO_2$, and may be termed *lead orthoplumbate*

Lead Dioxide, Lead Peroxide, or *Puce-coloured Oxide of Lead,* PbO_2 —This substance was discovered by Scheele, who observed that red lead is coloured brown when treated with chlorine water, whilst Priestley found that nitric acid produces the same reaction The properties of the puce-coloured lead oxide were more exactly examined by Proust and Vauquelm

Lead dioxide may be prepared according to a variety of methods The simplest plan is to act upon red lead with dilute nitric acid

$$Pb_3O_4 + 4HNO_3 = PbO_2 + 2Pb(NO_3)_2 + 2H_2O$$

[1] **Milbauer,** ***Chem Zeit,*** **1909, 33, 950, 960**

It is likewise obtained by the action of chlorine upon lead salts in the presence of alkalis (Wohler), or by treating a hot solution of a pure lead salt with a soluble hypochlorite (Bottger)

$$PbO + NaClO \overset{c}{=} PbO_2 + NaCl$$

It is also prepared by the electrolysis of a solution of sodium chloride, in which litharge is suspended [1]

It is obtained in the dry way by fusing 4 parts of lead monoxide, 1 part of potassium chlorate, and 8 parts of nitre (Liebig and Wohler) Lead oxide is also converted into the dioxide by the action of ozone as well as of hydrogen peroxide It is deposited at the positive pole when a solution of a lead salt in nitric acid is decomposed electrolytically [2]

This substance is found native in the form of plattnente, which crystallises in black, hexagonal prisms having a specific gravity of 9 4 The artificial dioxide sometimes assumes the form of brownish-black, six-sided tablets, but generally consists of a dark brown powder having a specific gravity of 8 9 to 9 2

Lead dioxide decomposes on heating into oxygen and the monoxide It loses oxygen when simply exposed to sunlight, red lead being formed It has a strongly oxidising action, and when triturated with one-sixth of its weight of sulphur, it takes fire and burns with a brilliant flame, forming sulphide of lead [3] Aqueous hypophosphorous acid is at once oxidised with formation of lead phosphate When exposed to sulphur dioxide at ordinary temperatures it becomes red hot and is converted into lead sulphate, whilst mtrogen peroxide and even ammonia convert it into lead nitrate A large number of organic acids and other carbon compounds when triturated with it likewise cause evolution of light and heat When treated with hydrochloric acid, chloride of lead and free chlorine are formed

Lead dioxide is often employed as an oxidising agent, as, for instance, in the analysis of organic substances containing sulphur, in order to separate the sulphur dioxide from carbon dioxide The mixture of nitrate and dioxide, termed oxidised red lead, obtained by treating red lead with nitric acid, is employed in the manufacture of lucifer matches

Lead dioxide is capable of acting as a weak basic oxide,

[1] *Chemische Fabrik, Grtesheim Electron,* German Patent, 124512

[2] Wolman, *Zat Elektrochem,* 1897, 3, 637, Hollard, *Compt rend,* 1903, **136,** 229, and others

[3] Vauquelin, *Ann Chim Phys,* 1807, 62, 221

yielding the unstable tetravalent lead salts, and also as a peroxide and an acid-forming oxide, forming compounds to which the name *plumbaTes* has been given *Orthoplumbates* having the composition $M^{I}_4PbO_4$ and *metaplumbates,* $M^{I}_2PbO_3$, are known,[1] and the free *metaplumbic acid,* $PbO(OH)_2$ or H_2PbO_3, is deposited at the positive pole as a black, lustrous substance on the electrolysis of a slightly alkaline solution of lead sodium tartrate

The orthoplumbates of the alkaline earths are obtained by heating the carbonates or hydroxides with lead monoxide in presence of air, the *calcium* salt, Ca_2PbO_4, crystallising with four molecules of water in almost colourless, microscopic, transparent crystals These compounds evolve oxygen on strongly heating, and it has been proposed to utilise this method for obtaining oxygen from the atinosphere on the large scale, the calcium salt has also been used as an oxidising agent[2]

The hydrosol of hydrated lead peroxide (plumbic acid) has been prepared by the dialysis of potassium plumbate [3]

Potassium Metaplumbate, $K_2PbO_3,3H_2O$, is obtained in crystals by fusing lead dioxide with excess of caustic potash in a silver crucible, dissolving in water, and evaporating in a vacuum[4] The solution gives with most metallic salts precipitates of the corresponding metaplumbates

Calcium Metaplumbate, $CaPbO_3,4H_2O$, is obtained by digesting the orthoplumbate with sodium peroxide and water, and from this other metaplumbates have been obtained [5]

As already mentioned, lead sesquioxide and red lead may be regarded as the metaplumbate and orthoplumbate of lead, their constitution being represented by the formulae $Pb^{11}PbO_3$ and $Pb_2{}^{11}PbO_4$ Lead metaplumbate has been prepared from the calcium salt and is identical with the sesquioxide [6]

When calcium meta- or ortho-plumbate is heated in dry air at 250°, *calcium perplumbate,* $CaPb_2O_6$, is formed[7]

[1] Compare Bellucci, *Atti R Accad Lmcei,* 1905, [5], 14, I , 457
[2] Kassner, *Arch Pharm* , 1890, **228,** 109, 1894, **232,** 375, 1895, **233,** 501
[3] Bellucci and Parravano, *Atti B Accad* Lincu, 1906, [5], 15, n, 542
[4] *Ann Chim Phys,* 1844, [3], 12, 490
[5] Grutzner and Hohnel, *Arch Pharm,* 1895, **233,** 512
[6] Hohnel, *Arch Pharm* , 1895, **233,** 501
[7] Kassner, *Arch Pharm,* 1899, **237,** 409, 1900, **238,** 449

then dissolved in water and mixed with lime-water in certain definite proportions, a snow-white precipitate having the composition given above is thrown down, which was at one time used as a paint in place of white lead

A hydrated oxychlonde is likewise obtained by warming lead oxide with a solution of common salt (Scheele), caustic soda being produced at the same time In the year 1787 Turner took out a patent for the purpose of preparing caustic soda by the reaction, and found that the residue when heated became anhydrous and possessed a yellow colour This oxychlonde is known under the name of *Turner's yellow* or *patent yellow* Vauquelin then showed that when lead chloride and lead oxide are fused together, a yellow-coloured body is obtained This is known as *Cassel yellow,* and is prepared by fusing together 1 part of ammonium chloride and about 10 parts of massicot, minium, or white lead, a part of the ammonium chloride sublimes undecomposed, and the resulting compound contains about one molecule of chloride to seven molecules of oxide, part of the lead being at the same time reduced by the ammonia

Lead chloride also yields a number of double salts with the chlorides of other metals

Lead Tetrachloride, $PbCl_4$—A solution of this compound is obtained by dissolving the dioxide in well-cooled hydrochloric acid, but it is best prepared by passing chlorine into lead dichlonde suspended in hydrochloric acid On addition of ammomum chloride, *ammonium plumbichloride,* $(NH_4)_2PbCl_6$, crystallises out, and the same compound is also formed by acting on lead tetracetate with concentrated hydiochlonc acid and then adding ammonium chloride [1] It may also be obtained by the action of hydrochloric acid and ammonium persulphate on lead chloride in the cold,[2] or by the electrolysis of concentrated hydrochloric acid with lead electrodes, the cathode being placed in a porous pot, when an orange solution of H_2PbCl_6 is formed, and this on addition of ammonia yields the above compound[3] When this compound is added to well-cooled sulphuric acid, it yields the tetrachloride, as a yellow, refractive, fuming liquid, which readily decomposes into the dichlonde and chlorine It has a specific gravity of 3 18 at 0°, solidifies at —15° to a yellowish, crystalline mass, and yields a hydrate with

[1] Hutchinson and Pollard, *Journ Chem Soc* , 1896, 69, 212
[2] Seyewetz and Trawitz, *Compt rend* , 1903,**136,** 686
[3] Elba and Nubling, *Zeit Elektrochem,* 1903, 9, 776

responding lead compound was termed horn-lead *(plumbum corneum)* Lead chloride occurs native in the craters of volcanoes as the mineral cotunmte Lead combines with chlorine, but slowly, and without incandescence Dilute hydrochloric acid dissolves the metal only in the presence of air, and then but slowly The boiling concentrated acid, however, converts it into chloride with evolution of hydrogen gas Lead chloride is easily prepared by the action of hydrochloric acid on the oxide or carbonate, and also by the precipitation of a tolerably concentrated solution of a lead salt by means of hydrochloric acid or a soluble chloride It is thus obtained in the form of a white, crystalline precipitate, of which 100 parts of water dissolve 0 909 part at 15°, and 3 2 parts at 100° The salt crystallises, when a boiling solution is cooled, in white, silky, rhombic needles, having a specific gravity of 5 8 It is less soluble in dilute hydrochloric acid and solutions of chlorides than in pure water, but dissolves more freely in concentiated hydiochlonc acid, hence a precipitate may be obtained by adding water to the latter solution, whilst the aqueous solution is precipitated by hydrochloric acid It also dissolves readily in the solutions of the acetates and thiosulphates of the alkali metals When heated in absence of air, lead chloride melts at about 485°, solidifying on cooling to a white, translucent, horny mass, it volatilises at a temperature of 861-934°, the vapour having a density of 5 8, corresponding to the formula $PbCl_2$[1]

Lead yields a large number of oxychlondes The compound $PbCl_2$,PbO occurs as the mineral matlockite, and may be obtained artificially by igniting the chlonde in the air till no further fumes are evolved The mineral mendipite has the composition $PbCl_2$,2PbO, and numerous others, some of which contain water of crystallisation, have been prepared Ruer[2] has examined the freezing points of mixtures of lead oxide and lead chloride, and has obtained evidence of the existence of the compounds, $PbCl_2$,PbO, $PbCl_2$,2PbO, and $PbCl_2$,4PbO The hydrate $PbCl_2$,PbO,H_2O, which may also be formulated as lead hydroxychlonde, Pb(OH)Cl, and occurs as the mineral launonite, was formerly prepared by a process patented by Pattinson in 1849 In this process chloride of lead is first prepared from finely pulverised galena and concentrated hydrochloric acid, this is

[1] Roscoe, *Proc Roy Soc* , 1878, 27, 428
[2] *Zert anorg Chem*, 1906, 49, 365

then dissolved in water and mixed with lime-water in certain definite proportions, a snow-white precipitate having the composition given above is thrown down, which was at one time used as a paint in place of white lead

A hydrated oxychlonde is likewise obtained by warming lead oxide with a solution of common salt (Scheele), caustic soda being produced at the same time In the year 1787 Turner took out a patent for the purpose of preparing caustic soda by the reaction, and found that the residue when heated became anhydrous and possessed a yellow colour This oxychlonde is known under the name of *Turner's yellow* or *patent yellow* Vauquelm then showed that when lead chloride and lead oxide are fused together, a yellow-coloured body is obtained This is known as *Cassel yellow,* and is prepared by fusing together 1 part of ammonium chloride and about 10 parts of massicot, minium, or white lead, a part of the ammonium chloride sublimes undecomposed, and the resulting compound contains about one molecule of chloride to seven molecules of oxide, part of the lead being at the same time reduced by the ammonia

Lead chloride also yields a number of double salts with the chlorides of other metals

Lead Tetrachloride, $PbCl_4$—A solution of this compound is obtained by dissolving the dioxide in well-cooled hydrochloric acid, but it is best prepared by passing chlorine into lead dichlonde suspended in hydrochloric acid On addition of ammomum chloride, *ammonium plumbichloride,* $(NH_4)_2PbCl_6$, crystallises out, and the same compound is also formed by acting on lead tetracetate with concentrated hydiochlonc acid and then adding ammonium chlonde [1] It may also be obtained by the action of hydrochloric acid and ammonium persulphate on lead chloride in the cold,[2] or by the electrolysis of concentrated hydrochloric acid with lead electrodes, the cathode being placed in a porous pot, when an orange solution of H_2PbCl_6 is formed, and this on addition of ammonia yields the above compound[3] When this compound is added to well-cooled sulphuric acid, it yields the tetrachloride, as a yellow, refractive, fuming liquid, which readily decomposes into the dichlonde and chlorine It has a specific gravity of 3 18 at 0°, solidifies at —15° to a yellowish, crystalline mass, and yields a hydrate with

[1] Hutchinson and Pollard, *Journ Chem Soc* , 1896, **69,** 212
[2] Seyewetz and Trawitz, *Compt rend* , 1903,**136,** 686
[3] Elba and Nubling, *Zeit Elektrochem,* 1903, 9, 776

a small quantity of water, but in presence of an excess is decomposed into lead dioxide and hydrochloric acid[1]

Lead Bromide, $PbBr_2$ —This compound closely resembles the chloride It is obtained by treating lead oxide with aqueous hydrobromic acid, or by precipitating a lead salt with a solution of potassium bromide, when it is thrown down in the form of white, shining needles It dissolves in hot water, and has a specific gravity of 6 6 When heated in a closed vessel it fuses, forming a red liquid which on cooling solidifies to a white, horny mass Fused in contact with the air, it emits white fumes and leaves a residue of *oxybromide,* $PbBr_2,PbO$, forming a pearly, yellow mass, whilst the *hydrated oxybromide,* $PbBr_2,PbO,H_20$ or PbBrOH, has been prepared by heating a mixture of solutions of sodium bromide and lead acetate [2]

Lead Iodide, Pbl_2—Hydnodic acid easily dissolves lead, and the iodide separates out from a concentrated solution in beautiful yellow crystals (Deville) When a solution of lead salt is mixed with a soluble iodide, a yellow precipitate of lead iodide is formed This is soluble in 1,235 parts of cold and 194 parts of boiling water, giving rise to a colourless solution from which the iodide separates out on cooling in yellow laminae resembling those of mosaic gold The specific gravity of this compound is 6 1, on heating, it becomes i eddish-yellow, then bright red, and lastly brownish-black, it melts in a closed tube to a reddish-brown liquid which solidifies to a yellow, crystalline mass, and may be sublimed unchanged by heating in carbon dioxide[3] Like the chloride and bromide, it forms basic salts

A number of mixed halogen compounds of lead have been described, which are mostly prepared by the action of the halogen salts of potassium or ammonium on those of lead In this way the compounds PbFBr, PblCl, and PbBrCl are stated to be formed, as well as double compounds of these with the halogen salts of ammoma [4] There is, however, some doubt as to whether these are true compounds or isomorphous mixtures [5]

[1] Friednch, *Monatsh,* 1893, 14, 505, Classen, *Zed anorg Chem,* 1893, 4, 100

[2] de Schulten, *Bull Soc franc Min* , 1897, 20, 186

[3] Schtscherbakoff, *J Russ Phys Chem Soc,* 1905, 37, 682

[4] Thomas, *Compt rend,* 1898, **126,** 1349, 1899, **128,** 1234, 1329, *Bull Soc c h i m* , 1898, [3], 19, 598, Fonzes Diacon, i*bid* , 1897, [3], 17, 346

[5] Herty and Bogg, *J Amer Chem Soc* , 1897,19, 820

then dissolved in water and mixed with lime-water in certain definite proportions, a snow-white precipitate having the composition given above is thrown down, which was at one time used as a paint in place of white lead

A hydrated oxychlonde is likewise obtained by warming lead oxide with a solution of common salt (Scheele), caustic soda being produced at the same time In the year 1787 Turner took out a patent for the purpose of preparing caustic soda by the reaction, and found that the residue when heated became anhydrous and possessed a yellow colour This oxychlonde is known under the name of *Turner's yellow* or *patent yellow* Vauquehn then showed that when lead chloride and lead oxide are fused together, a yellow-coloured body is obtained This is known as *Cassel yellow,* and is prepared by fusing together 1 part of ammonium chloride and about 10 parts of massicot, minium, or white lead, a part of the ammonium chloride sublimes undecomposed, and the resulting compound contains about one molecule of chloride to seven molecules of oxide, part of the lead being at the same time reduced by the ammonia

Lead chloride also yields a number of double salts with the chlorides of other metals

Lead Tetrachloride, $PbCl_4$—A solution of this compound is obtained by dissolving the dioxide in well-cooled hydrochloric acid, but it is best prepared by passing chlorine into lead dichlonde suspended in hydrochloric acid On addition of ammonium chloride, *ammonium plumhchlonde,* $(NH_4)_2PbCl_6$, crystallises out, and the same compound is also formed by acting on lead tetracetate with concentrated hydrochloric acid and then adding ammonium chloride [1] It may also be obtained by the action of hydrochloric acid and ammonium persulphate on lead chloride in the cold,[2] or by the electrolysis of concentrated hydrochloric acid with lead electrodes, the cathode being placed in a porous pot, when an orange solution of H_2PbCl_6 is formed, and this on addition of ammonia yields the above compound[3] When this compound is added to well-cooled sulphuric acid, it yields the tetrachloride, as a yellow, refractive, fuming liquid, which readily decomposes into the dichloride and chlorme It has a specific gravity of 3 18 at 0°, solidifies at —15° to a yellowish, crystalline mass, and yields a hydrate with

[1] Hutchinson and Pollard, *Journ Chem Soc* , 1896, **69, 212**
[2] Seyewetz and Trawitz, *Compt rend* , 1903,**136,** 686
[3] Elba and Nubling, *Zeit Elektrochem* , **1903, 9, 776**

a small quantity of water, but in presence of an excess is decomposed into lead dioxide and hydrochloric acid[1]

Lead Bromide, $PbBr_2$ —This compound closely resembles the chloride It is obtained by treating lead oxide with aqueous hydrobromic acid, or by precipitating a lead salt with a solution of potassium bromide, when it is thrown down in the form of white, shining needles It dissolves in hot water, and has a specific gravity of 6 6 When heated in a closed vessel it fuses, forming a red liquid which on cooling solidifies to a white, horny mass Fused in contact with the air, it emits white fumes and leaves a residue of *oxybromzde,* $PbBr_2$,PbO, forming a pearly, yellow mass, whilst the *hydrated oxybromide,* $PbBr_2$,PbO,H_20 or PbBrOH, has been prepared by heating a mixture of solutions of sodium bromide and lead acetate [2]

Lead Iodide, Pbl_2 —Hydnodic acid easily dissolves lead, and the iodide separates out from a concentrated solution in beautiful yellow crystals (Deville) When a solution of lead salt is mixed with a soluble iodide, a yellow precipitate of lead iodide is formed This is soluble in 1,235 parts of cold and 194 parts of boiling water, giving rise to a colourless solution from which the iodide separates out on cooling in yellow laminae resembling those of mosaic gold The specific gravity of this compound is 6 1, on heating, it becomes reddish-yellow, then bright red, and lastly brownish-black, it melts in a closed tube to a reddish-brown liquid which solidifies to a yellow, crystalline mass, and may be sublimed unchanged by heating in carbon dioxide[3] Like the chloride and bromide, it forms basic salts

A number of mixed halogen compounds of lead have been described, which are mostly prepared by the action of the halogen salts of potassium or ammonium on those of lead In this way the compounds PbFBr, PblCl, and PbBrCl are stated to be formed, as well as double compounds of these with the halogen salts of ammonia [4] There is, however, some doubt as to whether these are true compounds or isomorphous mixtures [5]

[1] Fnednch, *Monatsh,* 1893, 14, 505, Classen, *Zett anorg Chem,* 1893, 4, 100

[2] de Schulten, *Bull Soc franc Min ,* 1897, 20, 186

[3] Schtscherbakoff, *J Buss Phys Chem Soc,* 1905, 37, 682

[4] Thomas, *Compt rend,* 1898, **126,** 1349, 1899, **128,** 1234, 1329, *Bull Soc chim,* 1898, [3], 19, 598, Fonzes Diacon, *ibid,* 1897, [3], 17, 346

[5] Herty and Bogg, *J Amer Chem Soc ,* 1897,19, 820

LEAD AND SULPHUR

407 *Lead Sulphide*, PbS, occurs in nature as galena, crystallised in cubes or sesses a bluish-grey colour, and has a specific gravity varying from 7 25 to 7 7 This mineral was known to the ancients under its present name, but the fact that it contained sulplmr was not recogmsed until after some time Thus even Kunkel was unacquainted with this fact, though Boyle [1] was aware that when galena is heated with scrap iron metallic lead is formed, and recommended this mode of producing lead

When sulphur vapour is led over metallic lead it takes fire and burns, forming a crystalline sulphide, even tolerably thick strips of lead take fire in sulphur vapour, depositing half-fused globules of lead sulphide It can also be prepared by fusing lead oxide with an excess of sulphur When sulphuretted hydrogen is passed into a solution of lead nitrate, an amorphous, black piecipitate is formed, but if the gas be passed into a dilute solution of the salt contaimng nitric acid a crystalline precipitate is obtained, consisting of microscopic cubes (Muck)

Sulphide of lead fuses at a strong red heat—at 1120° + 10° according to Fnednch [2]—and when heated in a current of many gases sublimes in cubes which often have a diameter of 1 5 mm Crystals of galena are often obtained in lead works in a similar way On the other hand, octahedral crystals may be obtained by fusing 1 part of the precipitated sulphide with 6 parts of potash and 6 parts of sulphur (Schneider) Nitric acid converts galena, with separation of sulphur, partly into the nitrate and partly into the sulphate, the latter compound being formed in the largest quantity when the acid is strongest Hot concentrated hydrochloric acid dissolves it with evolution of sulphuretted hydrogen

When an aqueous solution of a lead salt containing an excess of hydrochloric acid is treated with a small quantity of sulphuretted hydrogen a yellowish- to dark-red precipitate is obtained which consists of a double chloride and sulphide of lead According to Hunenfeld,[3] this precipitate has the composition $3PbS,2PbCl_2$, whilst Parmentier[4] found the composition $PbS,PbCl_2$, it is converted by an excess of sulphuretted hydrogen

[1] ***A hydrostatical way of estimating ores of leal***
[2] ***Metallurgre* 1907, 4, 479, 1908, 5, 23**
[3] ***J pr Chem*, 1836, 7, 27** *** *Compt rend*, 1892, 114, 299**

into lead sulphide, and loses lead chloride on treatment with hot water The compound $PbS,4PbCl_2$ has been obtained by diluting a solution of lead sulphide in concentrated hydrochloric acid, whilst similar compounds with lead bromide and iodide have also been prepared [1]

A polysulphide of lead, PbS_5, is formed by the action of calcium polysulphide on lead nitrate at 0°, as a purplish-red precipitate which decomposes rapidly at ordinary temperatures into the monosulphide and sulphur [2]

Lead Sulphate, $PbS0_4$—This substance is found native as lead vitriol or anglesite in transparent, rhombic crystals, ISOmorphous with those of celestine and heavy-spar, or as pseudomorphs of galena It is obtained as a white powder by precipitating a lead salt with sulphuric acid or a soluble sulphate If a layer of water be poured on to a saturated solution of potassium sulphate, and a platinum wire on which some lead chloride has been fused allowed to dip into the water, crystals of lead sulphate are gradually formed [3] It may also be formed by the action of sulphur dioxide on lead peroxide [4] Lead sulphate has a specific gravity of 6 2 to 6 3 It melts at about 1100° without decomposition One part of the salt dissolves in 21,739 parts of cold water, 12,135 parts according to Schnal,[5] and in 36,504 parts of dilute sulphuric acid, whilst concentrated sulphuric acid can take up about 6 per cent, of the compound It also dissolves

in warm ar

acid with formation of lead chloride Sulphate of lead is likewise very readily soluble in ammoniacal salts, especially in the acetate, calcium acetate and many other salts also dissolve it

When lead sulphate is boiled with concentrated sulphuric acid, it is dissolved and is afterwards deposited in crystals, and if the mother-liquor be allowed to stand in contact with moist air crystals of the acid sulphate, $PbSO_4,H_2SO_4,H_2O$, similar to those of the corresponding barium salt, are formed

When the normal salt is treated with ammonia the basic sulphate, Pb_2SO_5 or $O<pi\ Q>SO_2$, is formed The same salt is obtained in microscopic needles when an excess of a hot solution of sodium sulphate is added to basic lead formate (Barfoed)

[1] Lenher, *J Amer Chem Soc* , 1895,17, 511, 1901, 23, 680
[2] Bodroux, *Compt rend,* 1900, **130,** 1397
[3] Manross, *Annalen,* 1852, 82, 300
[4] Marino, *Zert anorg Chem* , 1907, 66, 233
[5] *Compt rend,* 1909,**148,** 1394

The basic sulphates, $PbSO_4,2PbO$ and $PbSO_4,3PbO$, also exist[1]

Lead Persulphate, $Pb(SO_4)_2$, is obtained at the anode as a greenish-yellow, crystalline precipitate when a solution of sulphuric acid is electrolysed below 30° with an anode of lead placed in a porous sulphuric acid and lead dioxide, and is a powerful oxidising agent[2]

Lead Subsulphate, Pb_2SO_4, has been prepared[3]

LEAD AND NITROGEN AND PHOSPHORUS

408 *Lead Imide,* PbNH, is obtained by the action of potassamide on lead iodide in liquid ammonia, and is a reddish-brown, explosive substance If the lead iodide be in excess, the white basic salt, NPb_2I,NH_3, is obtained Lead lmide reacts with potassamide in liquid ammonia at low temperatures to form potassium ammono-plumbite, $KNPb,2½NH_3$, which loses half a molecule of ammonia at — 40° to form the compound $KPb(NH_2)_3$ At 60°, a further molecule of ammoma is lost with the production of the explosive compound $KNPb,NH_3$ If these substances are treated with ammonium iodide in liquid ammoma the successive products are lead lmide, an ammonobasic lead iodide, $Pb_2(NH_2)_3I$, and lead iodide Lead lmide is an amphoteric electrolyte in liquid ammonia[4]

Lead Nitrite, $Pb(NO_2)_2$ —This substance is most readily obtained by decomposing silver nitnte with lead chloride and concentrating the solution in a vacuum, when yellow prisms separate out which are easily soluble in water On evaporating the solution, nitric oxide is evolved, and a basic salt remains behind If lead nitrate be digested with water in contact with finely-divided metallic lead for a few hours at a temperature of 75°, a yellow solution is formed, which on cooling deposits the basic double salt, $Pb(NO_3)OH,Pb(NO_2)OH$, in glittering yellow plates Proust, who first obtained this compound, considered it to be a nitrate of a suboxide of lead, whilst Berzelius viewed it as a simple basic nitrite If its solution be boiled with metallic lead and a large quantity of water, orange-yellow prisms separate out on cooling, having the composition $Pb(NO_2)_2,Pb(NO_3)_2,5PbO,3H_2O$ This salt was formerly termed

[1] **Schenck and Rassbach,** ***Ber,*** **1908, 41, 2917**

[2] **Elbs and Fischer,** ***Zext Elektrochem,*** **1900, 7, 343**

[3] **Denham,** ***Journ Chem Soc*** **, 1919, 115, 109**

[4] **Franklin,** ***J Amer Chem Soc*** **, 1905, 27, 820, and** ***J Physical Chem*** **, 1911, 15,509**

lead hypomtrate If lead nitrate be boiled with one and a half times its weight of lead and fifty times its weight of water for twelve hours in a long-necked flask, pale red needles of basic nitrite of lead, $Pb(NO_2)_2,3PbO,H_2O$, are formed Other basic nitrites of lead are known [1]

Lead Nitrate, $Pb(NO_3)_2$—Lead nitrate is first mentioned in the *Alchymia* of Libavius It is here termed *calx plumb dulcis* " Fit per aquam fortem commmuto plumbo affusam vase in aqua frigida locato Fit mstar crystallorum " Lead dissolves slowly in warm dilute nitric acid Lead nitrate, or lead saltpetre, as it is sometimes called, is prepared on the large scale by dissolving lead scale or litharge in hot dilute nitric acid, having a specific gravity of 1 35 The solution is evaporated until it attains a specific gravity of 1 6, and is then allowed to cool in earthenware vessels, when the salt separates out in milk-white, regular octahedra exhibiting a combination of the regular dodecahedron If a cold solution of the salt be allowed to undergo spontaneous evaporation, transparent octahedral crystals are formed (Knop) It has a specific gravity of 4 5, and on dissolving in water gives rise to a reduction of temperature, 100 paits of water dissolve, according to Mulder, as follows

At	0°	10°	20°	40°	60°	80°	100°
$Pb(NO_3)_2$	36 5	44 4	52 3	69 4	88 0	107 6	127 0

It scarcely dissolves in strong alcohol and is only slightly soluble in aqueous nitric acid It has an astringent, metallic taste, decrepitates when heated, detonates with brilliant sparks when thrown upon red-hot charcoal, and deflagrates when triturated with sulphur When heated in a sealed tube at 357°, it decomposes partially according to the equation [2]

$$Pb(NO_3)_2 \wedge PbO + O + 2NO_2$$

The salt is largely used in dyeing and calico-printing, for the preparation of mordants and of chrome-yellow

When the normal salt is boiled with an equal weight of lead oxide and water, crystals of a basic nitrate, $Pb(NO_3)OH$, are thrown down on cooling These are sparingly soluble in cold and more readily soluble in hot water When gently heated it is converted into red lead If a solution of the normal salt

[1] Compare Chitesotti, *Atti R Accad Lmcei,* 1908, [5], 17, u , 377 and 474

[2] Baekeland, *J Amer Chem Soc,* 1904, 26, 391, Morgan, *J Physical Chem,* 1904, 8, 416

be precipitated with a slight excess of ammonia, and the solution heated in a closed vessel with the addition of some of the normal salt until the smell of ammonia has almost disappeared, a basic nitrate is formed, having the composition $2Pb(NO_3)OH,PbO$ It is a white powder slightly soluble in water When an excess of ammoma is employed the compound $Pb(NO_3)OH,2PbO$ is thrown down as a white powder

Phosphates of Lead—When common sodium phosphate is precipitated by acetate of lead a white precipitate of normal lead orthophosphate, $Pb_3(P0_4)_2$, is formed If a boiling solution of lead nitrate be precipitated by phosphoric acid, a glittering white, crystalline precipitate of $HPbP0_4$ is produced, and the same compound is obtained in the form of crystalline needles when lead pyrophosphate is heated with water to 250° The pyrophosphate and metaphosphate of lead are white precipitates

The following minerals are lead phosphates and arsenates isomorphous with apatite

Pyromorphite, $Pb_3(PO_4)_2,Pb_2Cl(PO_4)$,
Polysphaente, $(Pb,Ca)_3(PO_4)_2,(Pb,Ca)_2Cl(PO_4)$,
Mimetite, $Pb_3(AsO_4)_2,Pb_2Cl(AsO_4)$,
Campylite, $Pb_3[(As,P)O_4]_2,Pb_2ClL(As,P)O_4]$

Some of the chlorine is usually replaced by fluorine

Borates of Lead — If boron tnoxide and lead oxide be fused together in the proportion of two molecules of the former to three of the latter, a yellowish soft glass is obtained, which softens when exposed to the action of hot oil If double the weight of boron trioxide be employed the glass obtained is harder and less coloured, and if three times the weight be used a colourless glass is obtained, which possesses the hardness of flint glass and refracts light much more powerfully[1] When a lead salt is precipitated with borax, a compound having the composition $Pb_2B_6O_{11},4H_2O$ is formed, and this when warmed with strong ammonia is converted into a heavy, white powder having the composition PbB_2O_4,H_2, which again, when boiled with a solution of boric acid, yields amorphous $PbB_4O_7,4H_2O$ [2]

LEAD AND CARBON AND SILICON

409 *Carbonates of Lead—Normal Lead Carbonate*, $PbCO_3$, occurs as cerussite or white carbonate of lead in rhombic crystals

[1] Faraday, " On the Manufacture of Optical Glass," *Phil Trans*, 1830, 120,1

[2] But see also, Thompson, *Trans Engl Ceram Soc* , 1918-19,18, 510

isomorphous with arasonite, and also as pseudomorphs of galena and lead sulphate The same compound is formed by precipitating a cold polution of lead acetate by ammonium carbonate (Berzelius), or by passing carbon dioxide into a dilute solution of lead acetate (Rose) Cerussite forms colourless, transparent, lustrous crystals, having a specific gravity of 6 46, whilst the precipitated carbonate has a specific gravity of 6 43 It is scarcely soluble in water, one part dissolving in 50,500 parts of water at the ordinary temperature, but in presence of ammomacal salts it is somewhat more soluble (Fresenius) A solution of carbon dioxide in water also dissolves it slowly

Lead forms several basic carbonates, among which *white lead* is the most important, since it is manufactured on a very large scale In the pure state this compound consists of $2PbCO_3,Pb(OH)_2$, but the commercial product usually contains the normal carbonate in addition

White Lead has long been known, being called *yfn/uvOiov* by Theophrastus The process of manufacture as described by him consisted in the action of vinegar on lead, the material formed being scraped off after a time from the surface of the metal Pliny mentions the same subject under the name of *cerussa* and describes the above method of manufacture He also states that it may be obtained by dissolving lead in vinegar and evaporating to dryness Thus it would appear that the difference between white lead and sugar of lead was not known The Latin Geber describes the manufacture as follows " plumbum ponendo super vaporem aceti fit cerussa," a description which accords with the method employed even up to the present day For some time white lead was supposed to be a compound of calx of lead with vinegar, and it was not until 1774 that Bergman showed that white lead contained lead calx and fixed air, and gave to it the name of " luftsaurer blei-kalk " or " calx plumbi serata "

The oldest process for the manufacture of white lead is known as the *Dutch process* In this method conical glazed earthenware pots, 8 inches wide, are filled to one-fourth of their depth with malt vinegar At one-third of the height of the pot from the bottom are three projecting points on which a cross-piece of wood is laid, and on this are placed vertically a number of thin leaden plates rolled up into a spiral, and the whole is covered with a leaden plate, which often has holes punched in it The pots are then placed under a shed in rows upon horse dung or spent tannery bark and covered with boards, another layer of dung

or decomposing bark is laid upon the boards, and on this another row of pots, many rows of pots being thus placed above one another, and the whole covered by the tan or dung By the slow oxidation of the dung heat is evolved, which assists the evaporation of the vinegar and causes basic lead acetate to be formed, and this in contact with the carbon dioxide evolved from the putrefaction of the organic matter is converted into white lead In the course of from four to five weeks the greater portion of the lead is converted into white lead, the change taking place from without inwards The white lead is then detached, ground into a fine paste whilst moist, washed well to free it from adhering acetate, and dried in small round pots Unwashed white lead contains a considerable quantity (from 2 to 12 per cent) of the normal acetate

To reduce the risk of poisomng attending the drying of the white lead pulp, formed by the treatment of the corroded lead with water, it is customary in some works to dry the pulp in ovens in which a vacuum is maintained A further improvement, applicable in the manufacture of paint, is that described by Ismay (English Patent 23969, 1895) in which the white lead pulp is mixed with oil in a pug mill, in this way the greatei portion of the water is displaced by the oil, and the last portion is driven off from the paint by surrounding the mill with a heating jacket so arranged that the contents are heated in a partial vacuum In this way the use of drying stoves and the dangers attending it are completely obviated

According to the *German method* of manufacture, plates of lead are hung up in wooden boxes placed in an atinosphere of carbon dioxide in heated chambers containing a stratum of acetic acid, or the plates are suspended in heated chambers havmg their floors covered with tan and acetic acid

The *French method,* introduced by Thenard, and the *English method,* suggested by Benson, do not furnish a white lead which possesses the same covering power as that prepared by the other methods The process in these cases consists in passing carbon dioxide through a solution of a basic acetate of lead, obtained by boiling a solution of lead acetate with litharge

Another method, which yields a white lead of excellent covering power, is the process patented by Dale and Milner This consists in carefully grinding between millstones a mixture of litharge, or any insoluble basic lead salt, with water and sodium bicarbonate. Milner has improved upon this method by grinding

a mixture of *i* parts of finely-divided litharge with 1 part of common salt and 16 parts of water After about 4½ hours the reaction is complete The mixture of basic lead chloride **and** caustic soda is then brought into a leaden vessel, well stirred with a wooden pestle and a current of carbon dioxide passed through it until the liquid is neutral If the carbon dioxide be passed in too long the product is spoiled [1]

Another process, called, after its discoverer, the *Bischof process,* is now employed on a large scale at Mond's works at Bnmsdown in Middlesex[2] Metallic lead is converted into litharge, and the latter is heated at 250-300° in a stream of water gas It is thereby reduced to a black suboxide of unknown composition, and this is treated with water, when a yellow hydrate is formed with evolution of heat, which is further converted into white lead by treatinent with carbon dioxide This process, besides being rapidly completed, has the advantage of being carried out mechanically, and in such a manner that there is no dust, and thus a great source of danger to the workers is avoided The product has a composition practically identical with that formed by the German process

Several electrolytic processes have been proposed, but only a very small amount of white lead is produced by this means [3]

White lead is a white, earthy, heavy, amorphous powder which appears under the microscope to consist of round, transparent globules of the size of from 0 00001 to 0 00004 of an inch in diameter The specific gravity of that prepared by the Dutch method is somewhat greater than that prepared by the French method, and it therefore absorbs less oil or varmsh and gives rise to a thicker colour

Although it acts as a powerful poison, and is turned black by sulphuretted hydrogen, white lead is still almost exclusively used as the basis of pamt, and has been replaced only to a very small extent by zinc-white or baryta-white This is accounted for by the fact that it possesses a much greater covering power and is much more opaque than either of the other two

White lead is often mixed with heavy-spar and gypsum A mixture of equal parts of white lead and barium sulphate is known as *Venetian white,* whilst *Hamburg white* is a mixture of

[1] **Patent No 4053, 22nd November, 1875**

[2] **Caro, *Verh des Vereins zur Beforderung des Gewerbfleisses, Berlin,* 1906**

[3] **Luckow, D R . P , 91707 and 105143, Browe and Chaplin U S P , 551361, 1895 and 555232, 1896**

one part of white lead to two of barium sulphate, and *Dutch white* of one part to three of barium sulphate The amount of this admixture may be readily ascertained by treating a weighed portion of the powder with warm dilute mtnc acid, when the barium sulphate remains behind

Lead Cyanide, $Pb(CN)_2$, is obtained as a white powder when a solution of a normal lead salt is mixed with potassium cyanide

It is not soluble in the cyanides of the alkali metals and is decomposed on the addition of an acid When heated in a closed vessel a mixture of lead and charcoal remains behind which, if it has not been too strongly heated, is pyrophone

Lead Cyanate, $Pb(CNO)_2$, is obtained by mixing solutions of a cyanate and of a soluble lead salt A dense white precipitate is thrown down, which soon assumes the form of slender needles like chloride of lead Under the action of boiling water lead cyanate is readily and quantitatively hydrolysed into lead carbonate and urea[1]

Silicates of Lead —Silica fuses with lead oxide to form a yellow glass, and silicates obtained by " fritting " lead oxide with sihcious material are used by potters for preparing glazes Glass formed of equal parts of lead oxide and silica does not become dull when it is exposed to the action of sulphuretted hydrogen, but if 8 parts of the glass are fused with one part of potash, the glass produced becomes tarnished on exposure[2] In a similar manner it has been found by Thorpe and Simmonds[3] that the extent to which lead silicates are attacked by dilute hydrochloric acid depends upon the proportion of acidic to basic oxides present When there are present in the silicate two or more molecules of acidic oxides to one of basic oxide, dilute acid dissolves out very little lead, whereas when this proportion falls below two, the silicates are readily attacked Lead silicate forms a constituent of flint glass The existence of the definite compounds $2PbO,SiO_2$ and PbO,SiO_2 has been proved by various methods of investigation, and the existence of the compound $3PbO,2SiO_2$ is probable[4]

[1] **Cumming, *Journ Chem Soc* , 1903, 83, 1391**

[2] **Faraday, " On the Manufacture of Optical Glass," *Phil Trans*, 1830, 120,1**

[3] ***Journ Chem Soc*, 1901, 79, 791.**

[4] **Hilpert and Weiller, *Ber*, 1909,42, 2969, Cooper, Shaw and Loomis, *ibid*, 3991, Hilpert and Nacken, *ibid* , 1910, 43, 2565, Cooper, Kraus and Klein, *Amer Chem J* , 1912,47, 273**

POISONOUS ACTION OF LEAD SALTS

410 The soluble lead salts are strongly poisonous and are employed in medicine The normal or basic acetate given in doses containing 1 to 4 grams of lead mostly produces symptoms of acute lead poisoning, whilst 10 grams are said to be a fatal dose

When taken for a considerable time in small doses, especially in the case of the oxides and carbonates, chronic lead poisomng is observed The disease called painters' colic is the chrome form of poisomng by carbonate of lead The symptoms are pain in the abdomen, constipation, loss of appetite, thirst, and general emaciation, followed by a complex of nervous symptoms known as lead-palsy, epileptic fits, and total paralysis

A very characteristic phenomenon accompanying chrome lead poisomng is the appearance of a blue line at the edges of the gums due to the deposition of lead sulphide This line is often seen in the case of house-painters and the workmen engaged in white lead works, as well as those occupied in manufactures in which white lead is employed, as, for instance, in the manufacture of glazed cards Plumbers and others who have to handle metallic lead are also subject to lead poisomng

A serious source of lead poisomng is the material used by potters for compounding their glazes This generally consists of litharge, white lead, and red lead, which are readily dissolved by the acids of the gastric juice, and the use of suitable lead silicates has been suggested in place of these substances [1]

THE ACTION OF WATER UPON LEAD

411 Since lead acts as a cumulative poison, its salts produce serious results if taken into the system even in very minute quantities for a length of time Drinking water is often collected in lead-lin water in certain circumstances can take up notable quantities of lead it becomes of great importance to determine the conditions under which the solvent action is exerted A fresh bright surface of lead does not tarnish in a perfectly dry atinosphere, nor when sealed up in a vessel filled with pure distilled water from which all air has been expelled by boiling If, however, it be exposed to the united action of air and water the lead is oxidised to hydroxide, which dissolves After a

[1] **Thorpe and Simmonds, *Journ Chem Soc*, 1901,79, 791**

time, this is converted by the action of the atmospheric carbon dioxide into an insoluble basic carbonate Lead hydroxide is then again formed, and thus the corrosive action may be continued [1]

Potable waters always contain a certain amount of salts in solution and the corrosive action on lead depends upon the nature and quantity of the salts thus present The ammoniacal salts act most prejudicially on water in this respect, this is especially the case with ammonium nitrate, which greatly assists the oxidation and solution of the lead Other nitrates do not, however, appear to possess this power, and sulphates, phosphates, carbonates, and silicates either retard or altogether prevent this action, and hence water containing carbonic acid in solution or temporarily hard water consisting of a solution of calcium carbonate in carbonic acid gives rise to the formation of insoluble basic lead carbonate, [2] if, however, an excess of carbon dioxide be present, this is dissolved, the water taking up lead in considerable quantity

The following table (p 937) contains the results of experiments on the solubility of lead in water containing various salts in solution Bright plates of lead having a surface of 5,600 sq mm were placed in flasks containing 500 c c of water in which the salts were dissolved, and the saline solutions allowed to act upon the lead for different periods of time [3]

Many potable waters act as a solvent of lead, especially wateis of a peaty nature which contain organic acids (ulmic and humic acids) and waters containing little or no free carbomc acid, and destitute of calcium and magnesium salts Occasionally otherwise pure waters are found to contain a trace of free sulphuric acid sufficient to render the water plumbo-solvent and liable to cause lead poisoning

Epidemics of lead poisoning from such sources have necessitated the treatment of the water by the addition of calcium carbonate (precipitated chalk) alone, if such water contains sufficient free carbonic acid to enable 1 5 grains $CaCO_3$ per gallon to be dissolved, or if the water will not dissolve this amount the addition of from 1 to 5 grains of sodium carbonate (Na_2CO_3) per gallon also

[1] **See also Thresh, *Analyst,* 1921, 46, 270, Liverseege and Knapp, *J Soc Chem Ind* , 1920, 39, 27**

[2] **See also Antony and Benelli, *Gazz* , 1896,26, 11 , 97, 1898, 28, 11 , 135**

[3] **Muir, *Proc Manch Phil Soc,* 1875, 15, 31, *Journ Chem Soe,* 1877, I, 660 See also Carnelley and Frew, / *Soc Chem Jnd* , 1888,7,15,78, Reichardt, *Arch Pham,* 1887, [3], 26, 858, 1059, Muller, *J pr Chem,* 1887, [2], 36, 317**

Salt	Grams per litre	Milligrams per Litre of Lead dissolved		
		24 hours	48 hours	72 hours
NH_4NO_3	0 02	13 0		25 0
	0 04	15 0	—	32 0
KNO_3	0 02	20	20	—
$NaNO_3$	0 05			
KNO3	007 1	—	—	05
K_2SO_4	050			
KNO_3	0 045	—	—	03
K_2CO_3	0 308			
$CaCl_2$	0 25	05	05	0 5
NH_4NO,	0 02			
$CaCl_2$	006	—	—	18
Na_2SO_4	0 02			
K_2CO_3	0 04	—	—	01
$CaCl_2$	1 10			
K_2CO,	0 31	—	—	02
Distilled water with carbon dioxide at ordinary pressure		30	—	30
Ditto with carbon dioxide at a pressure of about 6 atmospheres		14 8	24 0	—
Distilled water		20	20	30

In testing for the presence of lead in water it is important to avoid any form of filtration, inasmuch as lead salts mordant with the filtering paper, and only a small amount of the original soluble lead is found in the filtrate [1]

DETECTION AND ESTIMATION OF LEAD

412 The soluble lead salts possess a sweet, astringent taste, whence the name " sugar of lead " has been given to the acetate, and are very poisonous These two properties of the lead compounds have been long known, and it became in early times of importance to detect the presence of lead, inasmuch as the compounds of this metal were largely employed for a great variety of purposes Thus, for instance, the Romans were in the habit of boiling their poor wines in leaden vessels, and Pliny mentions

[1] See, Kolthoff, *Pharm Weekblad,* 1921, 58, 152

the fact that the point at which the wine becomes sour can be detected by hanging a strip of lead in it and then observing when this undergoes any change in its appea|ance In later times the addition of metallic lead to a cask of sour wine was said to render it drinkable At a still later date, litharge appears to have been employed for the same purpose It was observed that the treatment of wine with lead could be detected by the addition of sulphuric acid, and in 1707 Zeller suggested that an extract of orpiment and lime water (containing, therefore, sulphide of calcium) was an invaluable test for the presence of lead, inasmuch as this liquid turns all lead salts black This reaction led to the simultaneous suggestion, in 1787, by Fourcroy and Hahnemann, of the application of water acidified with hydrochloric acid and then saturated with sulphuretted hydrogen for the detection of lead, and thus the most important reagent which we now employ in analytical chemistry for the detection and separation of the metals was introduced

Potable water may be examined in this way for lead by passing sulphuretted hydrogen through water slightly acidified with hydrochloric acid It is, however, to be remembered that many other metals, such as mercury, copper, and bismuth, also produce black precipitates The absence of these metals must, therefore, be ascertained before the presence of lead can be certainly proved Black lead sulphide can be readily distinguished from other black sulphides insoluble in dilute hydrochloric acid by dissolving it in warm dilute nitric acid and filtering the solution, on addition of sulphuric acid to the filtrate, from which the excess of acid should be removed by evaporation, a white precipitate of lead sulphate is obtained By means of this reaction lead may be detected in the presence of all the other metals and separated from them

Lead compounds, heated before the blowpipe on charcoal, yield a malleable bead of lead readily soluble in warm nitric acid, and the solution yields a precipitate with sulphuric acid

Another characteristic test for lead is, that when present in not too dilute solution, a crystalline precipitate of the chloride is obtained on the addition of hydrochloric acid This is soluble in boiling water, and separates out on cooling in crystalline needles Potassium chromate gives, in the presence of free nitric acid, a fine, yellow precipitate of chrome yellow, $PbCrO_4$ In order to detect small quantities of lead in presence of large masses of organic matter, as is necessary in cases of lead poison-

ing, the mass is evaporated to dryness with sodium carbonate, the residue lgnited gently, and the carbonised mass rubbed fine and carefully lixiviated, when small, glittering, heavy spiculae of metallic lead remain behind These can be examined as already described

Lead is easily estimated gravimetrically in the form of sulphate, being precipitated by adding dilute sulphuric acid and then two volumes of absolute alcohol For certain separations lead is also estimated as the chloride In this case the solution is precipitated by hydrochloric acid, evaporated on a water-bath, and the concentrated liquid treated with a mixture of ether and alcohol, in which the chloride is insoluble Lead carbonate and lead oxalate are also occasionally used for the estimation of lead, being converted by ignition into lead oxide

Volumetrically, lead is determined by the titration of the solution of lead sulphate in ammonium acetate solution with a standard solution of ammonium molybdate, the end point being detected on a spot plate by means of tannin solution [1]

Lead is also estimated electrolytically When a solution of lead salt, to which 5 to 7 per cent of nitric acid has been added, is electrolysed, lead peroxide is deposited at the anode

Lead compounds impart a pale tint to the non-luminous gas-flame, and this exhibits characteristic lines in the green (Werther) The spark spectrum of lead contains a large number of lines between the orange and violet The brightest and most characteristic of these are a violet line (4058), a somewhat less bright one in the green (5608), and a fainter one lying near the less refrangible of the " D " lines of Fraunhofer (5875) (Lecoq de Boisbaudran)

The Atomic Weight of lead was determined by Berzehus,[2] by the reduction of pure lead oxide in hydrogen, his results giving the number 207 06, later,[3] during his experimental work on the determination of the atomic weight of sulphur, he converted lead first into nitrate and then into sulphate, and from his results the number 206 96 is obtained Turner [4] by a similar method obtained 207 04, and Stas [5] 206 92 Baxter and Wilson [6] determined the atomic weight by analyses of lead chloride which

[1] See also Sasse, *Pharm Zert*, 1920, 65,559, 688, Kolthoff, *Pharm Weekblad*, 1920, 57, 934, Simmons, Gordon, and Boehmer, *Canad Chem J* , 1920,4, 139
[2] *Lehrbuch*, 3, 1218 [3] *Ibid* , 5th ed , 3, 1187
[4] *Phil Trans*, 1833, **123,** 527
[5] *Bull Acad roy Belg*, 1860, [2], 10, 298
[6] *J Amer Chem Soc*, 1907, 30, 187

had been previously fused in an atmosphere of hydrogen chloride, from the ratic of lead chloride to silver, the number 207 088, and from the ratio to silver chloride, 207 096 was obtained More recently Baxter and Thorvaldsen [1] have obtained the number 207 19 by analysis of the bromide while Baxter and Grover [2] found the numbers 207 21 and 207 19 by analysis of the chloride and bromide The weight of silver necessary to precipitate the halogen from a known weight of lead hahde, and the weight of silver halide produced, were both determined It was shown that lead from non-radioactive sources (' normal" lead) always has the same atomic weight, since the lead used was derived from several different minerals and from sources widely separated geographically The mean of these last numbers, 207 20, is now (1922) adopted as the atomic weight of lead, though later determinations, having as their object the comparison of the atomic weights of normal lead with that of lead from radioactive sources, rather than the absolute value of the atomic weight, indicate a slightly lower number. By analysis of the chloride, Homgschmid and Horowitz [3] obtain the number 207 18, Eichaids and Lembert[4] 207 15 Eichards and Wadsworth[5] 207 18 and Richards and Hall[6] 207 19

ISOTOPES OF LEAD

413 The study of radioactivity leads to the belief that there are nine isotopes *(q v)* of lead, of these, the final disintegration product of uranium (238), by loss of eight a-particles, should be lead of atomic weight 206, while the final product of thorium (232), by the loss of six a-particles, should be lead of atomic weight 208

Confirmation of this was first obtained by Soddy and Hyman,[7] who found lead derived from thorite, a radioactive mineral from Ceylon consisting chiefly of hydrated thorium silicate, has an atomic weight of 208 4 It has since been amply confirmed that lead from a radioactive source in which thorium predominates has a higher atomic weight than normal lead, though the number 208 4 is probably too high Homgschmid [8] obtained the number 207 90 for lead from Norwegian thorite Richards and his collaborators, and Honigschmid, have shown that lead derived

[1] *J Amer Chem Soc* , 1915, 37, 1021 [2] *Ibid* , 1915, 37, 1027
[3] *Monaish* , 1915, 36, 355 [4] *J Amer Chem Soc* , 1914, 36, 1329
[5] *Ibid* , 1916, 38, 227 and 2613 [6] *Ibid* , 1917, 39, 537
[7] *Journ Chem Soc* , 1914, **106,** 1402 [8] *Zeit Elektrochem,* 1919, 25, 91

from a radioactive source in which uranium predominates has a lower atomic weight than normal lead, the lowest value yet obtained, 206 05, is for lead from a crystallised uranium mineral from Morogoro in Tanganyika territory

It has been shown that different isotopes have the same melting point within the limits of experimental error,[1] that their atomic volumes are the same, for their densities are proportional to their atomic weights,[2] that the solubilities of their nitrates are the same, if the results are expressed in moles per litre,[3] that they cannot be separated by fractional crystallisation of their nitrates, and that the refractive indices for sodium light of their nitrates are the same Only a slight difference in the position of one line in the spec Hyman, and has been confirmed by Merton[4]

A possible partial separation of the isotopes of lead by a chemical method has been described,[5] but the results require confirmation

The lead content of radioactive minerals is regarded as a valuable indication of their age Since there is no evidence that all the lead present in a mineral is derived from radioactive disintegration, the lead content can only give an upper limit to its age[6]

[1] Richards and Hall, *J Amer Chem Soc,* 1920, 42, 1550, Lembert, *Zed Elektrochem* , 1920, 26, 59
[2] Soddy, *Nature,* 1921, **107,** 41
[3] Richards and Schumb , *J Amer Chem Soc* , 1918, 40, 1403
[4] *Proc Boy Soc* , 1920, 96, *[A],* 388, 1921, **100,** [4], 84
[5] Dillon, Clarke, and Hinchy, *Sci Proc Roy Dublin Soc* , 1922, **17,** 53
[6] Lawson, *Sitzungnber Akad Wiss Wien,* 1917, **126,** 2A, 721

GROUP V

Sub-group (a)	*Sub-group (b)*
Nitrogen	Phosphorus
Vanadium	Arsenic
Columbium (Niobium)	Antimony
Tantalum	Bismuth

413 As in the preceding group (p 831), the members of the two sub-groups resemble one another, especially in chemical properties, very closely, although they differ in certain respects

All the elements of the group are characterised by the existence of acid-forming oxides of the empirical formula R_2O_5, the acidity of the resulting acid diminishing as the atomic weight of the element rises Thus it is doubtful whether any salts of bismuthic acid exist, whereas the vanadates, arsenates, etc , are well-defined and stable salts

The elements vanadium, columbium, and tantalum, which, with nitrogen, belong to the even series, combine so readily with oxygen that it is difficult to obtain them pure They all have a metallic appearance, and melt and boil only at very high temperatures They do not form volatile compounds with hydrogen or the alcohol radicles

The elements of the odd series, phosphorus, arsenic, antimony, and bismuth, on the other hand, are easily reduced from their oxides, melt at moderate temperatures, and can all readily be volatilised. They exhibit in their external characteristics the gradual passage from a well-marked non-metallic element (phosphorus) to a well-defined metal (bismuth), and the same progression is to be traced also in their chemical properties Thus the lower oxide of phosphorus, of the empirical formula P_{23}, is the anhydride of a well-marked acid, but does not yield salts, even with strong acids Arsenious oxide yields unstable salts with strong acids, such as sulphuric acid, the corresponding oxide of antimony yields more stable salts, and the trioxide of bismuth is entirely devoid of acid-forming properties, and reacts with acids to form a whole series of salts of the type RX^1_3

The same morease in basicity is observable in the sulphides of these elements, as well as in the pentoxides

Phosphorus, arsenic, and antimony, as well as nitrogen, yield very characteristic volatile hydrogen compounds, a hydride of bismuth has also been prepared They all form organo-metallic derivatives

The group is further characterised by the large number of oxides and halogen derivatives formed by its members In many of these the valency of the elements varies considerably They are all distinguished by a tendency to form two series of compounds of the types RX^{1} and RX^{1}_{5} (or $K_2X^{II}_3$, $R_2{}^{XII}{}_5$), but, in addition to this, some of them act also as dyads and tetrads Thus nitrogen is divalent in nitric oxide, NO, and tetravalent in nitrogen peroxide, NO_2, whilst vanadium forms a dichloride, $VC1_2$, and a tetrachloride, $VC1_4$

The elements nitrogen, phosphorus, and arsemc, and their chief derivatives, have already been described in Vol I

THE VANADIUM GROUP

VANADIUM V = 510 At No 23

414 In 1801, Del E10 pointed out the existence of a new metal in a lead ore found at Zimapan, in Mexico,[1] and gave to it the name erythronium, from the fact that its salts became red when heated with acids In 1805, Collet-Descotils[2] expressed his opinion that this supposed new metal was an impure oxide of chromium, and Del Rio accepted this conclusion as correct In 1830, Sefstrom[3] described a new metal which he found in the celebrated iron of Taberg, and for this he proposed the name of Vanadium, from *Vanadis*, a cognomen of the Scandinavian goddess Freia In the same year Wohler[4] showed that Del Bio's discovery was a true one, and that the Zimapan ore was a vanadate of lead Unable to carry out the further investigation of the new metal, Sefstrom handed the materials, amounting only to a few grams, to Berzehus, and in 1831 this chemist[5] published the result of an exhaustive investigation on the subject, in which he described a large number of vanadium compounds, and came to the conclusion that vanadium

[1] *Gilbert's Ann*, **1801,71,**7
[2] *Ann Chim Phya*, 1805, **[1], 63,**260
[2] ***Pogg Ann*, 1830,21, 48** [4] *Ibid*, **1831, 22, 1** [5] *Ibid*

closely resembled chromium and molybdenum, yielding, like these metals, an acid-forming trioxide' This new was universally adoptecAmtil the year 1867, when Rosooe showed that the substance supposed by Berzehus to be vanadium was, according to the mode of its preparation, either an oxide or a nitride, that the volatile trichloride of Berzehus contained oxygen and possessed a composition analogous to that of phosphorus oxychlonde, and that the metal, instead of belonging, as was supposed, to the chromium group, was a member of the antimony group and intimately connected with the nitrogen, phosphorus, and arsenic family [1]

415 Vanadium is a somewhat rare substance, forming an essential constituent of only comparatively few scarce minerals Traces of this element are, however, tolerably widely distributed throughout terrestrial matter, it is found in meteorites of the stony type,[2] and it exists in the sun

The principal vanadium minerals are vanadimte, or lead vanadate, $3Pb_3(VO_4)_2,PbCl_2$, dechenite, $(Pb,Zn)(VO_3)_2$, descloizite, $Pb_2V_2O_7$, puchente, $BiVO_4$, psittacinite,

$$(Pb,Cu)_3(VO_4)_2,3Cu(OH)_4,6H_2O,$$

volborthite, $(Cu,Ca)_3(VO_4)_2,H_2O$, roscoehte (vanadium mica), a vanadium muscovite, containing the metal as the basic oxide,[8] V_2O_3, mottramite, $(Pb,Cu)_3(VO_4)_2,2(Pb,Cu)(OH)_2$, sulvanite, $3Cu_2S,V_2S_5$, carnotite, a potassium uramum vanadate found in Colorad which occurs in considerable quantity in Peru Mottramite has been found in tolerable quantity in the copper-bearing beds of the keuper, worked at Alderley Edge and Mottram St Andrews in Cheshire, and it is from this source that the vanadic acid of commerce was at one time obtained Small amounts of vanadium have also been found in a large number of clays, in trap and basalt,[4] in certain iron ores, especially magnetite,[5] and cast-iron, in larger quantities in the slag from the basic steel process at Creuzot, in rutile, in the ash

[1] **A bibliography has been compiled by Prandtl (Liepzig, 1906, Voss) More complete information concerning the compounds of vanadium may be obtained from the monograph by Ephraim (Stuttgart, Enke, 1904)**

[2] **Hasselberg, *K Vet Akad Forh Stockholm,* 1899, 66, 131**

[3] **Hillebrand, Turner and Clarke, *Amer J Set,* 1899, [4], 7, 451 It occurs in fairly large quantities associated with gold and gold tellurides in Eldorado Co in California, also in Colorado and at Kalgoorhe in Western Australia**

[4] **See Hdlebrand, *Amer J Set,* 1898, [4], 6, 209, 7, 294**

[5] **See Pope, *Journ Chem Soc,* 1900, 78, 11, 409**

of trees, in certain coals, lignites, and peats, and also in soda-ash, as well a in sodium phosphate

Extraction end Preparation of Vanadium Compounds—In order to prepare vanadium salts from mottramite, the keuper-sandstone, which contains the mineral deposited as a film on the surface of the grains of sand, is digested with strong hydrochloric acid, the acid liquor drawn off, and the sand well washed with water The acid solution, together with the washings, is evaporated down with an excess of ammonium chloride, when ammonium metavanadate separates out, and this is repeatedly crystallised to free it from copper and iron The crude ammonium metavanadate is then gently roasted in porcelain, by which means the vanadium pentoxide is obtained in a tolerably pure condition In order to purify this it is suspended in water and ammonia gas passed into the liquid A solution of ammonium vanadate is thus formed, which is separated by filtration from the residue containing silica, phosphates, etc , and then crystallised by evaporation in platinum vessels, the pentoxide obtained by several repetitions of this treatment is free from phosphorus

Vanadic acid may be prepared in a similar manner from *camotite,* which is an important mineral commercially, being a source of uranium and radium It is preferable, however, to boil the mineral with an excess of sodium carbonate, when practically all the uranium and about two-thirds of the vanadium pass into solution as sodium uranate and vanadate, and the radioactive matter remains in the residue By filtering the solution and concentrating until it is saturated with sodium carbonate, most of the uranium separates out as a yellow double salt, $UO_2CO_3,2Na_2CO_3$, and on cooling the hot filtrate from this salt much of the excess of sodium carbonate crystallises out The filtrate then contains sodium vanadate together with excess of sodium carbonate and a little uranium, which may be precipitated as sodium diuranate, $Na_2U_20_7,6H_20$, by addition of caustic soda[1]

416 *Metallic Vanadium*—Berzelius obtained brilliant metallic scales by heating the .oxytnchlonde in an atinosphere of ammoma These do not, however, consist of metallic vanadium, but of vanadium nitride Pure metallic vanadium was first obtained by the reduction of the dichloride in perfectly pure hydrogen Although this process appears simple enough, there is no metal more difficult to prepare in this way than vanadium This

[1] **See Plum,** *J Amer Chem Soc,* **1915, 37, 1797**

arises from the fact that whilst vanadium is stable at the ordinary atinospheric temperatures, it absorbs oxygen at a red heat with the greatest avidity, so that every trace of air of moisture must be excluded during its preparation Moreover, the dichloride itself cannot be readily obtained in quantity

Roscoe's apparatus is shown in Fig 189 The hydrogen generator (A) yields a stream of hydrogen which can be kept constantly passing through the wash-bottles for a week at **a** time, by occasionally adding fresh acid to the upper bottle and drawing off the zinc sulphate solution from the lower bottle The first wash-bottle contains a solution of lead acetate, the second one of silver nitrate, and the three others contain boiled sulphuric acid Traces of oxygen arising either from diffusion or from air absorbed in the dilute acid used are removed in the tube (CD) attached to the last washing-bottle, the first portion of the tube contains red hot platinum sponge (c), whilst the further portion of the tube (D) IS filled with phosphorus pentoxide and plugs of cotton-wool. The greatest care must be taken to have all rubber stoppers and joints made as tight as possible with copper-wire and paraffin At right angles to the drying tube (CD) IS placed the reducmg arrangement shown in the lower part of the drawing This consists of a porcelain tube (EE') placed in a Hofmann's furnace and protected in the central portions, where it is heated by an outer casing of sheet-iron The porcelain tube is connected with the hydrogen apparatus by means of the wide glass tube (FF') provided with the tubulus (G) and narrowed down to join the drying tube at F' The joint between the porcelain and glass tubes is made of seamless rubber, well wired and covered by an outer short glass cylinder, the space between the tubes and the cylinder being filled either with mercury or fused paraffin, and a similar joint is placed at the further end of the porcelain tube

The dichloride is contained in the bent tube (H) in which it was prepared and sealed up in hydrogen It is fitted through the tubulus (G) The platinum boat being in position, as shown in the figure, hydrogen is allowed to pass through the apparatus for twelve hours to dry it completely and clear out the air, the rubber stopper of the tubulus is then withdrawn and the end of the tube containing the dichloride cut off, and the tube and stopper are quickly replaced, so that the crystals he in the horizontal portion of the tube, which is then so turned in the **stopper that the crystals of dichloride fall into the platinum**

boat below This boat, charged with dichloride, is then drawn into the center of the porcelain tube by means of the platinum wire, the end cf which (w) passes tightly through a small hole

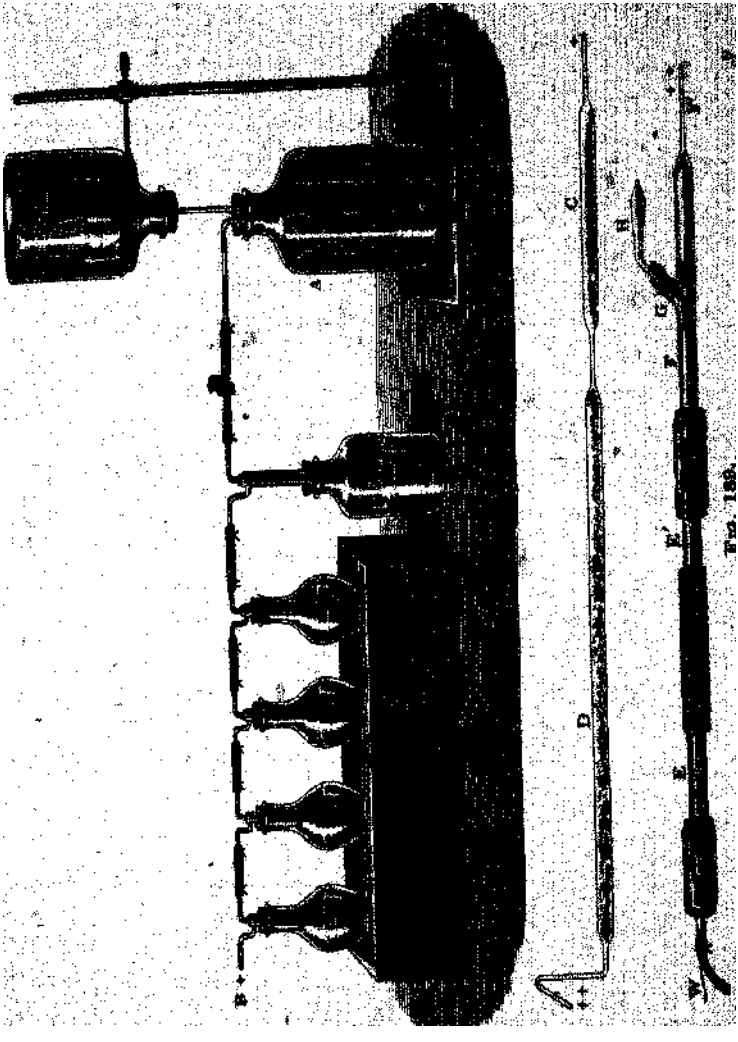

in the rubber tube at the end of the apparatus, the wire is then cut off short at the end of the glass tube, a proper joint made, and an exit tube attached dipping under sulphuric acid

The rubber stopper of the tubulus is surrounded by a bath of paiaffin and the hydrogen is allowed to bubble through for six hours The porcelain tube is then gradually raised to the highest

temperature (*a* bright red heat) the Hofmann's furnace will yield, and kept constant until some hours after the last trace of hydrogen chloride can be detected in the issuing hydrogen The process lasts from forty to eighty hours, according as the quantity of dichloride employed varies from 1 to 3 or 4 grams

Reduction of vanadium pentoxide with carbon in the electric furnace yields only an impure metal, containing a large amount of carbon[x] Pure vanadium can be prepared by reducing the pentoxide with a mixture of the metals of the rare earths, known as " mischmetall," obtained by the reduction of the waste oxides from the manufacture of thona[2] The oxide is mixed with the finely divided metal in a magnesia crucible and the mass ignited, as in the aluminium thermite process, a violent reaction occurs and a regulus of pure vanadium is produced The metal has been prepared also by passing the electric current through thin rods of V_2 contained in a vacuum,[3] by heating the trioxide and carbide in a zircoma crucible to 1950[0],[4] and by passing the vapour of vanadium chloride over heated sodium hydride[5] A regulus of crude vanadium, probably consisting of a mixture of the metal and the dioxide, can be obtained from vanadic oxide by Goldschmidt's aluminium reduction method It can be used for the preparation of the tetrachloride[6]

Metallic vanadium prepared by reduction from the dichloride in hydrogen, is a light whitish-grey coloured powder, which under the microscope reflects light most powerfully, and appears as a brilliant crystalline, metallic mass possessing a silver-white lustre The surface of a regulus of the metal is covered with twinned rhombohedral crystals, and the metal has a hardness greater than that of steel or quartz It is of a brilliant silver-white colour and takes a splendid polish which is not affected by air Vanadium does not decompose water at the ordinary temperature and is neither volatile nor fusible when heated to redness in hydrogen When the powdered metal is thrown into a flame, or rapidly heated in an excess of oxygen, it burns with brilliant scintillations The specific gravity of vanadium at 15° is 5 5, and the atomic heat, as deduced from the specific heat

[1] Moissan, *Compt rend,* 1893, **116,** 1225
[2] Weiss and Aichel, *Annalen,* 1904, **337,** 380
[3] Werner von Bolton, *Zeit Elektrocliem,* 1905, **11,** 45
[4] Ruff and Martin, *Zeit angew Chem ,* 1912, 25, 49
[5] Billy, *Compt rend,* 1914, **168,** 578
[6] Koppel and Kaufmann, *Zeit anorg Chem,* 1905, 45, ^52

of its alloys, s normal[1] The metal is not attacked by hydrochloric acid either when cold or hot, and neither strong nor dilute sulphurn acid acts upon it in the cold, but when heated with the strong acid it slowly dissolves, giving a greenish-yellow solution Hydrofluoric acid dissolves the metal slowly with evolution of hydrogen and formation of a green solution, whilst nitric acid of all strengths oxidises it with violence, evolving nitrous fumes and forming a blue liquid Vanadium also dissolves readily in chloric acid, perchloric acid, and ammonium persulphate, vanadic acid being produced[2] Both hot and cold solutions of caustic soda are without action on the metal, but when fused with the hydroxide, hydrogen is evolved and a vanadate formed Metallic vanadium precipitates platinum, gold, and silver from solutions of their salts, and reduces mercuric, cupric, and ferric salts to the corresponding lower salts (Marino) When heated in an atmosphere of pure nitrogen, it is converted into the monomtride (Roscoe)

Alloys of vanadium can be prepared in the electric furnace by reducing vanadic anhydride in the presence of the second metal or one of its oxides[3] It also forms an alloy with platinum Ferrovanadmm is manufactured on a commercial scale in the electric furnace in France and also in Colorado It is used in the production of vanadium steel (see Steel)

COMPOUNDS OF VANADIUM

VANADIUM AND OXYGEN

417 Vanadium forms five compounds with oxygen, analogous to the oxides of nitrogen, namely

Vanadium suboxide	V_2O
Vanadium monoxide, hypovanadious oxide	VO or V_2O_2
Vanadium sesquioxide, vanadium trioxide	V_2O_3
Vanadium dioxide, hypovanadic oxide	VO_2 or V_2O_4
Vanadic anhydride, vanadium pentoxide	V_2O_5

All these oxides form salts, the three first acting only as basic oxides, the two highest both as acid-forming oxides and as weak basic oxides

Some confusion exists as to the nomenclature of the various

[1] Matignon and Monnet, *Compt rend*, 1902, **134,** 542
[2] Marino, *Zeit anorg Chem*, 1904, 39, 152
[3] Moissan, *Compt rend*, 1896, **122,** 1297

oxides of vanadium and the series of compounds ^derived from them Roscoe, tomark the analogy with arseuc and phosphorus, termed the sesquioxide, V_2O_3, vanadiousf oxide, and its salts the vanadious salts, and to the lower oxide, VO or V_2O_2, he gave the name hypovanadious oxide The fact that V_2O_3 acts entirely as a basic oxide, and the close analogy existing between the derivatives of V_2O_3 and of VO and the corresponding chromium compounds, have led more recent investigators[x] to term the compounds derived from V_2O_3 the vanadic salts, and those derived from VO the vanadious salts, corresponding with the chromic and chromous salts respectively The salts formed by the oxide VO_2 with bases, termed by Roscoe hypovanadates, are now usually called vanadites, and the salts with acids contaimng the divalent radicle VO (or the tetravalent radical V_2O_2) are known as vanadyl (or divanadyl) compounds The more modern nomenclature has been adopted here

418 *Vanadic Anhydride,* V_2O_5 —The preparation of this oxide from mottramite has already been described In the pure state it is best prepared by decomposing the oxytnchlonde, $VOCl_3$, with water and fusing the residue, but it can also be obtained pure by heating pure ammomum metavanadate and avoiding any reduction[2] Vanadic anhydride crystallises in splendid yellowish-red, rhombic prisms (Nordenskiold), which have a specific gravity of 3 35 (J J Watts), and dissolve in about 1,000 times their weight of water, giving a yellowish solution, which does not possess any taste but turns blue litinus paper red Vanadic anhydride fuses without decomposition in absence of orgamc reducing matter to a red liquid, which on cooling yields brilliant, transparent, reddish-yellow needles, and at the moment of crystallisation exhibits the phenomenon of incandescence

Vanadic anhydride exists in several different modifications, which differ in solubility and other properties When it is prepared by igniting ammomum vanadate, evaporating with nitric acid, and gently heating the residue, it forms a yellow, hygroscopic powder, which unites with water to form hydrates containing 1, 2, and 8 molecules of water, and dissolves in cold water to the extent of 8 grams per litre When the oxide is heated for a long time at 440° or fused, it is converted into two different sparingly soluble modifications[3]

[1] **Piccini and Marino,** ***Zeit anorg Chem,*** **1902, 32, 57**
[2] **Matignon,** ***Chem Zeit,*** **1905, 29, 98b**
[3] **Ditte,** ***Compt rend,*** **1885, 101, 698**

Vanadic anhydride acts as a weak basic oxide as well as an acid-formmg oxide thus it dissolves in strong acids, forming red or yellow solutions yielding crystalline compounds, which separate out on spontaneous evaporation or cooling

Vanadic anhydride is reduced by sulphurous acid in presence of sulphuric acid, and by evaporation with hydrochloric acid, to VO_2, magnesium and hydrochloric acid, or evaporation with hydriodic acid, reduce it to V_2O_3, whilst zinc and hydrochloric acid carry the reduction to VO

Vanadic anhydride has been used in the preparation of aniline black, and its use has been suggested in the electrolytic oxidation and reduction of various organic compounds in an acid bath, *e g*, the manufacture of quinone from aniline, etc [1] It also greatly accelerates certain oxidation processes, such as the action of nitric acid on sugar, the oxidation of alcohol by atinospheric oxygen, etc [2]

THE VANADIC ACIDS AND THEIR SALTS

419 *Normal Vanadic Acid,* H_3VO_4, is not known

Metavanadic Acid, HVO_3, was discovered by Gerland [3] It forms a fine yellow pigment, sometimes termed vanadium bronze, and is employed in place of gold bronze It is obtained in the form of brilliant scales of a golden or orange colour by boiling aqueous sulphurous acid with copper vanadate, prepared by the double decomposition of ammonium metavanadate and copper sulphate A mixture of brown and orange-yellow crystals is obtained, and on continuing the ebullition with more sulphurous acid, the brown crystals dissolve, the yellow metavanadic acid being insoluble

Vanadium bronze may also be prepared by adding a solution of ammonium vanadate to one of copper sulphate containing excess of ammomum chloride until a permanent precipitate is formed, and then gently heating to 75°, when the yellow scales are slowly deposited, and after the lapse of a few hours nearly the whole of the vanadium is precipitated The larger the quantity of material employed and the slower the action takes place, the finer is the colour of the bronze [4]

[1] German Patent, 172654 (15/9/03)

[2] Moeser and Lindenbaum, *J pr Chem* , 1907, [2], 75, 146, German Patent, 183022 (18/8/05)

[3] *Proc Manch Phil Soc* , 1873,**12,** 50

[4] *Ber,* 1876, **9/874**

If the freshly prepared solution of copper vanadate be quickly evaporated flat a ilat dish, a crystalline residue is obtained which is soluble in warar, and when this solution zzis dialysed for some days a clear solution of pure vanadic acid is obtained which remains clear when heated, and deposits the red amorphous pentoxide on evaporation

A solution of vanadic acid is decomposed on heating with sulphuric acid [1]

Pyrovanadic Acid, $H_4V_2O_7$, is a brown precipitate closely resembling ferric hydroxide, obtained by treating a solution of an acid vanadate with mtnc acid When air-dried it possesses the above composition It is, however, unstable and loses half its water when dried over sulphuric acid (v Hauer)

Hexavanadic Acid, $H_4V_6O_{17} = 6V_2O_5,2H_2O$ —When a solution of pervanadic acid is allowed to stand it loses oxygen and forms an acid yellow liquid, which probably contains hexavanadic acid The solution .is unstable and soon deposits a brown precipitate of vanadium pentoxide [2]

The Vanadates —The so-called normal vanadates prepared by Berzelius correspond to the metaphosphates, it is also possible to prepare ortho- and pyro-vanadates analogous to the corresponding phosphates v Hauer's so-called di- and tn-vanadates [3] are most simply formulated as tetra- and hexa-vanadates, $Na_2V_4O_{11}$ and $Na_2V_6O_{16}$, but it is probable from the researches of Dullberg on the molecular weights and conductivities of these salts that they are in reality acid salts derived from hexavanadic acid, $H_4V_6O_{17}$, the normal salt of which, $Na_4V_6O_{17}$, is also known Thus we have

(1) Sodium Metavanadate	$NaVO_3$
(2) Sodium Orthovanadate	Na_3VO_4
(3) Sodium Pyrovanadate	$Na_4V_2O_7$
(4) Sodium Tetravanadate (v Hauer)	$Na_3HV_6O_{17}$
(5) Sodium Hexavanadate „	$Na_2H_2V_6O_{17}$

Other more complicated poly vanadates are known[4]

The order of stability of the soluble vanadates in aqueous solution differs remarkably from that of the phosphates, the

[1] Auger, *Compt rend,* 1921, **173,** 306
[2] Dullberg, *Zeit physikal Chem,* 1903, 46, 170
[3] *J pr Chem,* 1856, 60, 385, 1859, 76, 156, 929, 1860, 80, 324
[4] Carnelley, *Journ Chem Soc,* 1873, 36, 323, Rosenheim, *Zeit anorg Chem* , 1916, 96, 139, *ibid* , 98, 223

metavanadates being the most stable and the orthovanadates the least stable, whereas in the phosphorus series the order of stability is the reverse of this At a high temperature, on the other hand, the orthovanadate is the most stable, being formed when vanadium pentoxide is fused with an alkali carbonate, the meta-salt being produced when a solution of an alkali carbonate is boiled with vanadium pentoxide

The property which serves best to distinguish the ortho- from the meta-vanadates is the colour of the respective copper salts Copper orthovanadate possesses a blue-green colour, whilst the metavanadate is a light yellow, crystalline powder

The alkali pyrovanadates are soluble, and can be readily obtained by fusing one molecule of vanadium pentoxide with two molecules of the carbonate of an alkali metal, dissolving, and crystallising They are likewise obtained by the decomposition of an aqueous solution of the corresponding orthovanadate The pyrovanadates of the heavy metals are usually insoluble in water, and possess properties generally similar to those of the corresponding orthovanadates

The metavanadates are usually yellow some of them, especially those of the alkaline earths, zinc, cadmium, and lead, are converted into colourless isomeric modifications, in the solid state under water, in aqueous solution, and especially in the presence of alkali carbonates The metavanadates of the alkali metals are colourless, and on treatinent with an acid give rise to anhydro-salts, which have a fine yellowish-red colour The metavanadates of ammonium, potassium, sodium, barium, and lead are but sparingly soluble in water The other meta-vanadates are more soluble It is probable that sodium meta-vanadate has the molecular formula $Na_3V_3O_9$, thus corresponding with the tnmetaphosphate (Dullberg) The following are the properties of the most important members of these three classes of vanadates

Potassium Metavanadate, KVO_3, dissolves slowly in cold and readily in hot water, and with difficulty in caustic potash When it is boiled with water and vanadium pentoxide, or fused with the latter, *potassium tetravanadate,* $K_2V_4O_n,3H_4O$, or $K_3HV_6O_{17},4H_2O$ (Dullberg), is obtained, crystallising in broad, reddish-yellow tablets This salt is slightly soluble in cold and very easily soluble in hot water

Sodium Orthovanadate, Na_3VO_4—This salt crystallises with 16,12, 1O, and $8H_aO$, and in the form with $12H_2O$ is isomorphous

with sodium orthophosphate It has a stiongly alkaline reaction, and in aqueaus solution is completely hydrolysed to caustic soda and sodium^yrovanadate '

$$2Na_3VO_4 + H_2O = Na_4V_2O_7 + 2NaOH$$

Sodium Pyrovanadate, $Na_4V_2O_7{,}18H_2O$, crystallises in large, six-sided tablets, is easily soluble in water, and is precipitated by alcohol from its aqueous solution in pearly scales It fuses more easily than the orthovanadate, and is first formed in the preparation of the latter salt

Sodium Metavanadate, $NaVO_3$, resembles the potassium salt, and is converted in a similar manner into *sodium tetravanadate,* $Na_2V_4O_n{,}9H_2O$, or $Na_3HV_6O_{17}{,}13H_2O$ (Dullberg), which separates out in beautiful large orange-red crystals This salt is only slightly soluble in water, but possesses such powerful colouring properties that 1 part of it is sufficient to impart a yellow tint to 200,000 parts of water It effloresces on exposure to the air, becoming of a reddish-brown tint, and melts at a dark red heat, solidifying to a dark red, amorphous mass

Ammonium Metavanadate, NH_4VO_3, is the most important vanadate It is obtained by dissolving the pentoxide in an excess of ammonia and evaporating, or by precipitating with alcohol, in which it is insoluble It forms colourless, transparent, crystalline crusts, and is insoluble in concentrated solution of ammonium chloride, and accordingly is precipitated when a lump of ammonium chloride is allowed to remain in a solution of a metavanadate or pyrovanadate

$$Na_4Y_2O_7 + 4NH_4C1 = 2NH_4VO_3 + 2NH_3 + H_2O + 4NaCl$$

The solution of this salt becomes of a deep black tint when treated with tincture of galls, and Berzekus originally suggested the use of this liquid as an ink This ink is, however, not permanent, " for letters thus written by Berzelius are now quite illegible " (Wohler) It was once used in dyeing with aniline black, since its presence greatly facilitates the oxidation of the aniline hydrochloride on which the formation of the colouring matter depends

Ammonium Tetravanadate, $(NH_4)_2V_4O_{l15}4H_2O$, or

$$(NH_4)_3HV_6O_{17)}5|H_2O,$$

is obtained by the addition of acetic acid to a boiling solution of the metavanadate until the precipitate redissolves The salt separates out from the yellowish-red liquid on cooling in large,

transparent, orange-red crystals If it be recrystalhsed from water containing acetic acid, splendid red crystals of *ammonium hexavanadate,* $^{\wedge}(NH_4)_2V_6O_{16},6H_2O$ or $(NH_4)_2H_2V_6O_{17},5H_2O$ are obtained

Calcium Pyrovanadate, $2Ca_2V_2O_7,5H_2O$, is a white, amorphous precipitate obtained by double decomposition of the corresponding sodium salt with calcium chloride If the solution of sodium orthovanadate be precipitated by calcium chloride, the same salt is obtained mixed with calcium hydroxide, the orthovanadate being at once decomposed according to the equation

$$Ca_3(VO_4)_2 + H_2O = Ca_2V_2O_7 + Ca(OH)_2$$

Lead Orthovanadate, $Pb_3(VO_4)_2$, is a nearly white, insoluble precipitate obtained by adding a solution of lead acetate to one of sodium orthovanadate This salt occurs in nature combined with lead chloride as vanadinite, $3Pb_3(VO_4)_2,PbCl2$ or $Pb_3(VO_4)_2,Pb_2(VO_4)Cl$ This mineral crystallises in hexagonal prisms, having a reddish-brown colour, and is isomorphous with apatite It has a specific gravity of from 6 6 to 7 2, and frequently contains some phosphoric acid It was found by Del Kio in Zimapan in Mexico, and occurs also at Leadhills in Scotland, in Carmthia, and in the Urals It may be obtained artificially by fusing together lead oxide, vanadium pentoxide, and lead chloride, in the right proportions The fused mass contains druses, in which thm, needle-shaped crystals are contained If boiled with water it falls to a crystalline powder consisting of microscopic, hexagonal prisms, possessing the waxy lustre and the yellowish colour of natural vanadinite, and having a specific gravity of 6 7 (Roscoe)

Lead Pyrovanadate, $Pb_2V_2O_7$, is found in South America as descloizite in rhombic crystals, which have an orange-green or black colour, a bronze lustre, and a specific gravity of 5 839 It usually contains zinc, iron, manganese, and copper as impurities If a solution of sodium pyrovanadate be precipitated with lead acetate, the basic salt, $Pb_5V_4O_{16}$, is thrown down as a light-yellow precipitate

Lead Metavanadate, $(Pb(VO_3)_2$, is obtained as a yellow precipitate when a solution of a metavanadate is mixed with one of lead acetate. The mineral dechemte consists chiefly of this compound, a portion of the lead, however, being usually replaced by zinc It occurs together with lead ores, forming yellow,

brown, or deep-red reniform masses, having a specific gravity of 5 6 to 5 8

Lead Tetravanadate, $Pb_2V_4O_{11}$, is obtained by precipitating the corresponding potassium salt with lead nitrate in the form of a reddish-yellow precipitate slightly soluble in water

Copper Orthovanadate, $Cu_3(VO_4)_2,H_2O$; occurs as the mineral volborthite, in which a part of the copper is replaced by calcium, it crystallises in small yellow or green hexagonal tablets having a specific gravity of 3 55, and is found in Thurmgia and in the Urals *Copper Pyrovanadate,* $Cu_2V_2O_7$) is a yellow, crystalline precipitate, whilst *copper melavanadate* is an apple-green precipitate

Silver Orthovanadate, Ag_3VO_4, is obtained by precipitating a freshly prepared solution of the sodium salt with silver nitrate It is a deep orange-red coloured precipitate, which is easily soluble in nitric acid and in ammoma

Silver Pyrovanadate, $Ag_3V_2O_7$, is a heavy, yellow powder

Silver Metavanadate, $AgVO_3$, forms a pale yellow, gelatinous precipitate

Vanadic acid, like phosphoric acid, yields complex compounds with stannates,[1] tungstates, and molybdates, as well as with phosphates and arsenates[2]

Pervanadic Acid and the Pervanadates—The alkali meta-vanadates are readily converted by hydrogen peroxide into per-salts of the formula B/VO_4, many of which have been prepared pure They are decomposed by dilute acids with evolution of one atomic proportion of oxygen[3]

Pervanadic Acid, HVO_4, is foimed when vanadium pentoxide is added to hydrogen peroxide in dilute sulphuric acid solution A deep-red coloured liquid is formed,[4] which deposits unstable yellow crystals of the per-acid[5]

Potassium Pervanadate, KVO_4, is a yellow, microcrystalline precipitate, obtained by dissolving potassium metavanadate in a solution of hydrogen peroxide containing sulphuric acid, and precipitating with alcohol

Barium Metapervanadate, $Ba(VO_4)_2$, is obtained as an amor-

[1] Prandtl, *Ber,* 19O7, 40, 2125

[2] For an account of these complex derivatives, see the monograph by Ephraim quoted on p 944

[3] Scheuer, *Zett anorg Chem,* 1898, 16, 284, PiSsarjewsky, *J Buss Phys Chem Soc* , 1902, 34, 210, 472 See also Auger, *Compt rend* , 1921,**172,** 1355

[4] Werther, *J pr. Chem,* 1861, 83, 195

[5] Pwsarjewsky, *Zett physikal Chem,* 1903, 43, 173

phous, yellow precipitate, when a solution of barium chloride is added to a saturated solution of ammonium metavanadate in 30 per cent hydrogen peroxide Other salts have been prepared in a similar manner, they are characterised by being bright yellow or deep orange

More complex compounds are formed by the action of alkalis and hydrogen peroxide on the pervanadates, and these are probably salts of a pyropervanadic acid with the peroxides of the alkali metals The ammomum salt, $(NH_4)_4O_{11}$, and the potassium salt, $K_8V_5O_{26},2H_2O$, have been prepared in this way [1] Complex oxygenated products have also been obtained by the action of hydrogen peroxide on the compound of vanadyl trifluoride with potassium fluoride,[2] $VOF_3,2KF$

THE LOWER OXIDES OF VANADIUM

420 *Vanadium Suboxide*, V_2O, is formed by the prolonged exposure of finely divided metallic vanadium to the air It is a brown substance, which, when heated in the air, is gradually converted into the higher oxides No salts of this oxide have been prepared

Vanadium Monoxide or *Hypovanadious Oxide*, VO or V_2O_2 —In its power of uniting with oxygen vanadium surpasses even uranium,[3] and, like uramum, it can be separated from its last portions of oxygen only with extreme difficulty The oxide VO is, moreover, found to enter as a radicle into many compounds, so that the name vanadyl (VO) may appropriately be given to it This substance, which was regarded by Berzelius as metallic vanadium, may be prepared by reducing the higher oxides with potassium, or by passing the vapour of vanadyl trichloride, VOCI3, mixed with excess of hydrogen, through a combustion tube containing red-hot carbon [4] Thus obtained it forms a light-grey, glistening powder or a lustrous, metal-like crust, having a specific gravity of 3 64 It is brittle, difficultly fusible, and CQnducts electricity Heated to redness, it takes fire in the air and burns to the sesquioxide, V_2O_3, whilst when heated in chlorine the oxytnchlonde, $VOCl_3$, is formed It is insoluble in water, but dissolves in acids, yielding the corresponding salts These may

[1] Mehkoff and Pissarjewsky, *Zeit anorg Chem*, 1899, **1O,** 405, Pissar jewsky, *ibid*, 1903, 82, 341

[2] Mehkoff and Kasanezky, *Zed anorg Chem* , 1901, 28, 242

[3] Peligot, *Ann Chim Phys* , 1842, [3], 5, 5, 1844 [3], 12, 549

[4] Schafank, *Annalen*, 1859, **109,** 85

The oxide may likewise be prepared by the electrolysis of the fused pentoxide, or by the ignition of the oxychlonde, $V_2O_2O1_4,5H_2O$, in a current of carbon dioxide.

$$V_2O_2C1_4 + 5H_2O = 2VO_2 + 4Cl + 3H_2O$$

Divanadyl Hydroxide or *Hypovanadic Hydrate,* $V_2O_4,7H_2O$ or $V_2O_2(OH)_4,5H_2O$, forms a greyish-white precipitate, obtained when a solution of vanadyl sulphate or chloride is cautiously precipitated with a cold solution of sodium carbonate When dried it is a black, amorphous mass, having a glassy fracture This on heating to 1O0° loses four molecules of water, leaving the hydrate, $V_2O_4,3H_2O$ A hydrate contaimng $2H_2O$ is obtained as a pink, crystalline powder by boiling a solution of the dioxide, VO_2, in sulphurous acid [1] Vanadium dioxide acts both as a basic, and as an acid-forming oxide When dissolved in acids the vanadyl salts are formed,[2] whilst with alkalis the vanadites or hypovanadates are produced

The *vanadites* or *hypovanadates* are all insoluble except those of the alkali metals, which are not derived from the normal hypovanadic acid, $H_4V_2O_6$, but from the partial anhydrides, $H_2V_2O_5$ and $H_2V_4O_9$ The alkali vanadites are obtained by adding an excess of caustic alkali to a concentrated solution of vanadyl sulphate or chloride [3] The dark-brown solution thus obtained with potash deposits *potassium vanadite,* $K_2V_4O_9,7H_2O$, in reddish-brown, crystalline scales which, after washing first with potash solution, and then with alcohol, may be dried between filter-paper This salt is permanent in the air, and very soluble in water, yielding a dark brown solution

Sodium Vanadite, $Na_2V_4O_9,7H_2O$, is prepared in a similar way to the potassium salt, and exhibits analogous properties

Ammonium Vanadite, $(NH_4)_2V_4O_9,3H_2O$, is obtained as a dark-brown, crystalline precipitate by adding a vanadyl sulphate solution to ammoma, it dissolves in water, yielding an almost black solution (Crow)

VANADIUM AND FLUORINE

421 The oxides, V_2O_3, VO_2, and V_2O_5, all dissolve in hydrofluoric acid, but only the tnfluoride, $VF_3,3H_2O$, and the oxydifluonde, VOF_2, have been isolated A very large number of

[1] **Gain,** ***Compt rend,*** **1906, 143, 823**
[2] **Guyard,** ***Bull Soc chim*** **, 1876, [2], 25, 350**
[3] **See also Koppel and Goldmann,** ***Zat anorg Chem,*** **1903, 36, 281**

Vanadium Sesquioxide or *Vanadium Trioxide,* V_2O_s, is obtained by heating the pentoxide in hydrogen, or by igniting the same oxide in a carbon crucible It is also formed when vanadyl trichloride and hydrogen are passed through a red-hot tube, and when the pentoxide is heated in the oxy-hydrogen flame [1] It is a black powder which under pressure forms a coherent mass which conducts electricity It oxidises when exposed to the air, not only being pyrophoric when warm, but also slowly taking up oxygen when exposed in the air at ordinary temperatures, and being converted into small dark indigo-coloured crystals of the dioxide VO_2 It has a specific gravity of 4 7 When lgmted

in chlorine

VOCI3, and vanadium pentoxide

$$3V_2O_3 + 6Cl_2 = V_aO_6 + 4VOCl_3$$

It is insoluble in most acids, but the corresponding sulphate may be obtained *in.* solution by the reducing action of nascent hydrogen, evolved from metallic magnesium, on a solution of vanadium pentoxide in sulphuric acid A green liquid is thus obtamed, the further reduction observed with zinc, cadmium, and sodium amalgam not taking place with magnesium The green solution may likewise be obtained by the partial oxidation of the lavender-coloured solution of vanadious sulphate, VSO_4 If a current of air be passed through such a solution, in which the free acid has been neutralised by an excess of zmc and the remaimng metallic zinc removed, the liquid attains a permanent brown colour, which with a few drops of acid turns green, the solution then contains the sesquisulphate

Vanadium Dioxide or *Hypovanadic Oxide,* VO_2 or V_2O_4 —This oxide can be prepared either by the oxidation of the monoxide, VO, in the air, or by the partial reduction of the pentoxide It is readily converted by potassium permanganate into the pentoxide, and advantage is taken of this fact in the volumetric estimation of vanadium It is a lustrous, steel-coloured powder and dissolves in acids, forming solutions of the vanadyl salts, which possess a bright blue colour Solutions of these salts are also produced by the action of moderate reducing agents, such as sulphur dioxide and sulphuretted hydrogen or oxalic acid, upon solutions of vanadic acid in sulphuric acid. They may also be obtained by passing a current of air through acid solutions of the vanadious salts until a permanent blue colour is attained

[1] **Read,** ***Journ Chem Soc,*** **1894, 66, 314**

The oxide may likewise be prepared by the electrolysis of the fused pentoxide, or by the ignitidn of the oxychlonde, $V_2O_2O1_4,5H_2O$, in a current of carbon dioxide.

$$V_2O_2C1_4 + 5H_2O = 2VO_2 + mCl + 3H_2O$$

Divanadyl Hydroxide or *Hypovanadic Hydrate,* $V_2O_4,7H_2O$ or $V_2O_2(OH)_4,5H_2O$, forms a greyish-white precipitate, obtained when a solution of vanadyl sulphate or chloride is cautiously precipitated with a cold solution of sodium carbonate When dried it is a black, amorphous mass, having a glassy fracture This on heating to 100° loses four molecules of water, leaving the hydrate, $V_2O_4,3H_2O$ A hydrate contaimng $2H_2O$ is obtained as a pmk, crystalline powder by boiling a solution of the dioxide, VO_2, in sulphurous acid [x] Vanadium dioxide acts both as a basic, and as an acid-forming oxide When dissolved in acids the vanadyl salts are formed,[2] whilst with alkalis the vanadites or hypovanadates are produced

The *vanadites* or *hypovanadates* are all insoluble except those of the alkali metals, which are not derived from the normal hypovanadic acid, $H_4V_2O_6$, but from the partial anhydrides, $H_2V_2O_5$ and $H_2V_4O_9$ The alkali vanadites are obtained by adding an excess of caustic alkali to a concentrated solution of vanadyl sulphate or chloride [3] The dark-brown solution thus obtained with potash deposits *potassium vanadite,* $K_2V_4O_9,7H_2O$, in reddish-brown, crystalline scales which, after washing first with potash solution, and then with alcohol, may be dried between filter-paper This salt is permanent in the air, and very soluble in water, yielding a dark brown solution

Sodium Vanadite, $Na_2V_4O_9,7H_2O$, is prepared in a similar way to the potassium salt, and exhibits analogous properties

Ammonium Vanadite, $(NH_4)_2V_4O_9,3H_2O$, is obtained as a dark-brown, crystalline precipitate by adding a vanadyl sulphate solution to ammoma, it dissolves in water, yielding an almost black solution (Crow)

VANADIUM AND FLUORINE

421 The oxides, V_2O_3, VO_2, and V_2O_5, all dissolve in hydrofluoric acid, but only the tnfluoride, $VF_3,3H_2O$, and the oxydifluonde, VOF_2, have been isolated A very large number of

[1] **Gain,** *Compt rend,* **19O6, 143, 823**
[2] **Guyard,** *Bull Soc chim* **, 187b, [2], 25, 350**
[3] **See also Koppel and Goldmann,** *Zat anorg Chem,* **1903, 36, 281**

double salts of these compounds and of the oxyfluorides VO_2F and VOF_3 with hydrofluoric acid, metallic fluorides, and vanadium pentoxide have been described [x] Only a few of the most characteristic are mentioned here

Vanadium Tnfluoride, $VF_3,3H_2O$, crystallises from the dark green solution of vanadium tnoxide in hydrofluoric acid, in dark green, readily soluble octahedra The *double potassium salt,* $2KF,VF_3,H_2O$, is a bright green, crystalline powder, which is precipitated when a solution of potassium fluoride is added to one of vanadium trifluoride

Vanadium Oxydifluoride, VOF_2, is formed when the tetroxide is dissolved in hydrofluoric acid, and separates in blue, prismatic crystals containing water Several double salts with the fluorides of sodium, potassium, and ammonium may be prepared by adding solutions of these fluorides to the blue solution of the oxydifluonde (Petersen)

Potassium Vanadium Dioxyfluonde, $2KF,VO_2F$, is obtained by evaporating a solution o vanadium pentoxide in hydrofluoric acid almost to dryness, and adding it to potassium fluoride It crystallises in golden-yellow, six-sided prisms

Vanadium pentoxide also dissolves easily in a solution of hydrogen potassium fluoride with evolution of heat, and on cooling yellowish globular masses separate out consisting of pearly, probably hexagonal crystals, which have the composition $3KF,2VO_2F,H_2O$

Ammonium Vanadium Dioxyfluonde, $3NH_4F,VO_2F$, is formed when a solution of vanadium pentoxide in hydrofluonc acid is nearly neutralised with ammoma, it separates in large, golden-yellow crystals

Zinc Vanadium Dioxyfluonde, $ZnF_2,VO_2F,7H_2O$, is formed by dissolving zinc carbonate and vanadium pentoxide in hydrofluoric acid The salt crystallises in hard, yellow, tnclinic prisms

VANADIUM AND CHLORINE

The following chlorides and oxychlondes of vanadium are known

CHLORIDES

Vanadium	tetrachloride	$VC1_4$
„	trichloride	$VC1_3$ or V_2C1_6
	dichloride	$VC1_2$ or V_2C1_4

[1] Peterson, *J pr Chem,* 1889, [2], 40, 193, 271 See also Piccini and Giorgis, *Journ Chem Soc,* 1889, 56, 214, and Baker, *Journ Chem Soc,* 1878, 33, 388

The oxide may likewise be prepared by the electrolysis of the fused pentojpde, or by the ignitidn of the oxychlonde, $V_2O_2C1_4,5H_2O$, in a current of carbon dioxide

$$V_2O_2C1_4 + 5H_2O = 2VO_2 + 4HC1 + 3H_2O$$

Divanadyl Hydroxide or *Hypovanadic Hydrate,* $V_2O_4,7H_2O$ or $V_2O_2(OH)_4,5H_2O$, forms a greyish-white precipitate, obtained when a solution of vanadyl sulphate or chloride is cautiously precipitated with a cold solution of sodium carbonate When dried it is a black, amorphous mass, having a glassy fracture This on heating to 100° loses four molecules of water, leaving the hydrate, $V_2O_4,3H_2O$ A hydrate contaimng $2H_2O$ is obtained as a pink, crystalline powder by boiling a solution of the dioxide, VO_2, in sulphurous acid[x] Vanadium dioxide acts both as a basic, and as an acid-forming oxide When dissolved in acids the vanadyl salts are formed,[2] whilst with alkalis the vanadites or hypovanadates are produced

The *vanadites* or *hypovanadates* are all insoluble except those of the alkali metals, which aie not derived from the normal hypovanadic acid, $H_4V_2O_6$, but from the partial anhydrides, $H_2V_2O_5$ and $H_2V_4O_9$ The alkali vanadites are obtained by adding an excess of caustic alkali to a concentrated solution of vanadyl sulphate or chloride[3] The dark-brown solution thus obtained with potash deposits *potassium vanadite,* $K_2V_4O_9,7H_2O$, in reddish-brown, crystalline scales which, after washing first with potash solution, and then with alcohol, may be dried between filter-paper This salt is permanent in the air, and very soluble in water, yielding a dark brown solution

Sodium Vanadite, $Na_2V_4O_9,7H_2O$, is prepared in a similar way to the potassium salt, and exhibits analogous properties

Ammonium Vanadite, $(NH_4)_2V_4O_9,3H_2O$, is obtained as a dark-brown, crystalline precipitate by adding a vanadyl sulphate solution to ammoma, it dissolves in water, yielding an almost black solution (Crow)

VANADIUM AND FLUORINE

421 The oxides, V_2O_3, VO_2, and V_2O_6, all dissolve in hydrofluoric acid, but only the trifluonde, $VF_3,3H_2O$, and the oxydifluonde, VOF_2, have been isolated A very large number of

[1] **Gain, *Compt rend,* 19O6, 143, 823**
[2] **Guyard, *Bull Soc chim,* 1876, [2], 25, 350**
[3] **See also Koppel and Goldmann, *Zeit anorg CJiem,* 1903, 36, 281**

double salts of these compounds and of the oxyfluondes VO_2F and VOF_3 with hydrofluoric acid, metallic fluorides, and vanadium pentoxide have been described[x] Only a few of the most characteristic are mentioned here

Vanadium Trifluonde, $VF_3,3H_2O$, crystallises from the dark green solution of vanadium trioxide in hydrofluoric acid, in dark green, readily soluble octahedra The *double potassium salt,* $2KF,VF_3,H_2O$, is a bright green, crystalline powder, which is precipitated when a solution of potassium fluoride is added to one of vanadium trifluonde

Vanadium Oxydifluoride, VOF_2, is formed when the tetroxide is dissolved in hydrofluoric acid, and separates in blue, prismatic crystals contaimng water Several double salts with the fluorides of sodium, potassium, and ammonium may be prepared by adding solutions of these fluorides to the blue solution of the oxydifluoride (Petersen)

Potassium Vanadium Dioxyfluoride, $2KF,VO_2F$, is obtained by evaporating a solution o[e] vanadium pentoxide in hydrofluoric acid almost to dryness, and adding it to potassium fluoride It crystallises in golden-yellow, six-sided prisms

Vanadium pentoxide also dissolves easily in a solution of hydrogen potassium fluoride with evolution of heat, and on cooling yellowish globular masses separate out consisting of pearly, probably hexagonal crystals, which have the composition $3KF,2VO_2F,H_2O$

Ammonium Vanadium Dioxyfluoride, $3NH_4F,VO_2F$, is formed when a solution of vanadium pentoxide in hydrofluoric acid is nearly neutralised with ammonia, it separates in large, golden-yellow crystals

Zinc Vanadium Dioxyfluoride, $ZnF_2,VO_2F,7H_2O$, is formed by dissolving zinc carbonate and vanadium pentoxide in hydrofluoric acid The salt crystallises in hard, yellow, triclinic prisms

VANADIUM AND CHLORINE

The following chlorides and oxychlorides of vanadium are known

CHLORIDES

Vanadium	tetrachloride	$VC1_4$
„	trichloride	$VC1_3$ or V_2C1_6
	dichloride	$VC1_2$ or V_2C1_4

[1] **Peterson, *J pr Chem,* 1889,- [2], 40, 193, 271 See also Piccini and Giorgis, *Journ Chem Soc,* 1889, 56, 214, and Baker, *Journ Chem Soc,* 1878, 33, 388**

» OXYCHLORIDES

Vanadium oxytrichlonde .	$VOCl_a$
„ oxydichloride	$VOC1_2$
„ oxymonochloride	VOC1
Divanadyl monochlonde	v_2o_2ci
„ tetrachloride	$V_2O_2C1_{4>}5H_2O$
Divanadium tnoxydichloride	v,o,ca«,4H,o

Vanadium Tetrachloride, $VC1_4$, is formed when metallic vanadium or the monomtnde is heated to redness in an excess of chlorine It may be prepared by repeatedly passing the vapour of vanadium oxytrichlonde, together with an excess of dry chlorine, over a long column of pure sugar-charcoal heated to dull redness, also, by treating the crude vanadium, prepared as already described by the aid of aluminium, with chlorine and removing the oxytrichlonde, which is also formed, by fractional distillation ,* or by heating ferrovanadium in chlorine [2] Vanadium tetrachloride is a dark browmsh-red, thickish liquid, which evolves white fumes when exposed to moist air It boils at 154° with partial decomposition, losing chlorine and leaving a residue of the trichloride This decomposition takes place also at the ordinary temperature, especially on exposure to light It does not solidify at —18°, its specific gravity at 0° is 1 8584, and its vapour density at 205° is 6 69, the calculated vapour density being 6 675 When thrown into water the tetrachloride is at once decomposed, yielding a blue solution of vanadyl chloride It is soluble in carbon tetrachloride

Vanadium Trichloride, $VC1_3$ —The foregoing compound easily decomposes, as has been stated, into this body and chlorine The trichloride is obtained either by the slow decomposition of the tetrachloride at the ordinary temperature or at its boiling point, or, together with the dichloride, when the vapour of the tetrachloride mixed with hydrogen is passed through a red hot tube, as well as when the tnsulphide is heated in chlorine [3] It crystallises in fine peach-blossom coloured, shining tablets of density 3 0, closely resembling in appearance the crystals of chromium trichloride. It is non-volatile when heated in hydrogen, which reduces it to the dichloride, and decomposes to the pentoxide when heated in the air It is extremely hygroscopic, instantly deliquescing on exposure to moist air to a dark brown

[1] **Koppe), Goldmann and Kaufmann,** ***Zeit anorg Chem*** **, 1905, 45, 345**
[2] **Mertes,** ***J Amer Chem Soc*** **, 1913, 36, 071**
[9] **Halberstadt,** ***Ber,*** **1S82,15, 1619**

liquid, which on addition of **a** drop of hydrochloric acid becomes green It readily dissolves in absolute alcohol and in ether, forming green-coloured solutions

A hydrated compound of the composition $VC1_3,6H_2O$ can be obtained as a green, crystalline powder by evaporating *in vacuo* a solution of vanadium sesquioxide in hydrochloric acid,[1] or by dissolving vanadium pentoxide in hydrochloric acid, reducing the solution electrolytically with a platinum cathode, and saturating the green solution with hydrochloric acid[2] The salt decomposes when heated before all the water has been driven off The aqueous solution rapidly oxidises in the air Sparingly soluble double salts are formed with the chlorides of the alkali metals,[8] the potassium salt having the formula $VC1_3,2KC1,H_2O$

Vanadium Bichloride or *Vanadious Chloride,* $VC1_2$ —This is a solid body, crystallising in fine apple-green coloured plates, having a micaceous lustre and a hexagonal form It is prepared by passing vanadium tetrachloride, mixed with dry and pure hydrogen, through a glass tube heated to dull redness, and is also formed together with silicon tetrachloride when vanadium silicide, VSi_2, is heated in chlorine[4] Its specific gravity at 18° is 3 23 It is very deliquescent, yielding a lavender-coloured solution of vanadium dichloride, which possesses bleaching properties (p 958) A violet solution contaimng the chloride can be obtained by the electrolytic reduction of the trichloride When it is evaporated or when hydrochloric acid is added, hydrogen is evolved and the trichloride is formed, the reaction being extremely vigorous when a piece of platinum foil is placed in the acid liquid Vanadious chloride is therefore a more vigorous reducing agent than chromous chloride[5]

Vanadium Oxytrichloride or *Vanadyl Trichloride,* $VOCl_3$ —This compound, corresponding to phosphorus oxychlonde, is obtained either by the action of chlorine on the oxides VO and V_2O_3 as already described, or by heating a mixture of the pentoxide and charcoal in a current of chlorine

$$V_2O_5 + 3C + 3C1_2 = 2VOC1_3 + 3CO$$

In the latter case, the resulting liquid is red-coloured from the presence of tetrachloride, and is best purified by rectification

[x] **Locke and Edwards,** ***Amer Chem J,*** **1898, 20, 594**
[2] **Piccini and Bnzzi,** ***Zeit anorg Chem,*** **1899,19, 394**
[8] **Stahler,** ***Ber,*** **1904, 37, 4411**
[4] **Moissan and Holt,** ***Compt rend,*** **1902,136, 78**
[8] **Piccun and Marino,** ***Zett anorg Chem,*** **1902, 38, 68**

over clean sodium in a current of carbon dioxide It is also formed [1] when dry hydrogen chloride is passed over a mixture of vanadic and phosphoric anhydrides at 60—80°, and a solution in acetic acid may be obtained by treating vanadium pentoxide with a solution of hydrogen chloride in glacial acetic acid[2] Vanadyl trichloride is a bright lemon-yellow, mobile liquid, boiling at 126 7° and having a specific gravity at 14° of 1 841 It does not solidify at —15° The specific gravity of its vapour is 6 108 at 186°, the calculated specific gravity being 6 003

On exposure to most air vanadyl trichloride emits vapours of a cinnabar-red colour, and is soon decomposed in the presence of moisture into vanadic and hydrochloric acids When a small quantity of water is added it becomes thick and blood-red coloured owing to the formation of vanadic acid A large quantity of water, however, yields a clear yellow solution[3] When the oxychlonde is igmted in a current of dry ammonia gas, vanadium mononitride is obtained Vanadium oxychlonde combines with ether at 70°, forming a compound crystallising in long, red needles and having the composition $VC1_3(0C_2H_5)_2$ [4]

When vanadium oxychlonde is heated with zinc to 400°, vanadium dioxide and *vanadyl dichloride*, $VOCl_2$, are formed, the latter crystallises in green tablets which deliquesce on exposure to moist air The same compound is formed when the vapour of vanadyl trichloride and hydrogen are passed through a red hot tube In this case *vanadyl monochlonde*, VOC1, and *duanadyl monochlonde*, V_20_2C1, are likewise formed, the former as a flocculent, brown powder insoluble in water, and the latter in the form of a yellow, crystalline powder resembling mosaic gold The molecular formulae of these bodies are not known Vanadyl dichloride forms double compounds with two or four molecules of the hydrochlorides of pyridine and qumolme [5]

Duanadyl Tetrachloride, $V_20_2C1_4,5H_20$ or $V0C1_2,2\ 5H_20$ When vanadium pentoxide is dissolved in hot concentrated hydrochloric acid, chlorine is evolved and a green solution is obtained which becomes blue with deposition of sulphur when sulphuretted hydrogen is passed through the liquid A brown, amorphous, deliquescent mass is obtained on evaporation, possess-

[1] **Ephraim, *Zeit anorg Chem*, 1903, 36, 06**
[2] **Koppel and Kaufmann, *Zeit anorg Chem* , 1905, 45, 352**
[3] **See Agafonoff, *J Russ Phys Chem Soc*, 1903, 35, 649**
[4] **Bedson, *Journ Chem Soc*, 1876, l, 309**
[5] **Koppel, Goldmann and Kaufmann, *Zed anorg Chem* , 1905, 45, 345**

ing the above composition It dissolves in water, yielding a blue solution, but when treated with strong hydrochloric acid or alcohol the solution is brown, and this change may possibly be due to the existence of two different hydrates [1]

A compound of the formula $V_2O_3C1_2,4H_20$ has also been obtained as a dark green, deliquescent mass, by the action of hydrochloric acid on vanadium pentoxide [2]

VANADIUM AND BROMINE AND IODINE

423 *Vanadium Tribromide,* VBr_3—This is the only known compound of the above elements It condenses as a greyish-black, compact, amorphous sublimate when dry bromine vapour is passed in excess over vanadium nitride or over a mixture of vanadium trioxide and charcoal heated to redness It is a very unstable compound losing bromine even at the ordinary temperature in dry air, and deliquescing rapidly in moist air

The hydrated bromide, $VBr_3,6H_20$, and the corresponding iodide can be prepared in a similar manner to the hydrated chloride, which they closely resemble

Vanadyl Tnbrormde, $VOBr_3$, obtamed by passing dry bromine vapour over vanadium sesquioxide heated to redness, is a dark red, transparent liquid, having a density of 2 967 at 0° It may be distilled under diminished pressure, passing over without decomposition at a temperature of about 130° under a pressure of 100 mm When heated under the ordinary atinospheric pressure it suddenly solidifies at 180°, decomposing into free bromine and *vanadyl dibromide,* $VOBr_2$, which is a brownish-yellow powder,

Divanadyl Tetra-iodtde, $V_20_2I_4,8H_20$, is formed by the action of hydnodic acid on the pentoxide as a dark, deliquescent mass.[3]

VANADIUM AND SULPHUR

424 The sulphides of vanadium correspond to the oxides [4]

Vanadium Monosuljphide, VS, is formed when the sesquisulphide is strongly heated in a current of hydrogen It forms a brownish-black powder or glistening brown scales, soluble slowly in dilute, quickly in strong nitric acid It dissolves in alkali hydrosulphides, yielding a violet solution

Vanadium Sesquisulphide or *Tnsuljphide,* V_2S_3 —This was the

[1] Crow, *Journ Chem Soc* , 1876, 11, 453.
[2] Ditte, *Compt rend,* 1886,**102,** 1310
[3] *Ibid*
[4] Kay, *Journ Chem Soc,* 1880, 37, 728

only vanadi#i£ salt free from oxygen prepared by Berzehus He obtained it by hewing the sesquioxide in a current of sulphuretted hydrogen It can in like manner be prepared from the pentoxide, the oxychlonde, or any of the chlorides, but it is best obtained by acting on the ignited pentoxide with carbon disulphide vapour It is a greenish-black powder possessing properties similar to those of the monosulphide, VS

Vanadium Pentasulphide, V_2S_5, is formed by heating the foregoing with sulphur to 400° It is a black powder which on heating in a current of carbon dioxide yields sulphur and the sesquioxide (Kay)

Ammonium Thiovanadate, $(NH_4)_3VS_4$, is obtained by passing sulphuretted hydrogen into a cooled solution of ammonium metavanadate in ammonia of specific gravity 0 898 The crystals resemble those of potassium permanganate If weaker ammoma be employed, *ammonium hexasulphopyrovanadate,* $(NH_4)_4V_2S_60$, is formed in dark green crystals

Several similar sodium and potassium salts have been prepared from the corresponding meta- and pyro-vanadates [1]

Vanadyl or *Hypovanadic Sulphite,* $6V0_2,4S0_2,9HO$, is prepared by reducing barium vanadate with sulphur dioxide, and filtering from the barium sulphate

$$Ba(V0_3)_2 + H_2S0_3 = BaS0_4 + H_20 + 2V0_2$$

When the filtrate is evaporated in an atinosphere of sulphur dioxide, the sulphite separates as a dark blue, crystalline powder, which spontaneously decomposes It forms two series of double salts with the alkali sulphites [2]

Vanadious Sulphate, $VS0_4,7H_20$, can be prepared by the electrolytic reduction of the blue solution obtained by the action of sulphur dioxide on vanadic anhydride in the presence of sulphuric acid In order to obtain this salt in the pure state the greatest precautions must be taken to exclude oxygen The blue solution gradually becomes green, then blue again, and finally violet as the reduction proceeds It is then evaporated *%n vacuo,* and the crystals are separated and dried with filter paper in an atinosphere of carbon dioxide The salt is thus obtained

in reddish-violet, monocknic crystals, which become bluish-violet

[1] Kruss and Ohnmais, *Annalen,* 1891, **263,** 39, Kruss, *Zeit anorg Chem,* 1893,3, 264, Locke, *Amer Chem J,* 1898, **20,** 373

[2] Koppel and Berendt, *Zeit anorg Chem,* 1903, **36,** 154, Gain, *Compt, rend,* **1907,144> 1157.**

on drying and are very soluble in water, yielding a pure violet-coloured solution, which becomes bluish-violet in the presence of the slightest trace of oxygen The solution at once reduces copper salts to metallic copper, the reaction proceeding quantitatively thus

$$2VSO_4 + CuSO_4 = V_2(SO_4)_3 + Cu$$

The salts of silver, tin, gold, platinum, and mercury are also reduced to the metal

Vanadious sulphate appears to be isomorphous with ferrous sulphate, $FeSO_4,7H_2O$, and mixed crystals have been obtained both with ferrous sulphate and with magnesium sulphate It readily forms double salts of the type $R^{I}_2SO_4,R^{II}SO_4,6H_2O$ with the alkali sulphates These can be prepared by adding the proper sulphate to the liquid to be reduced and crystallising, etc , as in the preparation of the pure sulphate The *ammonium*, salt, $(NH_4)_2,SO_4,VSO_4,6H_2O$, forms reddish-violet, monochnic crystals and is less easily oxidised than the pure sulphate, and the potassium and rubidium salts closely resemble it [1]

Vanadium Sesquisulphate, $V_2(SO_4)_3$—When the blue solution of vanadyl sulphate, prepared from 100 grams of vanadic anhydride, 200 c c of water, and 100 c c of concentrated sulphuric acid, is reduced electrolytically until the vanadium is present in the trivalent form, the compound $V_2(SO_4)_3,H_2SO_4,12H_2O$, known as *vanadium sesquisulphate sulphuric acid*, separates out as a green, crystalline powder It readily forms a salt when evaporated with ammomum sulphate, green crystals separating out of the composition $V_2(SO_4)_3,(NH_4)_2SO_4,12H_2O$

When the acid salt is dissolved in a little water, sulphuric acid added, and the mass heated at 180° in a current of carbon dioxide, the anhydrous sulphate separates out as a microcrystalhne, yellow powder which is insoluble in water [2] These compounds have a very close resemblance to the corresponding derivatives of titanium sesquioxide (p, 835) A solution of the sulphate acts as a vigorous reducing agent, and precipitates the metal from an acid solution of copper sulphate (Rutter)

Vanadium Alums—Several alums have been prepared by treating a metavanadate with sulphurous acid in the presence of sulphuric acid, and then reducing electrolytically *Ammonium*

[1] **Piccini, *Zett anorg Chem* , 1899,19, 204, Picomi and Marino, *Zett anorg Chem* 1902, 32, 55, Marino, *Zett anorg Chem*, 1906, 50, 49, Rutter, *Zett Elehtrochem*, 1906,12, 230, *Zeit anorg Chem*, 1907, 62, 368**

[2] **Stahler and Weithwein, *Ber*, 1905, 38, 3978,**

vanadium alum, $(NH_4)_2S0_4,V_2(804)3,241120$, crystallises in hemihedral forms of the regular system and is violet-coloured Alums containing potassium, rubidium, caesium, and thallium have also been prepared[1] A good yield of the alum is obtained by the electrolysis of ammonium metavanadate The ammomum metavanadate is placed in a porous cell with 50 per cent sulphuric acid, a lead cathode being employed The electrolysis is continued until the solution becomes green, when on standing ammomum vanadium alum crystallises out[2]

The Vanadyl or Hypovanadic Sulphates—The blue solution obtained by the action of sulphur dioxide on a suspension of vanadic anhydride in dilute sulphuric acid contains sulphates of the radical $V_20_2^{IV}$ or VO^{TT} These were termed hypovanadic sulphates by Roscoe, but are now generally known as the vanadyl sulphates From all solutions in which the molecular ratio H_2S0_4 $V0_2$ is greater than 15 1, acid sulphates are obtained up to a temperature of about 201 5°, from solutions in which the ratio is less than this normal salts are obtained, and these are also formed by heating the acid sulphates to about 260°, or by treating them with water or alcohol At the boiling point of sulphuric acid oxidation occurs, vanadic anhydride and sulphur dioxide being formed (Koppel and Behrendt)

Vanadyl Sulphate, $V_20_2(S0_4)_2$, is deposited as an insoluble, blue, sandy powder by dissolving the dioxide, $V0_2$, in excess of sulphuric acid and heating the solution for some time to 260° [3] If the dioxide be dissolved in sulphuric acid, the solution evaporated, and the residue treated with absolute alcohol, a sky-blue powder remains, which is a soluble form of the sulphate and deliquesces in moist air This is also formed by heating the insoluble form with water at 130°. If the solution be allowed to evaporate spontaneously over sulphuric acid, fine, blue, rhombic prisms having the composition $V_20_2(S0_4)_2,4H_20$ are deposited (Berzelms) In addition to this, hydrates with 13, 10, 7, 3, and 2 molecules of water have been described

When the acid solution containing more than 1 5 molecular proportions of sulphuric acid is evaporated, various hydrates of the *acid salt*, $(V_20_2)H_2(S0_4)_3$ are obtained The hydrate with

[1] Piccim, *Zeit anorg Chem*, 1896, 11, 106, *Chem Centr*, 1897, 1, 223, Bultemann, *Zeit Elektrochem*, 1904, 9, 141

[2] Renschler, *Zeit ElecTctrochem*, 1912,18, 137

[3] Gerland, *Ber*, 1877, 10, 2109, Koppel and Behrendt, *Zeit anorg Chem*, 1903, 36, 154

$5H_20$ is prepared by evaporating the solution on the water-bath, and washing the dried' crystals with ether '(Crow), at 125° the hydrate with $3H_20$ is formed, and this can also be obtained by precipitating a concentrated solution of any of the vanadyl sulphates with concentrated sulphuric acid At 150° the dihydrate is formed, at 175° a salt with 0 5 molecule of water, and at 190° the *anhydrous compound,* $2V0_2,3S0_3$, which is a green powder, consisting of microscopic tetragonal tablets, and is sparingly soluble in water (Koppel and Behrendt) [1]

Many double salts also of this series are known and are described in the memoirs cited above

Normal Divanadyl Tnsulphate, $(VO)_2(S0_4)_3$, is obtained, according to Berzelius, by dissolving the pentoxide in hot sulphuric acid which has been diluted with half its weight of water [2] On evaporating at a low temperature the salt crystallises out in reddish-brown, very deliquescent scales The same compound is obtained in ruby-red octahedra by boiling the pentoxide with an excess of sulphuric acid When these are heated to the melting point of lead, the basic salt, $(VO)_20(S0_4)_2$, remains as a red mass with small, bright, crystalline faces

If the pentoxide be dissolved in concentrated sulphuric acid and the solution evaporated, the basic salt, $VO(OH)S0_4$, is formed[3] as a sandy, reddish-yellow powder According to Gerland, this is identical with the preceding compound

When potassium vanadate is dissolved in strong sulphuric acid and the excess of acid driven off by heat, the double salt, $K_2S0_4,(VO)_2(S0_4)_3$, is obtained as a yellow, crystalline powder, (Berzekus)

VANADIUM AND NITROGEN, PHOSPHORUS, AND ARSENIC

425 *Vanadium Monomtnde,* VN —The mononitride is obtained by strongly igniting the ammomo-oxychlonde in a current of dry ammonia (or rather of its component gases) at a white heat as a greyish-brown powder, which does not undergo change at ordinary temperatures It is likewise obtained when the black residue left on calcining ammonium metavanadate in the air is heated to whiteness in a current of dry ammonia. Other methods of obtaining the nitride are to expose the oxide or dichloride to the action of ammonia gas at a white heat

[1] See also Gain, *Compt rend,* 1906,143, 1164
[2] See also Bitte, *Compt rend* , 1886,**102,** 757.
[3] Gerland, *Ber,* 1878,**11,** 98

When heated in the air, vanadium mononitnde glows and slowly oxidises to the blue oxide, when 'heated with soda-lime, ammonia is produced.

Vanadium Dinitrade, VN_2, is obtained as a black powder by passing ammonia over vanadyl trichloride, heating the residue in a glass tube to expel ammomum chloride, washing with water, and drying in a vacuum over sulphuric acid

426 Extended series of phosphovanadic and arsenovanadic acids and their derivatives have been described by Berzelms,[1] Ditte,[2] and Gibbs [3] According to Friedheim [4] these substances are phosphates and arsenates of vanadium (and double salts of these with the vanadates), in which vanadic anhydride acts as a weak base, the radical $V0_2$ replacing one or two hydrogen atoms of phosphoric or arsenic acid They can be prepared by bringing the requisite salts together

Phosphovanadic Acid, $2(V0_2)H_2P0_4,9H_20 = P_20_5,V_20_6,11H_20$, is formed when vanadic anhydride is heated with syrupy phosphoric acid, and crystallises in golden-yellow flakes

Arsenovanadic Acid, $As_2O_5,V_2O_5,10H_2O$, is prepared in a similar manner, and forms yellow crystals

VANADIUM AND THE ELEMENTS OF THE CARBON GROUP

427 *Vanadium Carbide,* VC, is formed when vanadic anhydride is heated with carbon in the electric furnace It forms hard crystals of the specific gravity 5 405, burns in oxygen, and becomes incandescent when heated in chlorine [5] It is silvery-white, very hard, and melts at 2750° [6]

Vanadium Cyanides—Double salts of vanadium dicyanide and tricyanide with potassium cyamde of the formulae $K_4V(CN)_6,3H_20$ and $K_3V(CN)_6$ have been prepared [7]

Potassium Vanadic Thiocyanate, $V(SCN)_3,3KSCN,4H_20$, is prepared in a similar manner to the cyamde (Locke and Edwards), and separates in dark red crystals, the solution of which in water rapidly decomposes The ammomum and sodium salts have also been obtained [8]

[1] ***Lehrbuch,* [6], 3, 1037**
[2] ***Compt rend,* 1886,108, 757**
[3] ***Amer Chem J* 1886-6, 7, 118, 209**
[4] ***Ber,* 1890, 28, 1530, 2600**
[5] **Moissan, *Compt rend,* 1896,122, 1297**
[6] **Ruff and Martin, *Zeit angew Chem,* 1912, 25, 49**
[7] **Petersen, *Zett anorg Chem,* 1904, 38, 342, Locke and Edwards, *Amer Chem J,* 1898, 20, 594**
[8] **Cioci, *Zett anorg Chem,* 1899,19, 308**

Complex ammonia vanadyl thiocyanates and oxalates have likewise been prepared [1]

Vanadium and Silicon—Vanadium forms two compounds with silicon The *sihade,* V_2Si, is prepared [2] by heating 120 parts of the sesquioxide with 14 of silicon in the electric furnace, or better by heating this mixture with either carbon or copper It forms hard, silver-white prisms with a metallic lustre, and has the sp gr 5 48 at 17° It is only attacked by fluorine when gently heated, and it is readily decomposed when heated in chlorine, bromine, or hydrogen chloride It is insoluble in acids, with the exception of hydrofluoric acid, and is decomposed by fused potash. When it is fused with silicon it is converted into the *disiheide,* VSi_2, which can be obtained also by heating the sesquioxide with an excess of silicon in the electric furnace, or by igniting a mixture of the oxide and silicon with metallic magnesium [3] It forms hard prisms with a metallic lustre, has the sp gr 4 42, and melts and volatilises in the electric furnace It is soluble in hydrofluoric acid, burns when heated in fluorine, chlorine, or bromine, and is attacked by gaseous hydrogen chloride It is also decomposed by fused alkalis, and by molten copper, an alloy of this metal with vanadium being formed

DETECTION AND ESTIMATION OF VANADIUM

428 Insoluble vanadium compounds can be brought into solution by treatment either with acids or with alkalis The hydrochloric acid solution assumes a bright blue colour on the addition of zinc A solution of vanadyl sulphate cannot be distinguished in colour from one of copper sulphate when diluted to the requisite extent with water It, however, of course, does not become colourless in presence of metallic iron Solutions of certain vanadates also closely resemble solutions of the chromates Thus, for instance, a solution of the tetravanadate of potassium does not differ in appearance from one of potassium dichromate They may, however, be distinguished from one another, inasmuch as the vanadate solution becomes blue, whilst the chromate assumes a green colour, on reduction When a solution of vanadic acid or an acid solution of an alkali vanadate is shaken up with ether containing hydrogen peroxide, the aqueous solution assumes a red colour like that of feme

[1] **Koppel and** Goldmann, *Zeit anorg Client,* 1903, **86,** 281
[2] Moissan **and** Holt, *Compt rend* , **1902, 136, 493** [3] *Ibid* , 78

acetate This reaction serves to detect 1 part of vanadic acid in 40,000 p of chromic acid[1]

For the *quantitative* estimation of vanadium in a soluble vanadate it may be treated with lead acetate, when basic lead vanadate is precipitated The precipitate is insoluble in acetic acid but it dissolves readily in nitric acid, liberating vanadic acid, which separates out, but dissolves completely when the liquid is warmed In the analysis of a soluble vanadate this insoluble lead salt is collected on a filter, dried at 100°, and weighed, a given quantity of the dried salt is then dissolved in nitric acid, the lead precipitated by pure sulphuric acid, and the lead sulphate estimated with the usual precautions by evaporation, addition of alcohol, etc , or the filtrate is evaporated and the residue heated and weighed as vanadic anhydride[2] The lead sulphate thus obtained is quite free from vanadium, whilst the vanadium pentoxide in the filtrate is obtained perfectly pure and well crystallised on evaporation and ignition The filtrate from the lead vanadate, freed from excess of lead by means of sulphuric acid and evaporated, yields the alkali sulphate, containing no trace of vanadium Vanadium may be very readily estimated volumetncally when no other reducible metals are present For this purpose the solution of vanadic acid in sulphuric acid is diluted and reduced to a vanadyl salt by passing a current of sulphur dioxide through it and afterwards boiling to expel the excess of this gas Standard permanganate is then added until a permanent coloration is obtained The inverse process may also be employed, and the acid solution of a vanadate titrated with decmormal ferrous sulphate solution, potassium ferncyanide being employed as indicator[3] Under these circumstances the acid is reduced to VO_2 and the process can be carried out in the presence of copper The reduction may also be effected by repeated evaporation with hydrochloric acid[4]

The Atomic Weight of vanadium has been determined in several ways One is by igniting vanadium pentoxide in dry

[1] G Werther, *J pr Chem*, 1863, 88, 1%

[2] Cormimbceuf, *Ann Chim anal*, 1902, 7, 258

[3] Williams, *J Soc Chem Ind* , 1902, 21, 389

[4] Campagne, *Ber*, 1903, **36, 3164** See also Gooch and Stookey, *Amer J Sci*, 1902, **[4],** 14, 369, Gboch and Gilbert, *Zeit anorg Chem* , **1903, 36,** 420, **Nakazono** ***J*** *Chem Soc Japan*, **1921, 42, 761**

hydrogen, when it is reduced to the sesquioxide, and the atomic weight of vanadium is deduced from the loss in weight

In this manner Roscoe [1] obtained the value 51 38 A second and more trustworthy method for the determination of the atomic weight of vanadium is the analysis of vanadyl trichloride The chlorine in this compound was estimated by Roscoe both volumetncally and gravimetrically, the results being 51 06 and 51 26 respectively The gravimetric analysis of vanadyl trichloride by Prandtl and Bleyer [2] yielded the value 51 07, while McAdam,[3] by the conversion of sodium vanadate into sodium chloride found 50 97 A still further determination by Briscoe and Little,[4] who analysed vanadyl trichloride, gave the value 50 96, in close agreement with that of McAdam The value now adopted (1922) for the atomic weight of vanadium is 51 0

COLUMBIUM Cb = 93 1 At No 41

429 This metal is so closely connected with the next member of the same group, tantalum, that it will be most convement to consider their history together

In the year 1801, Hatchett[5] laid before the Royal Society an investigation on a mineral known as columbite, from Massachusetts, which he believed to contain a new metal to which he gave the name *columbium* In the following year, Ekeberg,[6] in Sweden, investigating the yttrium minerals, discovered a new element in a mineral to which he afterwards gave the name of yttrotantalite, whilst the same element also occurred in a mineral termed tantalite In consequence of this he named the metal *tantalum,* partly because mythological names were frequently used, and partly also as pointing to the fact " that when placed in the midst of acids it is incapable of taking any of them up and saturating itself with them "

In 1809, Wollaston [7] endeavoured to show that columbium and tantalum were identical, and a few years later Berzehus [8] more carefully investigated the oxides of the last-named metal obtained from tantalite, and prepared tantalic acid After-

[1] *Phil Trans,* **1868, 158, 6**
[2] ***Zett*** *anorg Chem* , **1909, 65, 152, 1910, 67, 257**
[3] ***J*** *Amer Chem Soc* , **1910, 32,1603**
[4] *Journ Chem Soc* , **1914,105, 1310**
[5] ***Phil Trans*** , **1802, 92, 49**
[6] *Ann Chim,* **1802, 43, 276**
[7] ***Phil Trans*** , **1809, 99, 246**
[8] *Pogg Ann* , **1820, 4, 6**

wards, in 1839, Wohler[1] found that the acid-forming oxide contained in pyrochor and in the Bavarian tantaktes possessed peculiar properties, and Rose[2] then observed that the columbites of Bodenmais contained the oxide of a new metal, to which he gave the name of niobium (Nb), and in 1846 he thought that he had found a third new metal, to which he gave the name of *pelopium* In 1853 he came to the conclusion on further investigation that niobic acid and pelopic acid were different oxides of niobium, and to the first of these he gave the name of mobic acid, whilst the latter was designated as hyponiobic acid These, however, exhibited " a relationship so peculiar that the wHble range of chemistry does not furnish an example of a similar kind"[3] In 1856-7 Hermann observed that niobium and tantalum usually occurred together, whilst in 1864-5, Blomstrand[4] showed that Rose's hyponiobic chloride contained oxygen, and was an oxychloride, and Mangnac[5] almost at the same time proved that the double salts which hyponiobic fluoride forms with metallic fluorides are isomorphous with similar double salts contaimng titamum fluoride, TiF_4, and tungsten oxyfluonde, WO_2F_2 Inasmuch as the sum of the atoms in all these isomorphous compounds is constant, and as, according to analysis, the hyponiobic fluoride contains three atoms of fluorine for one of oxygen, Mangnac concluded that it must be an oxyfluonde of the composition $NbOF_3$, and he succeeded in obtaining experimental evidence of the truth of this view At the same time, he showed that tantahc acid, which up to that time had been supposed to be analogous to titamc acid, and to which the formula TaO_2 had been given, must, like the highest oxide of niobium, be a pentoxide, as these two oxides occur in isomorphous mixture in several minerals, and as both metals form isomorphous double fluorides, such as K_2TaF_7 and K_2NbF_7

The name columbium, originally proposed by Hatchett, has always been employed in America for Rose's niobium, and has recently also been adopted in England, whilst in Germany the name niobium is retained

The truth of this view of the composition of the columbium and tantalum compounds was confirmed by the experiments of Deville and Troost,[6] who in 1865 determined the vapour

[1] *Pogg Ann* , 1839, 48, 91
[2] *Ibid* , 1844, 63, 307, 693, 1846, 69, 118
[3] *Ibid* , 1853, 90, 471
[4] *J pr Chem* , 1866, 97, 37
[5] *Ann Chim Phys*, 1866, [4], 8, 5, 49
[6] *Compt rend*, 1865, 60, 1221

densities of columbium chloride, columbmm oxychlonde, and tantalum chloride, which were found to correspond to the formulae $CbCl_5$, $CbOCl_3$, and $TaCl_6$ The investigations of Blomstrand and Mangnac next showed that the metal *diamum,* supposed by v Kobell to be contamed in vanous columbites, is in fact identical with columbmm, and Mangnac further showed that *ilmenium,* which Hermann believed he had discovered in samarskite, is a mixture of columbium and tantalum It appears certain that *neptunium,* also discovered by Hermann, is a similar mixture [1]

430 The only tantalum ore of commercial importance is *tantahte,* FeO,Ta_20_6, or ferrous tantalate, which is a black mineral the density of which varies from 6 5 to 7 3 Part of the tantalum is invariably replaced by columbium, and part of the iron by manganese, until in *manganotantalite,* MnO,Ta_20_6, manganese is the chief metal present *Mtcrolite,* or calcium tantalate, $Ca0,Ta_2O_6$, is also known, while a very interesting mineral is *shbiotantahte,* $(SbO)_2Ta(Cb)_20_6$

Colurnbite, FeO,Cb_20_6, is the most commonly occurring columbium-tantahim mineral Part of the columbium is always replaced by tantalum, and manganese accompanies the iron The density varies from 5 3 to 6 5, increasing with mcrease in the content of tantalum Like tantahte, the mineral crystallises in orthorhombic prisms

Columbite and tantahte have been found in Scandinavia, Finland, Russia, Greenland, Bavaria, Ceylon, Malay States, in Dakota and other parts of the United States, and particularly in Western Australia, in the Pilbara and Greenbushes gold-mining districts[2] The Pilbara district is the most important, and produces almost entirely manganotantalite The accompanying table records the analyses of various samples of the minerals already mentioned (See Table on p 976)

Of the numerous other columbium-tantalum minerals, several may be briefly mentioned, since they also contam the rare earths *Mschymte,* $Ce_2Cb_4O_{13}$,$Ce_2(TiTh)_5O_{13}$, is essentially a colurnbo-titanate of the cente earths, containing thorium in considerable quantity. It is found in Norway'and the Urals. *Fergusomte,* $(Y,Ce)(Cb,Ta)0_4$, is a metacolumbate of the yttrium earths

[1] **See Smith, *Proc Amer Phil Soc* , 1905, 44, 151, Hall and Smith, *J Amer Chem Soc* , 1905,27, 1369, Barr, *ibid* , 1908,30, 1668, Hildebrand, *ibid* , 1908, 30, 1672**

[2] **See Simpson, *Chem News,* 1909, 99, 49, 77.**

Mineral	Tantahte		Columbite		Manganolantalite	Microlite	Stibiotantalite
Locality	Greenbushes	Sweden	Greenland	Massachusetts	Pilbara	Pilbara	Greenbushes
Ta_2O_5	80 6	49 64	177 97	28 55	68 65	77 16	5195
Cb_2O_5	2 50	29 27	013	5153	1511		4 49
WO_3	013			0 76			
SnO_2	151	2 49		0 34	0 48		
TiO_2	0 71		0 73		0 40		
ZrO_2				0 24			
SiO_2			013				3 14
FeO	10 89	13 77		13 54	163	3 64	
Fe_2O_3			17 33				0 39
MnO	3 78	2 88		4 55	1415	0 60	
CaO			3 28			13 46	
MgO	0 19		0 23	0 42	015	0 42	
PbO			012				
$Na(K)_2O$							
Sb_2O_3						186	38 04
Bi_2O_3							0 79
CuO							0 20
H_2O	014			0 16	0 07		0 61
						128	
Analyst	Simp Bon	Rammelsberg	Blomstrand		Simpson		

containing also thorium and uranium It occurs in Greenland, Scandinavia, and various localities in the Umted States *Yttrotantahte* and *samarskite* are columbo-tantalates of yttrium, iron, and calcium, the latter mineral containing considerable amounts of uranium Samarskite occurs massive in North Carolina, and has also been found in India *Euxemte* is an orthorhombic columbo-titanate of yttrium, containing uranium, the ISOmorphous mineral *polycrase* is similar in composition, but contains less columbium and more titanium

Besides occurring in these and other minerals, columbium and tantalum are frequently found in small quantities in tinstone, wolfram, pitchblende, monazite, and other minerals

For the purpose of preparing columbium and tantalum compounds, it is best to start with columbite or tantalite, which contam very little titanium, rather than to employ one or

other of the minerals rich in titanium, since no methods are yet known for the quantitative separation of columbium and tantalum from titanium, at any rate when operating on a fairly large scale For decomposing the mineral, Giles[1] strongly recommends fusion of the finely powdered substance with 2¼ to 3 times its weight of potassium carbonate in a steel or wrought-iron crucible The fusion is carried out in a reducing atinosphere by placing the crucible, covered with a lid, inside a larger crucible, the inner crucible being completely surrounded with charcoal In this manner the columbium and tantalum are transformed into potassium columbate and tantalate, which may be extracted from the fusion with water, leaving behind the iron and manganese as monoxides in the form of a heavy, black sand Small amounts of easily reducible metals such as tin and antimony (and tin is a constant constituent of the minerals) are completely removed in the metallic state, the metal usually alloying with the metal crucible The aqueous extract is made slightly acid with hydrochloric acid and heated to boiling, when the hydrated pentoxides of columbium and tantalum separate out as a white precipitate The precipitate is thoroughly washed by decantation with hot water

The classic method for the decomposition of the minerals is fusion with acid potassium sulphate For this purpose, the mineral is finely powdered and fused with three times its weight of the bisulphate, the fused mass is completely boiled out with water, when a residue of crude columbic and tantalic hydroxides is left This is digested with ammonium sulphide for several days, in order to remove most of the tin and tungsten, which are always present The residue is washed, boiled with a little dilute sulphuric acid, and again thoroughly washed with water

The columbium and tantalum are separated by taking advantage of the different solubilities of the double potassium fluorides, $KaCbOF_5H_2O$ and K_2TaF_7, which dissolve in about 12 and 200 times their weight of water respectively at the ordinary temperature The hydroxides are dissolved in hot hydrofluoric acid, filtered from any mineral residue or potassium sihcofluonde, the solution treated with enough potassium fluoride to form the double tantalum salt, and concentrated if necessary On cooling, fine, characteristic, needle-shaped crystals of the tantalum salt separate out, and are washed with water On evaporating the mother-liquor and wash-waters, more of the salt is obtained,

[1] *Chem News*, 1909, 99, 1, 25.

which at last is mixed with scales of the columbmm salt The potassium tantalojuoride is purified from practically all impurities but a trace of silicofluoride by one or two crystallisations, mixed with its own weight of concentrated sulphuric acid and heated gradually to 400° until the hydrofluoric acid and most of the excess of sulphuric acid are expelled The residue is then disintegrated by boiling with water, and thoroughly washed, first with water, and finally with dilute ammomum carbonate, until all the potassium and sulphuric acid have been removed The pure tantalic hydroxide is then ignited if it is desired to form the pentoxide

The filtrate from the tantalum salt is treated with a further quantity of potassium fluoride and concentrated, when, on cooling, the columbium salt, K_2CbOF_5,H_20, separates out The salt thus obtained contains a little tantalum It is therefore heated to 200° for some hours and extracted with water, when a residue of potassium tantalum oxyfluonde is obtained and removed by filtration The solution is evaporated to dryness and the baking at 200° and extraction with water are repeated until all the tantalum has been removed From the purified columbium salt the silica-free hydroxide and oxide may be obtained as has already been described for tantalum [x]

The oxides of columbium and tantalum obtained in the preceding manner usually contain small quantities of oxides of tin and tungsten These may be removed by Rose's method of fusion with a mixture of sodium carbonate and sulphur, and extraction with water The tin and tungsten pass into solution as thiostannate and tungstate, and the residual sodium columbate or tantalate is then washed with cold water, in which it is nearly insoluble, and fused with potassium bisulphate to recover the oxide This treatinent with sodium carbonate and sulphur may have to be repeated several times.

The columbic oxide still contains small amounts of oxide of titanium, and no satisfactory separation of this impurity is known which does not remove also a considerable proportion of the columbium The simplest procedure is to crystallise the double fluoride, K_2CbF_7, from fairly concentrated hydrofluoric acid five or six times, this also eliminates tin and tungsten [2]

[1] **Hall, *J Amer Chem Soc*, 1904, 28, 1235, Hall and Smith, *ibid*, 1905, 27, 1369 See also Ruff and Schiller, *Zeit anorg Chem*, 1911, 72, 329**

[2] **Balke and Smith, *J Amer Chem Soc*, 1908, 80, 1637, cf Hall, *loc cit*, Hall and Smith, *loc cit***

t

Ruff and Schiller prefer to eliminate titanium by fractional distillation of the columbium pentachlonde, the titanium chloride being much the more volatile

431 Columbium was first obtained by Blomstrand,[1] by reducing the chloride in hydrogen, as a mirror-like deposit on the tube, but it was not certain whether this was the pure metal or a hydride Roscoe[2] obtained it in the form of a steel-grey crust, by passing the vapour of the pure chloride together with hydrogen repeatedly through a red-hot tube, this was then more strongly heated in a porcelain tube, through which hydrogen was passed The metal contained only 0 27 per cent of hydrogen as well as a small quantity of chloride and oxide, the latter being derived from diffused air It has been prepared

in a somew

the pentoxide with carbon in the electric furnace,[3] and by reducing the pentoxide with the mixed metals of the cerite earths, the method being the same as that employed for vanadium (p 948)[4] It can be obtained in the pure condition by preparing filaments of the oxide, CbO_2, by heating a mixture of the pentoxide and paraffin which has been pressed into threads, and then reducing this by passing through it an alternating current *in vacuo* The regulus obtained by the aluminium reduction of the pentoxide may moreover be freed from aluminium by being heated *in vacuo in* an electric furnace[5] The metal has the specific heat 0 071 and the density 8 4, and melts at about 1950° The pure metal has a light grey colour, and is about as hard as wrought iron It can be rolled into foil and then drawn into wire, and can be welded at a red heat A regulus fused in a vacuum consists of crystals, apparently rhombic, several mm in length It combines only slowly with oxygen, even when it is strongly heated, and unites with hydrogen to form the hydride, CbH This compound, which has also been obtained by Mangnac, resembles the metal in its behaviour to acids, and burns when heated in the air[6] Columbium is not dissolved by hydrochloric or nitric acid or aqua regia, even when heated, but when alloyed with other metals is attacked by acids It is attacked by fused alkalis and fused oxidising agents, and combines with nitrogen at 1200°

[1] *J pr Chem*, 1866, **97,** 37 [2] *Mem Manch Phil Soc*, [3], 6, **186**
[3] **Moissan,** *Compt rend*, **1901, 133, 20**
[4] **Weiss and Aichel,** ***Annalen,*** **1904,** 337, **380**
[5] **Werner von Bolton,** *Zett Elektrochem*, **1907, 13, 145**
[6] **Kruss and Nilson,** ***Ber,*** **1887, 20, 1691**

COMPOUNDS OF COLUMBIUM

COLUMBIUM AND OXYGEN

432 The two lower oxides of columbium are usually known as the dioxide, Cb_2O_2, and the tetroxide, Cb_2O_4, although they would more properly be termed the monoxide, CbO, and the dioxide, CbO_2

Columbium Dioxide, CbO or Cb_2O_2, is formed when dry potassium columbium oxyfluonde is heated with sodium under a layer of potassium chloride over a gas blow-pipe, and was thought by Rose to be the metal The fused mass is boiled with water, and the residue washed with water and afterwards with dilute alcohol It then forms a white powder which on heating in the air oxidises with vivid incandescence When gently warmed in chlorine gas, it burns with formation of oxychlonde, and it dissolves in the moist state in hydrochloric acid with evolution of hydrogen If the vapour of the oxychlonde be passed over heated magnesium wire, the same compound is formed in crystals which belong probably to the regular system

Columbium Tetroxide, CbO_2 or Cb_2O_4, is obtamed as a heavy, black powder, which appears blue by reflected light, by heating the pentoxide very strongly in hydrogen or with metallic magnesium [1] It is not attacked by acids, and burns in the air when heated to redness

Columbium Pentoxide, Cb_2O_5—The preparation of this oxide has been already described It is a white, amorphous, infusible powder having a sp gr of 4 5 to 5 0, according to its method of preparation, and becomes yellow and crystalline when strongly heated It may be obtained in prismatic crystals of sp gr 4 568 by fusion with boron tnoxide or borax

Columbic Acid or *Columbium Hydroxide,* $HCbO_3$, is obtained as already described on p 977, and is also formed by the decomposition of the oxychlonde or pentachlonde in moist air or with water It is a white powder which, when dried at 100°, retains varying quantities of water, and is converted into the pentoxide at a red heat with incandescence It is only slightly soluble in hot hydrochlonc acid, but the residue, after this treatinent, can be dissolved in water On the addition of zinc the solution becomes blue and a hydrated precipitate, probably of Cb_2O_4, separates out The solution of columbic acid obtained by

[1] Smith and Maas, *Zeit anorg Chem,* 1894, 7, 96.

treatment with hydrochloric acid gives, on the other hand, a brown colour with zinc, and a brown oxide separates out which has the composition Cb_30_5(= CbO,2Cb0$_2$) Columbic acid is easily soluble in caustic alkalis and their carbonates

Columbates —The salts of columbic acid are termed columbates Many of these salts were described by the early workers on columbium, but comparatively few were definite chemical individuals The first definite sodium salt, $7Na_20,6Cb_20_3,32H_20$, was prepared in 1905 by Bedford[x] Since then the columbates have been carefully studied by Balke and Smith,[2] who have shown that several series of these salts can be obtained

The 7 6 *series,* $7M^I_20,6Cb_20_5,zH_20$ —The *sodium* salt of this series may be prepared by precipitating potassium columbium oxyfluonde in aqueous solution with three times its weight of caustic soda, washing the precipitate with cold water, and recrystallising from boiling water The salt is not very soluble in hot, and almost insoluble in cold water It may also be obtained by fusing columbium pentoxide with four parts of caustic soda or 3 parts of sodium carbonate, extracting most of the excess of alkali with cold water, and crystallising the residual sodium columbate The salt is precipitated unchanged from its aqueous solution by the addition of alcohol, and from it, by double decomposition, the corresponding barium, silver, and zinc salts have been obtained The potassium, caesium, and lithium salts of this series are also known

The 4 3 *series,* $4M^I_20,3Cb_20_5,xH_20$ —The potassium, rubidium, and caesium salts are known The last two salts crystallise with $14H_20$ and are isomorphous with each other and with the corresponding tantalates The *potassium* salt crystallises with $16H_20$ and is the easiest columbate of potassium to prepare, being obtained by fusing columbium pentoxide with twice its weight of potassium carbonate and crystallising the product from water (Mangnac) Its aqueous solution yields the 7 6 salt when precipitated with alcohol

The 1 1 *series,* M^J_20,Cb_20_6,zH_20 —The sodium salt, $Na_20,Cb_20_5,7H_20$, separates out when the mother-liquor from the crystallisation of the 7 6 salt is allowed to evaporate spontaneously, and may be prepared by slowly evaporating an aqueous solution of the 7 6 salt on the water-bath while an atmosphere of carbon dioxide is maintained above the solution[8]

[1] ***J. Amer Chem Soc*, 1905, 27, 1216** [2] ***Ibid*, 1908, 30, 1637**
[3] **Smith and van Haagen, *J Amer Chem Soc*, 1915, 37, 1783**

It is much more soluble than the 7 6 salt It becomes anhydrous, but is stable at red heat From the aqueous solution, by double decomposition, the silver, magnesium, copper, cadmium, and aluminium salts have been prepared

The 3 4 *series,* $3M^{I}_{2}0,4Cb_{2}0_{53}xH_{2}0$ —Only the rubidium salt is yet known

Numerous crystalline columbates have been prepared by fusing the precipitated salts with the corresponding chlorides or with bone acid[1]

Percolumbic Acid is formed as an amorphous, yellow powder when columbic acid is warmed with hydrogen peroxide, or when sulphuric acid is added to a solution of potassium percolumbate and the solution dialysed and evaporated It has the composition of a hydrated percolumbic acid, $HCb0_{4}$, and is decomposed by dilute sulphuric acid only on warming, thus differing from other per-aeids[2] The percolumbic acid, $Cb(OH)_{6}$ or $Cb_{2}0_{6},H_{2}0_{2},5H_{2}0$, has also been prepared [3]

Orthopercolumbates of the general formula $M_{3}Cb0_{8}$, where M is a univalent metal, have been obtained by Balke and Smith, [4] these represent some of the most highly oxidised series of salts known They are prepared by adding an excess of hydrogen peroxide to an aqueous solution of an alkali columbate, together with the corresponding alkali hydroxide, and precipitating with alcohol The potassium, sodium, rubidium, and caesium salts are anhydrous, white, crystalline solids, quite stable in air and

in warm aq

liberation of oxygen, when the aqueous solutions are boiled By double decomposition the following percolumbates have also been prepared

$MgNaCb0_{8},8H_{2}0$	$MgCsCb0_{8},8H_{2}0$
$MgKCb0_{8},7H_{2}0$	$CaNaCb0_{8},4H_{2}0$
$MgRbCb0_{8},7iH_{2}0$	$CaKCb0_{8},4H_{2}0$

COLUMBIUM AND THE HALOGENS

433 *Columhum Pentafluoride,* CbF_{5}, is prepared by treating the pentachlonde with anhydrous hydrogen fluoride, and frac-

[1] Larsson, *Zeit anorg Chem,* 1896, 12, 188 See also Holmquist, *Journ Chem Soc,* 1898, 74, 11, 388

[2] Mehkoff and Pissarjewsky, *Zeit anorg Chem* , 1899, 20, 340

[3] Hall and Smith, *J Amer Chem Soc,* 1905, 27, 1369

[4] *J Amer Chem Soc,* **1908, 30, 1637.**

tionating out the pipduct under reduced pressure It is a colourless, crystalline solid of density 3 29, which melts at 75*5° and boils at 217—220° It is rapidly decomposed by water, acids and alkalis, alcohol, and ether [1]

Columhum Oxyfluonde, $CbOF_3$, is obtained by igniting a mixture of pentoxide and fluor-spar in a current of hydrogen chloride, in the form fluoride It forms double salts with other metallic fluorides, of which those of potassium and ammonium have been investigated by Mangnac, who prepared the following

$2KF,CbOF_3,H_20$	$2NH_4F,CbOF_3$
$3KF,CbOF_3$	$3NH_4F,CbOF_3$
$5KF,3CbOF_3,H_20$	$5NH_4F,3CbOF_3,H_20$
$4KF,3CbOF_3,2H_20$	$NH_4F,CbOF_3$
$HF,3KF,CbOF_3$	$3NH_4F,CbOF_3,CbF_5$

These are crystallisable, and are formed by dissolving columbic acid in a larger or smaller quantity of hydrofluoric acid and adding the other fluorides in various proportions The first salts of the two series, which Mangnac terms normal salts, are those which are readily formed The normal potassium salt is formed whenever the others are recrystalhsed, and is deposited in the form of thin, monoclmic scales soluble in 12 parts of water at the ordinary temperature It is isomorphous with potassium tungsten oxyfluonde, $2KF,W0_2F_2$, and with potassium titanofluonde, K_2TiF_6 By dissolving the normal oxyfluonde in hot hydrofluoric acid *potassium columfofluoride,* K_2CbF_7, is formed, which is deposited in glistening, rhombic needles The normal ammonium salt crystallises in rhombic tablets, and is isomorphous with ammomum tungsten oxyfluonde, $2NH_4F,W0_2F_2$

Rubidium, caesium, and thallous double fluorides of the type $2M^IF,CbOF_3$ are also known, and a sodium salt of the composition $3NaF,CbOF_3$ Like the potassium compound, the rubidium and caesium salts are transformed into double fluorides of the type $2M^JF,CbF_5$ when crystallised from fairly concentrated hydrofluoric acid (Balke and Smith)

A double fluoride of the formula 2KF,3Cb02F is gradually deposited in small quantity as a white powder when a solution

[1] Ruff and Schiller, *Zeit anorg Chem,* 1911, 72, 329

of the normal potassium oxyfluonde is bailed for a considerable time [1]

$$3(2KF,CbOF_3) + 3H_20 = 2KF,3Cb0_2F + 4KF + 6HF$$

It is readily soluble in hydrofluoric acid

Hydrogen peroxide converts the oxyfluonde into a peroxyfluonde, $Cb0_2F_3$, which crystallises in yellowish plates[2] The double sodium and rubidium peroxyfluondes have been similarly prepared (Balke and Smith)

Columbtum Trichloride, $CbCl_3$, is obtained when the vapour of the pentachlonde is slowly passed through a red hot glass tube, and when the oxide is heated with phosphorus pentachtonde [8] It either forms crystalline crusts which have the appearance of iodine, or is found crystallised in long needles which are dichroic It is neither volatile nor deliquescent, and is not decomposed by water or ammonia, but is easily oxidised by nitnc acid When heated in the air it emits thick vapours, and when ignited in a current of carbon dioxide it forms columbium oxychlonde, $CbOCl_3$, and carbon monoxide, a reaction which is not exhibited by any othei metallic chloride (Roscoe)

Columbium Pentachlonde, $CbCl_5$ —When an intimate mixture of columbium pentoxide and a large excess of sugar charcoal is heated in a current of chlorine perfectly free from air, yellow needles of the above compound are formed The chlonde is also formed [4] when the pentoxide is heated in the vapour of sulphur monochlonde and chlorine, or carbon tetrachloride and chlorine, or heated with carbon tetrachloride in a sealed tube at 200°, and, together with the oxychlonde, when carbon tetrachloride is passed over the heated pentoxide It has a density of 2 75, melts at 194°, and boils at 240 5°, but begins to sublime at 125° The yellow vapour has a specific gravity of 9 6 (Deville and Troost), the formula requiring 9 38 The chloride is soluble in carbon tetrachloride, sulphur monochlonde, chloroform, and alcohol It dissolves in hydrochlonc acid, forming a liquid which gelatinises on standing, and when diluted with water or boiled almost all the columbic acid separates out

[1] Kruss and Mson, *Ber,* 1887, 20, 1676
[2] Piccini, *Zeit anorg Chem,* 1892, 2, 22
[3] Pennington, *Chem News,* 1897, 75, 38
[4] Smith, *J Amer Chem Soc,* 1898,20,289, Hall and Smith, *ibid,* 1905, 27, 1369, Hall, *ibid,* 1904,26, 1235, Ruff and Schiller, *Zeit anorg Chem,* 1911, 72, 329

Metallic zinc brought into the solution turns it a deep blue colour

Columbmm Oxychloride, or *Columbyl Chloride,* $CbOCl_3$, is formed by the direct union of the dioxide with chlorine, and also when a mixture of the pentoxide with a small quantity of carbon is heated in chlorine It is best formed by heating the pentoxide in carbon tetrachloride vapour, and eliminating the pentachloride also produced by repeatedly distilling the mixture in a current of carbon dioxide over the pentoxide (Hall and Smith) It is a colourless, fibrous, crystalline mass, which volatilises without melting at about 400°, giving rise to a colourless vapour, the specific gravity of which was determined by Deville and Troost to be 7 88, theory requiring 7 48 When heated in carbon dioxide, and still more readily in hydrogen, it decomposes into pentoxide and pentachloride It deliquesces on exposure to moist air, with formation of crystalline columbic acid, whilst when brought into contact with water it decomposes violently, forming amorphous columbic acid

Double salts with various alkali chlorides and organic hydrochlorides have been prepared[1]

When columbmm oxide is heated in hydrogen chloride a hydroxychlonde, $Cb_20_4,3H_20,HCl$, is formed which is volatile at a high temperature[2] Hydrogen bromide yields an analogous compound

Columbmm, Pentabromide, $CbBr_5$, obtained by the direct union of its elements,[3] closely resembles the chloride in properties It is a purple-red mass, which forms deep garnet-red, prismatic crystals It melts at about 150° and boils at 270°

Columbmm Oxybromide, $CbOBr_3$—When a mixture of the pentoxide and double its weight of carbon is heated in bromine vapour a yellow, voluminous mass of the oxybromide is obtained, which sublimes without fusion in an inert atinosphere laden with bromine vapour, and even at comparatively low tempeiatures begins to decompose into the pentabromide and pentoxide (Barr)

HALIDE BASES OF COLUMBIUM

Chlorocolumbium Chloride, $(Cb_6Cl_{12})Cl_2,7H_20$, is obtained by heating columbium pentachloride with seven parts of 3 per cent

[1] Wemland and Storz, *Ber* , 1906, 39, 3056, *Zeit anorg Chem* , 1907, 54, 223.
[2] Smith and Maas, *Zeit anorg Chem,* **1894, 7, 96.**
[3] Barr, *J Amer Chem Soc,* 1908, 30, 1668

sodium amalgam i*n vacuo* at a temperature just sufficient to propagate the mitM reaction through the mass, and subsequently heating for an hour to a temperature at which Jena glass begms to soften The mass is cooled i*n vacuo,* extracted with boiling water, the solution filtered from brown residue, and concentrated after the addition of a little hydrochloric acid The yield is very small

The chloride separates in small, shining crystals which appear black but give a green powder It is very slightly soluble in cold and not very soluble in boiling water, the solution having an olive-green colour It is not completely decomposed by ammonia even on long boiling, but boiling nitric acid decomposes it The compound dissolves in concentrated alkalies to form a dark greenish-brown solution, from which, on adding excess of hydrochloric acid, a brown chloride, $Cb_6Cl_{14},9H_20$, is obtained differing in constitut it only differs in its water content The brown chloride is re-converted into the green chloride when dissolved in water, the rate of change being rapid in boiling solution

A solution of chlorocolumbium chloride, when treated with the theoretical amount of sodium hydroxide, gives a black, crystalline precipitate of *chlorocolumbium hydroxide,* $(Cb_6Cl_{12})(OH)_2,8H_20_>$ soluble in both acids and alkalis From its solution in hydrobromic acid, *chlorocolumbium bromide,* $(Cb_6Cl_{12})Br_2,7H_20$, may be obtained in crystals which resemble the chloride but are more soluble in cold water[1]

COLUMBIUM AND SULPHUR

Columbium Sulphide—When columbium pentoxide is heated to redness for a sufficient period in hydrogen sulphide it produces a brown product containing only columbium and sulphur The product is black when a mixture of hydrogen sulphide and carbon disulphide is employed No definite sulphide or oxysulphide has yet been obtained [2]

COLUMBIUM AND NITROGEN

435 *Columbium Nitride,* Cb_3N_6—Metallic columbium forms a yellow nitride[3] when it is heated in nitrogen at 1,200° A

[1] Harned, *J Amer Chem JSoc,* 1913, 36, 1076
[2] Bdtz and Gonder, *Ber* , 1907, 40, 4963
[3] Moissan, *Compt rend,* 1901, 138, 20, Muthmann, Weiss, and Reidelbauch, *Annalen,* 1907, 355, 58

nitride also is presumably precipitated when dry ammonia gas is led into a solution of the pentachlonde in carbon tetrachloride It is separated from co-precipitated ammonium chloride by washing with water, and is decomposed by caustic alkali with the evolution of ammonia.[1] When columbium pentoxide is heated to whiteness in ammoma it loses the half of its oxygen, and forms a black powder containing nitrogen If the oxychloride be treated with dry ammoma it becomes hot and turns yellow This mass, when heated, gives off ammonium chloride, and a black powder remains behind, which, when melted with caustic potash, yields ammoma in large quantity, and on heating in the air burns with incandescence It is not attacked either by boiling nitric acid or aqua regia, but dissolves readily in a mixture of hydrofluoric and nitric acids

DETECTION AND ESTIMATION OF COLUMBIUM AND TANTALUM.

436 All columbates and tantalates are decomposed when the finely powdered minerals are fused with six times their weight of potassium hydroxide in a nickel or silver crucible, and on extracting with water potassium columbate and tantalate pass into solution On acidifying the solution, columbic and tantahc acids separate out as a white, amorphous precipitate somewhat soluble in excess of acid After treating the washed precipitate with ammonium sulphide to remove any tungstic acid, it may be tested for tantalum by dissolving in hydrofluoric acid, adding potassium fluoride, concentrating to a small volume, and allowing it to cool, characteristic needles of potassium fluotantalate separate out if tantalum is present. The filtrate is evaporated with excess of sulphuric acid to expel fluorine, cooled, diluted gradually with water, and treated with metallic zinc, if columbium is present a blue coloration is developed, due to a compound in which columbium is quadrivalent or trivalent[2] For carrying out the colour test, Giles[3] recommends that the solution of potassium tantalate and columbate be acidified with an excess of either oxalic or phosphoric acid, which holds the acid earths in solution, and the hot solution treated with zinc dust, when a yellow, brown, or nearly black colour is developed, according to the amount of columbium present Titanium, if present, gives

[1] **Hall and Smith, *J Amer Chem Soc*, 1905, 27, 1369**
[2] **See also Stahler, *Ber*, 1914, 47, 841**
[3] ***Chem News*, 1907, 95, 37.**

a similar colour when oxalic acid is used; but a lilac or violet tint if excess of piosphoric acid is present

In a reducing flame, the microcosmic salt bead is coloured blue, violet, or brown by columbic acid, and after the addition of a little ferrous sulphate becomes red No colour is produced by tantalic acid.

For the quantitative estimation of columbium and tantalum there are several methods available for decomposing the minerals In some respects, the neatest method is to heat the finely divided mineral in a stream of sulphur monochloride vapour[x] Columbium, tantalum, titanium, silicon, zirconium (?), tungsten, antimony (?), and most of the iron are thus removed as volatile chlorides and collected in a receiver charged with dilute nitric acid This is treated with excess of ammonia, and hydrogen sulphide passed in until the separated sulphur has dissolved Tungsten and antimony remain dissolved in the liquor, and, on filtering and washing, the mixed hydroxides of columbium, tantalum, titanium, silicon, and zirconium are obtained, together with ferrous sulphide. These are boiled with dilute sulphuric acid until the residual hydroxides of columbium, tantalum, titanium, and silicon are white The small amount of the acid oxides which passes into the filtrate is reprecipitated by making the solution nearly neutral and boiling while a current of hydrogen sulphide passes through it to maintain the iron in the ferrous state. The titanium may now be removed from the mixed hydroxides by boiling for several hours with excess of salicylic acid solution, in which it dissolves,[2] forming a yellow solution

The method that has been most frequently used in decomposing columbium-tantalum minerals is fusion with an excess of potassium hydrogen sulphate, the mixed acid oxides bemg separated as has already been described on p 977 According to Simpson,[3] it is preferable to fuse with six parts of caustic potash, and extract with dilute hydrochloric acid, for opening up the minerals In both these procedures, the presence of much titanium causes a considerable amount of the columbium and tantalum, particularly the former, to remain in solution[4]

[1] **Hicks,** *J Amer Chem Soc,* **1911, 33, 1492**

[2] **Dittrioh and Freund,** *Zeit anorg Chem,* **1908, 56, 344, 346, Muller,** *J Amer Chem Soc,* **1911, 33, 1606**

[3] *Bull West Australia Qeol Soc,* **1906, 23, 71,** *Chem News,* **1909, 99, 243**

[4] **Noyes,** *Tech Quart,* **1904, 17, 218, Warren,** *Amer J Set,* **1906, [4], 22,520, Crook and Johnstone,** *Min Mag,* **1912, 16, 244, Simpson,** *loc cit* **See also Sohoeller and Powell,** *Journ Chem Soc,* **1921,119, 1927**

For the separate determination of the columbium and tantalum, it is simplest to weigh the mixed pentoxides and to determine the columbium by a volumetric process, based upon its reduction to a state corresponding approximately with the oxide Cb_2O_3 and titration with potassium permanganate The reduction is effected by means of zinc in a sulphuric acid solution, succimc acid being added to maintain the columbium and tantalum in solution[x]

The only gravimetric process known is the classic procedure of Mangnac,[2] or one of its modifications [3] The mixed hydroxides are dissolved in a small excess of hydrofluoric acid, and the hot solution mixed with one of potassium fluoride, using about two parts of the latter for each part of mixed oxides estimated to be present The solution is concentrated to a small volume (10 cubic centimetres per gram of mineral under analysis) and set aside to cool The bulk of the tantalum crystallises out as K_2TaF_7, which is washed several times with very little water Filtrate and washings are concentrated to half the previous volume and cooled, when a further small crop of tantalum salt is obtained, washed, and examined with a lens for flat plates of the columbium salt, which must be removed, if present, by further washing A third crop of crystals is similarly obtained, examined, and washed

The final filtrate and washings, containing the columbium, is heated with excess of sulphuric acid to expel the fluorine, diluted with water, made slightly aikahne with ammoma, and heated to boiling The columbic hydroxide is filtered, washed, ignited, and weighed as $0b_2O_6$ The tantalum is similarly estimated in the combined crops of crystals, and the result increased by a small correction based upon the volumes of mother-liquor and wash-liquor obtained from the third crop of crystals This correction is, of course, subtracted from the weight of Cb_20_5

The Atomic Weight of columbium was determined by Rose, Hermann, and Blomstrand, but their results are now of historical interest only, and the first fairly accurate value, 94, was determined by Mangnac in 1865, from analyses of K_2CbOF_7,H_20. This value was unchallenged for over fifty years, when in 1908

[1] **Metzger and Taylor,** ***Zeit anorg Chem,*** **1909, 62, 382,** ***Chem News,*** **1909, 100, 257, 270 See also Levy,** ***Analyst,*** **1915, 40, 204**

[2] ***Ann Chim Phys,*** **1865, [4], 8, 5, 49**

[3] **Meimberg and Winzer,** ***Zeit angew Chem,*** **1913, 26, 157, Ruff and Schiller,** ***Zeit anorg Chem,*** **1911, 72, 329**

Balke and Smith[1] determined the ratio $2CbCl_5$ Cb_2O_6 by decomposing the Alonde with water and igniting the columbic acid to oxide Their results led to an atomic weight of 93 5 Subsequent work has shown that this method is not capable of giving results of the highest degree of accuracy, and a more trustworthy method was found by Smith and van Haagen,[2] who transformed sodium metacolumbate into sodium chloride by heating it in sulphur monochlonde, and from the ratio $NaCbO_3$ NaCl obtained the value 9313 The number at present (1922) adopted is accordingly 93 1

TANTALUM Ta - 181 5 At No 73

437 Metallic tantalum was first obtained in an impure state as a black powder by Berzehus, who heated potassium tantalofluonde with potassium Moissan succeeded in preparing it as a fused regulus by reducing the pentoxide with carbon in the electric furnace, but the metal thus obtained contained carbon[3] It was first obtained pure by von Bolton,[4] who prepared it by carrymg out Berzehus's reaction, and then heating the compressed powder of the metal in an electric furnace in a vacuum, and also by passing a current through a filament of Ta_2O_4 in a vacuum, the oxygen being thus removed and a filament of the metal left[5] It is also formed when the pentoxide is reduced by crude cerium (Weiss and Aichel), but the temperature is not sufficiently high to melt the tantalum, which is obtained as a silver-white, porous mass It is manufactured by the action of sodium on sodium tantalofluonde, or by the electrolysis of fused potassium fluotantalate, followed by melting the crude metal in *vacuo*[6]

The pure metal is silver-white in colour, has the sp gr 16 64 (von Bolton), melts at 2,850° (Pirani and Meyer), and has a normal atomic heat Its compressibility is $0\ 54 \times 10^{-6}$.[7] It is as hard as soft steel, and when hot can be rolled, haminered, and drawn into wire The tensile strength of the metal is very high, a fine wire giving a breaking test of 93 kilograms per square mm.

[1] *J Amer Chem Soc*, 1908, 80, 1644 [2] *Ibid*, 1915, 37, 1788
[3] *Compt rend*, 1902, **134,** 211
[4] *Zeit Elektrochem*, 1905, **11,** 45, 503, 722, German Patents, 152848, 152870, 153826, 155548, 161081, 163414, 171562
[5] *Zeit angew Chem*, 1906, 36, 1, 637 [6] *Mining Journal*, 1906, **80,** 363
[7] **Richards and Bartlett,** ***J*** *Amer Chem Soc*, 1915, **37,** 470

When heated in the air, thin wire burns, whilst more compact masses are oxidised superficially The red hot powder decomposes water, and in the form of wire readily absorbs nitrogen and hydrogen, 740 volumes of the latter being *taken* up at a yellow heat About three-quarters of this is lost in a vacuum at a red heat, but the remainder, which renders the metal brittle and increases its electrical resistance, is lost only on fusion[1] Tantalum is not attacked by aqua regia nor by any single acid except hydrofluoric acid, which dissolves it much more readily when the metal is in contact with platinum It is attacked also by fused alkalis It combines with nitrogen at a high temperature, more readily with sulphur Carbon appears to form with it a carbide and renders the metal brittle Alloys with iron, tungsten, and molybdenum can be obtained

The chief purpose for which metallic tantalum is employed is for the preparation of filaments for electric lamps Wire of 0 05 mm diameter is employed, and as the resistance is much less than that of a carbon filament, a much longer filament is used than in a carbon lamp The lamps require only about half the energy needed by a carbon lamp of equal candle-power

It has also been suggested to use tantalum in place of the more expensive platinum for crucibles, electrodes, etc, and for dental and surgical instruments

COMPOUNDS OF TANTALUM

TANTALUM AND OXYGEN

438 *Tantalum Tetroxide,* Ta_2O_4 or TaO_2, is formed when the pentoxide is heated in a very small carbon crucible, exposed to the highest heat of a wind furnace, or reduced by metallic magnesium It is a porous, dark-grey mass which scratches glass, and when rubbed on a hone has a steel-grey colour It gives a dark-brown non-metallic powder, and is not attacked by acids, even by a mixture of hydrofluoric and nitric acids, but burns when heated, with formation of the pentoxide

Tantalum Pentoxide, Ta_2O_6 —The preparation of this body has already been described (p 977) It is a white, amorphous, infusible powder which when strongly heated becomes crystalline, and when ignited with boron trioxide or melted with microcosmic

[1] **Piccini,** ***Zeit Elektrochem,*** **1905, 11, 555**

salt in a porcelain furnace is obtained in rhombic prisms When gently heated it has a specific gravity of 7 35, which after exposure to a white heat rises to 8 7 The lgmted pentoxide does not dissolve in any acid

Tantahc Acid or *Tantalum Hydroxide,* $HTa0_3$, is obtained in the form of a gelatinous mass when the chloride is quickly mixed with water If, however, the same compound be exposed to moist air until it is decomposed, and then mixed with water containing ammonia, the hydroxide is obtained as a crystalline powder, which when dried at 100° possesses the above composition, and is converted with vivid incandescence into pentoxide when heated to low redness The hydroxide obtained from the double fluoride by treatinent with acid potassium sulphate does not exhibit this phenomenon Tantalic acid dissolves in hydrofluoric acid, and, when freshly precipitated, in other acids

The Tantalates—The normal tantalates, to which class the tantalum minerals belong, are all insoluble in water Besides these, others are known, derived from the unknown hydrate, hexatantahc acid, $H_8Ta_60_{19}$, or $4H_20,3Ta_20_5$, of which only the compounds of the alkali metals are soluble in water

Potassium Hexatantalate, $4K_20,3Ta_20_5,16H_20$, is formed by dissolving the acid in caustic potash, and also by fusing the pentoxide with double its weight of caustic potash The fused mass is dissolved in water and allowed to evaporate in a vacuum Transparent, glistening, monoclimc crystals are thus obtained which dissolve in lukewarm water without decomposition On boiling or evaporating in the air, salts containing more tantalum are formed If it be repeatedly lgmted with ammomum chloride and washed with water the normal salt, $KTa0_3$, is obtained

Sodium Hexatantalate, $4Na_20,3Ta_20_5,25H_20$, is obtained in a similar way to the potassium salt, a vivid incandescence occurring when the mixture is heated to redness The fused mass is boiled out with water, and the solution either allowed to cool or, inasmuch as the salt is insoluble in caustic soda, poured on to the top of a strong solution of this substance It crystallises in small, hexagonal tablets which dissolve at 13 5° in 493, and at 100° in 162 parts of water It is not decomposed by boiling water, and if the aqueous solution be mixed with alcohol a precipitate of $NaTa0_3,H_20$ is formed, and this becomes anhydrous on ignition The anhydrous salt is also formed by the ignition of the hexatantalate

Rubidium and *Cæsium* hexatantalates crystallise with $14H_20$ and are isomorpbous with the corresponding columbates[1]

When tantalum pentoxide is strongly ignited with the chlorides of calcium, magnesium, and other metals, crystalline tantalates of these metals are obtained [2]

Pertantahc Acid —When a large excess of hydrogen peroxide is added to a solution of potassium hexatantalate and potassium hydroxide and the liquid mixed with an equal volume of alcohol, a white, crystalline precipitate of *potassium pertantalate* K_3Ta0_8, is obtained [3] This salt is decomposed by sulphuric acid with formation of a white precipitate of hydrated *pertantahc acid,* $HTa0_4$ This substance is more stable than percolumbic acid, but yields hydrogen peroxide when heated for some time at 100° with dilute sulphuric acid, and evolves ozomsed oxygen when treated with concentrated sulphuric acid The salts appear to be derived from the unknown ortho-form of this acid, which would have the formula $(HO\ 0)_3Ta0_2$ The sodium, rubidium, and caesium salts are also known [4]

TANTALUM AND THE HALOGENS

439 *Tantalum Pentafluoride,* TaF_5, is prepared exactly like the columbium compound, which it closely resembles in properties It forms large, colourless prisms of density 4 744, melts at 96 8°, and boils at 229 2 to 229 5° [5]

Potassium Tantalofluonde, K_2TaF_7—The mode of preparing this salt has been already described (p 977) It forms small, rhombic needles which readily melt, but it does not decompose when ignited even to whiteness in a platinum vessel It is easily soluble in hot, though sparingly so in cold water (about 1 part in 200 parts of water) When the solution is boiled decomposition takes place rapidly, a white powder of the *oxyfluoride,* $K_4Ta_40_5F_{14} = 4KF,2TaF_5,Ta_20_5$, separating out Hence the salt should be crystallised from dilute hydrofluoric acid

Sodium Tantalojluonde, Na_2TaF_7,H_20, is obtained in a similar manner to the potassium salt, or by dissolving sodium hexa-

[1] **Balke and Smith,** ***J Amer Chem Soc*** **, 1908, 30, 1637**
[2] **Joly,** ***Compt rend,*** **1875, 81, 266, 1266**
[3] **Melikoff and Pissarjewsky,** ***Zeit anorg Chem,*** **1899, 20, 340**
[4] **Balke,** ***J Amer Chem Soc,*** **1905, 27, 1140, Balke and Smith,** ***ibid,*** **1908, 30, 1637**
[5] **Ruff and Schiller,** ***Zeit anorg Chem,*** **1911, 72, 329**

tantalate in hydrofluoric acid On evaporation, indistinct crystals of Na_3TaF_8 separate out, and then eight-sided rhombic tablets of the above salt, which lose their water below 100°

Ammonium, rubidium, and caesium salts of the type $2M^IF,TaF_5$ are also known, as well as the corresponding zinc and copper salts[1] Lithium, sodium, and caesium double fluorides of the type MT,TaF_5 have also been described[2] Hydrogen peroxide converts the potassium and rubidium salts, $M^r{}_2TaF_7$, into the *pervxytfluondes,* $2M^rF,TaG_2F_3,H_20$, which crystallise in colourless plates (Piccim, Balke and Smith)

Tantalum Pentachloride, $TaCl_5$, is obtained by heating an intimate mixture of the pentoxide and carbon in a current of chlorine, and is also formed when the pentoxide is heated with phosphorus pentachloride It is best prepared by heating the pentoxide in a current of chlorine mixed with either sulphur monochlonde or carbon tetrachloride[3] It forms light yellow needles and prisms of density 3 *68,* which melt at 211° and boil at 242°, but begin to volatilise at so low a temperature as 144°, and may be readily sublimed in a current of carbon dioxide or chlorine The specific gravity of the vapour, according to Deville and Troost, is 12 8, the calculated density being 12 42 It fumes in the air, and is converted into tantalic acid by water. It is reduced by aluminium in presence of aluminium chloride to a mixture of lower chlorides[4]

Tantalum Pentabromtde, $TaBr_5$, is prepared by heating a mixture of equal parts of the pentoxide and carbon in a current of bromine vapour It is best purified by sublimation *%n vacuo*[5] It forms yellow, elongated lamellae, which melt at 240° to a ruby-red liquid and boils at 320° The vapour resembles chlorine in colour It fumes in air and is rapidly decomposed by water The bromide may be sublimed in an atinosphere of hydrogen, but at high temperatures partial reduction to the metal takes place, also, traces of green bromotantalum bromide are produced When the bromide has been exposed to traces of moisture and is then sublimed in *vacuo,* tantalum oxybromide, $TaOBr_3$, is left as a small residue

[1] Mangnac, *Ann Chim Phys,* 1866, [4], 9, 247, Balke, *he cit*

[2] Balke, *J Amer Chem Soc,* 1905, 27, 1140

[3] Hall and Smith, *ibid,* 1905, 27, 1369, Balke, *ibid,* 1910, 32, 1127, Ruff and Schiller, *Zeit anorg Chem* , 1911, 72, 329

[4] Ruff and Thomas, *Ber* , 1922, 55, [B], 1466

[5] van Haagen, *J Amer Chem Soc* , 1910, 32, 729, Smith and Chapin, *ibid* , 1911, 33, 1497

Tantalum Pentaiodide, TaI_5, is prepared by distilling the pentabromide slowly several times in a brisk current of dry hydrogen iodide [1] It sublimes in nearly black lamellae, and fuses to a dark brown liquid which gives a vapour resembling bromine The iodide closely resembles the chloride and bromide in properties

HALIDE BASES OF TANTALUM

Bromotantalum Bromide, $(Ta_6Br_{12})Br_2,7H_20$, is prepared by heating tantalum pentabromide with four parts of 3 per cent sodium amalgam in vacuo, the temperature being gradually raised to a red heat The mass is cooled *in vacuo,* extracted with boiling dilute hydrobromic acid, filtered from the residual brown powder (a lower oxide of tantalum), and concentrated on a water-bath

The bromide forms small dark green crystals which are soluble in water, forming an emerald green solution, a one per cent solution of which appears opaque in a half-mch layer It is stable at 100° From boiling- and freezmg-point determinations, it has been found that the salt dissociates in solution into three ions, so that the formula should be written $(Ta_6Br_{12})Br_2,7H_20$, the group Ta_6Br_{12} behaving as a divalent radicle of considerable stability In cold aqueous solution, silver nitrate precipitates only one-seventh of the total bromine

By the interaction of the bromide with the theoretical amount of caustic soda, a green, crystalline precipitate of br*omotantalum hydroxide,* $(Ta_6Br_{12})(OH)_2,10H_2O$, is obtained, nearly insoluble in water S

hydnodic acids leads to the formation of *bromotantalum chloride,* $(Ta_6Br_{12})Cl_2,7H_20$, and *bromotantalum iodide,* $(Ta_6Br_{12})I_2,7H_20$, respectively The former may also be obtained from the bromide by evaporation with hydrochloric acid, and in cold aqueous solution it gives a precipitate of silver chloride, free from bromide, upon the addition of silver nitrate [2]

Chlorotantalum Chloride, $(Ta_6Cl_{12})Cl_2,7H_20$, is obtained by reducing tantalum pentachlonde with sodium amalgam, as in the case of the bromotantalum bromide, which it resembles in appearance and properties (Chapm) This salt was first obtained,

[1] van Haagen, *loc cit*
[2] Chapin, *J Amer Chem Soc,* 1910, 32 323

m very small dtaoiint, by Chabrie, who mistook it for a dichloride, $TaCl_2 2H_2O$[1]

TANTALUM AND SULPHUR

440 *Tantalum Bisulphide,* TaS_2, is produced in the crystalline form when the pentoxide is heated to 900° in a stream of hydrogen sulphide and carbon disulphide It begins to sublime at 1200° and is stable at 1300° [2]

TANTALUM AND NITROGEN

441 When tantalum chloride is heated in ammonia gas to a temperature not above the point of volatilisation of the ammonium chloride which is formed, an amorphous, yellowish-red mass of varying composition is obtained If thjs is powdered and heated to redness in a stream of ammonia it is converted into a bright red, amorphous powder having the composition Ta_3N_5 When this is raised to a full white heat in an atinosphere of ammoma, an amorphous, black powder of *tantalum nitnde,* TaN, is produced which exhibits a metallic lustre on burnishing II Rose, who first obtained this compound, believed it to be the metal [3] The nitride, Ta_3N_5, is also obtained when metallic tantalum is heated in nitrogen gas to a temperature of 1000 °

TANTALUM AND CARBON

Tantalum Carbide —When 6 parts of Ta_20_6, 1 part of sodium carbonate, and 1 part of charcoal are heated to a temperature of about 1480°, tantalum carbide, TaC, is produced in the form of fine needles [4]

DETECTION AND ESTIMATION OF TANTALUM

442 The detection and estimation of tantalum have already been discussed under columbium (p 987)

The Atomic Weight was determined by Mangnac,[5] who analysed the potassium and ammomum tantalofiuondes and obtained the number 183. For forty years the accepted value

[1] ***Compt rend,* 1907, 144, 804**
[2] **Biltz and Kircher, *Ber,* 1910, 43, 1636**
[3] **Muthmann, Weiss, and Riedelbauch, *Annalen,* 1907, 355, 58**
[4] **Joly, *Compt rend,* 1876, 82, 1195**
[5] ***Ann Chim Phys,* 1866, [4], 9, 251**

for the atomic weight rested upon the analyses made by Mangnac, which were by no means concordant, then, in 1906, by direct conversion of the metal into the pentoxide Hmrichsen and Sahlbom[1] obtained the number 181 Later, by converting the pentachlonde into the oxide, Balke[2] found 18152, and Chapm and Smith found 181·8 by transforming the pentabromide into the oxide[3] The number at present (1922) adopted is 181 5, but the work of Sears and Balke[4] indicates that this result is probably in need of revision

ANTIMONY (STIBIUM). Sb = 120 2 At No 51

443 This metal occurs in nature chiefly as stibnite, antimonite, or antimony sulphide, Sb_2S_3, a mineral which was known in very early times, having been long employed, as indeed is yet the case, by women in the East for painting the eyebrows In St Jerome's translation of the Hebrew of Ezekiel xxin 40, we read " circum-lmisti stibio oculos tuos ", and in the Second Book of Kings IX 30, we find, " Porro Jezebel introitu ems audito depixit oculos suos stibio " Of this latter passage Cheyne and Drover give as the translation of the Hebrew, " set her eyes in paint (literally antimony) "

The name for this mineral in Hebrew and Arabic is " Kohl," and this word passed as " alcool" or " alkohol" mto other languages, thus in the Spamsh translation of the Bible the above passage from Ezekiel is thus rendered, " Alcoholaste tus ojos " In the middle ages the word alcohol indicated any fine powder, it was only at a later period that it was employed to mean spirits of wine Dioscondes calls this metal , and mentions that it is also known by other terms, such as , the eye-expander, *yvvaifceiov*, belonging to womankind, etc Pliny, on the other hand, terms it *stibium* The Latin Geber, who also was acquainted with this substance, termed it *antimomum,* and up to the time of Lavoisier both these words were made use of to signify sulphide of antimony The German name was *spiessglas,* afterwards changed to *spiessglanz* As already mentioned (Vol I, p 9), the works attributed to " Basil Valentine," which have hitherto been regarded as the earliest known records concerning antimony and its derivatives, were shown by Schorleminer to be

[1] *Ber,* 1906, 39, 2600 [2] *J Amer Chem Soc,* **1910, 32, 1127**
[3] *Ibid,* **1911, 33, 1497** [4] *Ibid,* **1915, 37, 833, 1917, 39, 1582**

forgeries dating from about 1600 [1] There is no doubt, however, that the latro-chemists, from the time of Paracelsus, were acquainted with many antimomal preparations, and numerous references to these are scattered throughout the chemical literature of those times The statements of " Basil Valentine " may still serve to show the condition of knowledge concerning antimony in 1600 He remarks in his *Triumphal Car of Antimony* " In order, as is most proper, that I may say something about the name of the material, it should be understood that this material was long known to the Arabians, and from ancient time was termed by them *asmat* The Chaldeans entitled it *stibium,* and in the Latin tongue it has been called *antimonium* [2] up to the latest times, and in our own German mother tongue the same material has been foolishly called spressglas for this reason, that this material can be fluxed and a glass made from it "

Dioscorides mentions that in order to roast the crude antimony it must be heated in a current of air until it burns, for if more strongly ignited, it melts like lead This passage has given rise to the supposition that the author was acquainted with metallic antimony, and that this is probably the case is shown by the fact that an old Chaldean vase analysed by Berthelot consisted of pure antimony[3] Antimony was confounded with bismuth by some chemists, such as Libavius, even so late as the sixteenth century

The preparation of the metal was described by " Basil Valentine," who in his *Wiederholung des Grossen Steins der uralten Weisen* terms it *spressglas rex* and also *plumbum antimonn* It has already been stated that the alchemists considered each semi-metal to be a variation of a true metal

444 Antimony occurs in many other minerals besides stibmte The metal is found, though not frequently, in the native state, and also as arseniferous antimony or allemontite (AsSb) Antimony also occurs as the trisulphide, Sb_2S_3, combined with basic sulphides, and in these thioantimonites a portion of the antimony is usually replaced by arsenic Amongst such compounds are berthiente, FeS,Sb_2S_3, wolfsbergite or antimomal copper, Cu_2S,Sb_2S_3,

[1] MSS deposited in the library of the University of Manchester See also Pierce, *Science,* 1898, 8, 169, who conies to the same conclusion, chiefly from a study of the contents of Basil Valentine's works

[2] The story of the accidental poisoning of certain monks by spressglas having given rise to the name of the metal (antimoine) is on the face of it improbable, and must, as Kopp remarks, have been invented by a Frenchman, whereas Valentine wrote in German 1

[3] *Compt rend,* 1887,104, 265

boulangente, $5PbS,Sb_2S_3$, jamesonite $2PbS,Sb_2S_3$, bournonite, $2PbS,Cu_2S,Sb_2S_3$, pyrargynte or red silver ore, $3Ag_2S,Sb_2S_3$, etc In addition to these we have dyscrasite or antimonial silver, Ag_3Sb, breithauptite or antimonial nickel, NiSb, ullmanmte or nickeh-ferous grey antimony, NiSbS, valentinite or antimony oxide, Sb_20_3, cervamte or antimony ochre, Sb_20_4 and stiblite, Sb_20_4,H_20 Antimony is also found in small quantity in iron ores, ferruginous waters, in the coal formation, and in river sand

445 *Preparation of Metallic Antimony*[1]—The preparation of the metal from the sulphide is a very simple operation In order to free the ore from quartz or other earthy admixture, the mineral is either melted in vertical cylinders which have a hole at the bottom out of which the molten sulphide drops, or the preliminary fusion is carried on in reverberatory furnaces The purified sulphide is then fused with metallic iron, or roasted to convert it into oxide, which is reduced with carbon or crude tartar " Basil Valentine " describes both of these methods in his account of the preparation of the philosopher's stone, he states " Antimonmm is a master in medicine, and from it by means of cream of tartar and salt a King (regulus) is made, steel-iron being added to the spressglas during fusion Thus by an artifice a wonderful star is obtained which the learned before my time have termed the philosophical signet star " In the *Triumphal Car of Antimony* he gives the following receipt " Take good Hungarian spressglas and with the same quantity of crude tartar, and half as much saltpetre rub these small and let them fuse well in a wind furnace, afterwards pour out into a moidd and allow to cool when a regulus is found "

In the English process, three operations are used for the production of the best star-antimony The first of these is termed " singling ", in this 40 parts of the liquated sulphide are mixed with about 18 parts of thin scrap iron and 4 parts of salt, and this is then melted in plumbago crucibles, when metallic antimony and iron sulphide are formed The fusion lasts about an hour and a half, and when complete the charge is poured into corneal moulds The crude metal is then separated from the slag, consisting chiefly of sulphide of iron, which floats on the surface, and it is again melted in the second process of " doubling," with an addition of a small quantity of liquated stibnite, sodium sulphate or salt, and slag obtained in the following operation The charge for each pot is 80 lb of crude antimony, 7 lb of

[1] For full particulars, see *Antvnumy,* by C Y Wang (C Griffin & Co , 1909)

liquated stibnite, 2 lb of salt-cake, and 2 lb of slag, and the fusion lasts about an hour and a half The metal is cast in moulds, allowed to cool, and broken into small pieces ready for the third process, termed melting for star-metal" For this purpose 2 parts of pearl-ash and 5 parts of slag from a previous operation of the same kind are added to 60 parts of metal, and the fusion is repeated The molten metal is then poured into square moulds in which it is allowed to cool slowly, the surface being at the same time completely covered with slag in order that it may attain the peculiar crystalline structure which is required in cominerce

In the roast and reduction method for the extraction of antimony, two distinct processes are in use, in the first, the sulphide ore is roasted to the stable tetroxide, generally in reverberatory or muffle furnaces at a temperature of about 350° In the second process the volatile trioxide is formed by restricting the amount of air admitted, and working at a higher temperature, and is condensed in pipes and chambers This process has several advantages, for low grade ores may be treated with success, arsenic oxide may be separated owing to its greater volatility, and in the case of ores containing precious metals, these may be extracted from the residues

The oxide of antimony obtained by either process may be reduced to the metallic state by fusion with coal or charcoal, together with alkaline fluxes such as potash, soda, etc , in small reverberatory furnaces or crucibles

It has been stated already that " Basil Valentine " was acquainted with the crystalline surface exhibited by pure antimony, but he specially mentions that the regulus which is not starred possesses exactly the same composition as that which presents this peculiarity He, as well as some of his contemporaries, believed that the stellated surface was produced only when iron was employed in the preparation, whilst other chemists taught that the preparation of the stellated antimony was connected with a favourable conjunction of the stars Indeed this latter opimon was generally held until the time of Boyle, who, however, discredited both views

In his essay *On the Unsuccessfulness of Experiments,* Boyle [1] says " And it may perhaps also be from some diversity either

in antimo

observed) often failed in their endeavours to make the starry regulus of *Mars* and antimony Insomuch that divers artists

i ***Opera,*** **ed 1772,1, 325**

fondly believe and tfcach (what our experience will not permit us to allow) that there is a certain respect to times and constellations requisite to the producing of this (I confess admirable) body Upon this subject I must not omit to tell you that a while smce an industrious acquaintance of ours was working on an antimony, which unawares to him, was, as we then supposed, of so peculiar a nature, that making a regulus of it alone without iron, the common way (for his manner of operation I inquired of him), he found, to his wonder, and showed me his regulus adorned with a more conspicuous star than I have seen in several stellate reguluses of both antimony and *Mars* " Lemery, in his *Cours de Chymie,* published in 1675, also argues strongly against the supposition that the planet Mars has anything to do with the formation of the stellated surface

Cominercial antimony often contains traces of silver, gold, arsenic, iron, lead, copper, and frequently some sulphur In order to prepare the pure metal, 16 parts of the cominercial metal are fused with 2 parts of sodium carbonate and 1 part of sulphide of antimony for an hour, on cooling, the regulus is separated from the slag, and melted again for an hour with 1½ parts of sodium carbonate, and the operation again performed with 1 part of this salt,[1] a small quantity of nitre being added from time to time[2] The whole of the arsenic is thus separated, provided that a sufficient quantity of iron be originally present in the met about 2 per cent of iron sulphide[3]

Another method for preparing pure antimony is as follows[4] Redistilled antimony trichloride or pentachlonde is dissolved in concentrated hydrochloric acid, chlorine passed into the solution until it becomes greenish-yellow, and hydrogen chlorine then conducted into it, when chloroantimonic acid crystallises out This is purified by recrystallisation, decomposed by hot water to antimonic acid, and the latter reduced to the metal by fusion with potassium cyanide

446 *Properties* —Antimony is a lustrous silver-white metal, which when slowly cooled exhibits a coarsely laminated crystalline fracture When quickly cooled, on the other hand, the fracture is granular It crystallises in obtuse rhombohedra which can scarcely be distinguished from cubes, and has a specific

[1] Liebig, *Annalen,* 1857, **104,** 223 [2] *Ibid,* 1835, 19, 22
[3] Bensch, *ibid* , 1847, 63, 273 See also Meyer, *ibid,* 1848, 66, 238
[4] Groschuff, *Zeit anorg Chem,* 1918, **103,** 164

gravity of 6 71 to 6 86 Native antimony occurs in scaly masses, usually containing silver, iron, and arsenic Its most important localities are aj| Sahl in Sweden, Andreasberg in the Harz, Przibram in Bohemia, in the Dauphmy, in Canada, the United States, Mexico, Chili, Sarawak, in Borneo and Queensland Native antimony has a specific gravity of from 6 5 to 7 The metal has a normal atomic heat at ordinary temperatures, at 80° (Abs) its atomic heat is 5 19 [1]

Antimony is hard, and so brittle that it can be powdered, it melts at 630 3°,[2] and volatilises at a bright red heat in the air, or in a current of a gas, but not when fused under a layer of common salt It may be distilled in a current of hydrogen at a white heat The vapour density of antimony is 10 74 at 1572°, and 9 78 at 1640° (Meyer and Biltz),[3] numbers which are intermediate between those required for the molecular formulae Sb_2 and Sb It does not undergo any alteration on exposure to the air at the ordinary temperature, on heating it burns to form the oxide, and when heated on charcoal before the blowpipe, the oxide is evolved in thick, white fumes, and a portion of it is deposited as a white incrustation on the charcoal If the blast of air be stopped the globule of molten metal begins to glow, and is seen to be covered with a crystalline network of needles of oxide, and when the globule is thrown from some height on to a piece of paper, the edges of which are turned up, it breaks into many smaller globules which burn with a very bright flame Neither cold water nor dilute sulphuric acid acts upon the metal at the ordinary temperature, but at a red heat it decomposes steam with formation of oxide Nitric acid converts it into a white powder, the composition of which depends on the strength of the acid, nitrogen peroxide being evolved and no ammoma formed [4] Pure antimony does not dissolve in strong hydrochloric acid in the absence of oxygen,[5] but the ordinary metal is easily dissolved by hot hydrochloric acid as well as by cold aqua regia, and when hearted with concentrated sulphuric acid is converted into antimony sulphate Antimony combines directly with the elements of the chlorine group, with those of the sulphur group, and with phosphorus and arsenic

[1] Gunther, *Ann Phyaik,* 1920, [4], 63, 476

[2] Holborn and Bay, *ibid,* 1900, [4], 2, 505 See also Heycock and Neville, *Journ Chem Soc,* 1895, 67, 186, Grosschuff, *Zeit anorg Chem* , 1918, **103,** 164

[3] *Ber,* 1899, **22,** 725 See also *Annalen,* 1887, **240,** 317

[4] Montemartini, *Gazz* , 1892, **22,** 384

[5] Ditte and Motzner, *Compt rend* , 1892,**115,** 936

Colloidal solutions of antimony may be obtained by acting upon a tartaric acid solution of potassium antimonate with potassium hyposulphite [1]

Allotropic Modifications of Antimony—The grey, metallic form of antimony described above is the stable modification, although Cohen regards it as a mixture of several allotropic forms the relative proportions of which depend upon the previous history of the metal [2] Unstable yellow and black modifications, corresponding with the unstable yellow and stable grey forms of arsemc (Vol I, p 691) also exist [3] The yellow form is obtained by the action of oxygen on liquid stibine at —90°, and by the action of chlorine on stibine, both dissolved in liquid ethane at —100° It is amorphous, appears to dissolve slightly in carbon disulphide, and passes very readily, when the temperature rises above — 90°, into the black variety The latter can also be prepared by the rapid cooling of antimony vapour, and by the action of oxygen, on liquid stibine at —40° It is an amorphous black powder, has the specific gravity 5 3, oxidises spontaneously in the air, s stable metallic form with evolution of heat

Explosive or Electrolytic Antimony—This peculiar substance, discovered by Gore,[4] is obtained by electrolysis of an acid solution of antimony trichloride having a specific gravity of 1 35, or of a solution obtained by dissolving the trioxide in from five to six times its weight of hydrochloric acid of specific gravity 1 12, metallic antimony being, in each case, used as the positive, and copper or platinum as the negative pole The latter becomes covered with a grey, lustrous, metallic coating, having an amorphous fracture and a specific gravity of 5 78 It contains from 4 8 to 7 9 per cent of antimony chloride, together with a small quantity of free hydrochloric acid When scratched with a metallic point or touched with a red hot wire it decomposes with evolution of heat and liberation of the chloride, and when heated to 200° it flies into powder with a loud explosion If it be preserved under cold water it does not iminediately undergo any alteration, but when heated to 75° it decomposes with a hissing sound, hydrochloric acid is found in solution, and the water becomes turbid owing to the formation of basic antimony

[1] See Gutbier and Krautle, *Kolloul Zeit,* 1917, **20,** 194

[2] Cohen and van den Bosch, *Zed physikal Chetn ,* 1915, **89,** 757

[3] Stock and Guttinann, *Ber,* 1904, 37, 885, Stock and Siebert, *ibid,* 1905, 38, 3837

[4] *Phil Trans,* 1858, **148,** 185, 1859, **149,** 797, 1862, **152,** 323, Pfeifor, *Annalen,* 1881, **209,** 61

chloride Similar products are obtained by the electrolysis of acid solutions of the bromide and iodide (Gore), but not of the fluoride

This remarkabIe substance is probably a solid solution of an antimony halogen compound in an allotropic form of antimony, and the explosion consists in the sudden transformation of the latter into the stable metallic form, the heat evolved amounting to 20 cal per gram, the same change goes on slowly when the explosive material is preserved [1] This form is possibly identical with the black amorphous form described above, but the identity has not been definitely proved

Uses—Antimony is employed for the preparation of tartar emetic, and of other products used in pharmacy and in many processes of calico printing and dyeing Its alloys are also largely used in the arts When antimony is precipitated by zinc from a solution of the trichloride, the metal is obtained in a finely pulverulent state, as *antimony black,* this is employed for the purpose of imparting to the surface of gypsum figures and other objects the appearance of iron or steel

447 *Antimony Alloys* —" Basil Valentine " mentions that antimony is valuable for the preparation of medicines, and that it is likewise employed for other purposes, such as for the preparation of printers' type He adds that under certain favourable conjunctions of the planets alloys are made of antimony, and from these seals and amulets are cast, which are said to possess special virtues These same alloys can, according to Valentine, be cast in the same way to form both bells and mirrors

English type metal is an alloy of lead, antimony, and tin A small percentage of copper is sometimes added, but is found of little practical value The value of antimony in these alloys is that it imparts to them hardness, and gives them the property of expanding in the act of solidification so necessary in order to obtain an accurate cast of the letter The tin gives toughness and coherence to the metal, The following are analyses of English type metal

	I	II	III	IV	V	VI	VII
Lead	50	60 0	61 3	96 2	85 7	83 5	80 0
Antimony	25	30 0	18 8	19 5	14 3	13 5	15 0
Tin	25	10 0	20 2	9 1	—	3 0	5 0
Copper	—	—	—	1 7	—	—	—

[1] **Cohen and Ringer, *Zeit physikal Chem,* 1904, 47, 1, Cohen, Collins, and Strengers, *ibid,* 1905, 50, 291, Cohen and Strengers, *ibid,* 1905, 52, 129**

No I is supposed to give the best results for high, class work, but owing to the high price of tin No II is generally used No V is used for stereotype plates, No VI is linotype metal, and No VII monotype metal

Britannia Metal and *Pewter* —This silver-white metal is largely used for the preparation of spoons, cups, and other articles It consists mainly of tin and antimony, but frequently contains other metals, as is shown by the following analyses

	Britannia Metal		Plate Pewter	Ashbury Metal	Metal Argentum
Tin	85 7	819	89 3	77 8	85 5
Antimony	10 4	16 2	7 1	19 4	14 5
Copper	10		18		
Zinc	29	19		28	
Bismuth			18		

White or *anti-friction metal* is chiefly used for lining the brasses of various parts of locomotive engines and for the solid bushes for the coupling-rods Several alloys are used for this purpose, as is seen by the following analyses

	I	II	III
Copper	5 3	15	—
Antimony	10 5	13 0	20
Tin	84 2	45 5	20
Lead	—	44 0	60

The alloy employed for the manufacture of ship's nails consists of 3 parts of tin, 2 of lead, and 1 of antimony

Brass articles can be covered with a fine, lustrous coating of antimony by dipping them into a hot solution of 1 part of tartar emetic, 1 of tartaric acid, and 3 of water, to which 3 or 4 parts of hydrochloric acid and as much powdered antimony have been added

Antimony forms a beautiful purple alloy with copper which has the composition Cu_2Sb, and is known as Eegulus of Venus With tellurium it forms a continuous series of mixed crystals [1]

[1] Dreifuss, *Zat Flektrochem*, 1922, 28, 100, 224

COMPOUNDS OF ANTIMONY

ANTIMONY AND HYDROGEN

448 *Antimony Hydride* or *Stibine,* SbH_3—This substance was first prepared 111 1837 by Lewis Thompson,[1] and also independently by Pfaff [2] and other chemists It is formed when nascent hydrogen is brought into contact with a soluble antimony compound, or when an alloy of potassium or sodium with antimony is decomposed by water, or an alloy of zinc and antimony by dilute hydrochloric or sulphuric acid It is also formed when antimony oxide is added to an acid solution which is evolving hydrogen All these methods, however, furnish a gas which is largely mixed with free hydrogen,[3] and the preparation of pure stibine is a matter of some difficulty The liquefied gas was first obtained by Olszewski [4] in 1886, and the pure gas itself by Stock and Doht [5] in 1901 A gas containing as much as 14 per cent of stibine is first prepared by gradually bringing a powdered alloy of 1 part of antimony and 2 parts of magnesium, prepared by heating the constituents to redness in an atinosphere of hydrogen, into hydrochloric acid of sp gr 1 06 at 0°, which has been previously boiled When this gas is washed through water, dried over calcium chloride and phosphoric oxide, and cooled by liquid air, it yields a white mass of solid stibine, and this on evaporation gives pure stibine, free from admixed hydiogen The gas thus piepared can be collected over mercury, and when dry can be preserved for some hours without undergoing decomposition It is a colourless gas with a characteristic odour, faintly resembling that of sulphuretted hydrogen, and is very poisonous It condenses to a colourless liquid, which boils at —17°, and solidifies to a white mass, melting at — 88° The density of the gas is 4 36 at 15° and 760 mm , this being about 2 95 pei cent greater than the calculated normal density The density of the liquid is 2 26 at —25° Water dissolves about 0 2 vol of the gas, and in the absence of impurities the solution is stable for some time, whilst in the presence of mere traces of air decomposition sets in rapidly Alcohol dissolves 15 vols of the gas, and carbon

[1] *Phil Mag* , 1837, [3J, 10, 353 [2] *Fogg Ann* , 1837, 42, 339
[3] See Jones, *Journ Chan Soc* , 1876, 29, 1, 641
[4] *Montash* , 1886, 7, 371, *Ber* , 1901, 34, 3592
[5] *Ber,* 1901, 34, 2339, 1902,36, 2270, Stock and Guttinann, *ibid,* 1904, 37, 885

disulphide 250 vols , but both these solutions are very unstable Stibine decomposes slowly at the ordinary temperature into antimony and hydrogen, one volume yielding 1 544 vols of hydrogen The rate of decomposition has been carefully studied,[1] and is greatly accelerated by the presence of water, of metallic antimony, or of hydrogen chloride The gas is formed from its elements with absorption of 84,500 cal ,[2] and explodes when a spark is passed through it, or when it is strongly heated Spontaneous explosion also occurs occasionally and may extend to the liquid

Stibine is very readily decomposed by oxygen and air, with formation of water and metallic antimony, and is also attacked by nitric and nitrous oxides, and explodes when brought into contact with chlorine It is easily inflammable, burning with a greyish flame, and evolving white- fumes of antimony oxide If passed through a glass tube heated above 150° metallic antimony is deposited close to the heated spot in the form of a lustrous mirror, and if this be heated more strongly, microscopic metallic globules are formed Concentrated sulphuric acid decomposes the gas Caustic alkali solution becomes deep brown when the gas is passed through it, and at last a black powder separates out The brown solution absorbs oxygen rapidly, and especially if it be shaken with air The powder appears to possess the composition $Sb(OH)_3$ It rapidly decomposes on standing, becoming richer in antimony When antimony hydride is passed through a solution of silver nitrate, black silver antimonide, $SbAg_3$,[3] is first formed, the excess of silver nitrate present, however, causes a further reaction to take place, and the final precipitate consists of silver and antimony hydroxide, with a little metallic antimony[4] Sulphur decomposes the gas, becoming covered with a film of the orange-red antimony sulphide (Jones)

$$2SbH_3 + 6S = Sb_2S_3 + 3H_2S$$

Sulphuretted hydrogen has no action on the pure gas, but readily decomposes the impure mixture with hydrogen

[1] Stock and Guttinann, *Ber*, 1904, 37, 901, 1957, Bodenstein, *ibid*, 1904, 37, 1361, Stock, Gomolka, and Heynemann, *ibid*, 1907, 40, 532, Stock, Echeandia, and Voigt, *ibid*, 1908, 41, 1309

[2] Berthelot and Petit, *Compt rend* , 1889,**108,** 546

[3] Lassaigne, *J Chim Med* , 1840,17, 443

[4] Iteckleben, *Ber*, 1909, 42, 1458, see also Vitah, L'*Orosi*, 1892, 397

ANTIMONY AND OXYGEN

449 Conquerable doubt formerly existed as to the number of the oxides formed by antimony Thenard, in 1800, mentions several, whilst Proust, in 1804, admitted the existence of only two The exact number was ascertained by Berzelms in 1812 to be as follows

Antimony trioxide, Sb_4O_6,
Antimony tetroxide, Sb_2O_4,
Antimony pentoxide, Sb_2O_5

All these are acid-forming oxides, the first acting also as a feebly basic oxide

Antimony Trioxide, Sb_4O_6 —This occurs as the mineral valentinite with other ores of antimony, having been produced by the oxidation of these It forms pearly-white, rhombic crystals which are sometimes coloured yellow or red by the presence of iron and other metals, and have a specific gravity of 5 566 Another, though less frequent, form of antimony trioxide is senarmontite, which usually occurs together with other antimony ores, and crystallises in regular octahedra, having a specific gravity of 5 2 to 5 3 From this it appears that antimony tn-oxide is isodimorphous with arsenious oxide (p 238) Both these crystalline forms can be artificially prepared Thus when the metal or sulphide is heated in an inclined crucible a light, white oxide is formed at a red heat, and this when more strongly heated is deposited on the upper part of the crucible in glistening needles, sometimes mixed with octahedra, and known as *flores antimonn,* or flowers of antimony This latter form is also observed when the rhombic oxide is sublimed, and the octahedra, when quickly heated, are converted into the rhombic crystals [x] Both forms are also obtained by crystallising a hot saturated solution of the oxide or chloride in sodium carbonate (Mitscherhch) Antimony tn-oxide is prepared by diluting an acid solution of the oxide with water, and washing the basic salts which are thrown down, first with hot water, then with sodium carbonate solution, again with water, and finally converting the residue into oxide by ignition Obtained in this way, the oxide is a pale buff-coloured, crystalline powder, which can also be obtained, but not perfectly pure, by oxidising the metal with very dilute nitric acid It is scarcely soluble in water, and becomes yellow when lgmted, but assumes the pale buff tint again on cooling

[1] Terreil, *Compt rend,* 1866, 62, 302

At a dark red heat it melts, and the mass obtained on cooling is crystalline It volatilises at 1560°, yielding a vapour having a specific gravity of 19 9, corresponding to the molecular formula Sb_4O_6[1] It is insoluble in dilute sulphuric acid and in nitric acid, but is easily soluble in hydrochloric and tartaric acids and the caustic alkalis The solution of antimony trioxide in cream of tartar yields *potassium antimonyl tartrate* or *tartar emetic*, $C_4H_4KSbO_7$ Heated in the air it absorbs oxygen, the tetroxide[2] being formed at all temperatures between 390° and 775°, at very high temperatures, however, the latter decomposes and the tn-oxide is again formed[3] The trioxide is readily reduced when it is heated in hydrogen According to Bunsen, the presence of higher oxides can be easily detected by the addition of potassium iodide to the hydrochloric acid solution, when iodine is set free, as may be readily ascertained by shaking the liquid with a few drops of carbon disulphide

The trioxide in solution is readily conveited into antimonic acid by means of oxidising agents such as iodine, chlorine, or potassium/ dichromate, but the change cannot be completely effected by bromine water, nitric acid, or potassium chlorate and hydrochloric acid[4] It reduces the salts of many of the metals[5]

The mineral valentinite was probably known to the ancients Pliny states that two kinds of stibium exist " *Duo ejus genera mas etfemma Homdior est mas scabnorque et minus ponderosus, mmusque radians et arsenosior, femma contra nitet, friabilts, fissurisque, non globis, dehiscens* " Perhaps, however, under the feminine variety he may have understood the preparation obtained by roasting the sulphide, for this process is mentioned by Dioscondes, and Glauber also refers to it The operation is more fully described by " Basil Valentine " He says that by regulating the fire carefully " from the common regulus of the spressglas magnificently fine *flores* may be prepared, both yellow, red, and white/' Valentine certainly knew that the mineral which we now call valentinite is an ore of antimony, for he distinguishes between the black and the golden spressglas The oxide obtained by roasting the metal reduced by iron was formerly

[1] V and C Meyer, *Ber,* 1879,**12,** 1282
[2] Carnelley and Walker, *Journ Chem Soc* , 1887, 53, 86
[3] Read, *ibid,* 1894, 65, 314, Baubigny, *Compt rend,* 1897, **124,** 499, 560
[4] Bosek, *ibid,* 1895, 68, [1], 515
[5] Harding, *Zeit anorg Chem,* 1899, 20, 235

called *nixferium,* as it was believed that 'iron was necessary for its formation

Antimony trioxide acts as a weak acid-forming oxide and also as a weak basic oxide The salts with strong acids are decomposed by water with formation of basic salts, which in contact with water are gradually converted into the oxide

Antimomous Acid —Two hydrates of antimony trioxide have been described, which may be considered as the ortho- and pyro-acids, although it is not certain that they are definite compounds, since the amount of water contained in them varies gradually with the temperature at which they are dried The ortho-acid, H_3Sb0_3, is obtained by adding nitric acid to antimonyl tartaric acid or tartar emetic, and drying the precipitate at 100° The pyro-acid, $H_4Sb_20_5$, is formed by adding copper sulphate to a solution of antimony sulphide in caustic potash until no further orange-coloured precipitate is thrown down, but a white precipitate is formed After filtration, the liquid, on addition of acetic acid, yields a precipitate having the above composition [1]

Only sodium and potassium salts have as yet been obtained in the cryst

(unknown) meta-acid, $HSb0_2$

Sodium Antimonite, $NaSb0_2,3H_20$, separates out from a hot solution of the oxide in caustic soda in glistening octahedra, which are sparingly soluble in water

Hydrogen Sodium Anhmonite, $NaSb0_2,2HSb0_2$, is obtained from very concentrated solutions in large crystals almost insoluble in water, wl

belong to the monoclmic system [2]

Potassium Tnantimonite, $K_20,3Sb_20_3$, is formed in crystals when the trioxide is boiled with caustic potash [3]

Antimony Tetroxide or *Antimonious-antimonic Oxide,* Sb_20_4 — This oxide is a white powder formed when either of the two other oxides is strongly heated in the air When heated it becomes temporarily yellow, and dissolves only with difficulty in acids Antimony-ash, obtained by roasting the sulphide in the air, is an impure tetroxide, and was formerly employed for the preparation of the antimony compounds Impure tetroxide also occurs as the mineral cervantite, found together with other

[1] **Schaffner,** ***Annalen,*** **1844, 51, 182**
[2] **Terrell,** ***Ann Chim Phys,*** **1866, [4], 7, 380**
[3] **Cormimbceuf,** ***Compt rend,*** **1892,115, 1305**

antimony ores in Tuscany Antimony tetroxide forms salts with basic oxides which have been termed *hypoantimonates*

Potassium Hypoantimonate, $K_2Sb_20_5$, obtained by fusing together the tetroxide and potash and lixiviating with cold water, is a white mass soluble in hot water, addition of hydrochloric acid to this solution precipitates the salt $K_2Sb_40_9$

Other insoluble hypoantimonates can be obtained by double decomposition with the corresponding salts Some of these occur as minerals Thus romeite, $CaSb_20_5$, crystallises in tetragonal pyramids, and is found at St Marcel, in Piedmont, and ammiolite which occurs as a powder coloured red by the presence of cinnabar, found in Chih, is probably a copper hypoantimonate, $CuSb_20_5$

ANTIMONY PENTOXIDE AND THE ANTIMONIC ACIDS

450 *Antimony Pentoxide,* Sb_20_5, is obtained by rapidly evaporating the powdered metal or its lower oxides with nitric acid and gently heating the residue This product usually contains a small amount of the lower oxides, but the pure oxide may be prepared by gently heating the precipitate produced by adding dilute nitnc acid to a solution of potassium antimonate It is a light yellow powder, having a specific gravity of 5 6, practically insoluble in water, and turning blue litinus paper red Nitric acid does not dissolve it, whilst concentrated hydrochloric acid dissolves it only slowly, but completely, it volatilises completely when heated with sal-ammoniac It is reduced to the trioxide when it is heated with hydnodic acid, or treated with stannous chloride solution Antimony pentoxide acts as a stronger acid-formmg oxide than the trioxide, and at the same time as a weaker base, the only stable salts being the sulphide, fluoride, and chloride, of the typical formula SbR^1_5

Antimonic Acid —Antimony pentoxide is said to form several distinct hydrates, which correspond in composition to the hydrates of phosphorus pentoxide, and are known by similar names A certain amount of confusion exists in the nomenclature of these acids since Berzehus gave the name of antimomc acid to the hydrate, $HSb0_3$, the true metantimomc acid, whereas the true pyroantimonic acid, $H_4Sb_20_7$, was termed metantimomc acid by Fremy, and the same system extended to the salts

The hydrated pentoxide which is formed by the action of cold water on the pentachlonde, or by oxidising antimony tn-chlonde with nitric acid, and precipitating by water, is moderately

soluble in water According to Delacroix,[1] this solution contains pyroantimonic or tetra-antimonic acid, which is converted by boiling into the ortho- or tri-antimomc acid, and yields salts of the types $M_20,4Sb_20_5$ and $M_20,2Sb_20_5$, whereas Senderens [2] describes the preparation of metantimonates from the same solution

The *ortho-acid,* H_3Sb0_4, is formed when potassium antimonate is decomposed by dilute nitric acid and the precipitate dried at 100° The *meta-acid,* $HSb0_3$, is formed when this is heated to 175° These substances are white powders which are soluble in aqueous

into the pentoxide when heated The meta-acid was formerly employed as a medicine under the name of *materia perlafa*

The *pyro-acid,* $H_4Sb_20_7$ (Fremy's metantimonic acid), is formed by the decomposition of the pentachlonde by hot water The air-dried precipitate [3] possesses the formula $H_4Sb_20_7,2H_20$, and has the same composition as volgerite, a mineral which occurs in the province of Constantine, in Algeria

The composition and properties of all the hydrates of antimony pentoxide which have been prepared in the solid state depend on the mode of preparation and the temperature at which they have been dried, and according to the recent investigations of Jander [4] no really definite hydrates exist

The Anhmonates —Since the time of Berzehus, the antimonates have been chiefly investigated by Fremy,[5] Heffter,[6] Beilstem and Blase,[7] Knorre and Olschewsky,[8] Ebel,[9] Delacroix, and Senderens Doubt still exists as to the constitution of these compounds, since most of them contain water, which may be water of constitution or of crystallisation

Potassium Antimonate, $KSb0_3$, is obtained by deflagrating 1 part of metallic antimony with 4 parts of saltpetre and lixiviating with warm water A white powder is thus obtained, which when boiled for some time with water dissolves to a considerable extent On concentrating the solution to a certain point, a crystalhne mass separates, but if the liquid be further

i *J Pharm,* 1897, [6], 6, 337, *Bull Soc chim,* 1899, [3], 21, 1049, 1900, [3], 25, 288

[2] *Bull Soc chim* , 1899, [3], 21,47 But see also Tomula, *Zett anorg Chem* , 1921,**118,** 81

[3] Daubrawa, *Annalen,* 1877,**186,**110

[4] *Kolloid Zeit,* 1918,23, 122

[5] *Ann Chim Phys* , **1844, [3], 12, 499, 1848, [3], 23, 497**

[6] ***Pogg Ann* , 1852, 86, 418** [7] ***Journ** Chem Soc* , **1889, 66, 1123**

[8] ***Ber*, 1887,20, 3043** [9] ***Ibid*, 1889, 22, 3044**

evaporated, **a** gum-like mass, **$2KSb0_3,wH_20$, is obtained which** dissolves readily in warm water When dried at **100° this salt** contains $3H_20$, and at 185° still contains $2H_20$ When a **current** of carbon dioxide is passed through a solution of the **normal** salt, a sparingly soluble acid salt is precipitated which has the formula $2K_20,3Sb_20_{5)}7H_20$ at 100°, and still contains $2H_20$ at 350° This salt was probably known to the latro-chemists, and was much employed by quack doctors and known as *anhmonium diaphorehcum ablutum* The substance obtained by deflagrating the sulphide with saltpetre was employed at the end of the seventeenth century under the name *anhmonium diaphoreltcum non ablutum,* and Libavius and others treated this residue with acids in order to obtain their diaphoreticum, which, therefore, consisted chiefly of antimonic acid

Normal Potassium Pyroanhmonate, $K_4Sb_20_7$, was described by Fremy (under the name of metantimonate), but the substance obtained by him was probably a mixture of caustic potash and potassium antimonate A sparingly soluble *acid sail,* $K_2H_2Sb_20_7,7H_20$, can, however, be prepared by oxidising an alkaline solution of potassium antimomte with potassium permanganate and evaporating the filtrate [1]

Sodium Antimonate, $2NaSb0_3,7H_20$, is obtained when the metal or sulphide is deflagrated with Chili saltpetre and the mass washed out with water At 200° it loses two molecules of water, and becomes anhydrous at a red heat

A salt which is probably identical with this is formed as a voluminous white precipitate when sodium chloride is added to a solution of the gummy potassium antimonate This changes on standing into the crystalline *acid sodium pyroanhmonate,* $H_2Na_2Sb_20_7,6H_20$ It is only soluble in 350 parts of cold water, and is one of the least soluble of the inorganic salts of sodium A solution of potassium antimonate can therefore be used as a reagent for the detection of sodium Even when a solution contains only 0 1 per cent of sodium salt a crystalline powder separates out after standing for twelve hours Addition of alcohol facilitates the precipitation, free alkalis, on the other hand, retard its formation The salts of lithium, ammonium, and the metals of the alkaline earths give precipitates with potassium metantimonate, and hence these substances must be removed from solution before the above test for sodium can be applied

Ammonium Antimonate, NH_4Sb0_3, formed by dissolving the

[1] Knorre and Olschewsky, *Ber,* 1885,18, 2353,

acid in warm ammonia, separates out on cooling as a crystalbne powder, insoluble in water, and readily gives off ammoma This is the only ammonium antimonate known[1]

Many other salts have been prepared by the action of alkalis and metallic acetates on a solution of hydrated antimomc oxide in water (Delacroix, Senderens)

The antimonates of metals of the other groups are either sparingly soluble or insoluble in water They may be obtained by double decomposition as crystalline precipitates, which are decomposed by weak acids with formation of acid salts, whilst stronger acids, on the other hand, liberate antimonic acid Almost all the antimonates dissolve in strong hydrochloric acid

Normal Lead Antimonate, $Pb(Sb0_3)_2$, is a white, curdy precipitate, insoluble in water The *basic salt,* $Pb_3(Sb0_3)2(OH)_4,2H_20$, occurs as blemierite, at Nertschmsk, in Siberia, and Endelhon, in Cornwall, in remform or spheroidal masses, which possess a resinous appearance and a white, grey, brown, or yellowish colour Another basic salt, used in oil painting under the name of Naples yellow, is obtained by heating a mixture of 1 part of tartar emetic, 2 parts of lead nitrate, and 4 parts of common salt for two hours to the fusing point of sodium chloride, and lixiviating with water

ANTIMONY AND THE HALOGENS

451 *Antimony Tnfluoride,* SbF_3, is obtained as a dense snow-white mass by distilling antimony with mercury fluoride If a solution of the oxide in an excess of hydrofluoric acid be evaporated, the fluoride is also obtained in rhombic pyramids It is deliquescent, and is not decomposed by water, but if the solution be evaporated without an excess of hydrofluoric acid a basic fluoride is formed Antimony trifluonde forms crystalline double salts with one, two, or three molecular proportions of the fluorides of the alkali metals The potassium salt is used in calico printing

Antimony Pentafluoride, SbF_6, is obtained by boiling antimony pentachlonde with anhydrous hydrofluoric acid in a platinum retort provided with a reflux condenser of platinum for three days and fractionally distilling the residue[2] It is a thick, colour-

[1] **Raschig, *Ber,* 1885,18, 2743**

[2] **Ruff and Plato, *ibid,* 1904, 37, 673 See also *ibid,* 1906, 39, 4310, 1909, 42,4021**

less liquid of specific gravity 2 993 at 22 7°, it boils at 150°, solidifying when cooled It attacks the skin, and dissolves paraffin, but has no action on dry glass Exposed to air it unites with water, forming a hydrate with $2H_20$ It combines with antimony trifluonde, with evolution of heat and contraction, forming a series of additive compounds, varying in composition from SbF_5,$2SbF_3$ to SbP_6,$5SbF_3$ The pentafluonde forms difficultly crystalhsable double salts with the fluorides of the alkali metals [1] Chlorine has no action on it, but bromine forms a viscid, dark brown mass, probably containing SbF_5Br Iodine also reacts on the pentafluonde with development of heat and the formation of a bluish-green liquid or of a dark brown solid

Antimony Trichloride, $SbCl_3$ —" Basil Valentine " says " Take of fine white, well-sublimed corrosive sublimate, and of good spressglas the same quantity Rub these up together and distil them The oil which comes over is at first white, and congeals like ice or clots of butter " This preparation was termed *butyrum antimonn,* and was supposed to contain quicksilver until Glauber, in 1648, sh be prepared by distilling spressglas with oil of vitriol and common salt or hydrochloric acid Other methods of preparation are by heating sulphate of antimony with sodium chloride, and by heating an excess of metallic antimony, or its sulphide, in a current of dry chlorine

Antimony trichloride is a crystalline mass, melting at 73 2° and boiling at 223 5° (Kopp) [2] Its colourless vapour has the normal specific gravity of 7 8 and the salt dissolved in ether has the normal molecular weight[3] Its latent heat of fusion is 13 37 cal On exposure to moist air the solid deliquesces to a clear liquid, and this, on evaporation over sulphuric acid, yields crystals of the anhydrous chloride A solution of the chloride is best obtained by boiling the sulphide with strong hydrochloric acid When this is distilled in a retort, water comes over first, next the excess of hydrochloric acid, and lastly the anhydrous chloride The concentrated solution, which has a specific gravity of 1 35, is known as *liquid butter of antimony,* and is employed for giving a brown surface to iron and steel wares, such, for instance, as gun-barrels (brown Bess), it is also sometimes used for pharmaceutical purposes The anhydrous chloride yields with

[1] Mangnac, *Annalen,* 1868,**146,** 239
[2] See also Beokmann, *Zeit anorg Chem* , 1906, **51,** 96
[3] Lespieau, *Compt rend,* 1897,125, 1094

dry ammonia the brittle white compound $SbCl_3,NH_3$, which, on heating, gives off ammonia It combines with hydrochloric acid to form the crystalline compound $2SbCl_3,HCl,2H_20$, and also forms soluble crystalline double salts with a variety of metallic chlorides [1]

Powder of Algaroih — I f the acid solution of the chloride be diluted with water a white precipitate of the basic chloride is thrown down This was known to Paracelsus, who employed it as a medicine, and states in his *Archidoxa* that in order to prepare it, corrosive sublimate is to be distilled with antimony, and the product coagulated with water, when the *mercunus vitce* is obtained Towards the end of the sixteenth century it was much employed, especially by the Veronese physician, Algarotus, and was termed by him *pulvis angelicus,* although it has been generally known as *powder of Algaroih* The presence of tartaric or free hydrochloric acid prevents the precipitation of this substance Its composition varies according to the method of its preparation If ten parts of solid trichloride are mixed with seventeen parts of water, and allowed to stand until the precipitate has become crystalline, the compound SbOCl is deposited in small rhombohedra These may be washed with ether in order to remove the excess of the chloride The same compound is obtained by heating equal parts of the trichloride and absolute alcohol in sealed tubes to 140° If one part of the trichloride be mixed with three parts of water, and the precipitate filtered off quickly and mixed with ether, the same body is obtained as an amorphous powder When this substance is heated the trichloride is given off, and the oxychlonde, $Sb_40_5Cl_2$, remains behind The last named compound is formed as an amorphous precipitate when the chloride is mixed with from five to fifty parts of water, on standing, it gradually forms silky prisms If three times its bulk of hot water be added to the trichloride, and the liquid allowed to stand at 60° for some hours, crystals are obtained resembling soda crystals, which also possess the composition $Sb_40_5Cl_2$ [2] With larger quantities of water still more basic chlorides are formed, which if boiled repeatedly with water, are converted into the trioxide, this reaction taking place more quickly in the presence of sodium carbonate If antimony oxide be dissolved in boiling antimony trichloride, a pearl-grey, crystalline mass is obtained having the composition $SbOCl,7SbCl_3$, and this yields the substance $2SbOCl,Sb_20_3$ on treatinent with absolute alcohol

[1] See Ephraim, *Ber*, 1903, 36, 1815 [2] Sabanajew, *Zeit Chem* , 1871, 204

Antimony Pentachloride, $SbCl_5$, was discovered by H Rose in 1835, and is prepared by the direct union of antimony and chlorine, which takes place with evolution of light and heat It is also readily formed by saturating the fused trichloride with chlorine gas, Antimony pentachloride is a yellow, fuming, disagreeably-smelling liquid, which solidifies in a freezing mixture, forming crystals melting at 3° [1] It is readily volatile, partially decomposing on distillation into chlorine and trichloride, but under a pressure of 22 mm it boils without decomposition at 79°, whilst under the same conditions the trichloride boils at 113 5° [2] The vapour density [3] under a pressure of 58 mm at 218° is 10, the calculated number being 10 3 When brought in contact with the requisite quantity of ice-cold water it forms the monohydrate,[4] $SbCl_5,H_20$, crystallising from chloroform in thin, del added [5] a clear liquid is obtained, and this, on standing over sulphuric acid, deposits crystals of $SbCl_5,4H_20$, which are insoluble in chloroform (Anschutz and Evans) Hot water produces antimonic acid As it easily loses chlorine, antimony pentachloride is employed in orgamc chemistry as a chlorine carrier in the chlormation of many bodies With hydrocyanic acid it forms the white, crystalline compound $SbCl_5,3HCN$ which volatilises under 100° with partial decomposition It also forms solid compounds with various chlorides, oxides, etc , such as $SbCl_5,SCl_4$, $SbCl_5,PCl_5$, $SbCl_5,POCl_3$, $2SbCl_5,5NOCl$, $SbCl_5,NO$, $3SbCl_5,2NO_2$, $SbCl_5,N_4S_4$ By the interaction of antimony pentachloride and iodine the addition compounds $SbCl_5,2ICl$ and $SbCl_5,3ICl$ have been obtained as bluish-black crystals melting at 62—63° [6]

Antimony pentachloride forms a very large number of double salts, many of which are derived from the complex *metachloro-antimonic acid,* $HSbCl_6$, which is obtained in greenish-yellow prisms containing $4½H_20$ by the action of chlorine and hydrogen chloride on a solution of antimony trichloride [7]

Antimony Tetrachloride, $SbCl_4$, is probably present in the dark brown solution formed by the action of chlorine on an excess of

[1] Moles, *Anal Fis Quim,* 1914,**12,** 314
[2] Anschutz and Evans, *Ber,* 1886, **19,** 1994, *Journ Chem Soc,* 1886, 49, 708
[3] Anschutz and Evans, *Annalen,* 1889, **253,** 95 [4] *Ibid* , 1887, **239,** 239
[5] Weber, *Annalen,* 1863,**125,** 86 [6] Ruff, *Ber,* 1915, 48, 2068
[7] Wemland and Schmid, *Zeit anorg Chem,* 1905, 44, 37 See also *Ber* 1901,34,2633, 1903,36,244

antimony trichloride A number of salts have been prepared of the type $M^{\wedge}SbCl_6$, which appear to be derived from the tetrachloride and are characterised by their dark colour They are isomorphous with the corresponding salts of the tetrachlorides of lead, tin, and platinum[1] The *rubidium* salt, Rb_2SbCl_6, is obtained by adding rubidium chloride to a mixture of equal molecular proportions of the tri- and penta-chlondes of antimony in presence of hydrochloric acid It crystallises in lustrous, dark violet, microscopic octahedra, and is decomposed by water Analogous bromine compounds appear also to exist

Antimony Tnbromide, $SbBr_3$—Powdered antimony combines directly with bromine with evolution of light and heat The tnbromide sublimes in colourless, deliquescent needles, which melt at 95° and boil at 275°, water decomposes it with formation of a basic bromide Another method of preparation consists in heating an excess of powdered antimony with a solution of bromine in carbon disulphide, the tnbromide thus obtained on evaporation crystallises in octahedra

The *pentabromide* is obtained in combination with ether when the metal is covered with ether and treated with excess of bromine The compound forms grey crystals and is very unstable [2]

Antimony Tri-iodide, SbI_3—Antimony and iodine combine directly with evolution of so much heat that if large quantities are employed explosions may ensue The tn-iodide is a brownish-red mass, which crystallises in red, six-sided tablets from solution in carbon disulphide It melts at 171° to a garnet-red liquid and forms a violet-red vapour, which at a higher temperature becomes scarlet It sublimes at a temperature slightly above its melting point, boils between 414° and 427°, and is decomposed by water, with formation of a yellow oxy-iodide, which forms crystalline double salts with the various iodides

Both the bromide and iodide form numerous double salts

ANTIMONY AND THE SULPHUR GROUP

452 *Antimony Tnsulphide,* Sb_2S_3, occurs crystallised as stibmte in the older stratified rocks This is the most important ore of antimony, and it is found in considerable quantity, occurring in Cornwall, Hungary, Transylvania, in the Banat, in the Harz,

[1] **Setterberg, *Ofver K Vetensk akad For,* 1882, 23, Weinland and Feige, *Ber,* 1903, 36, 259, Weinland and Schmid, *ibid,* 1905, 38, 1080**

[2] **Raynaud, *Bull Soc chim,* 1920, 27, 411**

in Westphalia, in the Black Forest, in Bohemia, in the Auvergne, in Estramadura, Algiers, Corsica, Siberia, Nevada, New Brunswick, in Japan, where it is found in magnificently large and perfect crystals, and in Borneo in large quantities It crystallises in prisms, but is usually found in columnar or striated masses, which soil the fingers like graphite It is easily pulvensable, and readily fusible, and has a specific gravity of 4 62 The crude sulphide occurring in cominerce is obtained by melting the ore in the manner already described, and is sold in rounded masses having the form of the vessel in which the molten sulphide solidifies It has a metallic lustre, steel-grey streak, and crystalline fracture From early times this substance has been used in the East under the name of Kohl The alchemists occupied themselves much with the properties of this body, as it was used for the purification of gold, and was termed *judex ultimus* or *lupus metallorum* Antimony tnsulphide also exists in the amorphous state, and in this form was known to " Basil Valentine " He states that crude spressglas may be sublimed with formation of a red body when it is mixed with *sal ammoniacum* In this way antimony chloride and ammonium sulphide are formed, which again react on cooling, producing the original compounds, the antimony sulphide separating out as a red powder Glauber, and also Lemery, speak of the solution and the subsequent precipitation of the spressglas with caustic alkalis, but it was not until 1714 that attention was directed to the red sulphide of antimony In this year a Carthusian monk whose life had been despaired of by the Paris faculty was saved by a monk of the name of Simon administering to him a medicine which was first prepared by a German apothecary, a disciple of Glauber, and which was bought by the Parisian apothecary de la Lig6re This was soon known as the " poudre des chartreux," or Carthusian powder Simon, however, gave to it the name of *Alkermes mineral*, and such was the reputation which this medicine enjoyed that the French Government bought the receipt for its preparation in 1720 from de la Ligene The process consisted in boiling the spressglas with potashes and allowing the clear solution to cool, when the kermes was deposited as a red powder In 1728 Stabel found that when caustic potash was employed, a red powder was also obtained, which Mender in 1738 showed to be pure kermes, and C J Geoffroy in 1735 proved that the same preparation was obtained when spressglas was fused with carbonates of the alkali metals, and the liver of antimony thus

obtained boiled with water This body was believed to be a compound of antimony, sulphur, and alkali, though chemists such as Baume denied that it contained any alkali, and assumed that in spressglas regulus of antimony was combined with sulphur, whilst in mineral kermes calx of antimony was combined with sulphur Many other views were held concerning the composition of this compound until Kose in 1825, and Fuchs in 1833, showed that mineral kermes is merely amorphous antimony sulphide

Various methods may be adopted for the preparation of mineral kermes, which for fifty years was highly prized as a medicine, and even now is sometimes employed All these processes yield a preparation containing, as impurity, varying quantities of antimony oxide, both free and combined with the alkalis, and moreover on exposure to air oxidation occurs with formation of the oxide and free sulphur[1] Hence the preparation of the kermes should be carried on exactly according to the prescription of the pharmacopoeia

In order to prepare the amorphous sulphide free from oxide, the crystalline compound is boiled with caustic potash in absence of air, the liquid filtered, and the hot diluted solution precipitated with sulphuric acid The precipitate is then washed with very dilute acid, and afterwards with cold water, and to remove any oxide which may be present it is heated with a solution of tartaric aid Thus obtained, the precipitate becomes anhydrous when dried at 100° and forms a reddish-brown, light powder which readily soils the fingers This is more soluble in hydrochloric acid, in the fixed alkalis and their carbonates than the crystalline compound into which it is converted on fusion It may also be obtained by pouring fused stibnite into an excess of cold water It then forms an amorphous, lead-grey mass which appears of a hyacinth-red colour when seen in thin films, has a specific gravity of 4 15, and when triturated is converted into a dark reddish-brown powder

If sulphuretted hydrogen is passed into an acid solution of the trichloride or into an acidified solution of tartar emetic, an orange-red precipitate of amorphous hydrated sulphide is obtamed, which after drying at 100—130° becomes black at 200° The precipitated sulphide also becomes black when it is boiled with 2 parts of hydrochloric acid and 1 part of water in a current of carbon dioxide [2]

[1] Poilacci, *Boll Chim farm,* **1906, 46, 401**

[2] **Mitchell,** *Chem News,* **1893, 67, 291 See also** de Bacho, *Ann chim apphcata,* **1919,12, 143, Wilson and McCrosky *J Amer Chem Soc,* 1921, 48, 2178**

When the sulphide is heated at 850° in nitrogen, and the vapours are rapidly condensed, black needles are formed accompanied by lilac-coloured globules which appear to constitute^ a polymorphic variety of the sulphide [x] This form has the specific gravity 4 278 at 0°, and passes at 220° into the black, crystalline form, of specific gravity 4 652 and melting [2] at 540°

When a dilute solution of tartar emetic is added to sulphuretted hydrogen water a colloidal solution of antimony sulphide is produced, which is orange-red by transmitted light, and can be boiled without undergoing change Calcium chloride and many other electrolytes cause an iminediate precipitation of the sulphide [3] On heating in a current of hydrogen the trisulphide is reduced to metal, but it may be sublimed without decomposition in an atinosphere of mtrogen The equilibrium between the sulphide and hydrogen at various temperatures has been examined by Pelabon[4] Crystalline antimony sulphide is used for the preparation of other antimony compounds, in pyrotechny,

in the hea

firing breechloading firearms The amorphous sulphide is largely used for vulcanising caoutchouc, to which it imparts a reddish-brown colour

The compound known as *antimony cinnabar,* which is obtained by warming a solution of the trichloride with sodium thiosulphate, is the trisulphide This substance is used in oil painting as well as in water-colour painting and as a distemper

The Thioantimonites or *Livers of Antimony* are formed by the combination of the trisulphide with metallic sulphides [5] Those of the alkali metals are prepared by fusing the constituents together They are brown or black, and when they contain a large quantity of metallic sulphide they are easily soluble in water, but when the quantity of antimony mcreases, these livers of antimony become more sparingly soluble, and at last insoluble in water They are also formed when the trisulphide is dissolved

in a soluti

trisulphide is fused with an alkali or alkali carbonate or treated with the solution of an alkali

$$2Sb_2S_3 + 4KOH = 3KSbS_2 + KSb0_2 + 2H_20$$

[1] Guinchant and Chretien, *Compt rend* , 1904, **138,** 1269, **139,** 51

[2] See also Pelabon, *ibid,* 1904, **138,** 277, and Zani, *Bull Acad roy Belg,* 1909, 1169

[3] Picton, *Journ Chem Soc,* 1892, 61, 142, Biltz and Ceibel, *Nachr K Ges Wtss Gothngen,* 1906, 141

[4] *Compt rend,* 1900, **130,** 911

[5] See Pouget, *ibid,* 1897, **134,** 1445, 1518

Acids precipitate the amorphous tnsulphide from these solutions, which also absorb *oxygen* rapidly from the air Many of the throantimonites occur as minerals, and the composition of some of these has *faSen* already given[x] The alkali salts[2] belong to the types $MSbS_2$, M_3SbS_3, $M_2Sb_4S_7$, and $M_4Sb_2S_5$

Antimony Tetrasulphide, Sb_2S_4, and *Pentasulphtde,* Sb_2S_5, do not occur in the native state " Basil Valentine " mentions that when spressglas is boiled with strong caustic ley, and acetic acid added to the liquor, a red body is precipitated, and Quercetanus in 1603 mentions in his pharmacopoeia a preparation from spressglas and liver of sulphur by means of acids, terming it *sulphur antimonn auratum* In 1654 Glauber mentions in the " pharmacopoeia spagynca" the preparation obtained by precipitating the slag formed in the preparation of regulus of antimony by means of acetic acid, and recominends this product as *panacea antimoniahs* or *sulphur purgans universale* This preparation, which, as golden sulphuret of antimony, soon became a favourite medicine, was obtained from the more or less oxidised solution of liver of antimony, containing a thioantimonate When fractionally precipitated by hydrochloric acid a brown kermes is first thrown down and afterwards a golden-coloured sulphide, termed *sulphur auratum tertice prcecipitationis* Later, stibnite was boiled with alkali and sulphur and the solution precipitated with acid At the present day pure sodium thioantimonate is first prepared, this is dissolved in from 10 to 60 parts of water and a cold mixture of 3 3 parts of sulphuric acid and 100 parts of water is gradually added, the precipitate is well washed with distilled water and dried at a moderate temperature in the dark

The *sulphur auratum* thus prepared has generally been regarded as antimony pentasulphide mixed with tnsulphide and free sulphur According to F Kirchhoff,[3] however, it contains the tetrasulphide, Sb_2S_4, and no pentasulphide The tetrasulphide may be obtained in the pure state by decomposing zinc thioantimonate with dilute acids, and extracting free sulphur from the precipitate by means of carbon disulphide or acetone The zinc salt is readily obtained from Schkppe's salt by double decomposition with zinc chloride, when it forms a chrome-yellow

[1] See also Sominerlad, *Zed anorg Chem,* 1897, 15, 173, Pouget, *Compt rend ,* 1897,**124,** 1518, 1903, **136,** 1450

[2] See Pouget, *Compt rend ,* 1897, **124,** 1445, 1898,**126,** 1144, 1792, Stanek, *Zeit anorg Chem,* 1898, 17, 117

[3] *Zeit anorg Chem,* 1920,**112,** 67, **114,** 266

precipitate which becomes bright orange-red when dried and powdered, and contains about 6-7 per cent of free sulphur

The pure pentasulphide is precipitated when an excess of sulphuretted hydrogen water is added to a solution containing the antimony in the form of antimomc acid at the ordinary temperature (Bunsen) [1] When sulphuretted hydrogen is passed into the antimony solution a mixture of pentasulphide, trisulphide, and sulphur is formed, the proportion of the pentasulphide diminishing as the rate at which the gas is passed is lessened and as the temperature is raised Hydrochloric acid up to about 20 per cent favours the production of the pentasulphide, but in larger amount hinders it [2]

Antimony pentasulphide is a fine yellowish-red powder easily soluble in aqueous alkalis and their sulphides, and also, in absence of air, in warm ammoma It likewise dissolves in the carbonates of the alkali metals, but not in ammonium carbonate When exposed to sunlight, heated in water to 98°, or simply heated in absence of air, it decomposes into the black trisulphide and sulphur, and is decomposed by hot hydrochloric acid

Sodium Thioanlimonate, $Na_3SbS_4,9H_20$ —This is termed, from the discoverer, *Schhppe's salt,* and is obtamed by dissolving the trisulphide, sulphur, and caustic soda or a mixture of soda-ash and lime, in the requisite quantity of water, or by fusing together 16 parts of anhydrous sodium sulphate, 13 parts of stibmte, and 5 parts of carbon, dissolving, and boiling the solution with 2 5 part3 of sulphur It crystallises in large, colourless or yellow, regular tetrahedra which have an alkaline reaction and a saline, cooling, metallic taste resembling that of liver of sulphur It dissolves at 15° in 2 9 parts of water and is precipitated from aqueous solution by alcohol The hydrated crystals on exposure to moist air soon become covered with a kermes-coloured coating, and when they are heated in absence of air water is given off and the anhydrous salt formed, which fuses at a dark red heat

Potassium Thioanhmonate, $K_3SbS_4,9H_20$,]s prepared in a similar way to the sodium salt and forms deliquescent crystals

Ammonium Thioanhmonate, $(NH_4)_3SbS_4$, formed when the trisulphide and sulphur are dissolved in red ammonium sulphide, crystallises in unstable pale yellow prisms [3]

[1] *Annalen,* 1878,**192,** 305

[2] Bosek, *Journ Chem Soc,* 1895, 67, 515, Brauner, *tbid,* 527 See also Klenker, *J pr Chem,* 1899, [2], 59, 150, 353

3 Stanek, *Zeit anorg Chem* , 1898,17,117

Barium Thioanhmonate, $Ba_3(SbS_4)_2,6H_20$, is prepared by dissolving the freshly precipitated golden sulphide of antimony in barium prisulphide and precipitating by alcohol In this way stellate groups of needles are obtained

The *calcium* salt is prepared in a similar way and is thrown down as an oily liquid on addition of alcohol The throantimonates of the alkali metals have been examined by Donk [1] The thioantimonates of the other metals are yellow, red, brown, or black precipitates, almost entirely insoluble in water and are obtained by double decomposition

Antimony Oxysulphide, Sb_2S_20, is found, together with stibnite, as kermesite or antimony blende in needle-shaped crystals or thin, six-sided prisms which have a cherry-red colour and an almost metallic lustre It is obtained as a reddish-brown powder by adding antimony trisulphide to fused antimony iodide, and treating the mass with dilute hydrochloric acid, when a dark reddish-brown, lustrous powder of antimony thio-iodide, SbSI, remains behind When boiled with water and oxide of zinc, this is converted into the oxysulphide

Glass of Antimony or *Vitrum Antimonn* is obtained by fusing oxidised stibnite with a small quantity of the sulphide It forms a transparent, dark ruby-red mass, formerly largely employed for obtaining the other antimony compounds, but now used only for imparting a yellow tint to glass and porcelain

Antimonial Saffron or *Crocus Antimonn*—If stibnite is deflagrated with a quantity of saltpetre insufficient for complete oxidation a brownish-yellow powder is obtained on lixiviatioii which when heated melts to a yellow glass

Chlorosulphides of Antimony—Two compounds of this class, SbS_2Cl and Sb_2S_6Cl, have been obtained as reddish-brown, crystalline substances by the action of sulphuretted hydrogen on antimony trichloride at its melting point [2] The compound $SbSCl,7SbCl_3$ is obtained by heating the trichloride and trisulphide together Alcohol converts it into $2SbSCl,3Sb_2S_2$

Iodosulphides of Antimony —Compounds of the formulae SbS_2I and SbS_2I_3 are formed when antimony trisulphide is heated with iodine (Ouvrard)

Antimony Tnsulphate, $Sb_2(S0_4)_3$, is obtained as a white mass by heating either the metal or the oxide with concentrated sulphuric acid The composition of the salt depends on the concentration of the acid used, acid or basic salts being obtained

[1] *Ghem Weekblad,* 1908, 5, 529, 629

2 Ouvrard, *Compt rend,* 1893,**116,** 1516, **117,** 107

when the acid employed is stronger or weaker than that represented by the formula $HgSOa$[1] The normal salt crystallises from a tolerably acid concentrated solution in long, glistening, silky needles,[2] and is decomposed by water into a soluble acid salt, and an insoluble basic salt If antimony chloride be heated with fuming sulphuric acid a basic salt, $Sb_20(S0_4)_2$, is produced in small, glistening crystals, which in contact with alcohol are transformed into the salt $Sb_20_2S0_4$, consisting of a white powder, which, when treated with boiling water, yields the salt $Sb_40_5S0_4$ Several other salts have also been described

Antimony sulphate yields double salts with the alkali sulphates, such as $KSb(S0_4)_2$, which crystallises in nacreous leaflets These are decomposed by water, yielding antimomous hydroxide[3]

Antimony Thiosidphate—A number of complex antimony thiosulphates have been prepared by Szilagyi[4]

453 *Antimony Triselenide,* Sb_2Se_3, is formed when the two elements are fused together, a metallic, lead-grey, crystalline mass being produced[5] which melts at 572° When selemum hydride is passed into a solution of tartar emetic the same compound is precipitated as a black powder

Antimony Pentaselenide, Sb_2Se_5, is precipitated as a brown powder by adding dilute sulphuric acid to a solution of sodium seleno-antimonate

Sodium Seleno-anhmonate, $Na_3SbSe_4,9H_20$, is isomorphous with the corresponding thio-antimonate, and is obtained by fusing together sodium carbonate, antimony triselenide, selemum, and charcoal The fused mass is boiled out with water in absence of air and the nitrate covered with a layer of strong alcohol The salt separates out after some time in orange-red, transparent tetrahedra which are soluble in two parts of cold water and become red in air, with separation of selemum When a solution of Schlippe's salt is boiled with selenium, filtered, and the solution concentrated in absence of air yellow tetrahedra of $Na_3SbSeS_3,9H_20$ are deposited

Antimony and tellurium[6] when fused together yield only one definite compound, *antimony tritelluride,* Sb_2Te_3

[1] Adie, *Chem News,* 1890, **61,** *58*

[2] Schultz Sellack, *Ber* , 1871, 4, 13

[3] Gutinann, *Arch Pharm* , 1898, **236,** 477, Metzl, *Zed anorg Chem,* 1906, 48, 140, German Patent 161776 See also Kuhl, *Zeit anorg Chem,* 1907, 54, 256, Gutinann, *Arch Pharm* , 1908, **246,** 187

[4] *Zeit anorg Chem* , 1920, **113,** 69

[5] See Pelabon, *Compt rend,* 1906, **142,** 207, Chretien, *ibid* , 1339, 1412, Chikashige and Fujita, *Mem Coll Sci Kyoto,* 1917, 2, 233

[6] See Fay and Ashley, *Amer Chem J,* 1902, 27, 95

ANTIMONY AND THE NITROGEN GROUP

454 No jjefinite nitrate of antimony is known, although the white powder Obtained by the action of nitric acid on antimony contains nitrogen, and is converted by water into antimony pentoxide and mtric acid

If phosphorus be added to fused antimony a tin-white *phosphide of antimony* is obtained which when heated in the air burns with a greyish flame

Antimony Thiophosphate, $SbPS_4$ or Sb_2S_3,P_2S_5, is formed when the trichloride or trisulphide is heated with phosphorus penta-sulphide It is a fusible, insoluble, yellow, crystalline mass [x]

Antimony combines directly with arsemc The compound $SbAs_3$ occurs as allemontite in reinform or amorphous masses having a metallic lustre

MEDICINAL USES OF ANTIMONY

455 As we have seen, various antimony preparations are used as important medicines Paracelsus was one of the first to employ these for internal use, and his example was followed by the other latro-chemists, many of whom worked diligently on antimony and its compounds The disciples of the old Galemc school were violently opposed to the introduction of the antimony compounds into medicine, and they succeeded in inducing the Pans Parliament in 1566 to prohibit the use of antimony and its compounds by all physicians on pain of having their licences withdrawn In 1603 the medical faculty of Pans took a similar step, and this decree was not withdrawn until the year 1666

Metallic antimony itself was at one time employed for the preparation of goblets in which wine was allowed to stand overmght in order that it might be used as an emetic, but this practice fell into disuse even during Boyle's time Pills made of metallic antimony were employed at a later period, these were termed everlasting pills, because they, like the goblets, were believed only to act by contact and not to lose their weight This error was first combated by Lemery and Vigam, a Veronese quack doctor who lived in England, and they showed that both antimony and fused stibnite became acted upon when placed in contact with wine

Whilst formerly a large number of antimony compounds were

[1] **Glatzel, *Ber*, 1891, 24, 3886**

employed in medicine, the only ones which are used at the present day are tartar emetic or potassium antimonyl tartrate, $C_4H_4K(SbO)0_6$, and the trisulphide or *anttinonium sulphurcUum* The first compound is given in doses of 0 0027 to 0 008 gram as a diaphoretic, and from 0 065 to 0 13 gram as an emetic The dose of the second is from 0 065 to 0 13 gram

In larger doses it produces, like white arsenic, violent irritation in the intestines, vomiting and purging When one large dose only is administered the case proceeds rapidly to recovery or death, generally the former, if the case be placed early under proper treatment, and in this respect acute antimomal is distinguished from acute arsenical poisoning

In cases of chrome antimony poisoning the principal symptoms are dryness of the throat, pain on swallowing, nausea and vomiting, diarrhoea, loss of flesh, giddiness, fainting, and albuminuria Death takes place from exhaustion and wasting Several cases have occurred in this country to show that tartar emetic has been thus criminally and fatally used (Taylor)

DETECTION AND ESTIMATION or ANTIMONY

456 When a small quantity of an antimony compound is heated in the upper reduction zone of a Bunsen burner on a thread of asbestos the flame becomes of a bluish tinge, and when a small porcelain basin filled with cold water is held above it a brownish-black deposit of metallic antimony is found upon the basin, and this is but slightly attacked by cold nitric acid, and is insoluble in sodium hypochlorite Arsenic gives a very similar reaction, but this may be distinguished from antimony by the fact that during the reduction a garlic-like smell of arsemc is noticed, and that the metallic film is readily soluble in sodium hypochlorite If an antimony compound is heated on a carbomsed match a brittle metallic bead is obtained, whilst arsemc is completely volatilised Most of the antimony compounds are insoluble in water but dissolve in hydrochloric acid Those which do not thus dissolve may be obtained in solution by fusion with potassium carbonate and saltpetre, and subsequent solution in hydrochloric acid Sulphuretted hydrogen produces in acid solutions a very characteristic orange-red coloured precipitate of antimony trisulphide If other metals precipitable by sulphuretted hydrogen are present, the mixed sulphides, after washing, are treated with ammonium sulphide, filtered, and the filtrate acidified with hydrochloric acid This

precipitate may contain, together with antimony, the sulphides of tin and arsenic This last metal is removed by digesting with freshly prepaid solution of ammonium carbonate, and washing the residue with water This is then brought into solution by heating with hydrochloric acid, and the liquid is placed in a platinum dish containing a piece of zinc, the antimony is deposited upon the platinum as a black, adherent coating, which is readily soluble in nitric acid and can then be identified as antimony A more satisfactory method consists in dissolving the mixed sulphides in caustic soda and a few drops of yellow ammonium sulphide and then boiling with sodium peroxide, which converts the metals into stannate, antimonate, and arsenate respectively Tin is then detected by boiling with ammonium chloride, which precipitates stannic hydroxide, and arsemc and antimony are detected in the acidified filtrate by Bunsen's method described below [1] A rapid method of detection is to boil the sulphides with a 5 per cent solution of sodium carbonate, which leaves tin sulphide undissolved, the solution deposits antimony sulphide on cooling, whilst arsemc sulphide remains dissolved and can be detected as usual[2]

Antimony may also be detected by means of Marsh's test carried out as described under arsemc (Vol I, p 717) The mirror obtained is deposited much closer to the flame than that of arsemc, is formed at a lower temperature, does not yield a crystalline deposit of oxide when heated in the air, and is not soluble in sodium hypochlorite When the gas is passed into silver nitrate solution, silver antimomde is precipitated (p 1007)

Antimony trichloride gives a spark spectrum containing, among others, the following lines, mentioned in order of their relative brightness (Lecoq de Boisbaudran) *a* 6005, *j3* 5568, 7 6130, S 6079

Antimony is usually estimated gravimetncally either as the sulphide or the tetroxide In the first case it is obtained as a hydrated precipitate, which may also contain sulphur and pentasulphide It is necessary therefore, to dry this at 100°, to weigh it, and to bring a known fraction into a porcelain boat contained in a glass tube Through the tube dry carbon dioxide is passed, and the sulphide is heated, the pure anhydrous trisulphide remaining behind The sulphide may also be oxidised by means of nitric acid and the residue lgnited

[1] Walker, *Journ Chem Soc* , 1903, 83, 184
[2] Materne, *Bull Soc chim Belg* , 1906, 20, 46

and weighed as tetroxide, or it may be dissolved **in a large** excess of sodium sulphide, potassium cyanide added, and the resulting solution electrolysed and the metal weighed[1] Antimony is also frequently estimated volumetncally, the trioxide, in presence of sodium bicarbonate, being converted by means of standard iodine solution into the pentoxide, or the tuchlonde being converted into the pentachlonde by a standard solution of sodium bromate in presence of hydrochloric acid [2]

The *quantitative* separation[3] of antimony from other metals, with the exception of arsenic and tin, does not exhibit any difficulty Should these three elements be present together their sulphides must be first converted into oxides by treatment with nitric acid, and these fused for some time with eight times their weight of caustic soda The cooled mass is next allowed to soften in hot water until the sodium metantimonate has separated out as a white powder, and then one volume of alcohol of specific gravity 0 83 is added for every three volumes of the liquid After standing for some time the liquid is filtered and the precipitate well washed with dilute alcohol, to which at last some caustic soda is added The filtrate contains the stannate and arsenate, whilst the whole of the antimony is contained in the residue, and this is converted in the usual way into the sulphide (H Rose) A more rapid method of separation depends on the fact that in presence of free oxalic acid antimony is precipitated by sulphuretted hydrogen as the sulphide, whereas tin remains in solution [4] Antimony and tin can also be separated electrolytically [5]

The separation of antimony from arsenic, which had previously been difficult and unsatisfactory, was first rendered exact by Bunsen The moist and well-washed mixture of sulphides obtained by precipitation with sulphuretted hydrogen is dissolved on the filter in an excess of caustic potash, and the

[1] **Kohn and Barnes,** ***British Assoc Reports,*** **1896, 244 See also Law and Perkm,** ***Trans Faraday Soc,*** **1905, 1, 262, Hahn and Philippi,** ***Zeit anorg Chem*** **, 1921, 116, 201**

[2] **Nissenson and Siedler,** ***Chem Zed,*** **1903, 27, 749, Rowell,** ***J Soc Chem Ind,*** **1906,26, 1181**

[3] **See Darling,** ***Chem Zentr*** **, 1919, 11 , 890, 1920, 11 , 750 for a bibliography of the subject**

[4] **Clarke,** ***Chem News,*** **1870, 21, 124, Lesser,** ***Zat anal Chem,*** **1888, 27, 218, Warren,** ***Chem News,*** **1890, 62, 216, Clark,** ***Journ Chem Soc,*** **1892, 61, 424, Henz,** ***Zeit anorg Chem,*** **1903, 37, 1**

[5] **See Fischer,** ***Zeit anorg Chem,*** **1904, 42, 363, where the literature of the subject is quoted Compare Cohen and Morgan,** ***Analyst,*** **1909, 34, 3**

diluted solution treated with chlorine until all the free alkali has combined The excess of chlorine is then got rid of by repeated evaporation with hydrochloric acid, the solution diluted, and this treated with a freshly prepared solution of sulphuretted hydrogen until all the antimony is precipitated A rapid current of air is then passed through the liquid in order to expel the excess of sulphuretted hydrogen, and the precipitate washed first with water, then with alcohol, and at last repeatedly with carbon disulphide, in order to remove free sulphur After drying at 110°, pure pentasulphide of antimony remains, and this is afterwards weighed The arsenic in the filtrate may be estimated by continued treatment with sulphuretted hydrogen when the pentasulphide is precipitated and treated as above described

A still simpler method of effecting this separation consists in adding ferrous sulphate or chloride to a solution of the chlorides of the two metals in hydrochloric acid, saturating with hydrochloric acid gas, and distilling The whole of the arsenic passes over and may be collected in dilute hydrochloric acid, whilst the antimony remains behind and may be precipitated in the usual way after the ferric salt has been reduced to the ferrous state[1]

Atomic Weight —The methods which have at various times been employed for the determination of the atomic weight of antimony have led to somewhat divergent results The number 129 obtained by Berzelms was long accepted as correct, until Schneider's experiments[2] on the reduction of the sulphide proved that 120 55 was nearer the truth Dexter[3] then found the number 122 5 by treatment of the metal and trioxide with nitric acid, the resulting oxide being converted into the tetroxide by ignition This was confirmed by Kessler,[4] who adopted a similar plan, and by Dumas,[5] who analysed the trichloride and obtained the number 121 8 On the other hand, a very carefully conducted series of analyses of the bromide led Cooke[6] to the number 119 86, while analysis of the iodide gave 119 8 and synthesis of the sulphide 120 55 The electrolysis of the chloride led in the hands of Pfeiffer[7] and of Popper[8] to the number 121 2, but it has been shown that the method applied is not

[1] Fischer, *Ber,* 1880, **13,** 1778 See also Piloty and Stock, *Ber,* 1897, **30,** 1649, Beck and Fisher, *Chem News,* 1899, **30,** 259, where a critical discussion of the various methods is to be found

[2] *Pogg Ann* , 1856, 98, 293 [3] *Ibid* , 1857,**100,** 563

[4] *Ibid* , 1861, **113,** 145 [5] *Ann Chim Phya* , 1859, [3], 56, 129

[6] *Amer J Sci,* 1878,15, 41, 107, 1880,**19,** 382

[7] *AnncUen,* 1881, **209,** 173 [8] *Ibid,* 1886, **233,** 153

accurate[1] A series of determinations made by Friend and Smith,[2] by the indirect method of heating potassium antimonyl tartrate in hydrogen chloride and weighing the potassium chloride produced, gave the number 120 34

The value at present (1922) adopted is 120 2, which is based largely upon the work of Cooke Nevertheless, it is quite possible that the older determinations, giving a value round about 122, are more nearly correct A number of chemists have suggested that the higher value is preferable, basing their views upon the results of careful analytical investigations,[8] and, in an elaborate investigation into the preparation and analysis of pure antimony tnbromide, Willard and McAlpine have[4] recently obtained the value 121 77

BISMUTH Bi = 208 0 At No 83

457 The word *marcasite,* by which, up to recent times, the metal bismuth was often designated, is found in the authors of the thirteenth century Hence it has been supposed that this metal was known at that time This is, however, not the case, for the name marcasite had in those days, and even at a much later period, a very indefinite meaning, being given to any ore which had a metallic appearance, and especially to those ores which are now classed as pyrites

Bismuth was classed by Paracelsus amongst the semi-metals On the other hand, Agncola mentions *bisemutum* or *plumbum cmereum* as a true metal which is usually added to tin in order to make it work better Notwithstanding this clear statement, it was subsequently confounded by Libavius with antimony, and by Lemery with zinc Metallic bismuth was moreover described by " Basil Valentine" in his Last Testament " Antimonium must be placed between tin and lead, as bismuth or magnesia is placed under and between tin and iron," and he also states that " bismuth or marcasite is a bastard *joms* " Pott, in 1739, was the first to make us acquainted with the special properties of bismuth, and its reactions were exactly studied by Bergman

[1] **Cohen and Strengers,** ***Proc K Akad Wetensch Amsterdam,*** **1903, 5, 543**
[2] ***J Amer Chem Soc ,*** **1901, 23, 602**
[3] **Youtz,** ***Zext anorg Chem,*** **1903, 37, 337, Beckett,** ***Inaugural Dissertation*** **(Zurich, 1909), von Bacho,** ***Monatsh ,*** **1916, 37, 106**
[4] ***J Amer Chem Soc,*** **1921, 43, 797**

Bismuth is a comparatively rare metal It is found chiefly in the native condition, but also as the oxide or bismuth ochre, Bi_2O_3, less fftquently it occurs as bismuthite, Bi_2S_3, whilst it is found still more sparingly in the following minerals telluric bismuth or tetradymite, $Bi_2(Te,S)_3$, emplectite, $Cu_2Bi_2S_4$, bismuthite, $3(BiO)_2CO_3$,$2Bi(OH)_3$,$3H_2O$, aikmite, Bi_2S_3,$2PbS$,Cu_2S, bismuthosmaltite, $Co(As,Bi)_2$, puchente, $BiVO_4$, eulytite or bismuth silicate, $Bi_4(SiO_4)_3$, etc , and occurs in traces in the pyrites of Agordo Native bismuth is sometimes found nearly pure, but is usually alloyed with other metals or mixed with a variety of ores It is found in veins traversing gneiss or clayey slate in Bolivia, Saxony, Australia, etc , usually associated with ores of silver and cobalt

468 *The Metallurgy of Bismuth*—Formerly bismuth was obtained by heating the ore in sloping iron tubes, when merely that portion of the metal present in the elementary state was obtained, and this in a very incomplete manner The residue was employed in the manufacture of smalt, and the bismuth again extracted from the cobalt speiss

This liquation process has now been superseded by smelting methods Oxidised ores may be treated direct, but sulphides must be subjected to a preliminary roast Reduction is carried out in crucible furnaces or in small reveiberatory furnaces, the charge being made up of ore, caibon, slag, sodium carbonate, limestone, and sometimes fluorspar It is essential to have an easily fusible slag so as to avoid loss by volatilisation The products of this operation are generally crude bismuth, matte or speiss, and slag For ores carrying sulphide of antimony and arsenic scrap iron is also added to the charge

Bismuthiferous litharge and other metallurgical by-products are sometimes treated with hydrochloric acid, and the bismuth precipitated by means of iron, or the solution is largely diluted with water in order to precipitate the oxychlonde, which is dried and reduced

Crude bismuth, which generally contains lead, antimony, and arsenic, besides traces of iron, cobalt, mckel, silver, and sulphur, is refined by melting it in small iron kettles under a cover of salt, potassium chloride, caustic soda, and sufficient oxychlonde of bismuth to take up the lead The mass is constantly stirred, and in from one to three hours the whole of the lead is converted into chloride, and a corresponding amount of bismuth separated from the oxychlonde Antimony is removed in the same way

with a flux of soda, potash, and sulphur, sodium thioantimonate being formed, whilst for arsenic the flux used is caustic soda and mtre[1] A simple liquation process is also often used, the metal being melted on a slightly inclined iron plate

Bismuth which contains 1 or more per cent of lead melts at a lower temperature than pure bismuth Such an impure metal exhibits on cooling the peculiarity that the solid crust of pure crystallised bismuth is seen to be broken through by drops of a liquid alloy, and this property has been employed to separate bismuth from lead (Matthey) Silver behaves in a similar manner Cominercial bismuth frequently contains small quantities of gold, which, along with silver, may be removed by melting with 2 per cent of zinc and skimming off the surface layer, which is found to contain the precious metals[2]

When bismuth is required for pharmaceutical purposes it must be freed from traces of arsenic For this purpose it is melted with mtre or other oxidising agent, fused with metallic iron, or the molten metal is well stirred and exposed to the air, any antimony being simultaneously oxidised[3]

In order to prepare chemically pure bismuth, the cominercially pure metal is dissolved in nitric acid and evaporated with hydrochloric acid The chloride is then dissolved in hydrochloric acid and the solution mixed with alcohol, which precipitates the greater portion of the lead in the form of chloride The filtrate is poured into water and the precipitated oxychlonde washed, redissolved in hydrochloric acid, and again precipitated with water, this process being frequently repeated The oxychlonde is then again dissolved in hydrochloric acid and precipitated with ammonia and ammomum carbonate, this operation being repeated three times, after which it is finally reconverted into oxychlonde, and the latter reduced to metal by fusion with potassium cyanide The metal thus obtained still contains lead, from which it can only be freed by electrolysis For this purpose it is dissolved in nitric acid and the solution slowly electrolysed, any lead being deposited as peroxide on the positive pole The bismuth is then finally fused with potassium cyanide[4] Another method is as follows The fairly pure nitrate is dissolved in half its weight of 8 per cent nitric acid, mixed with an equal weight of the concentrated acid,

[1] Borchers, *Mineral Industry,* 1899, 8, 62
[2] Matthey, *Proc Boy Soc* , 1887, 42, 89
[3] *Ibid* , **1893, 52, 46**
[4] Classen, *Ber,* **1890, 23, 940**

and cooled to 0° to —10° The pure nitrate which crystallises out is washed with a little ice-cold nitric acid, heated to convert it into oxide and the oxide reduced by fusion with potassium cyanide If necessary, further purification may be earned out by melting the metal under paraffin, allowing it to crystallise

in part, an

a glass spoon [1]

459 *Properties*—Bismuth is a hard, brittle metal, having a bright, metallic lustre and a greyish-white colour, with a distinctly reddish tinge Its specific gravity at 15° is 9 747, it melts at 271° and expands in the act of solidification, the specific gravity of the solid at the temperature of the melting point being 9 673 and that of the liquid 10 004 [2] Its boiling point lies in the neighbourhood of 1420° (Greenwood), and it can be distilled in a current of hydrogen The vapour density between 1600° and 1700° is about 11, a number which is intermediate between the values corresponding to the formulae Bi and Bi_2 [3] When a large quantity is melted, allowed to cool slowly until the surface begins to solidify, the crust then broken, and the liquid metal poured out, fine large crystals are obtained These are obtuse rhombohedra which have the appearance of cubes as their angles approach closely to 90° Acicular needles consisting of elongated, hexagonal prisms have also been observed [4] The crystals oxidise in the air, and frequently become covered with an iridescent film of oxide The same colours may be obtained when the metal is melted in the air, but if the heat be continued, the metal gradually becomes altogether converted into oxide, at a red heat steam is slowly decomposed by bismuth This metal combines also directly with the elements of the chlorine group and with sulphur, hydrochloric and sulphuric acids do not act upon it in the cold, but the latter acid dissolves it on heating with evolution of sulphur dioxide Hydrochloric acid dissolves it in the presence of dissolved oxygen The best solvents for bismuth are nitric acid and aqua regia, both of which dissolve the metal readily in the cold

According to Cohen, bismuth is a mixture of two or more allotropes [5]

[1] **Mylius and Groschuff,** ***Zeit anorg Chem*** **, 1916, 96, 237**
[2] **Vicentini,** ***Journ Chem Soc*** **, 1891, 60, 518**
[3] **Meyer,** ***Ber*** **, 1889, 22, 726**
[4] **Heberdey,** ***Sttzungsber, K Akad Wien,*** **1895,104, 1 254**
[5] **Cohen,** ***Proc K Akad Wetensch Amsterdam,*** **1915,17,1236, Wurmschmidt,** ***Jahrb Min*** **, 1917, I, Ref 2**

Colloidal bismuth is obtained by reducing the nitrate by stannous chloride in the presence of ammonia and ammomum citrate,[1] or the oxychlonde by hypophosphorous acid [2]

Bismuth serves lor the preparation of many pharmaceutical products and cosmetics, and is also employed for the manufacture of alloys of low melting point, and in the construction of thermopiles

460 *Alloys of Bismuth* —Bismuth forms a number of alloys ot low melting point, which are known by the general name of fusible metal The temperature of the melting point depends on the proportion of the constituents, as is shown in the following table

	Newton's Metal	Rose's Metal	Lichten berg s Metal	Wood's Metal	Lipowitz
Bismuth	8	2	5	4	15
Lead	5	1	3	2	8
Tin	3	1	2	1	4
Cadmium	0	0	0	1	3
Melting point	94 5°	93 75°	916°	71°	60°

The melting point can be still further lowered by the addition of mercury Fusible metal is now largely used for stereotyping, obtaining copies of wood-cuts, etc , and is not only valuable on account of its low melting point, but also because it expands considerably in the act of solidification, and thus gives a perfect cast, it is important to make the cast when the metal is so far cooled that it is beginning to be viscid If any of these liquid alloys be poured into a glass vessel this flies to pieces when the metal cools Bismuth is also used in the manufacture of solder, and the soldering can be effected under hot water when a few drops of hydrochloric acid have been added Alloys of lead, tin, and bismuth mixed together in such proportion that the mixture fuses at some particular temperature above 100° serve as safety plugs for boilers and automatic sprinklers Bismuth alloys, melting at a given temperature, are used for

[1] **Lottermoser,** *J pr Chem* **, 1899, [2], 59, 489**
[2] **Gutbier and Hofmeier,** *Zeit anorg Chem* **, 1905, 44, 225**

tempering steel, the pencils used for writing on the so-called metallic paper likewise consist of an alloy of bismuth

Bismuth lit very small quantities renders gold and silver brittle, and greatly diminishes the conductivity of copper for electricity

Molten bismuth, to which 0 05 per cent of tellurium has been added, solidifies to a minutely crystalline mass, entirely different in appearance, fracture, etc, from the pure metal

When bismuth is treated with a solution of sodium in liquid ammonia a compound of the formula $BiNa_3$ is formed as a bluish-black mass, which takes fire in the air, and decomposes water with evolution of hydrogen [1]

COMPOUNDS OF BISMUTH

BISMUTH AND HYDROGEN

461 It has long been suspected that bismuth forms a volatile hydride, and its existence has now been demonstrated by Paneth and Wmternitz [2] A bismuth-magnesium alloy is prepared by heating equal weights of powdered bismuth and silicon-free magnesium in an iron crucible in a rapid stream of dry hydrogen When this is dissolved in 4N-hydrochloric or sulphuric acid the evolved hydrogen contains traces of bismuth hydride, the presence of which may be established by a mirror test or a luminescence test The former is made in the familiar Marsh's apparatus (see Vol I p 717), the mirror obtained closely resembles an antimony mirror in appearance The luminescence test is more delicate The gas issuing from the Marsh's apparatus is ignited and a piece of pure calcium carbonate held in the flame on a platinum loop The carbonate is allowed to cool, and then placed at the edge of the hydrogen flame, when a cornflower-blue luminescence is observed, due to bismuth, and visible in bright daylight

Bismuth hydride is absorbed by water and dilute sulphuric acid to some extent, a better absorbent is silver nitrate solution It is also absorbed by anhydrous calcium chloride and soda-lime, and to a considerable extent by sodium carbonate and potassium hydroxide solutions It is completely decomposed by concentrated sulphuric acid

[1] **Joannis, *Compt, rend*, 1892, 114, 585**

[2] **Paneth, *Ber*, 1918, 51, 1704, Paneth and Wmternitz, *Ber*, 1918, 51, 1728, Paneth, *Chem Zeit*, 1920, 44, 341, *Zeit Elektrochem*, 1920, 26, 452, Paneth, Matthies and Schmidt Hebbel, *Ber*, 1922, 5, *[B]*, 775**

BISMUTH AND OXYGEN

Only two well-defined oxides of bismuth are known

Bismuth suboxide or dioxide, BiO or Bi_2O_2
Bismuth trioxide, Bi_2O_3

The suboxide has only very feeble basic properties, whereas the trioxide is a well-marked, basic oxide and corresponds to the stable salts of bismuth of the general formula BiR^ Higher oxides are formed by the oxidation of the trioxide, to which the formulae Bi_2O_4 and Bi_2O_5 have been ascribed

Bismuth Suboxide, BiO —The question as to the existence of an oxide of this composition has given rise to much discussion,[1] but the experimental evidence renders it probable that the suboxide is a definite chemical substance

The suboxide was first described by Berzelms It is best obtained by gently heating basic bismuth oxalate, $(BiO)_2C_2O_4$, in absence of air (Tanatar)

$$(BiO)_2C_2O_4 = 2BiO + 2CO_2)$$

or by carefully adding an alkaline solution of stannous hydroxide (1 mol) to bismuth hydroxide (1 mol) suspended in dilute potash, washing the suboxide first with dilute potash in absence of air until all traces of stannic oxide are removed, then washing with water, and finally drying at 120° in a current of carbon dioxide (Schneider) It is a black powder which is stable in the air and has the specific gravity 7 2, this being considerably less than that of a mixture of bismuth and its oxide having the same percentage composition as the suboxide (8 9) When heated in the air it passes into the trioxide with incandescence, and in absence of air is convex ted into a mixture of bismuth and bismuth oxide

The suboxide is converted by hydrochloric acid into bismuth chloride, which dissolves, and insoluble metallic bismuth The heat evolved in this reaction is considerably less than that produced when a corresponding amount of the trioxide is dissolved, and this affords a further proof of the individuality of the

[1] **Vanmo and Treubert, *Ber,* 1898, 31, 1113, 2267, 1899, 32, 1072, where the older literature is quoted See also Schneider, *J pr Chem* , 1898, [2], 68, 562, 1899, [2], 60, 524, Tanatar, *ZeiCanorg Chem* , 1901, 27, 437, Herz and Guttinann, *Zeit anorg Chem,* 1907, 53, 63, Vanino and Zumbusch, *Arch Pharm,* 1910,248, 665, Herz, *Zeit anal Chem,* 1915, 54, 103, 413, Treubert and Vanino, *ibid* , 1914, 53, 564, 1915, 54, 255**

suboxide (Tanatar) It reduces Fehlmg's solution and potassium permangaaate, and is converted by excess of alkaline stannous chloride into Metallic bismuth

Bismuth Trioxide, Bi_20_3, is found as bismuth ochre in Cornwall, Virginia, Siberia, and Erzgebirge, as a yellow or greenish-grey, amorphous mass or as a powder, and it usually contains ferric oxide and other impurities In order to prepare it artificially, the hydroxide, carbonate, or nitrate is heated Thus obtained, it is a yellow powder having a specific gravity of 8 2 It fuses at 820°, forming a brown liquid, and when this is allowed to cool the solid which is first formed passes at 704° with evolution of heat into a second modification, which forms a yellow, crystalline mass When fused in porcelain a third form is produced which crystallises in long, yellow needles of specific gravity 8 55 [1] When a boiling solution of a bismuth salt is precipitated with potash the trioxide is obtained in microscopic needles, and if this be melted with caustic potash the product is found to crystallise in rhombic prisms When the oxide is prepared by adding potassium cyamde to bismuth mtrate solution, boiling and heating the resulting grey powder in the air, it crystallises in tetrahedra belonging to the regular system It is therefore isodimorphous with antimony oxide [2] The oxide prepared by roasting the metal appears to have been employed as a yellow paint in Agncola's time

Bismuth trioxide is a stronger base than the corresponding oxide of antimony, and forms a well-defined series of salts, which are characterised by the ease with which they are converted by water into insoluble basic salts

Bismuth Trihydroxide, $Bi(OH)_3$, is obtained as a white, amorphous powder by precipitating a bismuth salt with cold caustic soda or ammoma It is soluble in caustic potash in the presence of glycerol,[3] and when precipitated from this solution by acids is free from basic salts, which are always present in the hydroxide prepared by precipitation with alkalis [4] When dried at 100°, it has the composition Bi_20_3,H_20 or BiO OH

Higher Oxides of Bismuth—When a current of chlorine is passed into a boiling solution of caustic potash or soda containing bismuth hydroxide in suspension, a red powder separates out which contains alkali and yields chlorine on boiling with hydro-

[1] **Gurtler,** ***Zeit anorg Chem,*** **1903, 37, 222**
[2] **Muir and Hutchinson,** ***Journ Chem Soc*** **, 1889, 55, 143**
[3] **Lowe,** ***Zeit anal Chem,*** **1883, 22, 498**
[4] **Thibault,** ***J Pharm,*** **1900, [6], 12, 559**

chloric acid Under varying conditions, the nature of the products obtained in this reaction also varies and substances described as bismuth tetroxide, Bi_2O_4, a brown powder, and the dihydrate of this oxide, $Bi_2O_4,2H_2O$, an orange-yellow powder, have also been prepared by means of it Similar highly oxidised products are formed by the electrolytic oxidation of the trioxide, and by the action of persulphates, of hydrogen peroxide, and of potassium ferncyamde on the trioxide in the presence of alkali [x] According to Gutbier and Bunz,[2] none of these reactions leads in any case to a definite homogeneous product

Worsley and Robertson,[3] however, claim that definite oxides may be obtained Using 5-10 per cent sodium hydroxide and oxidising with chlorine, the only product is *bismuth tetroxide*, Bi_2O_4, which is freed from trioxide and alkali by repeated grinding with glacial acetic acid Two forms of the anhydrous oxide exist, brown and purplish-black in colour, and also two similarly coloured forms of the monohydrate, $Bi_2O_4,H2O$ All are soluble in nitric acid, sp gr 12, with liberation of oxygen, and decompose at 160° When concentrated alkali solution is used, a yellow dihydrate, $Bi_2O_4,2H_2O$, is formed together with a red *pentoxide*, Bi_2O_5,H_2O When ammonium persulphate or potassium ferncyanide are used as oxidising agents, the product is the tetroxide when the reaction proceeds in boiling dilute alkali, but with concentrated alkali a small amount of a *hexoxide*, Bi_2O_6, is also formed, which may be separated from the tetroxide owing to its insolubility in nitric acid, sp gr 1 2 The hexoxide is an anhydrous, pale brown powder which slowly loses oxygen and darkens in colour at the ordinary temperature

BISMUTH AND THE HALOGENS

462 *Bismuth sub-iodide*, BiI_2, is a volatile substance, crystallising in red orthorhombic needles[4] The *sub-oxyiodide*, $2BiI_2,3BiO$, is non-volatile and begins to decompose at 350°

Bismuth Trifluoride, BiF_3, is obtained as a white powder

[1] See Deichler, *Zeit anorg Chem*, 1899, 20, 81, where a critical discussion of the earlier literature will be found Muir, *Journ Chem Soc*, 1887, 51, 77, Hollard, *Compt rend*, 1903, **136,** 229, Hauser and Vanino, *Zeit anorg Chem*, 1904, **39,** 381, Aloy and Frebault, *Bull Soc chim*, 1906, [3], **36,** 396, Moser, *Zeit anorg Chem*, 1906, 60, 33

[2] *Zeit anorg Chem*, 1906, 48, 162, 294, 49, 432, 50, 210, 1907, 52, 124, *Chem Centr* , 1909,1, 732

[3] *Trans Chem Soc*, 1920,**117,** 63

[4] Denham, *J Amer Chem Soc*, **1921, 43,** 2367

by dissolving the oxide in hydrofluoric acid and evaporating the solution An *oxyfluonde,* BiOF, is formed when the acid is completely neutralised by the oxide The fluoride forms a double salt with ammonium fluoride, BiF_3,NH_4F *

Bismuth Dichlonde, $BiCl_2$, is said to be formed when a slow current of chlorine is passed over the fused metal, or when the metal is heated with calomel to 250° or fused with the trichloride Thermal investigation of the system B1-B1CI3, however, does not indicate the formation of any dichloride, but shows that within certain limits the metal and its trichloride form mixed crystals [2]

Bismuth Trichloride, $BiCl_3$, was first prepared by Boyle [8] by heating bismuth with corrosive sublimate It is also formed when the metal is burnt in a stream of chlorine, or when a concentrated solution of the oxide in hydrochloric acid is distilled, the receiver being changed after all the water has come over Bismuth trichloride is a granular, white mass, which melts at from 225° to 230°, boils at 435° to 441°, and yields a vapour having the normal specific gravity of 11 35 (Jaquelam) Heated in a current a syrupy liquid when dissolved in a small quantity of water, though a larger quantity of water decomposes it, with formation of *bismuth oxychloride,* BiOCl, as a pure white powder, insoluble in water, but readily soluble in acids It separates from a hot acid solution in tetragonal crystals [5] of the sp gr 7 717 at 15°, and is decomposed by excess of caustic potash [6] Heated in air, bismuth oxychloride loses chlorine and takes up oxygen, in absence of air it becomes yellow-coloured, fusing without decomposition

When a solution of the oxide in an excess of hydrochloric acid is evaporated, fine, needle-shaped crystals are deposited, having the composition $BiCl_3,2HCl$, whilst at 0° a saturated solution of the two deposits crystals of the compound $2BiCl_3,HCl,3H_20$ which are stable at the ordinary temperature [7] Bismuth tri-

[1] Helmholt, *Zeit anorg Chem* , 1892, 3, 115 See also Muir, Hoffmeister and Robbs, *Journ Chem Soc,* 1881, 39, 33

[2] Marino and Becarelli, *Atti R Accad Lmcei,* **1915,** [5], 24, n, 625, **1916,** [5], 25, i, 105, **171,** 221, 326

[3] *Experiments and Considerations Touching Colours*

[4] Muir, *Journ Chem Soc* , 1876, I , **144**

[5] de Schulten, *Bull Soc chim* , 1900, [3], 23, 156

[6] Herz and Muhs, *Zeit anorg Chem* , 1904, 39, **115**

[7] Engel, *Compt rend,* 1888, **106,** 1797

chloride forms double salts with the chlorides of the alkali metals,[1] the chlorides of many bivalent metals,[2] and with many orgamc bases Ammonia yields three compounds—$BiCl_3 3NH_3$, a very volatile, colourless substance, $BiCl_3,2NH_3$, a dirty-grey, non-volatile mass, and $2BiCl_3,NH_3$, a red, crystalline body They combine with hydrochloric acid to form double salts, which are also obtained when ammonium chloride is added to the solution of bismuth in the right proportion and the mixture evaporated [3]

Bismuth trichloride combines also with nitric oxide [4] to form the yellow compound $2BiCl_3,NO$, and with mtrosyl chloride [5] to form an orange-coloured powder, $BiCl_3,NOCl$

Bismuth Tribrornide, $BiBr_3$ —When bromine vapour is passed over powdered bismuth an energetic reaction takes place and a red liquid volatilises This cools to a golden-yellow, glistening, deliquescent, crystalline mass, which melts at 210° and boils at 453° Bismuth tribromide crystallises from ether in prisms, and water decomposes it into the white insoluble *oxybromide,* BiOBr It forms crystalline double salts with the bromides of the alkali metals and also with the cyamdes of various metals [6] with ammonia it yields compounds similar to those of the chloride

Bismuth Tri-iodide, Bil_3, is obtained by treating the powdered metal with iodine and heating the product, by precipitating a bismuth salt with potassium iodide solution, dissolving in hydnodic acid, and reprecipitating with water, or, better, by adding bismuth oxide to a solution of iodine in stannous chloride saturated with hydrochloric acid [7] It sublimes in greyish-black, metallic, glistening, six-sided tablets, which are not decomposed by cold water, though they are converted by hot water into an insoluble oxyiodide If a solution of the iodide in hydnodic acid be evaporated, rhombic pyramids of $BiI_3,HI,4H_20$ are deposited Bismuth iodide forms a large number of double salts [8]

Bismuth Oxyiodide, BiOI, is obtained by decomposition of the

[1] See Brigham, *Amer Chem J,* 1892, **14,** 164, Field, *Journ Chem Soc,* 1893, 63, 546, Aloy and Frobault,, *Bull Soc chim ,* 1906, [3], 35, 396

[2] Weinland, Alber, and Schweiger, *Arch Pharm ,* 1916, **254,** 521

[3] Deherain, *Compt rend,* 1862, **54,** 924

[4] Thomas, *Compt rend ,* 1895, **121,** 128

[5] Sudborough, *Journ Chem Soc,* 1891, 59, 662

[6] Voumazos, *Compt rend,* 1921,**172,** 535

[7] Birckenbach, *Ber,* 1907, 40, 1404

[8] Nickles, *Compt rend,* 1860, 50, 872, *J Pharm,* [3], 39, 116, Linau, *Pogg Ann,* 1860, **111,** 240, Wells and Foote, *Amer J Sci,* 1897, 3, 461, Pfeiffer, *Zeit anorg Chem ,* 1902, 31, 191, Canneri and Penna, *Gazz ,* 1922, **52,** l , 241

tri-iodide with boiling water, or by heating the same in the air,[1] as a copper-red, crystalline mass, which can be sublimed when heated in the absence of air, but is gradually converted in presence of air into a crystalline oxide

BISMUTH AND THE ELEMENTS OF THE SULPHUR GROUP

463 *Bismuth Subsulphide,* BiS, was first described by Werther [2] and Lagerjhelm[3] as a grey, metallic, lustrous mass of needle-shaped crystals, obtained by fusing bismuth with sulphur and cooling quickly, but this contained free bismuth and the sulphide, Bi_2S_3 The existence of the same compound has been deduced by Pelabon,[4] but denied by Aten,[5] from the study of the equilibrium curve for bismuth and sulphur and the behaviour of these two elements in the presence of hydrogen

Bismuth Trisulphide, Bi_2S_3, occurs as bismuthite in rhombic crystals, and also massive with a foliated or fibrous structure, its specific gravity is 6 4 It is found at Brandy Gill, Carrock Fells in Cumberland, at Kedruth and Botallack and other localities in Cornwall, in the Erzgebirge, in Bolivia, and in other places It is obtained artificially by fusing the metal with an excess of sulphur, or by precipitating a solution of bismuth chloride with sulphuretted hydrogen or sodium thiosulphate Thus prepared, it forms a blackish-brown precipitate easily soluble in nitric acid and in boiling concentrated hydrochloric acid, but not in alkalis Its solubility in pure water has been found by the conductivity method to be 0 35 x 10^{-6} gram-molecules (0 2 mgm) per litre When it is heated to 200° in a solution of an alkali it becomes crystalline, assuming the form of bismuthite, and when heated in the electric furnace yields metallic bismuth [6]

The amorphous sulphide dissolves in potassium sulphide solution and very sparingly in sodium sulphide solution,[7] and

[1] Compare Dubrisay, *Compt rend,* 1909, **149,** 451

[2] *J pr Chem* , 1842, **27,** 65

[3] *Schweiggers Journ* , 1816, **17,** 416

[4] *Ann Chim Phys* , 1902, [7], 25, 365, *J Chim phys* , 1904, 2, 321, *Compt rend* , 1903,**137,** 648, 920

[5] *Zeit anorg Chem,* 1905, **47,** 386 Compare Schneider, *Pogg Ann* , 1856, **97,** 480, Herz and Guttinann, *Zeit anorg Chem,* 1907, 53, 63, 1908, 56, 422

[6] Mourlot, *Compt rend* , 1897, **124,** 768

[7] Ditte, *Compt rend* , 1895,**120,** 186 See also *J Amer Chem Soc* , 1896, 18, 683, 1091

forms salts of the formulae Bi_2S_3,K_2S and Bi_2S_3,Na_2S when it is fused with sulphur and an alkali carbonate [1]

Bismuth Oxysulphides —The compound Bi_4O_3S occurs as karelilinite at the Savodmck Mme in the Altai, it is a crystalline mass having a strongly metallic lustre

Bismuth Chlorosulphide, BiSCl, is obtained by fusing together in the air 1 part of sulphur and 8 parts of ammonium bismuth chloride, or by heating the latter compound in a current of sulphuretted hydrogen (Schneider), and also when the chloride is heated in dry sulphuretted hydrogen or the sulphide in dry chlorine It is a reddish-brown solid, not decomposed by water The corresponding *sulphobromide* is obtained similarly, whereas the *sulphwdide* can be prepared only by heating bismuth iodide with the trisulphide All three compounds are decomposed by sulphuretted hydrogen at a bright red heat [2]

Bismuth Trisulphate, $Bi_2(S0_4)_3$, is obtained as an amorphous, white mass by dissolving the metal or the sulphide in concentrated sulphuric acid and evaporating This salt is decomposed by water with formation of the basic salt, $Bi_20_3,S0_3,2H_20$ When this is heated it loses water, and on cooling a yellow mass, consisting of $Bi_20_3,S0_3$, is obtained This salt is also obtained by heating the other sulphates Another of these basic salts has the composition $Bi_20_3,2S0_3,3H_20$, and is obtained in small needles by acting upon the nitrate with sulphuric acid Several other basic salts have also been described[8] Concentrated sulphuric acid yields the acid salt, $Bi_20_3,4S0_3$, several hydrates of which have been obtained [4]

Bismuth Thiosulphate—Complex thiosulphates are obtained by the addition of the alkali thiosulphates to bismuth chloride solution The *potassium* salt, $K_3Bi(S_20_3)_3,½H_20$, is sparingly soluble in water, and the solution rapidly decomposes, bismuth sulphide being deposited This solution does not react with iodine The *sodium, ammonium,* and *strontium* salts are also known [5]

464 *Bismuth Triselemde,* Bi_2Se_3, is obtained by fusing the elements together as a metallic, lustrous, brittle, crystalline

[1] Schneider, *Pogg Ann* , 1869, **136,** 460
[2] Muir and Eagles, *Journ Chem Soc* , 1895, **67,** 90
[3] See Allan, *Amer Chem J,* 1902, **27,** 284
[4] Adie, *Proc Chem Soc* , 1899, **15,** 226
[6] Carnot, *Compt rend* , 1876, 83, 338, Hauser, *Zeit anorg Chem,* 1903, **35,** 1 Vanino and Mussgnug, *Arch Pharm* ,1919, **257,** 264

mass, having a specific gravity of 6 82, which is attacked only by nitric acta and aqua regia

Bismuth Tntellurtde, Bi_2Te_3, occurs as the mineral tetradymite, in which some of the tellurium is replaced by sulphur It forms pale metallic steel-grey rhombohedra, or foliated or granular masses having a specific gravity of 7 2 to 7 9 Groth[x] considers this mineral to be an isomorphous mixture of the elements, as it is not isomorphous with bismuthite, Bi_2S_3, and as bismuth and tellurium can be fused together in all proportions[2] Other bismuth tellundes of varying composition have been described, some of which occur as minerals According to Monkemeyer[8] only one stable compound of these two elements exists, namely, Bi_2Te_3, which melts at 573°

BISMUTH AND THE ELEMENTS OF THE NITROGEN GROUP

465 *Bismuth Nitride,* BiN, is formed as a brown precipitate when bismuth iodide dissolved in liquid ammoma is added to a solution of potassamide in the same solvent[4]

Bismuth Trinitrate, $Bi(NO_3)_3,5H_20$, is obtained in large, transparent, tnclinic prisms by dissolving the metal in nitric acid and evaporating the solution, which corrodes paper, and must, therefore, be filtered through asbestos or pounded glass The crystals, which are deliquescent, are decomposed on heating, losing their water, and then leaving a residue, first of basic salt, and lastly of the trioxide Hydrates with 2 and $1|H_20$ also exist[5]

Bismuth mtrate is isomorphous with the nitrates of yttrium, lanthanum, and others of the rare earth metals,[6] and forms double salts which are isomorphous with the corresponding salts of the rare earths and have been utilised in the fractional crystallisation of mixtures of these[7]

When hydrated bismuth mtrate is ground with mannitol and water added, a clear solution is formed which is not precipitated

[1] *Tabell Uebersicht d Mmerahen,* p 12 (Braunschweig, 1882, Vie weg)

[2] See also Amadon, *Atti R Accad Lmcei,* 1915, [5], 24, 11, 200, 1918, [5], 27,i 131

[8] *Zeit anorg Chem* , 1905, 46, 415 See also Gutbier, *ibid* , 1902, **31,** 331

[4] Franklin, *J Amer Chem Soc* , 1905, 27, 820

[5] van Beminelen and Hutten, *Proc K Akad Wetensch Amsterdam,* 1900, 3, 196

"Bodman, *Ber,* 1898, 31, 1237, *Zeit anorg Chem,* 1901, 27, 254, *Zeit Kryst Mm,* 1902, 36, 192

[7] Urbam, *Compt rend,* 1903, **137,** 568, *J, Chim, phys,* 1906, 4, 105

on dilution and serves as a means of preparing many insoluble bismuth salts by double decomposition[x]

Basic Bismuth Nitrate, $Bi(OH)_2NO_3$—Libavius was aware that the solution of bismuth in mtne acid is precipitated by water, and Lemery, who describes the preparation of this compound, states that water containing common salt should be employed for this precipitation, pure water precipitating it, but much more slowly, and he adds that the product obtained weighs more than the metal employed The reason of this, he explains, is that a certain quantity of spirit of nitre remains behind even if the precipitate be well washed Boyle states that the solution of bismuth in aqua-fortis is almost completely precipitated by common water In spite of this, many chemists, looking at the analogy between lead and bismuth, believed that salt water was necessary for the precipitation, indeed, the substance was for some time termed horn-bismuth This error was definitely rectified by Pott, in 1739

Basic nitrate of bismuth, formerly termed *magistery of bismuth,* is used as an important medicine, and many different receipts are given for its preparation According to the method formerly prescribed in the British Pharmacopoeia (1874), *bismuth submtras* is best obtained by dissolving 2 parts by weight of bismuth in a mixture of 4 parts of nitric acid of specific gravity 1 42 with 3 parts of water The clear liquid is poured off from any insoluble matter and evaporated to the point at which it occupies two volumes, and this is then poured into 80 parts of distilled water The clear liquid is then decanted and the precipitate well stirred up with 80 parts of water, collected on a filter, and dried at a temperature not higher than 55° The German and French pharmacopoeias recominended somewhat similar processes In all these methods a considerable quantity of bismuth remains in solution, and this may be obtained, as the hydroxide, by precipitating with ammoma The bismuth is completely precipitated when 50,000 parts of water are present to one of the nitrate [2]

Basic bismuth nitrate is a crystalline powder which reddens moistened litmus paper. Its composition varies somewhat according to the quantity of water used in the preparation, and a large number of basic salts have been described, the conditions of formation and existence of which have been investigated by

[1] **Vamno and Hauser, *Zeit anorg Chem* , 1901, 28, 210, *J pr Chem*, 1906, [21 74, 142**

*** Antony and Gigh, *Gazz* , 1898, 28, I , 245**

van Betamelen and Hutten,[1] by Allan,[2] and by de Schulten[3] When washfe Jpr a long time it becomes more basic, until at last the hydroxide is left

Basic bismuth nitrate is largely used as a medicine in cases of chrome diarrhoea and cholera It is also employed in considerable quantities as a cosmetic, and this use is due to Lemery, who recominends it for softening the skin When utilised foi this purpose it was first termed *blanc d'Espagne,* which name, however, served to designate many other white pigments Another name for this cosmetic is *blanc defard*

The basic mtrate, as well as the oxide, is also used for giving a colourless, iridescent glaze to porcelain This is obtained by rubbing up basic mtrate with resin and gently heating the mixture with lavender oil, and can be coloured by the addition of oxides, such as oxide of chromium, which gives to it a sulphur or lemon-yellow colour With addition of 5 per cent of gold to the oxide of bismuth, a splendid copper-red colour with a reflected golden lustre is obtained When a smaller quantity is employed, the glaze assumes a violet or pure blue colour, whilst with another treatment a rose-red tint is obtained These glazes are also used in glass-staining

466 *Bismuth Orthophosphate,* $BiP0_4$, is precipitated when solutions of bismuth nitrate and phosphoric acid are brought together in presence of nitric acid When slowly precipitated by water from acid solution it forms microscopic crystals of sp gr 6 323 at 15° (de Schulten) In the same way, an insoluble *pyrophosphate,* $Bi_3(P_20_7)_3$, is prepared with pyrophosphonc acid When the oxide and phosphorus pentoxide are fused together, a clear glass is obtained, which on slow cooling becomes crystalline, and probably consists of the tetrametaphosphate

Bismuth Arsenate, $Bi_4(As_20_7)_3$, is a white precipitate insoluble in water and nitric acid, but soluble in hydrochloric acid The *ortho-arsenate,* $BiAs0_4$, forms monoclmic prisms of sp gr 7 142 at 15° (de Schulten)

Phosphorus and *arsenic* do not readily combine with bismuth The first of these forms a compound with molten bismuth, and if a current of phosphme be passed through a solution of bismuth, a black phosphide is precipitated, which, however, decomposes in absence of air into its elements An alloy of bismuth and arsenic gives up the whole of the latter when heated.

[1] *Proc K Akad Wetensch Amsterdam,* 1900, 3, 196
[2] *Amer Chem* J, 1901, 26, 307 [3] *Bull Soc chim,* 1903, [3], 29, 720.

Arsme produces a black precipitate in bismuth solutions which behaves in a precisely similar way

BISMUTH AND THE ELEMENTS OF THE CARBON GROUP

467 *Basic Bismuth Carbonate,* $2(BiO)_2C0_3,H_20$, is obtained as a white powder when ammonium carbonate is poured into a solution of bismuth nitrate and the precipitate dried at a gentle heat It is employed as a medicine At 100° it loses water, stronger heating converts it into the trioxide

The mineral bismuthite, $3(BiO)_2C0_3,2Bi(OH)_3,3H_20$, is another basic carbonate and is found at Schneeberg, at Chesterfield, South Carolina, and at other places, together with bismuth ores It is a white or siskin-green, earthy mass, and sometimes occurs in acicular pseudomorphous crystals

Bismuth Silicate, $Bi_4(Si0_4)_3$, is found as eulytite in small, glistening yellow or brown regular tetrahedra and occurs in the Erzgebirge together with phosphates of iron and manganese

DETECTION AND ESTIMATION OF BISMUTH

468 When a bismuth compound is heated in the upper reducing flame of the Bunsen burner on an asbestos thread, a cold porcelain dish, held above it, receives a brown or black deposit of metallic bismuth, which is only slowly dissolved by cold dilute nitric acid A brittle metalhc bead is obtained when the compound is heated on the carbomsed match, and this dissolves in nitric ac

excess of stannous chloride and caustic soda A characteristic reaction of the bismuth salts is the precipitation of the blackish-brown sulphide with sulphuretted hydrogen, insoluble in ammomum sulphide, and easily soluble in nitric acid In addition to this, water produces, in solutions which are not too strongly acid, a white precipitate of an insoluble basic salt, and ammoma throws down a white precipitate of the hydroxide insoluble in excess These reactions serve to separate bismuth from other metals, as well as to detect its presence If other metals precipitable by sulphuretted hydrogen are present, the washed precipitate is first digested with ammonium sulphide, in order to separate arsenic, antimony, and tin The precipitate is then well washed, dissolved in nitric acid, and dilute sulphuric acid added to the nitrate to separate lead, the precipitate is filtered off, and an excess of ammoma added which throws down the

bismuth as the hydroxide, whilst any copper or cadmium present remains in solution The precipitate is dissolved in a small quantity of hydrochloric acid, the liquid concentrated by evaporation, and added to a large quantity of water, when the insoluble oxychlonde is precipitated Care must be taken that all the antimony is removed by long digestion of the sulphides with ammonium sulphide, and the residue well washed with water, for otherwise an insoluble oxychlonde of antimony may be precipitated and mistaken for bismuth

Bismuth can be estimated in several ways If the solution contains the nitrate only, it may be precipitated with ammomum carbonate, heated for some time almost to boiling, filtered, the precipitate dried and converted by ignition into the trioxide, which is weighed If other acids are present, the bismuth is precipitated by sulphuretted hydrogen, the washed precipitate dissolved in nitric acid, and treated as above, or it may be dried, excess of sulphur removed by carbon disulphide, and the residual sulphide dried at 100° and weighed The phosphate may also be precipitated in the presence of phosphoric acid or dilute nitric acid, ignited, and weighed [1] If the solution of the mtrate contains only a small quantity of free acid it may be precipitated with potassium dichromate, or with arsenic acid, and the precipitate dried and weighed Bismuth may also be estimated as the metal by reduction with potassium cyanide The metallic mass is well washed with water and alcohol, and weighed after drying Bismuth may also be separated electrolytically from an acid solution of the mtrate in the presence of alcohol, glycerol, or acid potassium sulphate [2]

The Atomic Weight of bismuth has been determined by several chemists, but without very concordant results In 1851 Schneider,[8] by converting the metal into the oxide, obtained the number 208 05, and this was confirmed in 1883 by Lowe,[4] who used the same method and obtained the number 207 8, and by Mangnac,[5] who, in 1883, found the atomic weight to be 208 16 by converting the oxide into the sulphate Dumas,[6] on the other hand, in 1859, by the analysis of the chloride, obtained the

[1] Stahler and Scharfenberg, *Ber*, 1905, 38, 3862, 3943, *Chem Zeit*, 1907, 31, 615

[2] *Compt rend*, 1900, 131, 179, *Zed anorg Chem*, 1901, 27, 1, *J Amer Chem Soc*, 1903, 25, 83, Richardson, *Zeit anorg Chem*, 1913, 84, 277

[3] *Pogg Ann*, 1851, 82, 303 [4] *Zeit anal Chem*, 1883, 22, 498

[5] *Zeit anal Chem*, 1884, 23, 120 [6] *Ann Chim, Phys* 1859, [3], 65, 177

number 210 7, which is certainly too high, and Mangnac, by analysing the oxide, obtained the value 208 6 In 1890 Classen [1] made a series of mne concordant experiments in which carefully purified bismuth was converted into the oxide and found the number 208 9 Schneider, in 1894,[2] repeated his experiments and again obtained the number 208 05 The lower determinations have been confirmed by the results obtained by Gutbier [3] and his co-workers, who obtained the values 208 02—208 15 by converting the metal into oxide, reducing the oxide to metal, converting the metal into sulphate, and determining the ratio $BiBr_3$ AgBr The value 208 0 is therefore (1922) adopted Nevertheless, it is possible that the higher results are more nearly correct, since Honigschmid,[4] who has analysed the pure chloride with all modern precautions, has obtained the value 209 02

[1] ***Ber*, 1890, 23, 938** [2] ***J pr Chem*, 1894, 56, 461**

[3] ***Zeit Elecktrcchtin*, 1905, 11, 831, *J pr Chem*, 1908, n, 77, 457, n 78, 409, 421 See also the Dissertations (Erlangen) of Birckenbach, 1905, Mehler, 1905, and Janssen, 1906**

[4] ***Zeit Elektrochem*, 1920, 26, 403 See also Honigschmid and Birckenbach, *Ber*, 1921, 54, *[B]*, 1873, Classen and Ney, *Ber*, 1920, 53, *[B]*, 2267**

GROUP VI

Sub-group (a)	*Sub-group (b)*
Oxygen	Chromium
Sulphur	Molybdenum
Selenium	Tungsten
Tellurium	Uranium

469 In this group, as in Groups I, I I, and **I I I,** the elements may be divided into two well-defined sub-groups, as shown in the above list, the sub-group *(a)* consisting of non-metallic elements (Vol I), whilst those in the sub-group *(b)* are metals Oxygen falls in the even series, and therefore strictly belongs to sub-group (6), but as in the case of glucmum in Group I I, it is much more nearly allied to the members of the odd series

Oxygen is gaseous at the ordinary temperature, whilst sulphur, selenium, and tellurium are solids, the melting and boiling points of which rise with increasing atomic weight The elements of the chromium group melt only at high temperatures, and are reduced from their oxides with difficulty

All the metals unite with the elements of the oxygen group to form oxides, sulphides, selenides, and tellundes, and the different series of compounds thus formed present strong analogies among themselves, as has already been seen in the description of the compounds of the metals of the previous groups The analogy which exists between the " oxy-salts " obtained by the union of a basic and an acidic oxide, and the " thio-salts " formed in a similar manner from the acidic and basic sulphides, has also been frequently alluded to

The most characteristic compounds formed by these elements (with, of course, the exception of oxygen) are the trioxides and their numerous derivatives All these behave as acid-formmg oxides, and give rise to well-defined series of compounds having the general formula $M^{I}{}_{2}B,{}^{VI}0_{4}$, in which M^{1} represents hydrogen, or a univalent metal, and R^{VI} an element of the group under consideration These possess strongly marked analogies with each other, and the salts of the same metal are as a rule isomorphous These oxides also form salts containing from

two to eight equivalents of the acidic oxide to one of basic oxide, such as the disulphates, $M^{I}_{2}0,2S0_{8}$, and dichromates, $M^{1}_{2}O,2CrO_{3}$, the tnchromates, $M^{1}_{2}O,3CrO_{3}$, the octotungstates, $M^{1}_{2}O^{\wedge}WOg$, etc

The constitution of the normal acids corresponding to the trioxides is represented by the formula $0_{2}R^{VI}(OH)_{2}$, and the hydroxyl groups in these acids may be replaced by negative radicles such as the halogens The compounds thus formed from the elements of lower atomic weight, such as sulphur and chromium, are acidic chlorides, and are at once decomposed by water with formation of the acid, but as the atomic weight of the element increases, the basicity of the radicle $R^{VI}0_{2}$ also increases, and the compounds become more stable, until, in the case of uranium, the compounds formed by negative radicles with the group $U0_{2}$ constitute the most stable series of salts

The elements of this group also form other oxides containing a less amount of oxygen than the trioxide, in the case of sulphur, selenium, and tellurium, these oxides ($R0_{2}$) are acidic or neutral, whilst with the metals of the chromium group (RO, $R_{2}0_{3}$, and $R0_{2}$) they are usually basic, and give rise to series of salts which often have strong reducing pioperties, owing to their tendency to umte with oxygen, forming derivatives of the trioxide

The elements of sub-group *(a)* combine with hydrogen and the alkyl radicles forming volatile compounds, the elements of sub-group *(b)* do not form similar derivatives

Oxygen is bivalent in almost all of its compounds, but possibly sometimes acts as a tetrad The remaining elements are, as stated above, sexavalent in their most characteristic oxygen compounds, but the valency in their other compounds, especially with the halogens, varies very considerably, the elements sulphur, selenium, and tellurium are always bivalent towards hydrogen and the alkyl radicles, and usually either bi-, quadri- or sexa-valent in their other compounds, but no such regularity is observed in sub-group (6)

CHROMIUM. Cr = 52-o. At No. 24.

470 In 1762 Lehmann, in a letter to Buffon, " de nova minerse plumbi specie crystalline rubra," described a new mineral from Siberia, now termed crocoisite Vauquehn and Macquart investigated the composition of this mineral in 1789, and came to the conclusion that it contained lead, iron, alumina, and a large

quantity of oxygen However, when the former chemist re-investigated the subject in 1797, he found that the lead present was combined with a peculiar acid, which he recogmsed as the oxide of a new metal To this the name of *chromium* was given, because its compounds are usually coloured (from %poiyia, colour) Chromium was discovered in crocoisite simultaneously and independently by Klaproth

Chromium is not a very common substance, and except for its occurrence in very small amounts in certain meteorites it is not found in the free state It is found in several other minerals besides crocoisite or lead chromate, $PbCr0_4$, especially as chrome iron stone or chromite, FeO,Cr_20_3, a mineral which is the chief ore of chromium and is the one usually employed for the manufacture of the chromium compounds Deposits in Khodesia and New Caledoma are of special economic importance, but the mineral occurs also in a number of localities in Europe, Asia Minor, North America, and New Zealand Chromium is widely distributed amongst certain classes of rocks, *e g*, basalts, in many of which it occurs in small amounts Chromitite, $(Fe,Al)_20_3,2Cr_20_3$, occurs as minute, lustrous crystals in the sand of some of the streams descending from the Kopaomk Mountains, Serbia [1] Ceylomte, which occurs in Western Australia, contains nearly 23 per cent of chromic oxide [2] Uvarovite or chrome garnet is $3CaO,Cr_20_3,3Si0_2$ Chromium also forms the colouring matter of several minerals, thus the green colour of emerald, as was shown by Vauquelin, is due to chromium, whilst serpentine, pennine, chromic mica or fuchsite, possibly sapphire,[3] and other minerals owe their colour to the same metal Attempts to imitate the unique spectra of such natural substances have met with partial success only[4]

Metallic chromium is obtained by the reduction of the oxide or chloride, thus Deville obtained it by strongly heating the oxide with sugar charcoal in a lime crucible,[5] and Wohler by heating chromic chloride with zinc under a layer of sodium chloride, and treating the alloy of zinc and chromium thus obtained with nitric acid,[6] it then forms a grey powder consisting of minute octahedra[7] Jager and Kruss obtained

[1] Jovitschitsch, *Monatsh,* **1909, 30, 39,** *Bull Soc franc Min,* **1912 (1913), 35, 511**
[2] **Simpson,** ***Mm Mag,*** **1920, 19, 99**
[3] **Duboin,** ***Ber,*** **1898, 31, 1977**
[4] Moir, *Trans Roy Soc S Africa,* **1918, 7, 129**
[5] *Compt rend,* **1857, 44, 673**
[6] *Annalen,* **1859, 111, 230**
[7] **Prinz,** ***Compt rend,*** **1893, 116, 392**

the pure metal by this process in tin-white rhombohedra[x] Magnesium and sodium have also been employed in place of metallic zinc, the first of these being specially suitable for a laboratory preparation[2] If a mixture of chromic chloride with finely divided iron is heated at 700-1200°, ferric chloride is volatilised, and the metallic chromium remains in a finely divided form[3] Another method of preparation is that of Moissan,[4] which consists in heating a mixture of chromium sesquioxide and carbon in the electric furnace, the first product contains large quantities of carbon, which is removed by first heating strongly with lime when the greater part of the carbon is converted into calcium carbide, and then eliminating the remainder by fusing the purified product in a crucible brasqued with the double oxide of calcium and chromium

Metallic chromium is easily prepared from chromic oxide by the " thermite " process (p 737), which consists in mixing finely divided aluminium with chromic oxide in slight excess of the equivalent proportion and igniting the mixture[5]

$$Cr_2O_3 + 2Al = 2Cr + Al_2O_3$$

When once started, the reduction proceeds rapidly with great evolution of heat, and produces a fused mass of metallic chromium of considerable purity This is shown by the following analysis [6] Cr 99 55 per cent, Fe 0 14 per cent, Si 0 31 per cent

Metallic chromium finds its chief techmcal application in the form of its alloys, large quantities are used in the form of ferro-chrome, manufactured by the reduction of chromite in the electric furnace or by means of aluminium, these ferro-chromes generally contain between 60 and 70 per cent of chromium Chromium has also been prepared by the electrolysis of a warm solution of chromic chloride or of a cold solution acidified with hydrochloric acid, and is thus obtained as a bright silver-white deposit[7] It can also be deposited from the violet solutions of chrome alum, but not from the green solutions

Pure chromium is somewhat harder than glass, and has a

[1] *Ber,* 1889, 22, 2052 [2] Glatzel, *Ber,* 1890, 23, 3127

[3] Weber, U S Pat 1373038

[4] *Compt rend,* 1893, **116,** 349, 1894, **119,** 185, *Ann Chim Phys,* 1896, [7], 8, 559

[5] *J Soc Chem Ind,* 1898, 17, 543 [6] *J Iron Steil Inst,* 1902, 1, 185

[7] Cowper Coles, *Chem News,* 1900, 81, 16, Feree, *Bull Soc chim,* 190), [3], 26, 617, Neumann, *Zeit Elektrochem,* 1901, 7, 656, Carveth and others, *J Physical Chem,* 1905, 9, 231, 353, *Zeit Elektrochem,* 1906, 12, 329, Askenasy and Revai, *Zeit Elektrochem,* **1913,** 19, **344**

melting point considerably higher than that of platinum, probably between 1520° and 1550°, whilst if it contains 1 5—3 per cent of carbdR it melts at a lower temperature, but can be cut only by the diamond It may be distilled in the electric furnace[1] The polished metal resembles iron, but is brighter and has a somewhat whiter colour it has a density of 6 92 at 20°, a specific heat [2] of 0 1080 at 50°, and burns when heated in the oxy-hydrogen flame more brilliantly than iron It is attacked by dilute hydrochloric acid, slowly in the cold and rapidly on heating, and also dissolves slowly in dilute sulphuric and nitric acids With concentrated sulphuric acid it evolves sulphur dioxide, with formation of a deep-coloured solution, but it is unaffected by hot concentrated nitric acid, its rate of solution in acids is characterised by periodic variations Chromium, like iron, has been found to exist in a " passive " state [3] Colloidal chromium has also been prepared [4]

471 *Chromium Alloys* —By far the most important are those with iron and mckel, since they are very resistant to corrosion, either with acids or by heating in the air " Nichrome " wire of the average composition 58—62 per cent Nl, 8—& per cent Cr, 23—26 per cent Fe, 0 5—2 per cent Mn, Zn, $Si0_2$, and 0 2—1 per cent C, is largely used as a resistance wire for electrically heated apparatus " Stainless steel " is an iron-chromium alloy [5]

Chromium Amalgams—By electrolysis of chromic chloride under suitable conditions, using a mercury cathode, a solid chromium amalgam is obtained having the composition Hg_3Cr Under pressure this loses mercury, yielding an amalgam of the composition HgCr When either of these amalgams is heated in a vacuum at 300°, the whole of the mercury is driven off, leaving the chromium as a powder which is pyrophonc at the ordinary temperature, and also combines with nitrogen on heating [6]

[1] Moissan, *Compt rend,* 1906, **142,** 425

[2] Schubel, *Zeit anorg Chem,* 1914, 87, 81 Seo also Jager and Kruss, *Ber,* 1889, **22,** 2028

[3] Hittorf, *Zeit physikal Chem,* 1898, 25, 729, 1899, 30, 481, Ostwald, *Zeit physikal Chem,* 1900, 35, 33, 204, Morgan and Duff, *J Amer Chem Soc,* 1900, **22,** 331, Brauer, *Zeit physikal Chem,* 1901, 38, 441, Dormg, *J pr Chem,* 1902, [2], 66, 65, Bernoulli, *Physikal Zeit,* 1904, 5, 632, Aten, *Proc K Akad Wetensch Amsterdam,* 1918, **21,** 138

[4] KMel, Ger Pat 197379, Svedberg, " *Herstellung kolloider Losungen anorgamscher Stoffe,*" 1909, p 413

[5] See Janecke, *Zeit Elektrochem,* **1917,** 23, 49, Murakami, *Sci Rep Tdhoku Imp Univ,* 1918, 7, 217

[6] Feree, *Compt rend,* 1895, **121,** 822

COMPOUNDS OF CHROMIUM.

CHROMIUM AND OXYGEN

472 Chromium combines with oxygen to form the well-defined oxides, chromium sesquioxide, Cr_2O_3, and chromium trioxide, CrO_3 The former is a basic oxide, corresponding to the chief series of chromium salts, in which the metal is tervalent, whilst the latter is an acidic oxide, which combines with water to form chromic acid, H_2CrO_4, the salts of which resemble the corresponding sulphates, selenates, and tellurates, and are frequently isomorphous with them

In addition to these, chromium monoxide, CrO, and the corresponding hydroxide have been prepared, and the latter yields with acids the *chromous* salts, in which the metal is bivalent A number of other oxides have been described which may be regarded as combinations of one or other of the basic oxides with the trioxide, the best defined of these is chromium dioxide, which has really the constitution $Cr_2O_3{\cdot}CrO_3 = 3CrO_2$, and will be described with the other chromates

Chromium Monoxide, CrO —An oxide of this composition is obtained as a black powder by the oxidation of chromium amalgam by exposure to air or by treatment with dilute nitric acid It cannot, however, be obtained by direct reduction of the sesquioxide When heated in air or when struck with a haminer it inflames and burns to the sesquioxide It is insoluble in nitric acid, but dissolves in hydrochloric acid with liberation of hydrogen and formation of chromous and chromic chlorides [x] By the action of hydrogen at 1000° it is reduced to the metal

Chromous Hydroxide, $Cr(OH)_2$, is formed by the action of aqueous potash, freed from air, on chromous chloride solution, as a brownish-yellow precipitate, which is readily oxidised with evolution of hydrogen, and on drying in absence of air has a dark brown colour [2] On ignition, it decomposes thus

$$2Cr(OH)_2 = Cr_2O_3 + H_2O + H_2$$

Chromium Sesquioxide, or *Chromic Oxide,* Cr_2O_3, occurs in the hydrated form as chrome ochre, and is obtained artificially as a dull green, amorphous powder by igniting the hydroxide or the

[1] Feree, *BuU Soc chim,* 1901, [3], 25, 619, Dieckmann and Hanf, *Zeit anorg Chem* , **1914, 86,** 301 See also Field, *J Ind Eng Chem* , **1916, 8, 238**

[2] Moberg, *J pr Chem,* **1848, 43, 114, 44,** 322, P&igot, *Compt rend,* 1844, 19, 609, 734, *Ann Chim phys,* **1844,** [3], **12, 528**

trioxide, or by heating a mixture of potassium dichromate with sulphut **5r ammonium** chloride, **and** lixiviating the residue The colour of then oxide prepared by gently igniting mercurous chromate, Hg_2Cr0_4, in a covered crucible is a very fine green It melts at the temperature of the oxy-hydrogen blowpipe, solidifying to a crystalline, almost black mass Chromic oxide is also obtained in the crystalline state by fusing the amorphous substance with calcium carbonate and boron trioxide, or by ignition in a stream of oxygen Wohler[1] considered that crystalline chromic oxide is formed by passing the vapour of chromyl dichloride, $Cr0_2Cl_2$, through a red hot tube, but the product appears to contain a large though varying proportion of a magnetic oxide, Cr_60_9 [2] Another method consists in heating potassium dichromate either alone, or, better, mixed with common salt, the ignited mass is dissolved in water, when chromic oxide remains in bright, iridescent spangles, which have a density of 5 01 [3]

The amorphous oxide glows when heated at 500—610°, [4] after strong ignition it is almost insoluble in acids, and in order to bring it into solution it must either be heated for a long time with strong sulphuric acid, or fused with potassium hydrogen sulphate The heats of formation of the various forms of chromic oxide exhibit striking differences [5] Chromic oxide is used in the preparation of coloured glass, enamels, and porcelain, imparting to them a fine green tint It forms one of the most permanent green pigments, known as chrome-green, it also finds limited application as a catalyst

Chromic Hydroxides—Pure chromic hydroxide, Cr_20_3,a:H_20,[6] may be obtained by precipitation of boiling solutions of chromic salts, free from alkali, with ammoma Several modifications are known, the first, which reacts directly with three equivalents of acid forming the normal chromic salts, is obtained by the action of alkalis on cold solutions of violet chromic salts, and has probably the constitution $Cr(OH)_3$ It is best prepared

[1] *Annalen,* 1846, **60,** 203

[2] Sone and Ishiwara, *Sci Rep TShoku Imp Umv,* 1914, 3, 271, Wedekind and Horst, *Ber,* 1915, 48, 105

[8] Schroder, *Pogg Ann,* 1859, **106,** 226, **107,** 113 See also Ditte, *Compt rend* , 1902, **134,** 336

[4] Rothaug, *Zeit anorg Chem,* 1913, 84, 165, Endell and Rieke, *Zentr Mm Qeol,* 1914, 246, Mixter, *Amer J Sci,* 1915, [4], 39, 295

[6] Mixter, *loc cit*

• Weiser, *J Physical Chem,* 1922, 26, 401, considers thab an indefinite number of hydrous oxides exists

by adding ammonia to a solution of a violet chromic salt free from alkali, and forms a pale blue precipitate, which, after drying over sulphuric acid, has the composition $Cr(OH)_3,2H_20$ When heated in a current of hydrogen at 200° it yields the hydroxide, CrO(OH), some water is retained even on long heating in hydrogen at 420^0,[1] but at a red heat it cominences to glow strongly and passes into chromic oxide A hydroxide of this composition, or Cr_20_3,H_20, has also been obtamed as a brown substance by the electrolysis of neutral solutions of chromic chloride[2] Another hydroxide, which has probably the constitution $Cr_20(OH)_4$, is obtained by dissolving the first-named hydroxide in sodium hydroxide solution and reprecipitating with hydrochloric acid, and is also formed by the action of alkalis on the green chromic salts of oxy-acids (p 1082), when treated with acids it reacts with only two equivalents of the latter, yielding the above green salts, which, however, on keeping in contact with acid gradually combine with it, forming the normal violet salts Another hydroxide which behaves similarly is formed, according to Recoura, by the action of alkalis on the chromic oxychlonde obtained by oxidation of chromous chloride solution It differs from the foregoing in the amount of heat evolved by the action of two equivalents of acid[3] Whilst chromic hydroxide, when freshly precipitated in the cold, is soluble in acids, it becomes insoluble when kept or heated

GuigneCs Green is obtamed by fusing together potassium dichromate and crystallised boric acid in equal moleculai proportions and lixiviating the fused mass with water The residue after grinding is a fine green powder, and is largely used as a pigment It is usually described as having the composition $Cr_20(OH)_4$, but it always contains boric acid, and may possibly have the composition $3Cr_20_{3)}B2()3,4H_20$

Colloidal Chromic Hydroxide—Freshly precipitated and washed chromic hydroxide dissolves in aqueous chromic Ghlonde, and on dialysmg this solution Graham obtained a liquid containing 33 molecules of Cr_20_3 to one of HCl If the dialysis is carried out with hot liquids, much purer chromic hydroxide sols are obtained in a few hours instead of in as many weeks at the ordinary temperature[4] The dark green solution does not undergo change on boiling or dilution, but at once coagulates

[1] Mixter, *he cit* [z] F6ree, *Bull Soc chim*, 1901, [3], 25, 620
[8] *Ann Chim Phys*, 1887, [6], 10, 60
[4] Neidle and Barab, *J Amer Chem Soc*, 1916, 38, 1961, 1917, 39, 71 See also Weiser, *loc cit*

on addition of the smallest quantity of a salt,[1] or slowly on merely keeping at the ordinary temperature The precipitated colloid has no costant composition between 15° and 280°[2] Violet and green jellies of chromic oxide can be produced by addition of caustic alkahs to stationary solutions of chromic salts containing a sufficient amount of sodium acetate[8]

Chromites—Although the solubility of chromic hydroxide in aqueous alkahs is doubtless due largely to the action of the alkali in converting the gel into a true colloidal solution,[4] it must depend in part on the fact that, like alumina, chromic oxide acts as an acidic oxide towards strong bases, yielding salts termed the chromites[5] Thus a green compound of chromic oxide with an alkali is thrown down on the addition of potash or soda to a solution of a chromic salt, and the alkali cannot be removed even by boiling water This precipitate is, however, easily soluble in an excess of the precipitant, but can be again thrown down either by partial neutralisation with acids or by boiling the solution When caustic soda is added to a solution of a chromic salt and a salt of magnesium (for instance), a precipitate is obtained of a compound of magnesia and chromic oxide which does not dissolve in an excess of alkali In this way, " chromites " or " absorption compounds" of sodium, potassium, calcium, barium, magnesium, zinc, lead, iron, cobalt, mckel, copper, and cerium have been obtained, in a gelatinous condition, or their existence has been indicated by physical measurements Their composition depends upon the conditions of their preparation

The chromites may be obtained also by the action of boiling aqueous alkahs on the corresponding sulphochromites

Better defined compounds are produced by fusion of the appropriate oxides, by strong ignition of metallic chromates, and by fusion of alkali chromates or dichromates with metallic

[1] Graham, *Phil Trans,* 1801, **151,** 183, Meunier, *J Soc Leather Trades Chem,* 1921, 5, 103 ,

[2] van Beminelen, *Rec trav chim,* 1887, 7, 114 See also Blitz, *Ber* , 1902, **35,** 4431, 1904, 37, 1095, Paal, *Ber* , 1914, 47, 2211, and Picton and Linder, *J Chem Soc,* 1897, 7i, 572, Lottermoser, *Uber anorg Kolloide,* Stuttgart, 1901, Siewert, *Z ges Nat,* 1861, 18, 244, van Beminelen, *Die Absorption,* Dresden, 1910, Baikow, *J Buss Phys Chem Soc,* 1907, **39,** 660, Reinitzer, *Monatsh,* 1882, 3, 249

[3] Bunce and Finch, *J Physical Chem,* 1913, 17, 769, Nagel, *ibid,* 1915, **19,** 331, 569

[4] Nagel, loc *cit,* Fischer and Herz, *Zeit anorg Chem,* 1902, **31,** 352, 1904, 40, 39, Bancroft, *Chem News,* 1916, **113,** 113

[6] Wood and Black, *J Chem Soc* , 1916, **109,** 164

chlorides In this way, chromites of lithium, barium, calcium, magnesium, zinc, copper, cadmium, manganese, iron, and cobalt have been prepared

Ferrous Chromite, $FeCr_20_4$ —This occurs in nature as chromite or chrome iron ore, a mineral of the spinel group, $M"0,M'"_20_3$, the proportions of ferrous oxide and chromic oxide exhibiting considerable variation withm limits Sometimes the composition approximates to $Fe_2Cr_2O_5$,$Fe_3Cr_4O_0$,[1] and alumina and magnesia frequently occur as isomorphous constituents Chromite is rarely found crystallised in regular octahedra, generally occurring massive, with a granular, crystalline fracture It is largely used in the manufacture of " neutral " refractory furnace-lmmgs

Chromous Chromite, CrO,Cr_20_3,xH_20 —This is stated to be a reddish-brown oxide, fairly stable in dry air[2]

CHROMIUM TRIOXIDE, CHROMIC ACID, AND THE CHROMATES

473 Chromic oxide is unchanged when heated alone in air, the hydroxide is not so stable, and in presence also of certain metallic oxides under appropriate conditions of pressure, oxygen is readily absorbed[3] A mixture of chromic acid with an alkali or alkaline earth can be completely oxidised by oxygen at a red heat, whilst if oxygen is supplied to the alkali-fusion in the form of potassium nitrate or chlorate, the reaction takes place even more readily, yielding a yellow, soluble mass of an alkali chromate

Alkaline solutions of chromic salts are easily oxidised to chromates by chlorine, bromine, hydrogen peroxide,[4] persul phates, and a number of other oxidising agents

$$Cr_20_3 + 10KOH + 3Br_2 = 2K_2Cr0_4 + 6KBr + 5H_20$$

Acid solutions are also susceptible to oxidation, though less easily, by potassium permanganate, lead dioxide, manganese dioxide, eene nitrate, and particularly by persulphates[5]

Electrochemical oxidation of chromic salts can be so successfully carried out that this method is now largely used for the

[1] Christomanos, *Ber,* 1877, 10, 343

[2] Moberg, *J pr Chem,* 1843, 29, 175, P61igot, *Compt rend,* 1844, 19, 609, 734, *Ann Chim Phys,* 1884, [3], **12,** 528, Bauge, *Compt rend,* 1898, **127,** 551

[3] Millbauer, *Chem Zeit,* 1916, 40, 587

[4] Bourion and Senechal, *Compt rend,* 1919, **168,** 59, 89

[5] Salinger, *Zeit anorg Chem ,'*1903, 33, 342

cominercial regeneration of chromate solutions from the chromic salts mtio *vjhich* they have become converted [1]

The chromates are usually yellow, yellowish-red, or red in colour, basic salts are known, but acid salts do not appear to exist The salts frequently termed acid salts are dichromates corresponding to the disulphates (pyrosulphates), and are salts of dichromic acid, $H_2Cr_20_7$ Tnchromates and other polychromates are also known

Chromium Tnoxide or Chromic Anhydride, $Cr0_3$—This compound is formed by the action of strong sulphuric acid on solutions of the chromates According to Zettriow[2] the best yield is obtained when 300 grams of potassium dichromate are mixed with 500 c c of water, 420 c c of concentrated sulphuric acid added, and the mixture is kept for twelve hours in order that the potassium hydrogen sulphate may crystallise out The mother-liquor is then heated to 80° or 90°, and 150 c c of sulphuric acid are added, together with enough water to dissolve the crystals of trioxide which at first separate out After twelve hours the liquid is poured off from the crystals which have separated, and a second and a third crop may be obtained by concentration The liquid is drained from the crystals, which are then washed on a pumice-stone or asbestos filter with pure nitric acid, of density 1 46, the adhering nitric acid being removed by passing a current of dry air over the crystals heated in a tube at 60-80° [3]

Chromium trioxide may also be obtained by the action of an excess of nitric acid of density 1 38 on barium chromate, the barium nitrate being separated by crystallisation [4]

Chromium trioxide exists either as a red, woolly mass or as lustrous, scarlet, rhombic prisms, it has a density of 2 78, and melts[5] at 198° to a dark red liquid, which solidifies to a reddish-black, crystalline mass, having a metallic appearance At about 420° it is completely resolved into oxygen and the sesquioxide [6]

Chromium trioxide is easily converted into chromic oxide by reducing agents, such as sulphur dioxide, hydrogen sulphide, stannous chloride, arsemous oxide, ferrous salts, zinc, etc, and many orgamc compounds also act in the same way Thus if

[1] Askenasy and ReVai, *Ze%t Elehtrochem,* 1913, **19,** 344, Boehringer, Ger Pat, 251694, *Zett Elehtrochem,* 1913, **19,** 248, Goldberg, Ger Pat, 303165

[2] *Fogg Ann,* 1871, **143,** 471 [8] Bunsen, *Annalen,* 1868, **148,** 290

[4] Duvilher, *Compt rend,* 1872, 75, 711

[6] Jaeger and Germs, *Zett anorg Chem,* 1921,**119,** 145

* Honda and Son6, *Set Bep Tohoku Imp Univ,* 1914, 3, 223

strong alcohol be dropped on to the dry trioxide reduction takes place with incandescence, paper, sugar, oxalic acid, etc, also reduce the solution of the trioxide, especially on warming When the trioxide is heated with aqueous hydrochlonc acid, chlorine is liberated, the dry gas yjelding chromyl chlonde (p 1070), and when heated with sulphuric acid it decomposes with evolution of oxygen The aqueous solution of chromium trioxide as well as its solution in glacial acetic acid is often used in organic chemistry as an oxidising agent Still more commonly, a mixture of potassium dichromate and dilute sulphuric acid is employed for this purpose, in which case chrome alum is obtained as a by-product Chromium trioxide dissolves without alteration in cold dilute alcohol and pure ether, and it is soluble also in concentrated sulphuric acid, apparently[x] with formation of the compounds $Cr0_3,S0_3$ and $Cr0_3,S0_3,H_20$, but least in acid containing 16-17 per cent of water It deliquesces in the air, forming a brown solution which on dilution with water becomes yellowish-red This dyes the skin, as well as silk and wool, a yellow colour, and possesses an acid and astringent taste

Chromic Acid, H_2Cr0_4—The existence in the solid condition of normal chromic acid has been asserted by Moissan[2] From the conductivity, molecular refractivity, and molecular solution volume it has been concluded[3] that solutions of chromium trioxide contain only dichromic acid, $H_2Cr_20_7$, on the other hand, Costa[4] and Dehn[5] consider that both chromic and dichromic acids are present in a state of equilibrium It is observed that in very dilute solutions, chromic acid, dichromates, and chromates have identical colour, the hydrolysis $H_2Cr_20_7 + H_20 = 2H_2Cr0_4$ is then regarded as complete, more concentrated solutions contain both chromic and dichromic acids, whereas further increase of concentration or temperature apparently dehydrates the molecules, forming *tnchromic acid,* $H_2Cr_3O_{10}$, and *tetrachromic acid,* $H_2Cr_40_{13}$, the salts of which may be represented as $(M'0)Cr0_2\,O\,Cr0_2\,O\,Cr0_2(OM')$ and

$$(M'0)Cr0_2\,0\,Cr0_2\,O\,Cr0_2\,O\,Cr0_2(OM')$$

respectively

[1] **Gilbert, Buckley and Masson,** *J Chem Soc* **, 1922,121, 1934, Meyer and Stateozny,** *Zext anorg Chem,* **1922, 122, 1**

[2] **Moissan,** *Compt rend,* **1884, 98, 1581**

[8] **Ostwald,** *Zeit physikal Chem,* **1888, 2, 78, Datta and Dhar,** *J Amer Chem Soc,* **1916, 38, 1303**

[4] **Costa, Gazz , 1906, 86, i, 535**

[5] **Dehn,** *J Amer Chem Soc,* **1914, 38, 829, Dhar,** *Zeit anorg Chem, 1921,* **121, 99.**

Chromic acid, $CrO_2(OH)_2$, in its chemical properties resembles sulphuric acid, and the normal salts are usually isomorphous with the corresponding sulphates, similarly, dichromic acid correspondiAo disulphunc (pyrosulphunc) acid

By direct solution of metals[1] or by reaction with bases, there are produced the normal chromates and dichromates, of which potassium dichromate is the most important

Normal Potassium Chromate, K_2CrO_4, is obtained by the addition of potassium hydroxide to a solution of the dichromate, evaporation yielding yellow, rhombic pyramids which are isomorphous with potassium sulphate Potassium chromate has a density of 2 71 at 3 9°, and does not undergo alteration in the air On heating to 666° it is converted into a second modification, it becomes red-coloured, and melts at 978° without decomposition, solidifying on cooling to a crystalline mass It dissolves in water with a yellow colour which is perceptible even when very small quantities of the substance are present, one part of the salt imparting a distinct yellow tint to 400,000 parts of water One hundred parts of water dissolve[2] at

—114°*	**0°**	**30°**	60°	**105 6°f**
54 57	57 11	65 13	74 60	88 8 parts

* Cryohydric point **t** Boiling point of saturated solution

The salt has a bitter, cooling taste and an alkaline reaction On evaporating its solution, red crystals of the dichromate are first deposited and afterwards the yellow crystals of the normal salt It is decomposed by all acids, even by carbonic acid, with formation of the dichromate It is insoluble in alcohol

Potassium Dichromate, or *Bichromate of Potash,* $K_2Cr_2O_7$, serves as the starting point for the preparation of almost all the other chromium compounds, and is prepared on the large scale from chrome iron ore

Up to the year 1820 potassium dichromate was used only for the purpose of making chrome yellow, and was prepared by the calcination of chrome iron ore with costly saltpetre In the above year Kochlm introduced potassium dichromate into the process of Turkey-red dyeing, and it was soon employed for a variety of other purposes, especially in wool dyeing In its preparation, potashes were employed instead of saltpetre,

[1] **See van Name and Hill,** ***Amer J Set,*** **1916, [4], 42, 301, 1918, [4], 45, 54**

[2] **Koppel and Blumenthal,** ***Zeit anorg Ghent,*** **1907, 53, 262**

and the chrome iron stone was oxidised in reverberatory furnaces by means of atinospheric oxygen An important improvement was made in the process by Stromeyer by the introduction of a certain quantity of lime together with the potash Not only was a saving of alkali thus effected, but the oxidation was rendered easier, inasmuch as the whole mass did not fuse, and therefore remained porous and more capable of absorbing the atinospheric oxygen The chrome iron ore is first roasted and 4½ parts of the finely ground ore are mixed with 2¼ parts of potassium carbonate and 7 parts of lime This mass after drying at 150° is heated to bright redness with an oxidising flame, the whole being constantly stirred At the end of the operation the charge is withdrawn from the furnace, and, after cooling, is lixiviated with the minimum amount of hot water If calcium chromate be found in solution, a hot saturated solution of potassium sulphate is added, when the calcium is thrown down as sulphate and potassium chromate remains in solution The liquor is next treated with the requisite quantity of sulphuric acid, diluted with twice its volume of water, to convert the chromate into dichromate, and allowed to cool The solution of chromate saturated at 16° contains nearly 1 part of salt to 2 parts of water, whilst the dichromate requires 10 parts of water for its solution, hence when the saturated solution of chromate is converted into dichromate, a precipitate of about 75 per cent of the dichromate is formed on cooling The precipitate is collected and recrystalhsed The mother-liquor, which contains potassium sulphate, is used to lixiviate another portion of the roasted mass

An important modification of this procedure consists in the manufacture of sodium dichromate (p 1065) by a similar process, and the final conversion of this into the potassium salt

This salt may be produced also by electrolysing a solution of potassium hydroxide or a potassium salt, using an anode of ferrochrome [1]

Potassium dichromate crystallises in splendid garnet-red tablets or prisms belonging to the trichnic system, having a density of 2 692 at 3 9° It melts at 396°, forming a transparent, red liquid, which when slowly cooled crystallises in the same form as from aqueous solution It is unchanged in the air, and decomposes at a white heat into oxygen, chromic oxide,

[1] Lorenz, *Zeit anorg Chem*, 1896, 12, 396, C F Gnesheim Elektron, Ger Pat, 143320

and the normal salt One hundred parts of water dissolve[1] at

—0 *	o°	30°	60°	104 8° f
4 50	4 64	18 09	4610	106 2 parts of salt

Cryohydnc point † Boiling point of saturated solution

Potassium dichromate has an acid reaction, a cooling, bitter, metallic taste, and is insoluble in alcohol, it acts as a powerful poison, probably on account of its oxidising properties The cominercial salt is usually almost chemically pure, and is employed for the preparation of other chromium compounds, as a reagent, and as an oxidising agent, as well as being largely used in dyeing and calico-printing

A film of organic matter saturated with a solution of potassium dichromate acquires a dark colour on exposure to light owing to a reduction to chromic oxide taking place, and a solution in gelatin is used as a sensitive agent in the Autotype and other similar photographic printing processes, commonly referred to as " carbon printing " These processes depend not merely upon the de-oxidation of the dichromate, but also upon the fact that this reduction renders the gelatin insoluble in, and non-absorbent of, water, so that those portions of the gelatin film which have been acted upon by the light remain unchanged when the film is iminersed in hot water, whilst those parts which have been protected from the action of the light dissolve away entirely A film is thus obtained in which the various shades of the original negative are represented by deposits of varying thickness of the insoluble gelatin, which can be coloured with a wide range of pigments, in this way the red or blue chalk drawings of the old masters can be reproduced with remarkable accuracy [2]

Potassium dichromate forms a double salt with mercuric chloride, $K_2Cr_20_7,HgCl_2$, which separates in red, well-developed, rhombic crystals

Potassium Tnchromate, $K_2Cr_3O_{10,}$ is formed by the action of chromic acid solution on the dichromate, but is best prepared by boiling the dichromate with nitric acid of density 1 19, on cooling, potassium mtrate separates almost completely, and the decanted liquor then deposits the tnchromate in deep red,

[1] **Koppel and Blumenthal, *Zeit anorg Chem,* 1907, 63, 262**

[2] **For a full and interesting description of these processes, see Abney's *Treatise on Photography* (Longmans)**

monochnio prisms of density 2 648 It is decomposed by hot water into chromic acid and the dichromate, and cannot therefore be recrystalhsed in this manner[1]

Potassium Tetrachromate, $K_2Cr_4O_{13}$, is obtained by heating the dichromate with nitric acid of density 1 41, and separates out on cooling in brownish-red crusts consisting of small, rhombic plates It has a density of 2 649, and, like the trichromate, is decomposed by water into chromic acid and the dichromate.

Normal Sodium Chromate, $Na_2CrO_4,10H_2O$, is obtained by direct oxidation of chromite in presence of lime and soda (p 1059), by fusing chromic oxide and sodium nitrate together, and evaporating the solution at a low temperature, or by allowing a solution of potassium chromate saturated with soda to evaporate at 0° However, the only method of obtaining the pure salt is by addition of sodium carbonate to a solution of carefully purified sodium dichromate The salt is deposited in deliquescent, transparent, yellow prisms, isomorphous with Glauber's salt When the solution is heated to above 65° the anhydrous salt separates out It has an alkaline reaction, and a bitter, metallic taste Hydrates containing $4H_20$ and $6H_2O$ have also been obtained [2]

Sodium Dichromate, $Na_2Cr_2O_7,2H_2O$ crystallises in thin tnclinic, yellowish-red, deliquescent prisms This salt is now manufactured on a large scale, since for many techmcal purposes it can replace the more expensive potassium salt It is much more soluble than the latter, and for this reason is used as a depolanser in chromic acid cells in place of the potassium salt Above 83°, aqueous solutions deposit the anhydrous salt, a deliquescent substance which melts at 230° and decomposes at 400°

The following salts are also known *sodium tnchromate,* $Na_2Cr_3O_{10},H_2O$, *sodium tetrachromate,* $Na_2Cr_4O_{13},4H_2O$, and a *basic chromate,* $Na_4CrO_5,13H_2O$

Ammonium Chromate, $(NH_4)_2CrO_4$ —This salt can be obtained pure only from solutions containing excess of ammonia, as it readily loses the latter, forming the dichromate It is obtained in golden-yellow, monoclinic needles by gently warming pure chromium trioxide with a quantity of ammonia just sufficient to dissolve the chromate formed, and cooling the solution in a

[1] **Jager and Kruss, *Ber* , 1889, 22, 2038**

[2] **Salkowski, *Ber*, 1901, 34, 1947, Richards and Kelley, *J Amer Chem Soc*, 1911,33,847**

freezing mixture One hundred parts of water at 30° dissolve 40 46 parts of the salt The *dichromate,* $(NH_4)_2Cr_20_7$, is readily obtained by adding the requisite quantity of chromium trioxide to ammonia, and separates out on evaporation in orange-red, monochnic crystals of density 2 367 At 30°, 47 17 parts dissolve in 100 parts of water The substance is stable in air, even at 100°, but on ignition it decomposes into nitrogen, water, a bulky, leaf-like mass of chromium sesquioxide, and generally a little ammonia This salt forms a number of crystalline double salts with mercuric chloride [x]

The *trichromats* and *tetrachromate* have also been prepared

Chromates, dichromates, etc, of the other alkali metals are known, as well as a number of double salts, these are formed not only amongst the alkali chromates themselves, and between the alkali chromates and chromates of other metals, but also between the alkali chromates and mercuric chloride and cyanide

474 Most of the other metals form chromates or basic chromates which are for the most part coloured substances insoluble in water, many of which are largely used as pigments The most important of these are the following

Copper Chromates —Copper Bichromate, $CuCr_2O_7,2H_2O$, is obtained by the action of concentrated chromic acid solution on copper hydroxide It forms blackish-brown, deliquescent crystals The solution when boiled deposits the basic salt $Cu_3CrO_6,2H_2O$[2] as a brown precipitate, which is also obtained when boihng solutions of normal potassium chromate and copper sulphate are mixed, cold solutions, on the other hand, yield a double salt The mineral vauquelmite, $(Cu,Pb)_3Cr_2O_9$, occurs in small, glistening, monochnic crystals or earthy masses, together with crocoisite *Normal copper chromate,* $CuCrO_4$, forms mixed crystals with copper sulphate

Silver Chromate, Ag_2CrO_4, is obtained as a brick-red, amorphous precipitate when a solution of potassium chromate is poured mto excess of a concentrated solution of silver nitrate either cold or hot[3] It is formed when silver dichromate is boiled for a long time with water as a deep green, crystalline powder,[4] which is insoluble in water, but dissolves with some difficulty in sulphuric acid, nitric acid, or ammonia The

[1] **Jager and Krtiss, *Ber,* 1889, 22, 2047**
[2] **Groger, *Monatsh,* 1903, 24, 483** [3] **Autenneth, *Ber,* 1902, 35, 2057**
[4] **Margosches, *Zeit anorg Chem,* 1904, 41, 68, 1906, 51, 231, Kohler, *ibid,* 1916, 96, 207**

solution obtained by dissolving silver chromate in as small a quantity as possible of warm ammonia of density 0 94 deposits ammonio-silver chromate, $Ag_2CrO_4,4NH_3$, on cooling in long, yellow needles [1] which by heating yield green silver chromate

The red chromate may be converted into the green form by heating in an atinosphere of carbon dioxide (Autenrieth)

Silver Dichromate, $Ag_2Cr_2O_7$, is obtained by the action of potassium dichromate on silver nitrate in acid solution, it forms small, red, triclinic crystals, and is decomposed by boihng water into chromic acid and normal chromate It is also obtained by warming silver chromate with dilute nitric acid [2]

Barium, Chromate, $BaCrO_4$, is a yellow precipitate, insoluble in acetic, but easily souble in nitric, hydiochlonc, and aqueous chromic acids From the last solvent, the salt $BaCr_2O_7,2H_2O$ may be obtained in yellow, stellar needles, which are decomposed by water with separation of the noimal salt Barium chromate is used as a pigment under the name of *yellow ultramarine* or *lemon chrome* It is, however, now very little used, as the lead chromates have a brighter colour and more body

Zinc Chromates —Potassium chromate gives with zinc sulphate a yellow precipitate of basic zinc chiomate, $Zn_2(OH)_2CrO_4,H_2O$ A similar compound, $2Zn_2(OH)_2CrO_4,H_2O$, is formed when zinc carbonate is heated with a solution of chromic acid The normal chromate and dichromate have also been prepared

If a salt or oxide of zinc is boiled with potassium dichromate the yellow compound, $Zn_4(OH)_6CrO_4$, is precipitated

The chromate obtained by the addition of a hot neutral solution of zinc sulphate to potassium chromate forms a stable yellow pigment sold under the name of *Zinc yellow* or *Buttercup yellow*

Lead Chromate^ $PbCrO_4$, occurs as crocoisite in translucent, yellow, monoclmic prisms, having a density of 5 9 to 6 1 The mineral is found in Siberia, in the Urals, Brazil, Hungary, and the Philippine Islands Crystals of somewhat higher density are artificially obtained when lead chloride is strongly heated with potassium chromate, as well as when solutions of lead acetate and normal potassium chromate are allowed slowly to diffuse into one another[3] A bright yellow precipitate of the normal

[1] Muthmann, *Ber,* 1889, 22, 2O51

[2] Autenrieth, *Ber,* 1902, 36, 2059, Shemll, *J Amer Chem Soc,* 1907, 29, 1641, Spitalsky, *Chem Zentr,* 1914, n, 376

[3] Drevermann, *Annalen,* 1863, 87, 121

chromate is obtained when a solution of a lead salt is precipitated with potassium dichromate The reaction $PbSO_4 + K_2CrO_4 = ^J)CrO_4 + K_2SO_4$ is practically complete, and can be used [x] for the manufacture of the normal salt, which is known as *chrome yellow, Pans yellow,* or *Leipsig yellow,* and is largely used as a pigment It is insoluble in water, but is readily dissolved by nitric acid and potassium hydroxide solution When strongly heated it fuses to a brown liquid, which on cooling solidifies to a crystalline mass [2] Since lead chromate at a red heat oxidises all orgamc substances, it is frequently employed in orgamc analysis, especially in the case of bodies which contain chlorine, sulphur, etc The chrome yellow of cominerce often contains admixtures, especially lead sulphate This, however, is not always to be considered as an adulteration, and it is used for the preparation of a light shade This is termed *Cologne yellow,* and is obtained by the precipitation of a mixture of the mtrates of lead and calcium with a mixture of sodium sulphate and potassium chromate, or more generally by heating lead sulphate with a solution of potassium dichromate

Calico is printed or dyed with chrome yellow by first mordanting the cloth with a solution of a lead salt, and afterwards steeping it in one of a soluble chromate

Basic Lead Chromate, Pb_2CrO_s, is known in cominerce as *chrome red* and is obtained as a fine red powder by digesting chrome yellow with cold sodium hydroxide solution, boiling it with a solution of normal potassium chromate, or fusing it with potassium mtrate Another basic salt, $Pb_3Cr_2O_9$, occurs as the mineial phoenicite, in hyacinth-red crystals of density 5 75, the salt $4PbO,CrO_3,H_2O$ is known, as also[3] are Pb_6CrO_8 and $Pb_7Cr_2O_{13}$

By making a suitable mixture of chrome yellow and chrome red, or by modifying the process of manufacture so as to obtain a mixture of these, pigments of any shade between the two may be obtained These are known cominercially as *chrome orange*

Lead dichromate and the chromate and dichromate of quadrivalent lead have been prepared by an electrolytic method [4]

[1] **Milbauer and Kohn, *Zeit phystkal Chem,* 1916, 91, 410**

[2] **Jaeger and Germs, *Zeit anorg Chem,* 1921, 119, 145, find that lead chromate is trimorphous, the *a* form is stable below 707°, the)8 form between 707° and 783°, and the *y* form above 783°, melting at about 844° with evolution of oxygen**

[3] **Jaeger and Germs, *loc cit***

[4] **Elbs and Nublmg, *Zeit Elektrochem,* 1903, 9, 776 See also Mayer, *Ber,* 1903, 36, 1740, Cox, *Zeit anorg Chem* , 1906, 60, 226**

Bismuth Chromate—Normal *bismuth chromate* is unknown, but a number of basic salts have been described By addition of potassium chromate solution to a solution of bismuth mtrate, the compound $K_2O,Bi_2O_3,4CrO_3$ is obtained as a yellow precipitate, on boiling this with water, the compound $Bi_2O_3,2CrO_3$ or *bismuthyl dichromate,* $(BiO)_2Cr_2O_7$, is obtained as orange-yellow crystals, insoluble in water

Chromic Chromate, $Cr_2O_3CrO_3 = 3CrO_2$ —This compound, also known as *chromium dioxide,* is formed when chromic mtrate is gently heated, or when a solution of chromic oxide in nitric acid is evaporated to remove excess of acid and the residue dissolved in water and treated with ammomum hydroxide[x] It is likewise prepared by the partial reduction of the trioxide, and by the precipitation of a chromic salt with a soluble chromate The brown powder thus obtained is easily soluble in acids Alkalis precipitate chromic hydroxide from its solution, whilst a chromate remains in the liquid If chromic chromate be washed for some time with water, it is decomposed into soluble trioxide and insoluble sesquioxide, for these reasons the substance is regarded as a chromate When nitric oxide is passed into a tolerably concentrated solution of potassium dichromate, chromic chromate is obtained as a dark brown precipitate, which dries at 25O° to form a black, hygroscopic powder, and this, when heated in a current of hydrogen chloride, yields chromic oxide, water, and chlorine

A hygroscopic black powder has also been obtained by Manchot and Kraus[2] by heating chromic hydroxide in a current of oxygen This contains a little water, which it gives off at a red heat along with some of its oxygen, chromic oxide remains When washed with water, no chromium trioxide is obtained, and these investigators therefore consider it to be a dioxide, CrO_2, and not chromic chromate

When the vapour of chromyl chloride is passed through a red hot tube, violet, translucent prisms, having the composition Cr_5O_9 (*le,* $2Cr_2O_3,CrO_3$), are obtained These are magnetic, and on ignition are gradually converted into chromic oxide [3]

An oxide of the formula Cr_4O_9 (*i e,* $Cr_2O_3,2CrO_3$) has been

[1] Jovitschitsch *Helv Chim Acta,* 1920, 3, 40 See also Hooton, *Proc Chem Soc* , 1908, 24, 27, Ogata, *J Pharm Chim* , 1916, [7], 14, 144

[2] *Ber,* 1906, 39, 1352 See also Meerburg, *Zeit anorg Chem,* 1907, 54,31

[3] Geuther, *Annalen,* 1861, 118, 61, Sone and Ishiwara, *Set Rep Tdhoku Imp Umv,* 1914, 3, 271

described as being the product of the ignition of the trioxide between 500° and 510°.[1]

A number of crystalline double chromates have been described which have the general formula $M'_2M''(CrO_4)_2,6H_2O$, where M' is K, Rb, NH_4, or Cs, and M" is Nl, Mg, or Cd, as well as ammoniacal double chromates of the formula $M'_2M''(CrO_4)_2,2NH_3$, where M' is K or NH_4, and M" is Cu, Zn, Cd, Ni, or Co[2]

HALOGEN AND AMIDO-DERIVATIVES OF CHROMIC ACID

475 *Ohromyl Difluoride,* CrO_2F_2—This substance was first obtained by Unverdorben by the action of sulphuric acid on a mixture of lead chromate and fluorspar, and was regarded by him as chromium hexafluonde, Oliveri[3] has, however, characterised it as chromyl fluoride, derived from chromic acid by the replacement of the two hydroxyl groups by fluorine Ruff's[4] attempt to obtain a substance of definite composition by this method, or, better, by substituting fluorosulphonic acid for calcium fluoride and sulphuric acid, and a mixture of potassium dichromate and chromium trioxide for potassium dichromate alone, was, however, unsuccessful The substance is obtained as a red gas, condensing in a freezing mixture to a very volatile, blood-red liquid which attacks glass, and is converted by the moisture of the air into chromium trioxide and hydrogen fluoride

Fluorochromic acid, $CrO_2F(OH)$, is unknown in the free state, but its *potassium* salt is formed by heating potassium dichromate with hydrofluoric acid in a platinum vessel, it crystallises in red, tetragonal pyramids, which are soluble in water, but the solution decomposes on boiling into potassium dichromate and hydrofluoric acid The *ammonium* salt is also known

Chromyl Dichloride, CrO_2Cl_2, appears to have been discovered by Thomson[5], it was also investigated by Berzelius,[6] Dumas,[7] and Wohler[8] It is prepared[9] by treating a dry, finely divided mixture of five parts of common salt and eight parts of potassium dichromate with fifteen parts of fuming sulphuric acid

[1] Shukow, *Compt rend,* 1908, **146,** 1396
[2] Bnggs, *Journ Ckem Soc* , 1903, 83, 1391, 1904, 86, 672, 677
[3] Oliveri, *Gazz,* 886, **16,** 218 [4] Buff, *Ber,* 1014, **47,** 656
[5] *Phil Trans,* 1827, **117,** 159 [6] *Berz Jahresoer* , 1827, 6, 129
[7] *Ann Chim Phys* , 1826, [2], 31, 433, Walter, *ibid,* 1837, [2], **66,** 387
[8] *Pogg Ann,* 1834, 33, 343
[9] Moles and Gomez, *Zeit physikal Chern,* 1912, 80, 513, *Anal lis Qmm* , 1914, 12, 142

added in small quantities, and finally gently warming the mixture, in order to remove free chlorine, the distillate is repeatedly rectified in a current of carbon dioxide It is also formed by heating chromium trioxide in a current of hydrogen chloride, when it distils over, and an oily liquid remains which has been thought to be *chlorochromio acid,* CI CrO_2 OH It may readily be obtained by dissolving chromic acid in concentrated hydrochloric acid, and adding sulphuric acid to the cooled liquid in small quantities at a time The heavier chromyl chloride is then run off, dry air is blown through, and the liquid distilled [1] It may also be obtained [2] in 8O per cent yield by addition of acetyl chloride to a solution of chromium trioxide in carbon tetrachloride Chromyl dichloride is a mobile liquid of a splendid blood-red colour by transmitted, and nearly black by reflected light It boils at 116 7°, and has a density at 25° of 1 912 [3] The molecular weight of chromyl chloride, determined by the usual methods, gives values corresponding to the above formula It absorbs chlorine readily, dissolves iodine, and when dropped into water it remains unaltered for a few seconds, but is afterwards decomposed with violent ebullition into chromic and hydrochloric acids When brought into contact with phosphorus it explodes, whilst it takes fire in contact with sulphur, hydrogen sulphide, ammoma, alcohol, and many other orgamc bodies, and when diluted with acetic acid or carbon tetrachloride acts as an oxidising and chlorinating agent upon hydrocarbons With phosphorus hakdes it yields additive compounds [4] When chromyl dichloride is heated in a closed tube to 180° foi three or four hours, *tnchromyl chloride,* $Cr_3O_6Cl_2$, is formed as a black powder, which deliquesces on exposure to the air, [5] another solid oxychlonde is stated to have the composition $(CrO_2)_5Cl_6$ [6]

Bromine and iodine do not form analogous chromyl derivatives, a bromide or iodide, heated with sulphuric acid and potassium dichromate, yields free bromine or iodine This reaction is made use of for the detection of chlorine in presence of bromine or iodine, if chlorine be present the substance, when heated with

[1] Law and Perkin, *Journ Chem Soc,* 1907, **91,** 191
[2] Fry, *J Amer Chem Soc,* 1911, 33, 697
[3] Moles and Gomez, *loc cit* See also Thorpe, *Journ Chem Soc,* **1880* 37,** 327
[4] Fry **and** Donnelly, *J Amer Chem Soc* , 1916, 38, 1923, **1918, 40, 478**
[6] Thorpe, *Journ Chem Soc,* 1870, 23, 31
[7] Pascal, *Compt rend,* 1909,**148,** 1463

potassium dichromate and sulphuric acid, yields chromyl chloride, which is converted by water into chromic acid, which may be recognised by the usual tests

Chlorochromic acid, $ClCrO_2OH$, analogous to chlorosulphonic acid, is unknown, but its *potassium* salt is formed [1] when three parts of potassium dichromate are gently heated with four parts of concentrated hydrochloric acid and a small quantity of water, or when chromyl dichloride is added to a saturated solution of potassium chloride

$$CrO_2Cl_2 + KCl + H_2O = KCrO_3Cl + 2HCl$$

It crystallises in flat, red, rectangular prisms, having a density of 2 497 The salt is partially decomposed by water, but may be recrystalhsed from water containing hydrochloric acid, or from glacial acetic acid It decomposes at 100° with evolution of chlorine

$$4CrO_2(OK)Cl = K_2Cr_2O_7 + Cr_2O_3 + 2KCl + Cl_2 + O_2$$

Other chlorochromates have been described,[2] as well as potassium bromo- and lodo-chromates

Amidochromic acid, NH_2CrO_2OH — It is doubtful whether, by the action of dry ammonia on chlorochromates in solution or suspension in organic media, salts of amidochromic acid are formed, as has been suggested,[3] liquid ammonia, however, apparently leads to the formation of salts of *imidochromic acid,* $NHCrO(OH)_2$ [4]

Perchromic Acid and the Perchromates —A deep indigo-blue coloured solution is obtained when hydrogen peroxide is added to an aqueous solution of chromium trioxide, or to a solution of a chromate acidified with sulphuric acid If the freshly prepared solution be shaken with ether, this liquid takes up the perchromic acid and becomes of a dark blue colour The ethereal solution is more stable than the aqueous solution, but on evaporation it leaves a residue of chromium trioxide The same decomposition is effected by alkalis, a chromate being formed with evolution of oxygen The colouring power of

[1] Peligot, *J Pharm,* 1833, 19, 301

[2] Peligot, *Ann Chim Phys,* 1833, [2], 62, 267, Praetonus, *Annalen,* 1880, **201,** 1, Loewenthal, *Zeit anorg Chem* , 1894, 6, 355

[3] Hemtze, *J pr Chem,* 1871, [2], 4,212, Loewenthal, fee *cit* , Wyrouboff, *Bull Soc chim,* 1894, [3], **11,** 845, Werner and Klein, *Zeit anorg Chem,* 1895, 9, 291, Meyer and Best, *ibid,* 1900, **22,** 192

[4] Rosenheim and Jacobsohn, *Zeit anorg Chem,* 1906, 60, 297

perchromic acid is so great that its formation is employed as a most delicate test, both for chromic acid and for hydrogen peroxide The deepest coloration is produced when two molecules of hydrogen peroxide are used to one molecule of chromium trioxide The constitution of the substance thus formed is as yet uncertain It has been variously regarded as Cr_2O_7,xH_2O,[1] $CrO_6,3H_2O$,[2] CrO_3,H_2O_2,[8] and $2HCrO_4,H_2O_2$,[4] etc By the action of sodium peroxide on a thm paste of chromic hydroxide and water Haussermann[5] obtained a sodium salt having the composition $Na_6Cr_2O_{15},28H_2O$, which would be the salt of an acid derived from the anhydride CrO_6 When this salt is treated with sulphuric acid, the characteristic blue colour is first produced, but oxygen is soon evolved, and chromic sulphate remains in solution Salts of a perchromic acid, $HCrO_5$, $[O_3Cr\,O\,(OH)$, in which c and other organic bases have been prepared by Wiede,[6] by adding the bases to the blue ethereal solution of perchromic acid cooled below O° These are explosive crystalline compounds, which evolve oxygen when treated with strong acids In a similar manner, he has obtained blue potassium and ammomum salts, which he regards as $(NH_4)CrO_5,H_2O_2$ and $KCrO_5,H_2O_2$, the hydrogen peroxide acting like water of crystallisation On the other hand, according to Kiesenfeld,[7] the last two compounds are acid salts of the perchromic acid, H_3CrO_7, and have, therefore, formulae of the type $R^IH_2CrO_7$ They are also formed by the action of hydrogen peroxide on chromates in cold, faintly acid solution, in alkaline solution red salts of a perchromic acid, H_3CiO_8, are obtained The red ammomum salt, $(NH_4)_3CrO_8$, with dilute acids, gives off oxygen and forms the blue salt, $(NH_4)H_2CrO_7$, and both these compounds yield with pyridine Wiede's salt of the acid $HCrO_5$, finally, all three compounds with excess of ammonia form tnammine chromium tetroxide, $CrO_4,3NH_3$ This compound[8] is a brown, explosive, crystalline substance which has density 1 964 at 15 8°

[1] Barreswil, *Ann Chim Phys* , 1847, [3], 2O, 364
[2] Fairley, *Chem News,* 1876, 33, 337
[3] Moissan, *Compt rend,* 1883, 97, 96
[4] Berthelot, *ibid,* 1889, **108,** 25 [5] *J pr Chem* , 1893, [2], 48, 7O
[6] *Ber,* 1897, 3O, 2178, 1898, 31, 516, 3139, 1899, 32, 378 See also Hofmann and Hiendlmaier, *ibid,* 1905, 38, 3O59
[7] *Ber,* 1905, 38, 4068, 1908, 41, 2826, 1911, 44, 147, *Zeit anorg Chem,* 1912, 74, 48 Compare Hofmann and Hiendlmaier, *Ber,* 1904, 37, 1663
[8] Wiede, *Ber,* 1897, 3O, 2178, 1899, 32, 378, Riesenfeld, Wohlers, Kutsch, and Ohl, *Ber,* 1905, 38, 1885, 338O

Riesenfeld considers that when excess of hydrogen peroxide acts on a solution of chromic acid, the acid H_3CrO_8 (which, though blue, has a composition corresponding to the red perchromate) is mainly produced, but at the same time a little of the acid H_3CrO_7 is also formed, whilst the blue ethereal solution probably contains a mixture of several perchromic acids [1] When perchromic acid is prepared by the action of hydrogen peroxide on chromyl chloride or upon chromium trioxide in methyl ether solution at — 3O°, it is found to possess the formula $H_3CrO_8,2H_2O$, the water is water of constitution Thus the blue acid may be regarded[2] as having the formula $(OH)_4Cr(O\ OH)_3$, whereas the red perchromates are anhydro-salts of the formula $(MO\ O)_3CrO_2$

CHROMOUS SALTS

476 By dissolving metallic chromium in acids, or by reduction of chromic salts or chromates with metals or by an electrolytic process,[3] compounds of bivalent chromium are obtained It is essential that air should be excluded during the operation, since the chromous salts in solution are readily oxidised to chromic salts and chromic acid, with intermediate formation of unstable compounds [4] They are powerful reducing agents [5] The anhydrous salts are usually white, and yield solutions the colour of which is blue in the case of salts of strong acids, and yellow, brown, or red in other cases

Chromous Fluoride, CrF_2, known only in the anhydrous condition, is a green, lustrous substance It is obtained by the interaction of chromium or chromous chloride with hydrogen fluoride

Chromous Chloride, $CrCl_2$, is formed by the ignition of chromium in hydrogen chloride, or of chromic chloride in a current of hydrogen gas free from'oxygen, and forms white, silky, lustrous needles which are stable in dry air It dissolves in water with evolution of heat, forming a blue solution, which absorbs oxygen with extreme avidity, yielding basic chromic salts, and forms a power-

[1] See also Spitalsky, *Zeit anorg Chem*, 1907, 53, 184, 1907, 64, 265, 1907, 66, 72, 1910, 69, 179, *Ber* , 1910, 43, 3187

[2] Riesenfeld and Mau, *Ber*, 1914, 47, 548

[3] Traube and Goodson, *Ber* , 1916, 49, 1679, Taylor, Gersdorff and Tovrea, J *Amer Chem Soc*, 1922, 44, 612

[4] Piccard, *Ber*, 1913, 46, 2477, Traube and Passarge, *Ber*, 1913, 46, 16O5, have found that double salts with hydrazine are much more stable

[5] Traube and Passarge, *Ber*, 1916 49, 1692

ful reducing agent The solution is sometimes employed in gas analysis for the absorption of oxygen It is found, however,[1] that chromous chloride prepared by treating chromous acetate with hydrochloric acid is less stable than that prepared by reduction of chromic chloride in solution with nascent hydrogen, the latter solutions, however, do not give complete absorption Further, acid solutions of chromous chloride spontaneously decompose with liberation of hydrogen [2] $2CrO + H_2O = Cr_2O_3 + H_2$ Kecoura [3] states that the solution may be obtained by adding a mixture of 300 c c of pure fuming hydrochloric acid with 200 c c of water to 300-400 grams of amalgamated granulated zinc and 50 grams of finely powdered potassium dichromate in a flask of about 3 litres capacity A violent action occurs, the liquid becoming first green, then sky-blue

Hydrates of chromous chloride are known as follows $6H_2O$, $4H_2O$ (dark blue), $4H_2O$ (dark green),[4] $3H_2O$, and $2H_2O$ With ammonia, white chromous chloride forms a violet tnammine and an ashy-grey hexammine [5]

The vapour density of chromous chloride at 1300° was found by Nilson and Pettersson to be 7 8, considerably lower than is required by the formula Cr_2Cl_4 At 1600° the density is further reduced to 6 2, showing that probably at a higher temperature its density would finally reach 4 25, corresponding to $CrCl_2$ [6]

Chromous Bromide, $CrBr_2$, is obtained by gently heating chromic bromide in hydrogen gas, and also by heating the metal in gaseous hydrobromic acid It is a white, crystalline mass, yielding a green basic chromic bromide on exposure to moist air

Chromous Iodide, CrI_2, is a crystalline mass obtained by heating chromium in gaseous hydnodic acid [7]

Chromous Sulphide, CrS, is obtained by igniting chromous chloride in hydrogen sulphide, or by the long continued heating of chromic sulphide in hydrogen, and forms a black powder attacked only with difficulty by acids [8] It may also be prepared by heating chromium to a high temperature in hydrogen sulphide,

[1] **Anderson and Riffe, *J Ind Eng Chem*, 1916, 8, 24**

[2] **Traube and Passarge, *Ber*, 1916, 49, 1692**

[3] **Recoura, *Compt rend*, 1887, 100, 1227, *Ann Chim Phys*, 1887, [6], 10, 1**

[4] **According to Werner's views, these isomeric tetrahydrates have the formulae $[Cr(OH_a)JCl_a$ and $[CrCl(OH_2)_3]Cl,H_2O$ respectively See Knight and Rich, *J Chem Soc*, 1911, 99, 87**

[5] **Ephraim and Millmann, *Ber*, 1917, 50, 529**

[6] ***Journ Chem Soc*, 1888, 58, 830**

[7] **Moissan, *Compt rend*, 1881, 92, 1051** [8] ***Ibid*, 1880, 90, 817**

when it is obtained in needles having a density of 4 O8, and sufficiently hard to scratch quartz [1]

ChrOmouS Sulphate, $CrSO_4,7H_2O$, is prepared by dissolving the metal in dilute sulphuric acid It is best obtained by dissolving chromous acetate in dilute sulphuric acid, on cooling it separates in fine blue crystals isomorphous with ferrous sulphate The ammoniacal solution absorbs oxygen, nitric oxide, and acetylene If potassium sulphate be dissolved in a cold saturated solution of the chloride, alcohol added until a precipitate begins to form, and the mass kept for some weeks in absence of air, fine blue rhombic prisms, having the composition $K_2SO_4,CrSO_4,6H_2O$, and isomorphous with the corresponding ammonium salt, are deposited, these soon become green in the air owing to absorption of oxygen

Chromous Carbonate, $CrCO_3$, is obtained by precipitating the chloride with potassium carbonate A yellow to greenish-blue precipitate is obtained in the cold, which becomes reddish-brown on warming Several double salts of chromous carbonate with the alkali carbonates have been prepared by the action of carbon dioxide on a mixture of solutions of chromous acetate and the alkali carbonate [2] These are powerful reducing agents decomposing water at 10O° with evolution of hydrogen

Chromous Acetate is a red, crystalline precipitate obtained by addition of a concentrated solution of sodium acetate, saturated with carbon dioxide, to a solution of chromous chloride, and washing the product with air-free water

CHROMIC SALTS

477 The normal chromic salts have a blue or violet colour, and allow red light to pass through their solutions The cold solutions have a violet colour, which on heating changes to green, in some cases the solution iminediately becomes violet on cooling, but in others this occurs only on keeping the cooled solution for some time Only the violet solutions of the salts with oxy-acids yield crystalline salts, the green solutions depositing an amorphous mass on evaporation Many attempts have been made to explain the changes which take place, and much light has been thrown on the subject by the researches of Eecoura

[1] Mourlot, *Compt rend,* 1895, 121, 943, Wedekind and Horst, *Ber,* 1915, 48, 105

[2] Baugc, *Compt rend ,* 1896,122, 474, 1897,126, 1177, 1898,126, 1566

and others The salts which have been ijiost closely examined are the chloride, bromide, and sulphate

A certain complexity is thus introduced into the chemistry of the chromic salts owing to the existence of isomeric compounds the constitution of which can best be investigated from the point of view of Werner's [x] ideas of co-ordination compounds Thus the chloride forms three distinct hexahydrates, and the bromide two distinct hexahydrates These ionise differently in water, yielding solutions from which one-third, two-thirds, or the whole of the chlorine is precipitable by silver mtrate solution The constitution of such isomers will be discussed later

CHROMIUM AND THE HALOGENS

478 *Chromic Fluoride,* CrF_3 —The anhydrous salt is obtained by passing hydrogen fluoride over heated chromic chloride, and sublimes at about 12OO° in rhombohedra Hydrates with 3 5,6, and $9H_2O$ are known The last named, $[Cr(H_2O)_6]F_3,3H_2O$, is obtained by adding ammonium fluoride to a cold solution of chromic sulphate It is sparingly soluble in water, but dissolves in hydrochloric acid, forming a violet solution When heated in the air chromium trioxide [2] The salt is used to some extent in the dyeing of wool

Double fluorides with other metallic fluorides are known, as well as various complex salts [3] In the case of the salt of the composition $Cr_2F_2Cl_4$, the fluorine is not precipitable by barium chloride [4]

Chromic Chloride, $CrCl_3$ —The anhydrous chloride is obtained [5] by heating metallic chromium or an intimate mixture of chromic oxide and carbon to dull redness in a stream of dry chlorine It forms peach-blossom coloured scales, which have a density of 2 76 It volatilises at 1065°, yielding a vapour of the density 6 135, the formula $CrCl_3$ requiring 5 478, and Cr_2Cl_6 corresponding to a density twice as great, hence this latter compound cannot exist in the state of vapour From 1190° up to 13OO° the density

[1] For a detailed explanation of Werner's theories, see A Werner, " *Neuere Anschauung auf dem Gebiete der anorganischen Chemie* " (4th edn , Braunschweig, 192O)

[2] Poulenc, *Compt rend,* 1891, **116,** 253, Fabris, *Gazz* 1890, 2O, 582

[3] Reooura, *Compt rend,* 1913, **157,** 1525, Costachesou, *Ann Sci Univ Jassy* 1914, 8, 16

[4] Reooura, *loc cit*

[5] From chromite, see Badische Anilm- und Soda-Fabnk, Ger **Pat**, 281996

is 5 5 (Nilson and Pettersson) Chromic chloride is almost msdluble in cold water, but it is readily soluble in presence of a very snmll quantity (less than O OO1 per cent) of chromous chloride, cuprous chloride, stannous chloride, or other reducing agents[1] The dilute solutions of the chloride have a violet colour, whilst the concentrated solutions or those containing a large excess of acid are green Recoura[2] has shown that the heat evolved by the action of an equivalent quantity of soda is nearly 5O per cent greater in the case of the green solutions, and that as the concentration of the solution increases, the evolution of heat gradually increases from the value for the violet solution (+ 22 2 Cal) to that for the dark green (+ 31 5 Cal) The colour of the solution at the same time gradually changes from violet to pure green, thus indicating a gradual transition of the violet into the green modification It has also been shown[3] that equilibrium between the green and the violet salts is set up in solution, either salt leading to the same final conditions, depending on the concentration In dilute solutions, the salt is almost all present in the violet form, $[Cr(H_2O)_6]Cl_3$, whilst as the concentration increases the equilibrium shifts more and more

in favour

at the ordinary temperature, but may be attained in 24 hours at 84° Both modifications have been isolated in the crystalline condition by Recoura, and both have the same composition, $CrCl_3,6H_2O$[4]

The dark green chloride, $[CrCl_2(H_2O)JCl,2H_2O$, separates

in small, e

chloride is passed through a well-cooled, saturated solution of chromic chloride If the crude chloride be dissolved in its own weight of water, warmed for a few minutes to 80°, and then cooled to O°, the solution contains both the dark green and the -violet salt, and on passing in hydrogen chloride, only the latter sepaiates at first, and may be obtained free from the green modification if it be iminediately filtered oil It forms greyish-blue crystals which dissolve in water, forming the characteristic bluish violet solution Intermediate between the violet hexahydrate and the dark green hexahydrate is the light green hexahydrate,

[1] Rohland, *Zeit anorg Chem*, 1899, 21, 37, *ibid*, 1903, 29, 159, Druckcr, *Zeit fhysikal Chem*, 1901, 86, 173

[2] Recoura, *Ann Chim Phys*, 1887, [6], 10, 5

[3] Roozeboom and Olie, *Proc K Akad Wetensch Amsterdam*, 1905, 8, 6O, *Zed anorg Chem*, 1906, 51, 29, Werner and Gubser, *Ber*, 1901, 84, 1379,

[4] Marchetti, Gazz 1882, 22, 375,

$[CrCl(H_2O)_5]Cl_2,H_2O$, obtained by Bjerrum[1] by adding ether saturated with hydrogen chloride to the solution left after precipitating the violet salt with hydrochloric acid. It forms a light green, microcrystalline powder which is even more hygroscopic than the other isomers, on attempted drying *it* passes gradually into the dark green compound[2] The latter substance, however, when kept in a desiccator, loses two molecules of water, forming a tetrahydrate, whilst a decahydrate is also known[3] The constitution of these hydrates will be discussed in conjunction with that of the ammomacal compounds of chromium *(q v)* Certain lower hydrates are stated to possess a red colour, as also does the compound CrClg^CgH^OH

Basic chromic chlorides have been prepared,[4] the composition of which varies according to the method of preparation[5]

Double compounds of an oxychlonde of chromium with the chlorides of the alkali metals have been described, in which the chromium appears to be qumquevalent Thus the potassium compound, $CrOCl_3,2KCl$, is formed as a garnet-red, crystalline precipitate when a solution of potassium chloride is added to a concentrated solution of chromic acid which has previously been treated with hydrochloric acid at —2O°, and the mixture saturated at O° with hydrogen chloride Similar examples have been prepared with qumolme and pyridine hydrochlorides[6]

Chromic Bromide, $CrBr_3$ —The anhydrous salt is prepared in a similar way to the chloride It forms almost black, semi-metallic, translucent, hexagonal scales which in thin sections appear green by transmitted and red by reflected light In its properties it

[1] **Bjerrum, *Ber,* 1906, 39, 1597, *Zeit physikal Chem,* 1907, 59, 581 See also Wemland and Schumann, *Zeit anorg Chem* , 1908, 58, 176**

[2] **For double salts of these chlorides, see Larsson, *Zeit anorg Chem,* 192O, 110, 153, Weinland and Koch, *ibid,* 1904, 39, 296, Weinland and Schumann, *ibid* , 1907, 40, 3767**

[3] **Werner and Gubser, *Ber,* 1901,34,1379, Ohe, *Zeit anorg Chem,* 1907, 53, 268**

[4] **Moberg, *J pr Chem,* 1843, 29, 175, Schiff, *Annalen,* 1862, 124, 168, Ohe, *Zeit anorg Chem* , 1906, 52, 62**

[5] **For further information regarding the chromic chlorides, see Elias, *Anal Fis Quim,* 191816, 467, Feytis, *Compt rend,* 1913, 156, 886, Wyrouboff, *ibid,* 1913,156,1072, Heydweiller, *Zeit anorg Chem,* 1915, 91,66, Lamb and Fonda, *J Amer Chem Soc* , 1921, 43, 1154, Hopfgartner, *Monatsh* , 1919, 40, 259, Baldwin, *J Amer Leather Chem Assoc* , 1919,14,10, Kurilov, *KoUoid Zeit,* 1914,14, 171**

[6] **Meyer and Best, *Zeit anorg Chem,* 1899, 22, 92, Wemland and Fridrich, *Ber,* 1905, 38, 3784, Wemland and Fiederer, *Ber,* 1906, 37, 4042, 1907, 40, 2O90**

closely resembles the chloride, and dissolves easily in water, when a small quantity of chromous bromide, or any other reducing agent, su|jh as tinfoil, is present Solutions of chromic bromide behave in an analogous manner to those of the chloride, and yield two isomeric salts, the one forming bluish-grey, and the other green crystals, both of which have the composition $CrBr_3,6H_2O$ [1] The former has the constitution $[Cr(H_2O)_6]Br_3$ and the latter is $[CrBr_2(H_2O)_4]Br,2H_2O$ An octahydrate also exists

Chromic Iodide, $CrI_3,9H_2O$, forms unstable violet crystals [2]

CHROMIUM AND SULPHUR

479 *Chromium Sesquisulphide,* or *Chromic Sulphide,* Cr_2S_3 — This is obtained by heating chromium with sulphur, or by igniting chromic chloride, or the trioxide, in a current of hydrogen sulphide It forms either a blackish-grey powder with a metallic lustre, or an elastic mass having a density of 3 77 When heated in the air it burns with formation of the green oxide, and in chlorine yields sulphur chloride and chromic chloride This compound cannot be prepared in the wet way, as soluble sulphides precipitate the hydroxide from chromic salts, with liberation of sulphuretted hydrogen

$$2CrCl_3 + 6H_2O + 3(NH_4)_2S = 2Cr(OH)_3 + 6NH_4C1 + 3H_2S$$

Chromic Sulphate, $Cr_2(SO_4)_3$, is obtained by mixing equal parts of concentrated sulphuric acid and chromium hydroxide dried at 10O° The mixture is allowed to stand in a loosely-stoppered bottle, when the green solution becomes blue, and

in some week

purified by solution in water and precipitation with alcohol Thus obtained, it is a violet, crystalline powder, with less alcohol, blue octahedra containing 18 molecules of water are deposited Chromic sulphate and the sulphates of the alkali metals form double salts, corresponding to the alums, to which the name of *chrome-alums* is given

Potassium Chromic Sulphate, $K_2SO_4,Cr(SO_4)_3,24H_2O$, or *Chrome Alum* is best obtained by the reduction of a solution of potassium dichromate, $K_2Cr_2O_7$, by adding the requisite quantity of sulphuric acid, and passing sulphur dioxide through the solution

$$K_2Cr_2O_7 + H_2SO_4 + 3SO_2 = K_2SO_4 + Cr_2(SO_4)_3 + H_2O$$

[1] Recoura, *Compt rend* ,1890,110,1029 See also Hem, *Ber,* 1919,52, *[B],* 195
[2] Higley, *J Amer Chem Soc,* 1904, 26, 613

In place of sulphur dioxide any other easily oxidisable substance such as alcohol, etc, may be employed, but in this case more sulphuric acid must be added Chrome alum is now obtained in large quantity as alizarin from anthracene, $C_{14}H_{10}$, in which the hydrocarbon is treated with a mixture of sulphuric acid and potassium dichromate, when anthraqumone, $C_{14}H_8O_2$, is formed, and this is then subjected to fuither treatment The salt crystallises in large, dark purple-red, almost black octahedra, which, when seen by transmitted light, exhibit a ruby-red colour One litre of water at 25° dissolves 243 9 grams of the crystalline salt, the solution has a dingy blue colour, with a tinge of red, which when heated to 7O° becomes dark green After standing for several months, however, it returns to its ordinary colour (see below) Chrome alum is used in dyeing and calico-printing as well as in tanning

Ammonium Chromic Sulphate, $(NH_4)_2SO_4,Cr_2(SO_4)_3,24H_2O$, is obtained by crystallising a mixture of the two salts, or by reducing ammonium dichromate in presence of sulphuric acid The salt is less soluble than the potassium compound, and crystallises readily in fine ruby-red octahedra, which effloresce in the air

A number of other crystalline double chromic sulphates, both anhydrous and hydrated, have been described [x]

Action of Heat on Chromic Sulphate and its Double Salts —When the cold violet solution of chromic sulphate is boiled, there is produced a green solution which contains a considerable quantity of hydrogen ions, evidently hydrolysis has taken place, with the formation of soluble basic sulphates, probably of a complex, or even polymeric character In such modified solutions, the sulphate is only partially ionised, since precipitation with barium chloride yields only a proportion of the anticipated quantity of barium sulphate It is impossible to assign definite formula to such hydrolytic products, of which the composition is doubtless more complex than $[Cr_{40}(SO_4)_4]SO_4$ or $[Cr_4(H_2O)_n(OH)_2(SO_4)_4]SO_4$ as suggested by Recoura and others [2] By keeping at the ordinary

[1] Schrotter, *Pogg Ann,* 1841, 53, 513, Carstanjen, *J pr Chem,* 1867, **102,** 65, Pettersson, *Ber,* 1876, 9, 1559, Meyermgh, *ibid,* 1877, **10,** 1946, Klobb, *Compt rend ,* 1893,**117,** 311, *Ball Soc chim ,* 1893, [3], 9, 663, Sominer, *Zeit anorg Chem ,* 1916, 94, 7O, Ephraim and Wagner, *Ber ,* 1917, **5O,** 1088

[2] Recoura, *Ann Chim Phys,* 1895, [7], 4, 494, Favre and Valson, *Compt* mid, 1872, 74,1023, Whitney, *Zeit physikal Chem,* 1896, **2O,** 40, Dougal, *J Chem Soc,* 1896, 69, 1526, Colson, *Compt rend,* 1905, **140,** 42, 372, 1451, **141,** 119, 331, 1024, 1906, **142,** 402, 1907, **144,** 79, 2O6, 325, 637, **145,** 25O, *Bull Soc chim,* 1907 [4], 1, 438, 889, 1908, [4], 3, 90, *Ann Chim Phys* 1907, [8], **12,** 433 See also Meunier and Caste, *Compt rend ,* 1921, **172,** 1488,

temperature, these green solutions are gradually converted into the ordinary violet solutions The double salts, such as chrome alum, uncrergo an analogous reaction when the solutions are heated

Green Modifications of Chromic Sulphate — In addition to the above complex basic sulphate, a solid green salt of the same empirical formula as the normal violet salt is known, which, however, possesses entirely different properties [x] This is obtained by heating the crystals of the violet salt, $Cr_2(SO_4)_3,18H_2O$,[2] at 90° until they have the composition $Cr_2(SO_4)_3,6H_2O$ [3] The resulting green compound is readily soluble in water, but the freshly prepared solution shows the ordinary reactions neither of a chromium salt nor of a sulphate, further, it is capable of "masking" the sulphate-ion of other sulphates to a considerable extent[4] In the course of a few days the solution is gradually transformed into that of the normal violet sulphate In dry air, the green sulphate yields $Cr_2(SO_4)_3,3H_2O$, and becomes anhydrous at 40O° According to Werner's views, green chromic sulphate hexahydrate is formulated, $[Cr_2(SO_4)_3(H_2O)_6]$, whereas the corresponding violet compound is formulated

$$[Cr_2(H_2O)_{12}](SO_4)_3,xH_2O$$

It would be anticipated that intermediate salts of the form $[Cr_2(H_2O)(SO_4)_2](SO_4)$,aq and $[Cr_2(H_2O)_2SO_4](SO_4)_2$,aq, in which respectively one-third and two-thirds of the sulphate are precipitable by barium chloride would be found to exist Colson's observation[5] that such salts may be prepared does not, however, appear to have received definite confirmation Recoura[6] has reported the existence of a lilac-grey sulphate which appears to consist of 1 mol of the green salt and 2 mols of the normal violet salt At first, the sulphate ions corresponding to the green sulphate are masked, whilst those corresponding to the violet salt are precipitable, on keeping, however, the latter sulphate ions also become masked In explanation, the polymerisation of the green salt is put forward

[1] Recoura, *Ann Chim Phys*, 1895, [7], 4, 5O5 See also Cabrera and Marquina, *Anal Fis Quim*, 1917, **15,** 199, Shibata and Matsuno, *J Coll Sci Tokyo*, 192O, **41,** 6, 1

[2] But see Senechal, *Compt rend* , 1913, **156,** 552

[3] Wyrouboff, *Bull Soc chim*, 1902, 27, 676, Colson, *Compt rend*, 1907,**144,** 206, Kling, Florentin, and Huchet, *ibid*, 1914, **159,** 6O, Senechal, *ibid*, 1914, **159,** 243

[4] Recoura, *Compt rend*,, 1922, **174,** 146O [5] Colson, loc *cit*

[5] Itecoura, *Compt rend*, 192O,**17O,** 1494 See also *ibid*, 1919,**169,** 1163

Although acid chromic sulphates are known,[1] Eecoura has shown[2] that when the green sulphate combines with one, two, or three molecules of sulphuric acid or a sulphate, substances are obtained from which no barium sulphate can be obtained by precipitation in the cold, neither are chromium ions present, these may be regarded as the complex acids, *chromosuiphunc acid,* $[Cr_2(SO_4)_4]H_2$, *chromodisulphunc acid,* $[Cr_2(SO_4)_5]H_4$, and *chromotrisulphuric acid,* $[Cr_2(SO_4)_6]H_6$, or their salts These are stable in dry air, but in solution they gradually undergo conversion into the normal chromium salts The alkali chromosulphates are isomeric with the chrome alums, from which they may be readily obtained by heating the crystals of the latter for some time at 90° *Potassium chromosulphate,* $[Cr_2(SO_4)_4]K_2,4H_2O$, is thus obtained as a green salt which dissolves slowly but completely in cold water

The colloidal character of the chromosulphunc acids has been demonstrated by Strong[2]

An analogous series of acids has been prepared by the union of the green chromic sulphate with chromic acid These have the compositions $[Cr_2(SO_4)_3,CrO_4]H_2$, $[Cr_2(SO_4)_3,(CrO_4)_2]H_4$, and $[Cr_2(SO_4)_3,(CrO_4)_3]H_6$, and are called the *chromosulphochromic acids*[3]

Various complex *chrorniselenates* have also been prepared[4]

CHROMIUM AND NITROGEN, PHOSPHORUS, AND BORON

480 *Chromium Nitride,* CrN, is formed by the direct umon of its elements at a red heat,[5] and also by passing ammoma over heated chromic chloride It is a brownish-black powder, which takes fire and burns when heated to 200° in the air or in oxygen Cold chlorine does not act upon it, but when heated in this gas small explosions first occur owing to formation of nitrogen chloride, and finally chromic chloride remains It does not undergo change on ignition in hydrogen or in aqueous vapour, and is not attacked

[1] Wemland and Krebs, *Zeit anorg Chem* , 1906, 49, 157

[2] Strong, *Compt rend,* 1910, **150,** 1172 These compounds, particularly those composed of 1 mol of $Cr_2(SO_4)_8$ with 4, 5, and 6 mols of H_2SO_4, can therefore no longer be regarded as compounds of the type called " sulphochromio hydioxide " by Recoura, *loc cit,* See also Calvert and Ewan, *Proc Chem Soc,* 1896, **12,** 160

[3] Recoura, *Bull Soc chim,* 1897, [3], 17, 934, *Ann Chim Phys,* 1895, [7], 4, 494

[4] Meyer, *Zeit anorg Chem,* 1921, **118,** 1

[5] Bnegheb and Geuther, *Annalen,* 1862, **123,** 239

by potassium hydroxide, hydrochloric acid, or nitric acid Concentrated sulphuric acid converts it into the sulphates of ammonium and chromium

$$2CrN + 4H_2SO_4 - Cr_2(SO_4)_3 + (NH_4)_2SO_4$$

Chromic Azide, $Cr(N_3)_3$, has been obtained 1 as well as its pyridine compound, $Cr(N_3)_3,3Py$, which is explosive, and the compound $CrN_9,3NaN_3$ Basic salts are known

Chromic Nitrate, $Cr(NO_3)_3,9H_2O$, is obtained by dissolving the hydroxide in nitric acid, it crystallises in oblique, purple-red prisms The solution, like that of the sulphate, turns green on boiling, and on evaporation dries to a green, amorphous mass The green solution iminediately becomes violet on cooling

Chromium Phosphides—By heating finely divided chromium with red phosphorus in a sealed tube, the phosphide, Cr_2P_3, is obtained, when this compound is heated in hydrogen, chromic phosphide, CrP, is produced [2] Both are grey substances which are insoluble in acids

Chromic Hypophosphite, $Cr(H_2PO_2)_3,2H_2O$, is a green mass obtained by dissolving freshly prepared chromic hydroxide in hypophosphorous acid [3]

Chromic Phosphates—When a solution of sodium hydrogen phosphate is added to an excess of chrome alum solution a gelatinous precipitate is formed which on keeping for forty-eight hours is transformed into dark violet crystals of the phosphate,[4] $CrPO_4,6H_2O$, more prolonged contact with the precipitant yields a green, amorphous tetrahydrate By boiling the violet salt with water, the tetrahydrate is obtained in crystalline form, whereas treatment with acetic anhydride yields a dihydrate On ignition of a hydrate, the anhydrous salt is obtained as a brown, amorphous powder If chromic hydroxide is dissolved in excess of phosphoric acid and the solution evaporated and heated to 316°, *chromic metaphosphate,* $Cr(PO_3)_3$, is obtained, which has been employed as a green pigment *Chromic pyrophosphate* in alkaline solution gradually yields salts of the type $M'(CrP_2O_7),wH_2O$ *{chromi-pyrophosphates)* [5]

[1] **Ohven Mandate, *Gazz,* 1919, 49, u, 43, 1922, 52, l, 112, Wohler and Martin, *Ber* , 1917,5O, 595**

[2] **Dieckmann andHanf, *Zeit anorg Chem* , 1914,86, 291 See also Granger, *Compt rend,* 1897,124, 190, Maronneau, *ibid,* 190O, 13O, 656**

[3] **Mawrow and Zonew, *Zeit anorg Chem* , 1915, 93, 311**

[4] **Schiff, *Zeit anorg Chem,* 1905,43,3O4, Joseph and Rae, *Trans Chem Soc* , 1917, 111, 196**

[6] **Rosenheim and Tnantaphylhdes, *Ber* , 1915, 48, 582**

Chromium Arsenides —The compounds Cr_2As_3 and CrAs have been prepared similarly to the phosphides [1] An *arsemte, arsenates,* and a *metanttinonate* have been described

Chromium Borides —Two chromium bondes have been prepared by heating the elements together in the electric furnace,[2] these have the formulae CrB, and Cr_3B_2, and are grey, crystalline substances

CHROMIUM AND CARBON AND SILICON

481 *Chromium Carbides*—These fall into two groups [3] (1) those containing up to 8 5 per cent C, and (2) those containing a larger proportion of carbon The former are completely soluble in hot 24 per cent hydrochloric acid, the latter only partially The carbide Cr_5C_2 forms silvery crystals of density 6 9 It melts at 1665° and is unattacked by aqua regia The carbide Cr_3C_2 is darker in colour, has a density 6 68, and melts at about 1890° with partial decomposition to Cr_4C_2 and graphite Moissan[4] has described carbides of the composition Cr_2C_3 and Cr_4C respectively

Chromium Carbonate—Chromic hydroxide absorbs carbon dioxide from air, yielding a compound to which the formula

has been given [5]

Cyanogen Compounds of Chromium —Chromous cyanide is unstable in air *Potassium chromocyanide,* $K_4[Cr(CN)_6],2H_2O$, is obtained by the action of potassium cyamde on chromous acetate, and forms blue crystals It is soluble in water, and on exposure to air passes into

Potassium Chromicyamde or *Potassium Hexa-cyano-chromite,* $K_3[Cr(CN)_6]$, light yellow, monoclmic crystals, obtained also by pouring a solution of chromic acetate into a boiling solution of potassium cyamde

A number of chromicyamdes of other metals have also been prepared [6]

[1] Dieckmann and Hanf, *Zeit anorg Chem* , 1914, 86, 291

[2] Tucker and Moody, *Journ Chem Soc* , 1902, **81,** 16, Binet du Jassonneix, *Compt rend* , 1906, **143,** 897, Wedekind and Fetzer, *Ber* , 1907, **40,** 297

[3] Ruff and Foehr, *Zeit anorg Chem,* 1918,**104,** 27

[4] Moissan, *Compt rend,* 1894,**119,** 185

[5] Jovitschitsch, *Compt rend,* 1914,**168,** 872, *Helv Chim Acta,* 192O, 3, 46

[6] Fischer and Benzian, *Chem Zeit,* 1902, 26, 49, Cruser and Mdler, *J Amer Chem Soc,* 1906,28, 1132

Chromic Thocyanate, $Cr(SCN)_3$ —Chromic hydroxide dissolves in thiocyanic acid solution yielding a greenish-violet solution which when concentrated over sulphuric acid dries to a dark-green amorpl|Ous, deliquescent mass It forms a series of characteristic double salts, which are regarded as salts of complex acid radicles containing chromium [1] The complex ions present in such solutions are [2] $[Craq_6]^{+++}$, $[Craq_5(CNS)]^{++}$, $[Or\,aq_4(CNS)_2]^{+}$, $[Cr\,aq_3(CNS)_3]$ (non-electrolyte), $[Cr\,aq_2(CNS)_4]$-, $[Cr\,aq(CNS)_5]$" ~, and $[Cr(CNS)_6]$ Of particular importance is the potassium salt of the last-mentioned ion

Potassium Chromithwcyanate or *Potassium [Hexathocyano-chromite,* $K_3[Cr(SCN)_6],4H_2O$, is formed by heating a moderately concentrated solution of 6 parts of potassium thiocyanate and 5 parts of chrome alum for two hours at the boiling point, the sulphates formed are precipitated by the addition of alcohol, the filtrate evaporated, and the residues recrystalhsed from alcohol It forms tetragonal, almost black crystals, which appear ruby-red by transmitted light, and dissolve very readily in water and alcohol, forming wine-red solutions It is decomposed by alkalis and warm hydrochloric acid The solution gives precipitates of analogous compounds with lead and silver salts [3]

Chromium and Silicon—Several silicides of chromium have been described, these are all prepared by heating chromium Tuth silicon, or a mixture of silica and chromic acid with carbon or copper and aluminium in the electric furnace In this way tho compounds Si_2Cr, Si_2Cr_{3j} $SiCr_2$, and $SiCr_3$ have been obtained [4] The compound, Si_2Cr_3, is also formed when silicon chloride is heated for some time in contact with chromium [5]

Chromium and Tungsten —Chromic tungstates and derivatives of tungsto-chromic acid are known [6]

[1] Rosier, *Annalen,* 1867,141, 185

[2] Bjerruni, *Det K Danske Vidensk Selskabs Skrifter, Nat Math,* 1915, 7, 66, *Zeit anorg Chem,* 1921,118,131, 119, 39, 54, 179, see also Bohart, *J Physical Chem,* 1915, 19, 537, Scagharini, *Atti R Accad Lincei,* 1918, [5], 27, |, 442

[3] Rosier, *Annalen,* 1867, 141, 185, Rosenheim and Cohn, *Zeit anorg Chem,* 1901,27,293

[4] Moissan, *Compt rend,* 1895, 121, 621, de Chalmot, *Amer Chem J,* 1897, *19,* 69, Zettel, *Compt rend,* 1898,126, 833, Lebeauand Figueras, *ibid,* 1903, 136,1329

[5] Vigouroux, *Compt rend,* 1907,144, 83

[6] See Kantschev, *J Buss Phys Chem Soc,* 1914, 46, 729

AMMONIACAL AND OTHER COMPLEX COMPOUNDS OF CHROMIUM.

482 The salts of chromium readily combine with ammonia or substituted ammonias to form complex salts These contain, for each atom of chromium, up to six molecules of ammonia, and often other elements or groups of elements united with the metdl to form a complex radicle, which usually acts like a urn-, bi-, or ter-valent metal, but may in other cases have an acid function, or be neutral, that is, the complex is not lomsed in aqueous solution These complex salts are capable of undergong numerous double decompositions, giving rise to a large number of derivatives, among which many cases of isomerism occur Analogous compounds are formed by other metals, in particular, cobalt and the metals of the platinum group, and these are to be regarded as included in the general statement which follows

These compounds do not give the ordinary reactions of the metal, and in many cases this is also true of some or all of the acid radicles which they contain This is accounted for, as already explained (pp 37-38) by supposing that, in these latter cases, the acid radicle forms part of the complex group containing the metal, whereas those acid radicles which give the ordinary reactions are not contained in this group

The constitution of these complex radicles is still under discussion, two different views being held According to one of these (Blomstrand, Jorgensen) the metal retains its characteristic valency in all the compounds, the molecules of ammonia being attached to the metal in open chains by virtue of the pentavalent character of nitrogen That portion of the acid radicles which does not retain its ordinary properties is directly connected with the metal, whilst the other portion is combined with nitrogen Water may take the place of one or more of the ammoma groups, the oxygen atom being supposed to be quadrivalent The compound $Cr(NH_3)_5Cl_3$, in which only two of the chlorine atoms are precipitable by silver mtrate in aqueous solution, would thus receive such a constitutional formula as

$$\begin{array}{c} \\ \text{Cl NH}_3\text{ NH}_3\text{ NH}_3\text{—Cr—NH}_3\text{ NH}_3\text{ Cl} \end{array} \qquad \begin{array}{c} \text{Cl} \\ \\ \end{array}$$

The existence of isomerides may be readily expressed by a variation in the arrangement of the various groups

The second and more satisfactory view is that proposed by

Werner,[1] who classifies these compounds on the theory of principal and supplementary valency, an account of which has already been given (p 37) The theory has naturally undergone modification income details as experimental evidence has accumulated According to this theory, in the compound $[Cr(NH_3)_6]Cl_3$, for example, the ammoma groups are all united or *co-ordinated* with the chromium atom by means of its supplementary valencies, whilst the chlorine, according to Werner's more recent view, is combined with the complex radicle as a whole, without being attached to any particular atom in it, and is said to be in *indirect combination* with this radicle The ammonia groups ttaay be either partially or entirely replaced by acid groups such as CI, NO_2, SON, etc , yielding a large number of compounds, which usually contain six groups in the complex radicle, although in some cases only four such groups can be present The valency of the complex radicle is easily ascertained from the number and character of the groups withm it If the number of umvalent acid radicles be less than the principal valency of the atom of the metal, the complex radicle is basic and capable of combining with a number of acid radicles equal to the difference If, however, it be greater, the complex radicle has an acid character and is capable of combining with univalent basic radicles equal in number over the principal valency of the metal When the number in the complex radicle is equal to the principal valency of the metal, the compound is a neutral substance

This is illustrated in the following series of compounds derived from tervalent chromium, X representing a univalent acid and E a univalent basic radicle

$[Cr(NH_3)_6]X_3$ $[Cr(NH_3)_3(SCN)_3]$
$[Cr(NH_3)_5(SCN)])X_2$ $[Cr(NH_3)_2(SCN)_4]$ R
$[Cr(NH_3)_4(SCN)_2]$ X $[Cr(NH_3)(SCN)_5]R_2$ (unknown)
$[Cr(SCN)_6]R_3$

As already explained, the electrolytic dissociation and the reactions of these compounds in solution correspond with these formulae

[1] *Annalen,* 1902, 322, 261, *Neuere Anschauungen auf dem Oebiete der anorganischen Chemie* (Vieweg & Sohn, *Braunschweig,* 192O) See also *Ber ,* 1907, **40,** 15, where an account of the literature on the subject is given Recent investigations on the subject are described in papers by Jovitschitsch, *Monatsh ,* 1913,34,225, Dubsky, *J pr Chem ,* 1914, [2], 90, 61, Werner and others, *Annalen,* 1914, **406,** 212, **406,** 261, Mandal, *Ber,* 1916, 49, 13O7, Briggs, *Journ Chem Soc ,* 1919,**115,** 67, Mandal, *Ber ,* 1919, 52, [B], 33O, 489,Frowein, *Zeit anorg Chem ,* 192O, **110,** 107

In many cases, hydrated compounds of chromium may be formulated in a similar manner, instances have already been quoted in the cases of chromous chloride, chromic chloride, and chromic sulphate, Werner's formulation is in agreement with the behaviour of these substances in solution, when the whole or part only of the chloride or sulphate radicles is lomsed Examples may also be quoted of cases in which the ammoma groups in the complex radicle are only partially replaced by the " aquo " group, (OH_2), thus

$$[Cr(NH_3)_e]Cl_3, \quad [Cr(OH_2)(NH_3)JCl_3, \text{ etc } \quad [Cr(OH_2)_6]Cl_3$$

The bluish-violet chromic chloride hexahydrate is, of course, the final stage in such a substitution

Compounds are also known, derived from the bivalent atom of the metal, in which the complex radicle contains six umvalent acid groups^ and is therefore capable of umting with four basic radicles, examples being potassium chromocyanide, $[Cr"(CN)_6]K_4$, and potassium ferrocyanide, $[Fe"(CN)_6]K_4$

The ammonia compounds are known as the *arnmines,* this spelling of the word being adopted to avoid confusion with the organic *amines,* which have an entirely different constitution The nomenclature of these compounds was originally founded on the colours characteristic of the various compounds, terms such as roseo-, praseo-, luteo-, croceo-, fusco-, xantho-, etc , having been employed A much more rational method is due to Werner, the principle of which is that the names of the various groups contained within the complex radicle precede that of the metal, whereas those of the external group follow it, this being nothing more than an adaptation of the nomenclature frequently employed for organic compounds

Thus the well-known cobalt compound, $[Cl(NH_3)_5Co]Cl_2$, formerly known as purpureocobaltic chloride, receives the name chloro-pentammine-cobaltic dichloride, whilst the compound $[(OH_2)(NH_3)_5Co]Cl_3$ (roseocobaltic chloride) becomes aquo-pentammine-cobaltic trichloride *

[1] Some of the metals from more than one series of complex derivatives, corresponding to the different series of simple salts In order to distinguish these compounds, a special nomenclature has been introduced by Werner *(Neuere Anschauungen,* 192O, p 92), according to which the valency of the metal is designated by the letters a , o , 1 , e , an , on , in , en , for uni , bi , ter , quadri , quinque , sexa , septa , and octa valent elements respectively Thus among the complex halogen derivatives of the platinum metals, the compound $K_2[PtCl_4]$ is known as potassium tetrachloroplatinoate, $K_3[RhCl_6]$

Only a few examples of the chromium ammines are here described[1] Amongst salts containing the chromium complex as the *anion* are

6-(HSka)ammtrio-chromium salts, $[Cr(NH_3)_6]X^I_3$ (luteo-salts), which are prepared by addition of ammonium chloride and ammonia to a solution of chromous chloride and allowing the cold mixtures to oxidise slowly[2] Other members of this group are the ammino-aquo-chromium salts, in which some of the (NH_3) groups are replaced by (OH_2) groups 5-Ammmo-l-aquo (or aquopentammine)-chrommm salts, formerly called roseo-salts, are included

l-Actdo-5'ammino-chromium salts, eg, $[CrCl(NH_3)_5]Cl_2$ (pur-pureo-salts) This compound is obtained, together with its mono-aquo-substitution derivative, $[Cr(OH_2)Cl(NH_3)_4]Cl_2$, by the action of liquid ammoma on violet chromic chloride This group includes thiocyano-, nitrito-, nitrato-, etc , salts

2-AcidoA~amrnino-chromium salts, e g , $[CrCl_2\,en_2]Cl$,[3] obtainable in several different ways

3-Acido-3-ammino-chromium compounds, *e g,* $[CrCl_3(NH_3)_3]$, are not lomsed in aqueous solution The compound given as an example of this class may be prepared by adding the compound $CrO_4\,3NH_3$ (see p 1073) to cooled concentrated hydrochloric acid, filtering from a bluish-green precipitate, keeping the filtrate for two days, and separating the greenish-blue precipitate

Compounds containing the chromium complex as the *kation*

4-Acido-2-ammino-chromites, e g , $[Cr(SCN)_4(NH_3)_2]R'$ —When finely divided potassium dichromate is added to fused ammonium thiocyanate, ammoma is evolved, and the whole mass solidifies When this is treated with water, filtered, and a few lumps of

as potassium hexachlororhochate and $K_2[PtCl_6]$ as potassium hexachloro platineate This system has been adopted to some extent in Germany, but has not come into general use in England The neutral compounds are named as in the following examples $[Co(NO_2)_3(NH_3)_3]$, tnnitrotetramminocobalt, $[PtCl_2(NH_3)_2]$, dichlorodiamminoplatinum

[1] For a full account of the compounds which have so far been prepared, reference must be had to Werner, *Neuere Anschauungen,* 192O, Abegg's " Handbuch der anorganischen Chemie, Vol IV, (1), 2nd half, the literature quoted on page 1088, and the following papers Weinland and Reihlen, *Zeit anorg Chem,* 1913, 82, 426, *Ber,* 1913, 46, 3144, Weinland and Ensgraber, *Zeit anwg Chem,* 1913, 84, 368, Barbieri, *Atti R Accad Lincei,* 1915, [5], 24, i, 916, Weinland and Spanagel, *Ber,* 1916, 49, 10O3

[2] Jorgensen, *J pr Chem* , 1884, [2], 30, 1

[3] The symbol "en" is used for the ethylenediamine group, $NH_2\,CH_2\,CH_2\,NH_2$, corresponding to two ammonia groups

ammonium chloride are added, garnet-red scales of the salt $[Cr(SCN)_4(NH_3)_2]NH_4$ separate

b-Acido-\-ammino-chromites are unknown

6-Acido chromites, $M'_3[CrX_6]$, no longer " ammines " since they contain no ammonia groups, include such compounds as the chromicyanides, chromioxalates, chromisulphates, etc

A number of compounds have been described which contain organic amines, particularly ethylenediamine, and compounds such as pyridine, in the complex radicle in place of ammonia

Isomerism of Complex Chromium Compounds

A number of different types of isomerism[x] are known to which the complex chromium compounds are subject It will be possible to mention each of these only very briefly

1 *Polymerism*—Certain complexes may be regarded as polymers of simpler ones, although widely different in constitution Thus there are seven distinct compounds which possess the composition $Cr(NH_3)_3(SCN)_3$ or some multiple thereof

2 *Co-ordination isomerism* —Compounds with the same molecular formula may possess entirely different structural formulae from the point of view of their lonisation and co-ordination relationships, *e g,*

$$[Co(NH,),]^{ra}\ [Cr(CN)_6]^{ra} \text{ and } [Cr(NH_3)_6]^{m}\ [Co(CN)_6]^{ra},$$
$$[Cr(NH_3)_6]\ [Cr(C_2O_4)_3] \text{ and } [Cr(NH_3)_4(C_2O_4)]\ [Cr(C_2O_4)_2(NH_3)_2]$$

3 *Hydrate isomerism,* as exhibited and already described in the case of chromic chloride, of which three isomeric forms exist, namely, $[Cr(OH_2)_6]Cl_3$ (violet), $[CrCl(OH_2)_5]Cl_2,H_2O$ (light green), and $^{\wedge}CrCl_2(OH_2)_4]Cl,2H_2O$ (dark green)

4 *lonisation metamerism,* when different ions are furmshed in aqueous solution, *e g,* the sulphate, $[Co(NO_3)(NH_3)_5]SO_4$, and the nitrate, $[Co(SO_4)(NH_3)_6]NO_3$

5 *Salt isomerism* in which the differences exhibited are those between the salts of tautomeric acids, *e g,* nitrito- (O N O) and

nitro- *(* N < 1 groups

6 *Structural isomensm, eg,* $[(NH_2)_2CS]_2\ Co(SCN)_2$ and $(NH_4SCN)_2\ Co(SCN)_2$, in which case the distinction is that between the thiocarbimido- and thicyano-groups

[1] **This subject is discussed at some length in Werner's "** ***Neuere Anschauungen"*** **192O, p 327** ***et seq***

7 *Co-ordmative position isomerism, e g ,*

$$[ci(NH3)3Co<Q^{H}5>Co(NH_3)3Clla_2 \text{ and}$$

$(NH_3)_4CO/Q^{H}\wedge>CO(NH_3)_2C1_2]C1_2$ A similar difference exists between syminetrical and unsyminetncal dichloroethane, $CH_2C1\,CH_2C1$ and CH_3CHC1_2

8 *Geometrical isomerism*—As an example, complex radicles of the type $[MR_4X_2]$ may be cited The metal atom is regarded as situated at the centre of a regular octahedron the corners of which are occupied by the co-ordinated groups Two isomerides are then possible—the syminetrical or *trans-foxm* in which the groups X, X, are situated at opposite ends of a diagonal of the figure, and the asyminetrical or m-form, in which they are at adjacent corners, thus

cis-Forin Asyminetric *trans-T? ovm* Syminetric

Of the same class are the platinous complexes, *e g ,*

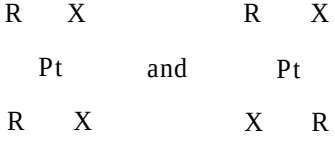

9 *Optical isomerism*—There is no difference between the configuration of a *trans-form* and its mirror-image, but in the case of a *cis-ioim* it is possible to obtain two distinct configurations which are not identical, but bear to one another the relationship of mirror-images, thus [x]

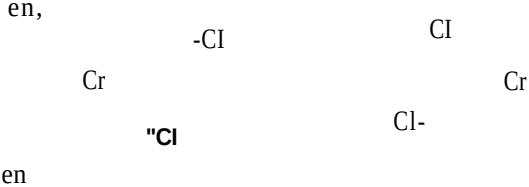

[1] **The symbol " en " is used for ethylenediamine, $NH_2CH_2CH_2NH_a$, which corresponds to two ammonia groups**

10. *Valency isomerism, e g ,*

$$Cr[(NH_3)_6]X_3 \qquad Cr[(NH_3)_6]X_2$$
$$V)H \quad \text{and} \quad \wedge>O—\bullet HX$$
$$Cr[(NH_3)_5]X_2 \qquad Cr[(NH_3)_5]X_2$$

where certain of the molecular components may be linked to a central atom by either of the two types of valency (principal or auxiliary)

DETECTION AND ESTIMATION OP CHROMIUM

483 *Chromous salts* in solution are unstable, readily becoming converted to green chromic salts with evolution of hydrogen, the solutions are therefore strong reducing agents *Chromic salts* and the corresponding *sesqmoxide* have a characteristic green or violet colour, with borax or microcosmic salt, both in oxidising and reducing flames, an emerald-green bead is produced In aqueous solution, ammonia * gives a gelatinous precipitate of the hydroxide, $Cr(OH)_3$, which partially dissolves in excess of ammonia, yielding a violet solution which contains complex ammines, complete precipitation of the hydroxide is, however, attained from boiling solutions By substitution of sodium or potassium hydroxide for ammonia, a solution of the chromic hydroxide, at first precipitated, in excess of the alkali is obtained, this is regarded both as a solution of a chromite and as a colloidal solution On boiling, almost complete precipitation takes place

$$Cr(OH)_3 + KOH ** 2H_2O + CrO(OK)$$

Oxidation of green chromic salts to chromates having a characteristic yellow colour is readily effected For qualitative purposes, it is sufficient to boil a solution of the salt with excess of sodium peroxide, sodium hypochlorite, or with nitric acid and lead dioxide,[2] but oxidation by fusion with a mixture of sodium carbonate and sodium peroxide convemently admits of quantitative application

The chromium salts do not impart any colour to the non-luminous gas flame The spark spectrum of the metal is a complicated one, the brightest lines being 5208 8, 5207 4, 5204 7 in the green, and 4289 9, 4275 O, 4254 5 in the dark blue [3]

[1] **Ammonium sulphide, or a mixture of potassium iodide and potassium lodate, may also be employed**

[2] **Term, *Gazz* , 1913, 43,11,63 See also Browning, *J Amer Chem Soc* , 1921, 43, 114**

[3] **The infra red spectrum has been examined by Randall and Barker, *Astrophys J* , 1919, 49, 54, and the *X* ray spectrum by Fricke, *Physical Rev*, 192O,16, 2O2**

Chromates—If, after fusion of a chromic compound with sodium carbonate and sodium peroxide or potassium mtrate the melt is dissolved in water, the whole of the chromium is present, in solution such a solution darkens in colour owing to production of the dichromate, $Na_2Cr_2O_7$ The reverse reaction, of course, takes place when alkali is added to solutions of dichromates From solutions of soluble chromates, barium chloride and lead mtrate precipitate the respective chromates which are yellow in colour, mercurous mtrate yields brown, amorphous, mercurous chromate which on boiling is converted into a red, crystalline form, some basic chromate also being produced With normal chromates silver mtrate yields a brick-red precipitate, Ag_2CrO_4, whereas cold concentrated solutions of dichromates yield $Ag_2Cr_2O_7$, which is darker in colour In presence of hydrogen sulphide, sulphurous acid, alcohol,[1] etc , chromates suffer reduction to green chromic salts, whilst in presence of hydrogen peroxide they are oxidised to perchromates The latter reaction is very sensitive when carried out in dilute solutions in presence of sulphuric acid, blue perchromic acid being formed, although unstable in aqueous solution, the blue compound may be extracted with ether, in which it somewhat less rapidly decomposes Another characteristic reaction of the chromates consists in the formation of red vapours of chromyl chloride, condensing to a red liquid, when a chromate is heated with a chloride and concentrated sulphuric acid An intense blue coloration is, moreover, produced by a-naphthylamine in presence of tartaric acid[2]

Estimation of Chromium—Chromium may be estimated gravimetncally—m the case of the chromic salts as chromic oxide, and in the case of the chromates as mercurous chromate—or volumetncally by taking advantage of the oxidising action of chromates on ferrous salts, potassium iodide, etc In view of the ease with which chromic salts are converted into chromates and *vice versa,* the choice of the method suitable in any particular case is of the widest

In order to estimate chromium gravimetncally in the chromic salts, a hot solution is precipitated with a very small excess of ammonia,[3] the solution boiled till the free ammoma is nearly

[1] **For the photochemistry of this reaction, see Plotnikow, *Zeit wiss Photochem* , 1919,19, 40**

[2] **Van Eck, *Chem Weekblad,* 1915, 12, 6**

[3] **The addition of 2 c c of 2½ per cent tannic acid solution to the liquid before the addition of the ammonia greatly facilitates the subsequent filtration**

all expelled, and the precipitate well washed with hot water, dried, ignited in a platinum crucible,[1] and weighed Calcium and magnesium salts, if present, take part in the reaction with formation of insoluble chromites, but it has recently been stated [2] that these elements may be removed by washing the precipitate with a boiling 5 per cent solution of ammonium nitrate

In the chromates, the gravimetric estimation of chromium is usually carried out by addition of mercurous mtrate to a solution made slightly acid with nitric acid, and boiling the mixture The red, crystalline precipitate of mercurous chromate so obtained yields on ignition a residue of chromic oxide Methods depending on the precipitation and weighing (as such) of silver, barium, and lead chromates have also been employed

Soluble chromates may be estimated volumetncally by direct titration with ferrous salts, using potassium femcyanide as an external indicator, or by an lodometnc method,

$$K_2Cr_2O_7 + 6KI + 14HC1 = 8KC1 + 2CrCl_3 + 7H_2O + 3I_2,$$

the liberated iodine being titrated in the usual way with sodium tluosulphate solution The valuation of chrome iron ore is commonly carried out by this method, the mineral being previously fused with an alkali and an oxidising agent, in order to convert the chromium into a soluble chromate

It is possible to differentiate between chromate and dichromate when present together in solution by an acidimetnc method [3]

Atomic Weight of Chromium—The older atomic weight determinations gave varying results, owing to the inexact methods and impure material employed Berlin[4] obtained the number 52 5 by the analysis of silver chromate, whilst Kessler obtained 52 3 from the determination of the equivalent quantities of potassium dichromate and potassium chlorate required to oxidise arsenious oxide to pentoxide[5] Siewert[6] found 52 O7 by the analysis of violet chromic chloride and of silver dichromate, and Baubigny [7] got 52 14 by the conversion of chromic sulphate into the trioxide Eawson,[8] by the conver-

[1] Rothang, *Zeit anorg Chem*, 1913, 84, 165, Schwarz, *Helv Chim Acta*, 192O, 3, 33O It is necessary to avoid formation, not only of complex ammines, but also of chromic chromate

[2] Toporescu, *Compt rend* ,1921,**172,** 6OO

[3] Sacher, *Farbenzeit*, 1916, **22,** 213

[4] *Annalen*, 1844, 56, 2O7, 1845, 6O, 182

[5] *Pogg Ann* , 1861,**113,** 137

[6] *Zeit ges Naturwiss* , **1861,17,** 53O

[7] *Compt rend* , 1884, 98, 146

[8] *Journ Chem Soc* , **1889,** 66, **213**

sion of pure ammonium dichromate into chromium trioxide, found the value 52 15, and Memeke[1] obtained the average figure 5512 by estimating (1) the quantity of silver and chromium in silver chro of oxygen in these two compounds, (3) the quantity of oxygen in potassiun of chromium in ammonium dichromate More recently, Baxter and others,[2] by reducing silver chromate or dichromate with sulphurous acid or hydrazine sulphate, and then precipitating the silver as chloride or bromide, have found 52 O1 + O O1 for the atomic weight of chromium The value now (1922) adopted is 52 O

M O L Y B D E N U M Mo = 96 o At No 42

484 The name *Molybdcena,* which occurs in the writings of Dioscorides and Pliny, is derived from the Greek word /£oAu/38o9, lead, and was originally employed for the designation of a variety of substances containing lead At a later time the name was used to sigmfy galena or substances similar in appearance to this body, and to these the name of plumbago or black lead was also given Even antimony sulphide and pyrolusite, to which latter mineral Linnaeus gave the name *molybdcenum magnesn,* were also classed among the same group of bodies At a still later period this word was applied solely to graphite and to the mineral sulphide of molybdenum, which are very similar in appearance

The difference between plumbago and the sulphide of molybdenum was first pointed out by Scheele in his treatise on " Molybdaena " in 1778, and in another on " Plumbago" in 1779 By heating the former mineral with nitric acid he obtained sulphuric acid, together with a peculiar white earth which he recognised as an acid-forming oxide, and termed *acidum moh/b-dcence,* and he assumed that the mineral was a compound of this acid with sulphur In 1781 Bergman suggested that the earth was probably a calx of a metal, and in 1782 he wrote that H]elm had succeeded in preparmg the metal, though the details of the experiments were first known in 1790

Another mineral containing molybdenum is the yellow molyb-date of lead or wulfenite first found in Carmthia This was investigated by the elder Jacqum, and he showed that it contained

[1] *Annalen,* **1891, 261, 339** [2] *J Amer Chem Soc ,* **1909, 31, 529, 541**
[3] *Vetensk Acad Hand I*

lead, but was doubtful as to the nature of the acid with which this metal was combined Salzwedel, who analysed it in 1790, believed that it was a lead tungstate, but Klaproth in 1797 ascertained its true composition Later Berzelms more closely examined the molybdenum compounds

Molybdenum is usually found as molybdemte, MoS_2, which occurs chiefly in Queensland and the Umted States, also as wulfemte, $PbMoO_4$ It occurs more rarely as molybdic ochre, which was for a long time believed to be molybdenum trioxide, MoO_3 Schaller,[1] however, from the analysis of a pure sample from Westinorland, New Hampshire, has shown it to be a hydrated ferric molybdate, $Fe_2O_3,3MoO_3,7JH_2O$ Iron ores frequently contain traces of molybdenum, and hence this metal is also found in pig-iron as well as in the slag Thus the iron slag obtained in the process of melting the cupreous schist at Mansfield is said to contain from 9 to 28 per cent of molybdenum [2] Chillagite[3]- has the composition $PbOWO_3,PbOMoO_3$ and powelhte, $CaMoO_4$, in which a portion of the molybdenum is usually replaced by tungsten

Metallurgy of Molybdenvm —Metallic molybdenum is obtained either electrically or by the " thermite " process

By the electrical method, molybdemte is heated in a carbon tube with an arc of 35O amperes at 6O volts, when sulphur dioxide is evolved, the current is then increased to 90O amperes at 5O volts, when complete fusion takes place and the sulphur is entnely expelled The metal prepared in this way, however, contains from 5 to 7 per cent of carbon, which may be removed by heating with molybdic oxide Molybdenum melts at 245O° ± 3O°[4]

A metal of 98 to 99 per cent purity, containing some iron and very small quantities of silicon, is obtained by the reduction of molybdic oxide by means of aluminium powder

Molybdenum is chiefly used in the form of rich ferromolybdenum alloys for the manufacture of special steels[5] It also finds employment in the construction of certain electrical apparatus, and, in the form of molybdic acid, is used in analytical laboratories for the estimation of phosphorus

[1] *Amer J Sci* , 1907, [4], 23, 297 [2] Heine, *J pr Chem* , 1836, 9, 177

[3] Ullmann, *J Roy Soc NSW*, 1912, 46, 186, see also Cook, *Amer J Set*, 1922, [5], 4, 5O

[4] Von Pirani and Meyer, *Zed Elektrochem*, 1912, 18, 137, Wolf, *Chem Zentr* , 1918, 1, 6O8, gives the freezing point as 225O°

[5] See Menmcke, *Elektrochem Zeit*, 1913, 2O, 181, 215, 25O, 271, Aitchison, *Journ Chem Soc*, 1915, **107,** 1531

Metallic molybdenum may be obtained on the small scale as a grey powder, which assumes a silver-white appearance under pressuii, by heating the trioxide or one of the chlorides in a current of nydrogen, but is best prepared by heating a mixture of molybdenum dioxide with one-tenth of its weight of sugar charcoal in a carbon crucible in the electric furnace, the action of the arc being stopped before the portions in contact with the crucible have had time to fuse It is thus obtained free from carbon, whereas if too strongly heated it takes up the latter in considerable quantities The pure metal is as malleable as iron, and is not hard enough to scratch glass, has a density [x] of 10 281, and can be forged when hot, it scarcely undergoes oxidation at the ordinary temperature, but is superficially attacked at a dull red heat, and rapidly at 6OO°, molybdenum trioxide subliming It is rapidly attacked by fused potassium chlorate and mtrate It may be distilled in the electric furnace, giving a vapour which solidifies in crystals[2] When coarsely powdeied it is attacked by fluorine at the ordinary temperature, by chlorine at a dull-red, and by bromine at a cherry-red heat, but not by iodine at the softening point of glass When molybdenum filaments are heated in introgen, nitrides are probably formed[3]

The metal is insoluble in dilute acids with the exception of nitric acid, but dissolves in concentrated sulphuric acid, the solution being first blue, but finally becoming colourless with formation of the trioxide, sulphur dioxide being also evolved It is slowly attacked by fused alkalis At high temperatures it is attacked by water vapour with liberation of hydrogen and formation of the dioxide[4] In the potential series, molybdenum falls between Hg^{1} and Sb^{111}

Molybdenum forms amalgams which may be obtained by the electrical method When these amalgams are distilled in *vacuo,* molybdenum is left behind in the pyrophoric state[5]

Although not obtainable by reduction of its compounds, molybdenum in a *colloidal* form has been prepared by an electrical dispersion method[6]

[1] Muller, *J Amer Chem Soc,* 1915, 37, 2O46, but Wolf, *Chem Zentr,* 1918, I, 6O8, gives 8 95

[2] Moissan, *Compt rend,* 1906, **142,** 425

[3] Langmuir, *J Amer Chem, Soc* , 1919, **41,** 167

[4] See Chaudron, *Compt rend,* 192O, **17O,** 182, 1056

[5] Feree, *Compt rend* , 1896, **122,** 733

[6] Svedberg, " Herstellung kolloider Losungen anorgamscher Stoffe " (Dresden, 1909)

MOLYBDENUM COMPOUNDS.

MOLYBDENUM AND OXYGEN

485 Molybdenum combines with oxygen to form

Molybdenum sesquioxide, Mo_2O_3,
Molybdenum dioxide, MoO_2,
Molybdenum trioxide, MoO_3

The first two are basic oxides, but very little is known of their salts other than the halogen derivatives, the complex thiocyanates of the first, and the complex cyamdes of the second The trioxide is the most important, and like the analogous chromium oxide is an acid-f ormmg oxide giving rise to the important series of *molybdates* A blue oxide, which is usually regarded as a combination of the dioxide with the trioxide, is also known, but its composition is not definitely settled, whilst an oxide, Mo_2O_5, and a peroxide have also been described

The compound formerly described as a hydrated monoxide has been shown to be the hydroxide of molybdenum sesquioxide, nor are simple salts of the hypothetical monoxide known, but only polymolecular complexes

Molybdenum Sesquioxide, Mo_2O_3, is stated to be formed as a black substance when one of the higher oxides is treated with sodium amalgam, zinc, etc , but it is doubtful whether the product really has the composition Mo_2O_3 It is also formed by heating the metal in air or water vapour The *hydroxide*, $Mo(OH)_3$, is first obtained as a brownish-black powder by precipitating with ammoma, washing with dilute ammonia, and drying in a current of hydrogen at 10O° When gently lgnited in absence of air, the water evolved causes partial oxidation A black precipitate of this hydroxide is also produced when molybdenum dichloride is boiled with caustic potash, hydrogen being evolved during the reaction [1] The hydroxide is also reported to have been prepared by an electrolytic method,[2] and by reduction of ammomum paramolybdate in solution by hydrogen in presence of colloidal palladium [3] Molybdenum sesquioxide is insoluble in acids, and even the hydroxide dissolves only with difficulty

[1] **Muthmann and Nagel, *Ber* , 1898, 31, 2OO9**
[2] **Smith and Hoskinson, *Amer Chem J* , 1885, 7, 90, Wolf, *Chem Zentr*, 1918, l, 6O8**
[3] **Paal and Buttner, *Ber*, 1915, 48, 22O**

Salts of the Sesquioxide —With the exception of the metaphosphate, simple salts are not known in the crystalhne form, althoughsolutions of the hydroxide in acids yield amorphous residues on evaporation A complex pyrophosphate [1] and oxalate containing tervalent molybdenum have, however, been prepared

Molybdenum Dioxide, MoO_2, is formed when the sesquioxide is gently heated in a current of air, or when sodium tnmolybdate is lgmted for several hours in a current of hydrogen It is the only oxide formed when molybdenum trioxide is reduced by heating in hydrogen,[2] and may be prepared pure by heating this oxide first at 47O° in a stream of the gas, and then in a current of dry hydrogen chloride, when any unchanged trioxide is converted into a volatile oxychlonde and thus removed [3] It is formed also when ammonium molybdate is heated alone or fused with molybdenum trioxide,[4] and the product may be purified by washing successively with caustic soda, hydrochloric acid, and water, and then dried at 110° The pure oxide is a brown or violet-brown, crystalline powder, and is reduced directly to the metal when heated at 600° in hydrogen It is obtained in dark blue prisms resembling indigo by fusing sodium tnmolybdate with one-third of its weight of zinc, and extracting the mass alternately with caustic potash and hydrochloric acid, [5] this product, however, always contains a little admixed zinc molybdate, but it may be obtained pure by fusing together 8 grams of fused ammomum molybdate, 14 grams of potassiunf carbonate, and 7 grams of boron sesquioxide, and extracting the cooled melt with water It then forms opaque tetragonal crystals, having a Violet reflex, and is insoluble in boiling hydrochloric acid and caustic potash [6]

Molybdenum Tetrahydroxide, $Mo(OH)_4$—It is probable that by interaction of alkalis with solutions of the reduction products of molybdic acid, only impure molybdenyl hydroxide, $Mo(OH)_3$, has been obtained, and not the tetrahydroxide as claimed If, however, ammomum paramolybdate in aqueous solution is reduced at ordinary temperatures with hydrogen in presence of colloidal palladium, a greemsh-black precipitate is obtained which has a composition corresponding approximately to

[1] Rosenheim and TnantaphyHides, *Ber* , 1915, **48,** 582
[2] Gmchard, *Compt rend,* 1899, **129,** 722
[3] Fnedheim and Hoffmann, *Ber* , 1902, 36, 791
[4] Gmchard, *Compt rend,* 1899, **129,** 722, 190O, **131,** 998
[5] Ulhk, *Annalen,* 1867,**144,** 227
[6] Muthmann, *Annalen,* 1887, **238,** 114

$MoO(OH)_2$ [1] By a modification of the procedure, the compound can be prepared in a colloidal form [2]

Salts of the Dioxide—With the exception of the chloride, bromide, and sulphide, which are prepared by dry methods, and possibly the fluoride and iodide, these are known with but little certainty, even in solution there is liability of confusion between the salts in question and a mixture of those of quinquevalent and tervalent molybdenum On the other hand, a fairly large number of complex cyamdes containing quadrivalent molybdenum have been prepared

Molybdenum Pentahydroxtde and the Oxide, Mo_2O_5—It has already been mentioned that claims of the earlier investigators to have prepared the tetrahydroxide by interaction of alkalis with the reduction products of molybdic acid have not been substantiated, but that more or less impure molybdenyl hydroxide, $MoO(OH)_3$, the hydroxide of qumquevalent molybdenum, results Klason[3] prepared the compound, by treating ammomum molybdenum oxychlonde, $(NH_4)_2Mo_vOCl_6$, with ammonia, as a brown substance which gives a colloidal solution with water It is insoluble in alkali hydroxide solutions, but soluble in those of alkali carbonates, though it possesses no acid properties [4]

When the hydroxide is heated in a stream of carbon dioxide, a residue of the oxide, Mo_2O_5, is obtained as a violet-black powder The existence of pure compounds of this composition is, however, doubtful

Among other compounds containing quiquevalent molybdenum must be mentioned the pentachlonde, the double thiocyanates, the sulphate, $Mo_2O_3(SO_4)_2$, and a series of complex oxalates Barbien [5] has prepared double molybdyl formates and oxalates containing the radicle Mo^vO_2

MOLYBDENUM TRIOXIDE AND MOLYBDIC ACID

486 *Molybdenum Tnoxide,* MoO_3, was supposed to occur as molybdic ochre, but this has been shown to be hydrated ferric

[1] Paal and Brunjes, *Ber* , 1914> 47, 2214, Paal and Buttner, *Ber* , **1915, 48,** 22O

[2] See also Freundkch and Leonhardt, *Roll Chem Beihefte,* 1915, 7, 172

[3] Klason, *Ber,* 1901, 34, 148

[4] Mawrow and Nikolow, *Zeit anorg Chem,* 1915, 92, 135, disagree with this statement

[5] Barbien, *Atti B Accad Lmcei,* **1916,** [5], 26,1, 775

molybdate Gagarme[1] states, however, that he has found pure molybdic oxide as white or grey pseudomorphs after molybdenite in specimens from the Ilmen Mountains It has a pearly lustre and is semi-transparent It has probably been obtained by the oxidation of molybdemte which occurs there as pure sulphide without a trace of iron

In order to prepare the trioxide in the pure state on the small scale the native sulphide may be heated in a combustion tube in a curre limed[2] On the larger scale, it may be obtained by mixing the same powdered mineral with an equal weight of pure quartz sand, and roasting the mixture on a flat iron plate The roasted product is then boiled with dilute ammonia, and a small quantity of ammonium sulphide added to the solution in order to precipitate the copper The filtered liquid is then evaporated to dryness, and the residue again dissolved in dilute ammoma Crystals of ammonium molybdate are obtained from the filtrate on concentration These are decomposed by nitric acid, evaporated to dryness, and the residual trioxide well washed with water Molybdenum trioxide can also be obtained from native lead molybdate by first treating the mineral with dilute hydrochloric acid in order to remove iron, zinc, etc , then decomposing it with hot concentrated hydrochloric acid, evaporating down and digesting with dilute ammonia, when ammonium molybdate remains in solution and can be crystallised out as already described[3] The ammonium molybdate may also be converted into the trioxide by being lgmted in a platinum dish and subsequently heated to a dull red heat in a current of oxygen[4]

Molybdenum trioxide is a white, impalpable powder, which when heated becomes yellow, it melts[5] at 795° to a dark yellow liquid, which, on cooling, solidifies to a yellowish-white, fibrous, crystalline mass, having a density of 4 696 It volatilises at very high temperatures when heated in closed vessels, but in the air it sublimes more easily, depositing small, colourless, transparent, rhombic tablets It dissolves in 5OO parts of cold, and in about 96O parts of hot water The solution reddens litinus paper, turns turmeric paper brown, and possesses a sharp metallic taste

Molybdic Acid, H_2MoO_4,H_2O or MoO_3,$2H_2O$, crystallises out in yellow crusts when three parts of ammonium molybdate are

[1] *Bull Acad Sci St Peter sbourg,* 1907, 287
[2] Wohler, *Annalen,* 1856, **10O,** 376
[3] Muthmann, *Annalen,* 1887, 238, 117
[4] Wohler, *Mmei alanalyse,* 146
[5] Jaeger and Germs, *Zeit anorg Ghent,* 1921, **119,** 145

dissolved in twenty parts of water, the same quantity of nitric acid of specific gravity 116 is added, and the whole set aside The deposition of the acid frequently takes place only very slowly, and the addition of a crystal of the compound renders its separation more easy [1]

When the solution of the trioxide in nitric acid is allowed to evaporate spontaneously, a white, crystalline powder separates, which on heating loses water (Berzelius) This consists of the anhydrous acid, H_2MoO_4, which was once obtained by Ullik in the form of thin, prismatic crystals by the decomposition of magnesium molybdate with nitric acid It is also formed when the yellow acid is heated at 6O°, or its solution in water concentrated at 40-5O°, and is thus obtained in white needles which are very sparingly soluble in cold, but more readily in hot water [2] Two forms are distinguished as the a- and /?-forms respectively

Colloidal Molybdic Acid —When the hydrochloric acid solution of ammomum molybdate is dialysed, a yellow, strongly acid, astringent solution of molybdic acid remains, which on evaporation yields a deliquescent, gummy mass[3] After drying over sulphuric acid for several weeks it has the empirical formula $H_2Mo_2O_7$, but the determination of the molecular weight by Raoult's method indicates that it contains four MoO_3 groups [4] If ordinary ammonium molybdate is precipitated with barium chloride, and the washed precipitate decomposed with the exact quantity of sulphuric acid, a colourless solution is obtained, possessing an acid reaction and metallic taste When dried over sulphuric acid for several months it has the composition $H_2Mo_2O_7$, and on heating at 10O°, 12O°, and 16O-17O°, the residues have the compositions $H_2Mo_2O_7$, H_2MO_4 and $H_2Mo_8O_{25}$ respectively, at 25O° pure molybdenum trioxide remains behind Colloidal molybdic acid is rapidly reduced to the blue oxide by alcohol

Molybdenum trioxide generally behaves as an acid-forming oxide analogous to chromium trioxide, and umtes with bases to form molybdates The normal molybdates are unstable, and show a great tendency to form polymolybdates corresponding to the polychromates by uniting with further molecules of the

[1] Gmelin Kraut, 2, **171,** Rosenheim and Bertheim, *Zeit anorg Chem,* **1903, 34, 427, 1906, 5O,** 32O, Graham, *Journ Franklin Inst,* 1907,**164, 69**

[2] Rosenheim and Davidsohn, *Zeit anorg Chem* , **1903,37, 314, Burger,** *ibid* , **1922,121, 240**

[3] **Graham,** *Journ Chem Soc,* **1864, 19, 326, See, however, Brum and Pappada,** *Gazz* , **1901, 31,1, 244, Rosenheim and others,** ***he cit***

[4] **Sabaneef,** *Journ Chem Soc,* **1890, 68, 1215**

trioxide, as many as ten molecules of MoO_3 combining with one equivalent of a basic oxide

The molybdates also combine with other acidic oxides, forming the series of salts known under the general term of the complex molybdates The best known of these are the phosphomolybdic acids, in which a varying number of molecules of molybdenum trioxide and of phosphoric anhydride are combined with a basic oxide, similar compounds are formed by the acidic oxides of arsenic, sulphur, vanadium, antimony, and also of iodine, tin, silicon, and manganese[x] The exact constitution of these salts is not yet known

Molybdenum trioxide acts towards strong acids as a basic oxide, thus it combines with two molecules of hydrochloric acid to form a volatile crystalline compound, which is probably the *hydroxychlonde*, $MoO(OH)_2Cl_2$, with sulphuric acid it yields the compound[2] MoO_2SO_4, analogous to the salts formed by the trioxides of tungsten and uranium

Salt formation between molybdenum trioxide and bases is attended by the formation of a series[3] of compounds of complex constitution Thus there may be formed substances of the type

$E_2O\ MoO_3$ (normal molybdates)
$K_2O\ 2MoO_3$ (di-molybdates)
$5R_2O\ I2MOO3$ (para-molybdates)[4]
$E_2O\ 3MoO_3$ (tn-molybdates)
$R_2O\ 4MoO_3$ (tetra-molybdates)
$R_2O\ 8MOO3$ (octa-molybdates)[5]
$R_2O\ IOMOO3$ (deca-molybdates)
$R_2O\ I6MOO3$ (hexakaideca-molybdates)

[1] Pechard, *Compt rend,* 1901, **132,** 628, Rosenheim and Itzig, *Zeit anorg Chem* , 1898, **16,** 76, Friedheim and Samelon, *Zeit anorg Chem* , 190O, **24,** 65, Rosenheim and Lie bkneeht, *A nnalen,* 1899,**3O4,** 40, Aseh, *Zeit anorg Chem,* 1901, **28,** 273 See also Rosenheim and Jaenicke, *Zeit anorg Chem,* 1912, **77,** 239, Copaux, *Compt rend,* 1913, **156,** 1771, Mazzucchelh and Ranucci, *Gazz,* 1914, **44,** 11, 116, Rosenheim, Weinberg, and Pmsker, *Zeit anorg Chem* , 1913, **84,** 217, Rosenheim and Traube, *ibid* , 1915, 91, 75, Prandtl and von Blochm, *ibid,* 1915, 93, 45, Mawrow and Nikolow, *ibid* , 1915, 93, 17O, Weinland and Gaisser, *ibid* , 1919,**108,** 231, Weinland and Ziminermann, *ibid* , 1919, **108,** 248, Forsen, *Compt rend,* 1921, **172,** 681, Darmois, *ibid,* 1921, **172,** I486, Posternak, *ibid* , 1921,**172,** 597, Tanret, *ibid* , 1921,**173,** 43

[2] Compare Guichard, *Compt rend* , 1906, **143,** 744

[3] Forsen, *Compt rend,* 1921,**172,** 215, 327

[4] Rosenheim, *Zeit anorg Chem,* 1916, 96, 139, but Copaux, *Compt rend,* 1913, **166,** 1771, Posternak, *ibid,* 192O, **171,** 1058, regard paramolybdates as of the form $3R_2O\ 7MoO^3$

[5] Rosenheim, Felix, and Pinsker, *Zeit anorg Chem,* 1913, 79, 292, regard octamolybdates as hydrogen tetramolybdates

The di-, para-, and tn-salts are sometimes called " isopoly " salts, tetra- and octa-salts, possibly derived from a sexabasic heteropoly-acid, are grouped as " meta " salts

Sodium Molybdates—The normal molybdate, Na_2MoO_4, is formed by fusing the trioxide with the requisite quantity of sodium carbonate, and crystallises from water in acute rhombohedra, containing two molecules of water, below 6° prisms containing 10 molecules of water separate, resembling Glauber's salt in appearance, these effloresce in the air, forming the first named salt The *dimotybdate*, $Na_2Mo_2O_7$, is formed when sodium carbonate and the trioxide are fused in the requisite proportions, and is a crystalline mass soluble with difficulty in cold and only slowly in hot water A solution yields the hexahydrate *Sodium paramolybdate*, $5Na_2O,12MoO_3,36H_2O$, to which Rosenheim ascribes the formula[1] $Na_5H_6[H_2(MoO_4)_6],15\,5H_2O$ is obtained by allowing a solution of the calculated quantity of the trioxide

in sodium

spontaneously On heating it loses water, with eventual loss of its individuality The *tnmoh/bdate*, $Na_2Mo_3O_{10},7H_2O$, obtained

in a similar

dissolve in 10O parts of water at 2O°, and in 137 parts at 10O° Other hydrates have been described The *tetramolybdate*, $Na_2Mo_4,6H_2O$,[2] is prepared by the action of the calculated quantity of hydrochloric acid on the normal salt, and forms small, glistening crystals soluble with difficulty in cold, but readily in hot water *Sodium octamolybdate*, $Na_2Mo_8O_{25},17H_2O$, is formed as clear, lustrous, monoclmic crystals when a solution of the normal molybdate spontaneously evaporates in presence of the calculated quantity of hydrochloric acid A sodium octamolybdate crystallising with $15H_2O$ is said to be obtained by the action of sulphur dioxide on a solution of the tetramolybdate[3] The *decamolybdate*, $Na_2Mo_{10}O_{31},12H_2O$, is a white, crystalline powder obtained by heating the normal salt on the water-bath with sufficient hydrochloric acid to saturate the requisite quantity of sodium It is sparingly soluble in water Salts containing $6H_2O$ and $22H_2O$ have also been prepared[4] The compound

[1] **Rosenheim, *Zeit anorg Chem*, 1916, 96, 139, various other formulae have, howe\er, been ascribed, in particular, $3Na_aO,7MoO_a,22H_2O$**

[2] **But see Rosenheim and Felix, *Zeit anorg Chem* , 1913, 79, 292 See also VVempe, *tbid* , 1912, 78, 298**

[3] **Rosenheim, *Zeit anorg Chem*, 1897,15, 18O**

[4] **Ulhk, *Annalen*, 187O, 153 373, Rosenheim and Davidsohn, *Zeit anorg Chem*, 1903, 37, 314, Rosenheim, and Felix, *loc at* , Rosenheim, Felix and Pinsker, *loc cit***

$Na_2Mo_{16}O_{49},9H_2O$ was obtained by Ullik * by boiling a solution of the normal molybdate with nitric acid It may probably be regarded as an acid salt of a lower type

Potyfpium Molybdates —The normal salt, K_2MoO_4, obtained in a similar manner to the sodium salt, crystallises in microscopic four-sided crystals, which are readily soluble in water It is tnmorphous [2] When hydrochloric acid is added drop by drop to a solution of the trioxide in potassium carbonate until a permanent turbidity is produced, the *paramolybdate* of the composition $K_6Mo_7O_{24},4H_2O$ (or $5K_2O,12MoO_3,8H_2O$) separates out on standing, in monoclmic prisms, it is decomposed by water into the *tnmolybdate,* $K_2Mo_3O_{10},3H_2O$, which forms silky, pliable needles[3] By heating a solution of sodium octamolybdate with potassium chloride, the *tetramolybdate,* $K_2Mo_47H_2O$, is obtained A crystalline *octamolybdate,* $K_2Mo_8O_{25},13H_2O$, and hydrates of the *decamolybdale,* $K_2Mo_{10}O_{31}$, are also known (Rosenheim)

Ammonium Molybdates —The *normal molybdate,* $(NH_4)_2MoO_4$, is produced when molybdenum trioxide or an ammonium polymolybdate is heated with excess of concentrated ammonia, and crystallises in four-sided prisms which are decomposed by water The *dimolybdate,* $(NH_4)_2Mo_2O_7$, separates out on evaporating the mother-liquor of the normal salt, in the form of a white, crystalline powder [4] When a solution of the trioxide in ammonia is evaporated, the compound $(NH_4)_6Mo_7O_{24},4H_2O$ (Delafontame) crystallises out in large, colourless, monoclmic crystals This is the salt usually known as ammonium molybdate According to Klason,[5] however, the molecular weight in aqueous solution, taking into account the degree of dissociation indicated by the electrical conductivity, shows that this salt is probably a double salt, $(NH_4)_3H_3Mo_3O_{12},(NH_4)_2H_4Mo_3O_{12}$, which is resolved into its constituents, tnammomum and diammomum tnmolybdates, when dissolved in water On the other hand, Junius [6] gives the formula as $(NH_4)_{10}Mo_{12}O_{41}$ Results of physico-chemical measurements show that in aqueous solution the amon is $Mo_{12}O_{41}$,

[1] Ullik, *loc cit*

[2] Huttner and Tammann, *Zeit anorg Chem* , 1905, 43, 215, Amadon, *Atti R Accad Lincei,* **1914,** [5] 23, i, 8OO, van Klooster, *Zeit anorg Chem,* **1914, 85,49**

[3] Forsen, *Compt rend,* 1921, **172,** 215, 327, reports the existence of two potassium tnmolybdates of the same degree of hydration

[4] Compare Klason, *Ber,* 1901, 34, 153

[5] *Ber* , 1901, 34, 153 [6] *Zeit anorg Chem* , 1905, 46, 428

consequently this would appear to be the correct formula [1] The *trimolybdate,* $(NH_4)_2Mo_3O_{10},H_2O$, is frequently formed by the decomposition of a solution of the ordinary salt at a low temperature, when it separates out in silky needles, sparingly soluble in cold, but readily so in hot water It may also be formed by interaction of a solution of the ordinary paramolybdate with a suitable quantity of hydrochloric acid Other crystalline ammonium salts have been described, which contain a larger proportion of molybdenum trioxide [2]

Calcium Molybdate, $CaMoO_4$, is obtained by precipitating a solution of the ordinary ammonium salt containing an excess of ammonia with calcium chloride It forms a white precipitate consisting of microscopic tetragonal pyramids If calcium carbonate is boiled with an excess of the trioxide and water, and the solution allowed to evaporate spontaneously, *calcium trimolybdate,* $CaMo_3O_{10},6H_2O$, is deposited The salt $H_2CaMo_8Q_{26},17H_2O$ crystallises from a solution of the normal salt in the requisite quantity of hydrochloric acid It is deposited

in small, o

cold but readily dissolve in hot water

Barium Molybdate, $BaMoO_4$, is obtained in tetragonal pyramids by fusing together sodium molybdate, barium chloride, and common salt, and is difficultly soluble in acids

When the ordinary ammonium salt is precipitated with barium chloride, a flocculent precipitate of $Ba_3Mo_7O_{24},9H_2O$ or possibly $5BaO,12MoO_3,:rH_2O$, is thrown down, which is slightly soluble in water A compound, $BaMo_3O_{10},3H_2O$, having properties similar to the last salt, is obtained by precipitating a soluble trimolybdate When barium carbonate is dissolved in soluble molybdic acid and the solution kept, oblique prisms of the salt $H_2BaMo_8O_{26},17H_2O$ are deposited, and if the normal salt be treated with dilute nitric acid the compound $BaMo_{9028},4H_2O$ is formed This is insoluble in water and is not completely decomposed by acids, even by sulphuric acid

Magnesium Molybdate, $MgMoO_4,5H_2O$, is obtained by boiling magnesia with water and molybdenum trioxide, and evaporating the solution, when the salt separates out in long, glistening,

[1] **Sand and Eisenlohr,** ***Zeit anorg Chem,*** **1907, 52, 68, Rosenheim,** ***ibid,*** **1916, 96, 139, Posternak,** ***Compt rend,*** **192O,171, 1058**

[2] **Klason,** ***Ber,*** **1901, 34, 153, Rosenheim,** ***Zat anorg Chem,*** **1897, 15, 18O, 1903,34,427, Myhus,** ***Ber*** **1903,36,638, Wempe,** ***Zut anorg Chem,*** **1912,78,298, Barbien,** ***Atti R Accad Ltncet,*** **1919, [5], 28, i, 390, Posternak,** ***loc cit***

transparent prisms A Jieptahydrate is also known Magnesium molybdate forms with the Jtalybdates of potassium and sodium double salts such as $K_2MoO_4,MgMoO_4,2H_2O$, which appear to be isomorphous with the corresponding manganese and ferrous salts Magnesium forms para-, tn-, octa-, and 16-molybdates

Lead Molybdate, $PbMoO_4$, occurs native as wulfemte in orange-red, transparent, tetragonal tablets and octahedra, which have a specific gravity varying from 6 to 7 When one part of sodium molybdate is fused with six parts of lead chloride and four of sodium chloride in a closed crucible, bright yellow, translucent pyramids or tablets of the artificial compound are obtained, which have a specific gravity of 6 811 If a solution of a molybdate be added to one of lead mtrate the same compound is obtained

n the form

only other lead molybdate known [x] has the formula Pb_2MoO_5

Molybdenum Molybdates—When molybdic acid is reduced in solution by hydrogen sulphide, sulphur dioxide, stannous chloride, zinc,[2] alcohol,[3] etc , a blue solution is obtained, and this reaction forms one of the most characteristic tests for molybdenum This is due to the formation of an oxide or oxides intermediate between the di- and the tn-oxide, and the solutions deposit a blue precipitate of this oxide which contains water and is termed *molybdenum blue* It may also be obtained by adding a cold dilute hydrochloric acid solution of molybdenum dioxide to one of ammonium molybdate, and in several other ways The solubility in water of the blue oxide varies with the conditions of precipitation It is colloidal in nature, and behaves as a negative colloid

Much doubt exists as to the composition of this oxide, Eammelsberg assigned to it the formula $Mo_2O_5 = MoO_2,MoO_3$, and others have regarded it as $Mo_3O_8 = MoO_2,2MoO_3$, whilst according to Guichard[4] it has the composition $Mo_5O_{14},6H_2O = MoO_2,4MoO_3,6H_2O$ On the other hand, Klason[5] states that more than one compound exists, and regards these as complex derivatives of an oxide, Mo_2O_5, and molybdic acid, analogous to phosphomolybdic acid Junius [6] has obtained it at the cathode

[1] Jaeger and Germs, *Zeit anorg Chem* , 1921, **119,** 145 See, however, Dittler, *Zeit kryst Mm* , 1913, 63, 158, 1914, 54, 332

[2] Scott, *J Ind Eng Chem,* 192O, **12,** 578

[3] Benrath, *Zeit wiss Photochem* , 1917,16, 253

[4] *Compt rend,* 1899, **129,** 722, Rogers and Mitchell, *J Amer Chem Soc,* 190O, **22,** 35O, Junius, *Zeit anorg Chem* , 1905, 46, 426

[5] *Ber,* 1901, 34,148 See also Bailhache, *Compt rnd,* 1901,**133,**1210.

[6] *Zeit anorg Chem,* 1905, 46, 428

by the electrolysis of molybdic acid in strong hydrochloric acid, and gives to it the formula, Mo-O The composition of the single individual compound—if, indeed, the substance is such—is known only approximately, it is possible therefore to ascribe to it various formulae in which it may be regarded as a simple or complex molybdate of molybdenum or of the molybdenyl radicle

Several crystalline ammomacal double molybdates have been described[1] of the general formula $M^{I}_2M^{II}(MoO_4)_2,2NH_3$, where M^{I} = K or NH_4, and M^{II} = Cu, Zn, Cd, Nl, or Co

Molybdates exhibit catalytic activity in several interesting ways, *e g* , in influencing the oxidation of thiosulphates by hydrogen peroxide to sulphates instead of, as normally, to tetrathionates [2]

487 *Pkosphomolybdtc Acid,* $P_2O_5,24MoO_3,63H_2O$ or $H_7[P(Mo_2O_7)_6],28H_2O$ —This yellow complex acid is obtained by the repeated treatment of the ammonium salt with small quantities of aqua regia, and crystallises out on evaporation of the combined solutions It forms also crystalline hydrates containing $22H_2O$ and $12H_2O$

The composition of these bodies has been investigated by Rosenheim and others [3] In common with a number of other complex acids, such as those containing molybdic acid in association with silicic, oxalic, formic, arsenic, sulphurous, etc , acids, they are classed as " *heteropoly-acids"* the complex amon being composed of several amonogen radicles, of which at least one differs from the remainder[4] Such compounds are subject to

[1] Bnggs, *Journ Chem Soc* , 1904, 85, 672

[2] Abel, *Zeit Elehtrochem* , 1912, 18, 7O5, Abel and Baum, *Monatsh,* 1913, 34, 425, 821 See also Schilow, *Zeit phystkal Chem,* 1898,27,513, Brode, *tbid* , 1901, 37,299, Titoff, *ibid* , 1903, 45, W I , Milbauer, *ibid* , 1907, 57, 649

[3] See Abegg, *Handbuch der anorganischcn Chemie,* IV, [1], 11, also Fnedheim, *Zed anorg Chem,* 1893, 4, 274, Fnedheim and Meschoirer, *ibid,* 1894, 6, 33, Kehrmann, *tbid,* 1894, 7, 406, Le\i and Spelta, *Gazz,* 1903, 33, 1, 2O7, Miolati, *ibid,* 1903, 33, 11, 335, *J pr Chem,* 1908 [2], 77, 417, Rosenheim and Pinaker, *Zeit anorg Chem,* 1911, 7O, 79, Rosenheim, *Zeit Elektrochem,* 1911,17, 694, Rosenheim and Traube, *Zeit anorg Chem,* 1915, 91, 96, Rosenheim and Jaenicke, *tbid* , 1912, 77, 239, 1917,**101,** 247, Mawrow and Nikolow, *ibid,* 1915, 93, 17O, Rosenheim and Tnantaphyllides, *Ber,* 1915, 48, 582, Ephraim and Herschfinkel, *Zeit anorg Chem* , 1909, 65, 233, 237, Ephraim and Brand, *ibid,* 1910,65,233

[4] See Copaux, *Compt rend,* 1913,**156,**1771, Barbien, *Atti R Accad Lmcet,* 1913, [6], *22,* 1, 781, Rosenheim, Weinberg, and Pinsker, *Zett anorg Chem,* 1913, 84, 217, Rosenheim and Traube, *he cit* , Rosenheim and Seller, *ibtd,* 1914, 89, 224

certain types of isomerism, as have already been described in the case of the chromiattimines

The phosphomolybdic acias and their derivatives fall into two mam groups *(a)* the more complex compounds, of a yellow colour, are derivatives of the amons $[PO_6]^{VI1}$ and $[Mo_2O_7]^n$, *(b)* the less complex compounds, colourless, are derivatives of the amons $[PO_4]^m$ and $[MoO_4]^n$ The yellow compound already mentioned belongs to the first class A solution of this substance on long keeping undergoes hydrolysis, resulting in the production of a complex phosphomolybdic acid of the formula $H_{12}[P_2O_2(Mo_2O_7)_9]24\ ^{tO}\ 3OH_2O$ Further hydrolysis of salts of this acid yields salts of an unstable acid containing the anion $[P_{404}(Mo_2O_7)_{17r}$»

If the yellow phosphomolybdates are treated with alkalis, *e g,* ammonia solution, white salts of the second class are obtained, the latter can also be produced directly from smtable proportions of their components, but no free acid corresponding to this group of salts has yet been prepared

Ammonium Phosphomolybdate, $(NH_4)_3PO_4,12MoO_3$—This salt is formed as an insoluble, canary-yellow precipitate when a solution of a molybdate is mixed with ammoma, and a small quantity of phosphoric acid in nitric acid solution added, or when the free acid is added to a strongly acid solution of the ammomum salt Pyro- and meta-phosphates do not yield this precipitate, it is formed only when they are converted into orthophosphates, and when this change takes place slowly the compound is obtained in glistening yellow crystals (Debray) It is almost insoluble in water and in dilute acids and is also insoluble in a nitric acid solution of ammomum molybdate The presence of hydrochloric acid and chlorides, as well as of many organic acids, with the exception of acetic acid, retards the formation, whilst in presence of an excess of phosphoric acid no precipitation occurs Phosphates are commonly estimated by this method, so that the recovery of molybdic acid from the filtrate is a matter worthy of attention [x] It is usually effected by precipitation with sodium phosphate, solution of the precipitate in ammoma, and removal of the phosphoric acid with magnesium salts The molybdenum may, however, be recovered as sulphide

[1] **See Brown,** *J Ind Eng Chem* **, 1915, 7, 213, Armstrong,** *ibid* **, 1915,7, 764, Kinder,** *Stahlu Eisen,* **1910, 36, 1094, Rudnick and Cooke,** *J Ind Eng Chem* **, 1917, 9, 109, Lehner and Schultz,** *ibid* **, 1917, 9, 684, Lynas,** *Chem Met Eng* **1918,169, NeubauerandWolferts,Zei*** *anal Chem,* **1919, 58, 445, Makwan,** *Chem Zeit,* **1918,42,410**

When dried above 130°, the salt always has the composition given above, in which the ratio P_2O_5 MoO_3 is 1 24, but according to Gibbs the hydrated precipitate has the composition $(NH_4)_3PO_4,12MoO_3,(NH_4)_2HPO_4,llMoO3,8H_2O$, it is commonly, however, regarded as $(NH_4)_3PO_4,12MoO_3,2HNO_3,H_2O$ It dissolves in 10,OOC nitric acid, and in 55O parts of hydrochloric acid of specific gravity 1 12 It is readily soluble in alkalis, and on allowing the ammoniacal solution to stand, glistening needles or prisms having the composition $2(NH_4)_3PO_4,5MoO_3,7H_2O$ separate These are sparingly soluble in cold, readily in hot water, forming a slightly acid liquid

Phosphomolybdic acid also precipitates strongly acid solutions of the salts of rubidium, caesium, thallium, and the orgamc alkaloids, but not solutions of sodium or lithium salts The heavy metals are also not precipitated if a sufficient amount of free acid be present This acid is used as a reagent for the alkaloids or, in place of this, a liquid prepared by saturating a solution of sodium carbonate with molybdenum trioxide, and adding one part of sodium phosphate to every part of the trioxide, may be employed, this solution is evaporated to dryness, the residue fused, dissolved in water, filtered, and nitric acid added until the liquid becomes yellow

Complex Arsenomolybdic acids likewise exist

Permolybdic Acid —The molybdates when treated with hydrogen peroxide in acid solution give a yellow coloration, but the yellow substance cannot be extracted with ether If molybdenum trioxide be treated with hydrogen peroxide on the water-bath, and the mixture evaporated under diminished pressure, *permolybdic* or *ozomolybdic acid*,[1] H_2MoO_5,wH_2O, is obtained as an orange-red, amorphous substance Potassium tnmolybdate dissolves in hydrogen peroxide, yielding an orange-yellow solution, which on concentration at a moderate heat yields yellow crystals of *potassium permolybdate*, this, according to Muthmann and Nagel,[2] has the composition $K_2O,2MoO_3,MoO_4,3H_2O$ These chemists have shown that the molybdates of the alkali metals, when dissolved in hydrogen peroxide, can take up more oxygen to the extent of one atom or less per atom of molybdenum, in this way they have prepared a number of *pet molybdates* which readily lose oxygen on heating

[1] Muthmann and Nagel, *Ber* , 1898, 31, 1836

[2] *Zeit anorg Chcm*, 1898, 17, 73 Compare Pechard, *Compt rend^*, **1891,** 112, **72O.**

A compound, $K_2O_2,]\backslash IoOg,H_2O_2$, is formed by the action of hydrogen peroxide at —2° #n a solution of potassium permolybdate containing potassium hydroxide, followed by alcohol at —12° This is a brick-red mass which explodes spontaneously when preserved in quantity, and loses oxygen on exposure to the air, or on treatment with water [x]

There are also known both red and black *perthtomolybdates* of the composition $RMoS_5$ and $RMoS_6$ respectively, and *oxyfluoropermolybdates, eg,* $K_2[F_4MoO(O_2)],H_2O$.

MOLYBDENUM AND THE HALOGENS

488 Normal salts of bivalent molybdenum are unknown, corresponding polymolecular complexes exist, but these do not yield the simple doubly-charged molybdenum ion

Molybdenum Dichlonde, Mo_3Cl_6, is prepared by heating the trichloride in a current of dry carbon dioxide

$$2MoCl_3 = MoCl_2 + MoCl_4$$

The tetrachloride volatilises, leaving the dichloride as a sulphur-yellow, amorphous powder, which does not alter in the air, and does not dissolve in water but is soluble in alcohol or ether, separating from these solutions in the amorphous condition [2] The dichloride is convemently obtained[3] by passing carbonyl chloride over powdered molybdenum at 7OO-8OO°, when a small quantity of the pentachlonde sublimes, and the metal gradually becomes coated with a heavy, protective layer of the dichloride, which is removed by extracting it with concentrated hydrochloric acid It is also produced when chlorine, mixed with a large excess of carbon dioxide, is passed over gently heated molybdenum in absence of oxygen [4] It is soluble in the hydracids, in hot sulphuric acid, and in the alkalis, yielding compounds which must be regarded as salts of the radicle (Mo_3Cl_4) Thus the hydrate $[Mo_3Cl_4]Cl_2,3H_2O$, crystallises from the hydrochloric acid solution, on keeping, in pale-yellow plates insoluble in water, but when the solution is evaporated long prisms having the formula $Mo_3Cl_6,HCl,4{:}H_2O$, are deposited Similarly, the solutions in alkalis contain compounds of the type $[Mo_3ClJ(OH)_2$ The

[1] Melikoff and Pissarjewsky, *Ber,* 1898, 31, 632
[2] Liechti and Kempe, *Annalen,* 1873,**169,** 351
[3] Lindner and others, *Ber,* 1922, 55, [J5], 1458
[4] Blomstrand, *J pr Chem,* 1859, 77, 96, Wolf, *Chem Zentr,* 1918, I, 6O8, Lindner and others, *loc cit*

molecular weight of the dichloride in alcohol corresponds to the formula Mo_3Cl_6 [1]

Molybdenum Dibromtde, Mo_3Br_6, is formed by the decomposition of the tnbromide by heat It is a yellowish-red, infusible mass which does not dissolve in water or in acids

Molybdenum Di-iodide, MoI_2, or Mo_3I_6 (?), is formed by heating the pentachlonde in a current of hydrogen iodide It is a brown, amorphous substance of density 4 3, and is insoluble in water [2]

Chloromolybdic Hydroxide, $[Mo_3Cl_4](OH)_2,2H_2O$, precipitated by acetic acid from a solution of the dichloride in alkali, possesses amphoteric properties, and forms well-defined salts with acids [3]

Chloromolybdic Bromide, $Mo_3Cl_4Br_2,3H_2O$, is obtained by heating the hydroxide or the chloride with hydrobromic acid It crystallises on cooling in glistening reddish-yellow plates which scarcely dissolve in water or in dilute hydrochloric acid Hydnodic acid forms a corresponding cotnpound

Bromomolybdic Hydroxide, $Mo_3Br_4(OH)_2,8H_2O$ —When molybdenum dibromide is dissolved in dilute alkali and the solution allowed to remain exposed to the air, or when ammonium chloride is added to the hot solution, the above compound is deposited in the form of golden-yellow, glistening rhombohedra closely approximating in form to the cube These lose six molecules of water on drying over sulphuric acid, and assume a dark red colour At 10O° they lose all their water, a fine red powder remaining behind [4]

Bromomolybdic Fluoride, $Mo_3Br_4F_2,3H_2O$, is prepared with hydrofluoric acid in the same way as the chloride, which it closely resembles

Bromomolybdic Chloride, $Mo_3Br_4Cl_2,3H_2O$, is obtained as a pale-yellow powder on adding an excess of hydrochloric acid to the alkaline solution of the hydroxide

Bromomolybdic Sulphate, $Mo_3Br_4SO_4,3H_2O$, can be obtained in the same way in the form of a yellow precipitate, whilst when the solution of the hydroxide is treated with ammonium molybdate and acetic acid, *bromomolybdic molybdate,* $Mo_3Br_4MoO_4,2H_2O$, is thrown down as a reddish-yellow precipitate

Molybdenum Trifluoiide has not been isolated, except in the form

[1] Muthmann and Nagel, *Ber* , 1908, **31,** 2009 See also Koppel, *Zeit anorg Chem* , 1912, **77,** 289

[2] Guichard, *Compt rend* , 1896,**128, 821**

[3] Blomstrand, *J pr Chem,* **1859, 77, 10O**

•**Atterberg,** ***Ber,*** **1873, 6, 1464**

of double salts, but it is known to exist in solutions of molybdenum trihydroxide in hydrofltTonc^icid

Molybdenum Trichloride, $MoCl_3$, is formed when the pure pentachlonde is volatilised in a current of carbon dioxide, the tube being heated strongly at one point only The trichloride is deposited as a copper-red, crystalline crust * If the pentachlonde is heated in a current of hydrogen to 25O° the trichloride is obtained in a form closely resembling red phosphorus[2] The trichloride is the main product of the reaction of carbonyl chloride and molybdenum at about 6OO°[3] Heated in the air it forms a white, woolly sublimate, whilst impure dichlonde remains behind It is insoluble in cold water and is decomposed by boiling water It likewise does not dissolve in hydrochloric acid, though it is easily soluble in hot nitric acid, whilst sulphuric acid dissolves it, forming a blue solution which on heating becomes green If the hydroxide is dissolved in hydrochloric acid a brown liquid is obtained which on evaporation dries to a black, pitch-like mass By interaction with ammonia, a series of amido-compounds is obtained

Molybdenum Tnbromide, $MoBr_3$, is formed by the action of bromine vapour on the heated metal, it can also be prepared electrolytically[4] It sublimes as a mass of fine blackish-green needles which are insoluble in water though soluble in cold dilute nitric, and in boiling hydrochloric, acids On boiling with alkalis the hydroxide is formed (Blomstrand)

Molybdenum Tetrachloride, $MoCl_4$, is obtained together with the dichloride, as has been stated, by heating the trichloride in an atinosphere of carbon dioxide The tetrachloride volatilises as a dark yellow vapour which condenses to a brown, crystalline powder A better method[5] is to heat the dioxide with a solution of chlorine in carbon tetrachloride at 25O° When heated in moist air it is decomposed It reacts readily with water, but is incompletely dissolved It is only slowly soluble in h}drochlonc acid, and dissolves in concentrated sulphuric acid, giving a bluish-green colour

Molybdenum Tetrabromide, $MoBr_4$, is formed in small quantities

[1] **Blomstrand,** ***J pr Chem*** **, 1859, 77, 96**

[2] **Liechti and Kempe,** ***Ann,*** **1873, 169, 344, Wolf,** ***Chem Zentr,*** **1918, l, 608**

[3] **Lindner and others,** ***Ber*** **, 1922, 55,** ***[B],*** **1458**

[4] **Rosenheim and Braun,** ***Zeit anorg Chem*** **, 1905, 46, 311**

[5] **Michael and Murphy,** ***Amer Chem J,*** **1910, 44, 3O5**

in the preparation of the tnbromide as black, glistening needles, which fuse when heated, volatilising in brownish-red vapours These readily decompose into bromine and dibromide. In presence of air the compound deliquesces, forming a dark liquid giving with more water a yellowish-brown solution

Molybdenum Tetriodide, MoI_4—Liquid hydrogen iodide and molybdenum pentachloride yield black, insoluble crystals, probably of this compound Double salts have also been described [1]

Molybdenum Pentachloride, $MoCl_5$—This, the highest chloride of molybdenum, is formed [2] by heating molybdenum or molybdenite in dry chlorine for some time, when bright, metallic, glistening, black crystals are formed which melt at 194° and boil at 268°, giving a dark red vapour with a density of 9 4-9 53,[3] corresponding to the above formula The compound fumes on exposure to moist air, giving MoO_2Cl_2, and becomes coloured bluish-green, gradually deliquescing to a brown liquid which on dilution with water becomes colourless Absolute alcohol, ether, and certain other solvents [4] yield green solutions, whilst chloroform, carbon disulphide, and mtrobenzene are examples of solvents yielding red-brown solutions, which differ physically from the former, the chloride also dissolves in hydrochloric acid with evolution of heat It is decomposed by water with formation of the tetrachloride, molybdic acid, and hydrochloric acid,[5] $MoOCl_3$ probably being formed intermediately

"When molybdenum trioxide is heated with phosphorus pentachloride to 17O°, the compound $MoCl_5$,$POCl_3$ is formed It crystallises m dark green prisms, and when further heated decomposes into its two constituents

Molybdenum Hexafluonde, MoF_6, is obtained by passing dry fluorine over powdered molybdenum at 6O-7O°, the product being collected in a receiver cooled by a mixture of solid carbon dioxide and alcohol, and then purified by distillation It is a snow-white, crystalline substance, melting at 17° to a colourless liquid, which boils at 35°, and is decomposed by water with formation of a blue oxide [6] It is not acted upon by chlorine,

[1] **Guichard,** ***Ann Chim Phys,*** **1901, [7], 23, 498, Rosenheim and Koss,** ***Zeit anorg Chem,*** **1906, 49, 148**

[2] **Lindner and others,** ***Ber ,*** **1922, 55,** ***[B],*** **1458**

[3] **Debray,** ***Compt rend,*** **1868, 66, 732**

[4] **Lloyd,** ***J Physical Chem,*** **1913, 17, 592**

[5] **Guichard,** ***Bull Soc chim,*** **1901, [3], 25, 188**

[6] **Ruff and Eisner,** ***Ber ,*** **1907, 40, 2926**

but reacts with arsenic trichloride and antimony pentachlonde, it is reduced and turned blue by organic compounds

OXY-HALIDE DERIVATIVES OF MOLYBDENUM

489 No oxyfluonde or oxychlonde containing qumquevalent molybdenum is known with certainty to exist, although a considerable number of double salts, *e g*, $MoOF_3,2KF,H_2O$ and $K_2(MoOCl_5),2H_2O$, have been prepared The former class are blue or green, and the latter green, crystalline substances The hydroxy bromide, $MoO(OH)Br_2$,l $5H_2O$ yields double salts of the types $K(MoOBr_4),2H_2O$ and $K_2(MoOBr_6)$

Sexavalent molybdenum forms a large number of derivatives containing oxygen and the halogens, many of which are volatile and crystalline, and yield crystalline double salts with other metallic halides

Molybdenyl Tetrafluoride, $MoOP_4$, is formed by the action of anhydrous liquid hydrofluoric acid on the corresponding oxychlonde as a white, hygroscopic body, melting at 97° and boiling at 180° [1] It forms a double salt with potassium fluoride [2]

Molybdenum Dioxydifluoride, MoO_2F_2, is obtained by heating the trioxide with cryolite or lead fluoride as an amorphous sublimate having a bluish tinge, which decomposes in the air into hydrogen fluoride and molybdenum trioxide, [3] it is obtained m solution by dissolving the trioxide m hydrofluoric acid It may also be obtained by the action of anhydrous liquid hydrofluonc acid on the dioxydichloride as a white, hygroscopic mass, which sublimes at about 27O°, and turns blue m the air [4] Crystalline double salts are formed by dissolving the normal and polymolybdates m hydrofluoric acid, thus *potassium molybdenum oxyfluonde,* $K_2MoO_2F_4,H_2O = MoO_2F_2,2KF,H_2O$, forms lustrous plates or scales, and is soluble in water

Molybdenyl Tetrachloride, $MoOCl_4$, has been stated to be formed by the action of chlorine on a moderately-heated mixture of carbon and molybdenum dioxide There is formed a dark green, crystalline mass, or, if obtained at a higher temperature, light-green plates having a metallic lustre It is readily decomposed by water, deliquescing m moist air to a blue liquid, and this

[1] **Ruff and Eisner,** ***Ber*** **, 1907, 40, 2931**
[2] **Marchetti,** ***Zeit anorg Chem,*** **1895, 10, 66**
[3] **Schultze,** ***J pr Chem*** **, 188O, 21, 442**
[4] **Ruff and Eisner,** ***Ber,*** **1907, 40, 2933**

on addition of water gives a blue precipitate which becomes brown in presence of ammonia It is probable, however, that it is not an individual compound, but a mixture of the pentachlonde and dioxydichloride [1]

Molybdenum Dioxydichloride, MoO_2Cl_2—This compound was originally supposed to be the hexachlonde, its true composition being first ascertained by Kose It is obtained by heating the dioxide m chlorine, and also, together with other chlorides, when a mixture of the trioxide and carbon is substituted for the dioxide It sublimes usually as an amorphous mass, and melts only in closed vessels, in which it may be sublimed at low temperatures yielding thm tetragonal plates, or mossy aggregates It dissolves readily in water and alcohol

The *oxychloride,* $Mo_2O_3Cl_6$, is obtained by the repeated sublimation of the " oxytetrachloride," and forms well-developed violet prisms, which are decomposed on heating in the air into molybdenum dioxydichloride and chlorine When heated to a temperature somewhat higher than that needed for its formation, it yields $Mo_3O_5Cl_8$, which forms pale red needles and is stable in the air Oxychlondes having the composition $Mo_2O_3Cl_5$, $Mo_2O_3Cl_4$, and $Mo_3O_3Cl_7$ have also been described [2]

Molybdenyl Dihydroxydichloride, $MoO(OH)_2Cl_2$, is obtained by the action of hydrogen chloride on the trioxide at 15O-2OO°, and is a white, crystalline substance which is volatile without decomposition only m an atinosphere of hydrogen chloride [3]

A number of salts of chloromolybdic acids, which may be regarded as molybdates in which the oxygen and the hydroxyl groups are partially replaced by chlorine, have been described The acid, $MoOCl_3\,OH,7H_2O$, is obtained by the action of fuming hydrochloric acid on molybdenyl hydroxide, and a number of its salts have been prepared [4]

Molybdenum Dioxydibromide, MoO_2Br_2, is formed when bromine vapour is passed over the heated dioxide, or when a mixture of molybdenum trioxide and boron trioxide is heated with potassium bromide

$$MoO_3 + B_2O_3 + 2KBr = MoO_2Br_2 + 2KBO_2$$

It forms yellow tablets which deliquesce on exposure to air

A hydroxybromide of the composition $Mo(OH)_3Br_3$ exists

[1] See also Klason, *Ber* , 1901, 34, 148 [2] *Annalen,* 188O, **2O1,** 123
[3] Debray, *Compt rend* , 1858, **46, 1101**
[4] Weinland and Knoll, *Ber,* 1904, 37, 569, *Zeit anorg Chem* , 1905, 44, 81

A number of bromomolyjxiates have been described (Wemland and Knoll)

MOLYBDENUM AND SULPHUR

490 *Molybdenum Sesquisulphide,* Mo_2S_3, is obtained when the disulphide is heated m the electric furnace It forms steel-grey needles of density 5 9 at 15°, and is converted into metallic molybdenum when heated to a higher temperature than that at which it is formed [1]

Molybdenum Disulphide, MoS_2, is found native as molybdemte in Sweden, Norway, Bohemia, Saxony, the Urals, at Caldbeck Fells in Cumberland, in Connecticut, California, and elsewhere It commonly occurs in foliated masses or in scales, and sometimes in tabular hexagonal prisms, and in its general appearance is very similar to graphite, since it possesses a metallic lustre and pure lead-grey colour, and leaves a grey trace on paper It possesses interesting electrical properties, and between ordinary temperatures and a red heat it exists in two distinct states [2] Molybdemte generally occurs embedded in or disseminated through granite, gneiss, zircon-syemte, granular limestone, and other crystalline rocks

When the trioxide is fused with sulphur, or heated in a current of hydrogen sulphide, the same compound is obtained m the form of a glistening black, powder, easily distinguished from graphite by the facts that when heated before the blowpipe it is incombustible, that it oxidises when heated m the air with evolution of sulphur dioxide and formation of molybdenum trioxide, and that it is readily oxidised by nitric acid and aqua regia

Dimolybdenum Pentasulphide, $Mo_2S_5,3H_2O$, is produced when a solution of ammonium molybdate containing sulphuric acid is reduced with zinc, the liquid filtered and treated with hydrogen sulphide It is a browmsh-black precipitate which on carelul dehydration in a stream of carbon dioxide yields black Mo_2S_5 It is soluble in alkali sulphide to red solutions [3]

Molybdenum Tnsulphide, MoS_3, is formed when hydrogen sulphide is parsed into the concentrated solution of a molybdate and hydrochloric acid is added to the liquid It may likewise be prepared by boiling the molybdate of an alkali metal for a short time with ammonium sulphide, and then precipitating with

[1] Guichard, *Bull Soc chim,* 190O, [3], 23, 147
[2] Waterman, *Phil Mag ,* 1917, [6], 33, 225 [3] Kriiss, *Annalen,* **1884,225,1**

dilute sulphuric acid Thus obtained, it is a reddish-brown precipitate which dries to a blackish-brown powder On heating in absence of air, it splits up into the disulphide and sulphur With basic sulphides it forms soluble thio-salts

Potassium Thiomolybdate, K_2MoS_4, is formed when potassium molybdate is saturated with hydrogen sulphide in presence of potassium hydroxide On evaporating the solution, the compound crystallises out in ruby-red four- or eight-sided tablets which have a green, metallic lustre, and dissolve in water to form a yellowish-red solution

Ammonium Thiomolybdate, $(NH_4)_2MoS_4$, is obtained by dissolving the trisulphide in ammonium sulphide, and crystallises in cinnabar-red scales

A series of mono- and di-thiomolybdates has been described by Kruss

Molybdenum Tetrasulphide, MoS_4, is obtained by heating pentathiomolybdic acid to 140° as a cinnamon-brown powder which undergoes slight oxidation in the air The pentathio-acid is obtained as a reddish-brown powder by the action of dilute hydrochloric acid on the potassium salt

Potassium Pentathiomolybdate, $KHMoS_5$, is obtained[x] by evaporating a solution of potassium dimolybdate which has been saturated with hydrogen sulphide, and separates in sparingly soluble, blood-red prisms probably belonging to the Thombic system A black powder consisting of molybdenum di- and tn-sulphides separates out at the same time[2]

Perthiomolybdic Acid, $HMoS_6$—When a solution of normal ammonium thiomolybdate is mixed with a solution of ammonium polysulphides, *ammonium hexathiomolybdate* or *pei thiomolybdate* separates out m black, lustrous needles, which are sparingly soluble in water or alcohol By the action of caustic potash it yields the potassium salt, $KMoS_6$, which crystallises in thin, dark-brown plates, more soluble in water than the ammonium salt The free acid, $HMoS_6$, is obtained by tieating the ammonium salt with cold 10 per cent hydrochloric acid and washing the product with carbon disulphide[3]

Sulphomolybdic Acid, $H_2[MoO(SO_4)_2(MoO_4)]$, has also been prepared[4]

[1] **Kruss, *Ann*, 1884, 225, 1 Hofmann, *Zed anorg Chem*, 189G, 12, 55, ascribes the formula $KMoS_5$ to this compound**

[2] **Kruss, *loc cit***

[3] **Hofmann, *loc cit***

[4] **Meyer and Stateczny, *Zett anorg Chem* 1922, 122, 1**

MOLYBDENUM AND NITROGEN, PHOSPHORUS, BORON, CARBON, *AN§* SILICON

491 *Molybdenum Nitride*—When molybdenum oxide, hydroxide, or mixtures of the two are heated to 500-600° with equal parts of nitrogen and hydrogen under a pressure of about 6O atinospheres a molybdenum nitride is formed Direct interaction, with formation of a nitride, takes place at high temperatures between molybdenum and nitrogen [1] It is also the final product when molybdenum trichloride or pentachloride is heated in a stream of ammonia When heated m hydrogen or water-vapour, Mo_3N_2 yields pure metallic molybdenum and ammonia,[2] its techmcal application as a catalyst for the union of mtrogen and hydrogen has been the subject of investigation

Molybdenum Phosphide, MoP, is obtained by strongly heating molybdenum trioxide and metaphosphonc acid m a carbon crucible It forms a grey, vesicular mass having a metallic lustre and containing crystals in the cavities On ignition in the air, it oxidises slowly, and it takes fire when dropped into fused potassium nitrate

Molybdenum Metaphosphate, $Mo(PO_3)_3$, is formed when a solution of molybdenum trioxide in metaphosphonc acid is reduced with hydrogen at a red heat [3]

Molybdenum Boruie, probably Mo_2B, has been piepared by an arc method

Molybdenum Carbides —The carbide, MoC, is obtained by fusing in the electric furnace [4] a mixture of molybdenum, carbon, and aluminium, as a grey, crystalline powder of density 8 40 at 2O°, whilst the compound, Mo_2C, is formed when calcium carbide is heated in the electric furnace with molybdenum dioxide [5] The *carbonyl,* $Mo(CO)_6$, or moie probably [6] $Mo_5(CO)_{26}$, is known

Molybdenum Cyanides and Thwcyanates—Tervalent molybdenum forms a series of complex molybdo-thiocyanates of the type $K_3Mo(CNS)_6,4H_2O$, quadnvalent molybdenum forms three distinct series of complex cyanides[7], qumquevalent molybdenum

[1] Ltderer, 1911, Langmuir, *J Amer Chem Soc* , 1919, 41, 167
[2] D R - P , 246554, Austr Pat 62524
[3] Colani, *Compt rend,* 1914, **158,** 499, 794, *ibid* , 1917, **165,** 185
[4] Moissan and Hoffmann, *Compt rend,* 1904, **138,** 1558
[5] Moissan, *Compt rend,* 1897, **125,** 839 See also Hilpert and Ornstein, *Ber* , 1913, 46, 1669
[6] Mond and Walks, *J Chem Soc* , 1922, **121,** 29
[7] See a review by Collenburg, *Zeit anorg Chem* 1922,**121,** 298

forms double hydroxy thiocyanates of the form $Mo(OH)_2(CNS)_3 Py_2$ as well as complex oxalo-denvatives

Molybdenum Sihcide, Mo_2Si_3, is formed as a crystalline compound when the oxide obtained by calcining ammonium molybdate is heated with silicon in the electric furnace[2] Sihcides of the formulae MOS1 and $MoSi_2$ have also been described[2]

DETECTION AND ESTIMATION OF MOLYBDENUM

492 Probably the most delicate qualitative test for molybdenum compounds consists in their reduction by means of stannous chloride or zinc, m the presence of a soluble thiocyanate, a blood-red coloration, due to the formation of moybdenum thiocyanate which is soluble m ether, indicates the presence of as little as 1 part in 6 millions[3] Formation of a plum-coloured compound, $MoO_3(OEt\ CSSH)_2$, with xanthic acid is another sensitive reaction,[4] as also is that of red ammonium permolybdate by means of hydrogen peroxide[5] Acidified solutions of molybdates, when brought into contact with zinc or other suitable reducing agents, become blue, then green, and finally brown, hydrazine, iodides, or quinol give a blue coloui, whilst catechol yields an orange solution[6] Keduction is effected by sulphurous acid only if the solutions are neutral or but slightly acid When a trace of a molybdenum compound is evaporated nearly to dryness with a few drops of sulphuric acid, a blue colour develops This reaction also is very sensitive

Molybdenum trisulphide is slowly precipitated from an acid solution of a molybdate by hydrogen sulphide, which first causes the development of a blue colour The precipitate dissolves readily in ammonium sulphide solution, yielding ammonium thiomolybdate which on acidification again deposits the brown trisulphide.

[1] Vigouroux, *Compt rend,* 1899, **129,** 1238

[2] Honigschmid, *Monatsh,* 1907, **28,** 1017 , Watts, *Chem Zentr* , 1908, 1, 598, Wedekmd, D R-P 294267

[3] Browning, *Amer J Set,* 1915, [4], 40, 349, Moir, *J Chem Metall Mm Soc S Africa,* **1916,16,** 191, StSrba Bohm and Vostrgbal, *Zeit anorg Chem* , 192O, **110,** 81

[4] Koppel, *Chem Zeit,* 1919, 43, 777, Malowan, *Zeit anorg Chem,* 1919, **108,** 73

[5] Komarowsky, *Chem Zeit,* 1913, 37, 957

[6] Moir, *loc cit* See also Kafka, *Zed anal Chem,* 1912, 51, 482, Poz/i Escot, *Bull Soc chtin* , 1913, [4], 13, 402, 1042

Fuchs,[1] describes a test for molybdenite whereby the mineral is dissolved in fused potassijpa hydroxide, yielding a red double sulphide, if this is dissolved in water, a series of colour changes, through blue, green, and yellow, takes place

A solution of ammonium molybdate in nitric acid becomes yellow-coloured on the addition of a few drops of sodium phosphate solution, and on keeping or warming a heavy yellow precipitate of ammonium phosphomolybdate[2] separates out

Molybdenum compounds impart to a bead of microcosmic salt or borax m the reducing flame a fine green colour, the bunsen flame is coloured green by molybdic acid

For the gravimetric estimation of molybdenum, the compound is converted into a neutral molybdate which is precipitated from aqueous solution as mercurous molybdate or lead molybdate, the latter method now being almost exclusively employed[3] In the former case, mercury is removed during ignition, and the residual molybdenum trioxide, which must not be heated to more than 425°, is weighed[4] If the molybdenum is to be estimated by way of the sulphide,[5] the latter may be directly precipitated by hydrogen sulphide from a solution acidified preferably with formic acid, or the gas may be passed into an ammomacal solution containing the molybdic acid, and the resulting solution of ammomum thiomolybdate decomposed with acid In either case the sulphide is usually converted into the trioxide by roasting and treatment with nitric acid, but it may be dried m carbon dioxide and weighed as such

It is also possible to estimate molybdenum by volatilisation of the trioxide in a current of carbon tetrachloride vapour[6]

Molybdenum trioxide can be separated from admixture with tungsten trioxide by dissolving it in a mixture of selenium oxychlonde and sulphuric acid[7]

Volumetric methods which have been proposed include the titration of the sesqui-compounds with potassium permanganate and methods based on the reactions $2MoO_3 + 2HI = H_2O$ -f

[1] *Informaciones y mem soc mg Peru,* 1918, 2O, 423

[2] Arsenates give a precipitate of similar appearance

[3] Raper, *Biochem J* , 1914, 8, 649, Taylor and Miller, *J Biol Chem* , 1915, 21, 255, Weiser, *J Physical Chem* , 1916, 2O, 640

[4] Treadwell, *Zeit Elehtrochem* , 1913,19, 219, Wolf, *Zeit angew Chem* , 1918, 31, i, 140

[5] Binder, *Chem Zeit,* 1918,42, 255, Wolf, *he cit,* Sterba Bohm and Vostrebal, *loc cit*

[6] Jannasch and Laubi, *J pr Chem* , 1918, [2], 97, 154

[7] Merrill, / *Amer Chem Soc* , 1921, 43, 2383

$Mo_2O_5 + I_2$, and $KIO_3 + Mo_2O_3 + 2HC1 = KC1 + Mo_2O_5 + IC1 + H_2O1$

Atomic Weight of Molybdenum—The determination of the atomic weight of molybdenum has been frequently made, but with varying results After an inaccurate determination by Berzehus, Svanberg and Struve obtained the number 92 5, which was confirmed by Berlin, and then generally adopted The investigation of Dumas [2] then showed that the number just quoted was distinctly too low, the average obtained by the reduction of the trioxide to the metal in a current of hydrogen being 95 9, the numbers in the different experiments varying, however, from 95 3 to 96 2 Debray [3] obtamed the number 95 5 by the same method, whilst Liechti and Kempe [4] by the analysis of the di-, tn-, and penta-chlondes of molybdenum obtained the same average number as Dumas, but in this case also the numbers found in the different experiments varied considerably Smith and Maas [5] found the number 96 O6, the method adopted being to heat pure sodium molybdate in a current of hydrogen chloride

$$Na_2MoO_4 + 4HC1 = 2NaCl + Mo(OH)_2OCl_2 + H_2O$$

The last two being volatile, only pure sodium chloride remains behind, and from the amount of this obtained from a given quantity of sodium molybdate, the above number was obtained as the average of ten closely agreeing experiments Seubert and Pollard, [6] by the acidimetnc determination of molybdic acid, obtained the number 95 92, and by the reduction of the trioxide to the metal in a current of hydrogen the number 96 O1 By a determination of the ratio Mo MoO_3, Vandenberghe [7] obtamed the value 96 O6, whilst Muller, [8] employing the same ratio, found the value 96 O29 The mean value of the best determinations is 96 O4 ± O O1 The atomic weight now adopted (1922) is 96 O [9]

[1] Jamieson, *J Amer Chem Soc*, 1917, 39, 246 For details of certain other methods, see Zinberg, *Zeit anal Chem*, 1913, 52,529, Marbaker, *J Amer Chem Soc*, 1915, 37, 86, Travers, *Compt rend*, 1917,**165,** 362, Hoepfner and Binder, *Chem Zeit*, 1918, 42, 315, 564, Scott, *J Ind Eng Chem*, 192O,12, 578, Camp and Marden, *ibid*, 192O,12, 998, Nakazono, *J Chem Soc Japan*, 1921, 42, 526

[2] *Ann Chim Phys*, 1859, [3J, **55,** 129

[3] *Compt rend*, 1868, **66,** 732 [4] *Annalen*, 1873, **169,** 36O

[5] *Zeit anorg Chem*, 1893, 5, 28O [6] *Ibid*, 1895, 8, 434

[7] *Mem Acad Belg*, 1898, **56** [8] *J Amer Chem Soc*, 1915, 37, 2O46

[9] Gerber, *Mon Sci*, 1917, [5], 7, 73, claims that molybdenum is not a simple substance, but is accompanied by *neo molybdenum* of higher atomic weight

TUNGSTEN § W = 184·0 At No. 74.

493 The minerals tungsten or heavy-stone, now termed scheelite or calcium tungstate, and wolfram (the *lupi spuma* of Agricola) were, up to the middle of the eighteenth century, both classed among the tin ores In 1781, Scheele proved that tungsten was composed of lime combined with a peculiar acid, and in the same year Bergmann stated that, in his opimon, this acid was a metallic calx Two years later the Spanish chemists Juan, Jose, and Fausto d'Elhujar,[1] showed that this same acid is contained in the mineral wolfram, combined with iron and manganese They also prepared metallic tungsten

Tungsten is not a common metal, being found only in a few minerals, some of which occur, however, in fairly large quantities The most important of these are wolfram, or wolframite, a tungstate of iron and manganese, $(Fe,Mn)WO_4$, found m Cornwall, in Cumberland, on Rona in the Hebrides, m County Wicklow, at Zinnwald, in many localities m the United States, in Burmah, and also in Austria-Hungary, Spam, Portugal, Queensland, New Zealand, Tasmania, Canada, and various parts of South America, and scheelite or calcium tungstate, $CaWO_4$ In addition to these, tungsten occurs in the following somewhat rare minerals wolframochre, WO_3, stolzite or lead tungstate, $PbWO_4$, ferberite, $FeWO_4$, which occurs m large quantities m Colorado, hubnente, $MnWO_4$, cuproscheelite, or cuprotungstite, $(Ca,Cu)WO_4$, chillagite,[2] $PbWO_4$,$PbMoO_4$, and tungstemte,[3] WS_2(?)

Metallic Tungsten is obtained from wolfram by a method which consists of three distinct stages[4] Sodium tungstate is first prepared by heating together a mixture of the ground ore and sodium carbonate When this operation is carried out under proper conditions the extraction is complete, and at the same time any tin and silica present are left insoluble The sodium tungstate thus formed is dissolved in water and separated from the oxides of iron, aluminium, manganese, tin, and silicon by filtration, and tungstic acid, H_2WO_4, is then precipitated by

[1] *A Chemical Analysis of Wolfram and Examination of a New Metal, which enters into its Composition* Translated from the Spanish by C Cullen, to which is prefixed a translation of Mr Scheele's analysis of the Tungsten, or heavy stone, with Mr Bergmann's supplemental remarks London, 1785

[2] Ullmann, *J Hoy Soc New South Wales* 1912, 46, 186

[3] Wells arid Butler, *J Washington Acad Sci*, 1017, 7, 596

[4] Hadfield, *J Iron Steel Institute*, 1903, 64, 38

means of acid In this step care is necessary to prevent the formation of hydrated tungstic acid, which is soluble The tungstic acid thus obtained is washed free from sodium salts and dried, and the resulting tungstic oxide is mixed with carbonaceous materials and submitted to a high temperature in crucibles for reduction to metal A well-fired crucible when opened should be uniform throughout, with the exception of a thin layer of tops or undecomposed tungstic oxide and carbon, which can be readily removed

Tungsten containing 99 per cent of the metal has been obtained by fusing tungsten trisulphide with lime [1]

Metallic tungsten may be prepared on the small scale by the reduction of the trioxide with carbon or in a current of hydrogen,[2] by the reduction of the chloride in hydrogen or sodium vapour, or by heating a mixture of the trioxide with one-tenth of its weight of sugar charcoal in the electric furnace, if care be taken that complete fusion of the metal does not occur, the latter is free from carbon [3] The metal thus obtained is as a rule fused on the surface, but is porous internally, and can be welded like iron It has been obtained in the form of a regulus by reducing the oxide with aluminium turnings and at the close of the reaction adding aluminium foil, and blowing in a stream of oxygen, or by adding liquid air to a mixture of the oxide and aluminium and igniting as m the thermite process [4] The powdered metal can be prepared also by heating the oxide with zinc and extracting the product with caustic soda solution,[5] and by the action of dilute acids on the alloys of manganese and tungsten [6] Electrolysis of the fused trioxide or salts, or of the latter in solution, has been found to yield metallic tungsten

Powdered tungsten, or the massive form obtained from it by fusion (although this process is not simple, the metal attacking the receptacle at the high temperatures necessary and becoming impure) are used in the manufacture of alloys, particularly ferrotungsten The massive form is not sufficiently ductile, nor indeed sufficiently pure, for use in the manufacture of tungsten filaments for electric incandescence lamps, so that until recently it was necessary to form the filaments of the powdered metal

[1] Weiss, *Zeit anoig Chem* , 1910, 65, 279
[2] Davis, *J Ind Eng Chem,* 1919, **11,** 2O1
[3] Moissan, *Compt rend* , 1896,**123,** 13 See also Menmcke, " Metallurgy c'es Wolframs," Beilin, 1911
[4] Stavenhagen, *Ber,* 1899, **32,** 1513, 3064
[5] Delepme, *Compt rend* , 190O, **131,** 184 [6] Arnvant, *xbid,* 1906,**143,** 594

together with an appropriate binding material Now,[1] however, the finely divided metal is formed into rods by pressure alone, and heated in hydrogen by slowly drawing it through a small heated coil, whereby it is converted into elongated crystals, it then responds to the mechanical treatment necessary to give malleability and ductility

In the form of a regulus, tungsten has a slightly darker colour than zinc, shows a crystalline (cubic[2]) structure, is harder than glass, (its degree of hardness depends on its previous treatment, and is higher if the metal is impure), its density is above 19, but figures varying between 18 7 and 21 4 have been obtained The metal is not magnetic, it has a mean specific heat O O340 between 15° and 93°, O O375 between 15° and 423°,[3] melts[4] at 3540° ± 3O°, and can be volatilised m the electric furnace, but is more refractory than iron, molybdenum, or uranium[5]

Tungsten has the smallest compressibility of any substance hitherto studied[6] It occupies a place m the potential series between antimony and mercury, and exhibits passivity under certain conditions[7] It is attacked by fluorine at the ordinary temperature with incandescence, and by chlorine at 25O-3OO°, but has no action on nitrogen or phosphorus at a red heat, when heated with carbon, silicon, or boron in the electric furnace, it yields crystalline compounds having a metallic lustre which are hard enough to scratch rubies It is slowly attacked by fuming sulphuric acid and by fused alkalis[8] At a red heat, the powdered metal burns in air, forming the trioxide,[9] but it is not readily oxidised by moist air, although slowly attacked by water containing carbon dioxide[10], it is readily oxidised when heated with oxidising agents such as lead dioxide or potassium chlorate Sulphuric, hydrochloric, and hydrofluoric acids act upon it slowly, but it is more readily dissolved by a mixture of nitric and hydrofluoric acids, the powdered metal is rapidly oxidised by aqua

[1] Gross, *Jahrb Radioaktiv Elektronik,* 1918, 15, 27O
[2] Debye, *Physihal Zeit,* 1917, **18,** 483
[3] Defacqz and Guichard, *Ann Chim Phys,* 1901, [7], **24,** 139 See also Worthing, *J Franklin Inst,* 1918,**186,** 7O7
[4] Langmuir, *Physical Rev,* 1915, 6, 138
[5] Moissan, *Compt rend,* 1906, **142,** 425
[6] Richards and Bartlett, *J Amer Chem Soc* , 1915, 37, 47O
[7] Fischer and Roderburg, *Zeit anorg Chem* 1913, **81,** 17O, Fischer and Rideal, *ibid* , Koerner, *Trans Amer Electrochem Soc,* 1917, 31, 221
[8] Ruder, *J Amer Chem Soc,* 1912, 34, 387
* Langmuir, *J Amer Chem, Soc* ,1913, 35, 105
[10] Wohler and Prager, *Zext Elektrochem* , 1917, 23, 199

regia, and dissolves in boiling potassium hydroxide solution with formation of potassium tungstate and evolution of hydrogen, whereas the fused metal is not attacked by aqua regia, but dissolves slowly m fused potash (Stavenhagen) Tungsten is utilised for the production of filaments for incandescence electric lamps which have a very high efficiency[x] It is also largely employed in the manufacture of tungsten steels, generally m the form of ferrotungsten In the finely-divided form, it is a valuable catalyst in Haber's process for the synthesis of ammonia

Alloys—Certain definite compounds of tungsten with other metals are believed to exist, ferrotungsten is, however, the most important[2] Cobalt forms the alloys[3] Co_6W and CoW

COMPOUNDS OF TUNGSTEN

TUNGSTEN AND OXYGEN

494 Tungsten forms two definite oxides[4] tungsten dioxide, WO_2, and tungsten trioxide, WO_3 These combine together to form compounds analogous to the blue oxides of molybdenum

A black gelatinous precipitate, considered to be the hydrated *sesqmoxide*, W_2O_3, is formed when potassium hydroxide solution, followed by a weak acid, is added to the product of reduction of tungsten hexachlonde with sodium amalgam It is unstable, being converted into the dioxide[5]

Tungsten Dioxide, WO_2 —This oxide is formed when a current of hydrogen is passed over the trioxide, WO_3, at a dull red heat It may also be obtained m the wet way by reducing the trioxide, mixed with hydrochloric acid, by means of metallic zinc, or by the action of water on the tetrachloride In preparing it m the diy way care is needed, as if the temperature be too high metallic tungsten is formed, whereas if the heat be not sufficient, the intermediate blue oxide is produced Tungsten dioxide is a brown powder of density 12 1, whichhas a copper-red colour when

[1] *J fur Gasbehuchtung,* 1906, 49, 756, *Nature,* 1907, 76, 156, *J Inst Elect Engineers,* 1907, 38, 211, Weber "Die elektrischen Metalifadengluhlampen," Leipzig, 1914, Muller, "Metalldrahtlampe," Halle, 1914, Luminer, "Grundlagen, Ziele und Grenzen der Leuchttechnik," Berlin, 1918

[2] Honda and Murakami, *Sci Hep Tohdku Imp Univ,* 1918, 6, 235, state that the only compound formed in tungsten steels has the formula Fe_8W

[3] Kreitz, *Metall u Erz,* 1922,19, 137

[4] For the thermochemistry and vapour pressures of the oxides, see van Liempt, *Zeit anorg Chem,* 1921,**120,** 267

[5] Hill, *J Amer Chem Soc,* 1916, 38, 2383

crystalline trioxide is employed for its preparation It is strongly pyrophonc, and must be cocfcd in hydrogen for some time before it is exposed to the air It is slightly soluble m concentrated hydrochloric acid and sulphuric acid, yielding purple solutions Oxidising agents convert it rapidly into the trioxide It dissolves in potash to form hydrogen and potassium tungstate

$$WO_2 + 2KOH - K_2WO_4 + H_2$$

Tungsten Tnoxide, WO_3 —This oxide occurs native as wolframme, a yellow powder found together with other tungsten minerals in Cumberland, near Limoges, in Connecticut, and in North Carolina In order to prepare the trioxide, the method already described may be adopted, or finely powdered wolfram may be digested for a long time with hydrochloric acid, the mixture frequently shaken, the acid renewed, and a little nitric acid added towards the end of the process to oxidise the iron This is continued until the acid has dissolved out the whole of the iron and manganese and the brown powder has become yellow-coloured The insoluble portion consisting of tungsten trioxide and undecomposed wolfram and quartz, after being well washed, is shaken up with a solution of ammonia which dissolves the liberated tungstic acid The solution is crystallised and the crystals are converted into the trioxide by ignition m the air Wohler converted the wolframite into calcium tungstate by fu&mg the finely powdered mineral for an hour with twice its weight of calcium chloride and then lixiviating, when calcium tungstate remained behind This was then decomposed by nitric acid, and tungsten trioxide obtained by igniting the yellow precipitate formed The native calcium tungstate (scheelite) can also be decomposed m this way

Tungsten trioxide is a bright canary-yellow coloured, amorphous powder which becomes dark orange on heating, but regains its bright yellow colour on cooling, it melts at 1473° A veiy slight admixture of sodium salt imparts to the oxide a greenish tint which no amount of oxidation can remove (Roscoe) It also becomes greemsh on exposure to light* Tungsten trioxide has been obtained m the crystalline state by Debray, by igniting a mixture of sodium tungstate and carbonate m a current of hydrochloric acid, when the trioxide is obtained m olive-green rectangular prisms which sublime at a white heat The crystalline trioxide has also been prepared by heating hydrated tungstic

[1] See van Liempt, *loc cit* , Burger, *Zett anorg Chem* , 1922,121, 240

acid with borax in a porcelain tube (Nordenskjold) The density of tungsten trioxide is 7 2 It is insoluble in water Keduction to the metal is effected by hydrogen or carbon, various oxides of indefinite conposition being formed intermediately[1] The amorphous oxide is soluble and the crystalline oxide insoluble in sulphur monochlonde [2]

TUNGSTIC ACID AND THE TUNGSTATFS

495 Tungsten trioxide is an acid-forming oxide, and yields two tungstic acids, the normal acid, H_2WO_4, and metatungstic or tetratungstic acid, H_2W_{4013}, the salts of which correspond to the tetrachromates and tetramolybdates In addition to the salts corresponding to these acids, a large number of other tungstates analogous to the polychromates and polymolybdates have been prepared, the formulae ascribed to which are given in the following table [3]

M^WO,	== $M_{<2}O,WO_3$	$M'_2W_8O_{25}$	= w_tO,SWO_a
$1F_8W_2O_7$	== $M^I.O,2WO_3$	$M«_4W_6O_{17}$	= $2M^I_2O,5WO_3$
M W V	= M^O^WOg	$W_BW_7O_u$	= $3M^I_2O,7WO_3$
MWAa	== BPgO^WO,	$M^I_8W_3O_{13}$	= $4M^I_2O,3WO$,
$M'_2W_6O_{16}$	= M'jO.SWO,	$W_{10}W_{12}O_n$	= $5M^I_2O,12WO_3$
W_2Wfi_{iB}	= $WP_8O,6WO_8$		

Many of these crystallise with a number of molecules of water, forming well-developed crystals The salts of the formula $M^r{}_{10}W_{12}O_{41}$ are termed paratungstates Copaux[4] formulates the paratungstates as $R_5[H(W_2O_7)_3]$,aq, whilst Rosenheim[rj] formulates them as $R_5H_5[H_2(WO_4)_6]$,aq

The tungstates also yield complex salts with many other acidic oxides analogous to the complex molybdates

Tungstic Acid, H_2WO_4 — When a solution of a tungstate is

[1] Davis, *J Ind Eng Chem* , 1919, **11,** 2O1

[2] Smith and Fleck, / *Amer Chem Soc* , 1899, 21, 10O8

[3] See Schaefer, *Zeit anorg Chem,* 1904, 38, 142, where the literature is quoted Acids containing a complex radicle composed of one kind of anionogen radicle only are termed " iso poly acids ", those composed of two or more different anionogen radicles are termed " hetero poly acids" The exact quantitative examination of these bodies is rendered difficult by the high atomic weight of tungsten, for this and other reasons there is still considerable uncertainty regarding the formulation of the complex tungstic acids

[4] *Compt rend,* 1913,**156,** 1771

[6] *Zett anorg Chem,* 1916, 96, 139 See also Prandtl, *Ber* , 1915, 48, 692

precipitated by an acid in the cold, a white precipitate is gradually[1] thrown down consisting of hydrated tungstic acid, H_2WO_4,H_2O[2] This is soluble in water, possesses a bitter taste, and reddens litinus If, on the other hand, an excess of hot acid be used, anhydrous tungstic acid, H_2WO_4, separates as a yellow powder, insoluble m water and in all acids except hydrofluoric acid If pure tungsten hexachloride be exposed to the action of moist air, the red monoxychlonde is first formed, and this soon passes into a fine flocculent mass of white tungstic acid

The tungstates are insoluble m water, except those of the alkali metals, and even of these, some tungstates of potassium and ammonium are only sparingly soluble The tungstates of the alkahne-earthmetals, and of the heavy metals are mostly amorphous powders, but they may be obtained crystalline by double decomposition at a high temperature

Metatungstic Acid,

$$H_2W_4,8(?85)H_2O, \text{ i e, } H_6H_4LH_2(W_2O_7)_6,]21H_2O$$

—The salts of this acid were discovered by Marguentte,[3] but the acid was first prepared by Scheibler[4] For this purpose the barium salt is decomposed by dilute sulphuric acid or the lead salt with hydrogen sulphide Metatungstic acid crystallises in small, yellow octahedra which efHoresce m the air On ignition it is converted into the trioxide It is readily soluble in water and the solution possesses a harsh, bitter taste When the solution is concentrated by boiling, a white hydrate is deposited and afterwards the trioxide separates The metatungstates of the alkali metals are formed when the ordinary tungstates are boiled with tungstic acid until the filtrate gives no precipitate on addition of hydrochloric acid[5] The metatungstates of the other metals are, as a rule, easily soluble in water, and are best prepared by double decomposition of the barium salt with the corresponding sulphate or carbonate The warm solutions usually yield the salts in amorphous masses when evaporated, but when concentrated over sulphuric acid they frequently crystallise The metatungstates possess a bitter taste, and are not precipitated by acids, on long boiling ordinary tungstic acid is deposited

[1] Lottermoser, *Kolloid Zeit,* 1914,**15,** 145

[2] See, however, Huttig and Kurre, *Zeit anorg Chem,* 192Ji, **122,** 44, also Burger, *ibid* , 1922,**121,** 240

[3] *Ann Chim Phys* , 1846, [3], 17, 475 [4] *J pr Chem,* **1861,** 83, 310

[5] **Copaux,** *Ann Chim Phys,* 1909, [8], 17, 2O7, *Compt rend,* **1913,156,** 71

Colloidal Tungstic Acid—This modification of tungstic acid was discovered by Graham,[1] and is obtained by dialysmg a 5 per cent solution of sodium tungstate to which sufficient hydrochloric acid has been added to combine with the sodium The liquid remaining m the dialyser possesses a bitter, astringent taste and does not gelatinise on the addition of acids, even on boiling On evaporating m a vacuum, a transparent, gum-like mass is obtained, and this can be heated to 2OO° without losing its solubility, whilst at a red heat it is transformed into tungsten trioxide, losing 2 4 per cent of water When moistened with water the colloidal acid becomes pasty and adhesive like gum, dissolving completely in one quarter of its weight of water It can also be obtained by dialysmg a solution of freshly precipitated tungstic acid in oxalic acid[2] The photo-chemical and other behaviour of colloidal tungstic acid suggest that it exists m two forms

Sodium Tungstales—The *normal salt,* $Na_2WO_4,2H_2O$, is prepared like the potassium salt, and is obtained on the large scale by fusing wolfram with soda ash It crystallises m thm, lustrous, rhombic prisms which dissolve m four parts of cold and in two parts of boiling water[3] The solution possesses a bitter taste and has an alkaline reaction The crystals do not undergo alteration m the air, and they are insoluble m alcohol, a deca-hydrate is also known When heated to 2OO° the salt becomes opaque and loses its water, and fuses at 665°

Sodium Paratungstate, $Na_{10}W_{12}O_{41},28H_2O$—This salt, which is the one known cominercially as tungstate of soda, is prepared on the large scale by roasting wolframite with soda ash and lixivi-ating the fused mass The boiling solution is nearly neutralised with hydrochloric acid and allowed to crystallise at the ordinary temperature, when the salt separates in large trichnic crystals At a higher temperature crystals containing 25 and 21 molecules of water are formed The salt can also be prepared by electrolysis of solutions of the normal tungstate[4] It is sometimes used in place of sodium stannate as a mordant in dyeing and calico printing, and is also employed for rendering cotton, linen, " flannelette," etc , uninflammable[5] Rosenheim[6] formulates

[1] *Journ Chem Soc* , 1864,**19,** 325

[2] Pappada, *Qazz,* 1902, 32, 11, 22 Compare Sabaneeff, *Zeit anorg Chem* , 1897, 14, 354 See also Wassiljewa, *Zeit wiss Photochem* , 1013, 12, 1

[3] Mangnac, *Ann Chim Phys,* 1863, [3], **69,** 39

[4] Lottermoser, *Kolloid Zeit,* 1922, 3O, 346

[5] Versmann, *Reports of the Junes of the Exhibition of* 1862

[6] *Zeit anorg Chem,* **1916, 98, 139** Mangnac considered that the para tungstates **obtained by him were of the** form $3Na_2O,7WO_3$

the compound $Na_{10}HJH_4(WO_4)_6(W_2O_7)_3],24H_2O$ The anhydrous salt melts at 7O5 8° ^

Sodium Metatungstate (Tetratungstate), $Na_2W_{4013},10H_2O$, is formed by prolonged boiling of the normal salt with tungsten trioxide[x] It ciystallises m efflorescent octahedra piobably belonging to the regular system Cold water dissolves 10 69 times its weight of tins salt, there is a rapid increase in solubility with rise of temperature It loses its water at a red heat (Mangnac and Scheibler), fusing at 7O6°

Tungstates typified by the salt, $4Na_2O,10WO_3,23H_2O$ (which melts, when anhydrous, at 68O 8°), have also been found to constitute a definite series[2] The salt, $9Na_2O,22WO_3$, melts at 683 3°

Potassium Tungstates —The *normal salt* K_2WO_4,[3] is obtained by adding tungsten trioxide little by little to its own weight of fused potassium carbonate On cooling a solution of the fused mass in hot water, normal potassium tungstate crystallises in large, acicular, anhydrous crystals, or in large, prismatic crystals, $K_2WO_4,2H_2O$ (Mangnac) When the noimal salt is treated in aqueous solution with an acid, or when tungsten trioxide is added to its boiling solution until no more dissolves, glistening scales of the *paiatnngstate,* $K_{10}W_{12}O_{41},l]H_2O$, are deposited, metatungstate is formed at the same time The paratungstate dissolves moie leadily in hot than in cold water, and the solution has an acnd taste and acid reaction When alcohol is added to the aqueous solution a precipitate is formed, this dissolves on waiming, but, on cooling, the solution deposits scales of *potassium metatungstate,* $K_2W_{4013},5H_2O$, a second hydrated salt containing $8H_2O$, crystallising in octahedra, is obtained from the mother-liquor of the normal tungstate The following compounds have also been described $K_2O,2WO_3,2H_2O$, $2K_8O,5WO_8,4H_2O$, $K_2O,3WO_3,2H_2O$, $K_2O,8WO_3$

Ammonium Tungstates —The normal salt is extremely unstable[4] When a solution of tungstic acid in ammoma is allowed to evaporate over calcium oxide, warty concretions of the salt $2(NH_4)_2O,3WO_3,3H_2O$ are sometimes deposited, which easily give off ammoma The usual product is, however, the *paratungstate,* $5(NH_4)_2O,12WO_3,11H_2O$ [or possibly $3(NH_4)_2O,7WO_3,6H_2O$],

[1] **See also Lottermoser,** *loc cit,* **for an electrolytic method**

[2] **Smith,** *J Amer Chem Soc* **, 1922, 44, 2O27**

[3] **Potassium tungstate is trimorphous, see Amadon,** *Atti R Accad Ltncet,* **1914, [5], 23, 1, 800**

[4] **Rosenheim and Jacobsohn,** *Zeit anOrg Chem,* **1906, 6O, 297**

formulated by Rosenheim as $(NH_4)_{10}H_4[H_4(WO_4)_6(W_2O_7)_3],7H_2O$ If, however, the ammomacal solution of the trioxide be allowed to evaporate whilst warm, monoclmic crystals of $(NH_4)_{10}W_{12}O_{41},5H_2O$ separate out When tungsten trioxide is boiled with ammoma, tetragonal prisms of *ammonium meta-tungstate,* $(NH_4)_2W_4,8H_2O$, *ic* $(NH_4)_OH_4[H_2(W_2O_7)_6],2lH_2O$, are obtained These are very soluble, and effloresce quickly on exposure to the air A hexahydrate is also known Besides these, many other ammomum tungstates have been prepared (Marignac), as well as compounds of these with ammonia, and ammomacal derivatives of other tungstates[1] Comineicial ammomum tungstate is stated[2] to possess the formula $(NH_4)_4W_6O_{17)}2H_2O$

Normal Calcium Tungstate, $CaWO_4$—This occurs native as scheehte in vitreous, yellowish-white, tetragonal pyramids Its chief source is Australia, but it is also met with m the following localities Zmnwald, Caldbeck Fell in Cumberland, Piedmont, Dalecarlia, m the Vosges, at Huntingdon m Connecticut, and at the Mammoth mining district m Nevada The crystals usually contain iron, and are found m crystalline rocks in connection with tin-ore, topaz, apatite, wolfram, etc

It is prepared artificially as a white, insoluble precipitate by mixing solutions of calcium chloride and a normal tungstate, and can be obtained in the crystalline form of scheehte by heating the precipitate mixed with lime in a current of hydrogen chlonde If a hot solution of metatungstic acid be saturated with calcium carbonate, calcium metatungstate, CaW_410H_2O, is obtained crystallising in small, tetragonal octahedra [3]

Lead Tungstate, $PbWO_4$, occurs as stolzite at Zmnwald in Bohemia, at Bleiberg m Cannthia, in Chih, and at Southampton, Massachusetts It crystallises in translucent, tetragonal pyramids having a density of 7 87 to 8 13

Ferrous Tungstate, $FeWO_4$, occurs as wolfram, $(Fe,Mn)WO_{4\%}$ which contains manganese as an isomorphous constituent, in Cornwall, Cumberland, France, the Erzgebirge, and various parts of the United States Wolfram crystallises in the monoclmic system in dark grey or brownish-black prisms having a metallic lustre and a density of 7 3

[1] Taylor, *J Amer Chem Soc,* 1902, 24, 629, Bnggs *Journ Chem Soc* 1904, 85, 672

[2] Arnold, *Zett anorg Chem,* 1914, 88, 74

[3] See also Smith, *J Amer Chem Soc* , 1922, 44, 2O27.

Manganese Tungstate, $MnWO_4$, is found as hubnente in Nevada in a vein from three to four feet wide

Chromium Tungstates—A number of such compounds have been described, but there is little doubt that some are merely mixtures of simplex compounds [x]

Tungsten Tungstates —By the partial reduction of tungsten trioxide a number of oxides of tungsten have been prepared, having a composition intermediate between that of the dioxide and trioxide These have a blue or purple-red colour, and are probably combinations of the acidic trioxide with the more basic dioxide Thus by the action of hydrogen on the trioxide at 25O° the compound $W_3O_8 = 2WO_3,WO_2$ is formed, which has a deep blue colour, the same oxide, when prepared by heating ammomum metatungstate to a red heat, has a purple-red colour and metallic reflex [2] Other blue oxides having the compositions $W_2O_5 = WO_2,WO_3$, $W_{40u} = 3WO_3)WO_2$, $W_6O_M = 4WO_3)WO_2$ have been described, m addition, Desi has obtained oxides containing less oxygen than the dioxide, by the action of concentrated sulphuric acid on metallic tungsten under suitable conditions It is therefore uncertain whether the blue oxide is a chemical individual or an admixture Hydrated blue oxides are readily obtained by reduction of tungsten trioxide or tungstic acid, *e g*, with stannous chloride, hydrogen iodide, or alcohol [3]

496 *Tungsten Bionzes*—These remarkable compounds, obtained by the partial reduction of the alkali and alkaline-earth tungstates, are usually regarded as compounds of the tungstates with tungsten dioxide, but their exact constitution is as yet unknown Owing to their bronze-like appearance and insolubility in acids and alkalis, they have been employed as bronze powder substitutes

They are scarcely affected by aqua regia, but are oxidised by ammoniacal silver nitrate solution, a reaction which is utilised for their analysis Owing to their insolubility they can be freed from metallic tungsten and its oxides only by successive

[1] Lotz, *Ann,* 1864, **91,** 49, Lefort, *Ann Chim Phys,* 1879, [5], **17,** 47O, Smith and Dieck, *Zeit anorg Chem,* 1894, 5, 13, Kantschev, *J Buss Phys Chem Soc* , **1914, 46, 729**

[2] Desi, ***J*** *Amer Chem Soc* , 1897,**19, 213,** see also Hallopeau, *Compt rend* , 1898, **127, 57,** *Bull Soc chim,* 1899, [3J, **21,** 267, Allen and Gottschalk, *Amer Chem* ***J*** , **1902, 27,** 328

[3] Allen **and** Gottschalk, *Auer Chem* ***J*** , **1902, 27, 328,** Benrath, *Zeit wiss Photochem,* **1917,16, 253**

extractions with aqua regra, hydrochloric acid, potassium carbonate, and water

Tungsten Sodium Bronze was first obtained by Wohler by the reduction of solium tungstate with hydrogen, and may also be obtained by substituting coal-gas, zinc, iron, or tin for hydrogen, or by means of electrolysis It forms fine golden cubes, which have a specific gravity of 6 617, and conduct electricity well On ignition in the air, it oxidises and fuses It is not attacked by any acid except hydrofluoric acid, nor is it acted upon by alkalis except on fusion [1] According to Philipp,[2] the products are a mixture of different compounds, the relative propoitions of which vary according to the method of preparation and the nature of the original tungstate The substance obtained by heating the ditungstate in hydrogen, which was formerly supposed to have the composition $Na_2W_3O_9$, is, according to Philipp, $Na_5W_6O_{18}$, and has a golden-yellow colour By the electrolysis of fused sodium paratungstate a blue bronze, $Na_2W_5O_{15}$, is obtained, which forms dark blue cubes or plates having a red reflex A purple-red bronze, $Na_2W_3O_9$, is obtained by strongly heating a mixture of 12 9 grams of sodium carbonate and *68* 9 grams of tungsten trioxide with 2O grams of tinfoil, and a reddish-yellow bronze, $Na_4W_6O_{16}$, by fusmg 6O-8O grams of a mixture of two molecular proportions of sodium tungstate and one of the trioxide with 3O grams of tinfoil for two hours It forms reddish-yellow cubes and yields a brownish-yellow powder

Tungsten Potassium Bronze is obtained m a similar manner to the sodium bronzes, but only one compound [3] appears to exist, K_2W_4 Bronzes containing lithium and rubidium have also been prepared as well as a number of mixed bronzes containing both sodium and potassium or an alkali metal along with one of the alkaline-earth metal groups [4]

497 *Phosphotungstic Acids* —Tungstic acid combines with phosphoric, arsenic, antimomc, and vanadic acids to form complex substances analogous to the corresponding molybdic derivatives A very large number of these have been prepared, the relation R_2O_5 WO_3 varying from 1 7 to 1 24 *Phospho-*

[1] Knorre, *J pr Chem*, 1883, [2], **27,** 63

[2] *Ber* , 1882,15, 499

[3] Schaefer, *Zeit anorg Chem*, 1904, 38, 142, where references to the literature are given, Hallopeau, *Compt rend* , 1898, **187,** 57, *Bull Soc chtin* , 1899, [3], **21,** 267

[4] See Engels, *Zeit anorg Chem*, 1903, 37, 125, Hallopeau, *Compt rend*, 1898,**127,** 512

duodeetiungstic acid, $H_5PW_{12}O_{40},xH_2O$, is obtained by evaporating a mixture of the requisite quantities of orthophosphoric acid and metatungstic acid, or by the exact decomposition of the barium salt with sulphuric acid or of the mercurous salt with hydrochloric acid It crystallises in tetragonal pyramids containing water of crystallisation, the amount of which is variously stated by different investigators Phosphotungstic acid is largely used as a reagent for the precipitation of the alkaloids, proteins, and certain of their hydrolysis products, and also for the detection of potassium and ammonium salts, with which it yields insoluble precipitates For this purpose it is prepared by acidifying a solution of 4 parts of sodium tungstate and 1 of common sodium phosphate with sulphuric acid and extracting the concentrated solution with ether, in which phosphotungstic acid is readily soluble[1] Two sodium salts are known, having the formulae $Na_2HPW_{12}O_{40},xH_2O$ and $Na_3PW_{12}O_{40},xH_2O$, and are obtained by heating together solutions of sodium hydrogen phosphate and tungstate In presence of an excess of hydrochloric acid the former salt is obtamed m yellow crystals, whilst when the acid is gradually added with stirring until crystallisation cominences the latter salt separates in transparent colourless octahedra.

The number of complex phosphotungstates and similar compounds is very large, and many of them crystallise well[2]

498 *Silicotungstic Acids*—These peculiar compounds were discovered and investigated by Mangnac,[3] but the composition of many of them is doubtful

Silwodeeitungstic Acid,

$$H_8W_{10}SiO_{36},3H_2O \ (= 4H_2O,SiO_2,10WO_3,3H_2O)$$

—To prepare this acid, gelatinous silica is boiled with ammomum poly tungstate and the solution evaporated, ammonia

[1] Winterstein, *Chem Zeit,* 1898, **22,** 539

[2] See Scheibler, *Ber,* 1872, 5, 8O1, Sprenger, *J pr Chem,* 188O, [2], **22,** 48, Gibbs, *Amer Chem J,* 188O, 2, 217, 281, 1882, 4, 377, 1883, 5, 361, 391, 1885, 7, 31, 392, Kehrmann, *Ber,* 1887, **2O,** 18O5, 1811, 1891, **24,** 2326, 1892, **26,** 1966, *Annalen,* 1888, **246,** 45, *Zeit anorg Chem,* 1891, 1, 428, Drechsel, *Ber,* 1887, **2O,** 1452, Pechard, *Compt rend,* 1889, **109,** 3O1, 1890, **110,** 754, Hallopeau, *Compt rend,* 1896, **123,** 1065, Kehrmann and Riittimann, *Zeit anorg Chem,* 1899, **22,** 285, Rogers, / *Amer Chem Soc* , 1903, **26,** 298, Copaux, *Ann Chim Phys,* 1909, [8], 17, 251, Rosenheim, *Zeit Elektrochem,* 1911, 17, 694, Rosenheim and Jaemeke, *Zeit anorg Chem,* 1912, 77, 239, 1917, **101,** 254, Copaux, *Compt rend,* 1913, **166,** 71, Prandtl and Hecht, *Zeit anorg Chem,* 1916, **92,**198, Sweeney, *J Amer Chem Soc* , 1916, 88, 2377

[3] *Ann Chim Phys,* 1864, [4], 3, 5

being added from time to time The *ammonium salt*, $(NH_4)_8SiW_{10}O_{36},8H_2O$, is thus obtained in short, rhombic prisms which are soluble in water, the solution is then precipitated by silver nitrate, and the precipitate washed and decomposed by hydrochloric acid On evaporating the filtrate in a vacuum the acid is left as a yellowish, glassy mass, and on exposure to air splits into fragments, which then deliquesce Its salts have not been carefully examined

On dissolving it in water and evaporating the solution, some silicic acid separates out, and the thick mother-liquor yields short trichnic prisms of *octabasic tungstosilicic acid*, $H_8W_{12}SiO_{42},2OH_2O$ (= $4H_2O,SiO_2,12WO_3,2OH_2O$), which are readily soluble in water and alcohol It forms both normal and acid salts [1]

Silicoduodecitungstic or *Silicotungstic Acid* was formulated by Mangnac as an octabasic acid,

$$H_8SiW_{12}O_{22},29H_2O \quad (= 4H_2O,SiO_2,12WO_3,29H_2O),$$

but according to Wyrouboff[2] it is tetrabasic, and has the formula $2H_2O,SiO_2,12WO_3,3lH_2O$, the normal salts of Mangnac being basic salts and his acid salts m reality the normal salts All the salts contain water of crystallisation, and m view of the uncertainty as to their constitution are at present best formulated in terms of the oxides The salts of this acid are formed by boiling gelatinous silicic acid with the polytungstates of the alkali metals To obtain the acid the salts are precipitated with mercurous nitrate and the washed precipitate is decomposed by hydrochloric acid It crystallises below 40° in large tetragonal pyramids of the formula $H_8SiW_{12}O_{42},29H_2O$, above 40°, or in presence of hydrochloric acid, in rhombohedral forms, $H_6SiW_{l2}O_{42},22H_2O$, and readily dissolves in water, alcohol, or ether Silicotungstic acid is a valuable reagent for alkaloids

The salts, with the exception of the mercurous salt and a few others, are soluble in water Boiling hydrochloric acid converts the normal salts into acid salts without decomposing them further (Mangnac), whilst alkalis decompose their solutions with the separation of silicic acid They have been very thoroughly examined both by Mangnac and by Wyrouboff

Potassium Sihcotungstate —Three distinct salts are known [3] The

[1] See, however, Kehrmann, *Zeit anorg Chem*, 1904, 89, 98, Rosenheim and Jaemoke, *ibid*, 1912, 77, 242, 1917, **101,** 240, Copaux, *Compt rend*, 1913, **156,** 71 [2] *Bull Soc franc Min*, 1896,19, ?19

[3] See also van Liempt, *Zeit anorg Chem*, 1922,**122,** 175

salt $4K_2O,SiO_2,12WO_8$ $J4H_2O$ forms hard, granular crusts, consisting of prisms closely resenting cubes, $2K_2O,SiO_2,12WO_3,18H_2O$ forms transparent, glistening, hexagonal crystals, and $3K_2O,2SiO_2,24$:WO3,$3OH_2O$ crystallises in monocknic prisms

Mangnac formulates the first of these as the normal salt, $K_8SiW_{12}O_{42},14H_2O$, and the others as acid salts, $H_4K_4SiW_{12}O_{42},16H_2O$ and $2H_6K_3SiW_{12}O_{42},25H_2O$, whereas Wyrouboff regards them as a basic salt,

$$K_4SiW_{32}O_{40},4KOH,12H_2O,$$

a normal salt, $K_4SiW_{12}O_{40},18H_2O$, and a double salt,

$$K_4SiW_{12}O_{40},K_2H_2SiW_{12}O_{40},29H_2O$$

Zircono-,[1] mangano-,[2] boro-,[3] bismutho-,[4] and silico-vanadio-tungstates[5] have also been obtained

Pertungstic Acid—When a solution of sodium paratungstate is boiled for a few minutes with hydrogen peroxide, a yellowish solution is obtained, which no longet gives a precipitate with nitric acid[6] When the solution is allowed to evaporate in a vacuum, small white crystals having the formula $NaWO_4,H_2O$ are deposited, which are the sodium salt of the unknown pertungstic acid, HWO_4 The same salt is formed m solution by the electrolysis of slightly acid solutions of sodium tungstate[7] More highly oxidised compounds are formed by the action of caustic alkali and hydrogen peroxide on a solution of a pertungstate,[8] the unstable salts, Na_2O_2,WO_4,H_2O_2, $Na_2O_2,WO_4,H_2O_2,(Na_2O_2)_2WO_4,7H_2O$, and K_2O_4,WO_4,H_2O having been isolated in this way Aqueous solutions of pertungstic acid and hydrogen peroxide appear to contain the unstable acids[9] $WO_2(O_2H)_2$ and $WO_2(O_2H)(OH)$

TUNGSTEN AND THE HALOGENS

499 *Tungsten Hexafluoride*, WF_6, is formed by the action of anhydrous hydrofluoric acid on tungsten hexachlonde in the cold, and can also be prepared by the action of arsenic tri-

[1] **Hallopeau, *Bull Soc chim*, 1896, [3], 15, 917**
[2] **Just, *Ber* , 1903, 36, 3619**
[3] **Rosenheim andJaenicke, *Zeit anorg Chem*, 1912,77, 239, Rosenheim and Schwer, *ibid* , 1914, 89, 224**
[4] **Sweeney, *J Amer Chem Soc* , 1916, 38, 2377**
[5] **Fnedheim and Henderson, *Ber* , 1902, 35, 3242**
[6] **Pechard, *Compt rend* , 1891,112, 106O**
[7] **Thomas, *J Amer Chem Soc* , 1899, 21, 373**
[8] **Mehkoff and Pissarjewsky, *Ber* , 1898, 31, 632**
[9] **Pissarjewsky, *J Russ Phys Chem Soc*, 1902, 34, 472**

fluoride or antimony pentafluonde on the hexachlonde The preparation by the last of these methods can be carried out m glass vessels and proceeds according to the equation

$$WC1_6 + 3SbF_5 = WF_6 + 3SbF_3Cl_2$$

Antimony pentafluonde is gradually added to the tungsten hexachlonde contained in a flask until no further reaction occurs, and the contents of the flask are finally heated to 90° The hexafluonde volatilises, and is condensed IN a receiver cooled by a freezing mixture of alcohol and solid carbon dioxide A trace of chlorine is present, which can be removed by allowing the liquid m the receiver to boil for a moment [1]

Pure tungsten hexafluonde is a colourless gas, which has the normal density corresponding with the formula WF_6, and is therefore about ten times as heavy as air It condenses to a faintly yellow liquid which boils at 19 5° and solidifies at 2 5° to a snow-white mass It is at once decomposed by water and fumes in the air, nearly all the commoner metals, except gold and platinum, are attacked by it It is absorbed by alkali fluorides and reacts violently with ammonia

Tungsten Oxytetrqfluoride, WOF_4, can be prepared by the action of anhydrous hydrofluoric acid on the oxytetrachlonde m the cold, or by heating tungsten trioxide with lead fluoride to redness m an electric furnace It sublimes m white plates, melts at 110°, and boils at 185—190° It is decomposed by water, and is soluble IN chloroform, absolute alcohol, or benzene It appears to unite with ammoma, forming an orange-coloured substance (Ruff)

Tungsten Dioorydifluonde, WO_2F_2, has not been prepared pure, but is formed m small amount by the action of moisture on the vapour of the oxytetrafluonde Double salts with the alkali fluorides, such as $2KF,WO_2F_2,H_2O$, have, however, been prepared by the action of hydrofluoric acid on the tungstates [2] A double salt of the formula KF,WO_2F_2,H_2O is also known

500 Four compounds of tungsten and chlorine are known, viz

Tungsten dichloride	$WC1_2$
Tungsten tetrachloride	$WC1_4$
Tungsten pentachlonde	$WC1_5$
Tungsten hexachlonde	$WC1_6$

[1] **Ruff and Eisner, *Ber* , 1905, 38, 742, Ruff, Eisner, and Heller, *Zeit anorg Chem* , 1907, 52, 256**

[2] **Mangnao, *Ann Chim Phys*, 1863, [3], 69, 7O**

Tungsten Dichloride, $WC1_2$—This body may be obtained m pale grey crusts by reducing the hexachloride m hydrogen at a moderately high temperature, or by reduction in a stream of nitrogen with powdered aluminium and quartz [1] It is, however, best prepared by heating the tetrachloride in a current of carbon dioxide at the temperature of a moderately hot zinc bath The dichloride is a non-volatile, loose, grey powder without lustre or crystalline structure It alters perceptibly on short exposure to the air and dissolves slightly in water, forming a brown solution The remainder is converted into the brown oxide, a slow evolution of hydrogen occurring (Roscoe) In view of the fact that a compound of the formula $W_3C1_6,HC1,4\ 5H_2O$ has been prepared,[2] the dichloride may perhaps be regarded as having the composition W_3C1_6

Tungsten Trichloride—Although this compound has not been obtained, double salts of the form $M_3W_2C1_9$ have been prepared by reduction of tungstic acid in hydrochloric acid solution in presence of alkali chloride [3]

Tungsten Tetrachloride, $WC1_4$, is produced by the incomplete reduction of the hexachloride or pentachlonde by hydrogen, and forms the non-volatile residue obtained by the distillation of the hexachloride in hydrogen In order to obtain it in the pure state a mixture of hexa- and penta-chlonde is distilled at a low temperature from a bath of sulphuric acid in a current of dry hydrogen or carbon dioxide, and the volatile pentachlonde poured back again once or twice over the residue to convert into the tetrachloride the lower chlorides or metal which are also formed Tungsten tetiachloride is a loose, soft, crystalline powder of a greyish-brown colour It is highly hygroscopic, though not so much so as the pentachlonde, and is partially decomposed by cold water into the brown oxide and hydrochloric acid The tetrachloride is non-volatile and infusible under ordinary pressure, but on heating it decomposes into penta-chlonde, which distils off, and dichloride, which remains behind On heating in hydrogen to a temperature above the melting point of zinc the tetrachloride is reduced to metallic tungsten, some of which is deposited as a black, tinder-like powder and undergoes spontaneous ignition on exposure to air (Roscoe) By reduction of an acidified solution of tungstic acid in presence of alkali chloride, Olsson [4] has prepared the compound $K_2W(OH)C1_5$

[1] **Lindner and others, *Ber* , 1922, 55, *[B],* 1458**
[2] **Hill, *J Amer Chem Soc* , 1917, 38, 2383**
[3] **Olsson, *Ber,* 1913, 46, 566, Rosenheim and Dehn, *ibid,* 1915, 48, 1167**
[4] ***Loc cit***

Tungsten Pentachloride, $WC1_5$ —This compound is formed by the incomplete reduction of the hexachlonde in a current of hydrogen If the temperature be kept but slightly above the boiling point of the hexachlonde, the dark red colour of its vapour is seen to disappear and a light greenish-coloured vapour takes its place, and this soon condenses either to black drops or to long, lustrous, black, needle-shaped crystals After two or three distillations in hydrogen a pure volatile product is obtained For the production of the pentachloride, it is, however, more convenient to reduce the hexachlonde at a higher temperature, when a further loss of chlorine takes place, the solid non-volatile tetrachloride remaining behind and the volatile pentachloride distilling over The latter compound only requires redistillation in order to be obtained in the pure state Tungsten pentachloride crystallises in long, black, lustrous crystals, but if quickly condensed the crystalline powder possesses a dark green colour, resembling potassium manganate It melts at 248°, boils at 275 6°, has the normal vapour density at 35O°, and is extremely hygroscopic, the crystals becoming instantly covered with a dark golden-green film on exposure to air, whilst the small particles are converted into liquid The crystals do not decrepitate on cooling like those of the hexachlonde On treatment with large quantities of water, the pentachlonde forms an olive-green solution, although the greater part is at once decomposed into the blue oxide and hydrochloric acid

Electrolysis of a solution of the hexachlonde^x in absolute alcohol gives a compound of qumquevalent tungsten of the formula $[WC1_2(OC_2H_5)_3]_2$

Although the oxychloride, $WOCl_3$, is unknown, two series of *chlorotungstttes* have been prepared, having respectively the formulae [2] M_2WOC1_5 and $MWOCl_4$

Tungsten Hexachlonde, $WC1_6$ —This substance is prepared by heating metallic tungsten in an excess of dry and pure chlorine, platinum black may be employed as a catalyst [3] It is necessary for the preparation of the pure compound that every trace of oxygen and of moisture be excluded, as otherwise some red oxychlonde is invariably formed, and this cannot easily be separated from the hexachlonde by distillation Metallic tungsten

[1] Fischer and Roderburg, *Zeit anorg Chem,* **1913, 81, 17O, Fischer** and Michiels, *ibid* , **1913,** 81, **102**

[2] Collenberg, *Zeit anorg Chem,* 1918, **102,** 247, *Arkiv Kem. Mm Geol,* 1918, 7, No 5, 1

[3] **Hill,** *J Amer Chem Soc* , 1916, **38, 2383**

takes fire at a moderate teat in dry chlorine, and the action goes on by itself until all the c h i n e has disappeared

In order to obtain the hexachlonde in quantity, the metal is first lgmted in a current of dry hydrogen, then the hydrogen is completely displaced by a current of dry carbon dioxide, and lastly chlorine free from air substituted, and the tube or retort moderately heated At the cominencement of the operation a slight sublimate of red, needle-shaped crystals of the oxychlonde is frequently formed owing to the unavoidable presence of traces of oxygen, but this is easily driven to the end of the tube beyond the point at which it is intended to collect the hexachlonde On raising the temperature of the metal, a granular sublimate of dark violet, opaque crystals of the hexachlonde makes its appearance, and if in large quantity the hexachlonde collects as a blackish-red liquid In order to saturate this liquid, it is slowly distilled in a current of chlorine The dark violet crystals decrepitate on cooling, and the crystalline mass thus readily breaks up into a powder

Perhaps the simplest method of preparing the hexachlonde consists in the interaction of tungsten trioxide and carbon tetrachloride at 280° [1]

When pure, the solid hexachlonde does not undergo any change even in moist air, but in the presence of the slightest trace of oxychlonde it at once absorbs moisture, evolving copious fumes of hydrogen chloride and changing in colour from violet to brown Water does not act upon the pure hexachlonde, but on boiling decomposition occurs If, however, the oxychlonde be present the whole is suddenly decomposed by cold water into a greenish oxide It is soluble in carbon disulphide and crystallises from the solution in six-sided plates

The melting point of the hexachlonde is 275°, it boils under a pressure of 759 5 mm at 346 7° The vapour density of tungsten hexachlonde has been determined m sulphur vapour and in mercury vapour, at 440°, the mean experimental density compared with that of hydrogen is 168 8, whilst at 35O° the density is 190 9, the calculated density being 196 9 The alteration of the density from 191 at 35O°, only 3° above the boiling point, to 169 at 440° points to the fact that dissociation occurs That this is the case is shown by the fact that when a current of dry carbon dioxide is passed through the fused hexachlonde a continuous liberation of chlorine takes place,

[1] **Michael and Murphy, *Amer Chem J*, 1910, 44, 365**

whereas the pentachloride treated in the same way does not undergo a similar decomposition

Tungsten Oxychlorides —The *oxytetrachlonde,* $WOCl_4$, and the *dioxydichloride,* WO_2C1_2, have been studied by Blomstrand and Riche The dioxydichloride is best obtained by passing chlorine over the brown oxide, WO_2 Combination takes place at a moderate temperature, the oxide becoming covered with a whitish crust, which as the temperature increases sublimes without melting, condensing in small square scales of a light lemon-yellow colour The dioxydichloride volatilises at a temperature approaching redness with partial decomposition, the crystals do not fuse, and are not acted upon by moist air or cold water Even when boiled with water the dioxydichloride is not completely decomposed

The splendid red needle-shaped crystals of the oxytetrachlonde, prepared by Wohler, are obtained by passing the hexachloride vapour over heated oxide or dioxydichloride

$$WO_3 + 2WC1_6 = 3WOC1_4,$$

and also by acting on the trioxide with phosphorus pentachloride,[1] and by the interaction of tungsten trioxide with a solution of chlorine in carbon tetrachloride at 240°[2] Attempts to prepare tungsten dichloride by interaction of the metal with carbonyl chloride result in the formation of this compound[3] The crystals melt at 210 4°, and the liquid boils at 227 5°, forming a red vapour rather lighter coloured than that of the hexachloride, and having the normal density at 35O° (Roscoe) On repeated distillation over red hot charcoal in a curient of chlorine the hexachloride is formed On exposure to the air the oxytetrachlonde becomes at once covered with a yellowish crust of tungstic acid

501 Bromine acts rapidly on red-hot tungsten, forming dark, bromine-like vapours, which condense to a crystalline sublimate Special precautions similar to those taken in the preparation of the chlorides must also be employed for the bromides, as the oxybromides formed in the presence of air and moisture possess almost the same colour as the bromide, and therefore the detection of the impurity is not so easy as with the chloride

Tungsten Dtbromtde, WBr_2, is formed by the reduction m hydrogen of the pentabromide, heated in a bath of fused zinc

[1] Schiff, *Ann* , 1879,**197,** 185 [2] Michael and Murphy, *loc cit*
[3] Lindner and others, *Ber* , 1922, 55, *[B],* 1458

chloride A residue of non-volatile dibromide remains in the form of a bluish-black, velvely, crystalline powder

Tungsten Pentabromide, WBr_5, is prepared by the action of an excess of bromine on tungsten, and is formed also when the hexachlonde is heated in dry hydrogen bromide, but cannot be prepared pure in this way[1] The pentabromide forms dark crystals having a metallic lustre resembling iodine, melting at 276°, and boiling at 333° It is at once decomposed by an excess of water into hydrobromic acid and the blue oxide When the pentabromide is heated in a current of hydrogen, the metal is formed in the state of pyrophonc powder

Tungsten Hexabromide, WBr_6, is obtained, according to Schaffer and Smith,[2] by gently heating tungsten in dry bromine vapour in an atinospheie of nitrogen It can be sublimed, and forms bluish-black needles It decomposes very readily when heated, fumes in the air, and is decomposed by water with formation of a blue oxide

Liquefied hydrogen bromide converts the hexachlonde at 60—70° into a mass of olive-green crystals which melt at 232° and have the composition WCl_6,$3WBr_6$, whilst at the ordinary temperature a similar substance of the composition WCl_6,WBr_6 is formed (Defacqz)

Tungsten oxybroinides, corresponding to the oxychlondes, exist The *dioxydibromide,* WO_2Br_2, is prepared by passing bromine vapour over red hot tungsten dioxide It forms light red, transparent crystals which yield a yellow powder It does not melt, but volatilises at a temperature approaching a red heat, and is not acted upon by water The *oxytetrabromide,* $WOBr_4$, is formed m the same circumstances as the last-named compound in brownish-black, lustrous needles, which are readily fusible and can be separated from the dioxydibromide by gently heating, when the latter compound remains behind It melts at 277°, boils at 327 5°, and is decomposed by water

Tungsten Di-iodide, WI_2, is obtained in the form of green, metallic scales when iodine vapour is passed over the metal heated to redness [3] (Eoscoe), and is formed also by the action of hydrogen idoide on the hexachlonde at 40O° (Defacqz) [4]

Tungsten Teiia-iodide, WI_4, obtained by Defacqz[5] by the action of liquefied hydrogen iodide on the hexachlonde at 10O°,

[1] Defacqz, *Ann Chim Phys* , 10O1, [7], 22, 247
[2] *J Amer Chem Soc* , 1897,18, 1098 [3] *Ann* , 1872,162, 349
[4] *Ann Chim Phys,* 1901, [7], 22, 239 [5] *Lot at*

is a black, infusible, crystalline mass, which is decomposed by water into the brown oxide and hydriodic acid

TUNGSTEN AND SULPHUR

502 *Tungsten Disulphide,* WS_2, is obtained by the action of sulphur, hydrogen sulphide, or carbon disulphide on lgmted metallic tungsten It may be prepared also by heating tungsten trioxide in a crucible with six times its weight of cinnabar or with potassium carbonate and Sulphur, and by heating the hexachlonde in a current of hydrogen sulphide (Defacqz) It forms soft, black, needle-shaped crystals which soil the fingers like graphite

A *chlorosulphide,* $WC1_6,3WS_3$, is formed, by the action of liquefied hydrogen sulphide on the hexachlonde at 60° (Defacqz)

Tungsten Trisulphide, WS_3, is obtained only in the wet way by dissolving tungsten trioxide in ammonium sulphide and precipitating with an acid, or by saturating an aqueous solution of an alkali tungstate with hydrogen sulphide, and acidifying When dry it is black, yielding a liver-coloured powder It yields a colloidal solution with water, and is precipitated by ammonium chloride and acids It is easily dissolved by potassium carbonate and also by ammonia Heated with potassium cyanide, it forms the disulphide, this is unaltered by fusion with excess of the reagent

The Thiotungstates—The thiotungstates of the alkali and alkaline-earth metals are prepared by dissolving the tn-sulphide m the corresponding hydrosulphide, or by treating the corresponding tungstate with hydiogen sulphide The ammonium salt, $(NH_4)_2WS_4$, is deposited from concentrated solution in yellowish-red crystals, the potassium salt, K_2WS_4, forms anhydrous, yellow crystals, whilst the sodium salt, Na_2WS_4, crystallises with difficulty Salts of the form $M_2WO_2S_2$ and a salt of the composition K_2WO_3S,H_2O are also known

TUNGSTEN AND NITROGEN, PHOSPHORUS, CARBON, SILICON, AND BORON

503 Tungsten does not combine directly under ordinary conditions with nitrogen, and neither the metal nor the dioxide is attacked when strongly heated in ammoma [1] By the action

[1] Langmuir, *J Amer Chem Soc* , 1913,36, 931,1915,87,1139, has, however, shown that under the conditions obtaining in a nitrogen filled tungsten filament electric incandescence lamp, a nitride, WN_2, is formed

of ammonia on the oxytetrachlonde or the hexachloride in the cold, a black, semi-metallic powder is obtained, which has the composition W_2N_3 It is insoluble in caustic soda, nitric acid, or dilute sulphuric acid, but is converted by concentrated sulphuric acid into ammonia and tungstic acid [1]

By the action of ammoma on tungsten trioxide at a dull red heat Wohler obtained a black, amorphous product which he termed "*tungsten nitretamidoxide*" the formula of which is $W_5N_eH_3O_5$ (Rideal) It is insoluble in acids and alkalis, but dissolves in sodium hypochlorite solution, and on ignition decomposes, ammoma, mtrogen, and hydrogen being evolved Other compounds which have been described are $W_4N_4H_2O_4$, $W_3N_6H_4$, $W_3N_4H_4$, and W_3N_2

Phosphides of Tungsten —Phosphorus and tungsten combine directly when the finely powdered metal is heated to redness in phosphorus vapour, a dark green powder of the composition W_3P_4 being formed Another compound, W_2P, is obtained, when a mixture of phosphorus pentoxide and tungsten trioxide, in the proportion of two molecules of the former to one molecule of the latter, is reduced at a high temperature in a charcoal crucible,[2] and forms a vesicular mass, the hollow portions of which contain large crystals

A black, amoiphous *diphosphide,* WP_2, is formed when the hexachloride is heated in phosphme, and this reacts with copper phosphide at a high temperature to form *tungsten mono phosphide,* WP, which crystallises m grey prisms with a metallic reflex, has density 8 5, and is oxidised to tungsten trioxide when heated in air (Defacqz) An *arsenide,* WAs_2, has also been prepared in a similar manner to the diphosphide, which it resembles

Tungsten and Carbon—Tungsten forms two carbides The compound obtained by heating the oxide with carbon or calcium carbide [3] has the formula W_2C, whilst in presence of a large amount of iron [4] the carbide WC is produced They are both hard, iron-grey, crystalline substances The compound W_3C is also considered to be definite[5] Several complex carbides

[1] Wohler, *Ann,* 185O, 73, 190, 1858, **105,** 258, Rideal, *Journ Chem Soc* , 1889, **55,** 41

[2] Wohler, *Journ Chem Soc* , 1853, 8, 94

[3] Moissan, *Compt rend,* 1896,**123,** 13, 1897,**125,** 839

[4] Williams, *Compt rend,* 1898,**126,** 1722

[5] Ruff and Wunsch, *Zeit anorg Chem* , 1914, 85, 292 See also Hilpert and Ornstem, *Ber,* 1913,_46, 1669.

containing iron or chromium have also been prepared,[1] and the existence of a compound WCO is postulated [2]

Quadrivalent tungsten forms a series of double cyanides of the general formula $R_4[W(CN)_8], xH_2O$, quinquevalent tungsten forms a series of double cyanides of the type $B_3[W(CN)_8],; rH_2O$, double thiocyanates, and double oxalates, in none of these cases, however, is the constituent simple tungsten salt known

Tungsten Sihcide, W_2Si_3, is obtained by heating the trioxide with silicon In the electric furnace,[3] and freeing the product from metal by electrolytic oxidation It forms beautiful, steel-grey plates with a metallic lustre, and burns in oxygen It is attacked by a mixture of nitric and hydrofluoric acids, and by fused potash Other sihcides which have been described are WSi_2 and WSi_3

Tungsten Boride, WB_2, is obtained by fusing the two elements together by a convenient electrical method, it crystallises in hard octahedra of density 10 77 [4] It is attacked by concentrated acids [5]

DETECTION AND ESTIMATION OF TUNGSTEN [6]

5O4 All the insoluble tungsten compounds can be converted into soluble tungstates by fusion, either with caustic alkali alone, or with the addition of mtre The solution when brought into contact with zinc or aluminium [7] and hydrochloric acid becomes blue-coloured, owing to the formation of the blue tungsten oxides (or tungsten tungstates) When ammomum sulphide is added to the colourless solution of the tungstate, and then dilute hydrochloric acid, a brown precipitate of tungsten sulphide is obtamed, whereas hydrochloric acid alone precipitates tungstic acid, which on heating turns yellow If the tungsten compounds are fused with a small quantity of tin in the reducing flame with microcosmic salt, a blue bead is obtained, whilst

[1] *Compt rend*, 1898,**127,** 1410, 1899,**128,** 207, 1903,**137,** 292
[2] Langmuir, *J Amer Chem Soc*, 1915, **37,** 1139
[3] Vigouroux, *Compt rend*, 1898, **127,** 393 See also Warren, *Chem News,* 1898, **78,** 318
[4] Wedekind, *Ber,* 1913, **48,** 1198
[5] Tucker and Moody, *Journ Chem Soc*, 1902, **81,** 16
[6] The arc spectrum of tungsten has been examined by Belke, *Zett wiss Photochem,* 1917, **17,** 132, 145, and the *X* ray spectrum by Barnes, *Phil Mag,* 1915, [6], 3O, 368, Ledoux-Lebard and Dauvilher, *Compt rend,* 1917, **164,** 687, Siegbahn, *Phil Mag,* 1919, [6], **38,** 639, de Broghe, *Compt rend,* 1919,**169,** 962, Buane and Patteison, *Phys Rev,* 1920,**16,** 626
[7] Torossian, *Amer J Set,* 1914, [4], **38,** 537

tungsten compounds containing iron yield in the reducing flame a blood-red bead Tungsticoxide can be very readily detected by fusing with potassium bisulphate and adding sulphuric acid and a crystal of phenol or quinol (hydroqumone), when a blue or violet coloration is produced, by the aid of which the presence of O OO2 mgm of tungstic oxide can be recogmsed (Defacqz)

Tungsten is estimated *giavimetrically* as the trioxide For the purpose of ascertaining the quantity contained in wolfram, for instance, the finely powdered mineral is heated with aqua regia, evaporated to dryness, the residue treated with water, the soluble chlorides of iron and manganese are filtered off, and the insoluble tungstic acid is washed with alcohol and dissolved in ammoma The solution is then evaporated down, and the residue heated gently, and afterwards lgnited in presence of air, when the trioxide remains, and is weighed Solutions of tungstates may also be precipitated with benzidine hydrochloride,[1] mercurous nitrate,[2] or "nitron,"[3] and the precipitate ignited and weighed as the trioxide (compare also Wolter)[4] Colonmetric methods, in which titanous chloride[5] or stannous chloride[6] are employed, may also be used

For recent investigations on the estimation of tungsten the original literature should be consulted[7]

Atomic Weight of Tungsten —The atomic weight of tungsten has been determined by numerous investigators Schneider,[8] by the reduction of tungsten trioxide to metal and oxidation of the metal to trioxide, found the average value 184 11, whilst

[1] v Knorre, *Ber,* 1905, 38, 783, Kantschev, *J Buss Phys Chem Soc,* 1914, 46, 729

[2] Defacqz, *Compt rend ,* 1896, **123,** 3O8

[3] Gutbier and Weise, *Zeit anal Chem,* 1914, **63,** 426

[4] *Chem Zeit,* 1910, 35, 2

[5] Travers, *Compt rend,* 1918, **166,** 416

[6] Heath, *Chem Trade J ,* 192O, **66,** 629

[7] Hilpert and Dieckmann, *Ber ,* 1913, 46, 152, Tread well, *Zeit Elektrochem ,* 1913,19, 219, 381, Zinberg, *Zeit anal Chem ,* 1913, **52,** 529, Hermann, *ibid ,* 1913, 52, 557, Kafka, *ibid,* 1912, 52, 6O1, Wunder and Schapira, *Ann Chim anal,* 1913,18, 257, Arnold *Zeit anorg Chem,* 1914, 88, 74, 333, Dieckmann and Hilpert, *Ber,* 1914, 47, 2444, Marbaker, *J Amer Chem Soc,* 1915, 37, 86, Dittler and Graffenned, *Chem Zeit,* 1916,40, 681, Gughalmelh and Hordh, *Anal Soc Quim Argentina,* 1917, 5, 81, Travers, *Compt rend ,* 1917,**165,** 408, Sweeney, *J Amer Chem Soc,* 1916, 38, 2377, van Duin, *Chem Weekblad,* 1917,14, 169, Fenner *Chem Zeit,* 1918, 42, 403, Jannasch and Leiste, *J pr Chem,* 1918, [2], 97, 141, Hodes, *Zeit angew Chem,* 1917, 3O, 240, Erlich, *Ann Chim anal,* 192O, [2], 2, 102, Corti, *Anal Soc Quim Argentina,* 1917, 5,3O8, Lowy, *Zeit angew Chem,* 1919,**32,**379

[8] J *pr Chem,* 185O, 5O, 152

Marchand[1] found an almost identical value Roscoe[2] by the same method obtained the number 183 48, and by the analysis of the hexachlonde the number 184 O2, whilst Waddell[3] by the reduction of the trioxide found the higher number 184 33 More recently Pennington and Smith and Desi[4] have found the still higher number 184 8 by Schneider's method, but their results have been criticised by Schneider[5] as untrustworthy The investigations carried out by Smith and Exner,[6] who converted the hexachlonde into the trioxide by the action of water and synthesised the trioxide from the metal, gave an average value for the atomic weight of 184 O6 The best mean value is probably 184 1 ± O 1 The value now (1922) adopted is 184 O[7]

URANIUM 11 = 2382 At No 92

5O5 The mineral known as pitchblende was formerly believed by certain chemists to be an ore of either zinc or iron, whilst by others it was thought to contain tungsten Klaproth, in 1789, was the first to point out the existence in this mineral of a peculiar metal, to which he gave the name of uranium, in remembrance of Herschel's discovery of the planet Uranus in the year 1781 The substance obtained by Klaproth by the reduction of the calx of uranium was supposed by all the chemists who subsequently investigated the subject to be the metal, until Peligot[8] in 1842 proved it to be an oxide Peligot likewise isolated the metal and determined its equivalent

Uramum is not a very abundant element, and its chief ore is pitchblende or uraninite This consists of impure uranoso-uramc oxide, U_3O_8, and is found in Cornwall, at Joachimsthal, Johanngeorgenstadt, Adrianople, and other localities Carnotite, potassium uranyl vanadate, is found in Colorado, Utah, and S Australia, autunite, uranyl calcium phosphate, is found in France, Portugal, the Umted States, and Madagascar Varieties found in Cornwall are called bassetite and uranospathite[9]

[1] *Ann* , 1851, 77, 261
[2] *Mem Manch Phil Soc* , [3], 5, 77, *Annalen*, 1872, **162,** 366
[3] *Amer Chem J*, 1886, 8, 28O [4] *Zeit anorg Chem*, 1895, 8,198, 2O5
[5] *J pr Chem* , 1896, [2], 63, 288 [6] *J Amer Chem Soc* , 1904, **26,** 1082
[7] Gerber, *Mon Set*, 1917, [5], 7, 73, claims that tungsten is not a simple substance, but is accompanied by *neotungsten* of higher atomic weight
[8] *Ann Chim Phys*, 1842, [3], 5, 5
[9] Halhmond, *Min Mag* , **1915.17, 221**

Uranium is found also as a double phosphate with copper in torbernite or uranium-midP, as carbonate in hebigite, voglite, and uranothalhte, whilst as uranotantahte or samarskite it is found combined with columbium and tantalum Other uranium minerals are gilpmite,[1] brannente,[2] becquerelite,[3] $UO_3,2H_2O$, and soddite,[3] $12UO_2,5SiO_2,14H_3O$ Pitchblende is the best source of uranium, this mineral usually containing from 40 to 90 per cent of uranoso-uramc oxide, U_3O_8 The following analysis[4] gives the composition of a specimen of pitchblende from Connecticut UO_3, 26 48 per cent , UO_2, 57 43, ThO_2, 9 79, CeO_2, O 25, $(La,Di)_2O_3$, O13, $(Y,Er)_2O_3$, O 2O, Fe_2O_3, O 40, PbO, 3 26, MnO, trace, CaO, O O8, alkalies, trace, H_2O,0 61, SiO_2,0 16, insoluble, 0 70 Total 99 49 per cent

The uramum minerals always contain the radioactive element radium, as well as helium, the occurrence of which is discussed under the heading of Radioactive Elements Small amounts of compounds of copper, bismuth, silver, zinc, arsenic, and aluminium are often present

The process employed for the extraction of uramum from pitchblende is described by Meyer[5] as follows The finely ground mineral is first roasted and then calcined with sodium carbonate in a reverberatory furnace, the soluble uranium compound being extracted from the melt with water, alternatively, the mineral may be decomposed by fusion with sodium sulphate, followed by extraction of the melt with dilute sulphuric acid, or the mineral may be decomposed with a mixture of sulphuric and nitric acids In all cases the uramum compounds pass into solution, and in presence of excess of sodium carbonate remain in solution as sodium uranyl carbonate, on boiling with a suitable excess of dilute sulphuric acid, a yellow precipitate of sodium uranate, $Na_2U_2O_7,6H_2O$, is obtained The insoluble residue contains the radium salt in admixture with a number of other compounds

The method recominended by Wohler[6] consists of the decomposition of the pitchblende with a mixture of sulphuric and nitric acids, volatilisation of the acid, and extraction with water, yielding a solution through which hydrogen

[1] Larsen and Brown, *Amer Mm* , 1917, 2, 75
[2] Hess and Wells, *J Franklin Inst*, 1920, **189,** 225
[3] Schoep, *Compt rend* , 1922,**174,** 1066, 1240
[4] Clarke, " *The Data of Geochemistry," U S Oeol Survey Bull*, 1916, No 616
[5] Abegg's " *Handbuch der anorgamschen Chemie"* **1921, IV,** [1], 11, p 891
[6] ***Fogg*** *Ann*, **1845, 84, 94**

sulphide is passed, the filtrate, after being oxidised with nitric acid, is treated with ammonia, and the precipitate digested with a concentrated solution of ammonium carbonate containing excess of ammoma Uramc hydroxide dissolves and yellow ammonium uranyl carbonate crystallises out on cooling Peligot's [1] method depends on the facility with which uranyl nitrate crystallises, and on its ready solubility ;n ether

Metallic uramum was first prepared in the pure state by Pehgot, who obtained it by the action of sodium or potassium on uramum tetrachloride, a mixture of the tetrachloride, potassium chloride, and sodium being usually employed [2] It is also obtained by heating 5OO parts of the oxide, U_3O_8, with 40 parts of sugar charcoal in the electric furnace in a carbon tube, closed at one end The product contains a little carbon, which is partially removed by heating it in a crucible brasqued with uramum oxide, and enclosed in a larger crucible brasqued with titamum to protect the uramum from the action of mtrogen [3] Uranium may also be obtained by heating the dioxide to redness with carbon and starting the reduction by means of a cartridge of magnesium and barium dioxide,[4] or by reducing the trioxide with aluminium, a fused regulus of the metal containing a little aluminium being thus obtained [5] A satisfactory method consists m first preparing the tetrachloride by passing chlorine over the heated dioxide mixed with carbon, or by heating the oxide in a stream of chlorine and sulphur chloride, and then reducing this with sodium or magnesium [6]

Pure uramum has a white colour, and takes a high polish, it has a density of 18 7 at 14°, and a specific heat of O O2765, in the powdered state it oxidises on exposure to the air and, if fleshly prepared, may be spontaneously inflammable It decomposes water slowly at the ordinary temperature, and more quickly at the boiling point In the same condition it burns in oxygen at 17O°, in fluorine at the ordinary temperature, in chlorine at 180°, in bromine at 210°, m iodine at about 26O°, and in sulphur vapour at 500° It melts at a high temperature,

[1] *Ann Chim Phys*, 1842, [3], 5, 5, 1844, 12, 549, 1848, 22, 329, 1869, [4], 17, 368
[2] *Ibid*, 1869, [4], 17, 368
[3] Moissan, *Compt rend*, 1896, **122,** 1088
[4] Aloy, *Bull Soc chim*, 1901, [3], 26, 344
[5] Stavenhagen, *Ber*, 1899, 32, 3O65, Stavenhagen and Schuohard, *tbtd*, 1902, 25, 909
[6] Kideal, *J Soc Chem Ind*, **1914, 33,** 673, Lely and Hamburger, *Zeit, anorg Chem* , 1914, 87, 2O9, Baragiola, *Schwetz apoth Zett*, 1915, 53, **477**

and has a higher boiling point than iron, condensing in small, non-magnetic spheres, free from carbon[1] It readily combines with nitrogen at 10OO° Uranium has a potential between those of copper and hydrogen [2]

Several alloys with iron, manganese, and cobalt have been prepared by the aluminium reduction method An amalgam [3] can be obtained by the electrolytic method, and leaves pyrophonc uranium when the mercury is distilled off at 242°

Metallic uramum and its compounds are radioactive (see the section on the Eadioactive Elements)

COMPOUNDS OF URANIUM

URANIUM AND OXYGEN

5O6 Uramum combines with oxygen to form two[4] well-defined oxides, UO_2 and UO_3, and these combine, forming intermediate oxides Both these oxides are more magnetic than the metal [5] The dioxide is a basic oxide, and gives rise to the uranous salts, in which the metal is quadrivalent The trioxide, like the corresponding oxide of the other metals of this group, behaves as an acid-forming oxide, yielding salts known as the *uranates,* analogous to the chromates, molybdates, and tungstates Like the other trioxides of the group, uramum trioxide also yields a large number of derivatives in which only one of the three oxygen atoms is replaced by negative groups, these may be regarded as derivatives of the bivalent compound radicle *uranyl,* UO_2 This radicle has more decidedly basic properties than the corresponding radicles derived from the other metals, and the derivatives, therefore, correspond to the salts of a basic oxide, whilst the similar compounds of the other metals are more nearly allied to the acid chlorides, such as sulphuryl chloride, SO_2C1_2, and phosphoryl chloride, $POC1_3$ This view of the constitution of the uranyl salts is supported by the electro-chemical properties of their solutions In aqueous solution the salts of strong acids, $UO_2 E^x_2$, are hydrolysed to a small extent, corresponding in this respect to the analogous salts of aluminium

[1] **Ziminermann,** ***Annalen,*** **1883, 216, 1, Moissan,** ***Compt rend,*** **1893, 116, 1429, 1896, 122, 1088, 1906 142, 425**

[2] **Fischer and Roderburg,** ***Zeit anorg Chem,*** **1913, 81, 170, Fischer and Rideal,** ***ibid***

[3] **Feree,** ***Bull Soc chim*** **1901, [3], 25, 622**

[4] **See Lebeau,** ***Compt rend*** **, 1922,174, 388**

[5] **Wedekind and Horst,** ***Ber,*** **1915, 48, 105.**

and gluemum The non-hydrolysed portion of the salt dissociates in the normal manner, and on electrolysis the uranyl ion migrates to the cathode Complex derivatives are, however, very readily formed, especially with salts of organic acids [1]

Uranium Dioxide, UO_2—This oxide, formerly mistaken for the metal uranium, is prepared on the technical scale by fusing 35 parts of sodium chloride, 2O parts of sodium uranate, and 1 part of powdered charcoal in a cast steel pot at a red heat, lixiviating with water and treating the residue with hydrochloric acid [2] It is obtained by heating uranoso-uranic oxide, U_3O_8, or uranic oxalate in a current of hydrogen, or by the electrolysis of uranyl nitrate solution under suitable conditions [3] Thus prepared it is a pyrophonc powder, havmg a brown or copper-red colour, and a density of 10 95 When heated in the air it takes fire, and is completely converted into the oxide, U_3O_8 [4] It dissolves m strong acids, forming the green uranous salts [5] It may be obtained in jet black octahedra isomorphous with thona by fusing with borax, and then removing the latter with dilute hydrochloric acid [6] It is also formed in microscopic, black, non-pyrophonc crystals when crystalline uramc hydroxide is reduced in hydrogen, [7] and is left as a brick-red mass, which becomes black on heating, when uranyl bromide is heated in the air [8]

Uranous oxide is oxidised to the trioxide by ammoniacal silver solutions [9]

Uranous Hydroxide, $UO_2,2H_2O$ (?), is precipitated in reddish-brown flakes, which become black on ebullition, by adding an alkali to a uranous solution [10] In presence of alcohol, uranyl salts are reduced by light to uranous salts, or uranous hydroxide It dissolves easily m dilute acids, whilst the calcined oxide is only slightly soluble in these liquids The

[1] Dittnch, *Zeit physikal Chem,* 1899, 29, 449, Ley, *ibid,* 1900, 30, 193, *Ber,* 190O, **33,** 2658 Compare Kohlschutter, *Annalen,* 1900, **311,** 1
[2] Parsons, *J Ind Eng Chem,* 1917, 9, 466
[3] Oechsner de Coninck and Camo, *Bull Acad roy Belg,* 1901, 321
[4] Jolibois and Bossuet, *Compt rend,* 1922,**174,** 386 Oechsner de Coninck, *Bull Soc chim* , 1912, [4], **11,** 1037 states that the oxide U_4 i s thus formed
[5] See Colani, *Compt rend,* 1912, **155.** 1249, Raynaud, *ibid,* 1911, **153,** 148O, *Bull Soc chim,* 1912, [4], **11,** 802
[6] Hillebrand, *Zeit anorg Chem* , 1893, 3, 249
[7] Aloy, *Bull Soc. chim,* 1900, [3], 28, 368
[8] Oechsner de Coninck, *Compt rend,* 1902,**135,** 90O
[9] Smith and Shinn, *Zeit anorg. Chem,* 1894, 7, 47
[10] See Aloy, *Bull Soc chim,* 1899, [3], 21, 613.

substance has also been obtained electrolytically in a colloidal form [1]

Uranic Oxide, UOg, or *Uranyl Oxide,* $(UO_2)O$ —When uranyl nitrate is heated in a gladf tube to 25O° so long as acid fumes escape, this oxide is left behind in the form of a brownish-yellow powder, whereas, when the nitrate is rapidly decomposed, a red modification of the oxide is produced [2] It can also be prepared by heating ammomum uranyl carbonate or ammonium uranate in air

Uremic Hydroxide (Uranic Acid), UO_3,H_{20}, cannot be obtained by precipitating a uranyl salt by an alkali, the precipitate thus formed consisting of an alkali uranate It may, however, be prepared, according to Berzehus, by gently calcining the nitrate in a sand-bath as long as nitric acid is evolved The residue contains uranic hydroxide mixed with a basic salt, which can be removed by washing with boiling water It may likewise be obtained by evaporating a solution of uranyl nitrate in absolute alcohol, at a moderate heat, until a yellow mass remains, consisting of the hydroxide, $UO_2(OH)_2,H_{20}$, or by the electrolysis of uranyl salts at a low current density[3] This hydiate loses half its water at 80°,[4] or in a vacuum at the ordinary temperature, but at a temperature of 40O° it begins to lose oxygen, and is converted into uranoso-uranic oxide, U_3O_8 Uranic hydroxide is yellow, and has a density of 5 92 It does not undergo change

in the air, nor does it absorb carbon dioxide

An orange-coloured hydroxide, UO_3,H_{20}, can be obtained by the electrolysis of the nitrate,[5] and is formed in rhombic crystals when the violet hydrate of the oxide U_3O_8 is boiled with water in the air [6]

This oxide, as mentioned above, yields by the action of acids the *uranyl* salts, whilst with bases it gives rise to the *uranates* The former have a yellow colour, and most of them possess a remarkable fluorescence,[7] which they impart to glass The absorption bands exhibited by these compounds have been

[1] Samsonow, *Kolloid Zeit,* 1911, 8, 96

[2] Oechsner de Coninck, *Compt rend,* 1901,**132,** 204, *Bull Acad roy Belg,* 1904, 363, 448

[3] Pierle, *J Physical Chem,* 1919, **23,** 517

[4] de Forcrand, *Compt rend,* 1913, **156,** 1954

[5] Oechsner de Coninck and Camo, *Bull Acad roy Belg,* 1901, 3, 222, Pierte, *J Physical Chem,* 1919, **23,** 517

[6] Aloy, *Bull Soc chim,* 190O, [3], **23,** 368

[7] See Trumpler, *Zeit physikal Chem* , 1915, 90, 385, Bauer, *Schweiz Chem Zeit,* 1918,2,40, Nichols and Howes, *Physical Rev* , 1919, [2], 14, 293, Nichols, Howes, and Wick, *ibid,* 1919, [2], 14, 201, Nichols and others, *Carnegie Inst Washington Publication,* 1919, **298,** 1

studied by Becquerel and others These salts are highly sensitive to light and have been employed for photographic purposes The most important are described in the sequel, together with the other uranium salts

The Uranates—The alkali uranates are obtained by precipitating a uranic salt with an alkali, those of the alkaline earths and other metals by precipitating a mixture of a uranyl salt and a corresponding metallic salt with ammonia They are also formed when a mixture of a metallic uranate and the acetate or carbonate of the metal is heated in the air The uranates generally have the composition $M_2O,2UO_3$, and correspond to the dichromates They are yellow, insoluble in water but soluble in acids, and are decomposed by heat, like uranic oxide itself Normal uranates are, however, known, as well as potassium and sodium salts of tri-, tetra-, penta-, and hexa-uranic acids

Potassium Di-uranate, $K_2U_2O_7$ —This is obtained as a pale orange-yellow coloured powder by precipitating a uranyl salt with an excess of potash Probably the hydroxide is first precipitated and then two molecules unite by the elimination of water, forming uranic acid, which umtes with the excess of alkali to form the potassium salt The *normal* salt can be produced by fusing uranyl chloride with potassium chloride and ammonium chloride, or by heating uranium trioxide with potassium chlorate Potassium uranate can also be obtained by electrolysis of a neutral solution of potassium uranyl cyanide[1]

Sodium Di-uranate, $Na_2U_2O_7$ is obtained in a similar manner to the potassium salt, and is known as *uranium yellow*, being used for painting on glass and porcelain, as well as for preparing the yellow glass known as uramum glass It is prepared on a large scale by roasting 10O parts of pitchblende, containing 45 per cent of U_3O_8, with 14 parts of lime in a reverberatory furnace The resulting calcium uranate is treated with dilute sulphuric acid, and the solution of uranic sulphate thus obtained is mixed with sodium carbonate The uramum is precipitated, together with the other metals, but re-dissolves in an excess of the alkali On treating this liquid with dilute sulphuric acid, a hydrated sodium uranate, $Na_2U_2O_7,6H_2O$, is obtained[2]

Ammonium Uranate —This salt sometimes occurs in cominerce as a fine deep yellow-coloured precipitate, termed, like the sodium salt, uramum yellow It is easily obtained by adding ammonium chloride or sulphate to a boiling solution of sodium

[1] **Pierte, *J Physical Chem*, 1919, 23, 617**
[2] **Patera, *J pr Chem*, 1854, 61, 397**

uranate, washing the resulting precipitate, and drying at a gentle heat When heated to redness this salt yields pure uranoso-uranic oxide, and serves tjprefore as the raw material for the preparation of other uranium compounds

Uranoso-uranic Oxide or *Green Oxide of Uranium,* $U_3O_8 (= UO_2,2UO_3)$, occurs more or less pure in pitchblende The pure oxide can be obtained by gently heating the trioxide or the dioxide in the air in the form of a satiny, dark-green powder, having density 7 2, and soluble in strong acids It forms a violet hydroxide which can be prepared by the action of Light on a solution of uranyl oxalate or an alcoholic solution of the acetate [1] A number of violet compounds of uranium are known, being obtained whenever a uranous and a uranic salt are present together at the requisite temperature in neutral or feebly acid medium By loss of their acid radicles they yield hydrated uranoso-uranic oxide [2]

Black Oxide of Uranium, or *Uranium Penloxide,* $U_2O_5 (= UO_2,UO_3)$, is formed when the other oxides, or ammonium uranate, are strongly lgnited in the air, and when the nitrate is electrolysed Ziminermann stated that it possesses no constant composition,[3] but there seems to be no reasonable doubt regarding its individual existence

An oxide of the composition $U_3O_{10}, 2H_2O$ is stated to be formed when uranium salts are electrolysed [4]

Uranium Peroxide, UO_4—When a very dilute solution of hydrogen peroxide is added to one of uranyl nitrate, a yellowish-white precipitate of peruranic hydroxide, UO_4, xH_2O is formed, which evolves chlorine when treated with hydrochloric acid [5] *Peruranates* are formed by the action of alkali and hydrogen peroxide on the uranyl salts (Fairley) Two types of salt are known, in one of these the metal appears to be present as a peroxide and the salt can be hydrolysed by weak acids or bases into a peroxide and uranium peroxide, the hydrolysis of salts of the second type yields uranium peroxide and an ordinary metallic oxide [6]

[1] See Aloy, *Bull Soc chim,* 190O, [3], **23,** 368
[2] Aloy and Rodier, *Bull Soc chim,* 1920, [4], **27,** 101
[3] *Annalen,* 1885, **232,** 276 See also Lebeau, *Compt rend,* 1922, **174,** 388
[4] Pierte, *J Physical Chem,* 1919, **23,** 517
[5] Eairley, *Journ Chem Soc,* 1877, *i,* 127, Huttig and Sohroeder, *Zett anorg Chem* , 1922, **121,** 243
[6] Melikoff and Pissarjewsky, *Ber,* 1897, 3O, 2902, *Zeit anorg Chem,* 1898, 18, 59, Pissarjewsky, *J Buss Phys Chem Soc,* 1902, **34,** 472

Sodium Peruranate, $(Na_2O_2)_2\ UO_4 8H_2$, is precipitated when alcohol is added to a solution of uranyl nitrate, sodium hydroxide, and hydrogen peroxide, and crystallises in golden-yellow needle-shaped crystals, which are somewhat more stable than the potassium salt If the minimum quantity of caustic soda be employed, a red crystalline salt separates out, having the composition $Na_2(UO_4)_2, 6H_{20}$ A red, crystalline salt, Na_2UO_5, H_2, O is formed when peruranic hydroxide is added to hydrogen peroxide containing alcohol, sodium hydroxide being then gradually introduced It slowly decomposes with evolution of oxygen[1] The formation of a salt of this type is the cause of the red coloration produced when hydrogen peroxide and solid potassium carbonate are added to a uranyl salt[3]

Lead Peruranate is formed as a double salt with lead uranate, $(PbO)_2UO_4, PbUO_4$, by the action of sodium peruranate on lead acetate Hydrogen peroxide is liberated in the reaction and the resulting lead salt, when treated with dilute acetic acid, yields lead acetate and peruranic hydroxide, but no hydrogen peroxide (Melikoff and Pissarjewsky) Other salts of the heavy metals are prepared in a similar manner, they are more stable than the corresponding salts of molybdenum and tungsten

URANIUM AND THE HALOGENS

507 *Uranium difluoride,* $UF_2, 2H_{20}$, has been obtained by electrolytic reduction of uranyl chloride in presence of excess of hydrofluoric acid[3]

Uranium Tetrafluonde or *Uranous Fluoride,* UF_4, is obtained in the for

acid is added to a solution of uranous chloride It is insoluble in water and hydrofluoric acid, and when heated in the air it leaves a green residue of oxide When lgnited in hydrogen it loses hydrofluoric acid[4] The hexahydrate is obtained by electrolysis of potassium uranyl fluoride in acid solution[5]

Uranous fluoride forms double salts with the alkali fluorides Potassium urano-fluonde, KF, UF_4, is obtained by the action of reducing agents, such as formic and oxabc acids under the influence of light, upon the potassium urano-oxyfluonde, described

[1] **Aloy,** ***Bull Soc chtin,*** **1903, [3], 29, 292** [2] ***Ibid*** **, £7, 734**
[3] **Giolitti and Agamennone,** ***Atti R Accad Lmcet,*** **1905, [5], 14, 1, 114, 165**
[4] **Canington Bolton,** ***Ber Akad Wtss Berhn,*** **1866, 299, see also Smithells,** ***J Chem Soc,*** **1883, 48, 125**
[5] **Pierle,** ***J Physical Chem,*** **1919, 23, 517**

below It is a green powder, resembling uranous fluoride, insoluble in water and in dilute acids

The *hexafluoride* is also known The reaction between fluorine and uranium is extremely vigorous and the product is mainly the tetrafluonde and small quantities of the hexafluoride, UF_6 The hexafluoride is best prepared from fluorine and the pentachlonde cooled in an alcohol and carbon dioxide mixture It forms glistening, colourless, fummg, monoclmic prisms, which sublime without melting at ordinary temperatures under reduced pressure [1]

Uranyl Fluoride, UO_2F_2, is a green solid, obtained by the action of hydrofluoric acid on the oxide U_3O_8 It was considered by Smithells [2] to exist in two modifications It combines with potassium fluoride, yielding *potassium uranyl fluoride,* UO_2F_2,3KF, which is a lemon-yellow, crystalline precipitate, and is also formed when an excess of potassium fluoride is added to a solution of uranyl acetate It is tnmorphous (Baker)[3] Corresponding sodium, ammonium, and barium salts are known (Bolton) Hydrogen peroxide converts these salts into deep yellow-coloured peroxyfluondes [4]

Uranous Omjfluoride, UOF_2, is formed by the electrolytic or photochemical reduction of uranyl salts [5]

Uranium Trichloride, $UC1_3$, is obtained by heating the tetrachloride in hydrogen,[6] or by the continued reduction of uranyl salts with zinc and hydrochloric acid [7] It is a reddish-brown powder, and dissolves readily in water, forming a red solution, which gradually becomes green with evolution of hydrogen

Uranium Tetrachloride or *Uranous Chloride,* $UC1_4$—This is produced with vivid incandescence, when chlorine is passed over metallic uranium, and is obtained also by igniting uranium dioxide in hydrogen chloride, and, in solution by exposing a solution of uranic oxide in hydrochloric acid containing alcohol to sunlight, [8] other reduction methods may also be used It

[1] Ruff, Zedner, Schiller, and Heinzelmann, *Ber,* 1909, 42, 492

[2] *hoc cit* See also Giohtti and Agamennone, *he cit*

[3] *Journ Chem Soc,* 1879, 36, 763

[4] Lordkipamdze, *J Buss Phys Chem Soc,* 1900, **32,** 283

[5] Giolitti and Agamennone, *Atti B Accad Lmcei,* 1905, [5], 14, I , 114, 165

[6] Peligot, *Ann Chim Phys* , 1842, 5, 20, Rosenheim and Loebel, *Zeit anorg Chem,* 1908, 57, 234

[7] Ziminermann, *Annalen,* 1882, **213,** 320

[8] Aloy, *Bull Soc chim,* 1899, [3], **21,** 613, Aloy and Rodier, *ibid,* 1922, [4], **31,** 246

is best prepared by passing chlorine over a heated mixture of charcoal and any of the uranium oxides, or over uranium carbide[1] Some pentachlonde is simultaneously formed, and may be removed by heating the product in a current of carbon dioxide It can also be prepared by passing carbon tetrachloride over U_3O_8 at a red heat[2] It crystallises in splendid dark-green octahedra, having a metallic lustre, and volatilising at a red heat to form red vapours with the normal density of 13 3 It is extremely deliquescent, fumes strongly on exposure to the air, and dissolves readily in water, with evolution of heat and formation of a deep emerald-green solution This, when concentrated in a vacuum, leaves an amorphous, dehquescent mass of uranous chloride, but when evaporated by heat it decomposes, yielding a soluble residue, probably consisting of the oxychlonde Solutions of uranous chloride yield with alkalis a precipitate of uranous hydroxide The solution acts as a powerful deoxidising agent, reducing gold and silver salts, and converting ferric chloride into ferrous chloride It was by the analysis of this chloride that Peligot ascertained that the supposed metal was in reality an oxide

Uranium tetrachloride combines directly with ammoma, forming the compound $3UC1_4,4NH_3$, and umtes with the heated chlorides of potassium, lithium, and the metals of the calcium group, forming green salts, $UCl_4,2M^{1}Cl$ or $UCl_4,M^{11}Cl_2$, which are decomposed by water (Aloy)

Benrath[3] considers that the greenish-yellow powder deposited when uranyl chloride dissolved in ether is exposed to sunlight is the *oxychlonde,* $UOCl_2$

Uranium, Pentachlonde, $UC1_5$, is obtained by the direct umon of the tetrachloride with chlorine It exists in two distinct forms, according as it is produced slowly or quickly. When the current of chlorine is slow, the uranium pentachlonde forms long, dark, needle-shaped crystals, which reflect light with a green, metallic lustre, but are of a splendid ruby-red colour when viewed by transmitted light If the rate at which the chlorine passes be rapid, the pentachlonde is deposited in the form of a light brown, mobile powder Both forms are hygro-

[1] Aloy, *Bull Soc chtin,* 1899, [3], 21, 264, Roderburg, *Zeit anorg Chem* , 1913, 81, 122, Lely and Hamburger, *ibid,* 1914, 87, 209, Rideal, *J Soc Chem Ind,* 1914, 83, 673

[2] Colani, *Ann Chim Phys,* **1907,** [8], **12, 59**

[3] *Zeit wise Photochm,* **1917, 16, 253**

scopic, yielding yellowish-green liquids on exposure to the air for a few minutes, and hissing and giving off fumes of hydrochloric acid when thrown into water Uranium pentachlonde cannot be volatilised without partial decomposition, since uranium tetrachloride and free chlorine are formed The tetrachloride when similarly heated loses no chlorine [1] There are reasons for regarding uranium pentachloride as possessing the constitution $UC1_4\,UC1_6$ The free hexachlonde is not, however, known

Uranyl Chloride or *Uranium Oxychloride,* UO_2C1_2, is formed when dry chlorine gas is passed over uranium dioxide at a red heat The tube then becomes filled with the orange-yellow vapour of this compound, which solidifies to a yellow, crystalline mass, and is easily fusible, but not very volatile When strongly heated in dry air, it yields chlorine and the dioxide, which then becomes oxidised [2]

Uranyl chloride is soluble in water, alcohol, or ether, and its aqueous solution yields on evaporation crystals of the hydrate, UO_2C1_2,H_{20} This may be obtained in solution by acting upon uranic oxide with hydrochloric acid, or by oxidising a solution of uranous chloride with nitric acid [3]

Uranyl chloride forms double chlorides with the chlorides of the alkali metals The ammonium salt, $2NH_4C1,UO_2C1_2,2H_{20}$, crystallises in rhombohedra from a syrupy solution of the mixed salts The potassium salt, $2KC1,UO_2C1_2,2H_{20}$, is obtained by dissolving potassium uranate in excess of hydrochloric acid, adding potassium chloride, and evaporating, when large, rhombic tablets separate out, which have a yellowish-green colour, and are very soluble [4] The anhydrous compound can be obtained by passing the vapour of the oxychlonde over heated potassium chloride[5] Uranyl chloride combines also with the hydrochlorides of the orgamc bases (Greville Williams) Several basic chlorides have been described [6]

[1] Roscoe, *Journ Chem Soc*, 1874, 933, Ruff and Hemzelmann, *Ber*, 1909, 42, 492, *Zett anorg Chem,* 1911, 72, 63, Cambouhves, *Compt rend,* 1910, **16O,** 175

[2] Oechsner de Coninok, *Ann Chim Phys*, 1904, [8], 3, 6OO

[3] See Mylius and Dietz, *Ber*, 1901, 34, 2774

[4] See Rimbach, *Ber*, 1904, 37, 461

[5] Aloy, *Bull 8oc chim,* 1901, [3], 25, 153

[6] *Ibid,* 1899, [3], 21, 613, Orloff, *J Buss Phys Chem Soc,* 1902, 34,375, 1903, 36, 513

Uranium Tribromide, UBr_3, has been described as dark brown needles [1]

Uranium Tetrabromide, UBr_4, is obtained by heating in an atinosphere of bromine vapour a previously lgnited mixture of uranous oxide and six times its weight of starch, or of the green oxide with sugar charcoal [2] The bromide is deposited in the more strongly-heated portions of the tube in lustrous brown tablets of density 4 838 at 21°/4°. The density of its vapour is 19 5 It loses its lustre and becomes dull yellow on the surface

in the prese

is very deliquescent

Uranyl Bromide or *Uranium Oxybromide,* UO_2Br_2, is obtained by treating uranous oxide with bromine and water, or by dissolving uranic oxide in hydrobromic acid On evaporation, yellow needles are deposited, which have a styptic taste and decompose when heated [3]

Uranium Tetraiodide, UI_4, described by Eaminelsberg, is obtained by dissolving uranous hydroxide in hydnodic acid A green solution is thus formed which decomposes on evaporation The solid substance is formed as a crystalline sublimate when iodine vapour is passed over uranium at a temperature of 5OO° in sealed vacuum tubes It forms black needles melting at 5OO°, and dissolves in water, giving a green acid solution [4]

Uranyl Iodide, UO_2I_2, is formed when a slight excess of barium iodide is added to an ethereal solution of the nitrate, and separates in red, deliquescent, unstable crystals [5]

Uranyl chlorate, perchlorate, and *lodate,* and double compounds of the last-named with potassium lodate, have been described

UEANIUM AND SULPHUR

5O8 *Uranium Sesquisulphide,* U_2S_3, is prepared by heating UBr_3 in hydrogen sulphide, and yields *uranium monosulphide,* US, when heated in hydrogen [6]

Uranous Sulphide, US_2, is obtained, according to Pehgot, when metallic uranium is heated in sulphur vapour The mass takes fire and an amorphous, greyish-black powder is obtained

[1] Ahbegoff, *Annalen,* 1882, **233,** 104, **131,** 135
[2] Richards and Mengold, *Zeit anorg Ckem,* 1902, **31,** 260
[3] See Oechsner de Coninck, *Bull Acad toy Belg,* 1902, **12,** 1025
[4] Guichard, *Compt rend,* 1907, **145,** 921
[5] Aloy, *Ann Chim Phys,* 1901, [7], **24,** 412
[6] Alibegoff, *Annalen,* 1886, **233, 117**

which becomes crystalline when ignited in absence of air It may also be formed Ijy passmg a carefully dried mixture of hydrogen and sulphur vapour over sodium uranium chloride The sulphide is thus obtained in small, flattened crystals [1]

Ammonium sulphide always gives a black precipitate of the hydrated sulphide with uranous salts In moist air it loses hydrogen sulphide and forms uranyl sulphide, UO_2S

An *oxysulphtde,* UOS, is obtained when UO_2,U_3O_8 or ammonium uranate is heated in hydrogen sulphide

Uranyl Sulphide, UO_2S, is precipitated when ammonium sulphide is added to a solution of uranyl nitrate It oxidises quickly on exposure to air, and dissolves easily in acids and in ammonium carbonate When heated in the presence of water until all the ammonium sulphide has been driven off, it decomposes into sulphur and the dioxide If air be excluded the ammonium sulphide acts as a reducing agent,[2] and the residual black powder has the composition U_7O_{10} Uranyl sulphide is formed in black, needle-shaped, tetragonal crystals when the green oxide is strongly heated with potassium thiocyanate and sulphur [3]

Uranium Red—When hydrogen sulphide is passed into a solution of uranyl nitrate to which about 2 8 molecular proportions of potassium hydroxide have been added, an orange-yellow precipitate is produced which dries to a hard, amorphous, brick-red mass and has the composition $5UO_3$,$2K_{20}$,H_2S_2 When this substance is treated with potassium carbonate or hydroxide it is converted into uranium red, which is a blood-red precipitate and dries to a brittle, amorphous mass resembling potassium permanganate in appearance and yielding a carmine-red powder This compound has not been obtained free from water, but has the composition $5UO_3$,$2K_{20}$,HS_2K,xH_2,O and is converted into the orange-yellow substance by carbonic acid Acids decompose it with liberation of half the sulphur as free sulphur and half as hydrogen sulphide[4] An analogous ammonium-red can be obtained by the action of ammomum sulphide on uranyl nitrate, and it was in this way that uranium red was first prepared [5]

[1] Colani, *Ann Chim Phys,* 1907, [8], **12,** 59

[2] For conditions of formation of *uranous* sulphide, see Wilke Dorfurt, *Chem Zentr* , 1921, l, 17O

[3] Milbauer, *Zeit anorg Chem,* 1904, **42,** 448

[4] Kohlschutter, *Annalen,* 190O, **314,** 311

[5] Patera, *J pr Chem,* 185O, 51, 122, Remete, *Annalen,* 1865, **126,** 209, Zimmermann, *ibid,* 188O, **204,** 204

The *selenides,* USe_2 and U_2Se_3, and the *telluride,* U_2Te_3, have been obtained in the crystalline state by heating the double chloride, $UCl_4,2NaCl$, in hydrogen containing the vapour of selenium or tellurium [1] A crystalline *uranyl selenule,* UO_2Se, is obtained by heating the green oxide with potassium cyanide and sulphur [2]

Uranyl Sulphite—When sulphur dioxide is passed into a solution of uranyl acetate, a crystalline precipitate is produced which has the empirical composition $UO_3\,SO_2,4H_{20}$ and was regarded by Girard[3] as the normal sulphite, $UO_2\,SO_3,4H_{20}$ Kohlschutter,[4] however, formulates it as a uranyl sulphurous acid, $SO_3H\,UO_2\,OH,3H_{20}$, and has prepared a number of complex alkali salts A basic *uranous sulphite,* $UO\,SO_3,2H_2O$, is also believed to exist

Uranous Sulphate, $U(SO_4)_2,9H_2O$, crystallises from aqueous solution in greenish, monochnic, twinned prisms and is isomorphous with crystallised thorium sulphate[5] It is, however, usually obtained with $8\,H_2O$,In order to prepare this salt, the green oxide, U_3O_8, is dissolved in dilute sulphuric acid and the solution allowed to crystallise after addition of some alcohol The mother-liquor, which contains uranyl sulphate, yields another crop of crystals of uranous sulphate after it has remained exposed to the light, inasmuch as the uranyl salt present in solution is reduced by the alcohol

Sodium thiosulphate has also been found a satisfactory reducing agent Uranous sulphate forms a stable hydrate with $4\,H_2O$ and several other hydrates, and is readily decomposed by water with formation of basic salts.[6] It forms double salts with the sulphates of the alkali metals, [7] as, for instance, $U(SO_4)_2,K_2SO_4,2H_2O$, and $U(SO_4)_2,4(NH_4)_2SO_4,3H_2O$

An *acid uranium sulphate,* $(USO_4)_2H$, containing tervalent uranium, has been obtained by an electrolytic method [8]

[1] Colani, *Compt rend,* 1903, **137,** 382.

[2] Mdbauer, *Zeit anorg Chem,* 1904, 42, 450.

[3] *Compt rend,* 1852, 34, 22

[4] *Annalen,* 1900, **311,** 1

[5] Rammelsberg, *Zeit Kryst Min,* 1889, **15,** 640 For a general discussion of the relation of uranous salts to those of thorium, see Fleck, *J Chem Soc* , 1914, **105,** 247

[6] Orloff, *J Buss Phys Chem Soc,* 1902, 34, 381, Oechsner de Coninck, *Bull Acad roy Belg,* 1901, 483, Kohlschutter, *Ber,* 1901, 34, 3628, Giohtti and Bucci, *Gazz,* 1905, **35,** 11, 151, 162, Giohtti and Liben, *ibid,* 1906, 36, 11, 443 p See Kohlschutter, *Ber,* 1901, 34, 3619

[8] Rosenheim and Loebel, *Zeit anorg Chem,* 1908, **57,** 234

Uranyl Sulphate, $UO_2SO_4,3H_2O$, is obtained by heating uranyl nitrate with sulphuric acid, and does not crystallise readily It dissolves in atout 20 parts of water at the ordinary temperature[1] When dissolved in moderately concentrated sulphuric acid, fine, yellowish-green, fluorescent crystals of UO_2 SO_4,H_2SO_4 are deposited on cooling, whilst from a solution in concentrated sulphuric acid crystals of a disulphate, UO_2 S_2 are deposited, which do not fluoresce By the gradual oxidation of the pitchblende found in Joachimsthal, several new uranium minerals have been formed Amongst the more important are certain sulphates, such as uranium-vitriol or johannite, and some basic sulphates

Uranyl sulphate forms double salts with the sulphates of the alkali metals, such as UO_2 $SO_4,K_2SO_4,2H_2O$ This is very soluble, and crystallises in yellow crusts, whilst the sparingly soluble ammonium salt, UO_2 $SO_4,(NH_4)_2SO_4,2H_2O$, is deposited in monochnio, lemon-coloured prisms [2]

Uranyl *selemte*, *selenate*, *chromates*, *molybdales*, and *tunqstates* have been studied, and their existence has been confirmed

URANIUM AND NITROGEN, PHOSPHORUS, ARSENIC, AND BORON

5O9 *Uranium Nitride*—Uranium combines directly with nitrogen at 10OO°, forming a yellow nitride,[3] the composition of which is not stated The *nitnde*, U_3N_4, is obtained as a grey or black powder by heating the tetrachloride in ammoma, mixing the product with ammonium chloride, and again igniting in an atinosphere of ammonia [4]

Uranyl Nitrate, $UO_2(NO_3)_2,6H_2$—This salt, which is commonly known as uranium nitrate, is prepared by dissolving any of the oxides of uranium in nitric acid It crystallises in fine, lemon-yellow, fluorescent, rhombic [5] prisms, which are soluble in half their weight of water [6] and deliquesce on exposure Icositetra-,

[1] Oechsner de Coninck, *Bull Acad roy Belg*, 1901, 222, 349, 1902, 94, 161

[2] See also Oechsner de Coninck, *Bull Acad roy Belg*, 1904, 1171, 1905, 6O, 94, 151, 182

[3] Moissan, *Compt rend*, 1896, **122,** 274

[4] Kohlschutter, *Annalen*, 1901, **317,** 158 See also Colani, *Compt rend*, 1903, **137,** 382, Haber and Greenwood, *Zett Elektrochem*, 1915, **21,** 241, Ger Pat 229126

[5] See, however, Quercigh, *Riv mm enst Ital*, 1915, 44, 6

[6] See Oechsner de Coninck, *Compt rend*, 1900, **131,** 1219, 1303, 1901, **132,** 90, 204, *Bull Acad roy Belg*, 1901, 222, *Bull Soc chtin*, 1915, [4], **17,** 422

tri-, di-, and mono-hydrates and the anhydrous salt are known to exist [1] The aqueous solution has an acid reaction owing to the partial hydrolysis of the salt[2] The nitrate is prepared cominercially by igniting ammonium uranate, $(NH_4)_2U_2O_7$ and dissolving the oxide in nitric acid[3] When crystals of uranyl nitrate are shaken or ground together, triboluminescence (emission of light under such conditions) is observed The explosive property of uranyl nitrate, which has in these circumstances frequently been observed, is apparently not an inherent property of the salt, but is attributed to the presence of an unstable compound produced when nitric acid is present during its recrystallisation from ether[4] Uranyl nitrate readily forms double salts with the alkali nitrates[5]

Uranium phosphide, U_3P_4 , *arsenide,* U_3As_4, and *antimonule,* U_3Sb_4, have been prepared by Colam[6] in a similar manner to the tellunde as black, crystalline powders, readily oxidised by nitric acid

Uranyl hypophosphite, $UO_2(H_2PO_2)_2$, and complex alkali salts have also been prepared[7]

Uranous metaphosphate, $U(PO_3)_4$, *uranous pyrophosphate,* UP_{207}, and *uranous orthophosphate,* $U_3(PO_4)_4$, have been prepared by Colam,[8] as well as complex salts with alkali- and alkaline earth-metal phosphates

Uranyl Phosphates —The normal orthophosphate is not known The mono-hydrogen salt, $H(UO_2)PO_4,4H_{20}$, is deposited in yellow, tetragonal plates from a solution of precipitated uranium phosphate in hot water acidified with hydrochloric acid[9] When uranic oxide is treated with phosphoric acid, a crystalline powder is obtained which is partially soluble in water, and the solution deposits yellow crystals of the di-hydrogen salt,

[1] de Forcrand, *Compt rend,* 1913, **156,** 1044, 1207, *Ann Chim,* 1915, [9], 3, 5, Germann, *J Amer Chem. Soc,* 1922, 44, 1466

[2] Ley, *Zed physikal Chem,* 1899, 30, 193, *Ber,* 1900, **33,** 2658, Dittrich, *Zeit physikal Chem,* 1899, 29, 449 See also Gomez, *Anal Fis Quim,* 1919, **17,** 24

[3] Janda, *Oesier Zeit Berg Hutt,* 1901, 49, 325

[4] Ivanov, *J Buss Phys Chem Soc,* 1912, 44, 678, *Chem Zeit,* 1912, **36,** 297, 499, Andrews, *ibid,* 1912, **36,** 1463, *J Amer Chem Soc,* 1912, 34, 1686, Eichhorn, *Chem Zeit,* 1914, 38, 139, Muller, *ibid,* 1916, 40, 38, 1917, 41, 439, Siemssen, *ibid,* 1919, 43, 267, *ibid* , 1922, 46, 450

[5] Meyer and Wendel, *Ber,* 1903, **36,** 4055, Rimbach, *ibid,* 1904, **37,** 461

[6] *Compt rend,* 1903, **137,** 382

[7] Rosenheim and Trewendt, *Ber,* 1922, **55,** *[E]t* 1957

[8] *Ann Chim Phys,* 1907, [8], 12, 59

[9] Bourgeois, *Bull Soc franc Mm,* 1898, 21, 32.

$UO_2(H_2PO_4)_2,3H_2O$. Both the *pyrophosphate* and the *meta-phosphate* have been described

Uranyl Ammonium Phosyj/iate, $UO_2NH_4PO_4$, is a greenish-yellow precipitate, insoluble in acetic acid, obtained by adding a soluble phosphate to a solution of uranyl acetate containing ammonium chloride This reaction is employed for the volumetric estimation of uranium, or of phosphoric acid

Uranyl Arsenates —Several of these compounds exist as minerals (Winkler) Trogente has the composition $(UO_2)_3(AsO_4)_2,12H_2O$, walpurgite is a basic arsenate of uranyl and bismuth, urano-spimte is an arsenate of uranium and calcium Various simple and complex arsenates have been prepared artificially

Uranium Boride, UB_2—When an electric are is produced between electrodes of compressed powdered boron and uranium, a bonde, UB_2, is formed, having a metallic appearance It is stable towards alkalis and acids with the exception of a nitric-hydrofluonc acid mixture, but is readily attacked by fused alkali hydroxide[1]

URANIUM AND CARBON

510 *Uranium Carbide,* UC_2, is obtained by strongly heating a mixture of 5OO grams of green uranium oxide and 6O grams of charcoal in the electric furnace, and is a crystalline, lustrous solid, which scratches rock crystal but not corundum, and has a density of 11 28 at 18°. It was considered by Moissan to possess the formula U_2C_3 It is attacked by fluorine when gently warmed, by chlorine at 35O°, and by oxygen at 37O° In contact with water, about one-third of the carbon is evolved as a gaseous mixture containing O 2-O 7 per cent of acetylene, 5 O-7 O per cent of ethylene, 78-81 per cent of methane, and 13 5-15 O per cent of hydrogen, the remainder of the carbon being converted into a mixture of solid and liquid hydrocarbons[2] When two pieces of the carbide are rubbed together, or even shaken in a bottle, brilliant sparks are given off

Uranyl Carbonates—Double salts of uranyl carbonate and alkali carbonates are obtained by precipitating a uranyl salt with an alkali carbonate The potassium salt, $UO_2\,CO_3,2K_2CO_3$,

[1] Wedekind, *Ber,* 1913, 46, 1198

[2] Moissan, *Compt rend,* 1896, **122,** 274, Lebeau, *Compt rend,* 1911, **152,** 955, *Bull Soc chim,* 1911, [4], 9, 512, Lebeau and Damiens, *Compt rend,* 1913, **156,** 1987, Polushkin, *Iron and Steel Inst, Carnegie Schot Mem,* 1920, 10, 129

is obtained by dissolving potassium uranate in potassium bicarbonate, and evaporating at a moderate temperature, when the compound is deposited in silky, crystalline crusts [1] Water dissolves at the ordinary temperature 7 per cent of its weight of this salt The corresponding sodium salt is obtained in a similar way, and possesses similar properties The ammonium compound, $UO_2\,CO_3,2(NH_4)_2CO_3$, is prepared by gently warming ammonium uranate with a solution of ammonium carbonate, and separates out on cooling in lemon-yellow, small, flat, monoclinic prisms It dissolves at the ordinary temperature in 20 per cent of water, but is less soluble in water containing ammonium carbonate The mineral liebigite is a uranyl calcium carbonate, $UO_2\,CO_3,CaCO_3\ 10H_{20}$, which occurs as an apple-green, warty mass, together with other uranium minerals

Cyanides, etc—Potassium uranyl cyanide,[2] $K_2[UO_2(CN)_4]$, uranyl cyanate,[3] $UO_2(CNO)_2$, and its complex salts, and uranyl thiocyanates,[4] $UO_2(CNS)_2,8H_2O$, and its double salts have been described

Organic Complexes—Complexes with foimic, acetic, oxalic, and a number of other organic acids have been studied [5]

Uranium Sihcide, USi_2, has been prepared by an alumino-thermic method It is a grey, lustrous powder which is not easily attacked by oxygen [6]

DETECTION AND ESTIMATION OF URANIUM

511 The uranous salts are green and pass rapidly by oxidation into the uranyl salts, which have a yellow colour, and yield with alkalis or alkali carbonates yellow precipitates of the alkali uranates Although uranyl salts do not give precipitates with cupferron (nitrosophenylhydroxylamine), uranous salts are completely precipitated by this reagent[7] Uranyl salts with ammonium sulphide yield a brown precipitate of uranyl sulphide,

[1] See also Oechsner de Coninck, *Bull Acad roy JBelg,* 1904, 363, 448

[2] Aloy, *Ann Chim Phys,* 1901, [7], 24, 412

[3] Pascal, *Bull Soc chim,* 1914, [5], **15,** 11

[4] Pascal, *Compt rend,* 1914, **158,** 1672

[5] For recent work, see Mazzucchelh and d'Alceo, *Atti R Accad Lincet,* 1912, [51 21, 11, 620, 85O, 1913, [5], 22, 1, 41, Courtois, *Compt rend* , 1914, **158,** 1511, 1688, Henri and Landau, *ibid,* 1914, **158,** 181, Mazzucchelh and Sabatini, *Oazz* , 1915, **45,** [2], 225, Bauer, *Schweiz Chem Zeit,* 1918, 2,40, Hatt, *Zeit physikal Chem,* 1918, 92, 513

[6] Defacqz, *Compt rend,* 1908, **147,** 105O

[7] Auger, *Compt rend,* 1920, **17O,** 995 See also Browning, *J Amer Chem Soc* , 1921, 43, 114

UO_2S, soluble in dilute acids and in ammonium carbonate, potassium ferrocyanide also yields a brown precipitate In the absence of sulphuric or]prdrochloric acid, uranium compounds in nitric acid solution yield, after the addition of excess of zinc, a yellow deposit on the metal, consisting of the hydrated trioxide [1]

In the genera] separation of the metals, uranium is obtained together with iron In order to separate these, advantage is taken of the solubility of uranium oxide and uranates in ammonium carbonate solution, a complex ammonium uranyl carbonate being formed When a uranium compound is fused with microcosmic salt in the oxidising flame, a yellow bead is obtained which on cooling becomes green, and on re-heating attains a darker green colour In the reducing flame, the bead is green

Most of the uranyl salts show a strong fluorescence, and give a characteristic absorption spectrum, which has been examined by Morton and Bolton,[2] whilst the fluorescence and phosphorescence spectra have been described by E Becquerel[3] and H Becquerel [4]

The uranium compounds do not impart any tint to the non-luminous gas flame The spark spectrum of uranium is a complicated one, and has been mapped by Thalen It consists of a large number of lines, of which five in the green are conspicuous by their brightness, viz , 5495, 5482 5480, 5478, and 5475, there are also three specially bright lines in the more refrangible portions, viz, 4473, 4363, and 4341 [5]

In order to estimate uranium it is precipitated as uranyl ammomum phosphate and weighed finally as uranyl pyrophosphate, $(UO_2)_2P_2O_7$ or it is converted into a uranyl salt, precipitated with ammonia,[6] and the washed precipitate con-

[1] Buell, *J Ind Eng Chem* , 1922,**14,** 593

[2] *American Chemist,* 3, 360,401 See also Vogel, *Ber* , 1875, 8, 1535, 1878, **11,** 915, Ziminermann, *Annalen,* 1882, **213,** 285, Mazzucohelli and Perret, *Atti R Accad Lincei,* 1913, [5], **22, 11,** 445

[3] *Compt rend,* 1872, 75, 1879, 88, 1237

[4] *Ibid,* 1885, **101,** 1252, 1907, **144,** 459

[5] See also Exner and Haschek, " *Die Spektren der Elemente bet normalem Druck,"* Leipzig, 1911, Siegbahn and Fnman, *Phystkal Zeit,* 1916, **17,** 17, 61, *Phil Mag,* 1916, [6], **31,** 403, 1916, [6], **32,** 39, Siegbahn, *Ber deut phystkal Ges,* 1916, 18, 15O, Dauvilher, *Compt rend,* 1921, **172,** 135O, Moir, *Trans Boy Soc South Africa,* 1921, **10,** 33

[6] Schwarz, *Helv Chim Acta,* 1920, 3, 33O A summary of the best methods is also given by Kern, *J Amer Chem Soc* , 1901, **23,** 685 Recent papers on the subject are Konig, *Chem Zett,* 1913, **37,** 1106, Wunder and Wenger, *Zeit anal Chem,* 1914, 63, 371, Turner, *Amer J Set,* 1916, [4], **42,** 109, Scholl, *J Ind Eng Chem* , 1919,**11,** 842, Pierle, *tbid,* 1920,**12,** 6O

verted by ignition in hydrogen into the brown oxide, UO_2 Small quantities may be estimated colonmetncally by comparison of the red coloration obtained when a uranyl salt is treated with sodium salicylate [1] Further, it may, like iron, be estimated volumetncally with a solution of potassium permanganate, the uranyl compound being previously reduced to the uranous state by the action of zinc and sulphuric acid, or of titanous sulphate,[2] or a solution of uranyl acetate may be titrated with sodium phosphate

The *Atomic Weight* of uranium was determined by Pebgot by the analysis of the tetrachloride, which he found to contain 37 2 per cent of chlorine, whence he calculated the atomic weight to be 237 6 He afterwards obtained the number 238 3 by the conversion of the' acetate, $UO_2(C_2H_3O_2)2,H_{20}$, into the dioxide Ziminermann, on the other hand, by the same method, obtained the number 237 7, whilst from a series of experiments in which he converted the dioxide into the green oxide and *vice versa* the number 237 8 was found [3] Aloy,[4] by the determination of the ratio UO_2 N in pure uranyl nitrate, obtained the value 237 6 (N = 13 93), which becomes 237 1 when the more modern value N = 13 90 is adopted Richards and Mengold,[5] by analysis of the very carefully purified tnbromide, obtained the value 238 5, whilst Lebeau[6] found the same number by the reduction of uranyl nitrate dihydiate to uranium oxide by heating the salt in a current of hydrogen to 1100° Oechsner de Coninck,[7] by igniting uranyl oxalate to the dioxide, obtained the value 238 4, that of Honigschmid,[8] by the conversion of the tetrabromide to silver bromide, was 238 175 Honigschmid and Horovitz,[9] by determinations of the same ratio, obtained an atomic weight of 238 043 ± 0 018 when the tetrabromide was finally sublimed in bromine vapour, and 238 159 + 0 023 when it was finally sublimed in nitrogen The actual atomic weight appears, therefore, to be not higher than 238 2, hence this number is now (1922) adopted

[1] Muller, *Chem Zeit,* 1919, 43, 739
[2] Newton and Hughes, *J+ Amer Chem Soc,* 1915, 37, *711
[3] *Annalen,* 1885, **213,** 299
[4] *Compt rend,* 1901, **132,** 551
[5] *Zeit anorg Chem,* 1902, **31,** 235
[6] *Compt rend,* 1912, **155,** 163
[7] *Ibid* , 1511
[8] *Ibid,* 1914, **158,** 2004
[9] *Monatsh,* 1916, 37, 185

GROUP V I I .

Sub-group (a)	*Sub-group (b)*
Manganese.	Fluorine Chlorine Bromine, Iodine

512 In the periodic system, manganese is the only representative of the even series of the seventh group known

The halogen elements have already been described in Vol I The analogy of manganese with these elements is almost entirely confined to the derivatives of its highest oxide, Mn_2O_7 To this oxide corresponds permanganic acid, $HMnO_4$, the salts of which are isomorphous with the perchlorates

In its general behaviour, however, manganese shows strong resemblances to chromium, iron, and its neighbours in the same horizontal series of the periodic table

Group	**IV**	**V**	**VI**	**VII**	VIII	**I**	**II**
Element	Ti	V	Cr	Mn	(Fe Co Nl)	Cu	Zn

Manganese, titanium, vanadium, chromium, iron, cobalt, and nickel are all hard, white metals of high melting point Manganese, iron, cobalt, and mckel, or their alloys, have strong magnetic properties The whole of the elements in the above series have a great tendency to form double or complex salts

They all form oxides of the type RO, and a series of salts in which the metal is divalent, many examples of isomorphism between manganous and the corresponding ferrous, cobaltous, mckelous, cupnc, and zinc compounds are known, but our knowledge of the divalent compounds of titamum, vanadium, and chromium is slight

With the exception of copper and zinc, all these elements form an oxide of the type R_2O_3 and salts in which they are trivalent, a well-known isomorphous series bemg the alums which are formed by titamum, vanadium, chromium, manganese, iron, and cobalt Manganese, like chromium and iron, forms mixed oxides with other elements of the type RO,Mn_2O_3; it also forms

an oxide, Mn_3O_4 or MnO,Mn_2O_3, analogous to the similar compounds of iron, cobalt and nickel

Manganese has a dioxide, MnO_2, isomorphous with rutile, TiO_2, vanadium, chromium, cobalt, and nickel also form dioxides, all of which, except the chromium compound, can act as weak acidic oxides and form manganites *(eg,* $CaMnO_3$), titanates, vanadites, cobaltites, and nickelites Though iron dioxide is unknown, corresponding compounds *(e g,* $BaFeO_3$) are known The dioxides of manganese, titamum, and vanadium can also act as basic oxides, and give rise to a series of salts in which the metals are tetravalent

Manganese, like chromium, has a trioxide, MnO_3, which is a purely acidic oxide and forms manganates *(e g ,* K_2MnO_4), which are isomorphous with the corresponding chromates and ferrates

MANGANESE Mn = 54 93 At No 25

513 Black oxide of manganese, manganese dioxide, or pyrolusite was known in early times, but for a long period this compound was confounded with magnetic iron ore, and this fact explains the statement of Pliny that loadstone was employed in the manufacture of glass for the purpose of removing or attracting the impurities of colouring matters out of the glass He distinguished, moreover, special kinds of magnes, one of these, which is of the feminine gender, does not attract iron " magnes qui niger est et feminei sexus, ideoque sine viribus " This probably was manganese dioxide The derivation of the word magnet appears to be doubtful In the Middle Ages loadstone was distinguished as *magnes* or *magnesius lapis* Pyrolusite, however, was termed *magnesia* probably because Pliny had already pointed out the existence of two species of loadstone Many of the alchemists, however, believed it to be an ore of iron They likewise mention its use in glass-making, and in the Latin manuscripts of the sixteenth century it is termed *lapis manganensis,* or some similar name

In 1740, Pott, in his treatise entitled " *Examen chymicum magnesia vilranorum, Germanis Braimstem"* proved that the black oxide of manganese did not contain iron, and that from it a definite series oi salts could be obtained He did not, however, suggest that it contained a new metal Scheele's celebrated investigations on manganese were published in the year 1774 In these he showed that the mineral manganese possesses a strong attraction for phlogiston, and that it takes this substance up,

uniting with acids to form colourless salts, this being explained, according to our present views, by the fact that it gives off oxygen On the other hand, the solutions of manganese which did not contain phlogiston were shown to be coloured Scheele believed that the earth contained in this mineral resembled lime, but in the above-mentioned year Bergman, founding his deductions upon Scheele's experiments, came to the conclusion that manganese was probably the calx of a new metal, inasmuch as it coloured glass, and its solutions were precipitated by prussiate of potash, these being reactions common to the metallic calces Gahn was, however, the first to isolate the new metal In Germany, this was called braunstem-konig or braunstein-metal In other languages, in which braunstem was termed *magnesia niger, in* order to distinguish it from *magnesia alba,* the metal was called manganese or manganesium

Manganese occurs in nature chiefly as the dioxide or pyrolusite, MnO_2 It is found also in the following minerals braumte, Mn_{203}, hausmanmte, Mn_3O_4, psilomelane, $(Mn,Ba)O,MnO_2$, manganite, Mn_2O_3,H_2O, rhodocrosite or manganese spar, $MnCO_3$, which also frequently occurs as an isomorphous constituent in ferrous carbonate and other similar minerals Manganese occurs also as alabandite or sulphide of manganese, MnS, and hauente, or manganese disulphide, MnS_2 It likewise forms an essential constituent of many other minerals, although occurring in them only in small quantity Thus, for instance, most silicates contain manganese, which frequently imparts to them their peculiar colour By means of these minerals the metal manganese passes into the soil and into drainage water, whence it is absorbed in small quantities into the bodies of plants and ammals

The natural oxides of manganese usually contain traces of potassium, rubidium, silver, and copper, whilst gallium, indium, and thallium are occasionally present [1]

514 *Preparation of Metallic Manganese*—The higher oxides of manganese can be reduced only to manganese monoxide at a red heat, the metal not being formed either when the oxide is heated alone or mixed with charcoal in a current of hydrogen until the temperature rises to white heat The original method of preparing the metal, proposed by John,[2] depends upon this fact Finely divided oxide of manganese, obtained by the

[1] **Hartley and Bamage, *Journ Chem Soc*, 1897, 71, 533**
[2] **Gehlen's *Journ Chem Phys*, 3, 452**

calcination of the carbonate in a covered crucible, is well mixed with carbon, and the mixture formed into a paste with oil, the paste is then introduced into a crucible lined with charcoal, and the upper portion completely filled with powdered charcoal The crucible is first heated to redness for half-an-hour to sohdfy the mass, after which the cover is carefully luted down, and the whole exposed to a wind furnace for an hour-and-a-half to the highest temperature which the crucible can support without fusing The regulus thus prepared contains both carbon and silicon derived from the ashes of the wood charcoal By igniting the metal a second time in a charcoal crucible with some borax it was obtained by John in a more fusible and brilliant state, and so free from carbon that it left no black residue when treated with an acid

Deville's method[1] consists in mixing red manganese oxide, Mn_3O_4, prepared by heating the artificial dioxide, with sugar charcoal insufficient in quantity for complete reduction The mixture is heated to whiteness in a doubly-lmed crucible The regulus obtained is coated with a violet, crystalline mass, apparently calcium-manganese spinel, CaO,Mn_2O_3

Jordan [2] describes a method of preparing metallic manganese on a large scale by treating manganese ores in a blast furnace The metal obtained is really ferro-manganese, containing 85 per cent of manganese, 6 per cent of carbon, 8 per cent of iron, and traces of silicon, sulphur, and phosphorus

Other processes of preparing the metal consist in igniting a mixture of fluor-spar and chloride of manganese with metallic sodium,[3] or gradually adding 15 grams of metallic magnesium to a fused mixture of 10O grams of manganese chloride and 200 grams of potassium chloride [4] The metal may be obtained also by the electrolysis of a concentrated solution of the chloride according to the process described by Bunsen,[5] or by heating the amalgam, which can be prepared electrolytically [6]

The method of reducing manganese oxide by aluminium is due to Greene and Wahl,[7] who devised it for producing the pure metal cheaply The metal they obtained contained 96 5 per cent of manganese, 2 0 of iron, and 1 5 of silicon

A considerable amount of metallic manganese has been made

[1] *Ann Chim Phys*, 1856, [3], 46, 182 [2] *Compt tend*, 1878, 86, 1374
[3] Brunner, *Fogg Ann* , 1857,101, 264 [4] Glatzel, *Ber*, 1889, 22, 2857
[5] *Pogg Ann* , 1854, 91, 619 [6] Prelmger, *Monatsh* , 1894,14, 353
[7] *Trans American Institute of Mining Engineers*, 1893, 21, 887

by the Goldschmidt process (p 737) of a high degree of purity Lebeau [1] has, however, shown that metal so produced may contain as much as 5 25 per cont of silicon

With regard to the preparation of manganese in the electric furnace,[2] Moissan proved that by using excess of oxide, the reduced metal might be obtained free from carbon and silicon This method has recently been put into cominercial use, but the efficiency of the process is not such as to yield metal at a low cost, for Moissan has shown that manganese is highly volatile at electric furnace temperatures, and that as much as 400 grams of the metal may be volatilised in ten minutes in the electric arc High grade ferro-manganese, and other alloys such as sihco-manganese, are produced in large quantities in electric furnaces

Manganese has been obtained also by electrolysis Ferro-manganese anodes are allowed to dip into fused sodium chloride, and an electric current is passed Pure manganese is deposited at the cathode[3] It has been prepared also by electrolysing manganese dioxide dissolved in fused fluorspar [4]

Properties —Small amounts of impurities influence the properties of manganese considerably, since none of the methods of preparing the metal yield an absolutely pure product, its properties depend largely on how it has been prepared Obtained by the reduction process, it is a grey or reddish-white metal, having the colour and appearance of cast iron It is very hard and brittle, has a specific gravity of about 7 3, and oxidises so easily in the air that it must be kept under rock-oil or in well-sealed vessels Ferro-manganese is, however, unalterable in the air Manganese is readily dissolved by all dilute acids, yields sulphur dioxide with hot concentrated sulphuric acid,[5] and decomposes water with evolution of hydrogen, even in the cold, more rapidly when heated It melts [6] at 1260° and boils under atinospheric pressure at about 1900° (Greenwood)[7], its atomic heat increases from 4 51 between the temperatures —188° and —79°, to 5 90 at 0°, 6 29 at 100°, and 9 09 at 500° (Estreicher and Staniewski[8], Laminel [9]) its average compressibility between 100 and 500

[1] *Ann Chun Phys* , 1904, 1, 553
[2] *Compt rend*, 1892, **116,** 1429
[3] Ger Pat 74959
[4] Eng Pat 17190
[5] Adie, *Proc Chem Soc*, 1899,**15,** 133
[6] Burgess and Waltenberg, *J Washington Acad Sci*, 1913, 3, 371
[7] *Proc Roy Soc* , 1909, 82, *[A],* **396**
[8] *Bull intern Acad Sci Cracovie*, **1912,** *[A],* 834
[9] *Ann Physik,* **1905,** (iv), **16, 551**

megabars is 0 000,000,67 (Richards and Stull) [1] It is paramagnetic, but becomes ferromagnetic on heating it is exceptional in that its magnetic properties are not intensified by cooling in solid hydrogen (Weiss and Kamerhngh 0nnes) [2] Manganese combines rapidly with mtrogen above 1210°.

515 *Alloys of Manganese* —The alloys of manganese and copper closely resemble those of tin and copper [3] Those which contain from 5 to 8 per cent of manganese are malleable, but those in which a higher percentage of manganese is present become grey and brittle

Manganese bronze is made by adding cupro-manganese containing about 25 per cent of manganese to molten brass For industrial purposes it contains from traces to 2 per cent of manganese, 39 to 41 per cent of zinc, and less than 1 per cent each of tin, iron and aluminium, the rest being copper

Manganm is a copper-manganese alloy containing small quantities of nickel Its electrical resistance has a very low temperature coefficient, and it is largely used in the manufacture of electrical resistances

Alloys of manganese with aluminium, antimony, tin, bismuth, aisenic, and boron are noteworthy owing to the remarkable magnetic properties which they possess [4]

The alloys of manganese and iron, such as manganese steels, spiegel iron, and ferro-manganese, will be described under iron

Manganese Amalgam is prepared by electrolysing a saturated solution of manganous chloride, mercury being used as the negative pole

C0MPOUNDS OF MANGANESE

MANGANESE AND OXYGEN

516 Manganese forms a series of oxides, of which the following are the best defined

Manganese monoxide, MnO,
Trimanganese tetroxide, Mn_3O_4,
Manganese sesquioxide, Mn_2O_3
Manganese dioxide, MnO_2,
Manganese trioxide, MnO_3,
Manganese heptoxide, Mn_2

[1] *Pub Cam Inst*, 1907, 76, 55 [2] *Compt rend* , 1910,150, 687
[3] Valenciennes, *Compt rend*, 1870, 70, 607
[4] Hogg, *Brit Assoc Reports*, 1892, 671, Heusler, *Ber deut physikal Ges*, 1903, 5, 220

The first of these is a powerful basic oxide, whilst the sesquioxide is feebly basic, giving rise to an unstable series of salts, and the oxide, Mn_3O_4 behaves in many respects as a compound of the two The dioxide acts as a weak acidic oxide, yielding with strong bases salts known as the mangamtes Manganese trioxide and the heptoxide are well-marked acid-forraing oxides The manganates, derived from mangamc acid, H_2MnO_4, are very unstable, and as already mentioned are isomorphous with the sulphates and chromates Permangamc acid, $HMnO_4$, is a strong acid and yields stable salts, which are isomorphous with the perchlorates

Manganese Monoxide, or *Manganous Oxide,* MnO, is best prepared by fusing together a mixture of equal parts of anhydrous manganese chloride and sodium carbonate to which some ammonium chloride has been added, and lixiviating the fused mass with water[1] It is obtained also when a higher oxide or the carbonate is ignited in a current of hydrogen Manganous oxide is a greyish-green powder, which fuses at 1650° [2] without loss of oxygen It has a specific gravity of 5 09 When the powdered oxide is heated in hydrogen containing a verv small quantity of hydrogen chloride, it is obtained crystallised in transparent, regular octahedra of an emerald-green colour and an adamantine lustre [3] It has been found in Sweden as the crystalline mineral manganosite

Manganous Hijdroxide, $Mn(OH)_2$, is obtained as a white precipitate when caustic alkali is added to the solution of a manganese salt As it oxidises rapidly in the air and assumes a brown colour, forming the oxide Mn_3O_4 and finally Mn_{203}, it must be precipitated in an atinosphere free from oxygen, and dried at a moderate heat in a current of hydrogen The powder thus obtained is frequently pyrophonc and when touched with a piece of red-hot charcoal it begins to glow at the point of contact, the oxidation proceeding rapidly throughout the mass It occurs in Sweden as the mineral pyrochroite

When ammoma is added to a solution of a manganous salt containing an ammonium salt, no iminediate precipitation occurs, but on standing a precipitate separates out which consists of manganous hydroxide, if air be excluded, but of a brown hydrated oxide in the presence of air When manganous hydroxide is tieated with an ammonium salt it dissolves to an extent pro-

[1] **Liebig and Wohler,** ***Fogg Ann*** **, 1830, 21, 584**
[2] **Tiede and Birnbrauer,** ***Zeit anorg Chem*** **, 1914, 87, 129**
[3] **Deville,** ***Compt rend,*** **1861, 53, 199**

portional to the concentration of ammonium 10ns in the solution, probably complex ions containing ammonium and manganese are formed [1]

The manganous salts, MnR^{r}_{2}, are usually faintly pink-coloured, although, according to some chemists, this coloration is due to the presence of a trace of a mangamc compound The halogen salts, as well as the nitrate and sulphate, are readily soluble in water

Mangano-Mangamc Oxide, Red Oxide of Manganese, or Tn-*manganese Tetroxide,* Mn_3O_4, occurs with other manganese ores, and also by itself as the mineral hausmanmte This mineral crystallises in acute tetragonal pyramids, and one of its best localities is Ilmenau in Thunngia Its specific gravity is 4 85 If manganese monoxide is heated in contact with air, or if the higher oxides are strongly heated either in contact or out of contact with air, this same compound is obtained in the form of a browmsh-red powder, which then has a specific gravity of 4 72, and is converted into crystals of hausmanmte by being gently heated in a slow current of hydrogen chloride [2] It is obtained in the crystalline form also by heating a mixture of manganese sulphate and potassium sulphate to bright redness,[3] or by treating a mixture of manganous oxide and calcium chloride in the same way[4] This oxide dissolves in cold concentrated sulphuric acid, giving rise to a red solution containing a mixture of manganous and manganic sulphates, whilst acetic acid dissolves one-third of the manganese as manganous acetate and leaves the remainder in the form of the sesquioxide Mixed oxides of the type Mn_2O_3RO, which appear to be isomorphous with hausmanmte (Gorgeu [5]), have been prepared by fusing the corresponding sulphates and by the ignition of the metal IC mangamtes Hence the red oxide is often considered to be a compound having the formula MnO,Mn_2 On the other hand, other reactions suggest that it has the formula $2MnO,MnO_2$, thus, on heating with dilute sulphuric acid, manganous sulphate and manganese dioxide are formed, and boiling nitric acid decomposes it in a manner similar to that in which it acts on red lead

$$Mn_3O_4 + 4HNO_3 = 2Mn(NO_3)_2 + MnO_2 + 2H_2O$$

[1] **Herz,** ***Zeit anorg Chem,*** **1899, 21, 243, 22, 279**
[2] **Deville,** ***Compt rend*** **,1861, 68, 199**
[3] **Debray,** ***Compt rend,*** **1861, 52, 985**
[4] **Kuhhnann,** ***Compt rend*** **,1861, 52, 1283**
[5] ***Bull Soc chim,*** **1903, [3], 29, 1111, 1167**

Chlorine gas is given off when this oxide is heated with hydrochloric acid, and manganous chloride is formed

$$Mn_3O_4 + 8\,H(A\ 3MnCl_2 + 4H_{20} + C1_2$$

Manganic Oxide or *Manganese Sesquioxide,* Mn_2—This oxide occurs as the mineral braunite in obtuse tetragonal pyramids It possesses a sub-metallic lustre, has a dark brownish-black colour, and a specific gravity of 4 75 It may be obtained artificially by igniting any of the oxides of manganese in a mixture of oxygen and nitrogen containing not more than twenty six per cent of oxygen [1] It then forms a black powder having a specific gravity of 4 32

Manganic Hydtoxide, MnO(OH), occurs in nature as manga-mte in steel-grey or arsenic-black crystals belonging to the tetragonal system, and having a specific gravity of 4 3 It is usually accompanied by other manganese ores, calc-spar, and heavy-spar In general appearance it closely resembles pyrolusite but it may be distinguished from this compound by its giving a brown instead of a black streak when rubbed on an unglazed porcelain plate When the mineral is heated at 270-310° in the air it is converted without change of form into the dioxide [2] Manganic hydroxide is formed when manganous hydroxide is allowed to oxidise in moist air It may be prepared also by passing chlorine into water in which an excess of manganese carbonate is suspended, or by decomposing the corresponding manganic sulphate with water (Canus) [3] It forms a daik-brown powder which gives off its water at a temperature above 100° It dissolves in hot nitric acid

$$2MnO(OH) + 2HNO_3 = Mn(NO_3)_2 + MnO_2 + 2\,H_{2}.$$

From this reaction it would appear that in constitution this body resembles lead sesquioxide and analogous compounds, having the constitution MnO,MnO_2, but in other reactions it acts as a feebly basic oxide, the salts of which, with a few exceptions, are very unstable

The manganic salts, MnE_3 or Mn_2R_3, are unstable, strongly coloured substances The fluoride, sulphate, phosphates, and salts of some organic acids are "comparatively stable, as also are some double or complex salts, such as the double fluorides and

[1] Dittinar, *Journ Chem Soc* , 1864,**17,** 294
[2] Gorgeu, *Compt rend,* 1888,**106,** 1101
[3] *Annalen,* 1856, 98, 53

chlorides, the manganicyanides, and the alums Manganic chloride, bromide, lodate, penodate, selenite, and arsenate have been prepared

MANGANESE DIOXIDE AND THE MANGANITES

517 *Manganese Dioxide, Manganese Peroxide,* or *Black Oxide of Manganese,* MnO_2, is the most important ore of manganese It occurs in rhombic crystals and in crystalline and amorphous masses, being known to the mineralogist as pyrolusite It possesses a metallic lustre, an iron-black or dark steel-grey colour, and a black streak It is opaque and rather brittle, and has a specific gravity of 4 82 The most celebrated localities for this mineral are Ilmenau in Thurmgia, near Platten in Bohemia, near Mahnsch-Trubau in Moravia, on the Lahn, and in the Caucasus, France, Spain, and North America It occurs in the United States, abundantly at Vermont, and in Red Island Bay at San Francisco, and also in New Brunswick and Nova Scotia, large quantities too are found in India It is likewise found in Devonshire Pyrolusite seldom occurs in the pure state, but mixed with other manganese ores such as psilomelane, $(Mn,Ba)O,2MnO_2$, and manganite It almost always contains ferric oxide, silica, lime, carbonic acid, and traces of the oxides of cobalt and nickel Pure manganese dioxide is obtained by melting about 600 grams of the crystallised nitrate and warming until red fumes appear, the clear liquid is then decanted from the lower oxides which first separate out, and is heated in another vessel at 150-160° for 40-60 hours [1] If manganous carbonate is heated to 260°, in presence of air, and the residue then treated with very dilute cold hydrochloric acid, pure manganese dioxide remains behind (Forchhaminer)

A brown precipitate approximating in composition to hydrated manganese dioxide can be obtained from the manganous salts by the aid of a large number of oxidising agents such as potassium permanganate (p 1189), sodium hypochlorite, ammonia and bromine, nitric acid and sodium chlorate, ammonium persulphate and sulphuric acid,[2] and ozone [3]

It appears to be almost impossible to prepare perfectly pure hydrated manganese peroxide,[4] since this substance very readily

[1] **Gorgeu,** ***Bull Soc chim,*** **1890, [3], 4, 16**
[2] **Marshal],** ***Journ Chem Soc*** **, 1891, 59, 771**
[3] **Jannasch and Gottschalk,** ***Ber,*** **1904, 37, 3111**
[4] **Gorgeu,** ***Compt rend,*** **1890,110, 1134**

loses a portion of its oxygen, forming mixtures of the composition $xMnO + yMnO_2$, and moreover readily combines with bases forming mangamtes *9* Products of constant composition appear to be obtainable only from solutions acidified with a mineral acid[x] Thus the oxide formed by the reduction of permanganic acid by manganese sulphate, and by the decomposition of permangamc acid in presence of hydrated manganese dioxide, varies in composition from $5MnO_2 + MnO$ to $15MnO_2 + MnO$ On the other hand, the oxide precipitated from manganous sulphate by dilute potassium permanganate at 80° in presence of zinc sulphate contains all the manganese in the form of dioxide, but combined with alkali The oxide precipitated from manganese nitrate by nitric acid and sodium chlorate contains 98 per cent of the manganese as dioxide,[2] and that obtained with ammonium persulphate also contains less than the theoretical amount of oxygen[3] A similar oxide may also be prepared by treating mangamc hydroxide with hot nitric acid,[4] or by adding potassium permanganate to sodium thiosulphate solution The hydroxide thus obtained, after washing with water, is soluble in water, yielding a brown solution to which the name of manganous acid has been given This solution turns blue litinus paper red, and does not undergo alteration on standing for many weeks, but small quantities of acid oi alkali produce an instant precipitation Manganous acid appears to be identical with a colloidal solution of manganese dioxide, which can be conveniently prepared by the action of ammonia on a boiling solution of potassium permanganate [5] Manganese dioxide, like lead dioxide, possesses at the same time feebly basic and feebly acid properties Of the salts in which manganese behaves as a quadrivalent basic element, only the chlonde, sulphate, and selemte have been isolated Among the most stable are certain double or complex salts, K_2MnF_6, K_2MnCl_6, $K_2Mn(IO_3)_6$

On heating, manganese dioxide loses oxygen and forms the sesquioxide

$$4MnO_2 = 2Mn_{203} + O_2$$

The action is reversible, when the pressure of oxygen is below a certain value depending on the temperature the reaction goes towards the right hand side of the equation, when it is above that

[1] Rupp, *Zeit anal Chem,* 1903, **42,** 732
[2] Gooch and Austin, *Amer J Sci,* 1898, [4], 5, 260
[3] von Knorre, *Zeit angew Chem,* 1901,14, 1149
[4] Gorgeu, *Ann Chim Phys,* 1862, [3], **66,** 166
[5] Guy, *J Physical Chem.,* **1921, 26, 416**

value towards the left [1] When heated to higher temperatures the red oxide, Mn_3O_4, is produced

Manganese dioxide has long been used for the preparation of colourless glass, and hence pyrolusite has been known as *savon des verriers* Its mineralogical name, indeed, has reference to this employment of the mineral (from *irvp*, fire, and *\vco*, I wash) It serves also for the preparation of the manganese compounds and of oxygen, but by far the largest quantity of the mineral is employed for making chlorine, used in the manufacture of bleaching powder

The Mangamtes—Manganese dioxide combines with several basic oxides to form compounds which may be considered as salts of manganous acid The composition of these compounds seems to depend on the amount of alkali which is present A large number of them have been described *Potassium Manganite*, $K_2Mn_5O_{11}$, is obtained as a yellow precipitate when carbon dioxide is passed into a solution of potassium manganate, K_2MnO_4 *Calcium Manganite*, $CaMn_5O_{11}$, is a blackish-brown precipitate formed when a solution of manganous nitrate is poured into an excess of bleaching powder solution Many other compounds, such as Ca_2MnO_4, $CaMnO_3$, $CaMn_2O_5$, and $CaMn_3O_7$, have been prepaied

518 *Regeneration of Manganese Dioxide from the Chlorine Residues* —Before the year 1856 the whole of the manganese chloride obtained in the manufacture of chlorine from manganese dioxide and hydrochloric acid was allowed to run to waste In 1821 Forchhaminer [2] observed that when manganous carbonate is heated to 260° in an open vessel it is converted into dioxide Charles Dunlop [3] applied this reaction to the regeneration of manganese dioxide from the chlorine still liquors, the manganous carbonate being prepared by heating manganous chloride solution with calcium carbonate under pressure In 1857 this process was adopted by Messrs Charles Tennant and Co , at St Rollox, but the process was not adopted elsewhere

A much less troublesome process was invented by Walter Weldon, in 1867, and first practically carried out at Messrs Gamble's works at St Helens in 1868, it is now universally adopted wherever chlorine is made from manganese dioxide and hydrochloric acid

The crude manganese chloride solution remaining in the stills,

[1] **Askenasy and Klonowski, *Zeit Ekktrochem*, 1910,16, 107**
[2] ***Ann Phil*, 1821,17,60**
[3] ***Report of Patent Inxenhicms*, March, 1856, p 236**

I (Fig 190), which are fitted for using native manganese dioxide, is run into the well, and treated with limestone dust, which neutralises the residual frft hydrochloric acid, precipitates the sulphuric acid present as impurity in the hydrochloric acid in the form of calcium sulphate, and then precipitates the ferric chloride as ferric hydroxide, the muddy liquor is thrown by the pump, L, into the settling tanks, A, from which the clear manganous chloride solution is run into the oxidiser, B, while the sediment is run into the shute, H, and so to the drains In the agitator, E, lime is slaked to form a thick cream which is run through a sieve into a store and measuring tank, whence it is pumped as required into the oxidiser, B

If exactly the theoretical amount of milk of lime be added according to the equation

$$MnCl_2 + Ca(OH)_2 = Mn(OH)_2 + CaCl_2,$$

it is found that the whole of the manganese is not precipitated and the mixture absorbs oxygen exceedingly slowly, only half the manganese being converted into dioxide, by adding ten per cent more lime the liquor becomes free from manganese, but the most rapid absorption of oxygen and the most readily settling mud are obtained only by employing about sixty per cent more lime (Weldon) When air is pumped by the pipe, C, through this mixture at 55°, the alkalinity disappears owing, to the formation of calcium mangamte, CaO,MnO_2, and acid manganite, $CaO,2MnO_2$, whilst some of the manganous oxide is converted into manganous manganite, MnO,MnO_2

$$lOOMnO + 60CaO + 860 = 12(CaO,2MnO_2) + 48(CaO,MnO_2) + 14(MnO,MnO_2),$$

at about which stage the oxidation practically ceases An additional quantity of the manganous chloride is next added, which instantly reacts with the CaO,MnO_2, thus

$$48(CaO,MnO_2) + 24MnCl_2 = 24(CaO,2MnO>) + 24MnO + 24CaCl_2,$$

and the blowing being continued, the manganous oxide is oxidised to manganous mangamte

$$24MnO + 120 = 12(MnO,MnO_2)$$

The effect of the whole operation may be summarised thus

$$124MnCl_2 + 160Ca0 + 980 = 36(Ca0,2MnO_2) + 26(MnO,MnO_2) + 124CaCl_2$$

The resulting thin mud is run from the bottom of the oxidising tower by the pipe shown in the figure into one of the four settling tanks, G, from which the clear calcium chloride liquor is drawn

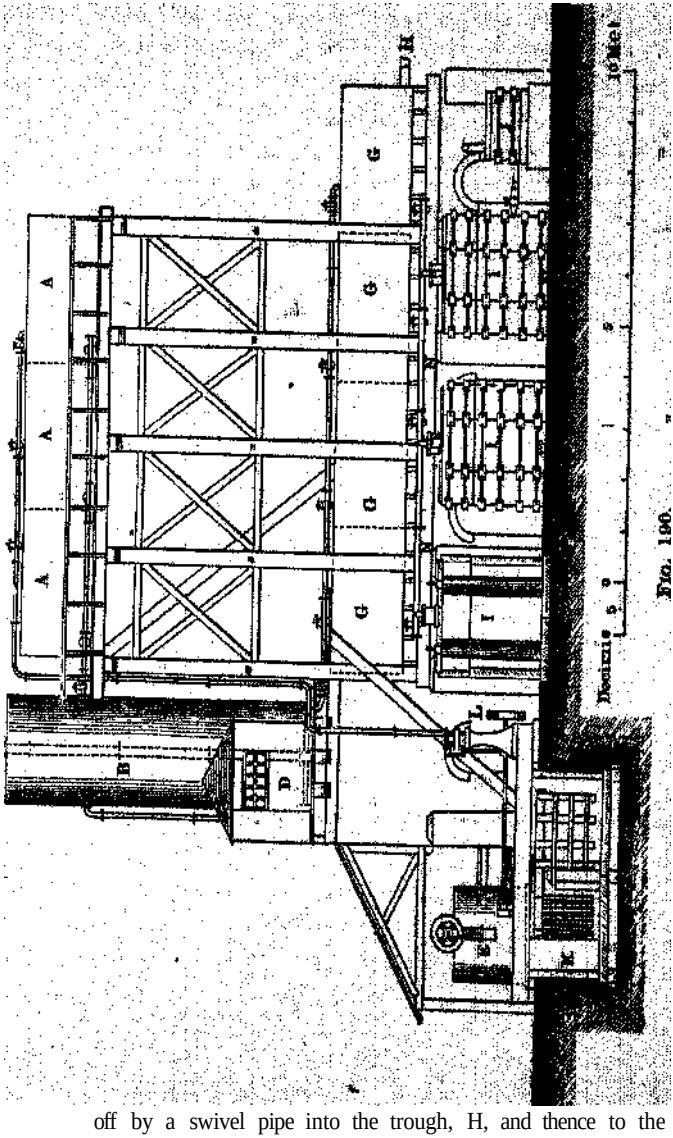

FIG. 190.

off by a swivel pipe into the trough, H, and thence to the drains

When the plant is stocked with manganous chloride solution and Weldon mud the treatment of native ore is suspended and

the chlorine made entirely from the mud, and as this, unlike the native ores, contains no iron which requires to be eliminated by precipitation with hmestoie dust, it now becomes possible to avoid the use of the latter and to utilise the excess of acid which is invariably left in the chlorine still, even when the artificial mud is used But as crude hydrochloric acid always contains sulphuric acid, which was eliminated as calcium sulphate in the mud run off from the settling tanks, A, in the process so far described, it is necessary to provide a new outlet for this impurity, and this is done by treating the hydrochloric acid with a portion of the waste calcium chloride liquor, the calcium sulphate formed being separated by a sand-filter The purified acid is then used to generate chlorine in the stone stills I, with thick manganese mud run from the settlers, G, by the pipe, N When no more chlorine is evolved the residual liquor is treated with an excess of mud more than enough to neutralise all the residual free acid, amounting to about 0 7 per cent of the liquor, the mixture is then allowed to settle, and the much richer manganese mud settling out forms part of the next batch to be treated with acid, the reaction being approximately

$$36(Ca0,2MnO_2) + 18HC1 = 18MnO_2 + 27(CaO,2MnO_2) + 9CaCl_2 + 9H_20$$

The Weldon operation thus converts $124MnCl_2$ into $98MnO_2$ -f 26MnO The equations given above are intended to express the average results obtained [x]

MANGANESE TRIQXIDE AND HEPTOXIDE, MANGANIC ACID, PERMANGANIC ACID, AND THEIR SALTS

519 In his work entitled *The Prosperity of Germany*,[2] published in 1656, Glauber mentions that when manganese is fused with fixed saltpetre (caustic potash) a mass is produced from which he obtained " a most dainty purple fiery liquor," this afterwards turning blue, red, and green In 1705 an anonymous treatise appeared, entitled *Key to the Secret Cabinet of Nature's Treasury, in* this it is stated that the product obtained by fusing saltpetre and manganese yields a solution of which the colour alters, first being grass-green, then sky-blue, violet-coloured, and

[1] **A detailed description is to be found in Lunge's *Sulphuric Acid and Allah Manufacture,* Vol I I I**

[2] **Packe's translation, 1687, p 353**

lastly rose-red The changes of colour which are here given are exactly the opposite of those which Glauber noticed Pott in 1740 described these changes, believing that they had -not been previously noticed, and Scheele, who endeavoured to explain these phenomena, gave to the colouring material the name of mineral chameleon, a term which had previously been apphed to other mineral colouring matters capable of undergoing changes of tint The properties of this mineral chameleon were afterwards investigated by many chemists, but it was not until the year 1817, when Chevillot and Edwards [1] investigated the subject, that a rational view of its composition was arrived at They showed that when much alkali is employed a green compound is formed, that when, on the other hand, an excess of manganese is fused with potash a red body is produced, and they succeeded in preparing the substance obtained by the latter reaction in the crystalline form They also showed that an absorption of oxygen takes place, and consequently they assumed that the potash salt forms with manganese a manganate, and that the green salt contains more base than the red Forchhaminer [2] investigated the subject in 1820, and ascribed the difference in colour to the existence of two distinct acids, but Mitscherlich [3] first showed their exact composition

Manganese Tnoxide, MnO_3, is a deliquescent, amorphous, reddish mass, prepared by dropping a solution of potassium permanganate in concentrated sulphuric acid on to dry sodium carbonate [4]

$$2(MnO_3)_2SO_4 + 2Na_2CO_3 = 2Na_2SO_4 + 4MnO_3 + 2CO_2 + O_2$$

It is formed only in extremely small quantity, and is carried forward by the carbon dioxide as a pink fume, which may be caught on fragments of glass placed in a freezing mixture

When thrown into water it is decomposed as follows [5]

$$3MnO_3 + H_2O = 2HMnO_4 + MnO_2$$

The *manganates* have a green colour, and their solutions are stable only when they contain large quantities of free alkali If carbon dioxide is passed through them, or if they are diluted with much water, or made slightly acid, the liquid passes from

[1] *Ann Chim Phys*, **1817,** [2], 4, 287
[2] *Ann Phil*, 1820,**16, 130, 1821,17, 160**
[3] *Pogg Ann* , 1832, 25, 287
[4] Franke, *J pr Chem*, **1887,** [2], **6,** 893
[5] Thorpe and Hambly, *Journ Chem Soc* , 1888, 53, 175

the chlorine made entirely from the mud, and as this, unlike the native ores, contains no iron which requires to be eliminated by precipitation with limestone dust, it now becomes possible to avoid the use of the latter and to utilise the excess of acid which is invariably left in the chlorine still, even when the artificial mud is used But as crude hydrochloric acid always contains sulphuric acid, which was eliminated as calcium sulphate in the mud run off from the settling tanks, A, in the process so far described, it is necessary to provide a new outlet for this impurity, and this is done by treating the hydrochloric acid with a portion of the waste calcium chloride liquor, the calcium sulphate formed being separated by a sand-filter The purified acid is then used to generate chlorine in the stone stills I, with thick manganese mud run from the settlers, G, by the pipe, N When no more chlorine is evolved the residual liquor is treated with an excess of mud more than enough to neutralise all the residual free acid, amounting to about 0 7 per cent of the liquor, the mixture is then allowed to settle, and the much richer manganese mud settling out forms part of the next batch to be treated with acid, the reaction being approximately

$$36(CaO,2MnO_2) + 18HC1 = 18MnO_2 + 27(CaO,2MnO_2) + 9CaCl_2 + 9H_{20}$$

The Weldon operation thus converts $124MnCl_2$ into $98MnO_2 + 26MnO$ The equations given above are intended to express the average results obtained [x]

MANGANESE TRIQXIDE AND HEPTOXIDE, MANGANIC ACID, PERMANGANIC ACID, AND THEIR SALTS

519 In his work entitled *The Prosperity of Germany*,[2] published in 1656, Glauber mentions that when manganese is fused with fixed saltpetre (caustic potash) a mass is produced from which he obtained "a most dainty purple fiery liquor," this afterwards turning blue, red, and green In 1705 an anonymous treatise appeared, entitled *Key to the Secret Cabinet of Nature's Treasury, in* this it is stated that the product obtained by fusing saltpetre and manganese yields a solution of which the colour alters, first being grass-green, then sky-blue, violet-coloured, and

[1] **A detailed description is to be found in Lunge's *Sulphuric Acid and Allah Manufacture,* Vol III**

[2] **Packe's translation, 1687, p 353**

lastly rose-red The changes of colour which are here given are exactly the opposite of those which Glauber noticed Pott in 1740 described these changes, believing that they had -not been previously noticed, and Scheele, who endeavoured to explain these phenomena, gave to the colouring material the name of mineral chameleon, a term which had previously been applied to other mineral colouring matters capable of undergoing changes of tint The properties of this mineral chameleon were afterwards investigated by many chemists, but it was not until the year 1817, when Chevillot and Edwards [1] investigated the subject, that a rational view of its composition was arrived at They showed that when much alkali is employed a green compound is formed, that when, on the other hand, an excess of manganese is fused with potash a red body is produced, and they succeeded in preparing the substance obtained by the latter reaction in the crystalline form They also showed that an absorption of oxygen takes place, and consequently they assumed that the potash salt forms with manganese a manganate, and that the green salt contains more base than the red Forchhaminer[2] investigated the subject in 1820, and ascribed the difference in colour to the existence of two distinct acids, but Mitscherhch[3] first showed their exact composition

Manganese Trioxide, MnO_3, is a deliquescent, amorphous, reddish mass, prepared by dropping a solution of potassium permanganate in concentrated sulphuric acid on to dry sodium carbonate [4]

$$2(MnO_3)_2SO_4 + 2Na_2CO_3 = 2Na_2SO_4 + 4MnO_3 + 2CO_2 + O_2$$

It is formed only in extremely small quantity, and is carried forward by the carbon dioxide as a pink fume, which may be caught on fragments of glass placed in a freezing mixture

When thrown into water it is decomposed as follows [5]

$$3MnO_3 + H_{20} = 2HMnO_4 + MnO_2$$

The *manganates* have a green colour, and their solutions are stable only when they contain large quantities of free alkali If carbon dioxide is passed through them, or if they are diluted with much water, or made slightly acid, the liquid passes from

[1] ***Ann Chim Phys*, 1817, [2], 4, 287**
[2] ***Ann Phil*, 1820,16, 130, 1821,17, 150**
[3] ***Pogg Ann*, 1832, 25, 287**
[4] **Franke, *J pr. Chem*, 1887, [2], 6, 893**
[5] **Thorpe and Hambly, *Journ. Chem Soc*, 1888, 53, 175**

a green to a blue and violet colour, the permanganate being formed, and the dioxide deposed

$$3K_2MnO_4 + 2H_{20} = 2KMnO_4 + MnO_2 + 4KOH$$

The manganates are also converted by direct oxidation into permanganates when they are dissolved in a large quantity of water containing dissolved oxygen

Manganates are produced by the partial reduction of permanganates in alkaline solution, and this change occurs when small amounts of reducing agents such as alcohol and sodium thiosulphate are added to the red, alkaline liquid The latter also gradually turns blue and afterwards green simply on exposure to air, this being caused by the reducing action of the organic matter contained in the atinosphere These reactions explain the changes of colour of the mineral chameleon In alkaline solution the manganates act as powerful oxidising agents

Potassium Manganate, K_2MnO_4 —The preparation of potassium manganate is important, since it is the first stage in the manufacture of potassium permanganate Potassium hydrate or carbonate is heated with manganese dioxide to dull redness in the presence of air, in the laboratory it is quicker and therefore more convement to use an oxidising agent such as potassium chlorate According to Bahr and Sackur,[1] the product is a complex manganite-manganate

$$8K_2CO_3 + 5MnO_2 + 3O = 8K_{20},Mn_6O_{13} + 8CO_2$$

The deep green-coloured mass is dissolved in water, when manganese dioxide is precipitated and an alkaline solution of manganate is obtained

$$8K_{20},Mn_5O_{13} + 5H_{20} = 3K_2MnO_4 + 2MnO_2 + 10KOH$$

By evaporation of the resulting deep green solution, after it has been separated from the precipitated dioxide by decantation and filtration, the salt is obtained in small crystals isomorphous with those of potassium sulphate It may be prepared also by boiling a saturated solution of potassium permanganate with caustic potash solution of specific gravity 1 33 (Aschoff)

On heating it is decomposed, potassium mangamte and oxygen being formed:

$$2K_2MnO_4 = 2K_2MnO_3 + O_2$$

[1] ***Zeit anorg Chem*, 1912, 73, 101. See also Askenasy and Klonowski, *Zeit Elektrochem*, 1910,16,104**

The reaction does not go to completion, however, for the mangamte forms a solid solution or complex manganite-manganate with the unchanged manganate of the composition $5K_{20},Mn_5O_{13}$ or $3K_3MnO_4,2K_2MnO_3$, this does not decompose easily (Bahr and Sackur)

Sodium Manganate, Na_2MnO_4, is formed when a mixture of equal parts of manganese dioxide and caustic soda is heated for sixteen hours, the mass is then lixiviated with a small quantity of water and the solution cooled down, when the salt separates out in small crystals isomorphous with Glauber's salt, and having the composition $Na_2MnO_4,10H_2$ OThese dissolve in water with partial decomposition, yielding a green solution. Sodium manganate is now used largely as a deodoriser

Barium Manganate, $BaMnO_4$, is formed when manganese dioxide is heated with baryta or barium carbonate or nitrate, or when barium permanganate is heated with baryta-water It is an emerald-green powder, consisting of microscopic, four-sided prisms or six-sided plates It has a specific gravity of 4-85, and is insoluble in water, but is readily decomposed by acids The employment of this salt in place of the poisonous Scheele's green has been suggested,[1] and it has been employed in a few instances, though not so generally as might be wished

520 *Manganese Heptoxide,* Mn_2 and *Permanganic Acid,* $HMnO_4$—The first of these compounds, also termed permanganic anhydride, was noticed by Chevillot, and afterwards investigated by Thenard,[2] Aschoff,[3] and Terrell[4] In order to prepare this compound, pure potassium permanganate free from chlorine is gradually added to well-cooled, highly concentrated sulphuric acid The salt dissolves with an olive-green colour,

$$2KMnO_4 + 2H_2SO_4 = (MnO_3)_2SO_4 + K_2SO_4 + 2H_{20},$$

and if the solution be cooled, and water carefully added the heptoxide separates as a dark reddish-brown liquid[5] which does not solidify at —20°

$$(MnO_3)_2SO_4 + H_{20} = Mn_{207} + H_2SO_4.$$

It is extremely unstable, constantly evolving bubbles of oxygen on exposure to the air These carry with them a small quantity

[1] **Sohad,** ***Deutsch Industnezett,*** **1865, 118, Rosenstiehl,** ***Dtngl Polyt Journ,*** **1865,177, 409**
[2] ***Compt rend,*** **1856, 42, 389** [3] ***Pogg Ann ,*** **186O, 111, 217**
[4] ***Bull Soc chim,*** **1862, 40**
[5] **Franke,** ***J pr Chem,*** **1885, [2], 31, 16b**

of the heptoxide, and thus violet fumes are emitted It rapidly absorbs moisture, and dissolve in water, yielding a deep violet-coloured solution, so much heat being thereby evolved that the liquid undergoes partial decomposition It dissolves in concentrated sulphuric acid with an olive-green colour On heating, it decomposes, with evolution of light and heat, and with violent explosion

Permanganic Acid, $HMnO_4$, is obtained in aqueous solution by adding the requisite quantity of dilute sulphuric acid to the barium salt or by electrolysing the potassium salt in a special form of apparatus and removing the alkali from the cathode compartment[x] A deep red liquid is thus obtained, which exhibits a blue colour by reflected light, and possesses a bitter, metallic taste It decomposes on exposure to light or when heated gently, and still more rapidly when boiled, with evolution of oxygen and separation of the hydrated dioxide It acts as a most powerful oxidising agent

Permangamc acid is formed also when manganese nitrate or any manganous salt, with the exception of the halide compounds, is warmed with nitric acid and lead dioxide, with potassium bromate and dilute sulphuric acid,[2] with the higher oxides of bismuth and nitric acid,[3] or with ammomum persulphate, silver nitrate, and nitric acid[4]

A weak solution of permangamc acid continually evolves oxygen at a very slow rate, manganese dioxide being deposited, and the rate of decomposition is greatly increased by the presence of hydrated manganese dioxide[5] When such a solution is shaken with hydrogen or carbonic oxide, the gas is rapidly absorbed and a considerable volume of oxygen evolved (Victor Meyer and Beckhnghausen)[6] It has been suggested that this is due to the fact that the hydrated manganese dioxide simultaneously formed is at first present in a specially active condition and thus greatly increases the normal decomposition of the permangamc acid (Morse and Reese)

Permangamc acid has been obtained in the form of violet-

[1] Morse and Olsen, *Amer Chem J*, 1900, 23, 431
[2] Vitah, *Boll Chim Farm*, 1898, 37, 545
[3] Schneider, *Dingl Polyt Journ*, 1888, **269,** 224
[4] Marshall, *Chem News*, 1901, 83, 76
[5] Morse, Hopkins, and Walker, *Amer Chem J*, 1896, 18, 401, Morse, *Ber*, 1897, 30, 48, Morse and Reese, *Amer Chem J*, 1898, 20, 521, Morse and Byers, *ibid*, 1900, 23, 313, Olsen, *ibid*, 1903, **29,** 242
[6] *Ber*, 1896, **29,** 2549, Hirtz and Meyer, *ibid*, 2828

black crystals by evaporating the solution obtained by the action of barium permanganate and sulphuric acid It decomposes very rapidly [1]

Potassium Permanganate, $KMnO_4$, is prepared on the large scale as a disinfectant The first stage is the preparation of an alkaline solution of potassium manganate *(q v)* This may be neutralised by carbon dioxide or sulphuric acid, manganates are only stable in presence of alkali, and when this is removed they decompose according to the equation

$$3K_2MnO_4 + 2H_2O = 2KMnO_4 + MnO_2 + 4KOH$$

This method involves the loss of two-thirds of the manganese and the neutralisation of the alkali The loss of manganese is prevented by Stadeler's method of passing chlorine into the solution, but this method is just as wasteful of the alkali

$$2K_2MnO_4 + Cl_2 = 2KMnO_4 + 2KC1$$

An electrolytic process of oxidation is now largely used This involves no loss of manganese, nor is the alkali neutralised, and the resulting permanganate has only to be separated from the very soluble hydroxide Numerous processes[2] have been described, in most the solution is electrolysed between iron electrodes separated by a diaphragm Oxidation takes place at the anode, thus

$$2K_2MnO_4 + H_{2\,0} + O = 2KMnO_4 + 2KOH$$

When the pure crystallised product is not required, the corresponding, difficultly crystalhsable, but cheaper, sodium permanganate is prepared in an exactly similar manner, solutions of this are sold as *Condy's Disinfecting fluid*

Potassium permanganate is isomorphous with potassium perchlorate, with which it crystallises in all proportions The crystals are almost black, and when freshly prepared possess a green, metallic lustre, which, however, on exposure to the air becomes of a steel-blue tint without any further alteration in the salt taking place The crystals have a specific gravity of 2 7, and yield a red powder One hundred parts of water dissolve [3] 2 83 parts of the salt at 0°, 6 34 parts at 19 8°, 12 56 parts at 40°,

[1] **Muir,** *Journ Chem Soc,* **1907, 91, I486**

[2] **See Brand and Ramsbottom,** *J pr Chem,* **1910, [2], 82, 336, Askenasy and Klonowski,** *Zeit Elektrochem,* **1910, 16, 170**

[3] **Baxter, Boylston, and Hubbard, /** *Amer Chem Soc,* **1906, 28, 1336, Patterson,** *ibid,* **1734**

and 25 03 parts at 65°, forming a deep purple-coloured solution. On heating to 240° they decompose as follows .

$$10KMnO_4 = 2K_2MnO_3 + (3K_2MnO_4 + 5MnO_2) + 6O_2$$

The final products are potassium manganite and a sohd solution or complex compound of potassium manganate with manganese dioxide [1]

Jones [2] has shown that hydrogen and phosphme decompose potassium permanganate, and that oxygen is evolved together with carbon dioxide when sulphuric acid acts on permanganate in presence of oxalic acid

Mixed with sulphur or phosphorus, a material is obtained which takes fire or explodes violently on percussion, and a mixture of the salt with charcoal burns like tinder

Potassium permanganate is largely used as an oxidising agent, both in analytical work and for the preparation of many organic oxidation products In alkaline solution it is first converted into manganate, which afterwards loses a further amount of oxygen and yields the hydrated dioxide, two molecules of the salt providing three atoms of oxygen

$$(1)\ 2KMnO_4 + 2KHO = 2K_2MnO_4 + H_2O + O,$$
$$(2)\ 2K_2MnO_4 + 2H_2O == 2MnO_2 + 3KHO + 2O$$

It is in this way, for example, that potassium permanganate acts when it is brought into contact with a hot solution of manganous salt, the whole of the manganese being precipitated as dioxide (Volhard), three-fifths of this is therefore formed by the oxidation of the manganese salt added and the remaining two-fifths by the reduction of the permanganate

$$3MnSO_4 + 2KMnO_4 + 2H_2O = 5MnO_2 + K_2SO_4 + 2H_2SO_4$$

In acid solution the manganese of the permanganate is finally converted into a salt corresponding to the monoxide MnO, five atoms of oxygen being rendered available

$$2KMnO_4 + 3H_2SO_4 = K_2SO_4 + 2MnSO_4 + 3H_2O + 5O$$

Thus the action of acid potassium permanganate solution on ferrous sulphate, in presence of sulphuric acid, is represented

$$2KMnO_4 + 10FeSO_4 + 8H_2SO_4 = K_2SO_4 + 2MnSO_4 + 5Fe_2(SO_4)_3 + 8H_2O .$$

[1] **Askenasy and Solberg *Nernst Festschrift,* 1912, 53**
[2] ***Journ Chem, Soc,* 1878, 33, 95**

The acid solution of potassium permanganate is reduced by hydrogen peroxide with evolution of oxygen,[1] half of which is due to the peroxide, half to the permanganate .

$$2KMnO_2 + 5H_2O_2 + 3H_2SO_4 = K_2SO_4 + 2MnSO_4 + 8H_2O + 5O_2.$$

The reduction of potassium permanganate by formic acid in slightly acid solution appears to take place in stages [2]

When potassium permanganate is used as an oxidising agent in volumetric analysis, it is often noticed that the first portion of permanganate added only reacts slowly, further additions react more rapidly The phenomenon is particularly noticeable in the titration of oxalic acid. This is an example of *autocatalysis* manganous sulphate catalyses, and is itself a product of the reaction Harcourt and Esson,[3] and Schilow,[4] have shown that the velocity of the reaction is proportional to the concentration of the manganous salt Similar results have been obtained in the oxidation of sulphites, and in the titration of hydrogen peroxide In the titration of ferrous salts in the presence of hydrochloric acid, besides the mam reaction shown in the equation above, a subsidiary reaction, induced by the presence of iron salts, occurs

$$2KMnO_4 + 16HC1 - 2KC1 + 2MnCl_2 + 8H_2O + 5C1_2$$

This secondary reaction can be prevented by the addition of manganous sulphate, which greatly increases the velocity of the mam, but not that of the secondary reaction, thus a negligible part of the permanganate only is used in the oxidation of the hydrochloric acid

Ammonium Permanganate, NH_4MnO_4, is obtained by the decomposition of the potassium salt with ammonium chloride It is isomorphous with potassium permanganate, and decomposes readily when gently heated,[5] forming ammomum nitrate, oxides of nitrogen, and an oxide of manganese of the composition $22MnO_2,MnO$ It explodes when rapidly heated, or when subjected to percussion

[1] On the nature of this reaction, see Baeyer and Villiger, *Ber,* 1900, 33, 2488, where the literature is quoted, Bach, *Ber,* 1901, 34, 3851

[2] Holluta, *Zeit physikal Ghent,* 1922, **101,** 34

[3] *Phil Trans,* 1866,**166,** 201 [4] *Ber,* 1903, 36, 2735

[5] Chnstensen, *Zeit anorg Chem,* 1900, 24, 203

Barium Permanganate, $Ba(MnO_4)_2$, forms hard, almost black prisms, soluble in water It is obtained by passing carbon dioxide through, water containing barium manganate in suspension,[1] or by the action of barium chloride on silver permanganate

Stiver Permanganate, $AgMnO_4$, separates out in large, regular crystals when warm solutions of silver nitrate and potassium permanganate are mixed It dissolves in 190 parts of water at 15°, and is much more soluble in warm water The solution decomposes on boiling

MANGANESE AND THE HALOGENS

521 *Manganous Fluoride,* MnF_2, is obtained by dissolving metallic manganese or the carbonate in hydrofluoric acid, the compound being deposited as a white, crystalline powder when the solution is boiled According to Edminster and Cooper,[2] however, the compound thus formed is an acid salt, $MnF_2,5HF,6H_2O$, of specific gravity 1 921 It is formed as a rose-coloured mass by the action of gaseous hydrogen fluoride on manganese It is insoluble in water, but may be recrystalhsed from fused manganese chloride and then forms rose-coloured prisms of sp gr 3 98, melting at 856° It dissolves in strong acids, yields an oxyfluonde when boiled with water, and is completely reduced by hydrogen at 1000° [3]

Manganic Fluoride, MnF_3, is obtained by the action of fluorine on manganous iodide in purple pseudomorphs of sp gr 3 54 It decomposes, when heated, into manganous fluoride and fluorine, dissolves in strong acids, forming unstable dark brown solutions, and is decomposed by water [4] A hydrated tnfluonde, $MnF_3,3H_2O$, is obtained in ruby-red crystals by dissolving the sesqui- or the di-oxide in hydrofluoric acid

Potassium Manganifluonde, K_2MnF_6, is obtained by decomposing potassium manganate with water and dissolving the resulting potassium mangamte in a mixture of hydrofluoric acid and potassium fluoride It forms small, golden-yellow, hexagonal tablets and is decomposed by water, but may be recrystalhsed from hydrofluoric acid It yields a dark brown-

[1] Bottger, *J pr Chem,* 1863, 90, 156.
[2] *J Amer Chem Soc,* 1920, 42, 2419
[3] Moissan and Ventun, *Compt rend,* 1900, **130,** 1158
[4] Moissan, *Compt rend* , 1900,**130,** 622

coloured solution in hydrochloric acid which evolves chlorine when gently heated A *rubidium salt* of similar properties has also been obtained[1]

Manganous Chloride, $MnCl_2$, is formed when the metal is burned in chlorine gas, or when hydrogen chloride is passed over heated manganous carbonate Prepared in this way, manganese chloride is a pale rose-coloured mass, having a lammo-crystalhne structure When heated to redness it fuses to an oily liquid, and decomposes in moist air at this temperature with formation of hydrochloric acid and the oxides of manganese Manganous chloride is obtained in solution by dissolving the carbonate or any of the oxides in hydrochloric acid Por this purpose the residues from the preparation of chlorine by means of pyrolusite and hydrochloric acid may be utilised These are always coloured yellow, from the presence of ferric chloride, and contain an excess of acid They must be evaporated to drive off the acid, then diluted with water, and a tenth of the solution precipitated with sodium carbonate The precipitate, consisting of manganese carbonate and ferric hydroxide, is then well washed with hot water and boiled with the remainder of the liquid for a long time By this means the whole of the iron is precipitated as ferric oxide The filtrate may contain copper, barium, and calcium, .which are separated by the usual methods On evaporation, a concentrated solution of manganous chloride deposits between 15° and 20° light pink-coloured, monochnie crystals of the hydrate $MnCl_2,4H_2O$ This hydrate is transformed at 58 O98° into the hydrate $MnCl_2,2H_2O$, this temperature having been determined with great accuracy by Richards and Wrede as a suitable fixed point for use in thermometry[2] The dihydrate is stable up to 198° and then passes into the anhydrous salt Below — 2° the hydrate $MnCl_2,6H_2O$is formed[3] In addition to these an isomeric /3-tetrahydrate is known (Mangnac)[4] which also forms monocknic crystals, but of a different form from the ordinary tetrahydrate, being isomorphous with those of hydrated ferrous chloride, $FeCl_2,4H_2O$The dihydrate may be prepared by heating the tetrahydrate for some time at 60° or passing hydrogen

[1] **Weinland and Lauenstein, *Zeit anorg Chem*, 1899, 20, 40**
[2] ***Zeit physikal Chem*, 1907, 61, 313**
[3] **Kuznetzoff, J *Russ Phys Chem Soc*, 1898, 80, 741, Dawson and Williams, *Zeit physikal Chem*, 1899,31, 59 See also Richards and Briggs, *ibid*, 1898, 28, 313**
[4] ***Compt rend*, 1857, 45, 650**

chloride into an alcoholic solution of the chloride One hundred parts of water dissolve

At	8°	25°	30°	57 85°	80°	100°
$MnCl_2$	62	77 2	80 7	105 7	112 7	116.

This salt is also soluble in alcohol, forming a green solution which burns on ignition with a red flame Manganous chloride forms double salts with the chlorides of the alkali metals, such as $K_2MnCl_4,2H_2O$ and K_4MnCl_6, and with the chlorides of some other metals The anhydrous salt combines readily with ammoma and similar compounds With ammonia, it forms the hexammine, $[Mn(NH_3)_6]Cl_2$, the diammine, $(NH_3)_2,MnCl_2$, and the monammine, NH_3MnC_2 [1]

Manganese Trichloride, $MnCl_3$, and *Manganese Tetrachloride*, $MnCl_4$, have only recently been obtained in the solid state When any one of the oxides, Mn_3O_4, Mn_2O_3 or MnO_2, is added to cold concentrated hydrochloric acid, a dark brown solution is formed, chlorine being simultaneously produced when the dioxide is employed This solution appears to contain the trichloride,[2] and yields double salts of the type $MnCl_3,2RCl$, with the chlorides of potassium and ammonium [3] The addition of water to the solution precipitates a mixture of hydrated oxides (Pickering) [4] When the dark brown solution is heated, chlorine is evolved,

$$2MnCl_3 = 2MnCl_2 + Cl_2$$

When manganese dioxide is treated with ether saturated with hydrochloric acid, a deep green solution is obtained, which was considered by Nickles [5] to contain the tetrachloride, $MnCl_4$, and by Franke [6] to contain the compound $MnCl_2,MnCl_4$ It is, however, probable that this green liquid contains the trichloride and not the tetrachloride, since it yields double salts with the hydrochlorides of pyridine and qumolme of the type $MnCl_3,2RHCl$, almost the whole of the manganese in the solution can be precipitated in this form More concentrated green solutions can

[1] Biltz and Huttig, *Zeit anorg Chem*, 1919, **109,** 88, Ephraim, *Ber*, 1912, 45, 1322, *Zeit physihal Chem*, 1913, 81, 513

[2] Pickering, *Journ Chem Soc*, 1879, 35, 654

[3] Neumann, *Monatsh* , 1894,15, 489, Rice, *Journ Chem Soc* , 1898, 73, 258

[4] See also Fisher, *Journ Chem Soc*, 1878, 33, 409, Christensen, *J pr Chem*, 1887, [2], 35, 57, 161, 541

[5] *Ann Chim Phys* , 1865, [4], 5, 169, 1867, [4], 10, 318

[6] *J pr Chem*, 1888, [2], 36, 31, 453

be prepared by the action of alcoholic hydrochloric acid on manganese dioxide or potassium permanganate [1]

When dry hydrogen chloride is passed into carbon tetrachloride in which manganese dioxide is suspended, a solid product is obtained which consists of manganese trichloride and tetrachloride On treating this with anhydrous ether, the trichloride dissolves, forming a deep violet-coloured solution A reddish-brown residue of the tetrachloride remains The trichloride is a black solid, having a greenish tinge, which is decomposed by water The tetrachloride is stable at ordinary temperatures, but is decomposed by moisture [2]

Derivatives of the tetrachloride can be obtained by boiling potassium permanganate with glacial acetic acid, and saturating the resulting reddish-brown solution with hydrochloric acid A dark crystalline precipitate of *potassium manganichlonde*, $MnCl_4$,2KCl, is thus produced, which rapidly loses chlorine in moist air, but may be preserved in dry air for some time If potassium acetate be added to the liquid before it is saturated with hydrochloric acid, Neumann's salt, $MnCl_3$,2KCl, is obtained (Meyer and Best)

Permanganic Oxychloride, MnO_3Cl —This chloride of permanganic acid was first prepared by Dumas, [3] he did not, however, analyse the compound, but from its mode of decomposition considered it to be manganese heptachlonde, $MnCl_7$ It is obtained by gradually adding fused sodium chloride to a solution of potassium permanganate in concentrated sulphuric acid A yellow gas is then evolved, which when passed through a freezing mixture condenses to a greenish-brown liquid This when exposed to the air emits a purple-red vapour, which possesses the peculiar smell of the oxides of chlorine, and like them acts most violently upon the mucous membrane, so that the smallest quantity of the chloride contained in cominercial permanganate can be thus readily detected [4] When heated, it explodes violently, and water decomposes it with formation of permanganic acid and hydrochloric acid These substances, however, mutually decompose with formation of free chlorine and manganese dioxide. A corresponding oxyfluoride, MnO_3F, exists, and was first prepared by Wohler [5]

[1] **Meyer and Best, *Zeit anorg Chem* , 1900, 22,169**
[2] **Holmes, *J Amer Chem Soc*, 1907, 29, 1277.**
[3] ***Ann Chim Phys*, 1827, [2], 36, 81.**
[4] **Aschoff, *Pogg Ann* , 1860, 111, 217**
[5] ***Pogg Ann*, 1827, 9, 619.**

Manganous Bromide, $MnBr_2$, is obtained by heating the powdered metal in bromine \^|pour, and when the compound is fused, it is obtamed as a pale red mass It can also be obtained by the action of the calculated quantity of bromine on finely divided manganese suspended in ether, but not in other orgamc solvents The crystalline compound $MnBr_2,(C_2H_5)_{20}$ is first obtained, this readily loses its ether on being heated to 100°, leaving manganous bromide as a white powder (Ducelliez and Eaynaud)[x] When the carbonate is dissolved in hydrobromic acid the hydrated bromide, $MnBr_2,4H_2O$, is obtained, and this was found by Mangnac to be isomorphous with the ordinary form of the chloride Other hydrates are known Unlike the chloride, it shows no tendency to form double salts with chlorides of the alkali metals It behaves in a similar manner to the chloride towards ammoma (Biltz, Ephraim)

Manganic Bromide, $MnBr_3$—When finely divided manganese is treated with a large excess of bromine in ethereal solution, two liquid layers are formed, from the lower of these Ducelliez and Raynaud obtained by cautious evaporation a yellow, amoiphous mass of the composition $MnBr_3,3(C_2H_5)_2O$, from which the ether could not be removed without formation of manganous bromide It is very soluble in water, and gives a black precipitate with sodium carbonate solution

Manganous Iodide, MnI_2 $4H_2O$, is obtained crystallised in colourless, deliquescent needles, which become coloured on exposure to air Hydrates with $6H_2O$ and $9H_2O$ are formed below — 2 7° and —9 3° respectively[2] It has little tendency to form double salts, and forms a hexammine and a diammine (Biltz, Ephraim)

Manganese Tetriodate, $Mn(10_3)_4$, is not known in the free state, but a double salt with potassium lodate, $Mn(IO_3)_4,2KIO_3$, is formed as a brownish-violet, insoluble, crystalline powder when hydrated manganese dioxide is boiled with iodic acid and potassium lodate [3]

MANGANESE, SULPHUR AND SELENIUM

522 *Manganese Monosulphide,* MnS, occurs as the mineral manganese blende, or alabandite, forming a steel-grey, crystalline mass with a green streak, and sometimes observed in cubes

[1] *Bull Soc chrm,* 1914, [4], 15, 273, 408
[2] Kuznetzoff, *J Rues Phya Chem Soc,* 1900, 32, 290
[3] Berg, *Compt rend,* 1899, **128,** 673.

and octahedra It has a specific gravity of 4 04, and occurs in veins in the coal mines in Transylvania, and in Freiberg and Mexico It may be obtained artificially in the form of a dark grey powder, which melts at a high temperature, forming a steel-grey, crystalline mass, by heating the monoxide, the carbonate, or the sulphate in a current of hydrogen sulphide (Arfvedson), or in green octahedra by heating manganous sulphide with a little sulphur in the electric furnace [1] Ammonium sulphide and the other monosulphides of the alkali metals precipitate anhydrous manganese sulphide from a solution of a manganous salt in the form of a light flesh-coloured precipitate, which dissolves readily in dilute acids and oxidises on exposure to the air, assuming a brown tint When left in contact with ammonium sulphide, or heated to 300°,[2] and when suspended in a dilute solution of sulphuretted hydrogen and exposed to a low temperature, it passes into the green, crystalline sulphide [3] According to Olsen and Rapalje a grey form of the sulphide also exists and the sulphide precipitated by ammonium sulphide is a mixture of this and a red form The sulphide precipitated by sodium sulphide does not contain the grey form,[4] and does not become green in contact with excess of the precipitant

Manganese sulphide combines with the sulphides of the alkali metals to form salts [5] The dark-red, crystalline potassium salt, $K_2S,3MnS$, is formed when anhydrous manganese sulphate is gradually heated to redness with three parts of potassium carbonate, 0 2 part of lamp-black, and excess of sulphur

Manganese Disulphide, MnS_2 —This substance is found as the mineral hauerite in crystals belonging to the regular system They possess a metallic, adamantine lustre, and a reddish-brown colour, and occur in clay at Kahnka in Hungary, together with sulphur and gypsum

Manganous Sulphate, $MnSO_4$, is best prepared by mixing cominercial black oxide of manganese to a paste with sulphuric acid and heating the mixture in a crucible to strong redness, when the greater part of the iron sulphate is destroyed The filtrate obtained after lixiviating the residue is then heated with

[1] **Mouriot, *Compt rend,* 1895, 121, 202**
[2] **Antony and Donnim, *Oazz,* 1893, 23, l, 560**
[3] **Vilhers, *Compt rend,* 1895, 120, 322, see also Hahn, *Zett anorg Chem,* 1922,121,209**
[4] ***J Amer Chem Soc,* 1904, 26,1615, where the literature is quoted**
[5] **Volker, *Annalen,* 1846, 59, 35, Brunner, *Arch in phys not,* 1889, 22, 68**

a small quantity of manganous carbonate in order to precipitate the last traces of iron

It has a specific gravity of 3 1, and is decomposed at a bright red heat, leaving a residue of red oxide of manganese Manganous sulphate forms a number of hydrates and the equilibrium curve for this substance and water is one of great complexity Below 8°, the heptahydrate separates out, between 8° and 27° the pentahydrate is the stable form, and above 27° the monohydrate The solubility of the latter decreases as the temperature rises, so that a maximum of solubility exists at 27° In addition to these stable forms, several labile hydrates exist, the most important of these being the tetrahydrate, which separates at about 30° in rose-coloured prisms of sp gr 2 097 (Kopp) Several other hydrates have been described, but it is doubtful whether they all exist[1] One hundred parts of water dissolve

At	**0°**	9°	15°	27°	50°	70°	**100°**
$MnSO_4$	53 2	59 3	611	66	59 5	52	33 2 parts

The last trace of water is expelled from the monohydrate only at 450°

Manganous sulphate is insoluble in absolute alcohol, this liquid removing a portion of the water from the hydrates Finely crystalline double sulphates[2] of the isomorphous series, $K^{1}_{2}SO_4,R^{11}SO_4,6H_{20}$, are formed when manganous sulphate and the alkali sulphates are crystallised together

Manganous Aluminium Sulphate, $MnSO_4,Al_2(SO_4)_3,24H_2$— This substance occurs as the mineral apjohnite found in Algoa Bay in South Afuca[3]

Manganic Sulphate, $Mn_2(SO_4)_3$ —Mangamc oxide and hydroxide dissolve with difficulty in sulphuric acid The red oxide, Mn_3O_4, on the other hand, dissolves readily, yielding a purple-red solution If the finely divided precipitated dioxide is treated with sulphuric acid, oxygen is evolved, and at a temperature of 138° a green liquid is obtained from which the sulphate is precipitated as a non-crystalline powder In order to purify this salt it is brought on to a porous porcelain plate, when the greater part of the sulphuric acid is absorbed, the residue

[1] Schieber, *Monatsh,* 1898, 19, 280, Cottrell, *J, Physical Chem* , 1900, 4, 637, Richards and Fraprie, *Amer Chem J,* 1901, 26, 75

[2] See also Scott, *Journ Chem Soc,* 1897, 71, 587, Mallet, *tbid,* 1900, 77, 221, 1902, 81, 1549

[3] ***Phil** Mag,* **1856,** [3], **12,103.**

is then washed with pure nitric acid, the salt dried in absence of air on another plate, and then heated to 150^0.[1]

Manganese Alums—Manganese forms a series of alums, $R^I_2SO_4,Mn_2(SO_4)_3,24H_{20}$, which crystallise in pink or red, octahedral forms They are decomposed by water, but are stable in a solution of 1 volume of sulphuric acid diluted with 3 of water, provided that the temperature is kept low The potassium and ammomum salts are extremely unstable and have not been obtained pure, but the caesium and rubidium salts can be prepared The salts obtained by the addition of the sulphates of potassium and ammonium to mangamc sulphate and evaporating are not true alums, but contain less water of crystallisation[2] An anhydrous ammonium mangamc sulphate has also been obtained and forms violet crystals which are decomposed by water[3]

Manganic Ccesium Alum, $Cs_2SO_4,Mn_2(SO_4)_3,24H_{20}$, may be prepared by dissolving caesium sulphate and mangamc acetate, $Mn_2(C_2H_3O_2)_3$ (obtained by the action of potassium permanganate on manganous acetate dissolved in glacial acetic acid), in dilute sulphuric acid and cooling to —20° (Chnstensen) It can be obtained also by electiolysmg at 10-15° a solution of manganous sulphate and caesium sulphate in dilute sulphuric acid placed in the anode compartment of an electrolytic cell[4] It farms coral-red crystals of the regular system (class 30, p 209) and is decomposed by water It melts at 40° in its water of crystallisation

The *Rubidium Alum* closely resembles the caesium salt, but decomposes at about 15°, whilst the potassium and ammomum alums decompose at still lower temperatures (Christensen)

Manganese Dioxysulphate or Persulphate, $Mn(SO_4)_2$, was first prepared by Fremy,[5] and can best be obtained by oxidising manganous sulphate in warm sulphuric acid with the calculated quantity of potassium permanganate When the solution is sufficiently concentrated, it is precipitated in the form of black crystals, which are soluble in sulphuric acid, forming a brown solution which is stable up to 80°, but above that temperature decomposes with the formation of mangamc sulphate On diluting the solution the salt is hydrolysed and manganese dioxide

[1] Canus, *Annalen,* 1856,98, 53
[2] Christensen, *Zeit anorg Chem,* 1901, 27, 328
[3] Lepxerre, *Compt rend,* 1895,**120,** 924.
[4] Piccini, *Zeit anorg Chem* , 1898,17, 355, 1899, **20,** 12.
[5] *Compt rend,* 1876, 82, 475, 1231

is precipitated Electrolysis[1] of a solution of manganese sulphate in sulphuric acid yields a solution of it, which, however, is not free from mangapc sulphate It has been used as an oxidising agent in organic chemistry

Manganous Dithionate, $MnS_2O_6 3H_2O$ —This salt is of interest inasmuch as it is employed for the preparation of dithionic acid (Vol I, p 459) It is obtained by passing sulphur dioxide through water in which finely divided manganese dioxide is suspended The solution always contains a small quantity of manganous sulphate, and for this reason baryta water is added as long as a precipitate of barium sulphate is formed Manganous dithionate forms easily soluble rhombohedral crystals

Double *selenates* of manganese with potassium, rubidium, caesium and ammonium have been prepared[2]

MANGANESE AND THE ELEMENTS OF THE NITROGEN GROUP

523 *Manganese Nitride,* Mn_3N_2—Nitrogen reacts vigorously with manganese at a red heat to produce this compound It is a dark coloured powder, which yields ammoma when heated in hydrogen or fused with potash, and is attacked only with difficulty by acids[3]

Manganous Nitrate, $Mn(NO_3)_2$—The hydrate with $6H_2$ ciystallises with difficulty in colourless, deliquescent needles which melt at 25 8°, and are readily soluble in alcohol A hydrate with $3H_20$ also exists[4] which is stable above 25° and melts at 35 5° The nitrate decomposes at 129 5°, at which temperature a black deposit of manganese oxides is formed

Manganese Phosphides —The freezing points of manganese-phosphorus mixtures have been determined by 2emczwznyj and Efremow[5] these prove the existence of two compounds The first has the formula Mn_6P_2, the second probably has the formula MnP The substance Mn_3P_2, described by many of the earlier workers, is really a eutectic mixture The magnetic properties of the compound Mn_5P_2 have been studied by Wedekind and Veit[6]

[1] *Zeit Elektrochem* , 1905, 11, 853
[2] Tutton, *Proc Boy Soc* , 1922, [4] 101, 225
[3] Prelinger, *Monatsh*, 1894, 15, 391, Haber and van Oordt, *Zeit anorg Chem*, 1905, 44, 341, Shukow, *J Buss Phys Chem Soc*, 1908, 40, 457
[4] Funk, *Ber* , 1899, 32, 96
[5] *Zeit anorg Chem*, 1908, 57, 241
[6] *Ber*, 1907, 40, 1268

Manganous Phosphates—These salts have been investigated by Hemtz,[1] Debray,[2] Bodecker,[3] and Erlenmeyer[4] The normal manganous orthophosphate, $Mn3(PO_4)2,7H_2$, is a white, imperfectly crystalline precipitate The *monohydrogen salt,* $HMnPO_4,3H_2$, forms small, prismatic, rose-coloured, rhombic crystals slightly soluble in water, and the *dihydrogen phosphate,* $H_4Mn(PO_4)_2\}2H_2$, crystallises in red, four-sided prisms which deliquesce on exposure to the air, decomposing into free phosphoric acid and the preceding salt[5]

Manganous salts are precipitated by ammonium phosphate as *manganous ammonium phosphate,*[6] $Mn(NH_4)PO_4,H_2$, which is converted by ignition into the *pyrophosphate,* Mn_2P_2

Manganic Phosphates —Both mangamc oxide and the dioxide dissolve in a concentrated solution of phosphoric acid, in the latter case with evolution of oxygen, with formation of a deep violet liquid, from which a violet-coloured, crystalline mass separates out (Gmelm) This decomposes in contact with water, and mangamc hydroxide is precipitated from the solution by alkalis On evaporating the red solution a peach-blossom-coloured powder separates, consisting of mangamc metaphosphate, $Mn(PO_3)_3,H_2$[7] The normal phosphate $MnPO_4,H_2$, an acid pyrophosphate, $MnHP_2$, and the salts $MnKP_2$ and $Mn_4P_6O_{21},14H_2$,[8] have also been prepared[9]

Manganese Arsenides—Two arsemdes of manganese are known,[10] the first of which, MnAs, is non-magnetic, but is converted by heating into the magnetic compound, Mn_2As

Manganous Arsenate—When arsenic acid is saturated with manganese carbonate, a sparingly soluble salt having the composition $HMnAsO_4,H_{20}$ is formed This dissolves readily in arsenic acid with formation of the salt $H_4Mn(AsO_4)_2$, which latter crystallises in rectangular plates Several double salts with the alkali arsenates are also known[11]

[1] *Pogg Ann* , 1848, 74, 450
[2] *Annalen,* 1849, 69, 208
[3] *Ann Chim Phys* , 1861, [3], 61, 433
[4] *Annalen,* 1877,**190,** 191
[5] Seo also Viard, *Compt rend,* 1899, 129, 412
[6] Dakin, *Zeit anal Chem,* 1900, **39,** 784
[7] Hermann, *Pogg Ann,* 1848, 74, 303 See also Barbier, *Compt rend,* 1902, 135, 1054, 1109
[8] Auger, *Compt rend,* 1901,**133,** 94
[9] Christensen, *J pr Chem* , 1883, [2], 28, 1, Scheming, *J pr. Chem* , 1892, **[2],** 45, 515
[10] Wedekind, *Zeit Elektrochem,* 1905, **11,** 850, *Ber deutsch physik Ges,* 1906, 4, 412 Schoen, *Metallurgie,* 1911, 8, 739
[11] Lefevre, *Compt rend,* 1890, **110,** 405

Manganese Anhmomdes—Two compounds, Mn_2Sb and Mn_3Sb_2, exist,[1] and .can be prepared by beating the elements in the right proportions, Ahe former is strongly, the latter only weakly magnetic.

MANGANESE AND BORON

524 *Manganese Dibortde*, MnB_2, is produced when a mixture of manganese thermite and boron is lgnited or the oxide reduced with boron, and may be purified by treatment with chlorine It forms grey-black crystals, which, when pure, are non-magnetic, decompose in warm water, and dissolve in concentrated acids [2]

Manganese Monoboride, MnB, is prepared by the reduction of red oxide of manganese with boron at a white heat in a magnesia crucible, or by the direct umon of its elements, and forms a black, crystalhne powder of specific gravity 6 2, which resembles the dibonde in its properties, but is strongly magnetic and dissolves more readily in acids [3]

Manganese borate is used in the preparation of drying oils and oil varnishes [4], it is made by adding manganous sulphate to a solution of borax, washing and drying the precipitate It is a mixture of varying composition, not a definite compound[5] The compounds $Mn(BO_2)_2$ and MnB_4O_7 have been prepared by melting manganese oxide or carbonate with boron trioxide [6]

MANGANESE AND THE ELEMENTS OF THE CARBON GROUP

525 *Manganese Carbide*, Mn_3C, is formed when red oxide of manganese is heated with charcoal or calcium carbide in the electric furnace It has the specific gravity 6 89, and with water yields equal volumes of hydrogen and methane

$$Mn_3C + 6H_2 = CH_4 + H_2 + 3Mn(OH)_2$$

It burns readily in oxygen, and is easily attacked by fluorine and chlorine [7] When very strongly heated it dissociates, the manganese volatilises, and the carbon remains as graphite [8]

[1] Williams, *Zeit anorg Chem*, 1907, **55,** 1
[2] Wedekind, *Ber*, 1905, 3& 1228, Wedekmd and Fetzer, *Ber*, 1907, 40, 1264, Binet du Jassonneix, *Ber*, 1907, 40, 3193
[3] Binet du Jassonneix, *Compt rend*, 1904,**189,** 1209, 1906,**142,** 1336
[4] Hartley and Ramage, *Journ Chem Soc*, 1893, 63, 129
[5] See Endemann and Paisley, *Zeit angew Chem*, 1903,**16,** 175
[6] Guertler, *Zeit anorg Chem*, 1904, 40, 244
[7] Moissan, *Compt rend*, 1896, **122,** 421, 1897, **125,** 839
[8] Gin and Leleux, *Compt rend*, 1898,**126,** 749

Manganese Carbonate, $MnCO_3$, occurs in the pure state in the rose-red crystals of manganese spar, rhodochrosite or dialogite, and also as an lsomorphous mixture with chalybite These minerals crystallise, like calc-spar, in rhombohedra, but manganocalcite, $(Mn,Ca,Mg)CO_3$, is isomorphous with aragomte

Hydrated manganese carbonate is obtained as a white precipitate by mixing a solution of the chloride or sulphate of manganese with sodium carbonate In the moist state it soon becomes brown-coloured on exposure to the air, it dissolves in 8,000 parts of pure water, and in about half this quantity of water saturated with carbon dioxide

Manganese and Cyanogen —When a concentrated solution of manganese acetate is warmed with solid potassium cyamde a green precipitate is thrown down of $KCN,Mn(CN)_2$, this gradually disappears, and in its place dark blue crystals of *potassium manganocyamde,* $K_4Mn(CN)_6,3H_2$, are formed[1] The manganocyamde is obtained also when manganous carbonate is heated to a temperature of from 40° to 50° with a solution of potassium cyamde[2] The salt crystallises in deep violet-blue, efflorescent, tetragonal tablets Its solution oxidises on exposure to air with formation of *potassium manganicyanide,* $K_3Mn(CN)_6$, which crystallises in dark-red prisms This latter salt when brought into contact with potassium amalgam in aqueous solution is again transformed into manganocyamde The constitution of these complex salts will be referred to under the corresponding iron compounds

Manganese Thiocyanate, $Mn(SCN)_2$, may be prepared from manganous sulphate and barium thiocyanate The anhydrous salt is yellow, and forms a green hydrate with $3H_{20}$, which crystallises at the ordinary temperature Concentrated aqueous solutions are green, but become pink when they are diluted[3]

Manganese Sihcides—Some doubts exist as to the number of definite compounds formed by these elements A study of the freezing-point curve for mixtures of the two[4] indicates the existence of the two compounds, Mn_2Si and MnSi The compounds $MnSi_2$[5] and Mn_3Si_2[6] have also been described

The silicide, Mn_2Si, is formed when the two elements are

[1] Eaton and Fittig, *Annalen,* 1868, **146,** 157
[2] Descamps, *Ann Chim Phys,* 1881, [5], **24,** 178
[3] Kumakoff Quoted by Grossmann, *Ber* , 1906, 87, 559
[4] Doennckel, *Zeit anorg Chem,* 1906, **60,** 117
[5] De Chalmot. *Amer Chem J,* 1896, **18,** 536
[6] Gin, *Compt rend,* **1906,148, 1229.**

heated together in the electric furnace,[1] by firing a mixture of silica, manganese oxide, and aluminium, or by heating a mixture of potassium sikcofluoride, red oxide of manganese, copper, and sodium (Lebeau) It is a very hard, brittle mass, which has a metallic lustre and steel-grey colour and a specific gravity of 6 4 It is not decomposed by water at the ordinary temperature, but it is attacked by steam, oxygen, or chlorine at a red heat, and dissolves in hydrochloric acid Fluorine decomposes it at the ordinary temperature

The *monosihcide,* MnSi, forms hard, lustrous, tetrahedral crystals of specific gravity 5 9, whilst the *disilictde,* $MnSi_2$, forms dark-grey, octahedral crystals of specific gravity 5 24 The compound described by 6m of the formula Mn_3Si_2 is probably impure Mn_2Si (Lebeau)[2]

Manganous Sihcates occur as isomorphous constituents ot many minerals, and some naturally occurring manganese silicates are also known Thus, for instance, rhodonite, $MnSiO_3$, occurs in light brownish-red, transparent, trichnic crystals, and tephroite, Mn_2SiO_4, crystallises in the tetragonal system in rose-red, brown, or grey masses, and usually occurs together with rhodonite

DETECTION AND ESTIMATION OF MANGANESE

526 Manganese is distinguished by forming a flebh-colomed sulphide readily soluble in dilute acids In the course of analysis manganese is thrown down with the sulphides and hydroxides of the metals which are precipitated by ammonium sulphide If the precipitate be tieated with very dilute cold hydrochloric acid, the sulphides of cobalt and nickel, if present, remain undissolved The solution is heated in order to remove the sulphuretted hydrogen, oxidised with potassium chlorate, and an excess of caustic soda is added Iron, manganese, and uranium are thus thrown down as hydroxides The washed precipitate is then dissolved in hydrochloric acid, the liquid neutralised, and ammoma and ammonium chloride are added, when the whole of the metals, with the exception of manganese, are thrown down, the filtrate is then evaporated to dryness, and the residues heated to get rid of ammonium salts The mass which

[1] Vigouroux, *Compt rend* , 1895,**121,** 771, 1905, **141,** 722, Lebeau, *Compt rend,* 1903, **186,** 89, 231, *Bull Soc chim,* 1903, [3], 29, 797, *Ann Chim Phys,* 1904, [8], 1, 553.

[2] *Compt rend,* 1907,**144,** 85

remains can be treated in various ways for the detection of manganese The simplest plan is to fuse a small quantity of the residue with caustic soda and saltpetre, when the dark-green potassium manganate is formed, and this colour becomes deep blue on coohng It dissolves in water with a green colour, which on addition of a little nitric acid turns red Other characteristic reactions for the manganese salts are the following Potash and soda precipitate the white hydroxide, which soon becomes brown on exposure to air Ammonia in the presence of ammonium chloride produces no iminediate precipitate, but the solution rapidly absorbs oxygen from the air, brown mangame hydroxide being deposited When a manganese compound is fused with borax an amethyst-coloured bead is obtained in the outer flame, and this in the inner flame becomes colourless

The non-luminous gas flame is coloured green by manganese chloride, and this exhibits a spectrum in which the lines in the green and yellow are [1] 5587(a), 5392(/3), and 5195(y) The spark spectrum of manganese contains a large number of bright lines, of which the most important are 6022, 6017, and 6014 in the orange, 4824 and 4784 in the green, 4766, 4762, and 4754 in the blue, 4235 and 4228 in the indigo (Lecoq de Boisbaudran)

The absorption spectrum of permanganic acid and its potassium salt exhibits in very dilute solution five distinct bands, a more concentrated solution gives continuous absorption in the yellow and green, and this is observed also in certain solutions of mangamc salts The latter, however, do not show the bands on dilution The manganous salts also show a characteristic absorption spectrum, chiefly in the ultra-violet [2]

In order to estimate manganese gravimetncally it may be precipitated as the carbonate or, by the action of bromine water and ammoma or nitric acid and a chlorate, as the dioxide These are both converted by ignition to the red oxide, Mn_3O_4, in which condition the manganese may be weighed, a better method is to ignite the precipitate, dissolve it in sulphuric acid, drive off excess of acid, and weigh as the sulphate, $MnSO_4$ Manganese may also be precipitated as the sulphide, and either weighed in this form by Kose's method, or converted to the oxide by ignition, or to the sulphate It may be precipitated as ammonium

[1] **Hoppe Seyler,** ***J Chem,*** **1870,110, 303.**
[2] **Lambert,** ***Compt rend,*** **1905,141, 357**

manganese phosphate and weighed as the pyrophosphate, $Mn_2P_2O_7$ Electrolytic methods have been proposed.

Manganese always occurs in nature together with iron In order to separate these the solution is heated with ammonium chloride, neutrahsed with the requisite quantity of ammonia, and the iron precipitated with ammonium acetate The manganese can then be estimated in the filtrate in the above way An equally accurate method, but easier and more rapid, is to remove the iron by precipitation with " cupferron " [1]

Manganese may be estimated volumetncally by titration with potassium permanganate in presence of zinc sulphate (p 1190), or by conversion into permanganate, which is then estimated by titration with standard oxalic acid, hydrogen peroxide, or some other reducing agent When small quantities are concerned this is best done by boiling the manganese salt with concentrated nitric acid, solid lead peroxide, and a little dilute sulphuric acid, and filtering the resulting liquid through asbestos, or by digesting the salt with nitric acid and sodium bismuthate, or a persulphate, sulphuric acid, and silver nitrate

Manganese may also be precipitated as the hydrated dioxide by boiling with dilute sulphuric acid and ammonium persulphate, and the dioxide either estimated volumetncally, or in the absence of other metallic salts, gravimetncally by conversion into the red oxide [2]

Very small traces of manganese can be detected and estimated colorimetncally by oxidising it to permanganate and comparing its colour with potassium permanganate solutions of known concentration [3]

Valuation of Manganese Ores —The most accurate and convenient methods for the estimation of the quantity of manganese dioxide in manganese ores are those of Bunsen,[4] and of Fresenius and Will[5] By the former method, the quantity of chlorine evolved on treatment with hydrochloric acid is directly determined The gas is collected in a solution of potassium iodide, and the liberated iodine estimated with a dilute solution of sulphurous acid or sodium thiosulphate

Fresenius and Will's method depends upon the action

$$MnO_2 + C_2(OH)_2 + H_2SO_4 = MnSO_4 + 2CO_2 + 2H_2,$$

[1] **See Fresenius, *Zext anal Chem*, 1911, 50, 35**
[2] **von Knorre *Zext angew Chem*, 1901,14, 1149**
[3] **See Marshall, *Chem News*, 1904, 88, 76,**
[4] ***Journ Chem, Soc*, 1856, 8, 219.** [5] ***Annalen*, 1843, 47, 87.**

i e 88 00 parts of carbon dioxide correspond to 86 93 parts of manganese dioxide The reaction is carried out in a weighed apparatus provided with a drying tube, the loss of weight being ascertained

Another method, based on the same reaction, is to start with a known amount of oxalic acid and to determine the excess of this, after the manganese dioxide has been reduced, by titration with standard potassium permanganate

The Atomic Weight of manganese has been determined by several chemists, among the earliest of whom were Berzehus,[1] Dumas,[2] and V Hauer[3] Dewar and Scott, by estimating the percentage of silver in silver permanganate, obtained 55 0 1 ,[4] and Mangnac, by converting pure MnO into $MnSO_4$, obtained 55 O2[5] Baxter and Hines from the analysis of the bromide and chloride have found 54 96[6] The value at present (1922) adopted is 54 93

[1] *Pogg Ann* , 1828,14, 211
[2] *Annalen,* 1860, 113, 25
[3] *Wten Akad Ber*, 1857, 25, 124
[4] *Proc Boy Soc*, 1883, 35, 44
[5] *Zeit anal Chem*, 1884, 23, 123
[6] *J Amer Chem Soc,* 1906, 28, 1560

GROUP VIII.

Sub-group (a) Iron, Cobalt, Nickel
„ *(b)* Ruthenium, Rhodium, Palladium
,, (c) Osmium, Indium, Platinum

527 The metals placed by Mendeleev in the eighth vertical group form a very remarkable feature of his arrangement of the elements They occur in three sub-groups, each containing three metals, forming the termination of the even horizontal series 4, 6, and 10, each group being the connecting link between the elements of the even series which precedes and those of the odd series which follows The three metals which make up each horizontal sub-group resemble one another very closely, and differ much less in atomic weight, atomic volume, and general physical properties than is usual in the successive elements of a horizontal series, as may readily be seen by a reference to Lothar Meyer's diagram (p 62)

This remarkable similarity is borne out by the chemical behaviour of these elements, the various platinum metals, for example, being so similar that their separation from each other is a matter of the greatest difficulty, and this is true also of cobalt and mckel

At the same time, a certain degree of similarity can be traced between those metals which are in the same vertical column, more particularly in sub-groups *b* and *c* Thus ruthenium and osmium, rhodium and iridium, palladium and platinum agree very closely in many of their most characteristic properties, such, for example, as the formation of a tetroxide, which is peculiar to ruthenium and osmium, etc

From the analogy of the preceding groups, it would be expected that the characteristic oxide of the metals of this group would have the formula MO_4 or M_2O_8Actually, however, only ruthenium and osmium form such an oxide, and this is not an acidic oxide, whilst all the metals of the group form lower oxides, many of which correspond to series of stable salts

All these metals, unlike the other members of the even series of the periodic system, form metallo-organic compounds [1]

A very characteristic property of the metals of this group is their tendency to form complex radicles with other elements or groups, which then act as basic or acidic radicles, and thus give rise to extended series of compounds These substances, as a rule, differ entirely in properties from the ordinary salts of the metal, this being due to the fact that each radicle has its own characteristic properties, and those of the metal appear only when the radicle has been broken up Some of the most important of these complex derivatives are the double cyamdes, such as the ferrocyanides and their analogues, the complex halogen derivatives of the platinum metals, the ammoniacal derivatives of cobalt and of the platinum metals, the double nitrites, sulphites, etc This tendency is shared by chromium and to some extent by manganese, copper, and other metals which either iminediately precede or follow the metals of Group VIII in the periodic system

SUB-GROUP *(a)*. THE IRON GROUP.

Iron, Cobalt, Nickel

528 These three metals are all magnetic, melt at a high temperature, are oxidised when strongly heated in arr or oxygen, and decompose steam at a red heat They all form basic oxides of the formula $M^{n}O$, and a corresponding series of coloured salts in which the metal is divalent The sesquioxides $M^{111}{}_2$ O_3also act as basic oxides, but the corresponding salts of mckel and cobalt are so unstable that they speedily decompose with formation of salts corresponding to the lower oxide Those of iron, on the other hand, are much more stable, and are formed from those of the lower oxide on exposure to the air These metals, moreover, all yield oxides of the formula M_3O_4, to which no stable salts correspond, and which are probably to be considered as being themselves salts of the formula $M^{11}M^{lll}{}_2$ O_4 Cobalt, in addition to these, probably forms an unstable acidic dioxide, whilst derivatives of the corresponding mckel oxide are also known, but no such derivatives of iron have been prepared, although the corresponding sulphide exists as iron pyrites Iron,

[1] **Pope and Peachey,** ***Proc Ghem Soc*** **, 1907, 23, 86**

however, forms a series of compounds known as the ferrates, which are derived from, a hypothetical acidic trioxide, FeO_3, to which no analogue is known? among the compounds of mckel and cobalt

Nickel and iron both unite with carbon monoxide to form volatile liquids, whereas cobalt forms a crystalline carbonyl ,

Nickel has much less tendency to form complex radicles than cobalt or iron, the most important of such derivatives formed by the last two being the cobaltammines and the cyanogen compounds of iron

IRON (FERRUM) Fe = 55 84. At No 26

529 Iron is the most important of all the metals It seldom occurs in the metallic state in nature, the ores of iron are, however, found widely distributed It is usually supposed that the iron age followed those of copper and bronze, although in many cases the art of working in iron became known at a very early period It is, however, to be remembered that metallic iron is rapidly destroyed by rusting, at any rate in damp situations, and this may to some extent account for the comparatively rare occurrence of very early iron implements

It appears probable that iron was first obtained from its ores in India, and it is certain that both the Assyrians and the Egyptians employed iron implements many centuries before our era In the Pentateuch the metal iron is mentioned, as well as the furnaces in which it was prepared, the Hebrew name for iron, Barzel, is derived from the root Bazal, which signifies " to be hard," whilst the derivation of the Greek word *airjpos,* which occurs in Homer, is unknown The Greeks obtained their iron from the Chalybes, a nation dwelling on the south coast of the Black Sea, from whom the Asiatic nations also obtained the metal The Komans, on the other hand, procured their iron, not only from this district, but also from Spam, Elba, and Noncum The Elban iron mines, which are to this day renowned for their fine specular iron, were worked by the Etruscans

The word iron, which is identical with the Scandinavian " larn " (instead of " isarn "), and with the German " Eisen " (adjective, " eisern "), appears to be connected with the Sanscrit " ayas " (Latin " aes "), and this, according to Grimm, is an indication that bronze was in use among the Germans at a much earlier date than iron The alchemists connected iron with Mars, the god of war, and gave to it the sign .

Native iron occurs, according to Andrews,[1] in small spicule distributed throughout the basalt of the Giant's Causeway, as well as in the old lavas of the Auvergne. The occurrence of terrestrial iron in large lumps has also been observed, these masses have, however, probably been formed in the firing of coal-pits when the burning mass has come in contact with ores of iron, the product is termed natural steel

The native metal occurs more frequently in the form of *meteoric iron* The meteorites falling in larger or smaller masses from extra-terrestrial sources may be divided into two groups "Earthy meteorites," which consist chiefly of silicates, and "Meteoric irons," which consist of iron together with a larger or smaller quantity of nickel, the presence of this latter metal being characteristic of meteoric masses[2] Meteoric iron likewise usually contains small quantities of cobalt and other metals, as well as graphite, ferrous sulphide, and schreibersite, $(Fe,Ni,Co)_3P$, this last compound being one which is not known to exist in any terrestrial mineral When the surface of a meteoric iron is planed and polished, and then treated with dilute nitric acid, peculiar configurations make their appearance which were first noticed by Widmanstatten in the year 1808 These consist of rhombic foha or crystalline markings (shown in Fig 191) which have a metallic lustre, the spaces enclosed by these markings are somewhat raised, so that a surface of meteoric iron thus treated may be used as a plate from which an engraving can be obtained Similar structures have been artificially obtained in iron, steel and other alloys by slow cooling Meteoric iron frequently occurs in considerable masses, thus, for instance, that which was discovered by Pallas in Siberia originally weighed 800 kilos [analysis *(a)*\ whilst that found in Bahia weighed nearly 7,000 kilos , a still larger mass occurs at Chaco-Gualamba in Peru, which is said to weigh 16,000 kilos , and similar large masses have been found in other localities, both in North and South America, as well as in Africa The largest known masses are those found at Ovifak on the Island of Disko, off Greenland, where fifteen blocks of meteoric iron occur, the weight of the

[1] ***Brit Assoc Reports*, 1852, 34**

[2] **See Fletcher's *Introduction to the Study of Meteorites* (published by the Trustees of the British Museum, 1904) See also Prior, *Mm Mag* , 1916, 18, 26, 1920,10,51**

two largest being, according to Nordenskjold,[1] 21,000 and 8,000 kilos [analysis (b)]

The following table gives the composition of several meteoric irons

Locality Analyst	(a) Siberia Berzehus	(b) 0vifak Nordenskjold	(e) Brazil Damover	(d) Tennessee J L Smith
Iron	88 04	84 49	63 69	9115
Nickel	10 73	2 48	33 97	8 01
Cobalt	0 46	0 07	148	0 72
Copper	0 07	0 27	0 05	0 06
Manganese	013			
Carbon	0 04	10 62	0 02	
Sulphur	trace	152	0 02	
Phosphorus		0 20	0 05	
Chlorine		0 72		
Silicate	0 53	0 09	—	
	100 00	100 46	99 28	99 94

Finely divided meteoric iron is constantly falling from extra-terrestrial space on to the earth the occurrence of this meteoric dust has been observed in Sweden and in the snow-fields of Northern Siberia, the snow enclosing black magnetic particles which contain cobalt as well as iron Similar particles of meteoric dust, consisting of metallic iron, have been found by Murray, of the *Challenger* expedition, at great depths in mid-ocean It is only under conditions such as the above that it is possible to detect this fine meteoric dust, in consequence of the enormous accumulation elsewhere of terrestrial dust

530 Iron is usually found in combination either with oxygen or sulphur 0f the large number of minerals which contain iron only those will now be mentioned which occur most commonly and in the largest quantity, the ores will be specially described hereafter The most important oxygen compounds of iron are red haematite, or specular iron ore, Fe_2O_3 brown haematite, $2Fe, 3H_2$, magnetic iron ore, Fe_3O_4, spathic iron ore, $FeCO_3$, the latter containing other isomorphous carbonates Again, iron pyrites, FeS_2, occurs largely, whilst magnetic pyrites, Fe_7S_8, is less common, iron sulphide also forms an important constituent of copper pyrites, $CuFeS_2$, arsenical pyrites, FeAsS, and other minerals Silicates of iron are found in most geological

[1] *Pogg Ann*, 1874,151, 164

formations, and from these iron oxide finds its way into the soil, in which it is usually present in considerable quantity, imparting to it a reddish or brown colour. This fact was known to Pliny, who mentions that the presence of iron may be recognised by the colour of the soil Iron compounds are contamed in solution in spring- and river-waters, as well as in the water of the ocean, and it is from one or other of these sources that plants obtain the iron which forms an essential constituent of their chlorophyll.

In 1702 N Lemery proved that the ashes of plants contained iron this observation was confirmed by the experiments of Geoffroy in 1705, who, however, assumed that the iron was not originally contained in the plants, but that it was produced when they were burned 0ther celebrated chemists, such as Becher, held the view that the iron which made its appearance when certain substances were subjected to chemical treatment was not contained in themi, but was produced independently This erroneous opimon was first disproved by Lemery

Iron likewise is a necessary constituent of the animal body, for instance, haemoglobin, the red colouring matter of the blood, contains 0 336 per cent of iron Iron preparations have also long been employed as medicine, especially in anaemia After the use of iron the number of red corpuscles is increased, and the amount of haemoglobin which they contain becomes larger The presence of iron in the blood was first shown by Menghim of Bologna in 1747

The existence of iron in large quantities in meteoric masses indicates a wide cosmical distribution of the element, and this conclusion has been confirmed by spectrum analysis, which indicates the presence of iron in the sun and many fixed stars

531 *Preparation of Pure Iron* —Iron is usually produced from its oxides by reduction with carbon, and is thus obtained on the large scale, thus prepared, however, iron is not pure, but contains carbon In order to obtain chemically pure iron, the oxide, or oxalate, may be heated in a current of hydrogen at the lowest possible temperature, the metal is obtained by this process as a black powder which oxidises and becomes incandescent in the air, if the reduction is carried on at a higher temperature the powdered iron is not pyrophoric Reduction at 1000° of the oxide or basic nitrate made by heating very carefully purified ferric nitrate gives a product with a distinct metallic lustre and a light grey colour The iron thus obtained is of exceptional purity and is remarkably inert [1]

[1] **Lambert and Thomson, *Journ Chem Soc*, 1910, 97, 2430**

Pure iron may be prepared also by electrolysis, [1] this process has received considerable attention during recent years and deposits containing 99 98per cent of iron have been obtained Two solutions from which satisfactory deposits can be obtained have been used on an industrial scale One consists of a highly concentrated solution of ferrous and calcium chlorides, which is used at a temperature between 90° and 110° with a current density of 18O amperes per square foot of cathode area The other solution consists of a concentrated solution of ferrous and sodium sulphates, it is used at a temperature near the boiling point with a high current density Electrolytic deposition has also been used for making up worn surfaces of machinery to correct gauge

Properties —Pure iron has a specific gravity of 7 86, possesses an almost silver-white lustre, and takes a high polish, it is, with the exception of cobalt and nickel, the most tenacious of all the ductile metals at the ordinary temperature, but becomes brittle at the temperature of liquid air [2] Its average specific heat over 15-10O° is O 10983, but this increases somewhat rapidly with the temperature up to 850°, after which it decreases [3]

Pure iron becomes soft at a red heat, and may be readily welded at a white heat, but above the welding point it becomes brittle under the haminer It fuses less readily than cominercial wrought iron, the melting point being 1505-1520°,[4] and when heated in the electric furnace it readily distils, much frothing taking place in the boiling liquid owing to the evolution of occluded gases [5] It is attracted by the magnet and may also be rendered magnetic, but loses this property rapidly Carbonised iron or steel, on the other hand, retains its magnetic property at the ordinary tejnperature, but loses it at a red heat

When iron is heated from the ordinary temperature to the melting point, it undergoes three changes These changes are

[1] Maximowitsch, *Zeit Eleklrochem,* 1905, **11,** 52, Ryss and Bogomolny, *ibid,* 1906, **12,** 697 Compare Amberg, *ibid,* 1908, **14,** 326, 1910, 16, 125, Muller, *MetaUurgie,* 1909, 6, 145 Pfaff, *Zeit ELEktrochem,* 1910, 16, 217 Fischer and Ouillet, *J Iron and Steel Inst,* **1914,** 90, 66, Hughes, *The Electrician,* 1920, **85,** 53O

[2] Dewar and Hadfield, *Proc Roy Soc* , 1905, 74, 326

[3] Harker, *Phil Mag,* 1905, [6], 10, 43O

[4] See Carpenter, *J Iron Steel Inst,* 1908, 78, 290

[5] Moissan, *Compt rend* , 1906,**142, 425**

accompanied by an absorption of heat and the curve of heating e"xhibits corresponding breaks Similarly, when molten iron is cooled, these changes occur in the reverse order, accompamed by evolution of heat, and the cooling curve exhibits similar breaks Owing to an inertia on the part of the iron to undergo these changes, the temperature at which each occurs is different according as the metal is heated or cooled, the breaks on the cooling curve are slightly lower than the corresponding ones on the heating curve The explanation of these changes lies in the fact that iron exists in four allotropic forms,[1] distinguished as a-, -, 7- and S-iron (fernte), though some regard the ß -modification as a solid solution of 7- in a-ferrite[2] The a-form, which is the sole constituent of pure soft iron and is capable of assuming magnetic properties, is stable from the ordinary temperature up to about 76O°, when the first change occurs, coinciding with the disappearance of magnetic properties, the ß-form is stable from this point up to about 90O°, when the second change takes place, the 7-form, which is the variety usually formed on solidification of the fused metal, is stable from this to about 140O°, when the third change occurs, the -form is stable from here to the melting point (15O5°) The a-, *ft-*, and 7-forms all crystallise in the regular system, the a- and /3-forms possess a space-centred and the 7-form a face-centred cubic lattice[3]

Iron combines readily with the elements of the chlorine group, and when strongly heated burns in oxygen, forming the magnetic oxide, and at a red heat decomposes steam with formation of the same oxide, it also burns at a red heat in sulphur vapour, and combines with carbon at a high temperature

Iron readily occludes many gases, notably hydrogen, mtrogen, and the oxides of carbon The solubilities of hydrogen and nitrogen in iron have been studied[4] and found to be proportional to the square root of the pressure of the gas The solubility increases with temperature, and shows a marked alteration near the ß-*y* transition point, namely, at 93O°. The excess of gas is

[1] Osmond and Caitaud, *Ann des Mines,* 1901, 17, 110, 18, 113, *Compt rend* , 1906,**142,** 153O, **143,** 44, Ruer and Goerens, *Ferrum,* 1915,**13,** 1

[2] Benedicks, *J Iron Steel Inst,* 1912, 86, 242, *Eighth Inter Cong App Chem,* 1912, **22,** 13, Carpenter, *J Iron Steel Inst,* 1913, 1, 315, Sauver, *J Inst Metals,* 1913, 88, 171

[3] Westgren and Lmdh, *Zeit physthal Chem,* 1921, 98, 181, Westgren and Phragmen, *ibid,* 1922,**102,** 1

[4] Sieverts, *ibid,* 1907, 8O, 129, Junsch, *Stahl und Eisen,* 1914, 84, 252.

liberated on cooling the molten metal, and that retained by the solid may be removed by heating it in vacuo

Iron is also permeable so hydrogen If an iron tube is iminersed in acid [1] or used as cathode in electrolysis [2] the liberated hydrogen diffuses throughthe metal to the inside Diffusion of molecular hydrogen through iron begins at about 350° and rapidly increases with temperature [3] During its passage it combines with any sulphur, carbon, or phosphorus which may be present, thus removing them and rendering the iron soft [4]

Iron dissolves in most dilute acids with evolution of hydrogen Dilute nitric acid dissolves it in the cold without the evolution of any gas and with the formation of ferrous nitrate, $Fe(NO_3)_2$, and ammonium nitrate, when heat is applied, or when a stronger acid is employed, oxides of nitrogen are evolved, and ferric nitrate, $Fe(NO_s)_3$, is formed

Passive Iron—When iron is placed in concentrated nitric acid it appears to undergo a change, and is then not attacked by the acid [5] It will then not precipitate metals, such as copper, from solutions of their salts, and us highly resistant to rusting Iron in this state is termed " pasowe " This condition may be brought about by the action, not only of nitric acid, but also of other substances such as chloric, Sromic, iodic, and chromic acids, and even hydrogen peroxide, as well as by electrolysis, the iron acting as anode in sulphuric acid solution [6]

The cause of this phenomenon has not yet been definitely ascertained, and many suggestions have been made to account for it It is possible that there are more kinds of passivity than one, and that no theory will cover all cases [7] Schonbein, Faraday, and Beetz regarded it as due to the format on of a thin film of oxide on the surface of the iron, which protects it from further action, and this film, according to Haber and Goldschmidt,[7] possesses metallic conductivity

[1] Fuller, *Trans Amer Elect Soc*, 36

[2] Charpy and Bonnerot, *Compt rend*, 1912,**154,** 592, Fuller, loc *cit*

[3] Charpy and Bonnerot, *Compt rend*, 1913, **156,** 394, Bellati and Lussana, *Nuovo Cim*, 1913, [6], 5, i, 389 See also Smits, *Stahl und Eisen*, 1919, 39, 3, 73, 406, Schmidt and Lucke, *Zeit physikal Chem* , 1921, 98, 152

[4] Kier, *Phil Trans*, 1790, 8O, 359 See also Young and Hogg, *J Physical Chem*, 1915,19, 617

[5] See Gunther and Schulze, *Zeit Elehtrochem*, 1912, 18, 326, Flade and Koch, *Zeit physikal Chem*, 1914, 88, 307

[6] Friend, *Journ Chem Soc*, 1912,**101,** 50

[7] *Zeit Elektrochem*, 1906, 12, 49 See also Gordon and Clark, *J Amer Chm Soc*, 1906, 28, 1534, Byers, *ibid*, 1908, 30, 1718, Krassa, *Zeit Elektrochem* , 1909,**15,** 490, Dunstan and Hill, *Journ Chem Soc* ,1911,99,1853

Fredenhagen[1] supports the hypothesis that in the passive condition the iron is coated with a thin layer of gas, and points out that iron rendered passive by anodic polarisation has a different behaviour from that made passive by nitric acid, probably because the protective layer is oxygen in the one case, and nitric oxide in the other Iron is readily rendered passive to a marked degree by mtrogen tetroxide and the presence of a film of this gas has also been suggested as the cause of passivity[2] Hittorf,[3] Heathcote,[4] and Fmkelstein,[5] on the other hand, regard the phenomenon as due to a chemical or electrical change taking place in the molecules forming the surface of the iron, the last-named author suggesting that ordinary iron consists of both ferrous and ferric iron molecules, and that by the action of the above substances the ferrous iron molecules are dissolved or converted into ferric molecules, which are not capable of attack by the reagents[6] A similar idea is found in the theory of Smits,[7] who postulates two lands of iron a, base, and *ft,* noble, which are in equilibrium During anodic polarisation, or in nitric ac

be established, and consequently there is produced on the surface an excess of */3* iron, the noble variety, so that the metal is resistant to attack or, in other words, is passive Hydrogen (as also the halogens) tends to accelerate the change of */3* to *a* During anodic polarisation or when the metal is dipped in nitric acid the hydrogen it contains is completely removed from the surface by oxidation In either case, therefore, the passivity produced will persist until hydrogen diffuses from the interior of the metal to the surface, when the equilibrium is accelerated, the *a* variety being re-foimed, and the metal becomes active again

Lambert and Thomson[8] have prepared iron of exceptional punty and found it to be extremely resistant to chemical action, or, in other words, " passive " It would therefore appear that pure iron is passive,[9] and Lambert[10] has proposed the following

[1] *Zeit physikal Chem* , 1903, 43, 1, 1908, 63, 1
[2] Young and Hogg, *loc cit* [3] *Zeit physikal Chem* , 190O, 34, 385
[4] *Ibtd,* 1901, 37, 368, *J Soc Chem Ind,* 1907, 26, 899
[5] *Ibid* , 1902, 39, 91
[6] See also Smits and Lobry de Bruyn, *Proc K Akad Welensch Amsterdam,* 1917,19, 88O, Brown, *J Phys Chem* , 1921, 26, 429
[7] *J Soc Chem Ind,* 1916, 35, 928, *De Ingemeur,* 1915,357 See also Smits, *The Theory of Allotropy* (Longmans), 1922, p 342
[8] *Journ Chem Soc* , 1910, 97, 2426
[9] See also Flade and Koch, *Zeit Elektrochem* , 1911,18, 335
[10] *Journ Chem Soc* , 1915,**107,** 218

definition of passivity The production by some chemical or electrochemical means of a physically homogeneous layer on the surface of a metal of which the surface was originally physically heterogeneous

Passive iron is rendered active agam by chlorine, bromine, or iodine ions Anodic polarisation by electrolysis of an iron salt can be made periodic by the addition of chlorine ions to the solution [1]

Finely Divided or Reduced Iron (ferrum redactum) has long been used in medicine *Spongy iron,* prepared by the reduction of burnt pyrites or other suitable iron ore, has been employed as filtering material for purifying water for domestic use

532 *The Rusting of Iron* —The formation of rust on exposed surfaces of iron was formerly supposed to be due to direct oxidation of the metal However, contact with both air and water in the liquid state is necessary for the production of rust [2]

The investigations of Crace-Calvert[3] and Crum Brown[4] indicated that carbon dioxide, too, plays an essential part in the reaction, and in most cases of rusting it is certainly an active agent The feebly acid solution of carbon dioxide in water attacks the iron with considerable rapidity, yielding a solution of ferrous carbonate or bicarbonate This is then oxidised by the oxygen with formation of hydrated ferric oxide and evolution of carbon dioxide, which is thus available for further attack, its action therefore being catalytic

$$Fe + 2H_2O + 2CO_2 = Fe(HCO_3)_2 + H_2$$
$$4Fe(HCO_3)_2 + 2H_2O + O_2 = 4Fe(OH)_3 + 8CO_2$$

Dunstan, Jowett, and Goulding[5] have suggested that the presence of carbon dioxide is not essential, but that the iron acts on the water and oxygen with formation of ferrous oxide and hydrogen peroxide These two substances then mteract with formation of hydrated ferric oxide

$$Fe + O_2 + H_2O = FeO + H_2O_2$$
$$2FeO + H_2O_2 = Fe_2(OH)_2,$$

[1] **Smits and Lobry de Bruyn,** ***Proc K Akad Wetensch Amsterdam,*** **1916, 18, 807**

[2] **Dunstan, Jowett, and Goulding,** ***Journ Chem Soc,*** **1905, 87, 1648,** ***Proc Chem Soc,*** **1907, 23, 63**

[3] ***Mem Manch Phi Soc,*** **1876, 5, 104**

[4] ***J Iron Steel Inst,*** **1888, II, 129**

[5] ***Loc cit***

the excess of hydrogen peroxide immediately reacting with iron to form a further quantity of rust No evidence of the intermediate formation of hydrogen peroxide has been found, the authors basmg their conclusion mainly on the fact that substances which destroy hydrogen peroxide appear also to prevent rusting

Water is itself dissociated into H and OH' ions, and Whitney [1] has suggested that iron combines directly with the OH' ions to form ferrous hydroxide while hydrogen is liberated The function of the oxygen is to oxidise the ferrous hydroxide to rust and also the hydrogen, thus disturbing the equilibrium and allowing the reaction to proceed further

Whether pure oxygen and water in the complete absence of carbon dioxide or other acid will cause iron to rust has been the subject of much discussion The researches of Moody [2] showed that under such conditions no rusting occurred In his experiments, however, the iron was cleaned by means of chromic acid, and the criticism has been made that it was thereby rendered passive Lambert and Thomson[3] found that an exceptionally pure sample of iron made by the reduction of carefully purified ferric nitrate did not rust, and it is therefore probable that the non-rusting of Moody's iron can be accounted for by the thorough cleaning of the metal Lambert[4] consequently concludes that only an impure iron will rust, and that rusting is due to differences of solution tension of different parts of a heterogeneous surface of impure metal The process is an electrolytic one and the oxygen acts as a depolanser by oxidising the hydrogen [5]

The formation of rust takes place to begin with but slowly, but as soon as a thin, superficial layer of rust has been formed the process goes on rapidly There is a difference of potential between rust and metal, so that electrolytic action is further increased [6] Friend [7] has suggested that rusting itself is due to the catalytic action of a sol of a higher oxide of iron which oxidises the iron and is thus reduced, but is oxidised again by oxygen He has shown that iron does not rust as quickly in moving

[1] *J Amer Chem Soc*, 1903, 86, 394
[2] *Journ Chem Soc*, 1906, 89, 720, *Proc Chem Soc* , 1907, 28, 84
[3] *Journ Chem Soc* , 1910, **97,** 2426
[4] *Ibid,* 1912,**101,** 2056, *ibid*, 1915,**107,** 218, *Proc Chem Soc,* 1912, 28, 197, *Trans Faraday Soc,* 1913, 9, 108
[5] See also Aitehison, *J Iron Steel Inst*, 1916, 1, 77, Goudnaan, *Chem Weekblad,* 1919,16, [40], 127O
[6] See Aston, *Trans Amer Elect Soc* , 1916, 29, 449
[7] *Journ Chem Soc,* 1921,**119,** 932, see also *Koll Zett,* **1921,** 28, 207.

water which would remove the sol, and that those substances which precipitate, dehydrate, dissolve, or act as protective colloids to the sol, also decrease rusting

Certain salts, especially those of ammonia,[1] promote rusting, while alkalis and alkali carbonates inhibit it[2]

Steel instruments may be kept bright by iminersion in a solution of caustic soda, or, better, of sodium nitrate In order to lessen the liability to rust, iron articles are coated with varmsh or oil-paints, or the surface is covered with oil, grease, or graphite A coating of magnetic oxide of iron, Fe_3O_4, is, however, the most efficient protection, and to obtain such a coating articles of iron are subjected to the action of superheated steam at a temperature of about 650°, this process being known, from the name of its inventor, as the Barff process

In contact with zinc, iron becomes electronegative, and is thereby to a considerable extent prevented from rusting Iron articles are therefore often covered with a coating of zinc to protect them from atinospheric corrosion This is usually done by iminersing the cleaned iron article in a bath of molten zinc (galvanising) or by packing the iron round with zinc dust in a closed chamber and heating to just below the melting point of zinc (sherardismg) The former method is more extensively employed, but the latter gives a more resistant product[3] Iron is also coated with tin by iminersion in the molten metal (tin-plate) but in this case the protection lasts only as long as the layer of tin is intact Once a portion of the iron becomes exposed it rusts much more rapidly than if no tin were present, because iron is electropositive in contact with tin The coating of iron with nickel by electro-plating is another important method of protecting it from atinospheric action

By alloying chromium with steel, a product is obtained which is capable of resisting all ordinary corrosive agents It is put on the market as *rustless* or *stainless steel*

533 *Iron amalgam* does not form readily, but on acting with a 1 per cent sodium amalgam upon a solution of ferrous sulphate a semi-sohd mass is obtained which, when in small globules, is attracted by the magnet On distilling this amalgam, metallic iron remains in a state of fine division

[1] See Vaubel, *Chem Zeit,* 1913, 37, 693

[2] See Friend and Marshall, *Journ Chem Soc,* 1914, **106,** 2776, *Proc Chem Soc* , 1914, 3O, 263

[3] Halla, *Zeit Elektrochem,* 1913,19, 221

(Bottger) The same amalgam can be formed by rubbing powdered iron with mercuric chloride and water. If an iron wire be attached to the copper pole of a Darnell element, and dipped into a solution of ferrous sulphate, whilst another iron wire from the zmc pole touches a drop of mercury lying in the solution, amalgams of varying composition are obtained according to the intensity of the current[1] Those containing only small quantities of iron are liquid, those in which more iron is present are soft and crystalline One containing 103 2 of iron to 100 of mercury forms a hard, black mass, and is obtained by submitting the liquid amalgam to a pressure of 50 tons to the square inch

METALLURGY OF IRON [2]

534 Several mythical stories point to the fact that in very early times meteoric iron, which, falling from the heavens, was considered as a gift of the gods to man, was employed in the manufacture of iron weapons Kumbary[3] relates that the chiefs in the Wadai country, in Central Africa, possess many weapons which have been worked up from meteoric masses But meteoric iron occurs so sparingly upon the earth's surface, and is, in fact, so unsuited to the manufacture of tough forgings, that at a comparatively early period in the history of civilisation men set about the smelting of iron from its ores[4]

The enormous deposits of ancient slag and furnace-cinder which are found spread over large areas in various districts of India point to the fact that the iron industry existed in that country in very early times, and even to the present day the manufacture of iron is carried on in India in the most primitive manner. It is also clear that the ancient Assyrians and Egyptians were well acquainted with the uses of iron, and the remains of their iron works have been found near Sinai But, independently of these sources, a knowledge of the methods of working iron ores also appears to have been gained by the tribes living in the North of Europe, whilst the inhabitants of the Western Hemisphere were not acquainted with these processes Little is known respecting the method employed by the

[1] **Joule,** ***Journ Chem Soc*** **, 1863,16, 378**

[2] **Further information on this subject may be obtained from the metallurgical works of Percy, Turner, Howe, Harbord, Sexton, and Carnegie**

[3] ***Compt rend*** **, 1870, 70, 649**

[4] **See " The Early Use of Iron," Brough,** ***J. Iron Steel Inst,*** **1906, 69, 233.**

ancients in the manufacture of iron, the slight information which we possess has been collected together by Agricola in his works, "De Vetenbus et Novis Metallis," and "De Re Metallica"[1] The apparatus employed was evidently of a primitive kind, and consisted of a small hearth or furnace to which was attached a bellows or blowing arrangement driven by hand, similar indeed to that which is now in use among the hill-tribes in India and in Central by igniting the iron ore with charcoal, the metal being obtained in the form of a porous lump or "bloom," which is pressed or haminered into a coherent metallic mass

The dexterity exhibited by the Hindus in the manufacture of wrought iron may be estimated from the fact of the existence near the Kutab Minar, Delhi, of a, wrought iron pillar 24 feet in length[2] This pillar stands about 22 feet out of the ground, and has an ornamental cap bearing an inscription in Sanskrit belonging to the fourth century An analysis of specimens obtained from the actual pillar by Hadfield shows that the material is an excellent type of wrought iron, made with a very pure fuel, probably charcoal

535 *Varieties of Iran and Steel* —Iron which is obtained from its ores by metallurgical processes is never pure, but contains other constituents, which greatly affect the properties of the metal and determine its value for various purposes The most important of these constituents are carbon, silicon, phosphorus, sulphur, and manganese, and, in special cases, nickel, chromium, tungsten, vanadium, cobalt, and molybdenum It is found that comparatively small variations in the amount of these substances exert an enormous influence on the properties of the metal

Four mam varieties of cominercial iron are usually distinguished

(1) *Cast iron* contains 2 2-4 5 per cent of carbon, besides varying quantities of the other elements mentioned above This variety fuses readily, and when cold is brittle and cannot be worked under the hammer

(2) *Wrought* or *malleable iron* contains little carbon and

[1] **See the translation from, the Latin edition of 1556, by H C Hoover and L H Hoover, published by *The Mining Magazine,* 1912**

[2] **A cast of this pillar was formerly to be seen in the Architectural Court of the South Kensington Museum, but was destroyed durmg a fire in 1885 A drawing of the pillar is found in St John Bay's *Prehistoric Use of Iron and Steel,* p 144, and a reproduction from a photograph in the *J Iron Steel Inst,* 1912, 85, 168, Plate 14**

fuses with difficulty, but is malleable and can therefore be worked under the haminer, and can be welded at a red heat The characteristic feature of malleable iron is that it is produced in a pasty s contains particles of slag, which cannot be completely removed from the unfused metal

(3) *Steel* comprises all malleable alloys of carbon and iron which have at any time been actually melted It contains very little slag, but otherwise does not necessarily differ in composition from malleable iron Steel possesses the valuable property of becoming hard when it is suddenly cooled from a high temperature, the intensity of this effect depending largely upon the amount of carbon which it contains

(4) *Special steels* contain, besides carbon, varying quantities of one or more of the following elements manganese, nickel, chromium, tungsten, silicon, vanadium, molybdenum, and cobalt Some of these steels have valuable mechamcal and physical properties not possessed by ordinary carbon steels

The general process of iron smelling consists essentially in the removal of the oxygen from the ores, and this is invariably carried out in practice by the action of carbon at a high temperature In addition to the oxygen, the extraneous matter contained in the ore, such as silica, alumina, lime, sulphur, etc , must also be removed, and the resulting iron must be exposed to such conditions that it acquires the composition which will fit it for the special purpose to which it is to be applied

536 *Ores of Iron*—The term iron ore includes only those minerals which contain iron both in sufficient quantity and also in a condi production of the metal Thus, for example, iron pyrites, FeS_2, which occurs in very large quantities and contains a high percentage of iron, cannot properly be described as an iron ore, although it is used as a source of iron after the removal of sulphur for the manufacture of sulphuric acid In like manner, arsenical pyrites, although it also contains a large quantity of iron, is unfit for the production of the metal, and the same may be said of many other minerals which contain large quantities of iron

The various ores of iron are composed of, or yield, the oxides of iron in more or less pure condition, and the value of an iron ore is influenced by the nature of the impurities which it contains as well as by the percentage of iron

The ores of iron occur in almost every geological formation, thus magnetic iron are is found in the older rocks, as in the Laurentian beds of North America, and the old slates and gneisses of Sweden, whilst red haematite occurs in beds or pockets in the carboniferous limestone of Cumberland and North Lancashire, and spathic ore and clay iron stone in the coal measures Again, the oolitic rocks furnish large deposits of brown haematite, and the Elba ore is probably a tertiary deposit Still more recent formations of iron ore are seen in the bog ore of Germany and the North of Ireland, whilst " lake ores " are being formed in Scandinavia at the present day Analyses of various ores are given on page 1227

Magnetic Iron Ore, Magnetite, or *Loadstone,* Fe_3O_4—This ore, in the pure state, constitutes the richest ore of iron, containing 72 4 per cent of the metal It occurs in the crystalline and massive state as well as in the form of sand, and is found in large deposits, especially in volcamc rocks, as well as in granite, gneiss, and mica-schist The most important localities of magnetite are Arendal, Dannemora, and other places in Norway, Sweden, and Lapland, the island of Elba, the Ural Mountains, and several localities in the United States, especially near Lake Superior In England, magnetic oxide of iron occurs on Dartinoor, at Brent in South Devon, and at Treskerby in Cornwall, but it cannot be said to be an important English ore In Germany it is found in large quantities at Schmiedeberg, in Silesia, and a few other localities

Frankhnite, $(Fe,Mn)_2O_3(Fe,Zn)O$, occurs in New Jersey, and is first worked for zinc, the residue being used as an iron ore for the production of spiegeleisen [1]

Red Hcematite, or *Specular Iron Ore,* Fe_2—This substance occurs crystalline as specular iron ore, and also in a massive state having a columnar, granular, or botryoidal form, as well as in the earthy condition Haematite occurs in veins as well as in beds and pockets One of its most remarkable localities is the island of Elba, where it occurs finely crystallised between talcous schist and crystalline limestone The Elba mines were worked by the Etruscans, and are still productive A fine haematite occurs in the Huroman rocks on the southern shore of Lake Superior, whilst at Iron Mountain, near St Louis, Missouri, enormous masses of this ore of iron are found On the continent of Europe haematite occurs in Belgium, and deposits of this ore

[1] ***J Iron Steel Inst,* 1894, 46, 416**

are found also in the Devonian formation on the Lahn in Westphalia The chief deposits of haematite in England are those near Ulverston in Lancashire, and on the coast of Cumberland near Whitehaven, the ore here occurs in beds or pockets in the carboniferous limestone, sometimes existing as hard botryoidal masses exhibiting crystalline structure, and sometimes in a soft or compact amorphous condition

Brown Hcematite, or *Limonite,* $Fe_2,O_32Fe(OH)_3 = 2Fe_2,O_33H_2$ —This substance occurs crystallised in rhombic prisms, but is more frequently found either in a fibrous, foliated, and scaly condition, or as a dark brown, remform mass and commonly known as Brown and Yellow Haematite In the massive state this ore occurs in large quantity, and, as it can be readily worked, it has been long employed as a source of iron It is found in the carboniferous limestone as well as in the older rocks, in the Forest of Dean, and at Llantrissant in Glamorganshire in the lower coal measure sandstones At Bilbao, in Spam, it occurs largely in the carboniferous limestone, whilst the newer and earthy brown haematite is found in the oolite and greensand

in Northa

worked in Germany and France, being the ore from which the greater part of the iron made in these countries is derived The bog ores which are worked in the plains of North Germany and Canada and in other places, as well as the peculiar iron ore of the North of Ireland and the Swedish lake ore, belong to this class, and are of the most recent geological formation

Spathic Iron Ore, or *Siderite*—Spathic iron ore consists of ferrous carbonate, $FeCO_3$, invariably mixed with the lsomorphous carbonates of manganese, magnesium, and calcium It possesses a yellowish-brown colour, and occurs often in globular or botryoidal forms having a silky, fibrous structure It is usually found in Devoman rocks, occurring in England at Weardale in

Yorkshire, at Brendon Hill in Somerset, and on Exmoor

Clay Iron-stone, or *Argillaceous Iron Ore,* is a spathic iron containing clay, and is chiefly found in nodules or bands interspersed throughout the clays and shales of the coal measures It is the most important English ore of iron The chief workable British beds occur in Yorkshire, Derbyshire, Staffordshire, Warwickshire, South Wales, and Scotland

The " black band " iron-stone is an important variety of this ore It contains from 20 to 25 per cent of carbonaceous matter, and is found in Lanarkshire, North Staffordshire, and South

Wales The Scottish beds were discovered by Mushet in 1800, but they were not worked until the year 1830 In 1855 the same ore was discovered in Westphalia, and it is worked also in Lower Silesia The coal measures of the Gard and of the Aveyron in France, and those in Pennsylvania and Maryland and other States, also contain large quantities of clay iron-stone The same ore is found in strata in the lias and also in the oolitic and tertiary rocks, the Cleveland iron ore belonging to this last class

537 *Preparation of Ores for Smelting* — In many cases iron ores require no preliminary treatment before smelting other than breaking to a size suitable for the furnace The correct size will depend on the nature of the ore In most cases it is not profitable to concentrate the ore or to separate it from associated impurities before smelting, but in the case of certain magnetites, magnetic separators are used which concentrate the ore and at the same time considerably reduce the amount of phosphorus which occurs as non-magnetic apatite The concentrates, which have necessarily been crushed to a fine state, are afterwards briquetted in suitable presses and hardened by submitting to a high temperature In some cases a binder is introduced before briquetting, the most common being lime, the briquettes in this case being submitted to the action of high pressure steam for hardening

Many methods of sintering, agglomerating or nodulismg fine ores such as the residues of pyrites burners have been recently introduced, some of which are carried out in a similar manner to that used in the blast roasting of galena (p 906)

The carbonate ores, clay iron-stones and brown haematites are submitted to a process of calcination prior to smelting Calcination is carried out in kilns, and during the process water is expelled, carbonic acid driven off, sulphur reduced considerably, coaly matter burnt, and ferrous oxide converted into ferric oxide The operation also results in a more porous material suitable for reduction by the agency of carbon monoxide in the furnace

THE MANUFACTURE OP IRON [1]

538 The application of the blast furnace to the manufacture of iron marks an era in the history of the iron industry, inasmuch as it was by its use that a continuous process of iron manufacture

[1] **For further information on this subject the reader is referred to Percy's admirable " Sketch of the History of Iron," *Iron and Steel,* p 873, and to Turner's *Metallurgy of Iron,* 1 *et sea***

Analyses of the Chief Ores of Iron

	Magnetic Iron Ore	Red Haematite	Brown Haematite		Spathic Iron Ore	Clay Iron-stone	
	Sweden	Ulverston	Forest of Dean	Spam	Erzberg	Lowmoor	**Cleveland**
Ferrous oxide	28 42				55 64	3614	39 92
Ferric oxide	62 06	86 50	90 O5	78 80		145	36O
Manganous oxide		0 21	O O8	0 65	2 80	138	0-95
Alumina			trace	3 50		6 74	7 86
Lime		2 77	O O6	trace	0 92	2 70	7 44
Magnesia	144	146	O 20	trace	177	217	3 82
Alkalis						0 65	0 27
Carbonic acid		2 96				26 57	22 85
Sulphur trioxide		011	trace				
Iron sulphide	007					010	011
Phosphoric oxide		trace	O O9	007		0 34	186
Silica	7 60	6 55	107	5 55		17 37	7-12
Insoluble matter							
Water			9 22	1165	38 35	177	2 97
Organic matter						240	164
Total	99 59	100 56	10O 77	100 22		99 78	100-41

99 48

became possible The discovery of a process by which fusible iron can be prepared appears to have been made, probably accidentally, about the end of the fifteenth century, in Germany, where the Stuckofen had long been in use for manufacturing blooms No description of the process is, however, to be found in the older writers upon metallurgy Thus Agricola, writing in 1556, although he appears to have been acquainted with cast iron, at any rate, the new method must have been at work in this country in 1543, for we find that in that year English cast iron cannons were used The great demand for cast iron, which was all made with charcoal, soon leading to a destruction of our forests, it became necessary, in the first year of the reign of Elizabeth, to endeavour to replace charcoal by some other fuel This was accomplished by the employment of coke instead of charcoal, a practice which was carried out in England by Dudley as early as the first half of the seventeenth century, but which afterwards fell into abeyance It was subsequently revived by Abraham Darby at Colebrookdale, about 1735

The blast furnace consists of a shaft varying in height from 5O to 10O feet, the largest diameter being 14 to 24 feet The essential parts of the furnace are, first, the hearth or crucible, and, second, a shaft or chimney formed of two truncated cones joined at their bases, the upper being termed the " body " and the lower one the " boshes " Fig 189 shows the construction of such a furnace on the scale of 1 180

The shaft, A, Fig 192, is 75 feet high, the diameter at the widest part (the belly or bosh) being 20 feet, whilst at the throat, B, it is 16 feet, and at the hearth, c, 11 feet The shaft is constructed of an outer shell of wrought iron or mild steel plates, supported by means of cast iron columns, B, and is lined with fire-brick In the lining of the boshes, which is exposed to the highest temperature, cooling boxes are inserted These consist of narrow, flat boxes made of bronze, which are built into the brickwork, and are cooled by a current of water, thus preventing the brickwork from becoming too hot The wall of the hearth, which is also hned with fire-brick, is pierced by several openings, the tapping hole, E, by means of which the molten iron is periodically withdrawn, the slag-notch (not shown in the diagram), which is situated at a higher level, and through which the lighter slag is allowed to flow away into trucks or ladles, and, finally, the openings by which the blast of air is introduced through the tuyeres.

JARROW , NO.5 FURNAEE

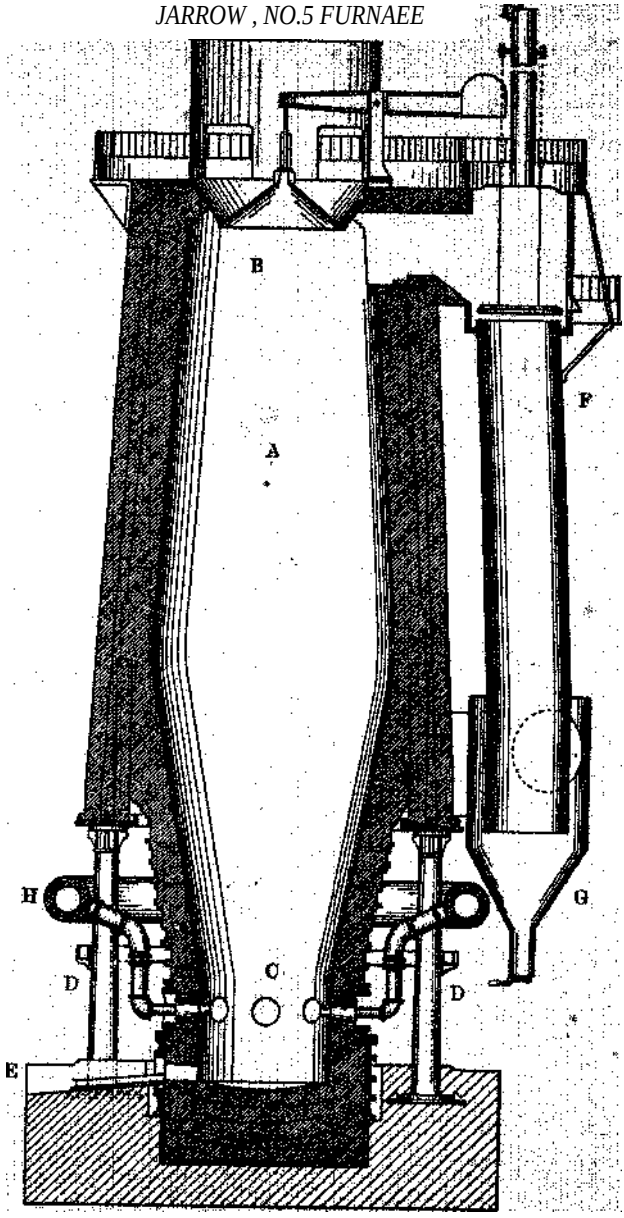

Feet

The throat of the furnace is closed by a contrivance known as the cup and cone arrangement, first introduced by G Parry at the Ebbw Vale works in 1810 It consists of a cast iron funnel, fixed at the mouth of the furnace, and closed by a cast iron cone, suspended at one end of a counterpoised lever, or by means of a cham and wheel The charge is tipped from barrows on to the cone, and is introduced into the furnace by momentarily lowering the latter When the cone is raised against the funnel (as shown in the figure) the throat of the furnace is closed, and the escape of gases into the air prevented, these then pass out of the furnace by the downcast, F, which is provided with a dust-catcher, G, and are, after further cleaning, conveyed through the main to the stoves for heating the blast, to the boilers, or to any other point where the heat produced by their combustion can be made available The gases are also frequently used direct in gas engines [1]

The blast of air is introduced near the bottom of the furnace through tuyere holes, perforating the walls of the hearth The tuyeres are made of wrought iron, cast iron, or bronze, and have a double casing through which water circulates to keep them cool, they vary in number from 8 to 16, according to the size of the furnace, are about 5 to 7 inches in diameter, and are fed from an annular pipe, H, which surrounds the lower part of the furnace, and is connected with the blowing engine

Hot and Cold Blast—Up to the year 1828 air was blown into the furnace at the ordinary atinospheric temperature, but in that year J B Neilson [2] patented a process for heating the air before it passed into the furnace, and this process, inasmuch as it saved from 15 to 25 per cent of the fuel, and was also accompanied by an increased productive power of the furnace, was soon generally adopted, although the cold blast is still employed in some works for the manufacture of certain brands of cold blast iron For the purpose of heating the air, the waste gases from the furnace are burned in a Cowper's or Whitwell's stove or some modification of these, such as the Massick and Crookes, the Ford and Moncur, or the Cowper-Kennedy, all these act on the principle of the Siemens regenerator, and after being heated sufficiently the gas supply is diverted and cold air passed through on its way to the furnace The air is thus introduced at a

[1] **Hubert, Bernhardt, and Westgarth on Blast furnace Gas Engines, *J Iron Steel Inst,* 1906, 71, 16—168**

[2] **Patent No 5701, March 3rd, 1828**

of iron passes into the slag, thus causing waste, whilst if an excess of these bases be used the lining of the furnace is attacked. The fusibility of the slag moreover, determines the temperature which can be reached, and is therefore of great importance, as this has a great effect on the nature of the iron produced The higher the temperature which is required for the reduction of the ore the less fusible must be the slag As soon as the proper proportions between the fuel, ore, and limestone have been ascertained, it is of the greatest importance that these proportions should be strictly adhered to, and for this purpose the charges are regularly weighed or measured and supplied at the top of the furnace, into which they are charged by lowering the cone as already described

On the average about one ton of coke and 8 to 12 cwt of limestone are required for each ton of iron produced, about 5 tons of heated air being used in the operation When the furnace is in regular blast, a constant stream of slag passes out from the slag-hole, the iron collecting in the lower part of the hearth, and being from time to time tapped by piercing a plug of sand and clay by which the tap-hole has been closed Before tapping, moulds are prepared for holding the metal, these are formed in the sand in commumcation with the tap-hole The blast of air is then shut off, and the tap-hole opened by piercing the plug with a long bar of iron The molten iron flows into the channels communicating with the moulds and assumes the form of semi-cylindrical bars or " pigs " umted to one another by one of larger dimensions termed the " sow "

If, owing to some accident to the machinery, a blast furnace is obliged to stand when hot, the operations may be suspended for several months if the throat and tuykre-holes are closed up with sand or clay Should, however, serious damage have occurred, the furnace must be "blown out" This is accomplished by reducing the burden, and thus increasing the temperature for a time so as to remove any aggregations of solid matter which are fusible only at a high temperature Finally only fuel is charged, the contents of the furnace are allowed to burn out, and the last tapping is made at a point as low down in the hearth as possible The life of a blast furnace varies considerably, lasting from five to twelve years, or even for a longer time, according to circumstances

The size and shape of blast furnaces have been and continue

to be very different When charcoal is employed, as was formerly universally the case, and is still so in countries where wood is plentiful, the furnace is usually only from 20 to 30 feet in height The charcoal iron which is thus manufactured in Sweden, Eussia, and America is especially valuable for the preparation of crucible steel Blast furnaces in which the fuel used is either coke, anthracite, or splint coal, are, on the other hand, of much larger dimensions, the exact height and capacity of the furnace being regulated by the nature and amount of iron which has to be produced, as well as by the nature of the ore and fuel to be used

In the year 175O each English blast furnace produced about 3OO tons of pig-iron per annum, whereas a large-size modern furnace yields up to 70,000 tons in the sapne period In the Cleveland district, where the blast furnaces are usually large, the average capacity of those built up to the year 1854 was about 7,000 cubic feet, whilst those built during the years 1870 and 1871 have an average capacity close upon 30,000 cubic feet, in some cases, however, the height rises to 105 feet, and the capacity to 50,000 cubic feet The production of a blast furnace increases, of course, with its size, but not in a direct ratio, thus Lowthian Bell has shown that an old furnace of 1853, having a capacity of 6,000 cubic feet, yielded one ton of iron per twenty-four hours for every 190 cubic feet of space, whilst in the high furnace built in 1870, 380 cubic feet of space are required to produce one ton of iron in the same time hence the maximum limit of economic action may be passed by increased size

The maximum production is at present gained in America where furnaces 75 to 90 feet in height are employed, and the blast is fed at a higher pressure, averaging about 10 lb to the square inch The furnace thus works more rapidly, producing as much as 10O,000 to 150,000 tons per annum [1]

540 *Chemical Changes in the Furnace*—A large number of investigations have been made on the subject of the changes which occur in the blast furnace, but in spite of these our knowledge of them is still far from complete The fuel at the hearth, uniting with the oxygen of the blast, which is insufficient for its complete combustion, burns with formation of carbon monoxide This gas, coming into contact with the constantly descending

[1] **One of the Carnegie Steel Company's furnaces produced 918 tons of pig-Iron in twenty four hours on March 3Oth, 1905**

charges of ore, reduces the ferric oxide to spongy metal, the change being accompanied by a slight evolution of heat

$$Fe_{203} + 3CO = 2Fe + 3CO_2 + 8{,}652 \text{ cal}$$

The zone in which this reduction occurs most rapidly is near the top of the furnace, its exact position depending on the nature of the ore, and its temperature varies from 600-900° When the ores are porous they are more easily permeated by the carbon monoxide, and the reduction takes place more quickly than when denser ores are employed The reduction in this upper zone is never quite complete, because metallic iron is itself oxidised when heated either in carbon dioxide or in carbon monoxide, free carbon being deposited in the latter case As the spongy iron, still containing a small amount of oxide, descends, it arrives at the hotter parts of the furnace, the temperature of which reaches 1000° in the belly or widest section At this point the reduction of the metal is completed by the solid carbon present, some of which is supplied by the dissociation of carbon monoxide, which takes place at a high temperature, with formation of carbon dioxide and free carbon [1]

Below this zone is the hottest part of the furnace, and the materials, which were formerly in a pasty state, melt completely, running down into the hearth, where the lighter slag floats on the surface of the heavier iron, and thus protects it from the oxidising action of the blast Other important changes in the composition of the iron occur as the metal passes down the furnace In the first place, the spongy iron, in passing through the zone of reduction, takes up sulphur from the ores and fuel, and secondly, when the temperature reaches the highest point in the zone of carbunsation, the phosphates contained in the ore are reduced, and the phosphorus is taken up by the iron At a still higher temperature the fused iron in the presence of carbon reduces the silicates to silicon, this, with manganese and other metals, remains as a constituent of the iron

It will thus be seen that three mam zones may be distinguished in the furnace In the *first* and highest, the greater part of the reduction occurs, whilst the partially reduced mass, in passing which is necessary for the reactions occurring in the *third* and last zone These comprise the complete reduction of the ore,

[1] **Cadletet, *Compt rend*, 1866, 62, 891**

the carburisation and fusion of the metal, and its impregnation with silicon, phosphorus, etc These various zones are, of course, not well defined, but pass gradually one into the other

541 *Gases of the Blast Furnace*—The composition of the blast furnace gases naturally varies in the different zones and under different conditions of burden The relation of the carbon dioxide to carbon monoxide present in the blast furnace gases is of great interest The monoxide is reconverted during the reaction into the dioxide, and this either remains unaltered or is reconverted by the iron into the monoxide, according to the temperature which prevails in the upper part of the furnace Carbon dioxide also is formed near the top of the furnace by the calcination of the limestone, and this is then partly reduced to the monoxide The researches of Lowthian Bell and von Tunner have shown that the relation between the volumes of the escaping carbon dioxide and carbon monoxide, under otherwise similar conditions, serves as an excellent criterion of the economical working of the blast furnace, and the limit of economical working is reached when from 40 to 6O volumes of carbon dioxide are present for 10O volumes of carbon monoxide The furnace gases contain, in addition, nitrogen of the air, hydrogen from the reduction of aqueous vapour, hydrocarbons, and, frequently, traces of cyanogen or hydrogen cyamde

Many analyses of the blast furnace gases, collected at various heights above the tuyeres and in varying circumstances, have been made The following figures give an idea of the varying nature of the composition of these gases

Wood Charcoal Furnace at Veckerhagen, near Cassd Height, 5 97 m (Bunsen)

epth in metres below the mouth—O 86	**2 59**	**4 32**
Nitrogen	62 34	63 89	64 58
Carbon dioxide	8 77	3 6O	5 97
Carbon monoxide	24 20	29 27	26 51
Methane	3 36	107	188
Hydrogen	133	217	106
	100 00	100 00	100 00

Hot-blast Coke Furnace at Seraing in Belgium Height, 14 43 m "(Ebelmen)

Depth in metres below the mouth—	0 30	3 05	13 71
Nitrogen	57 06	6167	54 63
Carbon dioxide	1139	108	—
Carbon monoxide	28 61	35 20	45 05
Methane	O 20	O 33	O O7
Hydrogen	2 74	172	O 25
	100 00	100 00	100 00

Cold-blast Coal Furnace at Alfreton Height 11 in (Bunsen and Playfair)

Depth in metres below the mouth—	1 52	5 18	10 36
Nitrogen	55 35	55 49	58 05
Carbon dioxide	7 77	12 43	
Carbon monoxide	25 97	18 77	37 43
Methane	3 75	4 31	—
Hydrogen	6 73	7 62	318
Ethylene	O 43	138	—
Cyanogen	—	—	134
	100 00	100 00	100 00

When coal is employed in the blast furnace instead of coke the waste gases are passed through coolers and scrubbers to remove the valuable tar and ammonia which they contain, and are then passed on to the Cowper stoves, etc

During the war of 1914-1918, considerable quantities of potash salts were recovered from the waste gases and flue dust of blast furnaces and additions of common salt were made to the charge in order to displace the potash contained in the materials

An interesting substance sometimes found in the blast furnace is a cyano-nitride of titanium (p 847), and, in addition to this, " kish," or graphite, as well as silicates and the oxides of other metals, occur as solid deposits in the furnace

The slags produced during the smelting of iron ores in blast furnaces vary considerably in appearance, properties, and composition, and are produced by the combination of the gangue and flux The colour and appearance of the slag afford a valuable

indication of the working of the furnace With an excess of lime, as is used in the manufacture of open-gramed grey iron, the slag is difficultly fusible, and when solid is white and of low specific gravity For a finer grained grey iron, a less basic slag is required, and this is harder, more compact, and usually of a grey colour with a tinge of blue or green With a white iron, the slag produced is dark in colour and has a higher specific gravity The chemical composition of the slags varies widely with different mixtures, and consists chiefly of silica, lime, and alumina The following analyses are given to indicate the wide differences which may be found in slags from different sources slag A was obtained from a furnace making grey iron, and slag B from a furnace making white iron

	A	B
Silica	29 81	42 23
Alumina	19 94	9 84
Lime 40	31	3713
Magnesia	2 95	132
Manganous oxide	trace	0 97
Ferrous oxide	trace	2 60
Calcium sulphide	6 92	4 32

VARIETIES OF CAST IRON

542 Molten iron usually contains 2 2-4 5 per cent of carbon, and when the iron is cooled this is either entirely, or only partly, retained in combination by the metal, whilst the remainder separates out in the form of graphite, its behaviour being determined by the composition of the mass, the conditions of the process of manufacture, and the mode of cooling When the greater part of the carbon separates in the form of graphite, the resulting metal is known as *grey iron,* whilst when the whole or the greater part of it is retained "m combination by the iron the metal is known as *white iron* Between these are several intermediate conditions classed together as *mottled iron* All these names are derived from the appearance of a freshly fractured surface pf the metal, the mottling characteristic of the last class being caused by the occurrence of spots of grey in a matrix of white iron

When white iron is dissolved in hydrochloric or sulphuric acid, various hydrocarbons are formed at the expense of the combined carbon which it contains, and these impart a peculiar

and disagreeable odour to the hydrogen which is evolved On the other hand, when grey iron is treated with acids the graphite separates out in the form of black, insoluble scales. This fact was known to Bergman, whist Guyton de Morveau proved that cast iron is formed when wrought iron is ignited with diamond powder, and Karsten showed that cast iron contains carbon both in the combined state and free in the form of graphite, this latter remaining behind when the iron is dissolved in an acid The graphite can also be mechanically separated from the iron by sieving (Snelus)

Both the total amount of carbon present and the mode in which it occurs depend very largely on the other substances contained in the crude iron, whilst these, of course, are determined by the conditions of the manufacture Thus chromium and manganese favour the presence of a large amount of carbon, which is retained in combination when the iron cools, whereas silicon diminishes both the total amount of carbon present and the proportion of it which remains in the combined form The way in which the metal is cooled also has a very important influence on the mode of occurrence of the carbon, slow cooling promoting the crystallisation of graphite and the consequent production of grey iron, whilst sudden cooling or chilhng favours the production of the more homogeneous white iron It is therefore possible, within certain limits, to obtain either grey or white iron from a given mass of the fused metal, simply by altering the conditions of cooling

The following analyses of Cleveland pig[1] show the gradual variation in composition from grey through mottled to white iron

	Grey	Mottled	White
Carbon, Graphitic	3 20	184	
„ Combined	trace	125	3 O5
Silicon	3 5O	101	O 67
Sulphur	O O5	O 32	O 40
Phosphorus	176	157	16O
Manganese	O 68	O 62	O 42

White Iron is formed when the furnace is working on a heavy

[1] **Quoted by Turner, *Metallurgy of Iron,* 3rd ed , p 28O**

burden or at a comparatively low temperature It is very hard and brittle, and when fractured presents a very close grain. It melts at a lower temperature than grey iron, is less liquid, and after cooling is often found to be vesicular or honeycombed from the evolution of gas given off as the metal cools

Grey Iron, on the other hand, is produced at a higher temperature, has an open-gramed fracture, melts to a thinner liquid, and is better adapted for fine castings than white iron

Mottled Iron is intermediate in its properties between white and grey iron

Spiegel or *Specular Iron* is a variety of white iron in which manganese is present as an essential constituent, and contains a large proportion of carbon, varying from 3 5-6 per cent, practically all of which is in the combined form It is extremely hard and brittle, and has a specific gravity of 7 6-7 7 When the alloy contains more than about 25 per cent of manganese it attains a granular structure and is termed *ferromanganese,* which commonly contains 8O per cent of manganese These two materials are largely used in the manufacture of steel by the Bessemer and open hearth processes as deoxidisers and recarburisers

Some analyses of pig-irons are given on p 1241

In foundry practice, castings of grey iron are made by pouring the molten metal into suitably prepared sand or loam moulds The molten iron is obtained in the foundry by melting a mixture of several grades of pig-iron together with a quantity of foundry and other scrap in a cupola or small blast furnace, using coke as a fuel, and with the addition of a little limestone to flux off the ash of the coke and the silica adhering to the pig-iron used The castings thus produced are always somewhat brittle, and

in the man

less brittle, the castings are first produced in white iron and then iron packed in iron ore and submitted to a long annealing process, during which the combined carbon is converted into finely graphitic or temper carbon and is also partially removed by oxidation from the surface

MANUFACTURE OF WROUGHT OR MALLEABLE IRON

543 Malleable iron can be produced, either by the direct reduction of the ore in such circumstances that it cannot take up sufficient carbon, etc, to convert it into cast iron, or

indirectly from cast iron by the removal of carbon and some of the other constituents

(I) THE DIRECT KEDUCTION OF MALLEABLE IRON FROM THE ORES

544 *Iron Furnaces'*—The simplest form of the iron furnace is that used on the west coast of India, as well as in the Deccan and Carnatic, and amongst the hill-tribes The low-caste Hindus who work in iron wander from place to place and build up their simple apparatus where they find fuel and ore, this latter consisting generally of magnetic oxide or brown haematite The furnaces are built on the ground and constructed in the form of a small round shaft or chimney At the lower part there are two openings, one of which serves for the blast and the other for the exit of the slag as well as for the extraction of the bloom of iron The bellows are usually made from a goat's skin or a buffalo hide, furmshed with bamboo tubes As soon as the furnace is warmed with charcoal, layers of the broken ore and charcoal are put in the shaft, and after from 4 to 6 hours a porous bloom of iron is obtained, varying in weight from 5 to 30 lb , and this is then worked under the haminer Throughout Central India and in the north-east provinces the manufacture of iron is somewhat further advanced, the furnaces being larger and of a similar character to those which have been or are still in use in various parts of Europe In many localities in England furnaces were erected on high ground, so as to take advantage of the prevailing wind to increase the draught The word "haminer," which frequently occurs in place-names in the south of England, usually marks the location of one of these old smelting works with its accompanying forge

(II) PRODUCTION OF MALLEABLE IRON FROM PIG-IRON

545 The change which occurs in the conversion of pig-iron into malleable iron consists essentially in the removal of a large proportion of the carbon, silicon, sulphur, phosphorus, and manganese from the former, and is effected by oxidation in the presence of some substance which can unite and form a fusible slag with the silica and phosphoric oxide produced As the removal of carbon, etc, proceeds, the melting point of

Analyses of Pig-irons

		Graphite	Com-bined Carbon	Silicon	Sulphur	Phos-phorus	Man-ganese	Chrom ium	**Iron**	
White	Durham		410	0 23	0 03	0 07	2 37			
	Alabama	010	2 92	0 95	0 30	0 64	010			
	South Wales		2 40	0.80	0 70	150	0 20			
	Staffordshire	0 20	200	0 71	019	0 47	0 50			
	Schwechat		2 83	0 52	0 08	018	2 67			
Mottled	Dsenburg	3 77	0 53	0 43	015	trace	143			
	Cleveland	2 28	0 72	135	0 03	117				
	Forest of Dean	2 37	131	040	0 06	0 07	0 **11**			
Grey	Forest of Dean	390	0 39	107	0 01	0 07	0 22			
	Scotland	4 40	trace	2 68	0 08	010				
	Staffordshire	3 30	0 40	188	0 02	0 71	040			
Spiegel	Dannemora		4 81	018	trace	012	199		**92 90**	
Spiegel	Siegen		5 04	0 41	008		5 75		**88 56**	
Ferromanganese	Prieger		715	0 87	0 02	0 07	7275		**1914**	
Ferrosilicon	Darwen	120	0 23	14 00	008	0 08	195			
Ferrochrome	Darwen		10 05	0 40			0 **42**	**6310**	25 38	
Ferrotungsten			2 87	0 85	010	0 05	**0** 47		**43 20**	**51.74**

the iron rises, so that at a certain stage the metal begins to solidify It is then worked into a porous ball or bloom, and haminered in order forcibly to squeeze out the slag which is contained in the pores

The Puddling Process—In 1784 Henry Cort introduced the puddling process, the essential feature of which is the use of a reverberatory furnace instead of an open-hearth furnace formerly used for the oxidation of the constituents of the cast iron In the older form of the process the oxidation was effected chiefly by the oxygen of the air The process was applicable only to white iron, and thence necessitated a preliminary *refining* of the metal when grey iron was employed The metal was charged along with a sufficient quantity of coke into an open hearth furnace, and there melted and exposed to the blast from six tuyeres When the oxidation had proceeded far enough to reduce the percentage of sihcon to the requisite point, the tap-hole was opened, the iron allowed to run into moulds, and the cast iron cooled by water The refined iron is highly crystalline, white, and brittle, the carbon being present in the combined state The following analyses by Abel of pig-iron, before and after refining, from Konigshutte in Silesia, give the different percentages of silicon, phosphorus, and sulphur, and show that in this process the silicon is largely eliminated, whilst sulphur and phosphorus are less affected, the total amount of carbon, moreover, is not much altered

	Pig iron	Refined Iron
Silicon	4 66	0 62
Phosphorus	0 56	0 52
Sulphur	004 0	03

The slag obtained in this process, known as *refinery-slag*, forms, when cold, a dark, crystalline mass, with an almost metallic lustre It consists chiefly of ferrous silicate, Fe_2SiO_4, in which, however, a part of the iron may be replaced by manganese, calcium, magnesium, etc Not infrequently, distinct crystals of olivine, $(Mg,Fe)_2SiO_4$, have been found

The refined iron was then melted on the bed of a reverberatory furnace and stirred by means of iron instruments, so as to expose it thoroughly to the air As soon as the oxidation had been carried out to a sufficient extent, the metal was removed and treated as already described

The Modern Puddling Process — In England and other countries

where grey pig is largely made, the preliminary process of refining has been done away with, and the pig-iron is at once submitted to the operation of puddling without previous refining, the process being termed " pig-boihng "

An ordinary puddling furnace is shown in elevation, section, and plan, in Figs 193, 194, 195 The bed or hearth of the furnace *(h)* is supported by a cast iron plate, at each end of the hearth, which is usually 6 feet long, is a wall built of fire-brick, one end being called the fire-bridge (6), and the other the flue-bridge *(d)* The bottom and side plates of the hearth are lined with a coating of tap-cinder, which is heated until it becomes soft, and is then spread evenly over the floor of the hearth Above this is placed a coating or " fettling " of ferric oxide of about 1| inches in thickness, and this is renewed from time to time as it wears away Neither of these coatings is shown in the figures The fire-bars, which are sometimes placed in a slant should be from one-half to one-third of that of the bed A powerful draught is obtained by means of a brick chimney, the top of which is furnished with a damper, which can be opened and shut at will by the workman by means of a handle, and thus the passage of air through the furnace regulated In some furnaces gas is employed with a Siemens regenerator, oil and natural gas have also been used as a source of heat

The distinguishing feature of the modern process consists in the fact that the iron is fused in contact with the oxides of iron which are present in the fettling, and with a fusible slag which is added to each charge In this way the oxidation of the carbon, etc , is carried out mainly at the expense of the oxygen of the fettling, and since an equivalent amount of metallic iron is thus produced the loss is rendered much smaller The time required for the oxidation is also greatly lessened, the whole operation lasting only two hours As soon as the charge has been completely melted, it is well stirred, so that it is thoroughly exposed to the action of the fettling and of the air It is then allowed to cool somewhat, and well mixed, whilst in a pasty state, with the oxide of iron present This brings about the oxidation of the carbon with formation of carbon monoxide, probably thus

$$Fe_2 + 3C = 2Fe + 3CO,$$

and the escape of this gas causes the whole mass to swell up or

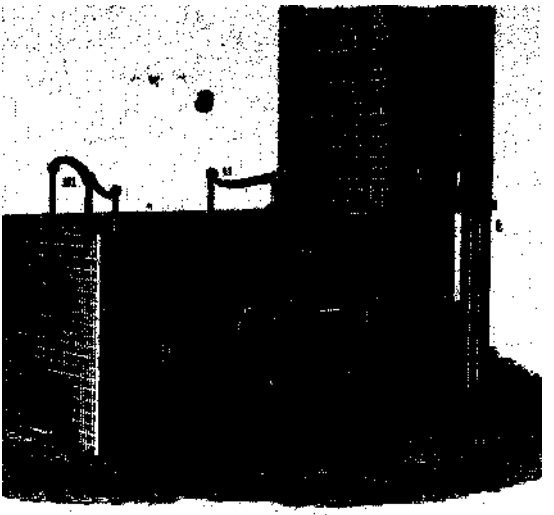

Fig. 193.

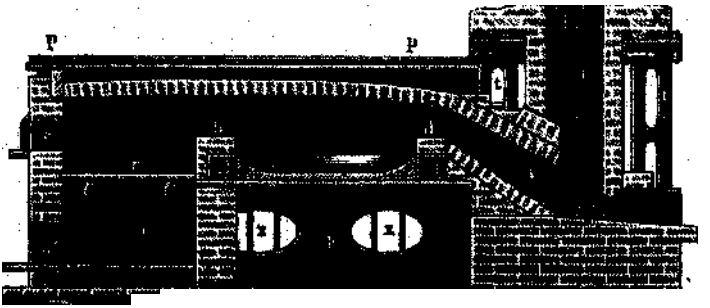

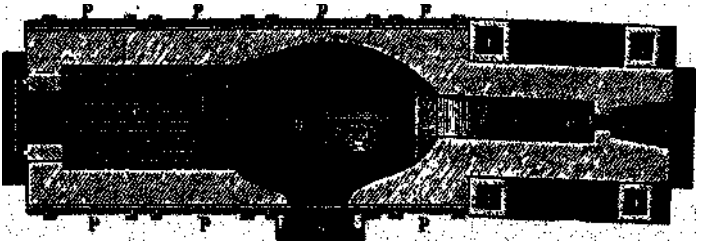

" boil " The iron then gradually subsides a little into a porous mass, or as it is termed, " comes to nature," and is worked into balls which are removed from the furnace and haminered to get rid of the fusible slag and to weld the porous iron into a homogeneous mass, this process being completed by passing the metal through the rolling mill It is to this treatment that the characteristic fibrous structure of the wrought iron is due

Mechanical Puddling Process—In order to avoid the heavy manual labour necessary in the ordinary puddling processes, revolving puddling furnaces have been invented by Danks, Roe,[1] and others These furnaces are in use to a small extent, but have not been generally adopted

546 The following analyses made by J G Snelus give an idea of the consecutive chemical changes which take place in the passage from cast to wrought iron *(a)* is the mottled Cleveland iron which was puddled in the Danks revolving furnace, *(b)* a portion taken out when meljfced, the composition ten minutes later is shown by (c), after a lapse of twenty minutes by analyiss *(d)*, the composition of the bloom is shown in (e), and of the puddled bar in (/), C C stands for combined carbon, and G C for graphite

	Fe	CC	GC	Si	P	S	Mn
a	93 19	145	138	124	149	011	0 63
b	95 03	2 83	—	0 82	0 91	0 09	—
c	96 46	2 80		0 20	0 58	—	—
d	98 09	117	—	0 05	0 52	—	—
e	98 40	0 15	—	0 09	0 45	—	—
f	9713	0 15	—	014	0 47	0 04	014

It will thus be seen that the silicon is first burned out along with most of the phosphorus, whilst the carbon afterwards disappears

A large proportion of the phosphorus contained in the pig is found in the slag or *tap-cinder* as phosphide and phosphate, the sulphur is left in the cinder as iron sulphide The tap-cinder is rich in iron, and is employed, after roasting in heaps, as fettling, or for the manufacture of common iron The following analyses of tap-cinder give an idea of its composition

SiO_2	FeO	MnO	Fe_2O_3	Al_2O_3	CaO	MgO	P_2O_5	S	Analyst
7 71	66 32	129	8 27	163	3 91	O 34	8 O7	1 78	**Riley**
1176	58 67	O 57	17 OO	2 84	2 88	O 29	4 27	3 11	
29 6O	48 43	113	17 11	128	O 47	O 35	134	161	**Percy**

[1] *J Iron Steel Inst,* 1906, 71, 264

Stahl considered iron to be an impure metal containing earthy materials, whilst steel was the pure metal saturated with phlogiston Similar views were held by the later chemists Bergman was the first to distinguish chemically between wrought iron, steel, and cast iron He found that the first when dissolved in acids yielded the largest quantity of inflammable air, steel somewhat less, whilst cast iron gave the smallest quantity, hence he concluded that steel contained less phlogiston than wrought iron He also showed that cast iron contained more graphite than steel, and this more than wrought iron, and hence he concluded that cast iron was converted into steel by loss of graphite and by absorption of phlogiston, whilst he supposed that when steel was produced from wrought iron the opposite reactions occurred Rinmann in 1782 developed similar views, and he especially insisted that malleable iron was a perfect metal, and was converted into steel by absorption of phlogiston, but that this phlogiston was not the substance usually thus designated, but plumbago In 1786 Monge, Vandermonde, and Berthollet published a research proving that the difference between the various kinds of iron is determined mainly by the variation in the amount of carbon which they contain, but the many doubtful points which remained were cleared up only by the comprehensive researches of Karsten and Sefstrom [1]

As already explained (p 1223), the amount of carbon present has now been found not to provide a convement distinction between malleable iron and steel, since specimens of these may contain the same amount of carbon and yet possess very different properties, owing to different internal structures

Steel can tie made in a very large number of different ways, the principles of which may be roughly summarised thus .

A Directly from the ore
B From malleable iron
  1 By the direct addition of carbon, accompamed or followed by fusion
  2 By fusion accompamed by the addition of more highly carburised metal
c From pig-iron
  1 By the removal of carbon and other impurities
  2 By the addition of a less highly carburised metal, such as malleable iron

[1] **Percy,** ***Iron and Steel,*** **p 116**

Many of the processes actually adopted involve two or more of these methods, and the number of different processes now employed is very large, but only two or three of the most important and typical methods are here described

549 *The Cementation Process* —Seventy years ago the only method by which steel could be made was the decarbunsation of the cast iron in the puddling furnace, and the subsequent re-carbunsation of the puddled bar by the cementation process The product was then either fused in a crucible, yielding cast steel, or drawn out under the hammer, whereby tilt steel or shear steel was obtained

The cementation method of preparing cast steel is mentioned

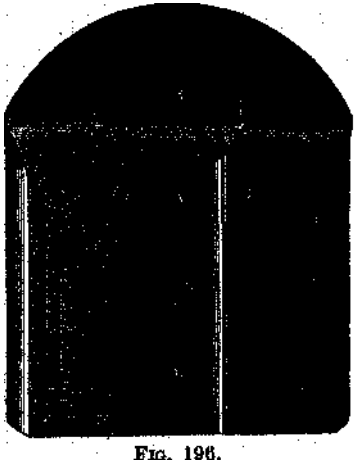

FIG. 196.

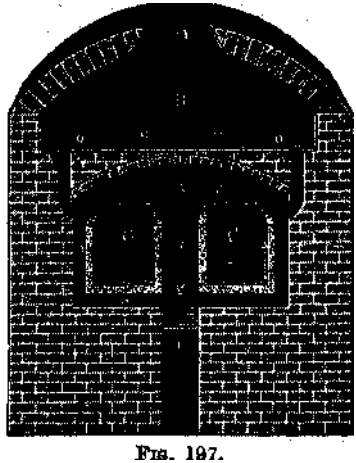

FIG. 197.

by Agncola in his *Le Re Metalhca,* whilst that for haminered or tilt steel was first described by Reaumur in 1722

In the manufacture of steel by the cementation process carbon is added to the otherwise pure wrought iron This is earned on in the furnace shown in Figs 196 and 197 Into the furnace are built two square boxes or " converting pots," c, c, Fig 197, of infusible fire-brick, and in these are placed the bars of non which are to be converted into steel The flames from a fire placed in the hearth *(g)* play roand these boxes The iron which has to be converted into steel is usually in the form of straight bars about 3 inches broad, and O 75 inch thick, which are somewhat shorter than the converting pot in which they are placed The interstices between the bars when piled in the pot are filled up with powdered charcoal, technically termed " cementing

powder," a thick layer of the charcoal being placed on the top of the bars, and the whole mass plastered over with grinders' waste The total weight of iron contained in each box is from five to six tons The fire is gradually raised to a full red heat, 10OO-110O°, and is maintained at this point for about seven to ten days, according to the quality of steel which is needed Spring steel requires seven days, shear steel eight days, and steel for welding from mne to ten days During the operation trial bais are removed by the openings (c) from the ends of the chests, and when it is found that the bar-iron has been completely converted mto steel the furnace is allowed to cool, and after several days the charge is removed The steel bars thus obtained retain the form of the original iron, but in physical properties they differ considerably from the original Thus the coloured surface of the fractured bar of steel has no longer the bluish tint of malleable iron, but has acquired a reddish tint, not very different from that of bismuth, and the texture has become distinctly crystalline The steel is also much more fusible than malleable iron, a varying amount of carbon having been taken up

The following is an analysis by David Forbes of cementation steel made at Sheffield from Swedish iron

Combined Carbon	Graphitic Carbon	Silicon	Sulphur	Phosphorus	Manganese
0 627	0 102	0 030	0 005	0 000	0 120

A remarkable alteration of the surface is likewise noticed in the passage of wrought iron into steel, it being covered with blisters, and hence it is termed *blister steel* The formation of these blisters is undoubtedly due to the production of gas withm the bar, the gas resulting from the combination of a part of the carbon with oxygen derived from the particles of oxide of iron contained in the slag in the interior of the bar The bars are finally cut up, sorted according to their quality as indicated by the fracture, melted in crucibles, and finally cast in ingots

Various hypotheses have been proposed to account for the phenomena observed in the cementation process According to one view, the carbon is absorbed from the exterior and passes to the interior of the bar partly from the sohd carbon, partly from the carbon monoxide formed by its partial combustion, and partly from the hydrocarbons derived from the hydrogen contained in the charcoal The probability of the view that the carbon monoxide is the active agent is strengthened by the

the pure Swedish charcoal-pig was used, indeed, the first real success in working the process was achieved with this iron at the Hogbo Ironworks, at Sanviken, and this was followed by the successful use of grey iron made from the Ulverston haematite, and now technically known as *Bessemer-pig* Other difficulties then arose such as the too complete oxidation, when the whole of the carbon is burnt out, a mass of pasty wrought iron being produced instead of liquid steel This was overcome by the important suggestion made by Mushet[1] of the addition of spiegel at the end of the operation in such quantity as is necessary for the conversion of the whole of the wrought iron into steel

The oxidation is carried on in an egg-shaped vessel, termed the converter (Figs 198-9), made of wrought iron plates bolted firmly together and lined with an infusible siliceous rock termed gamster, which is ground, moistened with water, and applied to the interior The lower portion is an interchangeable bottom, consisting of a shallow lower section of the vessel with tuyere-box or wind-box and tuyeres, together with the necessary arrangements for fixing these in their places This bottom is attached to the vessel in such a manner that the narrow space between it and the vessel lining may be ramined with plastic gamster by men working outside the vessel, and this joint can be easily made at once upon pulling away the old bottom This arrangement is of great advantage, inasmuch as by its use the number of blows per diem can be considerably increased The pig-iron, which must be free from phosphorus and sulphur, is first melted in a cupola, and from five to twelve tons of this are run into the converter, either directly from the cupola or from an intermediate ladle, the mouth of the converter being lowered to the proper angle to receive the molten metal The converter is then gradually raised to the vertical position, at the same time a moderate blast of air is forced through the tuyeres by means of the pipes L, N, and D, the pressure of the blast being afterwards raised to from eighteen to twenty pounds per square inch

The combustion of the silicon, manganese, and carbon, as also of a portion of the iron, then begins, and the temperature rises to a point sufficiently high to keep the metal liquid In the first part of the blow the graphite is converted into combined carbon, and a highly siliceous slag is formed, a portion of the silica being derived from the lining When the first period is complete, an orange-yellow flame edged with blue appears at the mouth of

[1] **Brit Patent, Sept 22, 1856**

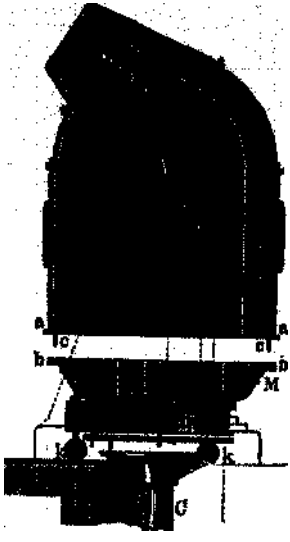

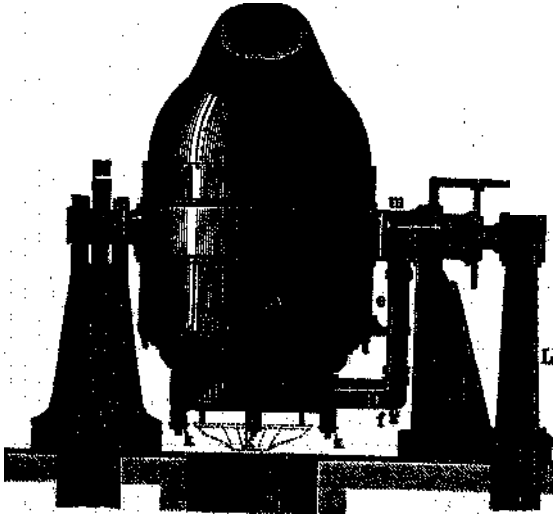

'Oku?

the converter, and the second period, termed the "boil," then begins In this, the slag containing oxide of iron oxidises the carbon, with formation of carbon monoxide which escapes throughout the mass, giving to it the appearance of a boiling liquid During this period particles of the slag and molten iron are thrown out from the mouth of the converter, and a very brightly luminous, flickering flame makes its appearance, accompanied by a rapid stream of sparks due to the combustion of the particles of iron After the lapse of from six to eight minutes the intensity of the action diminishes, the shower of sparks ceases, and suddenly the flame disappears and is said to drop The whole of the carbon has now been oxidised, and, if the blast be left on, the combustion is continued at the expense of a portion of the iron Hence, the force of the blast is now lessened, the converter inclined, then the blast stopped, and the requisite amount of spiegel or ferromanganese introduced to bring the steel to the requisite degree of carburisation The blast is then turned on again for a few seconds, or the mixture is simply allowed to stand for a short time, and the whole mass poured out into the ladle After standing for a few minutes in the ladle, the fluid steel is cast into ingot moulds, and the cast steel worked up under *t\e* haminer and in the rolling mill The whole process lasts from twenty to thirty minutes, and in this time from five to twelve tons of iron are converted into steel

552 The chemical changes which the pig iron undergoes in the various stages of the Bessemer process, as well as the composition of the slags obtained, are tabulated below

(a) Composition of the pig-iron used (3,517 kilos) *(b)* After the first period of twenty-eight minutes' blow *(c)* After the second period of seven minutes' blow *(d)* After the third period of three minutes' blow *(e)* Finished steel (3,O58 kilos) after the addition of 168 kilos of spiegel

Composition of Bessemer Metal

	a	6	c	*d*	e
Graphite	**3 18O**				
Combined carbon	**O 75O**	**2 465**	**O 909**	**O O87**	**O 234**
Silicon	**196O**	**O 443**	**O 112**	**O O28**	**O O33**
Phosphorus	**O O40**	**O O40**	**O O45**	**O O45**	**O O44**
Sulphur	**O O18**	**trace**	**trace**	**trace**	**trace**
Manganese	**3 46O**	**1645**	**O 429**	**O 113**	**O 139**
Copper	**O O85**	**O O91**	**O O95**	**O 120**	**O 105**
Iron	**90 5O7**	**95 316**	**98 37O**	**99 6O7**	**99 445**

Composition of Bessemer Slag

	a	*b*	*c*	*d*	*e*
Silica	40 95	46 78	5175	46 75	47 25
Alumina	8 7O	4 65	2 98	2 8O	3 45
Ferrous oxide	O6O	6 78	55O	16 86	15 43
Manganous oxide	2 18	37 00	37 90	32 23	3189
Lime	3O 36	2 98	176	119	123
Magnesia	16 32	153	O 45	O 52	O 61
Potash	O 18	trace	trace	trace	trace
Soda	O 14	trace	trace	trace	trace
Sulphur	O 34	O O4	trace	trace	trace
Phosphorus	O O1	O O3	O O2	O O1	O O1

Converter Gases—Snelus has investigated the composition of the gases issuing from the converter When the charge lasted eighteen minutes he found the following results on analysis of the gases drawn out at the times after the cominencement of the blow given in minutes in the first horizontal line

		2	4	6	10	12	14
CO_2		10 71	8 59	8 20	3 58	2 3O	13
O		O 92					
CO		—	3 95	4 52	19 59	29 3O	31 11
H	}	88 37	O 88	2 00	2 00	2 16	2 00
N	}		86 58	85 28	74 83	66 24	65 55

Elimination of Phosphorus—It was at first supposed that the non-elimination of phosphorus in the Bessemer process was due to the high temperature, and that if the process could be conducted at a lower temperature as in puddlmg, all the phosphorus would be found in the slag Messrs Thomas and Gilchrist[1] and Snelus have, however, proved that it is possible to eliminate phosphorus completely in the Bessemer process by using a basic lining of calcined dolomite for the converter instead of the usual siliceous one, phosphate of lime and magnesia being produced This is known as the " basic " process, and is now largely in use in the case of phosphoric pig, it constitutes one of the most important advances in metallurgy, since it renders possible the direct production of steel from ordinary pig-iron, such as Cleveland pig, which contains comparatively large quantities of phosphorus

The process is carried out in the main like the ordinary Bessemer process, but differs from it in one or two points A certain amount of lime is placed in the converter and heated by the combustion of a small quantity of coke before the molten

[1] *J Iron Stedlnst,* 1879,120

pig is run in The blow is then conducted in the ordinary way, but when the flame has dropped the blow is continued, and it is in this " after blow " that the phosphorus is chiefly removed This is well shown in the following table, which gives the results of a " blow " by the basic process *(a)* gives the composition of the Cleveland pig, *(b)* after five minutes' blow, (c) after ten minutes, *(d)* after fifteen minutes, *(e)* after eighteen minutes As soon as the phosphorus has been removed, a point which is indicated by the appearance of the fracture of a small sample of the metal, the process is concluded in the usual way by the addition of spiegel or ferromanganese The slag, which contains the whole of the phosphorus in the form of phosphate, is ground and sold as a valuable manure

	a	*b*	c	*d*	*e*
Carbon	3 5O	3 55	2 35	O O7	trace
Silicon	1 15	O5O	O O9	trace	OOO
Manganese	0 71	O 56	O 27	O 12	trace
Phosphorus	157	1 6O	143	122	O O8
Sulphur	O 16	O 14	O 13	O 12	O 10

Application of the Spectroscope to the Examination of the Bessemer Flame — It has already been stated that the point at which the flame drops is that at which it is found by practice to be necessary to stop the blast, but it is not always easy to hit this point with accuracy, and if the blow be stopped a few seconds too soon, or carried on for a few seconds too long the quality of the resulting steel suffers The application of the spectroscope to the determination of this point was made by Roscoe in 1863,[1] and has since been investigated by Watts, Lielegg, Snelus, Hartley,[2] and others

The spectroscope is more extensively used on the Contment than in this country for the examination of converter flames,[3] and in Belgian and Swedish foundries is used to control the blow in operations in which the whole of the carbon is not eliminated "but the air blast is stopped while the metal still contains 0 4 to 0 6 per cent of carbon At the beginning of the blow the spectrum is continuous and indefinite With the faint appearance of the flame the characteristic yellow line of sodium is seen, and for a short period this line is very faint and appears in flashes As the flame and temperature rise, the spectrum lines become

[1] *Proc Manch Phil Soc* , 1862-3, 3, 57
[2] *J Iron Steel Inst*, 1895, 48, 95, also 1901, 60, 197
Campbell *The Engineer*, 1921,**132,**137

more complex, the line spectrum of thallium and lithium and the banded spectrum of many other metals may be observed, but they are not of any particular value for the control of the blow The principal lines to be noted are those of carbon, which appear bright green They are faint at first, but gradually as the flame rises they become brighter and more distinct, until, with the falling of the flame, they diminish in number and fade completely away with the final drop of the flame

553 *Open-hearth Processes*—In these methods a reverberatory furnace is used, such as that shown in section in Fig 200, which represents a 12-ton Siemens regenerative steel furnace The furnace works on the regenerative system exactly as described on page 596, *cc'* and D D' are the chambers used for absorbing the waste heat of the furnace and for heating the gas and air, *k* is the hearth of the furnace, made of infusible siliceous material

in the acid being used when the pig-iron contains phosphorus

In the simple Siemens process a charge of pig-iron, together with scrap iron or steel when available, is put on the hearth of the furnace and melted When the charge is fused, iron ore in the form of haematite is added from time to time A violent reaction takes place on the addition of the ore, slag first being formed by the oxidation of the silicon present to silica, which combines with ferrous oxide from the ore

After the silicon has been oxidised and removed, the metal " comes to the boil/' the carbon present being oxidised by the basic ferrous slag, carbon monoxide being evolved and a certain amount of iron liberated The end of the process is determined by the quality of steel required, and is tested by taking out a small sample and judging by the fracture obtained

When the process is finished, the metal is tapped and a small amount of ferromanganese added to deoxidise and re-carbunse it

Instead of charging the furnace with pig-iron, liquid metal[1] is sometimes used direct from the blast furnaces or from large gas-fired containers or metal mixers, as this considerably shortens the time necessary to work off a charge.

In the basic open-hearth process, employed for making steel from phosphoric pig-irons, a certain amount of lime and limestone is charged in with the pig, ore, and scrap; further quantities

[1] **" The Use of Fluid Metal in the Open hearth Furnace," Riley, *J Iron Steel Inst.*, 1900, 57, 22**

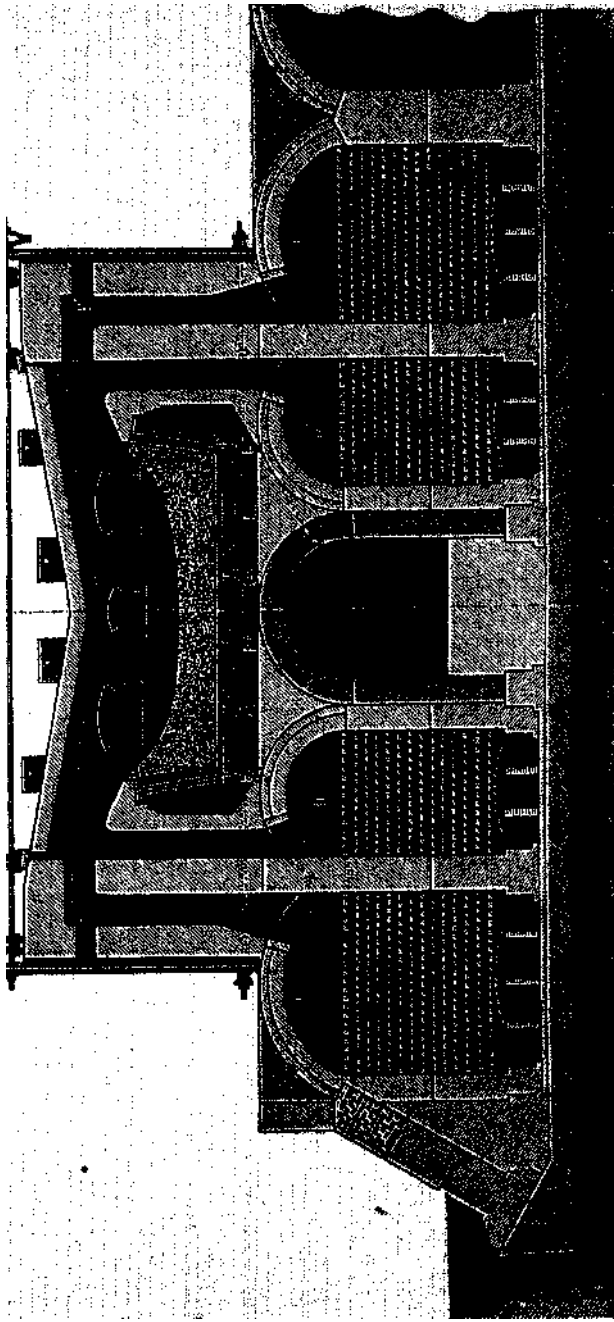

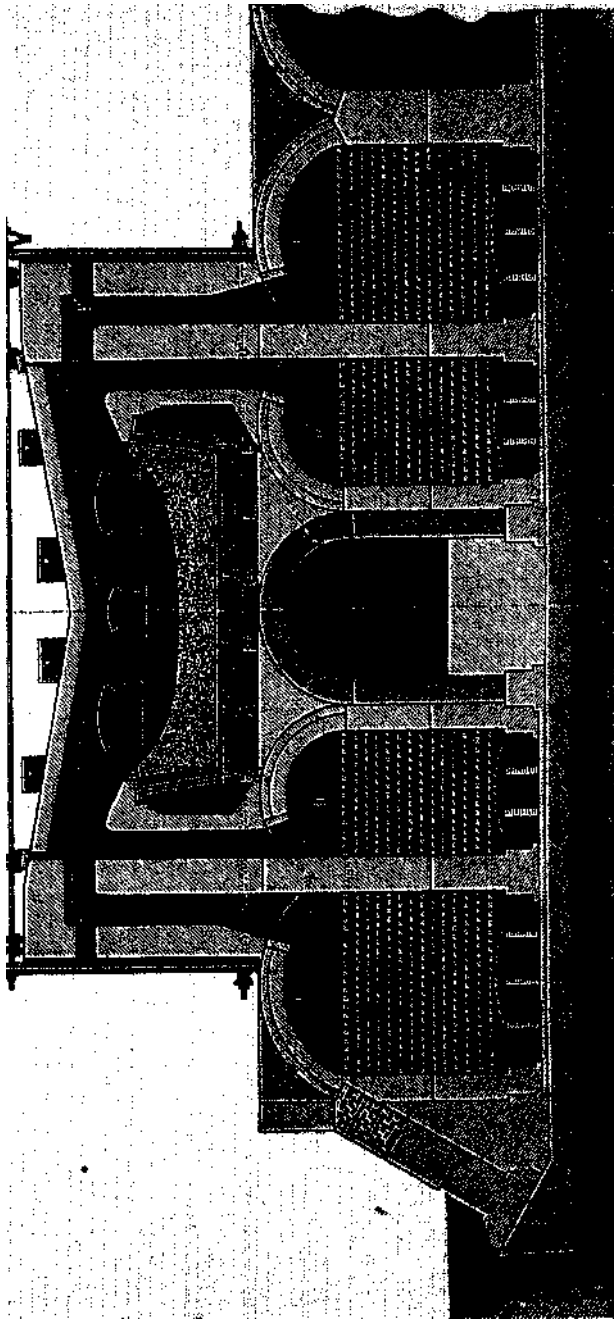

are added during the working, to keep the slag basic, the final slag containing from 40 to 50 per cent of lime

554 *Tilting Furnaes* —Tilting furnaces[1] have been introduced to overcome the mfficulties of tapping large charges from the furnaces Of these the Wellman rolling-furnace is an example, in which the furnace is a strong steel shell lined with silica bricks Underneath the body of the furnace are two curved rockers which roll on strong steel standards with horizontal surfaces. When pouring off slag or steel, the furnace is rocked forward by means of two hydraulic cylinders mounted on trunnions at their lower ends, and having the upper ends of their piston-rods attached to the pouring side

Many modifications of the open-hearth process are now in use Among these may be mentioned the Bertrand-Thiel[2] process, in which two or more furnaces are used to complete the operation As generally practised, two open-hearth furnaces are used, preferably placed at different levels, so that the metal can easily be transferred from one to the other Both furnaces are basic-lmed The pig is charged into the first furnace and is worked in the usual way, the scrap to be used is charged into thef second furnace and is heated up and oxidised, the molten steel from the first furnace is then run into the second, where a vigorous reaction takes place, the non-metals being rapidly eliminated By this process the time needed for working off a charge is considerably shortened and the yield materially increased, especially when large tilting furnaces and molten iron are used

Another important modification is the Talbot process,[3] for which large basic-lined tilting furnaces are used, which have a capacity of 50 to 75 tons The week's run is cominenced on Sunday evening with a charge of pig and scrap, the charge being worked down to steel in the usual way with ore and lime When this metal is of the required quality, about one-third of the charge is poured off, the furnace is turned back, and a considerable quantity of oxide of iron is added to the slag When this is thoroughly melted, a charge of molten pig-iron is run in to replace the amount tapped out A vigorous reaction at once takes place between the oxide of iron in the slag and the non-

[1] **Head, *J Iron Steel Inst*, 1899, 55, 69**
[2] **Bertrand, *ibid*, 1897, 51, 115**
[3] **The Open hearth Continuous Steel Process," Talbot, J *Iron Steel Inst*, 190O, 57, 33**

metals present in the iron, with a great elevation of temperature, so that during this reaction the gas-supply employed for heating the furnace is cut off After the metal has " boiled " for ten or fifteen minutes, the slag is partly poured off and the bath finished off with additions of ore and lime About one-third of the charge is again run off and the process is repeated as before, until the end of the week, when the furnace is emptied for repairs The chief advantages claimed for this process are a saving in fuel, an increase in output and yield, and a saving in charges for labour and furnace repairs

555 Electric furnaces are being used to a considerable extent in the production of high-class carbon and special steels from cold scrap, and also in the refining of steel from open-hearth furnaces and Bessemer converters in order to improve its quality Three types of furnace are used (1) The Induction Furnace, (2) The Resistance and Arc Resistance Furnace, and (3) The Arc Furnace

556 The ordinary Bessemer ingots are frequently found to be honeycombed and unsound from the presence of blowholes, and the same thing is found in all large steel castings These blowholes are small cavities or bubbles distributed throughout the metal, and vary in size from visible holes to microscopic cavities Many suggestions have been made for the prevention of blowholes, and one process largely ijsed consists in exposing the molten steel during its solidification to enormous pressure by means of hydraulic machinery[1] Casting under pressure was fir^t attempted by Bessemer in 1856, but was reintroduced and rendered practicable by Whit worth in 1865

For the production of sound castings and the elimination of blowholes, silicon and aluminium are often added to the molten steel, the sihcon as ferro-silicon and the aluminium as metal, very little aluminium is required for the purpose, and in the finished steel generally only a trace can be found

557 *Properties of Steel* —The most characteristic property of high carbon steel is its power of assuming an almost adamantine hardness when quickly cooled, as when plunged into water After this, treatment it is extremely brittle, almost perfectly elastic, and so hard that it cannot be attacked by a file The hardness and bnttleness may be practically removed by annealing, that is to say, heating the steel to a high temperature and then allowing it to cool slowly It may also be partially removed

[1] **Capron,** *J Iran Steel Inst,* **1906, 69, 28**

by a process of tempering which consists in heating the steel moderately and then allowing it to cool The temper of steel depends upon the heat to which the steel is raised, and the workman judges as to the temperature by observing the various colours which the surface of the metal assumes during the progress of the operation The tints thus observed are the colours of thm plates caused by the different thicknesses of the oxide formed on the surface When the requisite tint is reached the object is quickly cooled by being plunged into water, brine, oil, etc The hardest temper, such as is required for steel for surgical instruments, lancets, and razors, is that obtained at the lowest temperature, the tint employed for this purpose is that first reached, and is a light-straw colour, the temperature being about 230° At 255°, a brownish-yellow tint is attained, and steel thus tempered is bost fitted for cold chisels and shears for cutting metals At 265°, the first shade of purple shows itself, and this is the temper employed for axes, plane-irons, and similar tools A temperature of 277° gives a purple which is the tint for cutlery and cloth-shears, and for swords and watch-springs the metal is cooled when it has a bright blue colour, corresponding to a temperature of 288° At higher temperatures, from 290° to 316°, steel assumes a dark blue colour, and is used for shears, chisels, and especially for laige saws [x]

Damascening is produced by repeatedly welding, drawing out, and doubling up a bar composed of a mixture of steel and iron, the surface of which is afterwards treated with an acid The surface of the non retains its metallic lustre under the action of the acid, whilst that of the steel is left with a black, firmly attached coating of carbon

Case hardening is effected by more highly carbunsing the surface of mild steel Objects of mild steel are heated together with nitrogenous orgamc matter such as powdered charcoal, bone-dust, leather, etc , or potassium ferrocyanide, and thus a superficial coating of more highly carbunsed steel is given to them

The *Harvey 'process* is of a similar character, and is applied to armour plates in order to give them a hard surface capable of offering resistance to a modern projectile This process is carried out by heating the plate of mild steel or nickel steel to

[1] **See also *Report of* the *Lathe Tools Research Committee of the Manchester Association of Engineers,* published by the Department of Scientific and Industrial Research, 1922**

about the melting point of cast iron in contact with carbonaceous material, which is tightly ramined down upon its surface When the surface of the plate has absorbed about 1 per cent of extra carbon the plate is withdrawn from the heating chamber and quenched with cold water

Manganese steel is very tough and is largely used for the jaws of rock breakers and other mining and mechamcal machinery. Nickel is added to increase the tenacity and elastic limit, without reducing the ductility Chromium increases the hardness, whilst tungsten and molybdenum prevent the softening effect of the rise of temperature of the tool

The following tables give analyses (by Lambert) of various modern steels

	Carbon				Copper
Mild steel for structural work	O 247	0 476	0 063	0 052	0 049	0 054
Steel boiler plate	O 208	0 534	0 088	0 047	0 048	0 025
Steel rail, Indian Government	O 420	0 866	0 085	0 074	0 066	0 049
Steel tyre, N B Railway-	O 534	0 902	0 248	0 045	0 054	0 038
Steel axle, British specification	O 320	0 756	0186	0 038	0 035	0 051
Casting for hydraulic press	O 415	0 805	0 310	0 072	0 060	
Casting for snip's stern frame	O 393	0 730	0 164	0 055	0 048	traces
Gun steel, British	0 385	0 648	0 182	0 038	0 035	0 029
Forged shaft for ship's propeller	0 345	0 555	0 096	0 040	0 042	0 055
Double shear steel	0 668	0 107	0 055	0 012	0 018	
Spring steel, laminated, carriage	0 645	0 732	0 044	0 036	0 032	0 045
Tool steel for heavy work	0 750	0 468	0 238	0 021	0 018	0 022
Steel for swords, cutlasses, etc	0 986	0 255	0 124	0 017	0 020	
Die steel for striking coins	1085	0 264	0 133	0 011	0 009	
Tool steel for light work	1274	0 252	0 148	0 018	0 012	traces
Cast steel for razors, surgical in struments, etc	1445	0 305	0 112	0 014	0 016	traces

	Carbon	Man-	Silicon	Phos phorus	Sulphur	Special Element
Hadneld's manganese steel	0 875	13 330	0 068	0 030	0 047	
0rdnance steel	0 330	0 606	0 165	0 029	0 038	Ni, 3 94
Chrome projectile steel	0 807	0 505	0 246	0 012	0 055	Cr, 5 74
Self hardening tool steel	0 650	0 190	0 608	traces	0 042	W, 9 87
American self hardening tool steel	0 585	traces	0 034	0 009	0 014	Mo, 918
High speed steel	0 612	0 288	0 214	0 012	0 019	W, 18 21 Cr, 3 85

558 *Recalescence of Steel*—When ordinary steels, containing varying amounts of carbon, are allowed to cool from a temperature of about 1000°, it is found that at two or more temperatures

the regularity of the cooling is interrupted, an evolution of heat taking place which prolongs the period required for the metal to cool through a given ra^ge of temperature This phenomenon is known as recalescence, and the temperatures at which the retardation during cooling takes place are indicated by Ar_3, Ar_2, and A r , as these changes are reversible, there is a retardation of the rate of heating on raising the temperature of the steels, and the temperatures at which this retardation takes place are indicated by Ac_1, Ac_2, and Ac_3 These changes do not generally take place at the same temperature, the Ac point often being 30° higher than the corresponding Ar point

The Ar_3 change[1] is found only in steels containing not more than 0 38 per cent of carbon, and varies from 900° in pure iron to 770° in a steel of this composition, the Ar_2 change takes place at about 770°, and the A^ change takes place at about 690° These changes are not equally well marked in all varieties of steel The Ar_1 change is the most pronounced and can sometimes be observed by the naked eye when cooling down large masses, it can also be rendered evident by allowing a heated bar of steel to cool when loaded with a weight just insufficient to bend it when hot When the iron reaches the temperature of recalescence, it is seen suddenly to bend

559 *Constitution of Steel* —Many different views are held by chemists as to the constitution of steel, and the cause of hardening and of recalescence All agree in regarding the Ar_1 change as due to the separation of carbide of iron, Fe_3C All carbon steels which are slowly cooled from above this temperature (700°) contain the greater portion of the carbon in the form of this carbide, whilst steel which is suddenly cooled from a higher temperature contains scarcely any of it in the free state

According to one view (the "Allotropic "),[2] the two changes Ar_2 and Ar_3 mark the occurrence of allotropic changes in the iron present, the metal being supposed capable of existing in three allotropic forms, as y-iron above Ar_3, as /3-iron between Ar_3 and Ar_2, and as a-iron below Ar_2, of these varieties, 7- and B-irons are non-magnetic (see p 1217) When heated steel is suddenly cooled, the 7- or */3-iovm* persists and the result is a hard and brittle metal, if the temperature be allowed to fall below Ar_2, the a-form is produced, and a soft metal is the result. In the absence of carbon, the B-form invariably passes into

[1] **Carpenter and Keeling, *J Iran Steel Inst*, 1904, 65, 224**
[2] **See Stansfield, *ibid*, 1899, 56, 169, 1900,58, 317**

the a-condition, even when suddenly cooled, but carbon has a great tendency to retard this change, and thus, when present, keeps the iron in the hard form in quenched steels

According to the second or "carbon" theory, the hardening is due to the carbon present, and not directly, at least, to any allotropic condition of the iron In this connection, it is pointed out that without the presence of carbon, iron cannot be usefully hardened, whilst the effect increases with increase of carbon, at least to about 0 9 per cent This theory asserts that above Ar_3, the carbon exists in a state of solid solution, capable of imparting a hardened condition which may be retained by cooling sufficiently rapidly

The following are the most important constituents of steel

Ferrite, or pure iron, occurs in tnmorphic crystals with polygonal or rounded boundary lines produced by the interference of cubes or octahedra

Pearlite—A definite mixture of iron and carbide of iron, Fe_3C, forming the eutectoid (p 87) Pearhte contains 0 89 per cent of carbon or 13 per cent of Fe_3C, the carbon being molecularly associated with only about 12 per cent of the iron, 87 per cent of the latter being in the free state

Hardemte —According to Arnold, this constituent also contains 0 89 per cent of carbon, but in this case the carbon is associated with about 99 per cent of the iron It is found in quenched steels

Austenite[1] Is a solid solution of carbide of iron in iron and is stable at temperatures above the $A.T_3$-$_2$-$_1$ changes

Martensite is the first transition form between austenite and pearlite, and is obtained on quenching steels from the austenite range in water

Troostite is a transition form between martensite and sorbite

Sorbite is a transition form between troostite and pearlite It is formed by rapidly cooling the steel whilst passing through the Ar1 change

Sulphide of Iron is described by Arnold as occurring in masses or as a mesh-work in manganese-free steel and iron

Sulphide of Manganese is very frequently present in steels as globules or cigar-shaped masses of a dull grey or dove colour

Phosphide of Iron was observed by Stead[2] in 1900, and with free iron forms a eutectic similar to pearlite and known as steadite

[1] "The Constitution of Iron Carbon Alloys,' *J Iron Steel Inst,* 1906,72,493
[2] "Iron and Phosphorus," *ibid* , 1900, 68, 60

Manganese Silicate is often present in steels, sometimes visible to the naked eye, sometimes only under the microscope

Ghosts are drawn out segregations of ferrite, high in sulphur, phosphorus, and sometimes carbon, which appear dark when etched

COMPOUNDS OF IRON

IRON AND OXYGEN

560 Iron forms three oxides,

Iron monoxide, or ferrous oxide, FeO,

Magnetic oxide of iron, or ferroso-ferric oxide, Fe_3O_4,

Iron sesquioxide, or ferric oxide, Fe_{203}

The last two oxides occur in nature as minerals, and are used, not only as ores of iron, but also for medicinal purposes Indeed, rust of iron (hydrated ferric oxide) is said to have been used as a medicine by iEsculapms, and Dioscondes also mentions (probably iron-scales), as being a substance similar to rust, but possessing less active medicinal properties Red haematite was termed blood-stone, and the same author states that this may be obtained artificially by igniting load-stone Pliny terms iron rust or scale *squama fern,* red iron ore *haematites,* and loadstone *magnes,* and describes the action of the latter upon iron The reddish-yellow and red oxide of iron is called *crocus maitis* by the Latin Geber The later chemists describe various methods for its preparation, and in 1735 the artificially prepared black oxide was termed *cetheops martis* For a long time these compounds were distinguished only by their different medicinal action The supporters of the phlogistic theory considered them to be compounds of iron calx with various proportions of phlogiston Thus, for instance, Scheele in 1777 states that the precipitate which an alkali produces in a solution of green vitriol when exposed to the air gives rise to crocus martis, and that fire-air or oxygen disappears Hence he concludes that the precipitated calx gives up phlogiston in its conversion into crocus

Lavoisier distinguished two oxides, æthiops and crocus Other chemists, like Berthollet, believed that a large number of these oxides existed, and as late as 1811 the views of chemists on this

subject were much divided Gay-Lussac was the first to point out that in addition to the lower and higher oxides an intermediate compound exists, this was confirmed by Berzehus[1]

Ferrous oxide acts as a basic oxide, yielding the readily oxidlsable ferrous salts, FeR_2 (R — a umvalent negative radicle), in which the metal is divalent Ferric oxide acts as a basic oxide yielding the ferric salts, FeR_3, in which the metal JS trivaleot, it has also a feeble acidic function, forming with many basic oxides a series of compounds known as the ferrites, M^nO,Fe_{203} The magnetic oxide does not correspond to any characteristic series of salts, but yields a mixture of ferrous and ferric salts when it is treated with acids It may be regarded as a ferrous ferrite, FeO,Fe_{203} *Ferrates* are also known corresponding to the acidic oxide, FeO_3, which has not itself been prepared

Iron Monoxide, or *Ferrous Oxide,* FeO, is obtained when hydrogen is passed over the sesquioxide heated to 300°, as a black powder which oxidises with incandescence on exposure, but loses this property after it has remained for twelve hours in an atinosphere of hydrogen (Siewert) The reduction of ferric oxide at a high temperature (700-1000°) by a mixture of hydrogen and steam yields a product which, although not pure, contains a high proportion of ferrous oxide[2] This compound is formed also by the action of mtrous oxide on metallic iron at 200°[3] When ferrous oxalate, FeC_{204}, is heated at 150-160° in absence of air, a mixture of monoxide and metallic iron remains, as shown by Liebig's observation that the gas evolved consists of fifty-six parts of carbon monoxide and sixty-eight parts of carbon dioxide[4] If ferrous oxalate is added to boiling caustic potash the monoxide is obtained as a black, velvety powder, which when washed with water in the air takes up oxygen (Bottger)

Ferrous Hydroxide, $Fe(OH)_2$, is formed when a pure ferrous salt is treated with caustic potash or soda freed from air It is a white powder which, when washed with hot water and ether in absence of air, may be preserved in an atinosphere of hydrogen As, however, it is difficult to obtain perfect absence of air, the ferrous hydroxide is usually obtained as a green, pulverulent

[1] See Wohler and Balz, *Zeit Elektrochem* , **1921, 27, 406**

[2] **Hilpert and Beyer, *Ber,* 1911, 44, 1608, see also Sosman, *J Washington Acad Set,* 1917, 7, 55**

[3] **Sabatier and Senderens, *Compt rend* , 1892, 114, 1429**

[4] **See also Mixter, *Amer J Sci,* 1913, [4], 36, 556**

mass[1] It crystallises from solution in strong caustic soda in flat green prisms[2]

Ferrous hydroxide absorb oxygen, assuming first a dirty-green colour which rapidly darkens and finally becomes brown owing to the formation of ferric hydroxide On exposure of ferrous hydroxide to air, this process proceeds so rapidly that the mass sometimes becomes incandescent with formation of the sesquioxide Owing to its affinity for oxygen ferrous hydroxide is a powerful reducing agent It reduces nitrites and nitrates to ammonia, a reaction which may be used for the estimation of these substances[3] It also absorbs carbon dioxide rapidly, and dissolves in acids with evolution of heat

Ferrous hydroxide dissolves readily in acids to form the ferrous salts, which are produced also by the direct action of acids on metallic iron in the absence of oxidising agents, and by the reduction of the corresponding ferric salts The anhydrous ferrous salts of colourless acids are usually colourless, but the corresponding hydrated salts possess a pale greenish-blue tint The soluble salts possess a sweet, astringent, ink-like taste Their neutral or acid solutions absorb oxygen slowly with formation of a ferric salt, part of which is precipitated in the form of basic salt when there is no excess of acid present In presence of alkali, absorption of oxygen occurs rapidly, even at the ordinary temperature Copper salts even in traces exert a marked catalytic effect in increasing the oxidation of ferrous salts[4] In consequence of the ease with which they pass into a higher state of oxidation, the ferrous salts act as powerful reducing agents, and are largely employed for this purpose

Magnetic Oxide of Iron, Ferroso-femc Oxide, or Tnferric Tetroxide, Fe_3O_4, occurs in large masses as the mineral magnetite It crystallises in octahedra, dodecahedra, and other combinations of the regular system It has an iron-black colour, and a more or less strong metallic lustre It frequently occurs in granular or amorphous masses, and is found also in marshes as an earthy mass known as ochreous iron ore (or in German *eisenmulm)* The pure crystallised mineral has a specific gravity of 5 18, whilst that of the granular and earthy material varies considerably, inasmuch as it contains magnesia, lime, and titanic

[1] Schmidt, *Annalen,* 1840, 36, 101
[2] de Schulten, *Compt rend,* 1889,**109,** 266
[3] Miyamoto, *Journ Chem Soc , Japan,* 1922, 43* 397
[4] Maquenne and Demoussy, *Compt rend,* 1920,**171,** 65

oxide, and also often contains the iron in a more highly oxidised condition

The interesting observation that this ore has the power of attracting iron, and that by contact with it iron attains the same polar magnetic properties, was made at an early date According to some, the name is derived from a certain Magnes, who was the first to observe this property, whilst according to others the name is derived from Magnesia, a town in Lydia also called Heraclea, where the mineral was first found The latter explanation would seem to be the more probable, inasmuch as Plato and Theophrastus termed magnetite the Heraclean stone Ferroso-fernc oxide does not always possess the magnetic properties exhibited by loadstone, although attracted by the magnet

When iron is heated to redness in the air it becomes coated with an iron scale This is a mixture or a compound of the monoxide and sesquioxide in varying proportions The inner layer, which is blackish-grey, porous, brittle, and attracted by the magnet, has the composition $6FeO,Fe_{203}$, and is not magnetic The outer layer contains a large quantity of ferric oxide, is of a reddish colour, and is more strongly attracted by the magnet than the inner portion When iron is quickly burnt in oxygen or in the oxy-hydrogen blowpipe, the oxide which is formed varies in composition according to the conditions of the experiment, although it approaches the composition of the magnetic oxide, the occurrence of this oxide has also been observed in smelting operations

Magnetic oxide is obtained when excess of steam or carbon dioxide is passed over red-hot iron, but, on the other hand, when the oxides of iron are heated in a current of hydrogen or of carbon monoxide in excess, they are reduced to metal Pure ferroso-fernc oxide may be prepared by reducing ferric oxide at 40O° by a mixture of hydrogen and steam [x] It is also obtained as black crystals by strongly heating ferric oxide with excess of sodium chloride [2] or by fusing iron with sodium sulphate When the black oxide is dissolved in hydrochloric acid, or when a mixture of a ferrous and ferric salt is dissolved in the right proportions, and caustic alkali added to the solution, a black precipitate is obtained which dries to a brownish-black brittle mass giving a dark brown powder unalterable in the air This hydroxide contains about 7 per cent of water, and corresponds

[1] **Hilpert and Beyer,** ***Ber,*** **1911, 44, 1608**
[2] **Thompson,** ***Trans Ceramic Soc*** **, 1918,17, [2], 340**

which he regarded as definite hydrates, but van Beminelen [1] has shown that all the " red " hydrates are in reality colloidal substances, the amount of water retained by them depending only on the pressure of the atmospheric aqueous vapour with which they are in equilibrium [2]

When freshly prepared red ferric hydroxide is heated with water under a pressure of about 5,000 atmospheres, it is converted into definite hydrates agreeing in composition with the naturally occurring minerals[3] Between 30° and 42 5° limonite is formed, between 42 5° and 62 5 gothite, and above 62 5° hydrohaematite

Various pigments, notably red, yellow, and brown ochres, are made by heating the naturally occurring hydrates The exact colour produced depends upon the degree of heating [4]

Iron rust, when completely oxidised, is found to have a composition very close to that of limonite, viz $2Fe_2O_3,3H_2O$, freshly formed rust, however, usually contains considerable quantities of ferrous hydroxide and carbonate [5]

When ferric hydroxide is precipitated from solution, the quantities of salts and of water absorbed by it vary widely with the composition of the mother-liquor [6] Arsenious acid forms an adsorption compound with freshly precipitated ferric hydroxide, [7] the latter substance, therefore, can be employed as an antidote in cases of arsenical poisoning

Ferric hydroxide dissolves readily in acids to form the ferric salts, which may be obtained also by the action of oxidising agents on the corresponding ferrous salts In the anhydrous state they are generally colourless, in the hydrated state they are yellow or brown The soluble ferric salts possess a peculiar astringent taste, and they pass readily bv reduction into the corresponding ferrous compounds

Soluble Feme Hydroxide—When freshly precipitated ferric hydroxide is added to a solution of feme chloride it dissolves, forming a dark red solution of basic ferric chloride, which may

[1] *Rec trav chim*, 1889, 7, 37

[2] See also Posnjak and Merwm, *Amer J Set*, 1919, [4], **47,** 311

[3] Ruff, *Ber*, 1901, 34, 3417 Compare Fischer, *Zat anorg Chtem*, **1910, 66,37**

[4] Bouchonnet, *Bull Soc chim*, **1911,** [4], **9,** 345, **1912, [4], 11,** 6

[5] Moody, *Journ Chem Soc*, 1906, 89, 720

[6] See Weiser, *J Physical Chem*, **1913,17, 536**

[7] **Biltz,** *Ber*, **1904, 37» 3138** See also Lockemann and Lucius, *Zeit physikal Chem*, **1913, 83,1735,**

also be obtained by adding ammonium carbonate to a solution of ferric chloride until the precipitate first formed no longer redissolves On dialysis of these solutions, hydrochloric acid and ferric chloride first pass through the membrane, and finally hydrochloric acid alone, leaving ferric hydroxide in solution in the dialyser (Graham) It is not possible, however, to remove all the chlorine in this manner, thus after 210 days the composition of the residual solution was found to correspond to the formula $82Fe(OH)_3,FeCl_3$ [1] According to Tribot and Chretien,[2] the last portions of chlorine may be removed by subjecting the liquid to electrolysis, the colloidal solution being placed in a porous cell containing the cathode, the outer cell containing water, which is frequently renewed Precipitated ferric hydroxide can be brought into colloidal solution by repeated washings in a centrifuge until free from the precipitating agent[3] Colloidal ferric hydroxide can also be readily obtained by the action of potassium permanganate on a ferrous salt in absence of acid,[4] by boiling ferric nitrate with copper filings or fine dust,[5] or by dialysing a hot solution of ferric chloride[6] The solution is used in medicine under the name of *Liquor Fern Dialysati*

Colloidal ferric hydroxide solution is readily precipitated by electrolysis or by the addition of an electrolyte As usually prepared, the colloid is positively charged, so that the efficiency of the precipitating electrolyte is dependent on the valency of its amon[7] Negatively charged colloidal ferric hydroxide has also been made by adding the ordinary colloid or dilute ferric chloride solution to dilute sodium hydroxide solution with constant shaking[8] The charge on a colloid is due to absorption of ions from solution and its sign will therefore depend on whether anions or cations are in excess in the layers of solution next to the particles Non-electrolytes, as, for example, sugar and alcohol, do not bring about gelatinisation The nature of the precipitated gel depends upon the conditions of precipitation[9]

Ferric hydroxide forms a compound with sugar which is

[1] Linder and Picton, *Journ Chem Soc* , 1905, 87, 1920
[2] *Compt rend,* 1905,**140,** 144
[3] Bradfield, *J J , Amer Chem Soc* , 1922 **44,** ᶜ65
[4] Neidle and Crombie, *ibid* , 1918, 38, 26O7 *
[5] Cohen, *ibid* , 1914, 36, 19
[6] Neidle and Barab, *ibid,* 1917, 39, 71
[7] Freundlich, *Zeit physihah Chem,* 1903, **44,** 131, Pappada, *Zeit Chem Ind Kolhide,* 1911, 9, 233
[8] Powis, *Journ Chem Soc* , 1915,**107,** 818
[9] See Weiser, *J Physical Chem,* 1920, 42, 277, 5O5

soluble in water This fact is of great importance to the sugar refiners, as this compound destroys the crystallising power of sugar, and therefore meteases the quantity of molasses formed Hence raw sugar ought not to be brought into contact with iron, and the " char " employed for the decolorisation of the sugar should be as free as possible from the compounds of this metal

561 Ferric hydroxide has feebly acidic properties, and combines with strong bases to form unstable salts, termed *ferrites* The compound formed with the basic monoxides such as lime are analogous to ferrosofernc oxide, Fe_2O_3,FeO, which they resemble in being magnetic

Alkali Ferntes —Solutions of potassium and sodium ferrites are formed by boiling solutions of the corresponding ferrates, oxygen being evolved, the solution on standing deposits crystals of the ferrite, but these are very unstable and quickly decompose when removed from the alkaline liquid A similar solution is obtained by boiling ferric hydroxide with concentrated caustic soda[1] Sodium ferrite is also obtained by the electrolytic oxidation of iron in dilute caustic soda solution at low temperatures

in complet

solution of ferrous hydroxide or cathodic reduction of sodium ferrate solution, using platinum electrodes[2] Sodium ferrite is produced also when ferric oxide is heated with sodium carbonate to bright redness, carbon dioxide being evolved This reaction is made use of in the Lo wig process for the manufacture of caustic soda from sodium carbonate

Calcium Fernte, Fe_2O_3,CaO—This compound is obtained when an intimate mixture of 190 parts of ferric oxide and 66 5 parts of lime is heated to whiteness in a platinum vessel for several hours[3] It forms a brittle mass of interlaced acicular crystals exceeding an inch in length, with a dark metallic lustre and magnetic properties When ground it yields a brown powder, which is obtained also by precipitating a solution of ferric chloride, as nearly neutral as possible, with lime water or saccharate of lime, and igniting the precipitate Other calcium ferrites, containing different proportions of the two oxides, have also been prepared,[4] but Sosman and Merwin[5]

[1] Haber and Pick, *Zat Elektrochem* , 1901,7,215, 724
[2] Grube and Gmelin, *ibid*, 1920, 26, 459
[3] Percy, *Phil Mag* , 1873, [4], 46, 455
[4] Hilpert and Kohlmeyer, *Ber* , 1909, 42, 4581
[5] *J Washington Acad Sci*, 1916, 6, 532. See also Campbell, *J Ind Eng Chem,* 1919, 11, 116

maintain that only two such compounds exist, namely, Fe_{203},CaO and Fe_{203} 2CaO, the former giving deep red crystals and the latter black

Magnesium Fernte, Fe_{203},MgO, occurs in nature crystallising in black oc

by the ignition of a mixture of the two oxides in a current of hydrogen chloride, or by the precipitation of a mixture of ferric chloride and magnesium chloride with a quantity of caustic soda insufficient to throw down the whole Many analogous compounds can be prepared in a similar way [x]

Zinc Ferrite, Fe_{203},ZnO, was obtained by Ebelmen in black octahedra by strongly igniting both oxides together with boron trioxide The mineral franklinite has a similar composition

562 *Ferric Acid,* H_2FeO_4—This compound, like manganic acid, is not known in the free state In the year 17O2 Stahl noticed that when iron is fused with saltpetre and the solid mass lixiviated, or when a solution of iron in nitric acid is added to concentrated potash-ley, an amethyst or purple-red coloured solution iS formed Exactly a century afterwards Eckeberg published his memoir on " Yttria," in which he states that when gadolinite is fused with potash and the fused mass extracted with water, the solution possesses a dark purple-red colour, due to iron and not to manganese The potassium ferrate formed in .these circumstances was more carefully examined by Fremy [2] It is prepared by igniting iron filings or iron oxide with saltpetre or caustic potash, or a mixture of both The formation of the compound may be readily shown by heating a mixture of one part of powdered iron with two parts of saltpetre in a small glass bulb, over a Bunsen burner After a few minutes the mass becomes red hot, and when cold the residue is dissolved in water [3] The purple solution is obtained also by passing chlorine through a strong solution of caustic potash in which ferric hydroxide is suspended (Fremy)

Ferrates are readily produced also by the electrolytic oxidation of iron in caustic potash or soda solution When iron is used as anode in concentrated caustic potash or soda solution and a low current density employed, all varieties of iron yield ferrate, but the yield is greatest with cast iron, smallest with wrought iron, and increases with the temperature A good yield is obtained by iminersing two large iron plates in concen-

[1] **List, *Ber*, 1878, 11, 1512** [2] ***J Pharm*, 1841, 27, 97**
[3] **Hofmann, *Ber* , 1869, 2, 239**

trated alkali at 7O° and making these alternately cathode and anode, the reversal taking place four times per minute The iron plates become p#sive during the process [1] A better yield is obtained by imposing an alternating current on the direct current and working at a temperature not exceeding 5O°, above which there is appreciable decomposition of the ferrate with evolution of oxygen and precipitation of the hydroxide [2]

The concentrated potassium ferrate solution is almost black, and on addition of more potash deposits a reddish-brown precipitate, which is very unstable, but may be preserved by drying on a porous plate and sealing in a glass tube As already mentioned, the solution decomposes on boiling, with evolution of oxygen and formation of a yellow solution of potassium ferrite, from which ferric hydroxide readily separates Nitric acid and sulphuric acid yield a ferric salt with evolution of oxygen, whilst with hydrochloric acid chlorine is evolved

Barium Ferrate, $BaFeO_4,H_{20}$, is the most stable of the salts, and is obtained in the form of a dark red powder by precipitating a solution of the potassium or sodium salt with barium chloride It is fairly stable, and yields a red solution with acetic acid It is not decomposed by dilute sulphuric acid in the cold, but at once yields ferric and barium salts with hydrochloric and nitric acids, with evolution of chlorine and oxygen respectively [3]

IRON AND HYDROGEN

563 The absorption of hydrogen by iron and its diffusion through the metal have already been discussed

By the action of zinc ethyl, $Zn(C_2H_5)_2$, on anhydrous ferrous iodide in presence of ether, Wanklyn and Canus found that a mixture of ethylene, ethane, butane, and hydrogen is evolved, and that the residue on washing with ether yields a metallic powder resembling iron, which evolves hydrogen on heating and is decomposed by water with evolution of hydrogen, leaving a residue of metallic iron and ferrous oxide [4] It is possible that this product contains a compound of hydrogen and iron, but further investigation is needed

[1] Haber and Pick, *Zeit Elektrochem* , **1901, 7,** 215, **712,** 724
[2] Grube and Gmelin, ibid, **1920, 26, 153**
[3] Baschien, *Gazz* , **1906, 36,11, 282**
[4] *Annalen,* **1861,120, 74**

IRON AND THE HALOGENS

564 *Ferrous Fluoride*, FeF_2, is obtained in colourless or gieenish prjsms, $FeF_2,8H_2O$, by dissolving iron in hydrofluoric acid and evaporating, these crystals decompose when gently heated, leaving the anhydrous salt, this is formed also when iron or ferric chloride is heated in dry hydrogen fluoride, and crystallises in colourless rhombic prisms

A number of double fluorides with ammonium and alkali fluorides have been prepared

Feme Fluoride, FeF_3, is obtained by dissolving the hydroxide in hydrofluoric acid, colourless crystals of $2FeF_3,9H_{20}$ separating out from the colourless solution on evaporation On heating this at 100° the hexa-hydrate, $2FeF_3,6H_{20}$, is obtained The formula $FeF_4(OH)_2(HF)_2,4H_{20}$ has been proposed for this compound in order the more easily to account for the following reactions[1] (1) Only one-third of the fluorine enters into double decomposition with barium chloride in aqueous solution (2) When the solid is boiled with alcohol one-third of the fluorine is rapidly eliminated as hydrogen fluoride, but the remainder is lost very slowly (3) At 95°, the salt loses water rapidly and proportionally to the loss of fluorine until one-third has been eliminated, when no more water is lost (4) Prolonged heating at 95° yields an oxyfluonde in accordance with the equation

$$FeF_4(OH)_2(HF)_2 = FeOF_4 + H_{20} + 2HF$$

The anhydrous salt is obtained by heating the hexahydrate in a stream of hydrogen fluoride or by strongly heating iron, ferric oxide, or chloride in a stream of the gas It does not fuse even at 1000°, and forms ferric oxide when heated in the air [2]

Several double salts with the alkali fluorides are known

Ferroso-fernc Fluoride, $Fe_3F_8,10H_{20}$, has been described[3]

Ferrous Chloride, $FeCl_2$, is obtained by passing chlorine over iron filings (Thenard), but as a small quantity of ferric chloride is generally formed, even when an excess of iron is present, it is preferable to pass hydrogen chloride over iron filings or iron wire heated to redness (Wohler and Liebig), or to reduce ferric chloride by heating it in a stream of pure hydrogen Ferrous chloride is deposited in colourless, shining scales, which, according to Senarmont, are six-sided It has a specific gravity of

[1] Recoura, *Compt rend*, 1912,**145,** 655 [2] Poulenc, *ibid*, 1892, **114,** 941
[3] Deussen, *Monateh*, 1907, 28, 163

2 528 (Filhol), and is very deliquescent, dissolving readily in water and alcohol Jt fuses at a red heat, and volatilises at a yellow heat, when its vapour has a density of 6 38-6 67,[1] whilst at 1300-1500° it acquires the normal value of 4 3 [2]

When heated in the air it oxidises to ferric chloride, which volatilises, ferric oxide remaining behind

$$12FeCl_2 + 3O_2 = 8FeCl_3 + 2Fe_{203}$$

When heated in a current of steam, magnetic oxide is formed

$$3FeCl_2 + 4H_{20} = Fe_3O_4 + 6HC1 + H_2$$

When iron is dissolved in hydrochloric acid, and the solution concentrated in absence of air, bluish, transparent, monochmc crystals of $FeCl_2,4H_{20}$ are obtained, these have a specific gravity of 1 93, and deliquesce and become greenish coloured on exposure to the air, but effloresce at ordinary temperatures when kept over oil of vitriol If a solution of this salt is evaporated with sal-ammoniac in absence of air, and the solid mass is heated in a flask until the whole of the sal-ammoniac is volatilised, the residue is anhydrous ferrous chloride Hydrates with 1, 2, and 6 H_{20} have also been obtained Like other soluble ferrous salts, the solution of ferrous chloride absorbs nitric oxide, forming a dark, greemsh-brown solution, possibly containing the unstable compound $FeCl_2,NO$ (p 1293) The anhydrous chloride readily absorbs ammonia with evolution of heat and formation of a white powder (Faraday), which has the composition $FeCl_2,6NH_3$, gives off ammonia at 100°, and at higher temperatures yields ammonium chloride, iron nitride, and nitrogen [3] Two other ammoniates exist, namely $FeCl_2,2NH_3$, and $FeCl_2,NH_3$,[4] the former being produced by heating the hex-ammoniate in hydrogen at 100°

A number of double chlorides have been prepared

Ferroso-ferne Chloride, $Fe_3Cl_8,18H_{20}$ —Magnetic oxide of iron dissolves in concentrated hydrochloric acid, forming a yellow liquid, which on concentration over sulphuric acid deposits the above salt in opaque yellow deliquescent crystalline crusts

Ferric Chloride, $FeCl_3$ —The aqueous solution of this salt was

[1] Meyer, *Ber* , 1884,17,1335

[2] Nilson and Pettersson, *Journ Chem Soc* , 1888,53, 827

[3] Fowler, *ibid,* 1901, 79, 288 Compare Girardet, *Bull Soc chim,* 1910, 7, 1028

[4] See Biltz and Hiittig, *Zett anorg Chem,* 1919,**109,** 89

known to Glauber under the name of *oleum martis* He obtained it in the dry state by dissolving iron in hydrochloric acid and evaporating the solution in a flask " *In fundo* there remains a blood-red m*assa,* which is as hot to the tongue as fire It must be well-kept from the air, otherwise it liquefies to a yellow *oleum,.'*

Anhydrous ferric chloride is obtained by heating iron wire in a current of dry chlorine gas at a moderate red heat, when rapid combination with ignition takes place, ferric chloride being deposited It is produced also when hydrogen chloride is passed over heated amorphous ferric oxide, and is not infrequently found in the craters of volcanoes

Ferric chloride forms iron-black iridescent plates, or sometimes large hexagonal tablets, which exhibit a red colour by transmitted light, and a green, metallic lustre by reflected light It is very deliquescent, and easily soluble in water, alcohol, or ether It volatilises at about 28°, but under pressure melts at 3O1° Between 321° and 442° its vapour density is practically constant and agrees with the double formula Fe_2Cl_6 At higher temperatures it is dissociated into ferrous chloride and chlorine, $Fe_2Cl_6 = Fe_2Cl_4 + Cl_2$, and on raising the temperature to about 105O° the double ferrous chloride molecules are dissociated into single[1] When dissolved in boiling alcohol or ether it appears to have a molecular weight corresponding to the formula $FeCl_3$[2]

Ferric chloride forms with ammonia at the ordinary temperature the compound $FeCl_3,6NH_3$, which loses NH_3 on exposure to air, yielding the pentammoniate, $2NH_3$, when heated at 100°, leaving the tetrammoniate, at higher temperatures, it gives ammonium chloride[3] It also absorbs nitrosyl chloride, yielding a dark-coloured, deliquescent compound, $FeCl_3$,NOCl, and umtes with nitric oxide at the ordinary temperature to form several unstable compounds, whilst at higher temperatures it is reduced by the gas to ferrous chloride[4] It is also reduced to ferrous chloride by heating in a stream of hydrogen When heated in a current of steam it is decomposed into ferric oxide and hydrogen chloride, and when heated in oxygen, chlorine is evolved, ferric oxide

[1] Friedel and Crafts, *Compt rend,* 1888, **107,** 3O1 See also Grunewald and Meyer, *Ber ,* 1888, **21,** 687

[2] Muller, *Compt rend ,* 1894,**118,** 644

[3] Miller, *Amer Chem J ,* 1895,**17,** 57O

[4] Besson, *Compt rend,* 1889, **108,** 1012, Thomas, *tbid,* 1895, **120,** 447, **121,** 128

remaining Anhydrous ferric chloride, intimately mixed with calcium and heated to dull redness, yields metallic iron *

Ferric chloride forms compounds with a large number of orgamc compounds [2] The compound with ether is a dark red, very deliquescent solid which is decomposed quantitatively on heating at 100°, yielding pure ethyl chloride and the oxyehlonde, FeOCl [3]

$$FeCl_3,(C_2H_5)_{20} = 2C_2H_5C1 + FeOCl$$

For the purpose of obtaining a solution of ferric chloride, the hydroxide may be dissolved in hydrochloric acid and the liquid evaporated in order to drive off excess of acid, or a solution of ferrous chloride may be heated with the requisite quantity of hydrochloric acid and the heated solution oxidised by addition of nitric acid A solution of ferric chloride is, however, best prepared by dissolving iron wire in hydrochloric acid, as described under the preparation of ferrous chloride, and then passing chlorine into this solution until, after standing for some time, it smells strongly of the gas The excess of chlorine is then displaced by passing a current of carbon dioxide through the warm liquid A concentrated solution of ferric chloride has a dark brown colour and an oily consistency On dilution it becomes limpid, and has a slightly yellow colour It is readily hydrolysed in solution to the hydroxide and hydiochlonc acid;

$$FeCl_3 + 3H_{20} = Fe(OH)_3 + 3HC1$$

Owing to the formation of free acid, the electrical conductivity of the solution increases, and measurement of the rate shows that it is gradual This has been explained by assuming that the hydrolysis takes place in stages, each chlorine atom being hydrolysed in turn It is, however, more probable that the hydrolysis occurs iminediately on dilution and that the free acid produced is completely adsorbed by the colloidal particles of the hydroxide These particles are at first very small, but they gradually increase in size so that their total surface becomes less and less and the adsorbed acid is thus gradually liberated [4] Very dilute solutions of ferric chloride are practically colourless when freshly prepared, but they gradually darken in colour, finally becoming a dark

[1] Hackspill, *Bull Soc chim* , 1907,1, 895
[2] See Gangloff and Henderson, *J Amer Ghent Soc* , 1917, **39,** 1420
[3] Forster, Cooper, and Yarrow, *Journ Chem Soc* , 1917, **111,** 8O9
[4] Wagner, *Monatsh,* **1913,** 84, 95, **931** See also Quartaroli, G*azz,* 1915, 45, I, **139**

brown owing to the separation of the hydroxide In extremely-dilute solution the hydrolysis is so complete that owing to the absence of ferric ions no coloration is produced with potassium ferrocyamde

Four different hydrates of ferric chloride have been described by Eoozeboom [1] $FeCl_3,6H_{20}$, melting at 37°, $2Fea_3,7H_{20}$, melting at 32 5°, $2FeCl_3,5H_{20}$, melting at 56°, and $FeCl_3,2H_{20}$, melting at 73 5° Solutions which contain more iron than corresponds to the formula $FeCl_3,2H_{20}$ deposit the anhydrous salt when evaporated above the temperature of 66° A deliquescent compound, $FeCl_3,HCl,2H_{20}$, is formed by the action of hydrochloric acid on the pentahydrate, whilst similar compounds with $4H_{20}$ and $6H_{20}$ are also known [2] The aqueous solution of the normal chloride is decomposed on heating, the more easily the more dilute the solution is, an insoluble oxychlonde or soluble ferric hydroxide being produced according to the concentration of the liquid [3]

The solutions of ferrous and ferric chlorides have long been used in medicine An alcoholic solution of ferric chloride was formerly employed as a quack medicine of repute, known by the name of Lamotte's golden drops This solution loses its colour when exposed to light,[4] ferrous chloride being formed, the latter compound separating, when the solution is not too dilute, in fine green crystals, $FeCl_2,2H_{20}$ Dilute solutions of ferric chloride in ether are reduced to ferrous chloride almost iminediately on exposure to sunlight, the chlorine attacking the ether Concentrated solutions are reduced more slowly, and a black orgamc compound containing iron is also formed [5]

Ferric chloride forms garnet-red, crystalline double salts with the chlorides of the metals of the magnesium and alkali groups, such as$FeCl_3,MgCl_2,H_{20}$, $FeCl_3,2KCl,H_{20}$, and $FeCl_3,2NH_4Cl,H_{20}$ These are decomposed by water, and a mixture of the last salt with an excess of sal-ammoniac is termed iron sal-ammoniac, it was formerly obtained by sublimation of a mixture of iron oxide and ammonium chloride, and is mentioned

[1] *Zeit physikal Chem*, 1892,10, 477

[2] Sabatier, *Bull Soc chim*, 1881, [2], 36, 197, Roozeboom and Schreine makers, *Zeit physikal Chem* , 1894,**15,** 588

[3] Compare Malfitano and Michel, *Compt rend*, 1907, **145,** 187, 1275, 1908, **146,** 338, 1908, **157,** 8O3, Michel, *ibid*, 1908, **147,** 1052, 1288, Cameron and Robinson, *J Physical Chem* , 1907,**11,** 690

[4] See Benrath, *J pr Chem* , 1905, 72, 220, 1909, 8O, 283

[5] Puxeddu, *Gazz* , 1920, 5O, i, 154

by " Basil Valentine " Iron sal-ammoniac crystallises in yellow or bright red, transparent, regular crystals from a dilute solution of ferric chloride, there contain a varying amount of iron, and are very hygroscopic

Iron Oxychlondes—These compounds are formed in various ways Some are soluble whilst others are insoluble in water When freshly precipitated ferric hydroxide is added to a solution of ferric chloride, it dissolves in considerable quantity, and a dark red liquid is obtained, which, to one molecule of chloride, may contain twenty or more molecules of oxide, and this on dialysis furnishes Graham's soluble oxide These solutions may be diluted or warmed without any precipitation of ferric oxide Many acids and salts, however, precipitate either ferric hydroxide or a basic chloride from these solutions, which latter is again soluble in water If ferric chloride be incompletely precipitated with alkalis, a precipitate is obtained which is soluble in water w by the formula $FeCl_3,5Fe(OH)_3$

Insoluble basic ferric chlorides are formed, in the first place, by the oxidation of ferrous chloride in the air, secondly, by roasting iron in the presence of hydrochloric acid or a chloride, and, thirdly, by boiling a solution of ferric chloride for some time The composition and colour of these salts vary according to the mode of preparation They are generally sparingly soluble in hydrochloric acid

Ferrous Bromide, $FeBr_2$—When bromine vapour is passed over iron heated to dull redness, heat is evolved, and a yellowish, crystalline deposit of ferrous bromide is formed (Liebig) It readily absorbs ammonia, yielding a hexammoniate, $FeBr_2,6NH_3$, which, on warming, dissociates, yielding a di- and then a mon-ammoniate[1] An aqueous solution of ferrous bromide can easily be obtained by dissolving iroft. in hydrobromic acid, on crystallising, bluish-green, rhombic tablets are deposited, having the composition $FeBr_2,6H_{20}$ (Lowig)

Ferric Bromide, $FeBr_3$ —This is obtained in the form of dark red crystals by heating iron in an excess of bromine vapour When heated in absence of air it fuses, and a part may be sublimed without decomposition, another portion, however, being decomposed into ferrous bromide and free bromine The bromide deliquesces on exposure to air, and the solution, which may be simply obtained by dissolving the hydroxide in hydrobromic

[1] **Ephraim, *Ber*, 1912, 45, 1322**

acid, decomposes on evaporation, with formation of insoluble basic bromides By concentrating the solution over sulphuric acid, however, dark green needles of the hexahydrate, $FeBr_3,6H_{20}$, are obtained Like the chloride, the solution of the bromide dissolves feme hydroxide readily with formation of soluble oxybromides It forms double salts with certain of the alkali bromides

An unstable ferric chlorobromide, $FeCl_2Br$, is formed by the direct union of ferrous chloride and bromine [1]

Ferrous Iodide, FeI_2, is obtained by triturating iodine with a slight excess of iron filings, or by heating the latter in a covered porcelain crucible to redness, small quantities of iodine being gradually added, as soon as the whole mass becomes red-hot, a large quantity of iodine is thrown in, and the crucible is heated until iodine vapour ceases to be given off On allowing the crucible to cool it is found that a further evolution of iodine vapour takes place, probably owing to the fact that the fused mass contains an unstable ferric iodide, which decomposes on cooling The solid residue is a grey lamino-crystalhne mass, which melts at 177° [2] If a mixture of iodine and iron filings be warmed with water, these elements combine with evolution of heat, and a colourless aqueous solution of ferrous iodide is obtained, which on exposure to the air oxidises readily with separation of iodine This decomposition is prevented by the addition of sugar Ferrous iodide crystallises with $5H_{20}$ The anhydrous salt absorbs ammonia, giving a hexammoniate, $FeI_2,6NH_3$, which dissociates, yielding the diammoniate on heating [3]

Ferrous Perchlorate, $Fe(C10_4)_2,6H_{20}$, is the only iron salt of the oxy-acids of chlorine which is stable in the solid state It is obtained by the double decomposition of ferrous sulphate and barium perchlorate (Serullas), or by dissolving iron in dilute perchloric acid (Roscoe) It forms pale green deliquescent crystals, which give off water at 100°, and decompose at a higher temperature

[1] Lenormand, *Compt rend*, 1893, **116,** 820
[2] Wanklyn and Canus, *Annalen*, 1861,**120,** 69
[3] Biltz and Huttig, *Zett anorg Chem*, 1919,**100,** 89

IRON AND SULPHUR

565 *Iron SubsulphMe,* Fe_4S_3, is formed when iron is heated in the vapour of carbon disulphide, as a crystalline mass of specific gravity 6 957 It dissolves in dilute acids with evolution of hydrogen and sulphuretted hydrogen [1]

Iron Monosulphide, or *Ferrous Sulphide,* FeS, occurs as troilite in small quantities in many meteorites, and is formed readily by the direct union of the elements Iron wire burns in sulphur penetrates red-hot wrought iron and steel, but not cast iron, with formation of the molten sulphide [2] In order to prepare this substance a mixture of three parts of iron filings and two parts of sulphur is thrown gradually into a red-hot crucible The porous black mass obtained melts at a higher temperature, with separation of sulphur, if any higher sulphides have been formed, but as a rule the artificial sulphide contains an excess of iron, and this is removed by heating with excess of sulphur For the preparation of the monosulphide, Berzelius recominends Gahn's process, namely, stirring a white-hot rod of iron in molten sulphur The sulphide which is formed fuses and falls to the bottom of the crucible The operation is continued as long as any free sulphur remains

Pure monosulphide of iron is a yellowish, crystalline mass having a metallic lustre, and melting at 1300° [3] It has a specific gravity of 4 69, is not magnetic, and does not lose sulphur when lgnited in an atmosphere of hydrogen, or when raised to a white heat in the absence of air It is readily decomposed by hydrochloric and dilute sulphuric acids, forming sulphuretted hydrogen, and is used as a source of this gas in the laboratory As the sulphide usually contains free iron, the gas thus produced is always contaminated with hydrogen When heated in the air it oxidises, being converted partly into ferrous sulphate, whilst at a high temperature sulphur dioxide and ferric oxide are formed It is also oxidised when heated in steam, magnetic oxide being produced and hydrogen and hydrogen sulphide liberated

$$3FeS + 4H_aO = Fe_3O_4 + 3H_2S + H_2$$

[1] Gautier and Hallopeau, *Compt rend* , 1889,**108,** 8O6
[2] Evain, *Ann Chim Phys* , 1824, [2], 25, 106
[3] Treitschke and Tammann, *Zeit anorg chem,* 1906, 49, 320 Compare Allen, Crenshaw, Johnston, and Larsen, *Amer J Sci,* 1912, 33, 169

Ammonium sulphide precipitates ferrous sulphide from solutions of ferrous salts as a black, amorphous, hydrated mass. It is not precipitated from a neutral solution of a ferrous salt owing to the formation of acid, in which it is soluble,

$$FeSO_4 + H_2S \quad FeS + H_2SO_4$$

So sensitive is the equilibrium that ferrous sulphide has been suggested as an indicator in acidimetry A small crystal of ferrous ammomum sulphate is added to the liquid to be titrated and hydrogen sulphide is bubbled through it If the solution is alkaline, it becomes black owing to the formation of ferrous sulphide On the addition of acid, the black colour disappears iminediately the alkali is neutralised It is as sensitive as phenolphthalem or methyl-orange, and is particularly useful when dealing with coloured liquids or working in a bad light[1] By the addition of a salt of a weak acid, for example, sodium acetate, to a solution of a ferrous salt, the lomsation of the strong acid may be so depressed that ferrous sulphide is precipitated on passing hydrogen sulphide

Ferrous sulphide forms double sulphides[2] Some of these occur in nature, for example, magnetic pyrites, $5FeS,Fe_2S_3$, pentlandite, 2FeS,NiS, and marmatite, FeS,4ZnS

If seven parts of iron filings and four parts of sulphur are rubbed up to a paste with water, a black sulphide is produced with evolution of heat In this form it oxidises very quickly in the air with rise of temperature which, when the mixture is in large quantity, may lead to incandescence Hence, according to Lemery, artificial volcanoes may be formed if several pounds of the above mixture be buried in the earth The black, amorphous sulphide is formed also by the reduction of ferric oxide or its salts in presence of sulphates and decomposing orgamc matter This is the cause of the black deposit found in drains, as well as in the excrement, when iron is used as a medicine

Iron Sesquisulphide, or *Ferric Sulphide,* Fe_2S_3, does not occur pure in the mineral kingdom, but probably forms a constituent of magnetic pyrites and copper pyrites It is obtained by the action of ammonium sulphide solution on a solution of a ferric salt, so long as alkali is in excess,[3] but if the ferric salt be in ex-

[1] **Houben,** ***Ber,*** **1919, 52, [J8]f 1613**

[2] **See Houdard,** ***Compt rend,*** **1907, 144, 8O1, Bornemann and Schreyer,** ***Metallurgie,*** **1909, 6, 619, Rohl,** ***Iron Steel Inst Carnegie Mem,*** **1912, 4, 28, Horsch,** ***Bull Soc chim*** **, 1920, [4], 27, 777**

[3] **See Stokes,** ***J Amer Chem Soc,*** **1907, 29, 3O4, Malfatti,** ***Zeit cmal Chem,*** **1908,49,133**

cess a mixture of ferpous sulphide and sulphur is formed It is produced also by the action of sulphuretted hydrogen on moist ferric hydroxide or ferric hydroxide suspended in water The product is a black mass which, when moist in absence of air, is transformed into a mixture of the disulphide and ferrous sulphide,

$$Fe_aS_8 = FeS + FeS_2.$$

This reaction occurs in the presence of excess of hydrogen sulphide and takes about a week at ordinary temperatures, but only a few hours at 6O° It is prevented by the presence of a small quantity of alkali in the absence of air Exposed to air in the presence of alkali, the mass becomes light yellow in colour, sulphur being deposited[1] Since coal-gas always contains small quantities of ammonia, ferric sulphide is the chief product formed in its purifi

In the dry way, it is formed by gently heating sulphur and iron together, as well as by the action of sulphuretted hydrogen on ferric oxide at a temperature not above 100° The sulphide obtained at a red heat forms a yellow, non-magnetic mass which has a specific gravity of 4 4, and is decomposed by dilute hydrochloric acid into sulphuretted hydrogen, ferrous sulphate, and iron disulphide Iron sesquisulphide forms compounds with the other sulphides[3]

Potassium Ferric Sulphide, $K_2Fe_2S_4$, is obtained when iron filings, sulphur, and potassium carbonate are heated together, and the residue is extracted with water The purple-coloured, glistening, needle-shaped crystals thus obtained have a specific gravity of 2 863, and burn when heated in the air, but when lgnited in a current of hydrogen are converted without change of form mto the black compound, $K_2Fe_2S_3$

Sodium Ferric Sulphide, $Na_2Fe_2S_4,4H_2O$, is obtained in a similar way and forms brown, microscopic needles It is also formed by the addition of a ferric salt to sodium sulphide solution or by the action of the excess of sodium polysulphide on a ferrous salt in solution[4] It is found in the " black ash " liquors obtained in the manufacture of soda by the Leblanc process

Silver Ferric Sulphide, $Ag_2Fc_2S_4$, is a dark brownish-black,

[1] Rodt, *Zeit angew Ghent,* 1916, 29, i, 422, Mecklenburg and Rodt, *Zeit anorg Chem,* 1918,**102,** 13O

[2] Gedel, *J fur Gasbeleuchtung,* 1905, **48,** 400, Stokes, *loc cit*

[3] Schneider, *Pogg Ann,* 1869, **186,** 46O, Preis, *J pr Chem,* 1869, **107,** 10, Maliatti, *Zeit anal chem,* 1909, **48,** 352

[4] Mecklenburg and Rodt, *he cit*

crystalline powder obtained by the action of silver nitrate solution on the potassium compound

Cuprous Ferric Sulphide, Cu_2S,Fe_2S_3, occurs as the mineral copper pyrites It may be made by shaking an ammoniacal solution of cuprous chloride with potassium feme sulphide until all the copper has been precipitated.

Magnetic pyrites or *pyrrhotite* may be regarded as a compound of the mono- and sesqui-sulphides, but is probably not a definite compound but a solid solution of sulphur in ferrous sulphide[1] Its composition varies between $5FeS,Fe_2S_3$ and $6FeS,Fe_2S_3$ It crystallises in hexagonal plates, usually, however, occurring in the massive state, having a brownish-yellow or brassy colour, it is attracted by the magnet, sometimes being itself magnetic Its specific gravity vanes from 4 4 to 4 7, and it frequently contains as much as 5 5 per cent of nickel, the latter metal being obtained in Canada from this source in considerable quantities

Iron Disulphide, FeS_2, occurs very widely distributed as iron pyrites This mineral was known in early times, but was not distinguished from copper pyrites, both being known under the name of *TrvpiTqs* Agricola considered these as two varieties of the same mineral

Iron pyrites is found in all geological formations, it crystallises usually in cubes or pentagonal dodecahedra,[2] but occurs also in many ot no fewer than sixty-nine different forms having been described It is frequently found in spherical, botryoidal, or stalactitic masses, being formed by the action of orgamc matter on water which contains iron sulphate in solution Hence it is frequently found in peat and coal in crystalline masses often possessing the form of the original organic matter, such as wood, roots, etc It is likewise found in chalk cliffs, in similar concretionary forms In the pure state, iron pyrites has a brass-yellow colour, and a specific gravity of 5 185 It is very hard, giving sparks when struck with steel, for which purpose it was formerly employed

Iron disulphide occurs also as marcasite forming bright brass-coloured, rhombic crystals with a specific gravity of 4 68 to 4 85 This is also widely diffused, and occurs in various forms, especially in lignite b and is therefore also known as white iron pyrites The fracture exhibits a fibrous structure radiating from a point, hence the name

[1] **Allen, Crenshaw, Johnston, and Larsen,** ***Amer J Set,*** **1912, [4], 33, 169**
[2] **See Posohl,** ***Zeit Kryst Mm*** **, 1911, 48, 572**

radiated pyrites, which is also applied to the mineral Whereas iron pyrites is quite permanent m the air, marcasite is oxidised to ferrous sulphate and becomes disintegrated When heated to between 400° and 500°, marcasite is slowly transformed into pyrites and the change is not reversible In order to account for the differences in properties between pyrites and marcasite, the following constitutions have been suggested for them [1]



Iron disulphide may be obtained artificially by gently heating the monosulphide with sulphur, or by passing sulphuretted hydrogen over the oxides or chlorides of iron heated to redness It is also produced by boiling precipitated ferrous sulphide with flowers of sulphur or by adding sodium tnsulphide slowly to a boiling solution of ferrous sulphate when sulphur is also liberated [2] When an intimate mixture of ferric oxide, sulphur, and sal-ammomac is heated slowly above the temperature at which the latter compound volatilises, the disulphide is obtained in small, brass-yellow octahedra and cubes (Wohler) Crystalline pyrites is formed also when carbon disulphide vapour acts upon ferric oxide (Schlagdenhauffen), and when ferric chloride is heated with phosphorus pentasulphide [3] Iron pyrites and marcasite may be produced artificially also by the action of hydrogen sulphide on ferric sulphate solution [4] Iron disulphide is not magnetic, and is not attacked by dilute acids or sulphuric acid, but readily dissolves in nitnc acid with separation of sulphur There is some evidence showing that the iron in iron pyrites is in the ferrous condition [5]

Ferrous Sulphte, $FeSO_3$ —When iron is dissolved in aqueous sulphurous acid in absence of air, no gas is evolved, and the solution contains ferrous sulphite and ferrous thiosulphate

$$2Fe + 3H_2SO_3 = FeSO_3 + FeS_2O_3 + 3H_2O$$

The latter salt is a very soluble one, the first, however, is only slightly soluble, so that after a short time it is deposited in colourless or greenish crystals Ferrous sulphite is also produced

[1] Arbeiter, *Chem Zentr* , **1913, l, 1933**
[2] Rodt, *Zeit angew Chem,* **1916, 29, i, 422**
[3] **Glatzel, *Ber,* 1890, 23, 37**
[4] **Allen, *J*** *Washington Acad Sci,* **1911,1, 170**
[5] Benedek, *Zeit Kryst Min,* **1910, 48, 447, Plummer, *J Amer*** *Chem Soc* , **1911,33, 1487**

by passing sulphur dioxide into a suspension of freshly precipitated ferrous sulphide[1] The sulphide is dissolved and the sulphite separates out

$$FeS + SO_2 + H_{2}O = FeSO_3 + H_2S$$

A solution of ferrous sulphite becomes red on exposure to the air owing to oxidation[2]

Ferric hydroxide dissolves in sulphurous acid to give a yellow solution which probably contains ferric sulphite, but this compound has not been isolated The solution rapidly changes colour from yellow to green, owing to reduction of the ferric sulphite to ferrous sulphite and dithionate[3]

$$Fe_2(SO_3)_3\text{-}FeSO_3 + FeS_2O_6$$

Ferrous Sulphate, or *Green Vitriol,* $FeSO_4,7H_2O$, was probably used by Geber Agricola, in his discourse *De Re Metallica,* mentions two kinds of pyrites The one, such as coal-brasses, decomposes spontaneously and yields a vitriol, whilst the other, as the ordinary Mason's pyrites, does so only when it is roasted Its preparation by dissolving iron in sulphuric acid was described by " Basil Valentine " in his *Treatise on Natural and Supernatural Things "* Take oleum vitrioli, dissolve therein *mars,* and prepare a vitriol from it " In his last volume he describes the method for preparing sulphide of iron and for obtaining vitriol from it " *Limaturam fern* and *sulphur and* calcined in a potter's furnace until it becomes tinted purple, then pour upon this distilled water, when a fine green liquid is formed Draw this off *ad tertias,* allow it to deposit, and thus obtain an artificial vitriol " Green vitriol occurs as the mineral melanterite, either crystalline or in fibrous stalactitic forms, but generally massive and pulverulent It is usually derived from the decomposition of pyrites or marcasite Ferrous sulphate is likewise frequently found in solution in drainage water from mines, and it is manufactured on a large scale from this source Large quantities of green vitriol (about 100 tons per week) are manufactured in South Lancashire from the pyrites occurring in the coal measures These are piled up in heaps and exposed to the atmosphere The soluble ferrous sulphate, together with the excess of sulphuric acid formed, runs into underground tanks,

[1] **Henderson and Weiser, *J Amer Ckem Soc* , 1913, 35, 239**
[2] **Seubert and Elten, *Zeit anorg Ckem* , 1893, 4, 44**
[3] **Carpenter, *Journ Ghem Soc* , 1902, 81, 1**

where the excess of acjd is removed by means of scrap iron On evaporating the liquor l#ge crystals of ferrous sulphate are obtained Ferrous sulphate is formed also as a by-product in the manufacture of copper sulphate or blue vitriol (p 449) The cominercial salt not infrequently contains traces of copper sulphate, and this may be detected and separated, as was pointed out by Vigam, so long ago as 1683, by leaving the solution in contact with metallic iron until the whole of the copper is precipitated Another common impurity is ferric sulphate, this may be removed by recrystalhsation, but zinc sulphate, manganese sulphate, and other salts cannot thus be got rid of Hence when chemically pure ferrous sulphate is needed it is best to treat an excess of iron wire with dilute sulphuric acid When the evolution of hydrogen has ceased, the liquid is boiled together with the undissolved portion of the wire, filtered, and crystallised

Ferrous sulphate forms well-defined monoclmic crystals with a specific gravity of 1 889 at 4° (Joule and Playfair), but is dimorphous, often crystallising in rhombic prisms, which are isomorphous with zinc sulphate These are obtained when a crystal of zinc sulphate is thrown into a supersaturated solution of the ferrous salt, but, on the other hand, if a crystal of copper sulphate be employed, tnclimc crystals are obtained having the composition $FeSO_4,5H_{20}$ and isomorphous with copper sulphate (Lecoq de Boisbaudran) When ferrous sulphate is heated in a vacuum to 140°, it yields a white powder of the monohydrate, $FeSO_4,H_{20}$, and this, when gently heated in absence of air, yields the anhydrous salt, $FeSO_4$ Exposed to the air, the cominercial heptahydrate gradually loses water and becomes converted into basic ferric sulphate, but the pure dry salt is quite stable and does not effloresce or oxidise [1]

Up to 100° there are three hydrates which are successively in stable equ heptahydrate, stable from —1 82° (the eutectic point) to 56 6°, the tetrahydrate, from 56 6° to 64 4°, and the monohydrate, above the latter temperature [2] The solubility at various temperatures, in grams of anhydrous ferrous sulphate per 100 grams of saturated solution, is as follows

O°	10°	20°	40°	54°	64°	77°	90°
13 5	17 0	210	28 7	34 3	35 7	315	27 2

[1] De Forcrand, *Compt rend*, 1914,**168,** 20
[2] Franckel, *Zett anorg Chem*, 1907, 55, 223

In addition to those already mentioned, hydrates with $6H_2O$, $3H_2O$, and $2H_2O$ have been described.

Ferrous sulphate is insoluble in concentrated sulphuric acid and absolute alcohol, and the addition of strong sulphuric acid to a saturated solution of the salt causes the precipitation of the monohydrate[1] A solution of ferrous sulphate, like the chloride, absorbs nitric oxide The dark brown saturated solution, which probably contains the compound $FeSO_4,NO$ (p 1293), gives off the gas in a vacuum as well as when heated, in the latter case small quantities of nitrogen monoxide and ferric sulphate are formed When the brown solution is mixed with strong sulphuric acid, keeping the mixture cool, it becomes purple-red, upon this reaction the well-known test for nitric acid and the nitrates depends, as well as the method of detecting the presence of nitrous fumes in sulphuric acid

By treating a concentrated solution of ferrous sulphate with chlorine and allowing to evaporate the substance $FeSO_4Cl,6H_2O$ is obtained It may also be prepared by heating a mixture of ferric chloride and ferric sulphate[2]

Ferrous sulphate solution is readily oxidised by oxygen or air, and the rate of oxidation is proportional to the partial pressure of the oxygen[3] The presence of inert salts reduces the rate owing to the decreased solubility of oxygen in the solution[4] Potassium permanganate and dichromate also readily oxidise ferrous sulphate solution, and titration with solutions of these salts affords a rapid and convenient method of estimating iron The reducing power of ferrous sulphate is utilised in photography, where, in the process of "toning" ferrous sulphate is used to precipitate gold from gold chloride

$$AuCl_3 + 3FeSO_4 = FeCl_3 + Fe_2(SO_4)_3 + Au$$

Green vitriol is largely used in the arts and manufactures for the preparation of iron mordants, inks, Prussian blue, etc

Ferrous sulphate enters into the composition of various double salts There are, for instance, the red and yellow substances formed when sulphuric acid acts on a concentrated mixed solution of ferrous sulphate and copper sulphate[5] Again,

[1] Compare Kennok, *J Physical Ghent*, 1908, 12, 693, Wirth, *Zeit anorg Chem* , 1913, 79, 36O, Florentin, *Bull Soc chim* , 1913, [4], 13, 362

[2] Rohm, *Collegium*, 1921, **614,** 282.

[3] Ennos, *Proc Camb Phil Soc*, 1913,17, 182

[4] MaoArthur, *J Physical Chem* , 1916, 20, 645

[5] fitard, *Compt rend*, 1878,87, 6O2, Scott, *Journ Chem Soc* , 1897,71, 564, Allmand, *Zeit anorg Chem*, 1909,**61,** 202

ferrous sulphate, like the sulphates of the metals of the magnesium group, copper, and manganese, forms crystalline double salts, with the sulp^ptes of the alkali metals, of these the following is the most important

Ferrous Ammonium Sulphate or *Mohr's Salt,*

$$FeSO_4,(NH_4)_2SO_4,6H_{20},$$

is obtained when the calculated quantities of ammonium sulphate and green vitriol are dissolved in the minimum quantity of hot water, and the filtered solution is allowed to crystallise or is precipitated with alcohol It forms clear, hard, bluish-green, monochnic crystals, which have a specific gravity of 1 813 One hundred parts of water dissolve (Tobler)

At	O°	20°	3O°	6O°	75°
$FeSO_4,(NH_4)_2SO_4$	12 2	216	28 1	44 6	56 7

This salt is a very stable one, and does not readily undergo alteration in the air, being much less easily oxidised than green vitriol itself Hence it is largely used instead of the latter salt for the purposes of volumetric analysis The double sulphates of ferrous sulphate with those of the alkali metals are prepared in a similar manner and are all isomorphous [1]

Ferrous Disulphate, FeS_{207}, separates out as a white powder when a concentrated solution of ferrous sulphate is mixed with several times its volume of concentrated sulphuric acid It forms microscopic prisms, and is decomposed by water into sulphuric acid and green vitriol [2]

Ferric Sulphate, $Fe_2(SO_4)_3$, is obtained by the action of nitric acid on a hot solution of green vitriol to which the requisite quantity of sulphuric acid has been added

$$6FeSO_4 + 3H_2SO_4 + 2HNO_3 = 3Fe_2(SO_4)_3 + 2NO + 4H_{20}$$

The yellowish-brown solution gives a syrupy liquid when concentrated, from which colourless crystals are deposited on standing When these are heated, or when sulphuric acid is added to the concentrated solution, the anhydrous salt is formed as a white powder, which dissolves slowly in water, whilst by the action of green vitriol on boiling sulphuric acid the same salt is deposited in small, crystalline scales or rhombic prisms

$$2FeSO_4 + 2H_2SO_4 = Fe_2(SO_4)_3 + SO_2 + 2H_{20}$$

Various hydrates also have been described [3]

[1] **Tutton,** ***Proc Roy Soc,*** **1913,** ***[A*** **88, 361**
[2] **Bolas,** ***Journ Chem Soc,*** **1874, 27, 212**
[3] **Reooura,** ***Compt rend,*** **1905,141, 108, 1907,144, 1427**

When a dilute solution of feme sulphate is boiled or incompletely precipitated with alkalis, or when a solution of green vitriol is allowed to oxidise in the air, various basic ferric sulphates are formed[1] An iron mordant obtained by oxidising green vitriol with nitric acid deposits on standing large, transparent crystals, which are probably monochnic, having the composition $FeSO_4(OH),7H_{20}$, these are decomposed by water with formation of the insoluble salt, $Fe_2SO_4(OH)_4,5H_{20}$ [2] Various other basic ferric sulphates occur as minerals,[3] being formed by the oxidation of the sulphides of iron Amongst these may be mentioned vitriol ochre, $FeSO_4(OH)_4,2Fe(OH)_3,H_{20}$ This frequently occurs in long, brown, green, or ochreous yellow stalactites, whilst copiapite, $Fe_2(SO_4)_3Fe_2(SO_4)_2(OH)_2,10H_{20}$, occurs in sulphur-yellow tablets or crystalline scales, and fibro-ferrite, $2Fe_2(SO_4)_2(OH)_2,Fe_2SO_4(OH)_4)24H_{20}$, forms a pale yellow or nearly white pearly or silky mass

Anhydrous ferric sulphate, when heated, dissociates into ferric oxide and sulphur trioxide This fact is of importance in connection with the use of ferric oxide as a catalyst in the contact process of manufacturing sulphuric acid [4]

Ferroso-femc Sulphates—The two sulphates of iron form various double salts, of which some are found in the mineral kingdom Amongst these is roemente, $Fe_3(SO_4)_4,12H_{20}$, yellow, monochnic crystals, occurring at the Raminelsberg mine, near Goslar, with another similar mineral termed voltaite, in

which a part of the iron is replaced by isomorphous metals

Ferric Potassium Sulphate, $Fe_2(SO_4)_3,K_2SO_4,24H_{20}$, or *Iron Alum,* is obtained when the proper quantity of potassium sulphate is added to a solution of ferric sulphate and the concentrated solution allowed to stand for some days about O° The salt forms bright violet octahedra, and dissolves in about five parts of cold water If caustic potash is added to the solution and the dark liquid allowed to evaporate, transparent, yellowish-brown, hexagonal crystals separate out which have

[1] Compare Cameron and Robinson, *J Physical Chem,* 1907, 11, 641, Applebey and Wilkes, *Journ Chem Soc* 1921,121, 337, Posnjak and Merwm, *J Amer Chem Soc* , 1922, 44, 1965

[2] *Ber* , 1875, 8, 771

[3] See Schamer, *Zeit Kryst Min,* 1907, 43, 113, 1909, 46, 427,1913, 52, 372, Wirth and Bakke, *Zeit anorg Chem* , 1914, 87, 13

[4] Keppeler and D'Ans, *Zeit physikal Chem* , 1908, 62, 89, Wohler, Pluddemann, and Wohler, *Ber* , 1908, 41, 7O3, *ibid* , 1908, 62, 641, Bodenstein and Suzuki, *Zeit Elektrochem* , 1910,16, 912

the composition $5K_2SO_4,2Fe_2(SO_4)_2(OH)_2,16H_{20}$, and possess the peculiar optical properties of tourmaline This salt easily decomposes into iron slum and an insoluble basic ferric salt

Feme Ammonium Alum, $Fe_2(SO_4)_3,(NH_4)_2SO_4,24H_{20}$, closely resembles the potassium derivative, and is sometimes termed " iron alum " It is hydrolysed in solution, a basic iron sulphate, $2Fe_{203},SO_3$, being precipitated[1] Several other double salts of feme and ammonium sulphates have been described[2]

IRON AND THE ELEMENTS OF THE NITROGEN GROUP

566 *Iron Nitrides* —When nitrogen is passed over heated iron, the metal is rendered brittle, probably owing to the alternate formation and decomposition of an iron nitride, but the latter compound cannot be prepared in this manner[3] The nitride may, however, be obtained by heating the metal in ammonia, as shown by Berthelot and confirmed by Stahlschmidt[4]

If ammonia in excess is allowed to act on anhydrous ferrous chloride or bromide, or on finely divided reduced iron, or on iron amalgam at a temperature of about 420°, iron mtnde is obtained as a dull grey powder[5] In the compact state, it is best obtained by heating iron wire or rod to a bright red heat with a large excess of ammonia, excess being necessary inasmuch as the hydrogen formed reduces iron mtnde at the same temperature as that at which it is produced[6]

The substance has a composition corresponding with the empirical formula Fe_2N, and is so brittle that it may be readily powdered in a mortar, it is somewhat magnetic, and has a specific gravity of 6 O-6 5 It begins to evolve mtrogen at 500° and the decomposition is rapid at 600°[7] It readily oxidises when heated in the air, and lgmtes when warmed in chlorine It is dissolved by dilute hydrochloric and sulphuric acids with evolution of hydrogen, and formation of ferrous and ammonium salts

[1] See Rae, *Journ Chem Soc* , 1916,**109,** 1331

[2] Lachoud and Lepierre, *Compt rend* , 1892,**114,** 915

[3] See Maxted, *J Soc Chem Ind,* 1918, 37,105

[4] *Pogg Ann* , 1865,125, 37

[5] Fowler, *Journ Chem Soc* , 1901,79,285, White and Kirschbraun, *J Amer Soc* , 1906, 28, 1343, Girardet, *Bull Soc chtin,* 1910, 7, 1028 Charpy Various Wnerot, *Compt rend,* 1914,**158,** 944, Noyes and Smith, *J Amer Chem* , 1921, 43, 475

[6] Beilby and Henderson, *Journ Chem Soc* , 1901, 79, 1249

[7] Maxted, *he cit* , Charpy and Bonnerot, *he cit*

According to Guntz,[1] *ferrous nitride,* $Fe^{\wedge}S_{2i}$ and *ferric nitride,* FeN, both of which are black powders and differ from the foregoing, are formed by heating lithium nitride with ferrous potassium chloride and ferric potassium chloride respectively A substance of the formula Fe_5N_2 was found by Silvestn[2] as a lustrous, metallic deposit on the Etna lavas This may be a mixture or solid solution of iron and the mtnde, Fe_2N

Ferrous Nitrate, $Fe(NO_3)_2,6H_{20}$, is best obtained by the decomposition of green vitriol with barium nitrate, the filtrate being evaporated in a vacuum over sulphuric acid It is very soluble in water and very unstable, easily passing into ferric nitrate When iron is dissolved in cold dilute nitric acid, the following reaction takes place (Berzelms)

$$8Fe + 20HNO3 = 8Fe(NO_3)_2 + 2NH_4NO_3 + 6H_{20},$$

but the reaction varies greatly with the concentration of the acid and the temperature [3]

Ferric Nitrate, $Fe(NO_3)_3$, is formed by dissolving iron in nitric acid The brown concentrated solution deposits, on addition of nitric acid, according to the acidity and the concentration of the solution, colourless cubes of $Fe(NO_3)_3,6H_{20}$, or colourless, monochnic crystals containing 9 molecules of water [4] These are very deliquescent, and dissolve in water, forming a brown liquid, which becomes colourless when concentrated nitric acid is added to it Ferric nitrate is used as a mordant in dyeing and calico printing

Several basic ferric nitrates, soluble and insoluble, are known

Nitroso-compounds of Iron—As already mentioned, nitric oxide is readily absorbed by solutions of ferrous salts with formation of dark olive-green to black solutions, which contain unstable compounds of nitric oxide with the ferrous salt The maximum absorption for solutions of ferrous salts in water, alcohol, and other neutral solvents is found to be in the proportion of 1 mol NO to 1 mol ferrous salt The reaction, however, is reversible, the degree of dissociation not only varying with different ferrous salts, but being dependent also on the pressure, the temperature, the concentration of ferrous salt, the solvent, and the presence of other dissolved substances [5] When

[1] *Compt rend* , 1902,**135,** 738 [2] *Pogg Ann* , 1876,**157,** 165
[3] Montemartini, *Journ Chem Soc* , 1892, **32,** 1278
[4] See Cameron and Robinson, *J Physical Chem* , 1909,**13,** 251
[5] Manchot and Zechentinayer, *Annalen,* 1906, **35O,** 368, Manchot and Huttner, *ibid,* 1910, **372,** 153

dissolved in strong hydrochloric acid, ferrous chloride absorbs about twice as much nitric oxide as when dissolved in the same quantity of water.

Anhydrous ferric chloride also absorbs nitric oxide, forming the compounds $2FeCl_3,NO$ and $4FeCl_8,NO$, which are reddish-brown, non-crystalhne, hygroscopic powders When nitric oxide is passed into an ethereal solution of ferric chloride, nitrosyl chloride is formed, and on evaporation over sulphuric acid, black needles of the composition $FeCl_2,NO,2H_{20}$ are obtained, whilst at 6O° the anhydrous compound, $FeCl_2,NO$, is formed crystallising in yellow needles [2]

In addition to the foregoing unstable nitroso-denvatives others of a more stable nature have been prepared These were discovered by Roussin,[3] who prepared them by the action of ferrous sulphate on mixed solutions of the mtntes and sulphides of the alkahs, and they have since been investigated by many other chemists[4] Their exact constitution has not yet been determined, but they are closely allied to the ferrocyanides and similar compounds, and consist of salts of complex acids containing both the iron and nitroso-groups in the acid radical Two classes of salts have been prepared, viz , the *ferrodimtroso*-denvatives, such as the salt $K[Fe(NO)_2S]$, and the *ferrohepfa*-mtfroso-derivatives, such as the salt $K[Fe_4(NO)_7S_3]$

Potassium Ferrodinitrososulphide, $K[Fe(NO)_2S],2H_{20}$, is obtained by the action of potash on the heptamtrososulphide [5] It forms dark red crystals, insoluble in water, and decomposes violently when heated, yielding, among other products, potassium and ammomum sulphates By the action of sulphuric acid, it yields the free *acid,* $H[Fe(NO)_2S]$, which slowly decomposes in the cold into sulphuretted hydrogen, nitrogen, mtrous oxide, and the heptamtroso-acid

The corresponding salts of the other alkahs,[6] and in addition the crystalhne *ethyl* and *phenyl* derivatives, $C_2H_5[Fe(NO)_2S]$ and $C_6H_5[Fe(NO)_2S]$, are known

[1] Kohlschutter and Kutscheroff, *Ber* , 1907, 40, 873

[2] Thomas, *Compt rend* , 1895,**120,** 447

[3] Roussin, *ibid* , 1858, 48, 224

[4] Porczinsky, *Annalen,* 1863, **125,** 3O2, Rosenberg, *Ber,* 4879, 3, 312, Pavel, *ibid,* 1882,**15,** 2600, Marchlewski and Sachs, *Zeit anorg Chem* , 1892, 2, 175, Hofmann and Wiede, *ibid* , 1895, 8, 318, 1895, 9, 295, 1896,**11,** 281, Marie and Marquis, *Compt rend* , 1896,**122,** 137

[5] Pavel, *Ber,* 1882, **15,** 2600, Rosenberg, *Arkw Kem Min Geol,* 1911, 4, [3] 1

[6] Roussin, *Compt rend* , 1858, 46, 224

Potassium Ferrodimtrosothiosulphate, $K[Fe(NO)_2S_2O_3],H_2O$, is made by passing nitric oxide into a strong solution of potassium thiosulphate and ferrous sulphate On concentration, the salt is obtained as reddish-brown crystals which are sparingly soluble in cold water The corresponding salts of the other alkalis and of ammonium are prepared in a similar manner [x]

Potassium Ferroheptanitrososulphide, $K[Fe_4(NO)_7S_3],H_2O$, is the most stable of these salts, and is obtained by adding a solution of ferrous sulphate to one of potassium nitrite and sulphide [2] It is formed also by boiling a solution of the ferrodinitrosothiosulphate, sulphur dioxide being evolved and ferric hydroxide precipitated [x] It forms dark, monochnic crystals with a diamond lustre, and is only sparingly soluble in water Dilute sulphuric acid precipitates from its solution the free *jerrohepianitrososulphhydric acid* as an amorphous, brown mass, but when the salt is heated with concentrated sulphuric acid it yields nitric oxide, nitrogen, sulphuretted hydrogen, sulphur, and ferric ammonium and potassium sulphates

The corresponding salts of the other alkalis and of the alkaline earths have been obtained and also the *thallium* salt The *ammonium* salt is formed by the action of nitric oxide on freshly precipitated ferrous sulphide suspended in water, part of the nitric oxide being reduced to ammonia,[3] or by double decomposition of the sodium salt with ammomum carbonate The *ferrous* salt, $Fe[Fe_4(NO)_7S_3]_2$, is likewise prepared by double decomposition of the sodium salt with ferrous sulphate

567 *Phosphides of Iron* —In the year 178O, J C F Meyer, while examining the cause of the cold-shortness of iron, came to the conclusion that this was produced by the presence of a peculiar metal, to which he gave the name *hydrosiderum* The subject was investigated shortly afterwards by Bergman, who found that when the residue obtained by dissolving cold-short iron in sulphuric acid is fused before the blowpipe with reducing agents, a metallic bead is obtained which he also believed to be a peculiar metal, to this he gave the name of *siderum* In 1784, Meyer repeated his experiments and decided that the substance thus obtained was a compound of iron and phosphoric acid, later it was identified as a phosphide of iron

[1] **Hofmann and Wiede,** *Zeit anorg Chem* **, 1895, 8, 318, 9, 295**

[2] **Pavel,** *Ber,* **1879,12, 1407**

[3] **Hofmann and Wiede,** *loc cit* **See also** *Atti JR Accad Lincei,* **[5], 1906, 15, 11, 467, 1907, 16, 1, 654, 11, 542, 584, 658, 740, 1908, 17, 1, 202, 424, 545**

One phosphide of iron, Fe_2P, is obtained as a porous, non-magnetic powder by fusing fenous or ferric phosphate with lamp-black under a layer of sodium chloride, and in lustrous, grey crystals by fusing cuprous phosphide with 10 parts of iron filings in the electric furnace[x] When heated in the air, it is converted into a basic phosphate, $2Fe_{203},P_{205}$

The phosphide, Fe_3P, is obtained from fused mixtures of phosphorus and iron containing more than 84 4 per cent of iron, and is prepared also by fusing copper phosphide with a sufficient quantity of iron, when the compound Fe_3P, in an almost pure state, rises to the top as a separate phase [2] It has been found as small, tin-white crystals in iron from a blast furnace[8] This phosphide dissolves in concentrated hydrochloric acid, giving ferrous chloride, phosphoric acid, and pure hydrogen

When iron pyrites or iron powder is ignited in a stream of phosphme, a grey, non-magnetic powder, having the composition Fe_3P_4, is obtained, whilst the compound FeP is left as a dark-grey powder when the monosulphide is ignited in the same gas, or when iron is heated in phosphorus vapour The compound Fe_2P_3 is produced by strongly heating phosphorus and ferric chloride placed in separate boats in a tube in a current of carbon dioxide, and forms hard, metallic, non-magnetic crystals [4]

When obtained in distinct crystals, these phosphides of iron are mostly insoluble in single acids, but dissolve in a mixture of nitric and hydrofluoric acids, whilst in the loose porous state they are attacked by hot hydrochloric acid with evolution of phosphme and formation of phosphoric acid They do not undergo alteration in the air, and can be fused in all proportions with metallic iron Many other iron phosphides which have been described, and possibly some of the above, are probably in reality mixtures of a true phosphide and iron [5]

Ferrous Phosphate, $Fe_3(PO_4)_2,8H_{20}$, occurs as the mineral vivianite, crystallising in monoclimc prisms In its pure state it is colourless, but it generally possesses a green or blue tint, owing to partial oxidation. It is found also as an earthy mass

[1] Maronneau, *Compt rend*, 1900,**13O,** 656

[2] Le Chateher and Wologdine, *ibid*, 1909, **149,** 7O9 Compare Stead, *./ Iron Steel Inst*, 1900, 58, 6O, Saklatwalla, *ibid*, 1908, 77, 92, Gercke, *Metallurgie*, 1908, 5, 6O4, Konstantinoff, *J Buss Phys Chem Soc*, 1909, 4i, 1220

[3] Spencer, *Min Mag* , 1916,17, 340

[4] Granger, *Compt rend*, 1896,**122,** 936

[5] See Le Chateher and Wologdine, *loc cit* , Khun, *Chem Zeit*, 1910, **34,** 45

termed blue iron earth, sometimes dispersed through clay, and together with bog iron ore, and in the cavities in fossil bones. When a solution of green vitriol is precipitated with sodium phosphate, a white precipitate is obtained, which, however, soon becomes blue or green on exposure to air If the liquid and the precipitate are allowed to stand together for a week at a temperature of 6O-8O°, the compound is converted into small crystals which become blue on exposure to the air (Debray) The precipitated phosphate is used in medicine

The monacid salt, $FeHPO_4,H_{20}$, is prepared by dissolving iron in phosphoric acid solution An interesting derivative has been prepared by Manchot[1] When ammonium phosphate solution is added to a solution of ferrous chloride in alcohol saturated with nitric oxide, a dark brown, viscid oil is precipitated This may be solidified by placing in a freezing mixture, and on recrystallisation at low temperatures yields brown, flaky crystals having the composition $FeHPO_4$,NO and melting at 16° On exposure to air, the substance is slowly oxidised to ferric phosphate

When iron is dissolved in excess of phosphoric acid, colourless needles of the diacid salt, $Fe(H_2PO_4)_2,2H_{20}$, are deposited after some time, and these alter rapidly on exposure to air[2]

Feme Phosphates—The *normal orthophosphate,* $FePO_4,2H_{20}$, is obtained as a yellowish-white precipitate by adding ordinary sodium phosphate to normal ferric chloride It is soluble in dilute mineral acids, but not in cold acetic acid, and is slowly decomposed by water When ferric hydroxide is dissolved in orthophosphonc acid and the solution rapidly evaporated, the *diacid salt,* $Fe(H_2PO_4)_3$, is obtained as a pink, crystalline powder, which decomposes in moist air and deposits crystals of the *monacid salt,* $2FeH_3(PO_4)_2,5H_{20}$ (Erlenmeyer) *Feme metaphosphate,* $Fe(PO_3)_3$, is deposited in pink plates when ferric hydroxide is digested with glacial phosphoric acid at 100°[3] Ferric phosphate has been obtamed in the colloid state[4]

Basic iron phosphates occur in nature, and frequently form a constituent of limonite Ferric phosphate also occurs as dufrenite, $Fe_2(OH)_3PO_4$, which is found sometimes in rhombic crystals, but more generally in needles or as a radiated, fibrous mass Vivianite is often oxidised and is converted into beraunite,

[1] *Ber,* 1914, 47, 16O1

[2] Erlenmeyer, *Annalen,* 1878,**194,** 182

[3] Hautefeuille and Margotte, *Compt rend* , 1888,**106,**135 See also **Johnsson,** *Ber* , 1889, **22, 976**

[4] **Holmes and Rindfusz,** ***J*** *Amer Chem Soc* , 1916, 38, 197O

$Fe(PO_4),2Fe_2PO_4(OH)_3,4H_{20}$, occurring in small, foliated aggregates having a? hyacinth-red colour

568 *Arsenides of Iron*—When metallic iron is ignited with an excess of arsenic in the absence of air, a white and very brittle mass of FeAs is obtained The arsenide $FeAs_2$ occurs as the mineral lolhngite in silver-white, rhombic prisms It is obtained artificially by heating finely powdered iron with the vapour of arsenic under pressure [1] This artificial product, heated in a current of hydrogen, yields the arsemde FeAs as a silver-white, crystalline powder The study of the freezing points of alloys of iron and arsenic indicates the existence of other arsenides, viz —Fe_3As_2, Fe_2As, and Fe_6As_4[2] Mispickel or arsenical pyrites, FeAsS, crystallises in short, rhombic prisms of a silver-white colour, a portion of the iron is frequently replaced by cobalt, and this mineral serves as the chief source of arsenic compounds

Feme Arsemte — $Fe_{405}(OH)_5As[= 4Fe_{203},As_{203},5H_{20}]$. This basic salt is a voluminous, brown precipitate closely resembling ferric hydroxide, and is obtained by adding an aqueous solution of arsemous oxide, or an arsemte, to ferric acetate

Feme Arsenates—The normal arsenate occurs as scorodite, $Fe(AsO_4),2H_{20}$, in brown, rhombic, vitreous crystals Basic arsenates are also found in the mineral kingdom, amongst these we have iron-sinter or pharmacosidente, $3FeAsO_4,Fe(OH)_3,6H_{20}$, which occurs crystallised in the regular system in green or brownish-green, adamantine crystals The acid arsenate, $2Fe_2(HAsO_4)_3,9H_{20}$, is a white precipitate obtained by adding hydrogen disodium arsenate to a solution of ferric chloride It is easily soluble in hydrochloric acid, and separates on evaporation as a white powder Colloidal ferric arsenate has been prepared both as sol and gel[3]

IRON AND BORON

569 *Borides of Iron*—The compound FeB is formed when the vapour of boron chloride is passed over iron at a dull red heat, or when soft iron is heated with boron in the electric furnace It is thus obtained as an amorphous powder, or in yellowish-grey crystals of specific gravity 7' 15 [4] Other borides, viz, Fe_5B_2,

[1] Hilpert and Dieckmann, *Ber* , **1911, 44, 2378**
[2] Friedrich, *Metallurgie,* 1907, 4, **129**
[3] Holmes and Rindfusz, *J Amer Chem Soc* , **1916, 38, 197O**
[4] **Moissan,** *Compt rend,* **1895,18O, 173 Compare i*bid*, 1894,119, 1172**

Fe_2B, and FeB_2, have been prepared by heating reduced iron and boron in a porcelain tube in a current of hydrogen or in the electric furnace [1] These bondes of iron are oxidised by moist air, and are dissolved by hot concentrated acids

IRON AND CARBON

57O *Iron Carbide* or *tnferro carbide,* Fe_3C, occurs msteel (p 1262) and is known as cementite It is also found associated with the carbides of cobalt and nickel in meteorites as cohemte It is formed by heating together iron and carbon, and can be isolated by dissolving the excess of iron in dilute acid [2] It is a dark grey substance of specific gravity 7 4 and is very brittle It dissolves slowly in hydrochloric acid, hydrogen and hydrocaibons being evolved It is also soluble in nitric acid, giving a brown solution Comparison of the colour of such a solution produced from a given sample of steel with that obtained from a steel of known composition affords a ready method of estimating the amount of cementite in the sample Iron carbide when moist readily oxidises on exposure to air, and when heated burns, yielding the oxide

Diferro Carbide, Fe_2C —By heating together iron and carbon at a definite temperature, suddenly chilling the mass and estimating the combined carbon in the product, Euff and Goecke [3] showed that the amount of carbon which enters into combination with iron increases with temperature to a well defined maximum at 2220°, when the composition of the iron-carbon compound corresponds to Fe_2C The diminished solubility of graphite in iron above 2220° is due to dissociation of this carbide into iron and carbon Below 2220° it dissociates into cementite and carbon, while below 1837° the cementite further dissociates into iron and carbon [4]

Iron Dicarbide, FeC_2, is obtained as a pale yellow substance by heating iron with carbon and then cooling [5] It is also formed as

[1] Jassonneix, *Compt rend* , 1907, **146,** 121, *Eighth Inter Cong App Chem* , 1912, 2, 165, Hannesen, *Zett anorg Chem* , 1914, 89, 257, Tschischevsky and Herdt, *Rev Soc russe Met,* 1915,1,533 Compare Hoffmann, *Chem Zett,* 1910, 34, 1349

[2] Moissan, *Compt rend,* 1897, **124,** 716, Ruff and Gersten, *Ber,* 1912, **45,** 63 See also Hilpert and Dieckmann, *ibid* , 1915, 48, 1281

[3] *Metallurgies* 1911, 8, 417

[4] Ruff, *ibid* , 456 See alsoRunge, *Zeit anorg Chem,* 1921,**115,** 293, Honda and Murakami, *Sci Rep Tohoku Imp Univ,* 1921, 10, 273, *ibid,* **11,** 119

[5] Wittorf, *J Russ Rhys Chem Soc,* 1911, 43, 1613

a black, magnetic powder by igniting ammonium ferrocyanide or the double compound $(NH_4)_4FeCy_6,2NH_4a,3H_{20}$ On heating in air, it yields ferric oxide without any change in weight [1]

Other carbides of iron have also been described [2]

Ferrous Carbonate, $FeCO_3$, occurs naturally as spathic iron ore, which, however, contains larger or smaller quantities of the carbonates of calcium, manganese and magnesium The mineral is obtained artificially in microscopic rhombohedra by precipitating a solution of green vitriol with sodium bicarbonate and heating the mixture for twelve to thirty-six hours at a temperature of 15O° (Senarmont) When a cold solution of pure ferrous sulphate is treated with sodium carbonate, a flocculent, white precipitate is thrown down which rapidly$_t$ becomes dirty green from absorption of oxygen and evolution of carbon dioxide, and is at last converted wholly into ferric hydroxide If the precipitate is washed in total absence of air, it may be obtained pure and colourless, but usually it is a greyish powder, readily oxidised on exposure to air If the moist precipitate is mixed with sugar, it does not undergo such rapid change

Ferrous bicarbonate exists in many mineral waters, and is formed in solution by the action of carbonic acid on ferrous carbonate When such a solution is exposed to the air, carbon dioxide is evolved, and ferric hydroxide deposited A quantitative study of the rate of oxidation of ferrous bicarbonate has shown that the reaction is of the first order [3]

Ferric Carbonate is not known in the dry state, since the precipitate produced by the addition of a soluble carbonate to a ferric salt rapidly loses carbon dioxide

Ferropentacaibonyl, $Fe(CO)_5$, was first obtained by Mond, Quincke, and Langer [4] by allowing iron prepared by the reduction of ferrous oxalate to stand in contact with carbonic oxide It is evolved when the product is heated to 120°, and may be condensed in a receiver placed in a freezing mixture Dewar and Jones [5] describe it as a viscous, pale yellow liquid, which forms a yellow, crystalline solid at —20°, the latter becoming colourless at the temperature of liquid air It has a specific gravity of 1 46, and boils at 102 5 The vapour decomposes slowly below

[1] **Ljubavin,** *J Buss Phys Chem Soc* , 1912, 44, 6O9 See also Hanemann, *Zeit anorg Chem* , 1913, 84, 1

[2] Wittorf, *J Rues Phys Chem Soc,* 1911, 48, 1613

[3] Just, *Ber* , 1907, 40, 3695

[4] *Journ Chem Soc* , **1891, 59, 6O4, 1090**

[5] ***Proc Boy Soc* , *[Al* 1905, 76, 558, 1907, 79, 66**

18O°, but rapidly deposits a mirror of metallic iron above that temperature The vapour density at 129°, and the cryoscopic determination of the molecular weight in benzene solution, both agree with the molecular formula $Fe(CO)_5$ It is absorbed by metallic iron, and this may account for the slowness of the reaction between iron and carbon monoxide [1]

Ferropentacarbonyl is decomposed by chlorine, with formation of ferrous and ferric chlorides and carbomc oxide, and by concentrated nitric and sulphuric acids, the latter yielding ferrous sulphate, hydrogen, and carbomc oxide

$$Fe(CO)_5 + H_2SO_4 = FeSO_4 + 5CO + H_2$$

It is very sensitive to the action of air and moisture, quickly depositing a reddish-brown precipitate on exposure

When ferropentacarbonyl, either alone or dissolved in dry ether or light petroleum, is exposed to sunlight at the ordinary temperature, it darkens, carbomc oxide being evolved and *dtferro-nonacarbonyl,* $Fe_2(CO)_9$, formed

$$2Fe(CO)_5 =; Fe_2(CO)_9 + CO$$

The reaction however, is reversible, and ferropentacarbonyl which has been exposed to light becomes colourless on standing in the dark and no decomposition takes place when ferropentacarbonyl is exposed to light at temperatures above 6O°

Diferro-nonacarbonyl crystallises in lustrous orange, hexagonal plates which are quite stable in dry air, and have a specific gravity of 2 O85 at 18° It is practically insoluble in light petroleum and benzene, slightly soluble in alcohol and acetone, and more readily in pyridine At about 100° it decomposes

$$Fe_2(CO)_9 = Fe(CO)_5 + Fe + 4CO$$

Nitric oxide attacks it at 7O°-85°, forming a red liquid nitroso-compound [2]

$$2Fe_2(CO)_9 + NO = Fe(NO),3Fe(CO)_5 + 3CO$$

Ferrotetracarbonyly $Fe(CO)_4$ —When a solution of diferro-nonacarbonyl -in ether or toluene is heated to 5O°, it assumes an intensely green colour, and dark-green, lustrous tablets with the empirical formula $Fe(CO)_4$ are deposited This substance is

[1] Stoffel, *Eighth Inter Cong App Chem,* 1912, 2, 225, See also Mond and Walhs, *Journ Chem Soc* , 1921, 121, 29

[2] Mond and Wallis, *loc cit*

very stable at the ordinary temperature, but decomposes at 140-150° into iron and carbonic oxide It dissolves in many orgamc solvents, forming dark-green solutions which very readily undergo oxidation Attempts to determine the molecular weight in benzene solution showed that the substance must be a polymende containing many $Fe(CO)_4$ groups, possibly **$[Fe(CO)_4]_{20}$**

IRON AND CYANOGEN

571 Hydrocyamc acid gives no precipitate with solutions of ferrous salts, and on addition of ammonia a ferrous ammonium ferrocyamde, $(NH_4)_2Fe^{n}Fe^{ir}Cy_6$, is formed which rapidly oxidises to the corresponding ferric salt, $NH_4Fe^{m}Fe^{u}Cy_6$ [x] *Ferrous cyanide*, $FeCy_2$, can be prepared, however, by heating hydrogen ferrocyamde at 300° in absence of air, when hydrogen cyamde is evolved and ferrous cyamde left as a pale yellow powder[1] It is stable in absence of oxygen up to 430°, when it begins to evolve, mtrogen leaving a mixture of iron, carbon, and iron carbide When warmed in air, it glows, burning to ferric oxide It is probably an fcsocyanide, having the structure $Fe(NC)_2$ [2]

572 Our knowledge of the complex compounds of iron and cyanogen cominences with the discovery of Prussian blue in 1704 by a c observed that when this colour is boiled with caustic potash, oxide of iron remains, whilst a peculiar salt enters into solution which was named phlogisticated alkali, or yellow prussiate of potash This body was shown to contain iron and prussic acid by Berthollet in 1787 Proust, in 1806, next found that iron remains in combination with prussic acid when the alkali in the yellow prussiate is replaced by other bases, and Ittner in 1809 considered that the compounds of ferric oxide and other bases with prussic acid are double salts In opposition to this view, Porrett[3] described experiments from which he drew the conclusion that the so-called double prussiates containing iron are simple salts of a compound acid containing ferrous oxide and prussic acid This he called *ferruretted chyazic acid*, a name based on the fact that it is a compound of carbon, hydrogen, and azote or nitrogen Gay-Lussac's classical investigation of

[1] Hofmann, *Annalen*, 1907, **352,** 64
[2] Browning, *Journ Chem Soc*, 1900, 77, 1234
[3] *Phil Trans*, 1814, 527, *Ann Phil*, 1818,12, 214, 1819,14, 295

prussic acid followed immediately on Porrett's memoir In this he proved that the acid is a hydrogen compound of the radicle cyanogen Berzelius then showed that all the salts of iron and prussic acid may be considered to be double cyamdes, and that (according to our present nomenclature) the prussiate of potash is a cyanide of iron and potassium, $Fe(CN)_2,4KCN$ Three years later Gmelin,[1] by acting upon this salt with chlorine, obtained a new compound which, from its colour, was termed red prussiate of potash This may be regarded as the ferric double salt, $Fe(CN)_3,3KCN$ Gmelm likewise proved that the potassium in the salt may be replaced by hydrogen, thus giving rise to ferncyanic acid In the following year Gay-Lussac pointed out that the yellow prussiate may be supposed to contain a compound ladicle consisting of iron and cyanogen, to which he gave the name *cyanoferre* Liebig extended this explanation to the other cyanogen compounds containing iron, and considered the above salts as compounds of two isomeric radicles, FeC_6N_6, to which he gave the names of *ferrocyanogen* and *ferricyanogen*

Many suggestions have been made as to the constitution of these two radicles Graham[2] and Erlenmeyer[3] assumed these compounds to contain the radicle C_3N_3, on which supposition potassium ferrocyanide would have the constitutional formula (1), whilst Friedel[4] suggested the formula (2), Browning[5] that given under (3), Demges[6] has proposed (4) and Friend[7] (5), in which the iron atom can be linked to the mtrogen atoms in the 1 2, 1 3 or 1 4 positions

(1)

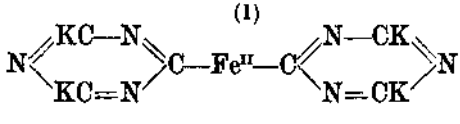

(2)

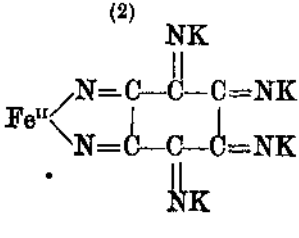

(3)

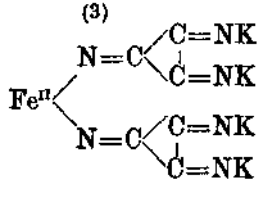

[1] *SchweiggerJ Journ* , **1822, 34, 325**
[2] *Elements of Chemistry*, **1850,** l, **200**
[3] *Lehrbuch Org Chem* , **1867, 148**
[4] ***Compt rend*, 1887,104, 995**
[5] ***Journ Chem Soc* , 1900, 77, 1238**
[6] ***Bull Soc chim*, 1916, 20, 79**
[7] ***Journ Chem Soc* , 1916,100, 715**

(4)

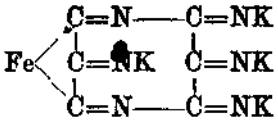

(5)

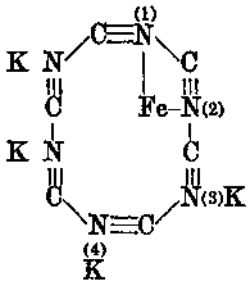

According to these various hypotheses, the ferrocyanides contain closed chains either of carbon atoms alone, or of carbon and nitrogen atoms No evidence, however, has been obtained in support of any of these views, and the general properties of the substances are quite distinct from those of the numerous compounds known to contain such closed chains Moreover, one of the six cyanogen radicles can be replaced by numerous other radicles without any great alteration in general properties, which would not be the case if any of the above formulae were correct It is noteworthy that in the methyl feirocyanides the methyl groups appear to be directly linked to nitrogen, and not to carbon,[1] as would be required by formula (1) Of the other formulae, only that of Deniges, in which the iron is linked differently from the potassium atoms, offers any explanation of the difference in reactiv linked to carbon, whereas, since ferrous cyamde has the *iso*-cyamde structure, it should probably be joined to nitrogen Further, these formulae admit of the possibility of isomerism which has not yet been found in the case of the inorganic ferro-cyanides.

Analogous complex cyamdes are formed by othei metals of the eighth periodic group, and by metals occupying positions near them in the periodic table, such as chromium, *% e* , by those metals which yield complex bases with ammonia, etc , and there is little doubt that these complex bases and the complex cyamdes are compounds of the same order The co-ordination theory of Werner (p 36), which has thrown much light on the relations of the complex bases, is also of great value in making clear the similar relations of the ferrocyanides and analogous compounds

According to this hypothesis, the iron atom occupies the centre

[1] **Hartley,** ***Journ Chem Soc,*** **1911, 99, 1549**

of the system and is combined with the six cyanogen radicles which are " co-ordinated " with it The complex radicle thus formed is of an acid nature and is capable of combining with basic elements or groups which form cations in solution Thus potassium ferrocyanide and femcyanide are formulated as follows, the co-ordinated group being enclosed in square brackets for the sake of shortness and simplicity the symbol Cy is used for the cyanogen radicle CN

Potassium Ferrocyanide	*Potassium Femcyanide*
$K_4[Fe^{11}Cy_6]$	$K_3[Fe^{11}Cy_6]$

The ferrocyanogen radicle is tetracidic, two of the cyanogen valencies being neutralised by the ferrous iron atom, whilst the ferncyanogen radicle is tnacidic, as the ferric iron atom neutralises the valency of three cyanogen groups

One of the six cyanogen groups may be replaced in both ferro- and fern-cyanides by a large number of other groups, including CO, NO NO_2, NH_3, H_{20}, SO_3, yielding substances which closely resemble the original salts in general properties If the replacing group be a monovalent acid radicle, such as NO_2, the valency of the group remains unchanged, whilst a divalent acid radicle increases the valency of the group by one unit, and a neutral substance reduces it by one unit The nitroso-group and ammonia behave in this connection as neutral substances Thus, sodium carbonylferrocyamde is $Na_3[Fe^{n}(CO)Cy_5]$, sodium nitrosoferncyamde (nitroprusside), $Na_2[Fe^{in}(NO)Cy_5]$, sodium sulphitoferrocyanide, $Na_5[Fe^{n}(SO_3)Cy_5]$, and sodium mtroferrocyanide, $Na_4[Fe^{n}(NO_2)Cy_5]$

FERROCYANOGEN COMPOUNDS

573 Until recent years the fenocyanides served as the point of departure for the preparation of almost all the other cyanogen compounds, and they are still mantfiactured on the large scale, although the cyanides specially required for the extraction of gold are at present largely obtained in other ways At present the sodiurti, potassium, calcium, and iron fenocyanides are all prepared in quantity

The method formerly adopted for the manufacture of potassium ferrocyanide, and now obsolete, consisted in heating crude potashes in a cast iron pan„ and adding from time to time a mixture of iron filings and mtrogenous orgamc matter (horns,

feathers, dried blood, etc) The fused mass was allowed to cool, and then lixiviated with warm water, ferrocyanide being obtained by the evaporation of this aqueous extract [1]

Ferrocyanides are now obtained as by-products in the coal-gas manufacture and other industries in which coal is subjected to destructive distillation The unpurified gas usually contains a small quantity of cyanogen compounds, chiefly if not entirely as hydrocyanic acid When the gas is purified by means of ferric oxide (Vol I, p 882), this is partially absorbed, together with the sulphuretted hydrogen, and when the absorbing oxide is completely spent it is frequently found to contain sufficient Prussian blue to repay the cost of extraction

A common method of obtaining the ferrocyanide from the spent oxide is to treat it with hot milk of lime, which converts the Prussian blue into calcium ferrocyanide, on addition of potassium or ammonium chloride to the filtered extract, the sparingly soluble potassium calcium or ammomum calcium ferrocyanide, CaK_2FeCy_6 or $Ca(NH_4)_2FeCy_6$, separates out, and from this pure potassium or sodium ferrocyamde can readily be prepared

In recent years the hydrocyanic acid has been extracted at a number of gas works by passing the gas, previous to the dry purification (Vol I, p 886), through a suitable apparatus in which it is brought into intimate contact with an alkaline liquid to which an iron salt has been added The latter is converted into ferrous sulphide by the action of the sulphuretted hydrogen in the crude gas, and this is acted on by the hydrocyanic acid in presence of alkali *(e g*, potash) as follows

$$FeS\ 4\ \ 6HCy + 2K_2CO_3 = K_4FeCy_6 + H_2S + 2CO_2 + 2H_{20}$$

The potash may be replaced by sodium carbonate or lime, in which case sodium or calcium ferrocyamde is obtained

If the gas is treated with a solution of ferrous sulphate previous to the removal of ammonia, the latter supplies the necessary alkali, and the hydrocyanic acid is absorbed and converted partly into ammomum ferrocyamde and partly into insoluble double ferrocyanides of ammomum and iron, the latter being almost the sole product when excess of ferrous sulphate is used This is filtered and converted into soluble ferrocyanides by boiling with alkalis, the ammonia evolved being recovered as sulphate by absorption in sulphuric acid

[1] **For full details of this and the modern methods of obtaining ferrocyanides, see the article on " Cyanides " in Thorpe's *Dictionary of Applied Chemistry***

Ferrocyanides are now prepared also from thiocyanates, the latter being either made synthetically from carbon disulphide or recovered from crude coal-gas (Vol I, p 887) The thiocyanate is fused in pots and completely dried by passing through it a current of inert gas, and then heated with dry iron borings free from rust, air being excluded

$$6NaCyS + 6Fe = 6NaCy + 6FeS$$

The melt is then treated with water and boiled up with steam in a vat, when sodium ferrocyamde is formed together with sodium sulphide [1]

$$6NaCy + FeS =* Na_4FeCy_6 + Na^S$$

Hydrogen Ferrocyamde or *Ferrocyanic Acid,* $H_4Fe^{II}Cy_6$ — This is best obtained when pure hydrochloric acid is added to an equal volume of a cold saturated solution of potassium ferrocyamde The precipitate which forms is dried on a porous plate in absence of air, then dissolved in alcohol, and precipitated by ether [2] It is a white powder crystallising in small needles Larger crystals may be obtained by pouring a layer of ether on to the alcoholic solution Ferrocyanic acid is easily soluble in water or alcohol It possesses a strongly acid taste and reaction, and liberates not only acetic, but even oxalic acid, from its salts It oxidises quickly on exposure to air, especially when warmed, forming hydrocyamc acid and ferric ferrocyamde

$$7H_4FeCy_6 + O_2 - 24HCy + Fe_4[FeCy_6]_3 + 2H_{20}$$

This reaction is employed in calico-printing, the cloth being printed with a mixture of tartaric acid and yellow prussiate, and then steamed

When the solution of the acid is boiled, hydrocyamc acid is evolved and a white precipitate of ferrous hydrogen ferrocyamde remains behind

$$2H_4[Fe"Cy_6] = 6HCy + H_2Fe^{II}[Fe^{II}Cy_6]$$

When heated at 300° in absence of air it decomposes, hydrogen cyamde being evolved and ferrous cyamde formed Some regard tlie product as a ferrous ferrocyamde, $Fe^{II}{}_2(Fe^{II}Cy_6)$, rather than as the simple cyamde

Ferrocyamc acid gives a series of salts in which it is tetrabasic, and also an ethyl derivative, $(C_2H_5)_4Fe(Cy)_6$ [3] The

[1] *J Soc Chem Ind,* 1895,14, 656 [2] Liebig, *Annalen,* 1853, 87, 127
[3] Hartley, *Journ Chem Soc,* 1913, **103,** 1196

molecular weight of the latter in aqueous solution is in accordance with the simple formula just given,[1] whereas the calcium and strontium salts exist as double molecules[2] The acid forms crystalline compounds with ether, ethyl acetate, and other orgamc esters[3]

Potassium Ferrocyamde or *Yellow Prussiate of Potash,* $K_4FeCy_6,3H_2O$ —The cominercial manufacture of this salt has been described above It is obtained also when a ferrous salt is added to potassium cyamde, a brown precipitate of uncertain composition is first formed, but quickly dissolves in excess of potassium cyamde, yielding potassium ferrocyamde The latter is formed also by the action of potassium cyamde solution on metallic iron in absence of air, slowly in the cold and quickly on heating

$$6KCy + Fe + 2H_2O = K_4FeCy_6 + 2KOH + H_2$$

Potassium feiroeyanide forms tetragonal pyramids, sp gr T83, in which the basal faces are usually dominant They are of a lemon-yellow colour and generally opaque Small crystals, on the other hand, are amber-coloured and transparent

Potassium ferrocyamde does not undergo alteration in pure air at the ordinary temperature, but when heated to 6O° it begins to lose its water of crystallisation, which is removed completely at 110°, the anhydrous salt remaining as a white powder It has a sweetish, saline, and somewhat bitter taste, and is not poisonous, acting in large doses as an aperient One hundred parts of water dissolve about 25 parts of K_4FeCy_6 at 25°, and about 87 parts at 100°, but the solubility is increased by the presence of sodium ferrocyamde It is insoluble in alcohol even when the latter is considerably diluted with water When its solution is exposed to light for some time Prussian blue separates out, and on long-continued boiling of the solution in the air ammonia is given off and the liquid becomes alkaline

By adding very dilute hydrochloric acid gradually to a boiling solution of potassium ferrocyamde, the compound $Fe_2^{m}Fe^{n}K_8[FeCy_6]_4,6H_2O$ is precipitated, and the use of ammonium chloride instead of hydrochloric acid gives the compound $Fe_2^{m}Fe^{II}(NH_4)_7K[FeCy_6]_4,3H_2O$[4]

[1] Buchbock, *Zed physihal Chem,* 1897, 23, 157

[2] Berkeley, Hartley, and Burton, *Phil Trans* , 1908, [-4], **209,**177, Berkeley, Hartley, and Stephenson, *ibid,* 319

[3] Browning, *loc ed* , Baeyer and Vilhger, *Ber,* 1901, 34, 2679

[4] Williams, *Proc Chem Soc,* 1913, **29,** 54

On boiling potassium ferrocyanide with dilute sulphuric acid, hydrogen cyanide is evolved and Eventt's salt is produced[1]

$$2K_4FeCy_6 + 3H_2SO_4 = 3K_2SO_4 + K_2Fe^n[Fe^nCy_6] + 6HCN$$

Concentrated sulphuric acid reacts with potassium ferrocyctnide with evolution of carbon monoxide

$$K_4FeCy_6 + 8H_2SO_4 + 6H_2O = 4KHSO_4 + FeSO_4 + 3(NH_4)_2SO_4 + 6CO$$

If the concentrated acid and anhydrous salt are used, the reaction proceeds extremely slowly, but if a little water be added, it is complete at 180° [2]

Potassium ferrocyanide, in addition to its use in the preparation of Prussian blue and other cyanogen compounds, is employed in calico-printing, and also for the case-hardening of iron The cominercial salt frequently contains considerable quantities of potassium sulphate, which can be removed by recrystallisation only with difficulty

Sodium Ferrocyamde, $Na_4FeCy_6,10H_2O$, or *yellow Prussiate of Soda,* is manufactured as already described, and may be obtained also by boiling Prussian blue with caustic soda or sodium carbonate It crystallises readily in large, monoclinic, pale yellow prisms, and effloresces slightly in the air, at 100° it loses the whole of the water, the residue being a white powder One hundred parts of water dissolve about 27 parts of $Na_4FeCy_6,10H_2O$ at 15°, and about 160 parts at 100°

Ammonium Ferrocyanide, $(NH_4)_4FeCy_6,3H_2O$, is obtained by the action of ammonia on ferrocyamc acid or on Prussian blue, and crystallises in yellow prisms isomorphous with the potassium salt Its solution decomposes readily on heating, with evolution of ammomum cyanide A dull green deposit of the formula $Fe^{III}Fe^{II}(NH_4)_8[Fe^{II}Cy_6]_4,3H_2O$ is produced on boiling the solution in contact with air[3]

Ammomum ferrocyamde gives a double salt with ammomum chloride [4] $(NH_4)_4FeCy_6,NH_4Cl,3H_2O$

Calcium Ferrocyanide, $Ca_2FeCy_6,12H_2O$, is formed when Prussian blue is boiled with the requisite quantity of milk of lime, or by passing hydrogen cyanide into a mixture of slaked

[1] Eventt, *Phil Mag,* 1835, [3], 6, 97
[2] Adie and Browning, *Journ Chem Soc,* 1900, 77, 150
[3] Williams, *Proc Chem Soc,* 1913, 29, 54
[4] Briggs, *Journ Chem Soc,* **1911, 99, 1019**

lime and ferrous hydroxide suspended in water It forms pale yellow, trichmc prisms, one part dissolves in O 66 part of water at 90°, and it is even more soluble in cold water The salt is very efflorescent and the analytical results for the water of crystallisation are always somewhat lower than are required for $12H_2O$ [x] Measurements of the osmotic pressure and electrical conductivity of solutions o5 calcium and strontium ferroeyanides indicate that these salts are associated in solution [2]

Potassium Calcium Ferrocyamde, $K_2CaFeCy_6,3H_2O$, and *Ammonium Calcium Ferrocyamde,* $(NH_4)_2CaFeCy_6\ 3H_2O$, are obtained as white, crystalline precipitates, very sparingly soluble in water w centrated solution of potassium or ammonium ferrocyamde, or by the addition of potassium or ammonium chloride to a solution of calcium ferrocyamde

Strontium Ferrocyamde, $Sr_2FeCy_6,14H_2O$, is most readily obtained by neutralising ferrocyanic acid with strontium hydroxide or carbonate It is very soluble in water, and crystallises from concentrated solution in monoclinic prisms, which lose $7H_2O$ on standing in the air, and a further $6H_2O$ over sulphuric acid

Barium Ferrocyamde, $Ba_2FeCy_6,6H_2O$, is obtained by boiling Prussian blue with baryta water, or by the action of ferrous sulphate on barium cyanide It forms flat, monoclmic prisms soluble in 58O parts of cold and 116 parts of boiling water

Barium Potassium Ferrocyamde, $K_2BaFeCy_6,3H_2O$ —This salt is deposited in small, yellow rhombohedra when boiling saturated solutions of 2 parts of potassium ferrocyamde and 1 part of barium chloride are mixed and allowed to cool It dissolves in 38 parts of cold and 9 5 parts of boiling water

Magnesium Ferrocyamde, $Mg_2FeCy_6,12H_2O$, is prepared in a similar manner to the calcium salt, and crystallises in pale yellow needles which are exceedingly soluble in water The crystals lose $5H_2O$ on standing in the air.

Zinc Ferrocyamde, Zn_2FeCy_6, is a white precipitate used in medicine

Copper Ferrocyamde, Cu_2FeCy_6 + aq , is a fine brown precipitate known as Hatchett's brown If solutions of $CuSO_4$ and K_4FeCy_6 are allowed to come into contact without mixing,

[1] Colman, *Analyst,* 1910, 35, 299 Compare Berkeley, Hartley, and Burton, *Phi Trans* , 1909, **209,** 18O

[2] Berkeley, Hartley, and Stephenson, *ibid,* **319**

copper ferrocyanide is formed as a thin membrane at the common surface This membrane is permeable to water, but impermeable to various dissolved substances, and on this ground has been extensively employed in the investigation of osmotic pressure [x]

Treatment of copper ferrocyanide with boiling concentrated hydrochloric acid removes half the copper, giving the double hydrogen or acid salt, $CuH_2FeCy_6,4H_{20}$, which is a yellow substance insoluble in water[2] It readily decomposes alkali carbonates with evolution of carbon dioxide, and when boiled with alkali chlorides it liberates hydiochlonc acid, forming double ferrocyamdes such as $CuNaHFeCy_{6)}$ $CuNaKFeCy_6$, and CuK_2FeCy_6

The ferrocyamdes of other heavy metals, for example, nickel, cobalt, and manganese, behave similarly [2]

A large number of other ferrocyamdes and double ferrocyamdes have been prepared, many of which crystallise well[3] Those of the heavy metals are mostly sparingly soluble or insoluble precipitates, some of which possess characteristic colours, as in the case of copper and uranium, and potassium ferrocyamde is therefore used as a reagent for these metals The ferrocyamdes of iron are described below

FERRICYANOGEN COMPOUNDS

574 *Ferncyamc Acid,* H_3FeCy_6 —This is obtained by decomposing the lead salt with dilute sulphuric acid, or, preferably, the silver salt with hydrochloric acid, and evaporating the solution at a moderate temperature The acid crystallises in brown needles and has an astringent, acid taste

Potassium Ferrzcyanide, or *Red Prussiate of Potash,* $K_3FeCy_{6)}$ is formed when potassium ferrocyamde is treated with oxidising agents It is obtained on the large scale by passing chlorine into a solution of the yellow prussiate

$$2K_4FeCy_6 + Cl_2 = 2K_3FeCy_6 + 2KC1$$

By repeated crystallisation it may be readily separated from the potassium chloride formed at the same time, and is obtained

[1] **Traube,** ***Archiv fUr Anatomie und Physiologie,*** **1867, 124, Heffer,** ***Osmotische Untersuchungen*** **(Leipzig, 1877), Morse,** ***Amer Chem J,*** **1911, 46, 558**

[2] **Williams,** ***Proc Chem Soc*** **, 1912, 28, 317**

[3] **Wyrouboff,** ***Ann Chim Phys,*** **1869, [4], 16, 28O, 187O, [4], 21, 271, 1876, [5], 8, 444, Messner,** ***Zett anorg Chem,*** **1895, 8, 368, Werner,** ***ZetL anal Chem*** **, 1919, 68, 23**

as large dark red, anhydrous monochnic prisms, sp gr 1 8, which occur frequently 9. twin forms Potassium ferncyamde possesses a faintly astringent and saline taste, and dissolves in water, giving a yellowish-brown solution, which on dilution becomes lemon-yellow One hundred parts of water dissolve [a]

At	4 4°	10°	15 6°	37 8°	100°
K_3FeCy_6	33 O	36 6	39 7	58 8	77 6 parts,

and 82 parts at 104°, the boiling point of the saturated solution It is only shghtly soluble in alcohol When exposed to light the solution becomes darker, and a blue precipitate is formed, potassium ferrocyamde remaining in solution When the salt is heated in a flame it burns, and when mixed with ammomum nitrate and heated, the mixture detonates It is a powerful oxidising agent, especially in alkaline solution, converting the monoxides of lead and manganese into dioxides, and forming potassium chromate and potassium ferrocyamde when boiled with a solution of chromium sesquioxide in potash

$$6K_3FeCy_6 + Cr_{203} + 10KOH = 6K_4FeCy_6 + 2K_2CrO_4 + 5H_{20}$$

In solution it is reduced to ferrocyamde by sodium amalgam, and by hydrogen dioxide

$$4K_3FeCy_6 + 2H_{202} = 3K_4FeCy_6 + H_4FeCy_6 + 20_2$$

It is also reduced by hydrogen sulphide, slowly in the cold, but rapidly on warming [2]

$$6K_3FeCy_6 + 3H_2S = 4K_4FeCy_6 + K_2Fe(FeCy_6) + 6HCN + 3S$$

Hydrochloric acid readily reduces it [3]

$$K_3FeCy_6 + 3HC1 = H_3FeCy_6 + 3KC1$$
$$2H_3FeCy_6 + 2HC1 - H_4FeCy_6 + Cl_2$$

Chlorine is formed, and since this oxidises ferrocyamc acid to ferncyamc acid, the reaction is reversible, but it proceeds to completion if the chlorine is removed from the sphere of action by reduced silver Because of their hydrolysis, the chlorides of iron, zinc, and aluminium behave in the same way as hydrochloric acid

Potassium ferncyamde is quantitatively reduced by an alkahne solution of hydrazine sulphate Nitrogen is evolved and

[1] Wallace, *Journ Chem Soc*, 1865, 7, 8O
[2] Venditon, *Atti R Accad Lvncei*, 1906, [5], 15, 1, 37O
[3] **Gillet,** *Bull Soc chim Belg*, 1912, 96, 236

measurement of its volume affords a method of estimating either of the reacting substances [1]

$$4K_8FeCy_6 + 4KOH + N_2H_4 = 4K_4FeCy_6 + 4H_{20} + N_2$$

In a similar manner, hydroxylamine reduces it, mtrogen and nitrous oxide being evolved [x]

Sodium Ferricyanide, $2Na_3FeCy_6,H_{20}$, is obtained by the action of chlorine upon sodium ferrocyanide It dissolves in 1 25 parts of boiling and 5 3 parts of cold water, and crystallises in ruby-red, four-sided, deliquescent prisms

Ammonium Femcyamde, $2(NH_4)_3FeCy_6,H_{20}$, is obtained in a similar way to the other ferricyanides It forms fine red, monoclimc prisms, easily soluble in water and permanent in the air

Lead Femcyanide, $Pb_3(FeCy_6)_2,16H_{20}$, is formed by mixing hot solutions of the potassium salt and lead nitrate It forms dark reddish-brown crystals shghtly soluble in cold, and rather more soluble in hot water

The ferricyanides of most of the other heavy metals are precipitates, generally possessing a yellow, greenish-brown, or reddish-brown colour, whilst some of them, like that of tin and mercury, are colourless A number of ferricyanides form stable double salts with mercuric cyanide [2]

FERRO- AND FERRI-CYANIDPS OF IRON

575 As already mentioned (p 13O2), the double cyamdes of iron were the earliest known cyanogen compounds, having been first obtained in 17O4 In spite, however, of much experimental work by Berzehus, Liebig, Williamson, and others, the exact composition and constitution of the various compounds formed by the interaction of ferro- and fern-cyanides with ferrous and ferric salts is still in many respects doubtful This is largely owing to the fact that the preparation of these compounds in a state of purity is very difficult, and, moreover, slight alterations in the conditions under which the interaction of iron salts and the ferrocyamdes takes place have frequently a very great influence on the nature of the product

576 *Ferrous Ferrocyamdes*—When ferrous sulphate is added to potassium ferrocyanide in cold neutral solution in absence of oxygen, a white precipitate is obtained having the composition

[1] **Ray and Sen,** ***Zat anorg Chem*** **, 1912, 76, 38O**
[2] **Williams,** ***Proc Chem Soc,*** **1912, 28, 317**

$Fe^{II}K_2[Fe^{II}Cy_6]$ This oxidises with great rapidity in the air, yielding the B-soluble blue described below. In acid solution, a precipitate of similiar composition is formed,[1] which, however, differs from the foregoing in being less readily oxidised, and yielding y-soluble blue (p 1317)

A third substance of the same composition, Eventt's salt, is obtained as an insoluble compound by the action of sulphuric acid on potassium ferrocyanide It forms a pale yellow powder which is seen under the microscope to consist of doubly refractive crystals of a pale greenish colour It is much less readily oxidised than either of the other compounds already described, but nitric acid or hydrogen dioxide converts it into Williamson's violet (p 1317)

Ferrous Hydrogen Ferrocyanide, $H_2Fe^{n}[Fe^{n}Cy_6]$, corresponding to the last named salt, is obtained by heating ferrocyanic acid solution at 110-120°, and on oxidation yields a violet substance, $Fe^{ni}H[Fe^{n}Cy_6]$, closely resembling Williamson's violet in appearance, but containing no alkali

577 *Ferric Ferrocyanides* —These substances are the most important of the iron-cyanogen derivatives, the various substances comprised under the general name of Prussian blue belonging to this class They are obtained (1) by the interaction of ferric salts and ferrocyamdes, (2) by the interaction of ferrous salts and ferncyamdes, (3) by the oxidation of ferrous ferrocyamdes, and (4) by the reduction of ferric ferricyamdes The compounds formed in the different ways, although they may have the same empirical composition, frequently differ

in both physical and chemical properties

The researches of Hofmann [2] have shown that all these compounds consist of ferrocyamc acid, in which the hydrogen is either wholly or partially replaced by ferric iron, or partly by ferric iron and partly by another metal, and all of them may be represented by one of the two simple formulae (1) $Fe^{III}[Fe^{II}Cy_6]_3$, and (2) $Fe^{m}X[Fe^{Ir}Cy_6]$, where X is either hydrogen or a monovalent metal The molecular weight is, however, undoubtedly much higher than that shown by the simple formulae, and the products having the same empirical composition bi?t different chemical and physical properties are, in all probability, polymers of the simple molecule.

[1] Compare Muller and Treadwell, *J pr Chem,* 1909, [2], 8O, 17O

[2] *Annalen,* 1904, **337,** 1, 1905, **340,** 267, 1905, **342,** 364, 1907, **362,** 54, *J pr Chem* , 1909, [2], 8O, 15O See also Vorlander, *Ber,* 1913, **46,** 181

With the single exception of one of the ferric ammonium ferrocyamdes, none of these compounds has been obtained anhydrous or in the crystalline form The remainder are all colloidal substances, which still retain water when dried for months over phosphorus pentoxide, and this water cannot be removed by heat without simultaneous decomposition of the compound On account of their colloidal nature, it is extremely difficult to prepare them in a state of purity, as, like other similar substances, they obstinately retain salts, and on this account very varying formulae have been attributed to them in the past by various workers

All the ferric ferrocyamdes possess an intensely blue or violet colour, and form valuable dyes, differing in this respect from all the other ferrocyamdes, for although most of the latter are coloured, none of them can be described as colouring matters Hofmann and Kesenscheck* suggest that the cause of the intense colour is the presence in the same molecule of ferrous and ferric iron atoms, thus derivatives of the type $Fe^{n}K_2[Fe^{n}Cy_6]$ are colourless, whereas $Fe^{iii}K[Fe^{ii}Cy_6]$ is Prussian blue. They point out that similar intense colour is present in many other compounds containing an element in different stages of oxidation For example, sulphur sesquioxide, S_{203}, is of a deep indigo blue colour, whereas both sulphur dioxide and trioxide are colourless, red lead, in the same way, is more highly coloured than litharge or the dioxide, the tungsten bronzes furnish another example It has also been supposed that the presence of chemically combined water was essential to the production of the colour, but the preparation of an anhydrous ferric ammonium ferrocyamde by Hofmann and Arnoldi [2] disproves thjs suggestion, as that substance is still intensely coloured

a-Soluble Prussian Blue or *a-Femc Potassium Ferrocyamde*, $4Fe^{m}K[Fe^{II}Cy_6],7H_{20}$, is obtained by precipitating a solution of potassium ferrocyamde with slightly less than one equivalent of a ferric salt, the precipitate is washed by decantation with potassium chloride solution, and then with 7O per cent alcohol, and dried over phosphorus pentoxide It forms a voluminous mass, having a beautiful bronze reflex, and yields a deep blue powder It dissolves in pure water, forming a deep blue solution, and like other colloids is precipitated by the addition of salts It also dissolves readily in oxalic acid, and is quickly converted into ferrocyamde and feme hydroxide by dilute

[2] *Annalen*, **1905, 842, 364** [1] *Ber*, **1906, 89, 2204**

ammonia The water in the dried substance cannot be driven off without decompqfition taking place, and is therefore probably "constitutional" water Hofmann states that it is in all probability a basic ferric salt of the simplest formula $(HO)_2Fe^{III}[Fe^{n}Cy_6]KH_2$, two molecules of which have lost one molecule of H_{20}, forming the anhydro-salt

$$KH_2[Fe^{II}Cy_6]Fe^{III}(OH)\ O\ (HO)Fe^{III}[Fe^{II}Cy_6]KH_2$$

When treated with dilute acid it loses potassium, yielding the corresponding *a-ferric hydrogen ferrocyanide,* $Fe^{III}H[Fe^{II}Cy_6]$ + aq, which closely resembles the ferric potassium salt, but is insoluble in water

When a solution of potassium ferricyanide is precipitated with slightly less than one equivalent of ferrous salt, a soluble Prussian blue is produced, which its mode of formation would indicate to be a ferrous potassium ferricyamde, $Fe^{IT}K[Fe^{III}Cy_6]$ It has, however, been shown by Skraup,[1] and by Hofmann, Heme, and Hochtlen,[2] that this substance is identical with that obtained in the manner already described from potassium ferrocyanide and a ferric salt Evidence other than that of the method of formation is therefore necessary to decide whether the substance possesses the constitution (1) or (2)

(1)
FeIIIe Potassium Ferrocyanide
$Fe^{III}K[Fe^{ir}Cy_6]$

(2)
Ferrous Potassium Ferncyamde
$Fe^{Ii}K[Fe^{III}Cy_6]$

Alkalis decompose it into potassium ferrocyanide and ferric hydroxide, which is in favour of the first formula, but this is not conclusive, inasmuch as potassium ferricyamde and ferrous hydroxide, which would be the products formed from a substance of the second formula, iminediately interact, yielding ferrocyanide and ferric hydroxide Hofmann has, however, shown that dilute hydrogen dioxide containing acid, which readily reduces the ferricyanogen group to ferrocyanogen, but has no effect on ferric salts, qiuckly reduces a ferric ferricyamde solution to Prussian blue, and also oxidises the ferrous ferrocyanides to Prussian blue This must therefore contain the ferric iron as the basic constituent, and ferrous iron in the acidic radicle, as given in formula (1) In fact, all the blue iron-cyanogen compounds are ferae ferrocyanides, the ferrous femcyanides apparently not being capable of permanent existence,

[1] ***Annalen,* 1877, 188, 371** * ***Ibid,* 1904, 337, 1**

intramolecular change taking place where their formation would be expected

^*Soluble Prussian Blue,* $Fe^{m}K[Fe^{n}Cy_6],H_{20}$, is obtained by the oxidation of the ferrous potassium ferrocyamde obtained in neutral solution (p 1313) It is soluble in water, and differs from the previous compound chiefly by its insolubility in oxalic acid

y-Soluble Prussian Blue is prepared in a similar manner by oxidising the ferrous potassium ferrocyamde obtained in cold acid solution It is soluble in water, but is much more stable towards alkalis than the two previous compounds, and only loses the potassium with difficulty by the action of dilute acids or of ferric chloride

Williamson's Violet, $Fe^{III}K[Fe^{Ii}Cy_6],H_{20}$ —This substance was first obtained by A W Williamson by the action of nitric acid or some other oxidising agent on Everitt's salt (p 1314) It forms a deep violet-blue powder, which is transparent in thin layers, allowing green light to pass through It is much more stable than any of the three compounds already described of the same empirical composition, being quite insoluble in mineral acids, which do not remove the potassium, and also in oxalic acid, and being only very slowly decomposed by dilute alkalis

Hofmann regards 7-soluble blue and Williamson's violet as formed by the union of two molecules of the simple substance $Fe^{III}K[Fe^{II}Cy_e]$, the former having an unsyminetncal and the latter a syminetrical constitution, as shown by the formula?

γ Soluble Blue



Williamson's Violet



In addition to the ferric potassium compounds, several ferric ammonium compounds have been prepared

Monthiers' Blue, $Fe^{III}NH_4Fe^{II}Cy_6]H_2O$, was first obtained by Monthiers[1] by the oxidation of the white precipitate formed by the action of ammoniacal ferrous chloride on potassium ferrocyamde, and given by hmi the formula $(Fe_2)_2(FeCy_6)_3,6NH_3,9H_{20}$, but it has been shown by Hofmann, Arnoldi, and Hiendlmaier[2] to have the formula given above It is also formed if any of the soluble Prussian blues be exposed to sunlight with

[1] *J Pharm,* **1846, [3], 9, 262** [a] *Annalen,* **1907, 352, 54**

ammonium oxalate solution, **and** the resulting white compound oxidised by hydrogen dioxide, but is most readily obtained by acting on a solution containing potassium ferrocyanide, ammonium chloride, and ammonia with iron wire, and oxidising the green precipitate with hydrogen dioxide It is a deep blue powder having an enamel-blue reflex soluble in water and oxalic acid, and decomposed slowly by dilute alkalis

A crystalline anhydrous *ferric ammonium ferrocyanide,* $Fe^{iii}NH_4[Fe^{II}Cy_6]$, is obtained together with nitroprusside by heating a solution of hydroxylamine hydrochloride with one of potassium ferrocyanide, and forms a deep blue, insoluble powder, which is seen under the microscope to consist of opaque violet-red, lustrous cubes In its pioperties it very closely resembles Williamson's violet[1]

Insoluble Prussian Blue, or *Ferric Ferrocyanide,* $FeIII_4[Fe^{II}Cy_6]_6$ or Fe_7Cy_{18}, is prepared by precipitating a solution of a soluble ferrocyanide with an excess of ferric salt, or by the action of the latter on soluble Prussian blue The exact composition of the precipitate depends on the proportions of ferric salt and ferrocyanide taken,[2] and it is exceedingly difficult to free it from the last traces of alkali The precipitate is insoluble in water and dilute mineral acids, but dissolves in ammomum tartrate solution, forming a violet liquid, and in oxalic acid, forming a blue solution The latter was formerly largely used as a blue ink, but has now been replaced by the blue aniline colours

The dried substance contains water which cannot be driven off without decomposition, the amount corresponding approximately to the formula $Fe_7Cy_{18},9H_{20}$, or $Fe_7Cy_{18},10H_{20}$. When strongly heated in the air, it burns like tinder, forming ferric oxide, and it is decomposed by alkalis into ferric hydroxide and the ferrocyanide of the alkali employed Concentrated sulphuric acid converts it into a white mass, neither iron nor hydrocyanic acid being removed, and when this is dried on a porous plate, an amorphous powder remains which is decomposed by water into Prussian blue and sulphuric acid (Berzehus) Prussian blue also dissolves in hot concentrated hydrochloric acid, forming a yellow solution from which ferrocyanic acid separates on standing It dissolves more readily in a mixture of hydrochloric acid with ethyl alcohol or higher alcohols, or

[1] **Hofmann and Arnoldi, *Ber* , 1906, 89, 2204**

[2] **Volschin, *J Buss Phys Chem Soc*, 1908, 40, 480, Muller and Stamsch, *J pr Chem* , 1909, [2], 70, 81 , 80, 153,**

with amyl acetate, small quantities of water causing a blue precipitate in the solutions [1]

Turnbull's Blue—Gmekn obtained a blue compound by the precipitation of potassium ferricyanide with excess of ferrous salt, which was afterwards manufactured in England under the name of Turnbull's blue. From its mode of preparation it was supposed to be ferrous ferricyanide, $Fe_3^{II}[Fe^{III}Cy_6]_2$ or Fe_5Cy_{12}, but it has been found [2] that the compound thus formed, after it has been washed in presence of air, during which oxidation probably takes place, is identical with the insoluble Prussian blue obtained from ferric salts and ferrocyanides (see also p 1314)

Another ferric ferrocyanide, differing from that above described, has been obtained by Hofmann and Eesenscheck [3] by the action of hydrogen dioxide on a solution of ferric ferricyanide in presence

composition $Fe_7Cy_{18},10H_{20}$ In coloui and properties it resembles Williamson's violet, but is less stable towards dilute ammonium hydroxide It is insoluble in oxalic acid.

Cominercial Prussian Blue is a mixture of a number of the ferric ferrocyanides above described, and consequently varies considerably in its colour and appearance It is sold in the form of lumps, powder, and paste All these have a deep blue colour and show a bronze reflex in varying degree The finest variety, known as Pans blue, is obtained by the precipitation of potassium ferrocyanide by a ferric salt, and the lumps of this product, especially when wet, have a splendid bronze lustre As ferric salts are dear, the blue is usually made by precipitating a ferrocyanide with ferrous salt, and oxidising the product by an oxidising agent such as bleaching powder The exact conditions are, however, mostly trade secrets

Prussian blue is still employed as a dye, although to a less extent than formerly, having been to a considerable degree replaced by the coal-tar colours

578 *Ferric Femcyanides*—When a ferric salt is added to a solution of a ferricyanide no precipitate is obtained, but the solution assumes a dark brown colour, and probably contains ferric ferricyanide, although no solid compound of that composition has been isolated from it [4]

[1] Coffignier, *Bull Soc chvm,* 1902, [3], 27, 696, Watson Smith, *J Soc. Chem Ind* , 1903, 22, 472

[2] Hofmann, Heme, and Hochtlen, *Annalen,* 1904,**337,**1 Compare, however, Muller and Stanisch, *J pr Chem* , 1909, [2], 79, 81, 8O, 153

[3] *Annalen,* 1905, **340,** 267 [4] See Haller, *Kolloid Zeit,* 1917, 20, 76

Prussian Green —When an excess of chlorme is allowed to act on a solution 6f a ferro- or fern-cyanide, or on Williamson's violet, a green hydrated compound is precipitated, to which the name Prussian green has been given The composition of this substance is variable, and numerous formula have been proposed for it, such as Fe_3Cy_8, Fe_5Cy_{14}, Fe_9Cy_{24} It has, however, been shown by Messner[1] that when chlorine is passed through a boiling solution in the dark, until no further action takes place, and the precipitate is washed with water in the dark, the green product has the empirical formula $FeCy_3$, and is probably a polymeric ferric ferricyanide, $[Fe^{III}(Fe^{III}Cy_6)]_x$ It readily loses cyanogen, forming Prussian blue, this being the cause of the varying composition found by the former investigators It is doubtful if the pure compound has a green colour, this being probably due to the presence of traces of Prussian blue

IRON PENTACYANO-DERIVATIVES

578 It has already been stated that one of the cyanogen groups in ferro- and ferri-cyanides can be replaced by other groups, forming stable salts, which in general properties are closely allied to these substances

Carbonylferrocyanic Acid, $H_3[Fe^{II}(CO)Cy_5]$ —This acid is made by treating a suspension of the copper salt in water with hydrogen sulphide It forms colourless crystals soluble in water Its solution is acid to litmus and will decompose alkali carbonates[2] The *potassium* salt is slowly formed by the action of carbomc oxide on boiling potassium ferrocyanide solution, the group CO replacing 1 molecule of potassium cyanide, which undergoes conversion into potassium formate and ammonia [3]

$$K_4FeCy_6 + CO + 2H_2O = K_3Fe(CO)Cy_5 + NH_3 + HCOOK$$

It forms pale yellow crystals containing $4H_2O$ The free acid forms colourless, crystalline plates

The salts of this acid are almost invariably present in the crude ferrocyanides obtained from coal-gas, their formation being due to the carbomc oxide always present in the gas They are readily separated by treatment with dilute alcohol, in which the carbonylferrocyanides are soluble, and the ferrocyanides insoluble [4]

[1] *Zeit anorg Chem*, 1895, 9, 136
[2] Muller, *Ann Chim Phys*, 1889, [6], 17, 93
[3] *Ibid , Compt rend*, 1898, **126,** 1421
[4] Compare Lecocq, *Bull Soc chim Belg*, 1911, 25, 72

With ferric chloride the carbonylferrocyanides give a precipitate of *ferric carbonylferrocyanide,* $Fe^{III}[Fe^{II}(CO)Cy_6]$ + aq , which differs from Prussian blue in possessing an intense purple colour The *copper* salt is pale apple-green

Nitroprussic Acid or *Nitrosoferricyanic Acid,* $H_2[Fe^{III}(NO)Cy_5]$ —Gmelin and other chemists observed that the coffee-brown solution obtained by the action of nitric acid on potassium ferrocyanide yields a splendid purple-red colour when treated with the sulphides of the alkalis Playfair,[1] in 1849, showed that this reaction i* produced by the presence of a peculiar compound which is formed by the action of nitric acid on ferro- or fern-cyanides, which he termed nitroprussic acid, and which may be regarded as ferricyanic acid in which one of the Cy groups has been replaced by the nitroso-group NO

The acid is formed when nitric oxide is passed into an acid solution of potassium ferrocyanide, the ferrocyamc acid, after oxidation to ferricyamc acid, acting with nitric oxide thus

$$H_3FeCy_6 + NO = H_2[Fe(NO)Cy_6] + HCy$$

The potassium salt is formed also by the action of potassium nitrite on a mixture of potassium cyanide and a ferrous salt

$$5KCy + 2FeSO_4 + KNO_2 + H_2O = K_2[Fe(NO)Cy_6] + Fe(OH)_a + 2K_2SO_4,$$

the ferrous hydroxide being further converted into ferric hydroxide,[2] with liberation of ammonia, by the action of the nitroprusside or the nitrite

Nitroprussides may be prepared from either ferrocyanides or cyanides In the former case powdered potassium ferrocyanide is treated with double its weight of strong nitric acid previously mixed with an equal volume of water The coffee-coloured solution evolves carbon dioxide, nitrogen, cyanogen, and hydrocyanic acid, and as soon as solution is complete it is warmed on the water-bath till a portion of the liquid gives only a slate-coloured precipitate with ferrous sulphate On cooling, the liquor is poured off from the separated potassium nitrate, and neutralised with sodium carbonate The solution is then concentrated, filtered, and the nitrates separated by fractional crystallisation, or the copper salt may be precipitated and decomposed, after washing, with soluble bases

[1] *Phil Trans* , 1849,**189,** 477

[2] Stadeler, *Anruden,* 1869, **161,** 1 See also Schwarzkopf, *Abhandl deut natururss med Ver Bohmen,* 1911, 3

To obtain them from cyanides, a concentrated aqueous solution of ferrous sulphate is mixed with a solution of equal parts of potassium cyanide and sodium nitrite, and allowed to remain for five hours at the ordinary temperature Ferric hydroxide separates, and nitrogen and nitric oxide are evolved The solution is then heated to 25°, made slightly alkaline with caustic soda, filtered, and the salt crystallised out

Nitroprussic acid is formed by decomposing the silver salt with hydrochloric acid, or the barium salt with dilute sulphuric acid The red, strongly acid solution leaves on evaporation in a vacuum dark red, deliquescent, prismatic needles This compound is very unstable and partially decomposes during the concentration of the liquid with formation of ferric hydroxide, hydrocyanic acid, etc

Potassium Nitroprusside, $K_2[Fe(NO)Cy_6]$, forms dark red soluble, deliquescent, monochnic prisms

Sodium Nitroprusside, $Na_2[Fe(NO)Cy_5],2H_{20}$, crystallises most readily of all the mtroprussides, and is usually prepared by concentrating the solution obtained as above described until a sufficient quantity of nitroprusside has crystallised out This is then removed from the warm solution in order to avoid any admixture of nitrates It is purified by crystallisation and forms large ruby-red, rhombic prisms It dissolves in 2 5 parts of water at 15°, and is more soluble in hot water When exposed to light, the solution decomposes with separation of Prussian blue and nitric oxide, but may be kept unaltered in the dark for a long time, especially if a trace of sulphuric acid be present [x]

Hydrochloric acid attacks sodium nitroprusside, giving hydrogen cyanide and ferric chloride, which reacts with the excess of nitroprusside to form ferric nitroprusside [2] Concentrated sulphuric acid also attacks it, carbon monoxide being evolved The reactions are very complex [3] Boiled with caustic soda, it yields ferrous hydroxide, sodium ferrocyanide, and sodium nitrite

Sodium nitroprusside is readily reduced by sodium amalgam or the zinc-copper couple to sodium ferrocyanide. In neutral solution the mtrogen is evolved as such, in alkaline solution as ammonia, and in acid solution part of it as hydrogen cyanide, Prussian blue also being formed [4]

[1] **Zuccan,** ***Ann Chim Apphcata,*** **1914, 2, 287, 1915, 3, 277**
[2] **Bhaduri,** ***Zeit anorg Ghent,*** **1913, 84, 95**
[3] **Bhaduri,** ***he cit ,*** **Pereira,** ***Anal Fis Quim,*** **1915,13, 166**
[4] **Bhaduri,** ***loc cit***

The nitroprussides of ammonium and of the alkaline-earth metals also form red, easily soluble salts, their solutions decomposing on standing or on boiling, with separation of Prussian blue and ferric oxide The silver salt and the ferrous salt are flesh-coloured precipitates

The splendid purple colour which the nitroprussides impart to a solution of an alkaline sulphide is very charactenstic, and this reaction is employed both for the detection of alkali sulphides and of small quantities of alkalis and alkaline earths in solution, by passing a little sulphuretted hydrogen through the liquid in the latter case and then adding a few drops of nitroprusside solution The purple compound thus produced is very unstable, its constitution is uncertain, but is very probably represented by the formula $Na_3[Fe^n(O\ N\ SNa)Cy_5]$, as Hofmann,[1] by the action of thiourea, $CS(NH_2)_2$, on sodium nitroprusside, has obtained the compound $Na_3[Fe^n(O\ N\ SCNH\ NH_2)Cy_5]$, which forms a beautiful carmine-red powder, closely resembling

in its prop

sulphides

Starting from sodium nitroprusside, Hofmann has obtained the following substituted ferro- and ferri-cyanides

Sodium nitroferrocyanide, $Na_4[Fe^{IT}(NO_2)Cy_5],10H_{20}$,
Potassium nitroferricyanide, $K_3[Fe^{TII}(NO_2)Cy_5]$,
Sodium aquoferrocyanide, $Na_3[Fe^n(H_{20})Cy_5],7H_{20}$,
Sodium aquoferricyanide, $Na_2[Fe^m(H_{20})Cy_5]$,
Sodium ammonioferrocyanide, $Na_3[Fe^{IT}(NH_3)Cy_6],6H_{20}$,
Sodium ammonioferricyanide, $Na_2[Fe^{III}(NH_3)Cy_5],H_{20}$,
Sodium sulphitoferrocyanide, $Na_5[Fe^{II}(SO_3)Cy_5],9H_{20}$,
Sodium arsenitoferrocyanide, $Na_4[Fe^u(AsO_2)Cy_5],10H_{20}$

The substituted ferrocyanides are yellow or reddish-yellow, crystalline salts, which give blue precipitates with ferric salts, and browmsh-red precipitates with copper salts The substituted ferricyanides have a deep carmine-red or purple colour, and give no precipitate with ferric salts, and pale green precipitates with copper salts All these compounds are converted into sodium ferrocyanide by boiling with sodium cyanide solution

IRON THIOCYANATES

58O *Ferrous Thocyanate*, $Fe(SCN)_2,3H_{20}$, is obtained in large pale-green, monochnic crystals by dissolving iron wire

[1] ***Annalen*, 1900, 312, 1 Compare Virgih, *Zeit anal Chem* , 1906, 45, 409**

m concentrated thiocyanic acid and evaporating the liquid in absence of air The salt dissolves readily in water, alcohol, or ether, and becomes red-coloured on exposure to the air

Ferric Thiocyanate, $Fe(SCN)_3,3H_{20}$—This compound is obtained in the pure state when a mixture of anhydrous ferric sulphate and potassium thiocyanate in equivalent proportions is treated with alcohol and the solution evaporated over sulphuric acid in a vacuum Dark red or almost black cubical crystals are deposited, and these dissolve readily in water, alcohol, or ether The production of this intense colour on the addition of a thiocyanate serves as a delicate test for ferric salts in solution If a concentrated aqueous solution is shaken with ether it becomes colourless and the ether attains a purple-red colour The aqueous solution is also decolorised in presence of reducing agents as well as on treatment with mercuric chloride or gold chloride

A solution of ferric thiocyanate is not permanent, and the colour gradually fades when the solution is allowed to stand at the ordinary temperatuie [1] This bleaching is due to the progressive reduction of the iron to the ferrous condition, and in the corresponding oxidation'of thiocyanate which occurs, carbon dioxide, sulphuric acid, and ammonia are formed [2]

The reaction between a ferric salt and potassium thiocyanate in aqueous solution is not complete when equivalent quantities are employed, and the state of equilibrium produced in any mixture of the two depends on the dilution, the temperature, and the relative proportion of the two salts present [3] When the deep red solution is diluted so as to be almost colourless addition of potassium thiocyanate restores the colour

The iron thiocyanates form double salts with other thiocyanates, which are analogous to the ferro- and fern-cyanides, and have the general formulae $M^{I}_4Fe(CNS)_6$ and $M^{I}_3Fe(CNS)_6$ Unlike these, however, they are very unstable substances and are completely dissociated by water into the constituent salts [4]

[1] See, for example, Oerum, *Zeit anal Chem,* 1904, 43, 152, Stokes and Cam, *J Amer Chem Soc ,* 1907, 29, 412, 445

[2] Philip and Bramley, *Journ Chem Soc,* 1913, **103,** 795

[3] Kruss and Moraht, *Ber ,* 1889, 22, 2061, *Zeit anorg Chem ,* 1892, 1, 399, Magnanmi, *Zeit physikal Chem,* 1891, 8, 1, Vernon, *Chem News,* 1892, 66, 177 *et seq ,* 1893, 67, 66, Gladstone, *ibid,* 1893, 67, 1

[4] Rosenheim and Cohn, *Zeit anorg Chem,* 1901, 27, 28O

IRON AND SILICON

581 *Silicides of Iron* —Iron can readily be alloyed with silicon, and since silica and silicates are reduced by carbon in the presence of iron, all cast iron contains silicon, probably as a silicide

The compound Fe_2Si is obtained by heating iron or ferric oxide with silicon in the electric furnace, and forms magnetic prisms of specific gravity 7 It is readily attacked by hydrofluoric acid,[1] and by sulphur chloride[2]

Compounds of the formulae FeSi, $FeSi_2$, and Fe_3Si_2 have also been described[3]

Mixtures of iron and silicon, known as " ferro-silicon " and Containing up to 90 per cent silicon, are prepared in the electric furnace on a large scale Under certain conditions ferro-silicon *te* liable to decompose, giving off poisonous gases[4]

Silicates of Iron —Several ferrous and ferric silicates occur in the imneral kingdom, but they are more frequently found as double silicates, in which the alkali metals and the metals of the alkaline earths are present These are generally isomorphous mixtures in which ferric oxide is replaced by alumina, whilst lime, magnesia, and the alkalis are substituted by ferrous oxide, manganous oxide, etc For a description of these compounds works on mineralogy must be consulted

The Iron Tree —In Glauber's description of the preparation of *oleum maitis* (p 1277) the following passage occurs —" When such a red *massa* before it deliquesces to an *oleum* is laid in *oleum arence vel silicum* (the modern sodium silicate) for one or two hours, a tree grows out of it, with roots, stems, many branches, and twigs, wonderful to behold " This phenomenon depends upon the fact that water-glass, which contains always some carbonate, decomposes the ferric chloride into ferric silicate and basic ferric carbonate, whilst bubbles of carbon dioxide are given off, and thus filiform processes are produced In place of the ferric chloride, ferrous chloride, cobalt chloride, nickel chloride, copper nitrate, and many other easily soluble

[1] Moissan, *Compt rend*, 1895, **121,** 621
[2] Nicolardot, *Ibid*, 1908, **147,** 676
[3] Compare Guertler and Tammann, *Zeit anorg Chem*, 1905, **47,** 163, Vigouroux, *Compt rend*, 1905, **141,** 828, Vanzetti, *Gazz*, 1906, 36, 1, 498 Murakami, *Set Rep Tohohu Imp Umv*, 1921,10, 79.
[4] See *Zed Nahr Genussm*, 1906, **12,** 132, *J Soc Chem Ind*, 1907, 26, 968, 1909, 28, 25, 143, 1910, 29, 154, 28O, 355, 955, *Stahl und Eisen*, 1912, 32, 267

metallic salts may be employed, and thus a series of differently coloured coral-like growths may be produced

DETECTION AND ESTIMATION OF IRON

582 A bead of microcosmic salt or borax is coloured dark-green by ferrous salts This colour readily changes to a yellow or reddish-brown by oxidation On cooling, the colour becomes less distinct, disappearing altogether if only traces of ferric oxide are present Iron can also be detected in the dry way by Bunsen's test For this purpose, the compound is heated on the end of a carbonised wooden match, which has previously been impregnated with fused sodium carbonate, held in the reduction zone of the non-luminous gas flame The whole is then rubbed up in an agate mortar with a little water, the particles of iron being extracted on the point of a magnetised knife-blade The adhering particles of finely divided iron are brought on to a small piece of filter paper, dissolved in a drop of aqua regia, and a drop of potassium ferrocyanide added, this confirmatory test being necessary since mckel and cobalt are also magnetic

The iron compounds do not impart any colour to the non-lummous gas flame The spectrum of the metal is extraordinarily rich in lines, more than 4,500 having been measured A dark line in the solar spectrum corresponds to each of the bright lines in the visible part of the spectrum

In solution, ferrous salts immediately give a dark blue precipitate with potassium ferricyanide, whilst ferric salts are coloured dark brown by this reagent, no precipitate being formed Ferric salts give a blue coloration or precipitate with potassium ferrocyanide, and ferrous salts, which, owing to absorption of oxygen usually contain larger or smaller quantities of ferric salts, give a bluish-white precipitate, and this on shaking with air assumes a dark blue colour Ferric salts are readily detected by the blood-red coloration which they produce with soluble thiocyanates

With alkalis ferrous salts give a white, or usually greenish precipitate, which quickly changes to a dark-green colour on exposure to air, and afterwards becomes brown Ferric salts at once give a reddish-brown precipitate

It has been stated already that manganese is obtained together with iron in the course of qualitative analysis and the mode of their separation has been described The precipitate containing ferric hydroxide may also contain uranium This is readily

separated by digesting the precipitate with a concentrated solution of ammonium carbonate The washed residue is then dissolved in hydrochloric acid and the confirmatory test for iron applied

In the processes of *quantitative analysis* iron is estimated both gravimetrically and volumetncally In the first case the iron must be present as ferric salt Ferrous salts are, therefore, previously oxidised with nitric acid and then precipitated with ammonia, the precipitate is washed with boiling water, dried, ignited, and weighed as the sesquioxide If the solution should contain tartaric acid, sugar, or other organic compounds, ammonia produces no precipitate In these cases the iron must be previously precipitated as sulphide, this is well washed with water containing ammonium sulphide, dissolved in nitric acid and the iron precipitated with ammonia, or the organic compound may be destroyed by ignition If other metals precipitable by ammonia and ammonium sulphide are piesent, the iron can be separated by adding sodium or ammonium formate, acetate, or succinate to the neutral solution and boiling, when basic ferric formate, acetate, or succinate is thrown down This is filtered whilst hot, washed with boiling water, dried, ignited, and weighed as ferric oxide The precipitate may contain alumina, and this must then be separated by means of caustic potash For the separation of iron from various other metals the use of nitrosophenylhydroxylamine, known as " cupferron," has been proposed [x]

The chief *volumetric* processes for the estimation of iron depend upon the amount of oxygen required to convert it from the ferrous into the ferric form, and the solutions to be tested must first have the iron completely reduced to the ferrous state For this purpose many reducing agents may be employed, the methods most frequently used being (1) treatment with zinc or aluminium in acid solution, (2) treatment with sulphuretted hydrogen, (3) boiling with ammonium bisulphite solution, (4) addition of stannous chloride to the boiling solution, and (5) shaking the solution acidified by hydrochloric acid with a little mercury[2] In the case of (2) and (3) the excess of reducing agent is removed by boiling, and in (4) the excess of stannous chloride is precipitated by addition of mercuric chloride

[1] **Baudisch,** *Chem Zeit,* **1909, 33, 1298, Biltz and Hodtke,** *Zett anorg Chem* **, 1910, 66, 426, Fresenius,** *Zett anal Chem* **, 1911, 6O, 35**

[2] **McCay and Anderson,** *J Amer Chem Soc* **, 1921, 43, 2372**

The oxidising medium employed is a standard solution of potassium permanganate or dichromate, these being standardised by means of pure iron wire, recrystalhsed oxalic acid, or pure ferrous ammomum sulphate, $FeSO_4,(NH_4)_2SO_4,6H_{20}$, the latter containing exactly one-seventh of its weight of iron In carrying out the permanganate method, the ferrous solution prepared as above described is acidified with sulphuric acid and titrated with the permanganate solution until a permanent pink coloration is produced Permanganate cannot, however, be used when hydrochloric acid is present without special precautions, and in that case it is better to employ dichromate, which may also be used in presence of sulphuric acid The completion of the reaction is ascertained in this case by bringing a drop of the solution in contact with a very dilute freshly prepared solution of potassium ferricyanide, free from ferrocyanide, on a white porcelain plate, the dichromate is added until no blue coloration is obtained

Methods have also been proposed for the direct volumetric estimation of ferric iron, without a preliminary reduction to the ferrous state The reducing agent chiefly employed for this purpose, in the form of a standard solution, is titamum trichloride (p 842), potassium thiocyanate being added as indicator to the acidified solution of the ferric salt The titration is carried out in an atmosphere free from oxygen, and the addition of titanium trichloride is continued until the red colour due to ferric thiocyanate has disappeared[1]

The Atomic Weight of iron has been accurately determined by several chemists Svanberg and Norhn,[2] by reducing the oxide in hydrogen, obtained the number 56 O9, Berzehus found 56 O5 by oxidising the metal with nitric acid, and Erdmann and Marchand,[3] who reduced the oxide in hydrogen, obtained 56 O2 Maumene,[4] dissolving pure iron wire in nitric acid and precipitating with ammonia, found the number 56 00, and Dumas,[5] by the analysis of ferric chloride, obtained 56 23, whilst the analysis of ferrous chloride gave 56 O9 By the reduction of ferric oxide, obtained from carefully purified ferric nitrate, with hydrogen, Richards and Baxter obtained the value 55 88 and from the amount of silver bromide yielded by ferrous bromide,

[1] **See Knecht and Hibbert, *New Eeduction Methods \n Volumetric Analysis* (Longmans, 1910)**

[2] ***Annalen*, 1844, 6O, 432**

[3] ***Ibid* , 62, 212**

[4] ***Ann Chim Phya* , 186O, [3], 3O, 38O**

[5] ***Ibid* , 1869, [3], 66 167.**

the number 55 85[1] The value at present (1922) adopted is 55 84

An examination of the mass spectrum of iron indicates that the element is a simple one and not a mixture of isotopes The atomic weight as given by this method is 55 94 ± O O5 There is possibly an isotope present in very small amounts of atomic weight 54[2]

COBALT Co = 58 97 At No 27

583 The word cobalt occurs in the writings of Paracelaus and Agricola as well as in those of " Basil Valentine ", two meanings were attached to this name, in the first place it signified a sprite or goblin supposed to haunt the mine, whilst in the second place it was used to denote certain minerals, which are too imperfectly described for exact identification It appears, however, that in this latter sense it was employed to designate minerals which, although they possessed the appearance of a well-known metallic ore, did not yield any of this metal when subjected to the usual treatment Hence the word came to signify a false ore In later times the same name was given to the mineral which was used for the purpose of colouring glass blue, and is still employed for the preparation of smalt In 1735, Brandt stated that the blue colour of smalt depends upon the presence of a peculiar metal to which he gave the name kobalt-rex, and in 1742 he showed that the colour of smalt does not depend, as had been believed, upon the presence of arsenic and iron, metals which are usually found in cobalt ores, for he found that some of these ores occur free from arsenic, and that these likewise give the blue colour The new metal was stated to be magnetic and extremely infusible These observations were confirmed by Bergman in 178O

Cobalt does not occur in the free state in nature, and its ores, which usually contain mckel, are not very widely distributed It is found as lmnaeite, $(Co,Ni,Fe)_3S_4$, skutterudite, $CoAs_3$, speiss-cobalt or jsmaltite, $(Co,Ni,Fe)As_2$, cobaltite or cobalt glance, (Co,Fe)AsS, earthy cobalt, or wad, $(CO,Mn)O,2MnO_2,4H_{20}$, erythnte, or cobalt bloom, $Co_3(AsO_4)_2,8H_{20}$, etc

[1] *Zeit anorg Chem*, 1900, **23,** 245, 1904, 88, 232 Compare Baxter and others, *J Amer Chem Soc* , 1911, 83, 319, 337, 1912, 34, 1657

[2] Aaton, *Nature,* **1922,110, 312**

The bulk of the cobalt of commerce is obtained from the district surrounding Cobalt city, in Ontario, where there are rich silver ores containing a notable proportion of cobalt and nickel, chiefly as arcades Deposits of oxides and sulphides of cobalt and nickel occur also in New Caledonia Cobalt is almost always found as a constituent of meteoric iron, and its presence has been detected in the solar atmosphere

Treatment of Cobalt Ores—For the preparation of cobalt compounds, speiss-cobalt or other arsenical ores are employed These, after roasting or calcination in the air, yield an impure cobalt arsenate which comes into commerce under the name of *zaffre*, and is further worked up as hereafter described The cobalt ores, however, mostly contain large quantities of nickel and iron as well as other metals, and for this reason they are usually smelted in order to get rid of the greater part of the iron, the process employed being similar to that which is used for the extraction of copper The roasted ore is fused with a flux of calcium carbonate or sand, when the iron slag flows on to the surface while the cobalt remains below as a heavy *speiss* or stone The roasted ore or the sperss is then dissolved in strong hydrochloric acid, any arsenate of iron which may be present being precipitated by the careful addition of bleaching powder solution and a small quantity of milk of lime, the clear supernatant liquid is drawn off, treated with sulphuretted hydrogen for the purpose of separating copper, bismuth, etc , and the oxide of cobalt is then precipitated from the clarified solution by bleaching powder The oxide thus obtained is washed and ignited, and this is brought into the market and largely used for colouring glass and porcelain, as well as for the preparation of the chloride and nitrate of cobalt This oxide usually contains iron, nickel, and other impurities

In the case of the New Caledonia ores, consisting chiefly of sulphides, the cobalt, nickel, etc , are converted into sulphates either by careful calcination at a moderate temperature, or by treatment with ferrous sulphate solution The cobalt is then separated from the other metals which form soluble sulphates, and is finally obtained as oxide

A small amount of cobalt is extracted in the form of oxide by the treatment of ores and metallurgical products containing mckel by a wet method These materials are roasted sweet *(i e* , free from sulphur and arsenic), and the oxides thus formed dissolved in hydrochloric or sulphuric acid. The solution is

then treated as described above for the separation of iron, the metals which are precipitated by sulphuretted hydrogen, and cobalt The liquid resulting from the separation of the cobalt is further treated with milk of lime for the separation of nickel hydroxide, which is afterwards reduced to metal[1]

584 *Preparation of Metallic Cobalt*—This metal is obtained as a grey powder by igniting the oxide in a current of dry hydrogen or carbon monoxide, or by reduction of the oxide with carbon or aluminium[2] By strongly heating the oxalate under a layer of powdered glass the metal can be obtained as a coherent mass, and this may be fused to a regulus by heating it in a crucible made of lime, magnesia, or graphite

Pure cobalt may be obtained, according to Winkler,[3] by electrolysing a solution of pure cobalt sulphate in presence of ammonium sulphate and ammonia, platinum electrodes being used The metal thus deposited invariably contains a small amount of oxygen (O 2—O 3 per cent), and must therefore be heated in pure hydrogen Pure metallic cobalt may be obtained also by heating cobalt carbonyl to a suitable temperature[4]

Cobalt possesses the colour of polished iron, it is, however, harder than this metal It melts at 14900,[5] and may be distilled in the electric furnace[6] It is malleable and very tough, it is magnetic up to 115O°, and has a specific gravity of 8 8 at 15°[7] Cobalt in the form of powder absorbs oxygen from the air, often with ignition, the compact metal, however, does not undergo change at the ordinary temperature, but slowly oxidises when heated, and at a very high temperature burns with a red flame The metal burns also at 15O° in nitric oxide, forming the monoxide[8] It is capable of absorbing 59-153 volumes of hydrogen, according to the physical state of the metal and the temperature The metal is readily soluble in hydrochloric, dilute sulphuric, and nitric acids, and decomposes steam at a red heat It may

[1] For other methods of treating cobalt ores, see Pedersen, *Metallurgies* 1911, 8, 335, Barth, *ibid* , 1912, 9, 199

[2] See *Report on Reduction of Cobalt Oxide, Department of Mines, Canada,* 1913, No 259

[3] *Zeit anorg Chem,* 1895, 8, 1

[4] Eng Patent 13207, 20/6/1908

[5] Day and Sosman, *Amer J Sci,* 1910,29, 161 See also Kalmus and Harper, *J Ind Eng Chem* , 1915, 7, 6

[6] Moissan, *Annalen,* 1906, **351,** 510

[7] Copaux, *Compt rend,* 1905, **140,** 657 See also Kalmus and Harper, *loc cit*

[8] Sabatier and Senderens, *Compt rend,* 1892, **114,** 1429

exist in the passive state, but exhibits this property to a less extent than nicker[1]

Cobalt combines with boron to form a crystalline compound which resembles the corresponding nickel compound, and is obtained in a similar manner[2]

The character of the alloys which cobalt forms with other metals has been investigated by the method of thermal analysis, controlled by microscopic observations[3]

Nickel and cobalt separate from their fused mixtures in mixed crystals, the composition of which is approximately that of the liquid from which they are deposited[4]

Cobalt may be used for electroplating A solution of 200 grams per litre of crystalline cobalt ammomum sulphate gives satisfactory coatings with a current density of 4 amperes per sq dem , but current densities up to 26 amperes per sq dem may be employed with a solution made as follows cobalt sulphate, 312 grams, sodium chloride, 19 6 grams, boric acid, nearly to saturation, water, 1 litre The deposition is then very much more rapid and the deposit much harder than in the case of nickel, so that thinner coatings suffice and they are also superior in appearance[5]

[1] Hittorf, *Zeit physikal Chem*, 1900,34,385, Byers, *J Amer Chem Soc*, 1908, 3O, 1718, Byers and King, *J Amer Chem Soc* , 1919, 41, 1902 W

[2] See du Jassonneix, *Compt rend* , 1907, 145, 240

[3] See Sahmen, *Zat anorg Chem* , 1908, 57, 1, Gwyer, *ibid* ,113, Lo konja, *ibid*, 59, 293, Ducellicz, *Bull Soc chim* , 1911, [4], 9, 1017, Hiege, *Zeit anorg Chem* , 1913, 83, 2,52, Uaydt and Tammann, *ibid* , 246, Kreiz, *Metall und Erz*, 1922, 19, 137

[4] Guerfcler and Tammann, *Zeit anorg Chem*, 1904, 42, 353, Kuer and Kaneko, *Metallurgie*, 1912, 9, 422 See also Ruer and Kaneko, *Fcrrum*, 1913, 10, 257

[5] Kalmus, Harper, and Savell, *J Ind Eng Chem* , 1915, 7, 379

COMPOUNDS OF COBALT,

COBALT AND OXYGEN

585 Cobalt forms three well-defined oxides

Cobalt monoxide, CoO,
Cobalt sesquioxide, Co_{203},
Tricobalt tetroxide, Co_3O_4

In addition to these, the dioxide, CoO_2, probably exists, and several others such as CogOg,[1] Co_6O_7,[2] Co_{405},[3] and Co_3O_5[4] have been described,[5] but are probably mixtures [6]

Of these oxides, the first, CoO, is a well-marked basic oxide, corresponding to the stable cobaltous salts in which the metal is divalent The sesquioxidq acts as a feebly basic oxide, the corresponding salts are unstable and are easily reduced to cobaltous salts The dioxide appears to have a decided acidic function, and several stable cobaltites are known

Cobalt Monoxide or Cobaltous Oxide, CoO—This compound is the stable oxide of cobalt when calcination takes place at 1000° and may be obtained by reducing the higher oxide by heating it either in a current of hydrogen to a temperature not above 25O°, or in a current of carbon dioxide to redness until its weight is constant (Russell)[7] It is a light brown powder, which does not alter in the air at the ordinary temperature When heated in the electric furnace, it melts and yields rose-coloured needles

Cobaltous oxide combines with certain metallic oxides when they are heated together, a flux such as potassium chloride being usually employed With others, it forms solid solutions Many of these substances are beautifully coloured and are used as paints and pigments With aluminium oxide at 1100°, a blue compound, CoO,Al_{203}, is produced, and above this temperature a green one-of the composition $4CoO,3Al_{203}$[8] The blue substance is known as *Cobalt blue, Cobalt ultramarine, Thenard's blue*$_y$ or *Azure blue* Its exact colour and composition

[1] *Zeit anal Chem* , 1868, 7, 336, *J pr Chem* , 1856, 69, 131
[2] *Pogg Ann* , 1844,61, 472, 1851, 84, 56O
[3] *Jahresber*, 1868, 265 [4] *Journ Chem Soc* , 1890, 58, 1213
[5] See also Taylor, *Mem Manch Phil Soc* , 1903, [5], 12, 1
[6] See Wohler and Balz, *Zeit Elektrochem* ,1921, 27, 406
[7] *Journ Chem Soc*, 1863,16, 51
[8] Hedvall, *Arkw Kern Min Qeol*, 1914, 5, No 16, 1,

depend upon the method of preparation, and as the cobalt is sometimes precipitated with sodium phosphate or arsenate it may contain cobalt phosphate and arsenate With stannic oxide, the dark green compound, $2CoO,SnO_2$, that is, cobalt orthostannate, Co_2SnO_4, is obtained [1] If excess of stanmc oxide be employed, the resulting mass acquires a blue shade, and the greater the excess the more pronounced does the blue colour become This substance is also manufactured and known as *Cceruleum, Ccehne,* or *Bleu Celeste* With zinc oxide, the green cobalt zmcate is produced, and this forms solid solutions with excess of zinc oxide [2] The substance is known as *Cobalt qreen,* or *Rmmann's green* With chromic oxide a green chromite, CoO,Cr_{203}, is obtained [2] which in the presence of excess of the oxide gives a bluish mass the exact shade of which depends upon the proportions of the oxides It is known as *New blue* A green vanadates tantalate, CoO,Ta_{205}, and a yellow uranate have also been observed[2] With magnesium oxide, cobalt oxide forms solid solutions the colour of which depends on the relative proportions of the oxides and varies from light to dark red [3] The mass is known as *Cobalt red* Solid solutions also result with manganous oxide and with nickelous oxide [4]

Cobaltous Hydroxide, $Co(OH)_2$, is obtained by precipitating a cobaltous salt with caustic potash in the absence of air A blue precipitate is first obtained, and this, on boiling, is quickly converted into a rose-red coloured hydroxide The blue precipitate was regarded as a basic salt, but Hantzsch [5] has shown that any basic salt present can be washed out without any change of colour occurring Both the blue and rose varieties are hydroxides which differ only in the manner in which the water is combined The blue compound is completely dehydrated at 17O°, whereas the rose compound retains some water even after prolonged drying at 300° The blue compound has therefore been given the formula CoO,H_{20} and the rose compound $Co(OH)_2$ It absorbs oxygen from the air, the colour changing to bTown, and dissolves in hot very concentrated potash, crystallising out on pooling in microscopic prisms[6]

[1] Hedvall, *Arliv Kern Min Geol* , 1914, 5, No 18, 1
[2] *Ibid* , *Zat anorg Chem* , 1915,93, 313, *ibid,* 1916, 96, 71
[3] *Ibid,* 1914, 86, 296
[4] *Ibid,* 1915, 92, 381
[5] *Zeit anorg Chem,* 1912,73, 3O4
[6] Be Schulten, *Compt rend,* 1889,**109,** 266 Compare Job , *ibid* , 1907,**144,** 1044

The cobaltous salts may be prepared by the action of acids on cobaltous hydroxide They are the most stable of the cobalt salts, but undergo oxidation more readily than the corresponding compounds of nickel In the anhydrous state they are deep violet or blue, in the hydrated condition, rose-red

Cobaltic Oxide or Cobalt Sesquioxide, Co_{203}, is a dark-brown powder, formed by gently igniting the nitrate

Cobaltic Hydroxide, $Co(OH)_3$, is prepared by precipitating a cobalt salt with an alkaline hypochlorite solution The composition of this precipitate depends on the conditions under which it has been produced, and frequently, especially when prepared in the cold, it contains more oxygen than corresponds to the formula Co_{203} [1] The sesquioxide is also obtained in a hydrated condition when an alkaline solution of cobalt sulphate is electrolysed,[2] or when a solution of the same salt is treated with potassium or ammomum persulphate [3] It forms a browmsh-black powder, which is decomposed by hydrochloric acid with evolution of chlorine, and by oxy-acids with evolution of oxygen

The sesquioxide and its hydroxide act, therefore, as peroxides, but at the same time they possess weak basic properties, inasmuch as they dissolve in well-cooled acids, forming brownish-yellow solutions believed to contain cobaltic salts One of the most stable of these compounds is a strongly coloured solution obtained by dissolving the hydroxide in acetic acid, this decomposes only when heated The corresponding sulphate and some of its double salts have been isolated in the crystalline form

Tricobalt Tetroxide or Cobalto-cobaltic Oxide, Co_3O_4—This compound, which corresponds to the magnetic oxide of iron, is formed when one of the other oxides or the nitrate is heated to a temperature below 910° in the air,[4] thus obtained, it forms a black powder having a specific gravity of about 6 O If a dry mixture of sal-ammoniac and cobalt oxalate or cobalt chloride be heated in the air, or in oxygen, this compound is obtained in hard, microscopic octahedra, which have a metallic lustre and are not magnetic It is obtained in the hydrated state by the oxidation of moist cobaltous hydroxide in the air and also by warmrtig cobaltous hydroxide with excess of potassium

[1] Camot, *Compt rend,* 1889, **108,** 610, Schroder, *Journ Chem Soc,* 1890, 58, 1213, Huttner, *Zeit anorg Chem,* 1901, 27, 81

[2] Coehn and Glaser, *Zeit anorg Chem* , 1903, 33, 9

[3] Mawrow, *Zeit anorg Chem,* 1900, 24, 263, Huttner, *loc cit*

[4] See Burgstaller, *Chem Zentr* , 1912, i l , 1525

persulphate, washing and heating the product at 100° with dilute nitric acid[1] When heated in the oxy-coal-gas flame it yields metallic cobalt, which becomes covered with a film of oxide as it cools[2] The substance obtained by fusing one of the oxides with caustic potash, which was thought to be a potassium cobaltite,[3] $Co_{9016}K_2,3H_{20}$, is probably cobalto-cobaltic oxide contaminated with potash,[4] or cobaltous potassium cobaltite[5]

Cobalt Dioxide, CoO_2, has not been obtained in the pure state It appears, however, to be formed as a greenish-black piecipitate when iodine and caustic soda are added to a solution of a cobaltous salt[6] An oxide approaching this in composition is also formed by the action of a hypochlorite on a cobaltous salt, and probably brings about the well-known evolution of oxygen which occurs when bleaching powder solution is warmed with a small quantity of a cobalt salt (Vol I, p 245)[7]

According to McConnell and Hanes,[8] when cobaltous hydroxide is suspended in water and tested with hydrogen peroxide, and the liquid filtered, a strongly acid, colourless filtrate is obtained which appears to contain cobaltous acid, H_2CoO_3 If potassium bicarbonate be added to this filtrate, or if the oxidation be carried out in presence of potassium bicarbonate, a green solution is obtained, which probably contains potassium cobaltite, K_2CoO_3 On the other hand, Durrant[9] has failed to obtain evidence of the existence of this acid, and considers the green colour to be due to a derivative of cobaltic oxide to which he assigns the formula $[Co(KCO_3)_2]_{20}$ Metzl[10] finds that the green precipitate is a mixture of cobaltous carbonate and cobalt cobaltite of the composition $CoCO_3,CoCoO_3$ Similar green compounds have been obtained with potassium salts of organic carboxyhc acids and these may be formulated as derivatives of the radicle $>CoOCo<$ Sulphuric and sulphurous acids decolorise the green solution, but the colour reappears on neutralisation with potassium bicarbonate Acetic acid does not

[1] Mawrow, *loc cit* [2] Read, *Journ Chem Soc*, 1894, 65, 314

[3] Schwarzenberg, *Annalen,* 1856, 97, 212, Pebal, *ibid,* 1856, **100,** 257, Mayer, *ibid,* 1857, **101,** 266

[4] McConnell and Hanes, *Journ Chem Soc*, 1897, 71, 584

[5] Bellucci and Dominiei, *Atti B Accad Lincei,* 1907, (5), 16, i, 315

[6] Vortinann, *Ber*, 1891, 24, 2744, Metzl, *Zeit anorg Chem*, 1914, 86, 358

[7] McLeod, *British Assoc Beports,* 1892, 669 But see Howell, *Journ Chem Soc,* 1923, **123,** 65

[8] *Loc cit*

[9] *Proc Chem Soc,* 1896, **12,** 96, 244, *Journ Chem Soc,* 1905, 87, 1781, see also Job, *Compt rend*, 1898,12?, 100 [10] *Loc cit*

decolorise the liquid, whilst, on warming with sulphuric acid, a pink solution of cobaltous sulphate is obtained

Barium Cobaltie, BaO,CoO_2, and *Barium, Dicobaltite,* $BaO,2CoO_2$, are formed in black crystals when cobalt sesquioxide is fused with baryta and barium chloride[1] These compounds evolve chlorine when treated with hydrochloric acid

Magnesium Cobaltite, MgO,CoO_2, is formed as a deep garnet-red mass when magnesia is fused with cobalt sesquioxide in the electric furnace[2]

Cobaltous Cobaltite, $CoO,2CoO_2,2H_{20}$, is obtained by fusing cobaltous oxide with potassium peroxide, washing the cooled mass first with water and then with dilute sulphuric acid, and finally again with water, and drying over phosphoric oxide in a vacuum It forms six-sided plates, and evolves chlorine when treated with hydrochloric acid[3]

COBALT AND THE HALOGENS

586 *Cobaltous Fluoride,* CoP_2, is obtained by dissolving the oxide or carbonate in hydrofluoric acid,[4] on evaporation, rose-red crystals are deposited having the composition $CoF_2,2H_{20}$ these are decomposed by boiling with the formation of a light red, insoluble oxyfluonde The anhydrous fluoride is prepared by heating the chloride with ammonium fluoride in a current of hydrogen fluoride, and forms rose-coloured prisms slightly soluble in water[5] It forms double salts with the alkali fluorides,[6] and absorbs dry ammonia to give the reddish-brown liquid hexammoniate, $CoF_2,6NH_3$ This loses ammonia in dry air giving the light pinkish-brown triammoniate, $CoF_2,3NH_3$, which loses all its ammonia at 40°[7]

Cobaltic Fluoride, CoF_3, is obtained as a green powder when a saturated solution of cobaltous fluoride in 40 per cent hydrofluoric acid is electrolysed in a platinum dish which acts as anode, a platinum wire being employed as cathode It is decomposed by water with formation of cobaltic hydroxide[8]

[1] Rousseata, *Compt rend,* 1889,**109,** 64 [2] Dufau, *ibid,* 1896,**123,** 239
[3] Hofmann and Hiendlmaier, *Ber,* 1906, 39, 3186 Compare Bellucci and Dominici, *Atti It Accad Lmcei,* [5], 1907,16,1, 315
[4] See Edminster and Cooper, *J Amer Chem Soc* , 1920, 43, 2419
[5] Poulenc, *Compt rend,* 1892,**114,** 1426
[6] Compare Bohm, *Zeit anorg Chem,* 1905, 48, 326
[7] Clark and Buckner, *J Amer Chem Soc* , 1922, **44,** 23O
[8] Barbien and Caizolan, *Atti R Accad Lincer,* 1905, [51**14,**1, 464.

Cobalt Chloride, CoCl —Powdered metallic cobalt takes fire when warmed in chlonlfe gas, forming blue, crystalline scales of the anhydrous chloride, which can be readily sublimed in a current of chlorine They dissolve in alcohol, forming a blue solution, and on addition of water first become violet, and then rose-coloured Cobalt chloride is obtained in aqueous solution by dissolving the carbonate, or one of the oxides, in hydrochloric acid, short, dark red, monochnic prisms crystallise on cooling the concentrated warm solution, these possess the composition $CoCl_2,6H_{20}$, and have a specific gravity of 1 84 When these crystals are allowed to stand over sulphuric acid at 5O°, the rose-coloured dihydrate, $CoCl_2,2H_{20}$, is formed, and when heated to 100° the deep violet monohydrate remains, which at 110-120° yields the blue, anhydrous chloride A hydrate with $4H_{20}$ has also been obtained[1] A strong aqueous solution is rose-coloured, but becomes blue when it is heated, and when concentrated hydrochloric or sulphuric acid or alcohol is added The rose colour is restored when the chloride of zinc, mercury, antimony, or tin is added to the solution which has been rendered blue by hydrochloric acid These changes of colour have been attributed by some to the formation and decomposition of double salts or complex ions, by others to the hydration and dehydration of the cobalt salt [2]

An unstable compound, $CoCl_2,HCl,3H_{20}$, separates in blue crystals at -23° from a saturated solution of cobalt chloride in hydrochlo which is also blue[3] A compound with iodine trichloride, $CoCl_2,2ICl_3,8H_{20}$, forms orange-red crystals [4]

When anhydrous cobalt chloride is treated with ammonia the compound $CoCl_2,6NH_3$ is formed [5] It is also obtained as dark rose-red crystals by passing ammonia into a saturated solution of cobalt chloride in methyl acetate [6]

[1] De Coninck, *Bull Acad roy Belg,* 1904, 117O.

[2] See Engel, *Bull Soc cmm,* 1891, 6, 239, Potilitzine, *ibid* , 264, fitard, *Compt rend,* 1891, **113,** 699, Charpy, *ibid,* 794, Sabatier, *ibid,* 1888, **107,** 42, Donnan and Bassett, *Journ Ghent Soc,* 1902, 81, 939, Hartley, *ibid* , 1903, 83, 401, Moore, *Zeit physikal Chem,* 1906, 55, 641, Lewis, *ibid,* 56, 223, Benrath, *Zeit anorg Chem,* 1907, 54, 328, Denham, *Zeit physikal Chem,* 1909, 65, 641, Houstoun, *Proc Boy Soc Edm,* 1911, **31,** 521-558 Kotschubei, *J Buss Phys Chem Soc* , 1914,46,1055

[3] Chassevant, *Ann Chim Phys,* 1893, [6], **3O,** 5

[4] Weinland and Schlegelmilch, *Zeit anorg Chem,* 1902, **3O,** 134

[5] Ephraim, *Ber* , 1912, 45, 1322

[6] Naumann, *ibid,* 1909, 42, 3789

Sympathetic Inks—If a dilute solution of the.chloride be used as an ink, the writing is not visible when it is allowed to dry in the air, but on warming, the characters appear of a bright blue colour, disappearing again gradually on standing in the air, owing to the absorption of moisture.

From this property the cobalt salts have been employed for the manufacture of the so-called *sympathetic inks,* by this is understood any liquid the writing of which is invisible under ordinary conditions, but can be rendered apparent by some simple treatment The first attempt at the preparation of such an ink depended upon the fact that a solution of lead acetate becomes black when treated with a decoction of orpiment in milk of lime These two liquids were mentioned by Lemery in 1681 as " encres appellees sympatluques " In the treatise termed *The Key to unlock the Cabinet of the Secrets of Nature,* published in 17O5, a method for preparing a sympathetic ink from certain bismuth ores is described The peculiar properties of this ink were believed to be due to bismuth, but in 1744 Gessner proved that the cobalt in the ores was the active agent in the production of the ink This property of the cobalt salts to change colour from rose to blue on loss of water has been applied also to the construction of floral hygrometers Artificial flowers are prepared, the petals of which are tinted with cobalt salts In damp weather the flower is pink, in dry weather violet or blue This invention is a Parisian one, and dates from 187O[2]

Cobalt Bromide, $CoBr_2$—If bromine vapour is passed over metallic cobalt at a dark-red heat, a green fused mass of the anhydrous bromide is formed By treating finely divided cobalt with bromine in dry ether, the compound $CoBr_2,(C_2H_5)_{20}$ is obtained as a green substance which, on heating, yields the anhydrous cobalt bromide, $CoBr_2$[2] The anhydrous salt absorbs water from the air, yielding a dark red kqiud This solution is obtained also by bringing cobalt, bromine, and water together, if the solution is allowed to stand over sulphuric acid, dark led prisms having the composition $CoBr_2,6H_{20}$ are deposited, and these when heat.ed to 100° give a purple mass containing $CoBr_2,2H_{20}$, which at 13O° yields the anhydrous bromide as an amorphous, green mass (Raminelsberg, Hartley) Several other hydrates are also known[3] Cobalt bromide forms a hexammoniate,

[1] **See Vanino, *Arch Pharm,* 1917, 255, 81**
[2] **Ducelhez and Raynaud, *Compt rend* , 1914,158, 2002**
[3] **Guaresohi, *Atti R Accad Set Torino,* 1913,48, 929**

$CoBr^{\wedge}NHg$, which is prepared in the same way as the corresponding chloride compound. It forms pale rose-red crystals which on heating to 120° dftompose, yielding the diammoniate, $CoBr_2,2NH_3$, which is light blue in colour

Cobalt Iodide, CoI_2—This substance is obtained in the anhydrous state by heating the metal in iodine vapour It is also produced with evolution of heat when finely divided cobalt is gently warmed with water and iodine The saturated solution is red up to 20°, and then passes through brown and ohve to green at 35° When poured into a saturated solution of magnesium chloride, a blue solution is formed (Etard) The hydrate, $CoI_2,6H_{20}$, is dark red, whilst the tetrahydrate and the dihydrate are green, and the anhydrous salt resembles iodine Double salts of this compound with other iodides are known [2] Cobalt iodide gives two ammoniates, $CoI_2,6NH_3$ and $CoI_2,4NH_3$

Cobalt Chlorate, $Co(C10_3)_2$, is a somewhat unstable salt, which forms various hydrates [3]

Cobalt Perchlorate has also been prepared [4]

Cobalt lodate, $Co(IO_3)_2$, crystallises from water in three forms as anhydrous salt, as dihydrate, and as tetrahydrate [5]

COBALT AND SULPHUR

587 *Cobalt Moyiosulphide,* CoS, is obtained as a black, hydrated piecipitate when a solution of a cobalt salt is mixed with ammonium sulphide It dissolves in concentrated hydrochloric acid with evolution of sulphuretted hydrogen The cold dilute acid dissolves it but slowly, whilst it is almost insoluble in dilute acetic acid The monosulphide is found as an Indian mineral known as syepoonte, occurring in ancient schists in grains O1 veins of a yellowish steel-grey colour It may be made artificially by heating cobalt sulphate with barium sulphide and sodium chloride

When the monosulphide is mixed with sulphur and the mixture ignited in a current of hydrogen, the following sulphides are formed according to the temperature employed CoS_2, Co_2S_3, CoS, and at a white heat, Co_2S (H Rose)

[1] **Naumann,** ***loc cit***

[2] **Dobroserdoff,** ***J Buss Phys Chent Soc,*** **1901, 38, 3O3, Mosmer,** ***Ann Chim Phys*** **, 1897, [7], 12, 374**

[3] **Meusser,** ***Ber,*** **1902, 35, 1417**

[4] **Goldblum and Terhkowski,** ***Bull Soc chim,*** **1912, [4], 11, 103, 146 Salvadon,** ***Gazz,*** **1912, 42, 1 458**

[5] **Meusser,** ***Ber*** **, 1901, 34, 2432**

Investigation of the freezing points of mixtures of cobalt and sulphur, containing up to 33*6 per cent of the latter element, indicates the existence of the compounds Co_4S_3 and CoS [1]

Cobalt pyrites or lmnaeite, $(Co,Ni,Fe)_8S_4$, occurs at Bastnas, near Riddarhyttan, at Mussen in Prussia, as well as at Mineral Hill in Maryland, and at Mine La Motte in Missouri It forms steel-grey or tarmshed copper-red regular octahedra, and occurs also in the massive state It usually contains more or less nickel, as well as some iron and copper It can be obtained artificially as a blackish-grey powder by heating a solution of a cobalt salt with potassium polysulphide to 160°

A *polysulphide of cobalt,* which probably has the formula Co_2S_7, is obtained as a black precipitate when a solution of sodium monosulphide saturated with sulphur is added to one of cobalt chloride at the ordinary temperature [2]

Cobaltous Sulphite, $CoSO_3$,5H2,O, is a pink, crystalline powder obtained by the action of sulphurous acid on cobaltous hydroxide. It forms double salts with the alkali sulphites

Cobaltic Sulphite has not been isolated, but several double compounds, which are probably salts of a complex cobalti-sulphurous acid, $H_3[Co(SO_3)_3]$, have been described [3]

Cobaltous Sulphate, $CoSO_4,7H_{20}$ —This salt occurs native as cobalt vitriol, or biebente, in crystalhne crusts It is prepared artificially by dissolving the carbonate or oxide in dilute sulphuric acid, and crystallises in red prisms isomorphous with ferrous and nickel sulphate, which are unalterable in the air It has a specific gravity of 1 924 (Schiff), possesses a weak, astringent, metallic taste, is easily soluble in water, but does not dissolve in alcohol According to Mulder, 100 parts of water dissolve

At	0°	10°	20°	30°	50°	70°	100°
$CoSO_4$	24 6	29 5	34 5	40 2	518	63 8	82 6

When its solution is allowed to stand at 40-5O°, monochnic crystals having the composition $CoSO_4,6H_{20}$ are formed, and these are isomorphous with the corresponding zinc salt If a concentrated solution of cobalt sulphate is poured gently into sulphuric acid a peach-blossom coloured powder, $CoSO_4,4H_{20}$, is deposited The hydrate, $CoSO_4,H_{20}$, is deposited when a solution of the salt is made slightly acid with sulphuric acid and

[1] Friedrich, *Metallurgie,* **1908,** 5, 212 Compare Bellucci, *Atti B Accad Lincei,* 1908, [5], **17,** i, **18**

[2] Chesneau, *Compt rend ,* **1896,**123, **1068**

[3] Berglund, *Ber,* **1874, 7, 469**

evaporated[1] All the hydrates lose their water on heating, but do not fuse, becoming opaque and of a rose-red colour (Proust) Cobalt sulphate forms numerous double salts The double sulphates with ammonium and the alkah metals form a series all isomorphous with the corresponding ferrous and nickle double salts,[2] and also with the double selenates.[3] The double salt of cobalt sulphate with mercuric cyanide, $CoSO_4,Hg(CN)_2,10H_{20}$, is interesting[4] Cobalt sulphate has the power of absorbing notable quantities of nitric oxide, although the absorption is not accompamed by any change of colour[5] It combines also with ammonia, giving a hexammoniate, $CoSO_4,6NH_3$[6]

Cobaltic Sulphate, $Co_2(SO_4)_3,18H_{20}$, is deposited in blue, silky needles, when a cooled acid solution of cobaltous sulphate is electrolysed in a divided cell It dissolves in water, forming a blue solution which rapidly decomposes to cobaltous sulphate with evolution of oxygen The crystals decompose on exposure to the air, finally becoming pink It forms a greenish-blue solution in dilute sulphuric acid, which gives a black precipitate with alkalis and is rapidly decomposed by reducing agents With hydrochloric acid, chlorine is evolved[7]

Cobaltic Ammonium Alum, $(NH_4)_2SO_4,Co_2(SO_4)_3,24H_{20}$, is obtained by adding ammomum sulphate to an acid solution of cobaltous sulphate and passing a weak current It forms blue octahedra and is stable when dry, but decomposes in solution, ozonised oxygen being liberated The potassium, rubidium, and caesium alums have been obtained in a similar manner[8]

COBALT AND NITROGEN

588 *Cobalt Nitride,* Co_2N, is obtained as a dull grey powder[9] when metallic cobalt is heated in ammonia at about 47O° It is soluble in hydrochloric and sulphuric acids, and loses its nitrogen when heated to 600° The nitride, Co_3N_2, is obtained by passing a mixture of cobaltous oxide and anhydrous cobalt

[1] **Lescoeur,** ***Ann Chim Phys*** **, 1895, [7], 4, 213**
[2] **Tutton,** ***Phil Trans,*** **1915,** ***[A],*** **216, 1**
[3] ***Ibid*** **,** ***Proc Roy Soc*** **, 1919,** ***[A],*** **96, 156**
[4] **Scagharini and Bonini,** ***Gazz*** **, 1920, 5O,11, 114**
[5] **Hufner,** ***Zeit physikal Chem,*** **1907, 59, 416**
[6] **See Ephraim,** ***Ber*** **, 1912, 45, 1322**
[7] **Marshall,** ***Journ Chem Soc*** **, 1891, 59, 76O**
[8] ***Idem*** **,** ***ibid*** **, Howe and O'Neal,** ***J Amer Chem Soc*** **, 1898, 20, 759**
[9] **Beilby and Henderson,** ***Journ Chem Soc,*** **1901, 79, 1251**

cyanide between the poles of an electric arc in an atmosphere of nitrogen It burns in oxygen, yielding cobaltous oxide and nitrogen peroxide, and is soluble in hydrochloric and nitric acids [1]

Cobalt Azoimide, or *Azide,* $Co(N_3)_2$, together with a *basic azoimide,* $N_3Co(OH)$, is obtained by the action of aqueous azoimide on a cobalt salt, as a violet powder [2] It has been prepared in the pure state by shaking the finely divided dry basic azide or cobalt carbonate with an ethereal solution of azoimide [3] It is extremely explosive, even gentle rubbing causing a violent detonation It is soluble in water, but the solution is rapidly hydrolysed Double compounds with potassium and ammomum azoimides have also been obtained

Nitro-cobalt, $Co_2(NO_2)$, is formed when diluted nitrogen peroxide is passed over reduced metallic cobalt It is a black mass, which is vigorously decomposed by water, and explodes when mixed with combustible matter [4]

Cobalt Nitrite—Neither cobaltous nor cobaltic nitrite has been prepared in the solid state [5] The double potassium salt described below differs in many of its properties from an ordinary nitrite, and is probably, like the cobalticyanides and the cobalt-ammine salts, a derivative of a complex acid [6]

Potassium Cobaltimtrite, $K_3[Co(NO_2)_6]$, which is known as Fischer's salt after its discoverer,[7] is obtained as a yellow precipitate when the solution of a cobaltous salt, acidified with acetic acid, is mixed with a solution of potassium nitrite

$$CoCl_2+5KNO_2+2HNO_2=K_3Co(NO_2)_6+2KCl+NO+H_2O$$

As this salt is somewhat soluble in water, it is best to wash it with a solution of potassium acetate, and then with 8O per cent alcohol It is also produced by passing nitrous fumes into a suspension of cobalt carbonate in a solution of potassium carbonate or nitrite Cobalt yellow, as this compound is also termed, is a bright yellow powder consisting of microscopic pyramids, or of four- or six-sided stellated forms According to Sadtler,[8] the salt is usually anhydrous, it can, however, be obtained,

[1] Vournasos, *Compt rend,* 1919,**168,** 889
[2] Curtius and Rissom, *J pr Chem,* 1898, [2], 58, 261
[3] Wohler and Martin, *Ber ,* 1917, 5O, 586, *Zeit angew Chem ,* 1917, 3O, i 33
[4] Sabatier and Senderens, *Bull Soc chim ,* 1893, [3], 9, 669
[5] See Suzuki, *Journ Chem Soc ,* 1910, 97, 726
[6] Hofmann and Burger, *Ber,* 1907, 40, 3298, Rosenheim and Garfunkel, *tbid,* 1911,44, 1865
[7] *Pogg Ann ,* 1848, 74, 124
[8] *Amer J Sci,* [2], 187O, 49, 189

according to the concentration of the solution, with from one to four molecules of water, and its colour then varies from a bright yellow to a dark greenish-yellow It is decomposed by nitric and hydrochloric acids, but only when heated Caustic potash solution attacks it with difficulty Caustic soda or baryta water, on the other hand, decomposes it readily, on gently warming, with precipitation of the brown hydroxide The salt suspended in water is only slowly attacked by sulphuretted hydrogen, but ammomum sulphide instantly precipitates black cobalt sulphide The fact that cobalt is precipitated by a solution of potassium nitrite, acidified with acetic acid, is employed in the analytical separation of cobalt from nickel and other metals [1]

Sodium cobaltinitrite is made in a similar way, but owing to its solubility in water it is precipitated from the aqueous solution by addition of alcohol A solution of this salt is used for testing for potassium,[2] a yellow precipitate of the insoluble potassium salt being obtained The corresponding compounds of rubidium and caesium are distinguished by being only one-tenth as soluble as their platimchlondes [3] The corresponding ammomum, silver, thallium, lead, and barium compounds can be prepared by double decomposition of a soluble salt with the sodium compound

If a solution of cobalt chloride be precipitated with potassium nitrite without addition of acid, a yellow, hydrated precipitate of potassium cobaltous nitrite, $2KNO_2,Co(NO_2)_2$, is obtained, soluble in hot water and yielding a red solution [4]

Cobalt Nitrate, $Co(NO_3)_2,6H_{20}$ —This substance is obtained by dissolving the oxides, hydroxides, or carbonate in nitric acid, and generally forms an indistinctly pink, crystalline mass It may be obtained by slow evaporation in monochmc prisms, having a specific gravity of 1 83 and not undergoing change in dry air It begins to melt below 100°, and when more strongly heated the violet liquid becomes thick and green, then it begins to boil, giving off nitrous fumes, and the black oxide is left Anhydrous cobalt nitrate is a slightly pink powder, which begins to decompose at 100-105°[5] Hydrates with nine and three

[1] **Funk,** ***Zeit anal Chem,*** **1907, 48, 1**

[2] **See Adie and Wood,** ***Journ Chem Soc,*** **1900, 77, 1076, Bnlmann,** ***Zeit anal Chem*** **, 1900, 39, 284, Cunningham and Perkin,** ***Joirn Chem Sot,*** **1909, 95, 1562, Burgess and Kamm,** ***J Amer Chem Soc*** **, 1912, 34, 652**

[3] **Rosenbladt,** ***Ber,*** **1886, 19, 2531**

[4] **Erdmann,** ***J pr Chem*** **, 1866, 97, 385**

[5] **Guntz and Martin,** ***Bull Soc chim*** **, 1909, [4], 5,1004**

molecules of water also exist [1] Cobalt nitrate gives a hexammoniate It forms a double nitrate with bismuth of the composition $3Co(NO_3)_2,2Bi(NO_3)3,24H_{20}$,[2] and a double salt with mercuric cyanide, $Co(NO_3)_2Hg(CN)_2,6H_{20}$[3]

AMMONIACAL COBALT COMPOUNDS OR COBALTAMMINE SALTS

589 In 1799, Tassaert[4] observed that a solution of a cobalt salt in ammonia assumes a brown colour on exposure to the air, and that this changes on boiling to a wine-red, whilst Thenard,[5] in 18O2, stated that these changes were brought about by an absorption of oxygen This latter observation was confirmed by Proust, who found that, on evaporating the solution, black cobaltic oxide separates out The compounds which are thus formed have attracted the attention of many chemists,[6] and a very large number of these cobaltammine salts have been prepared, as well as compounds with organic substituted ammonias such as pyridine, qumolme, ethylene diamine, etc A general account of this class of substances has been given on p 1087, and only one or two typical compounds of each class are here described

(1) *Rexammine Salts (Luteo-salts),* $[(NH_3)_6Co]X_3$, where X is a univalent acid radicle, are formed when dilute solutions of cobaltous salts, containing a large amount of ammonia and ammonium chloride, are exposed to the oxidising action of the air, they are produced also by the action of ammonia on many of the salts containing five molecules of ammonia

The compound *Hexammine-cobaltic Chloride (LuteocobalHc Chloride),* $[(NH_3)_6Co]Cl_3$, is obtained when an ammoniacal cobalt chloride solution is allowed to stand for some time, especially in the presence of sal-ammoniac The formation of the salt is facilitated by the addition of oxidising substances such as lead dioxide, bromine, etc (Braun, Mills) It crystallises in reddish-yellow, monoclmic prisms or pyramids, which dissolve slowly in cold but readily in hot water It forms a sparingly soluble platinichlonde

[1] Funk, *Zeit anorg Chem* , 1899, 20, 407
[2] Urbain and Lacombe, *Compt rend* , 1903,**137,** 568
[3] Scagharim and Bonini, *Gazz* , 1920, 5O, u 114
[4] *Ann Chim* , 1798, 28, 95 [5] *Ibid* , 18O2, 42, 210
[6] A history of these compounds wdl be found in *Untersuchungen der Ammoniakahsche Kobalt Verbindungen,* by Fr Rose, Heidelberg, 1871 For more recent work, see the references on p 1348

(2) *Pentammine Salts* form two distinct classes of compounds, the *aquo-pentammine salts ^roseo-salts),* $[H_{20}(NH_3)_5Co]X_3$, and the *acido-pentammine salts,* $[X(NH_3)_5Co]X_2$ The latter salts have been distinguished by different names according to the nature of the acid group in the complex radicle, the salts of the various series usually possessing characteristic colours

The aquopentammine salts, which are pink, lose water when heated with acids, forming derivatives of the second class, whilst the latter are reconverted into aquopentammine salts by boiling or standing with water By the action of ammonia on the aquopentammine salts the so-called hydroxypentamminecobalt salts are obtained, thus $[(H_{20})(NH_3)_5Co]X_3 + NH_3 = [(OH)(NH_3)_5Co]X_2 + NH_4X$

Chloro-pentammine-cobaltic Chloride (Chloropurpureo-cobaltie Chloride), $[Cl(NH_3)_5Co]Cl_2$, is obtained by boiling a solution of roseo-cobaltic chloride, it falls as a red precipitate, soluble at 10° in 287 parts of water, and crystallising in tetragonal prisms With platinichlonc acid, it forms the salt, $[Cl(NH_3)_5Co]PtCl_6$, which is almost insoluble in cold water, and separates as a browmsh-red powder If the chloride be triturated with strong sulphuric acid, a solution of *chloro-pentammine-cobaltic sulphate,* $[Cl(NH_3)_5Co]SO_4$, is formed, and if nitric acid be added to this solution fine, led, microscopic crystals of *chloro-pentammine-cobaltic nitrate,* $[Cl(NH_3)_5Co](NO_3)_2$, are thrown down, the solution of which is not precipitated by silver nitrate

(3) *Tetrammwe Salts* are analogous to the pentammine salts, but the complex radicle contains only four molecules of ammonia and two other groups, which may be water or the hydroxy-group or a univalent acid radicle

Dichloro-tetrammine-cobaltic Chloride (Praseo-cobaltic Chloride), $[Cl_2(NH_3)_4Co]Cl,H_{20}$, is usually formed together with the other cobaltammine chlorides It crystallises in small, glistening needles which possess an emerald green colour, whence the term praseo is derived These dissolve in water, yielding a green solution which soon becomes red, and undergoes decomposition on boiling If fusco-cobaltic chloride, $Co(NH_3)_4Cl_2(OH)$, be warmed with dilute hydrochloric acid, a deep violet solution is obtained, and this on cooling deposits small violet octahedra which possess the same composition as the green salt, and pass into the latter when dissolved in concentrated sulphuric acid, to which hydrochloric acid is gradually added

Dimtrito-tetrammine-cobaltic Sulphate (Croceo-cobaltic Sulphate),

$[(NO_2)_2(NH_3)_4Co]_2SO_4$, is formed when a mixture of solutions of cobalt sulphate and potassium nitrite, saturated with ammonia, is exposed to the air It is deposited in orange-yellow crystals together with green cobaltic hydroxide The mixture is filtered and the residue dissolved in hot dilute nitric acid, and from this solution the sulphate is obtained on cooling in the form of yellow tetragonal tablets Large wine-red crystals are also obtained from dilute solutions It is slightly soluble in boiling water

(4) *Tnammine compounds* are formed from the tetrammine salts by loss of ammonia They possess the general formula $[X_3(NH_3)_3Co]$, and are non-electrolytes in aqueous solution *Aqitotnammine salts* are also known, with one or more of the acid groups outside the complex radicle, which contains one molecule of water for each acid group replaced

Trinitrito-triammine-cobalt, $[(NO_2)3(NH_3)_3Co]$, is prepared by acting on cobaltous chloride solution with ammonia and potassium nitrite (Erdmann), and by the action of ammomum nitrite on cobaltous chloride in presence of acetic acid (Gibbs)

Triaquo-triammine-cobaltic Chloride, $[(H_{20})_3(NH_3)_3Co]Cl_3$, is prepared from trmitiito-triammine-cobalt by treating first with dilute acetic acid and then with hydrochloric acid at O°

(5) *Diammine salts* have been very slightly investigated

Potassium Tetranitrito-diammine cobaltite (Erdmann's salt) $[(NO_2)_4(NH_3)_2Co]K$, is obtained by adding ammomum chloride and potassium nitrite to a solution of cobaltous chloride and gently warming It forms yellow, rhombic crystals

In addition to the classes of compounds already described, several series of substances have been prepared which Werner terms multi-nuclear ammoniacal compounds[1] Examples of these are the *oxycobaltammines,* $\{O_2[Co_2(NH_3)_5]_2jX_4$, and the series $\{NH[Co(OH)_2(NH_3)_4]_2\}X_4$, and $Co[Co(OH)_2(NH_3)_4]_3X_6$

The relations between the various complex cobalt compounds just described have been successfully interpreted by means of Werner's theory of principal and supplementary valencies (see p 36) The further development of this theory has suggested the possibility of the occurrence of *cis-* and trans-isomerism and of optical isomerism—deductions that have been fully verified by the preparation of substances of this description These deductions are based on the view that the six groups associated

[1] **Werner, *Ber,* 1907, 40, 66, 2103**

with the cobalt atom are arranged round this central atom in the positions corresponding with the angles of an octahedron [1]

COBALT WITH PHOSPHQRUS, ARSENIC, AND ANTIMONY

590 *Phosphides of Cobalt*—When pieces of phosphorus are thrown on to heated cobalt a bluish-white, brittle mass with a metallic lustre is formed This tarnishes on exposure to air, melts at a lower temperature than cobalt, and contains 6 per cent of phosphorus On heating, it burns, with formation of a dark blue glass (Pelletier) When cobalt reduced in hydrogen is heated to dark redness in the vapour of phosphorus, a light grey mass with a metallic lustre is formed, containing 28 4 per cent of phosphorus (Schrotter), and corresponding nearly to the formula Co_4P_3 A compound, Co_3P_2, is also formed as a black powder by igniting a normal phosphate in a current of hydrogen

The *phosphide,* Co_2P, is obtained when cobalt formed by reduction of the oxide or oxalate is heated to redness in the vapour of phosphorus trichloride, tribromide or di-iodide,[2] and a substance of this composition is also produced in grey crystals when finely divided cobalt is heated with a copper phosphide in the electric furnace[3] The existence of this compound is indicated by the occurrence of a maximum on the freezing-point curve for mixtures of phosphorus and cobalt [4] Another compound, Co_3P_3, is obtained as a black, metallic mass by heating cobalt chloride to dull redness in phosphorus vapour [5]

Cobalt Arsenide, $CoAs_3$, occurs as skutterudite near Modum, in Norway, crystallised in octahedral forms as well as in the massive state It possesses a colour from tin-white to a pale lead-grey, and usually contains small quantities of iron and sulphur Smaltite or tin-white cobalt, $CoAs_2$, usually contains varying quantities of iron and nickel, and occurs in tin-white octahedral forms as well as in the massive state in the Erzgebirge Cobaltite, cobalt glance, or bright white cobalt, $CoAs_2$,CoS_2 or CoAsS, crystallises in the regular system, usually in pyramid octahedia and their combinations, and a portion of the cobalt is

[1] For a summary of Werner's later work, on both the theoretical and practical sides, see *Chemical Society's Annual Reports,* 1911, 8, 77, also Werner, *Ber* , 1912, 45, 121

[2] Granger, *Compt rend,* 1896, **123,** 176

[3] Maronneau, *ibid,* 1900, **13O,** 656

[4] Schemtschuschny and Schepeleff, *Zeit anorg Chem* , 1909, 64, 245

[6] Granger, *Compt rend,* 1896,**122,** 1484

generally replaced by iron It has a silver-white colour inclining to led, and occurs in Sweden, in Westphalia, and in the Bottolack Mine near St Just in Cornwall Other arsenides, Co_3As_2, CoAs, and Co_2As_3, have been prepared [1]

Cobalt anhmonide, CoSb, and *cobalt dt-antimonide,* $CoSb_2$, are crystalline powders melting about 1200° and 700° respectively [2]

Phosphates and Arsenates of Cobalt —The normal and monohydrogen cobalt salts of the different modifications of phosphoric acid are rose-red or violet-blue, insoluble compounds The di-hydrogen-orthophosphate is easily soluble in water and forms a gummy mass The arsenates are similar bodies, the normal arsenate, $Co_3(AsO_4)_2,8H_{20}$, occurs native as cobalt bloom or erythnte, in violet, monochnic needles isomorphous with vivianlte, or in earthy masses *Zaffre* is an impure basic arsenate obtained by roasting cobalt glance free from iron, or by dissolving the ore in nitric acid and precipitating with soda It is used for painting on porcelain

Three insoluble ammoniacal arsenates have been obtained by the action of arsenic acid on solutions of cobalt salts in the presence of ammonia and ammonium salts These compounds have the formuLe $Co_3(AsO_4)_2,NH_3,7H_{20}$, $Co_3(AsO_4)_2,2NH_3,6H_{20}$, and $Co_3(AsO_4)_2,3NH_3,5H_{20}$, and may be considered as the normal arsenate in which the water of crystallisation is partially replaced by ammonia [3]

COBALT AND CARBON

591 *Cobalt Carbide* has not been isolated Carbon dissolves* in molten cobalt and the solubility curve indicates the existence of a compound, Co_3C, analogous to cementite, Fe_3C, but it decomposes so rapidly on cooling that it cannot be detected even irf the quenched metal [4]

Cobaltous Carbonate—The normal salt, $CoCO_3$, is obtained as a bright-red powder, consisting of microscopic rhombohedra, by heating cobalt chloride to 140° with a solution of sodium bicarbonate saturated with carbon dioxide The hydrated salt, $CoCO_3,6H*_{20}$, is formed by allowing mixed solutions of cobalt nitrate and sodium bicarbonate, saturated with carbon dioxide, to

1 Ducelhez, *Compt rend* , 1908,**147,** 424 [2] *Ibid* , 1048
[3] Ducru, *ibid,* 1900,**131,** 675
[4] Ruff and Keiiig, *Zeit anorg Chem,* 1914, 88, 410 See also Arnold and Read, *Proc Inst Mech Eng,* 1915, 247

stand at a low temperature until the amorphous precipitate which is first formed becomes crystalline, the dry salt is converted into the anhydrous salt on winning When a solution of a cobalt salt is precipitated with normal or acid sodium carbonate$_9$ bluish or violet basic cobalt carbonates of varying composition are thrown down[x] Cobalt carbonate forms a pink double salt with potassium carbonate,[2] and a bright reddish-purple one with sodium carbonate[3] They have the formula $M_2CO_3,CoCO_3,4H_{20}$

Cobalt Tetracarbonyl, $Co_2(CO)_8$, is obtained by heating cobalt in a nickel-steel vessel at about 15O° with carbon monoxide under a pressure of not less than 3O atmospheres[4] In this way, fine, orange-coloured crystals of cobalt tetracarbonyl are obtained, which are best kept in a sealed glass tube in an atmosphere of hydrogen or carbon monoxide If left in contact with the air, the substance decomposes, yielding a basic cobalt carbonate Cobalt tetracarbonyl is insoluble in water, but dissolves more or less in orgamc solvents, such as carbon disulphide, ether, or alcohol The double molecular formula, $Co_2(CO)_8$, is established by cryoscopic determinations The pure crystals melt at 51° without decomposition, but this sets in imiediately thereafter At 6O°, decomposition is fairly rapid and results in the formation of

Cobalt Tricarbonyl, $Co(CO)_3$ —This compound crystallises from benzene in jet-black crystals, which may be decomposed with bromine water for the purpose of analysis It is very liable to change in air, and is sparingly soluble in the common solvents

Cobalt Nitroso-tncarbonyl, $Co(CO)_3,NO$ —Nitric oxide reacts with cobalt tetracarbonyl, slowly at ordinary temperature but instantaneously at 40°, partly decomposing it into the tncarbonyl and carbon monoxide and partly converting it into the nitroso-tricarbonyl[5]

$$Co(CO)_4 + NO = Co(CO)_3,NO + CO$$

Cobalt nitroso-tricarbonyl is a cherry-red mobile liquid of density 1 5126 at 14°, melting point — 1 O5°, boiling point 78 6° It may be distilled with only slight decomposition at

[1] Compare Meigen, *Journ Ghent Soc* , 1905, 88, u, 454, Nanty, *Ann Chim Phys* , 1912, [8], 27, 5, 1913, |8], 28, 77

[2] Wood and Jones, *Proc Gamb Phil Soc* , 1907,14,171, Applebey and Lane, *Journ Ghent. Soc* , 1918,**113,** 6O9

[3] Applebey and Lane, *loc cit*

[4] Mond, Hirtz, and Cowap, *Journ Ghent Soc,* 1910, 97, 798

[5] Mond and Walhs, *Journ Ghent Soc* , 1921, **121,** 29

5O°—6O° in a current of inert gas, but above this temperature it decomposes into the tricarbonyl and nitric oxide It is insoluble in water but miscible in all proportions with alcohol, ether, benzene or chloroform

Cobaltous Cyanide, $Co(CN)_2,3H_{20}$, is a reddish precipitate obtained when solutions of potassium cyanide and a cobalt salt are mixed It dissolves easily in excess of the precipitant, probably forming a solution of potassium cobaltocyanide If the solution is treated with dilute hydrochloric acid, cobaltous cyanide is again precipitated, but if the solution is previously warmed this does not occur, inasmuch as the more stable potassium cobalticyanide is formed (see below)

The cobaltocyanides and cobalticyanides are analogous in composition to the ferro- and fern-cyanides (p 13O2), and may be regarded as salts of a complex radicle containing cobalt[J] The cobalt is not precipitated by the usual reagents, but the compounds, especially the cobaltocyanides, are not so stable as the corresponding iron compounds

Potassium Cobaltocyanide, K_4CoCy_6, is a deep amethyst-coloured, crystalline powder, which is obtained by dissolving cobaltous cyanide in potassium cyanide at a low temperature and precipitating with alcohol [1] The formation of this salt is also indicated by the change in electrical conductivity as potassium cyanide solution is gradually added to cobalt chloride solution [2]

Potassium Cobalticyanide, K_3CoCy_6, is formed when an excess of potassium cyanide is added to a solution of a cobalt salt, together with a little acetic acid or hydrochloric acid, and the liquid well boiled

$$6KCy + 2CoCy_2 + 2HCy = 2K_3CoCy_6 + H_2$$

When a solution of potassium cobaltocyanide is rapidly oxidised by atmospheric oxygen, it is converted into the cobalti-cyanide, and twice as much oxygen is absorbed as is required by the equation

$$2K_4CoCy_6 + H_{2\,0} + O = 2K_3CoCy_6 + 2KOH$$

At the. end of the reaction hydrogen peroxide is found in the solution in an amount corresponding to the whole of the absorbed oxygen On the other hand, when a solution of the cobalto-cyanide is boiled, hydrogen is evolved equal in volume to the

[1] See Descamps, *Ann Chim Phys*, [5], 1881, 24, 193
[2] Rossi, Gazz, 1915, 45, i, 6

oxygen actually absorbed by the above oxidation Manchot and Herzog,[1] therefore, consider that the oxidation of potassium cobaltocyanide in solution is effected by the water, the absorbed oxygen uniting with the hydrogen liberated to form hydrogen peroxide

This salt crystallises in bright yellow crystals isomorphous with potassium ferricyanide [2] Copper sulphate yields a blue, and silver nitrate a white precipitate, the salts $Cu_3(CoCy_{()})_2$ and Ag_3CoCy_6 being formed *Ferrous cobalhcyanide,* $Fe_3(CoCy_6)_2$, is a white precipitate, whilst *cobalfovs cobalticyanide,* $Co_3(CoCy_6)_2,14H_{20}$, is a pink precipitate which becomes anhydrous and blue when heated to 200° Cobalticyanides of other metals [3] and also of organic bases [4] have been described When the copper salt is decomposed by sulphuretted hydrogen, *cobalttcyamc acid,* H_3CoCy_6, is formed, and this is deposited in colourless, silky needles on evaporating the solution It is deliquescent, has a strongly acid taste and reaction, and is not attacked even by strong nitnc acid

COBALT AND SILICON, ALUMINIUM, AND ZINC

592 *Cobalt Stlicides* —The compound Co_2Si is produced when cobalt is heated with silicon in the electric furnace, or at 1200-1300° 111 silicon tetrachloride vapour, and forms grey, metallic crystals of specific gravity 7 28[5] By heating cobalt in the electric furnace with copper sihcide the *monosihcide,* COS1, is formed, whilst with excess of silicon or a mixture of copper sihcide and silicon, the *disihade,* $CoSi_2$, is obtained [6] Other silicides are also known [7]

Silicates of Cobalt Smalt —The silicates of cobalt do not occur as minerals in nature Although certain specimens of ancient Egyptian glass have been found to be coloured blue by cobalt, the direct application of the ores of cobalt for this purpose appears to date from the sixteenth century Smalt is a potash glass coloured an intense blue by cobalt oxide Up to the middle of the nineteenth century smalt was largely used

[1] *Ber,* 1900, 33, 1742 Ste also Moore, *Chem News,* 1893,'68, 295
[2] Gmeiin, *Handbuch Org Chem,* 1, 397
[3] Miller and Mathews, *J Amer Chem Soc* , 1900, **22,** 62
[4] Wagener and Toliens, *Ber* , 1906, 39, 410
[5] Vigouroux, *Compt rend,* 1895, **121,** <>86, 1906, **142,** 635
[6] Lebeau, *Ann Chim Phys,* 1902, 27, 271
[7] Jenge, *Zeit anorg Chem* , 1921,**118,** 105

for colouring starch, paper, etc , but the introduction of artificial ultramarine has diminished the demand for cobalt blue

For the preparation of smalt, the ore, such as speiss-cobalt or cobalt glance, free as far as possible from iron and sulphur, is first carefully roasted so that the cobalt mainly is oxidised, whilst nickel, iron, copper, and bismuth remain for the most part unaltered together with sufficient arsenic to combine with them and allow them to separate out as an insoluble speiss when the mixture is melted with glass The roasted ore is then fused with a mixture of quartz sand and potashes, the fusion being effected in large earthen pots, arianged in a furnace similar to that employed for the manufacture of plate glass The arsenides of nickel and iron sink to the bottom of the pot and the glass is ladled out into cold water The blue glass is then ground with water to an impalpable powder under granite stones

Smalt varies in composition according to the differences in the ores, and the proportion of sand and potashes employed Thus the amount of silica varies between 56 and 7O per cent, that of potash between 12 and 22, and that of cobalt between 6 and 16 per cent In addition, smalt contains small quantities of alumina, ferric oxide, and frequently also lime and oxide of lead, the commoner varieties likewise contain oxide of mckel Smalt has the advantage as a paint over ultramarine that its colour is not destroyed by the action of acids

A number of other coloured substances containing cobalt are made by heating the oxide with other metallic oxides (p 1333)

DETECTION AND ESTIMATION OF COBALT

593 This metal is characterised by the fine blue colour which its compounds impart to the borax bead If a cobalt compound be reduced on a carbonised match, the metal is obtained in shining, white, magnetic particles, these dissolve in hydrochloric acid, forming a rose-red solution, which becomes blue on evaporation

Cobalt chloride imparts to the non-lummous gas flame an evanescent[1] rose-red colour, but this does not give any characteristic spectrum The spark spectrum of the chlonde contains a large number of bright lines, and the metal also gives a spectrum consisting of a large number of bright lines of which the following in the blue are the most characteristic (Thalen), 4868, 4840, 4815, 4793, 478O.

Solutions of cobalt salts give with ammonium sulphide a black precipitate of the sulphide which is insoluble in acetic and dilute hydrochloric acids With ammonium thiocyanate, they yield a blue coloration, and if this solution be shaken with a mixture of amyl alcohol and ethei and then allowed to stand, the latter separate on the top as an intensely blue layer [1] Addition of acetic acid and potassium nitrite to a solution containing cobalt yields a yellow precipitate of potassium cobalti-nitnte a-nitroso-B-naphthol gives a red precipitate with solutions of cobalt salts acidified with acetic acid [2]

The separation of nickel and cobalt is discussed under mckel (p 1385)

Cobalt may be estimated electrolytically in the same manner as nickel It may also be accurately estimated by precipitation with a~nitroso-B-naphthol, the precipitate is lgnited with a little oxalic acid to the oxide, reduced in a stream of hydrogen, and weighed as metal Cobalt may also be precipitated as the oxide (by alkaline hypobromite) or sulphide, which is similarly ignited, reduced in hydrogen, and weighed as metal

The Atomic Weight of cobalt, like that of mckel, has been frequently determined Among the earlier determinations may be mentioned those of Rothhoff,[3] Schneider,[4] Mangnac,[5] Gibbs,[6] Dumas,[7] Russell,[8] Ziminermann,[9] and Winkler[10] In an investigation by Hempel and Thiele[11] the reduction of tncobalt tetroxide gave the number 58 97, and the analysis of the chloride 58 89 Richards and Baxter[12] determined the ratios of cobalt bromide to silver bromide and to silver, and as the mean of a large number of experiments obtained the number 58 99 They determined also the weight of cobalt obtained by the reduction of cobaltous oxide, chloride, and bromide by heating in hydrogen, and obtained numbers between 58 93 and 59 O6

[1] See Powell, *J Soc Ghent Ind,* 1917, 36, 273

[2] Ilinski and Knorre, *Ber* , 1885,**18,** 699, Chapm, *J Amer Chem Soc* , 1907, **29,** 1929, Atack, *J Soc Chem Ind,* 1915, 34, 641

[3] *Pogg Ann,* 1826, 8, 185 [4] *Ibid,* 1857, **101,** 387

[5] *Arch Set Phys Nat,* 1858, [2], 1, 373

[6] *Amer J Set,* 1858, [2], 25, 438

[7] *Ann Chim Phys,* 1859, [3], 66, 129

[8] *Journ Chem Soc* , 1863,16, 51, *Chem News,* 1869, **20,** 20

[9] *Annalen,* 1885, **233,** 324

[10] *Zeit anal Chem,* 1867, 6, 22, *Zeit anorg Chem,* 1895, 8, 1,

[11] *Ibid,* 1896,**11,** 73

[12] *Ibid,* 1898, 16, 326, 1899, **21,** 25O, 1899, **22,** 221 Compare Winkler, *ibid* , **1898, 17,** 236

More recently, from the ratios of cobalt chloride to silver and to silver chloride, Baxter and Coffin [1] found the number 58 99 The value at present (1922) adopted is 58 97

The atomic weight of cobalt is higher than that of nickel Chemical analogies require that cobalt should precede nickel in the periodic system (p 69), and the atomic numbers of the elements are in this order (see p 74).

NICKEL Nl = 58 68 At No 28

594 The first mention of an ore of this metal is found in the writings of Hiarni in 1694, the name of kupfer-nickel, signifying false copper, being given to it because, whilst possessing the colour of a copper ore, this latter metal could not be extracted from it In spite of the failure, the ore was long supposed to contain copper, but after the discovery of cobalt many believed that this metal was contained in kupfer-nickel [2] In 1751, Cronstedt published in the *Transactions* of the Stockholm Academy an investigation upon an ore which was obtained from the mines of Helsingland This gave a green vitriol, which imparted a brown and not a blue colour to glass, and yielded a hard, brittle metal In 1754, he stated that a semi-metal occurred most abundantly in kupfer-nickel, and therefore he proposed to give to it the name of nickel He likewise showed that the speiss formed in the preparation of smalt consisted to a large extent of nickel, and was not, as had been believed, a burnt cobalt which had lost its spirit Cronstedt's views did not find general acceptance, but in 1774 Bergman's research on nickel made its appearance, and in this he showed that the nickel which Cronstedt had obtained only in the impure state was in reality a new metal

Nickel almost always occurs in nature together with cobalt, and occurs in niccolite, nickehne, or kupfer-nickel, NiAs, found in the Saxon mines, in Styna, at Leadhills, and in Connecticut, nickel glance, NiAsS, breithauptite, NiSb, millente or nickel blende, NiS, linnaeite, $(CO,Ni,Fe)_3S_4$, pentlandite, (Ni,Fe)S, nickel ochre or annabergite, $Ni_3(AsO_4)_2,8H_{20}$, rewdanskite, $(Ni,Fe,Mg)_3Si_{207},2H_{20}$, etc Nickel also occurs fiequently in magnetic pyrites, the deposits at Sudbury, Canada, at present

[1] *Zeit anorg Chem*, 1906, 51, 171
[2] See Link, *Phil Trans*, 1726, 34, 192

supplying about 6O-per cent of the world's production It consists of pyrrhotine as^gpated with small quantities of copper pyrites, pentlandite, and occasionally millente An important source of nickel has been opened out in New Caledonia, where large quantities of a silicate of nickel called garniente, $2(Ni,Mg)_5Si_4,O_{13}3H_2O$ occur

Nickel is an essential constituent of meteoric iron (p 1211), its presence in extra-terrestrial matter having been first detected by Poust It is contained also in the sun's atmosphere

METALLURGY OF NICKEL

595 The method adopted for the extraction of metallic nickel varies according to the nature of the ore to be treated Formerly nickel was largely obtained as a by-product from the treatment of complex ores of copper, etc , by long and complicated wet and dry processes, but at the present time most of the nickel is obtained from garmeite and nickeliferous pyrrhotite and chalcopynte [1]

The method of treating garmente, as at present practised, consists in smelting the ore with the addition of calcium sulphate or even alkali waste (chiefly calcium sulphide), for the production of a matte of nickel and iron, together with a slag, consisting of silicates of lime, magnesia, and other bases This matte, which generally contains about 50 per cent of nickel, 30 per cent of iron, and 20 per cent of sulphur, is either blown in small Bessemer converters similar to those used for enriching copper mattes (p 425), or is smelted in reverberatory furnaces together with a siliceous flux, yielding in both cases a rich pure nickel sulphide, containing 80 per cent of nickel and a siliceous iron slag containing a small amount of nickel

It is, however, impossible to blow this nickel sulphide to the metal, as can be done with copper sulphide, on account of reactions which yield NiO taking place more easily and at a lower temperature than those yielding metallic nickel The nickel sulphide has therefore to be carefully roasted, generally twice, sometimes with the addition of sodium nitrate, and the nickel oxide washed and dried The oxide is then pressed into the form of small cubes, and these are strongly lgnited with charcoal powder The reduction takes place from the outside,

[1] Steinhart, *Trans Inst Min and Met*, 1906-6, 16, 230 See also *Report of the Royal Ontario Nickel Commission*, 1917

the metal absorbing carbon and retaining the form of the cubes The operation is usually carried on in clay crucibles standing on the hearth of a reverberatory furnace, or in a special furnace[1] in which the reduction may be carried on continuously This consists of a furnace through which vertical fire-clay tubes pass, these tubes are charged at the top with the mixture of crude oxide and coal, and the metal is withdrawn from time to time at the bottom Cominercial nickel contains carbon, as well as small quantities of cobalt, copper, iron, and sulphur

For sulphides such as the Canadian ores, containing 3 per cent of nickel, and about 2 per cent of copper, the process is carried out as follows the ore is first heap-roasted to oxidise the iron and remove the excess of sulphur The roasted ore is then smelted in a blast furnace, producing a matte containing 36 to 40 per cent nickel-copper This matte is then concentrated, either by being again put through the cupola with a siliceous flux, or by being blown in a converter, to an 80 per cent nickel-copper matte

The separation of the nickel from the copper may be effected by what is known as " tops and bottom " smelting, by means of an alkaline sulphide The matte is mixed with coke and sodium sulphate (salt-cake), 30 tons of salt-cake and 7 tons of coke being used for 50 tons of matte, and is charged into a magnesia-lmed open-hearth reverberatory furnace The mixture is melted down and allowed to stand for five hours in the furnace, being frequently poled Practically complete solution of the copper sulphide, and any iron sulphide present, is thus effected in the sodium sulphide formed from the salt-cake The molten charge is then tapped from the furnace and allowed to separate in moulds, or the two strata are tapped separately from the furnace The nickel sulphide thus obtained may be roasted and reduced as already described A small amount of nickel is also extracted by a wet method as described under cobalt

Another method for the treatment of the rich matte consists in granulating it, followed by roasting and leaching out the copper The leached material is then smelted with suitable fluxes in an electric furnace The nickel-copper alloy obtained is cast into anodes and refined electrolytically by the Hybinette process, the slimes being treated for platinum, palladium, gold, indium, etc

[1] *Ber Entw Chem Ind,* 7, 866

The Mond Process,, which depends on the formation and decomposition of the volule nickel carbonyl $Ni(CO)_4$ is very important and interesting [1]

The ore is mined in the Sudbury region of Ontario and is there roasted, smelted, and bessemenzed, as described above, yielding a matte containing 40% Nl, 40% Ou, and less than 1% Fe, the remainder being almost entirely sulphur This matte is shipped to the refining-works at Clydach, Swansea It is crushed and calcined at the lowest possible temperature in a current of air The calcined matte is treated with about 15% sulphuric acid at 80° whereby about 70% of the copper and only about 7% of the nickel together with some of the iron are extracted as sulphates The copper-extracted matte is filtered off and dried It is reduced in a stream of water-gas by passing down over a series of shelves in a tower heated to about 330° The reduced matte is passed by air-tight conveyers to volatilizers which are exactly similar to the reducers, and is thus brought into intimate contact with a stream of water-gas at a temperature not exceeding 50° Under these conditions the finely-divided nickel combines with the carbon monoxide of the water-gas to yield the carbonyl which is swept over in the stream of gas to the decomposers These are specially constructed towers filled with nickel shot and heated on the outside by producer-gas to about 180° The carbonyl is decomposed

$$Ni(CO)_4 = Ni + 4CO.$$

and the carbon monoxide passes on for further extraction The nickel is deposited on the shot which are prevented from coalescing by being kept in constant motion and so grow individually An exceptionally pure metal containing nearly 99 9% Nl is thus produced

The liquors from the copper extraction are crystallized and yield a very pure copper sulphate The mother-liquor is then re-charged with acid and used for further extraction and crystallization, and this is repeated until it becomes too rich in nickel sulphate It is then treated with reduced matte when the finely-divided nickel replaces the copper of the remaining copper sulphate yielding a solution of nickel sulphate free from copper The iron is removed by oxidation and precipitation as ferric hydroxide and the nickel sulphate is crystallized

In each operation about 70% of the copper and 70% of the nickel are removed, and, after being concentrated by passing

[1] **See Mond, *J Soc Chem Ini* , 1895, 14, 945**

through, the cycle several times, the residual matte is sufficiently rich in the precious metals to be worked up for them

Pure nickel can be prepared, according to Winkler,[1] by electrolysing a solution of the pure sulphate containing ammonium sulphate and ammonia, a cathode of highly polished nickel being used, and the current passed until the nickel separates from the electrode in thin plates It is then heated in a current of pure dry hydrogen

In practice, small quantities of magnesium are often added to molten nickel, this is found to make the metal very fluid before casting, and also renders it malleable, and free from blow-holes due to gas

596 *Properties*—Nickel is a lustrous, silver-white metal with a steel-grey tinge It is very hard and takes a high polish, and may easily be rolled out into thin plates and drawn into wire The pure metal melts at 1452°, but may be welded below its melting point, and distils in the electric furnace more readily than cobalt[2] As 111 the case of iron, when the metal contains carbon it is less malleable and more readily fusible It has a sp gr of 8 35 when cast to 8 9 when rolled, and its average specific heat between 15° and 100° is 0 10842[3]

Nickel oxidises only with difficulty, even on heating in the air It decomposes steam very slowly at a red heat with formation of the monoxide, which is also formed when the metal is heated at 200° in nitric oxide[4] It is slowly soluble in hydrochloric or dilute sulphuric acid, and does not dissolve quickly even in the concentrated acid On the other hand, it dissolves readily in dilute nitric acid, but if it be dipped into the concentrated acid it becomes " passive," as does iron

Nickel exists in two allotropic modifications, the transition temperature being between 340° and 360° The metal is attracted by a magnet below this temperature, but is non-magnetic above it[5] The transition is also indicated by a sudden change at this temperature in the coefficient of expansion,[6] the

[1] *Zeit anorg Chem,* 1894, 8, 1, see Kohlschutter and Schodl, *Helv Chim Acta,* 1922, 5, 490, 593

[2] Moissan, *Qompt rend* , 1906,**142,** 425

[3] For detailed list of the physical properties of pure and cominercial nickel, see Menca, *Chem Met Eng,* 1921, **24,** 73

[4] Sabatier and Senderens, *Compt rend,* 1892, **114,** 1429

[5] Werner, *Zeit anorg Chem* , 1913, 83, 275, Honda and Ogura, *Set Reports TdhoTcu Imp Vniv* , 1914, 3, **113**

[6] Harrison, *Phil Mag,* 1904, 7, [6], 626, Janecke, *Zeit angew Chem,* 1918, 31, i, 229, *Zett Mektrochem,* **1919, 25, 9**

electromotive force against copper,[1] the electrical resistance[1] and the rate of cooling[2]

Nickel, like iron and cobalt, is capable of absorbing hydrogen The solubility is independent of the superficial area of the metal, so that the phenomenon is one of true solution and not of adsorption At constant temperature, the solubility in the solid and molten metal is proportional to the square root of the pressure The gas is more soluble in the molten metal, and when this solidifies about twelve volumes of hydrogen are liberated with much " spitting "[3]

Nickel is now largely employed for coinage, for electro-plating, for the manufacture of many important alloys, and as a catalyst The pure metal is also used for the manufacture of cooking utensils, and for the manufacture of crucibles which can be used in many laboratory operations, instead of those made of the more costly platinum

Nickel Coinage —The application of copper-nickel alloys to the manufacture of small com was first introduced into Switzerland in 1850 The Swiss pieces of twenty, ten, and five centimes contained respectively fifteen, ten, and five per cent of silver alloyed with 10 parts of nickel and 12 4 of zinc, the residue being made up of copper A yellow alloy containing twelve of nickel to eighty-eight of copper was adopted in 1856 by the Umted States Government for the one cent pieces In 186O the Belgian Government instituted a nickel-copper coinage, containing twenty-five of the former to seventy-five of the latter metal, this same alloy being adopted in 1866 by the United States for the five and ten cent pieces, by Brazil in 1872, and by the German Government in 1873 for the five- and ten-pfennig pieces The application of this alloy rapidly extended to other countries, including many parts of the British Empire, and at the end of 1912 no fewer than forty-nine countries had adopted it, more than four thousand million such coins being then in circulation

The alloy is very hard, so that the coins are resistant to wear and tear It is white and of pleasing appearance and does not readily tarmsh Unlike the pure metal, it is not magnetic, and coins made of the alloy may be distinguished from those of pure nickel by this simple test.

[1] **Werner,** ***he cit***

[2] **Balkon,lnt** ***Zeit Metallog*****, 1914, 6, 115, Laschtschenko,** ***J Russ Phys Chem Soc*****, 1914, 48, 311**

[3] **Sxeverts,** ***Zeit phystkal Chem*****, 1911, 77, 591**

It is a very remarkable fact that a coin of the Bactnan King Euthydemos, who reigned about 235 B C , analysed by Flight,[1] possesses a very similar composition to the alloy in question, viz 77 58 per cent of copper and 20 04 per cent of nickel

In 1881, the Swiss Government introduced a new issue of 20 centime pieces made of pure nickel These coins have proved so successful that many other nations have introduced pure nickel coinage to replace silver, bronze, and even cupro-nickel At the end of 1912, Switzerland, Austria, Italy, France, Serbia* Montenegro, Mexico, Turkey, and Siam had adopted the metal for small coinage, and about a thousand million pieces were in circulation [2]

The advantages of a nickel coinage, and especially of pure nickel, are many First, the metal is more valuable than copper, and consequently, for the same value, the coins can be of smaller size Secondly, it is extremely tough, and the coins wear so well that replacement costs are extremely small There is practically no deterioration in the Swiss coins which have been in circulation for forty years Thirdly, owing to its hardness, nickel is very difficult to work, extensive plant and machinery and highly skilled labour being required for the production of coins, so that the manufacture of counterfeits would not be an attractive and profitable business Lastly, nickel provides a clean and beautiful coinage It has a brilliant surface, takes the impress of the die most distinctly and permits, therefore, of the most elaborate designs, a further difficulty thus being placed in the way of the counterfeiter

In those countries where the silver and nickel coins are of about the same size, the latter are made readily distinguishable by being perforated, as in France, and Belgium, by having scolloped edges, as in India, or by being made square with rounded corners, as in Holland and Ceylon

Electro-nickel Plating —Pure nickel is used as the positive pole in processes for the electro-deposition of nickel, which are especially valuable for coating iron and steel with a thin film of pure nickel If the coating be well deposited, the metal scarcely undergoes any oxidation, but it is found to adhere better when a layer of copper is first deposited on the iron The process of nickel-plating was first applied to fire-arms in order to preserve them from rusting Now, however, it is also used for covermg

[1] The *Nummatic Chronicle*, 8, 395, and *Pogg Ann* , 1870,**189,** 507
[2] See *Report of the Royal Ontario Nickel Commission,* 1917

various parts of machines, locks, keys, surgical instruments, and other fine iron- and steel-work A great variety of proposals have been made for the preparation of the liquid used in this process, but the only bath which is practically useful is a solution of pure nickel ammonium sulphate, saturated at a temperature of 20-25° [1] The salt is only moderately soluble, and consequently, in order to increase the conductivity of the bath, it is usual to add ammonium sulphate or nickel sulphate or sodium chloride In a neutral solution, there is always a possibility of basic salts being formed and deposited on the cathode, thus spoiling the coating Bone acid is therefore sometimes also added to the bath

The article to be plated is made the cathode, and the anode is of pure nickel either cast or rolled The cast metal dissolves much more readily than the rolled, but the latter has a more umform composition and therefore dissolves more evenly and with less waste In either case, the plating must be done slowly owing to the difficulty with which nickel is soluble, and for the same reason the anode surface is made greater than that of the cathode

The deposit is usually very thin, and such only is necessary, but attempts to deposit thick layers of nickel have often met with failure The deposition of thick layers is possible only in solutions absolutely free of iron [2] Iron is deposited more easily than nickel, and the first layers are therefore richer in it than succeeding ones, so that strains are set up and the deposit flakes off Working in the hot (above 50°) has been recominended for the production of thick deposits, but these may be obtained quite satisfactorily in the cold in the complete absence of iron

Nickel plating can be recogmsed without damaging the plate by placing on it a spot of acid, absorbing this almost iminediately with filter-paper, and testing the wet spot on the paper by adding a drop of ammonia to neutralise the acid, then a drop of acetic acid and a drop of dimethyl glyoxime solution, when a red coloration is produced [3]

The thickness of the plating can also be determined without damaging the plate [4] The article is first thoroughly cleaned, a few drops of a solution containing by volume 1 part of nitric

[1] *Ber Entw Chem Ind,* I , 874, Bennett, Kenny, and Dugliss, *J Physical Chem,* 1914, 18, 373

[2] See Engemann, *Zeit Elektrochem* , 1911,17, 910

[3] Bianchi and di Nola, *Boll Chim farm* , 1910, 49, 517

[4] Pontio, *Compt rend,* 1915, 161, 175

acid, 2 parts of hydrogen peroxide, 3 parts of hydrochloric acid, and 5 parts of water are placed on it, after two minutes a drop of ammonia is added, the liquid is then removed and its colour examined If the plating is on copper, a blue colour indicates a nickel deposit of less than 1 mgr per sq cm , and if on iron a brown colour indicates a deposit of less than 4 mgr , per sq cm Other thicknesses can be estimated by varying the time of contact of the solution with the metal

Nickel can also be successfully plated on aluminium if this metal be first either subjected to a sand-blast * or else scoured with milk of lime and then dipped in an acid bath of a metallic chloride such as ferric chloride [2]

ALLOYS OF NICKEL

597 In 1825, Thenard in his *Trmti de Chimie* remarked that nickel was not employed for any practical purpose, although Engestrom had pointed out so long ago as 1776 that Chinese packfong is an alloy of copper, zinc, and nickel Packfong, or rather Pack-Tong, means white copper, and Tong-Pack probably means the same thing, although in Europe this name, changed to tomback, is employed to describe a particular kind of brass Since the middle of the eighteenth century a white alloy had been prepared at Suhl, in Hanneberg, from old copper slag, and Brandes in 1823 showed that this white copper consisted chiefly of an alloy of copper and nickel, and thus cominenced the manufacture of nickel alloys known under the name of German silver, nickel silver, or argentan, a trade which has now attained large dimensions

Nickel Silver, or *German Silver,* is an alloy of copper, nickel, and zinc, containing its constituents in varying proportions according to the method of preparation and the articles for which it is used As a rule five parts of copper, two of nickel, and two of zinc are used, thus giving rise to an alloy which has the appearance of silver alloyed with one-quarter of coppei In Sheffield, eight parts of copper, 3 5 of zinc, and three of nickel are employed A commoner and yellowish alloy is obtained when less nickel is used, whereas if more nickel be employed the alloy has a bright white colour, and takes a high, silvery polish The addition of 2 5 per cent of iron makes the alloy whiter, but also harder and more brittle

[1] **Guillet and Gasnier, *Compt rend,* 1920,170, 1253**
[3] **Mazuir, *Ann Chim anal,* 1920, [2J, 2, 335**

The following table gives the composition of several of these alloys No I is Chinese packfong analysed by Fyfe, II the same, by Kefferstein, III German silver by Bolley, IV-VI various samples of nickel silver used in Birmingham for articles to be plated, and analysed by Louyet, VII an alloy from Sheffield distinguished by extraordinary elasticity and used for the friskets of printing presses, analysed by Eisner; and VIII an alloy used for strong castings, such as high pressure steam fittings

	I	II	III	IV	V	VI	VII	VIII
Copper	40 4	26 3	54 0	63 34	62 40	62 63	57 4	70 0
Zinc	25 4	36 8	28 0	17 01	22 15	26 05	25 0	10 0
Nickel	316	36 8	18 0	1913	15 05	10 85	13 0	20 0
Iron	2 6	—	—	trace	trace	trace	3 0	—
	100 0	99 9	100 0	99 48	99 60	99 53	98 4	100 0

In preparing nickel silver it is usual to melt the zinc with half the weight of copper which it is ultimately to contain, this alloy being then cast into thin plates The other half of the copper is then fused with the nickel under a layer of charcoal powder, and the copper-zinc alloy is added After cooling, the alloy possesses a crystalline structure, and this is got rid of by haminering and rolling, again heating, and allowing to cool When it has once lost its crystalline structure, it can be worked like brass, and although it is harder and tougher it may be rolled out to foil and drawn to wire Hence this alloy is used for a great number of purposes, as it is much cheaper than silver, and less apt to be discoloured 0n the other hand, it is more readily attacked by liquids, and for this reason nickel silver articles employed for household use are generally covered with a coating of silver The addition of small

of aluminium has been shown to improve greatly the que and appearance of nickel silver [1]

Nickel and copper alone mix in all propoitions, giving many important alloys These alloys of nickel, on fusing, absorb a considerable quantity of gas, and the higher the temperature and the percentage of nickel the greater is the quantity absorbed Kunzel found that if an alloy of lighty parts of copper and twenty of nickel be fused in a rucible half filled with the mixture, and this quickly cooled, the mass froths up from the evolution of gas, and runs over the top of the crucible If a

[1] See Guillet, *Compt rend,* 1914,158, 704.

copper-nickel alloy be granulated in water, yellow globules are obtained, and these are frequently so thin that they float on the surface of the water[1]

An alloy of 75 per cent copper and 25 per cent nickel is utilised in many countries for the manufacture of currency

An alloy of nickel with four parts of copper, known as *cupro-nickel*, is used for the casing of bullets to be employed with small-bore rifles A very similar alloy containing 14 to 16 per cent of nickel and 84 to 86 per cent of copper is known as *Benedict metal*

Mond metal is an alloy of nickel and copper possessing remarkable mechamcal properties It is made directly from the nickel-copper matte produced from the Sudbury ores (see p 1358), and is therefore a "natural" alloy It contains from 60 to 72 per cent of nickel, from 0 5 to 6 5 per cent of iron and manganese, the remainder being copper

The addition of nickel to copper greatly increases its electrical resistance, the maximum resistance being obtained with about 40 per cent of nickel, the resulting alloy is known as *Constantan*, on account of its low temperature coefficient

Other high resistance alloys containing nickel are *Platmoid*, consisting of 60 per cent of copper, 24 per cent of zinc, 14 per cent of nickel, and 1 to 2 per cent of tungsten, *Rheostan*, containing 52 per cent of copper, 18 per cent of zinc, 25 per cent of nickel, and 5 per cent of iron, *Manganm*, containing 4 to 40 per cent of nickel, 60 to 80 per cent of copper, with 1 to 12 per cent of manganese, *Nichrome*, containing 60 per cent of nickel, 14 per cent of chromium, and 15 per cent of iron, and *Illium*, containing about 60 per cent of nickel, 6 per cent of copper, 21 per cent, of chromium, 4 per cent of molybdenum, 2 per cent of tungsten, and 1 per cent, each of iron, aluminium, manganese, and silicon[2] The two last named are also remarkably resistant to corrosion and to the action of acids, and possess great mechamcal strength

By far the most important application of nickel for alloys, however, is in the manufacture of *nickel-steel*, and fully half the world's production of nickel is used for this purpose. Nickel-steel contains usually 2 5 to 3 5 per cent of nickel, which gives it a far greater tensile strength and ductihty and also renders

[1] *Ber Entw Chem Ind* , 1,367

[2] Parr, *Journ Amer Chem.'Soc* , 1915, 37, 2515, *J Soc, Chem Ind*, **1915, 34, 1097**

it more resistant to wear and to corrosion. Apart from its use for armaments, nickel-steel is largely used in engineering, notably for bridge-building and for crank-shafts and other important parts of machinery Nickel-steel is the term applied to alloys of iron containing less than 5 per cent of nickel, but other alloys containing a higher percentage of nickel are also of importance *Invar* contains 35 per cent of nickel and about 0 5 per cent of carbon Its coefficient of expansion is practically nil, and as it takes a high polish and is not corrodible, it is largely used in the manufacture of chronometers *Phtinite* containing 46 per cent of nickel and 0 15 per cent of carbon has practically the same coefficient of expansion as platinum and is therefore used for fusing into glass instead of that expensive metal

Nickel as a Catalyst —Nickel in the finely divided state is a very important catalyst It is readily made by reducing the oxide in hydrogen, but its activity depends upon the mode of preparation The reduction should be carried out at as low a temperature as possible, and for this reason the oxide employed should be obtained by precipitation or by ignition at the lowest possible temperature A very active material is made by reducing the hydroxide in hydrogen at a temperature not exceeding 300° The metal obtained in this way is pyrophonc, and as the oxide produced on allowing this to oxidise is more readily reducible than the original, a still more active catalyst can be obtained by allowing it to oxidise and then reducing it again[1] The preparation of the active metal is best made in the vessel in which the catalysed reaction is to be carried out so that no oxidation may occur through any transference

The metal is very readily " poisoned " by certain substances, notably the halogens, sulphur, phosphorus, and arsenic The oxide is therefore prepared from the nitrate rather than the sulphate or chloride, but if the latter are used the precipitated hydroxide must be most carefully washed The hydrogen used for reduction and for subsequent reactions must be thoroughly freed from these substances, and this is best done by passing the gas first over copper turnings heated to redness and then through caustic potash Even though all the substances are highly purified, the activity of the nickel gradually becomes enfeebled during use owing to traces of toxic substances which gradually accumulate, and also to non- volatile matter condensing

[1] **Senderens and Aboulenc, *Bull Soc chin* , 1912, [4], 11, 641**

on the surface of the metal and thus preventing contact with the reacting substances [1]

The reactions are carried out simply by passing the vapour of the substance, or the vapour mixed with hydrogen, through a layer of the finely divided metal maintained at the requisite temperature In order to afford a larger active surface to the action of the vapours, the metal is sometimes deposited on a " carrier " such as pumice-stone or fire-clay

When acetylene is passed through finely divided nickel, even in the cold, into benzene and other polymendes, but the greater part being split up into carbon and hydrogen[2] Ethylene is completely decomposed by the metal at about 300°, chiefly into methane, with traces of higher hydrocarbons, and partly into hydrogen, carbon being deposited,[3] $C_2H_4 = CH_4 + C$

The catalytic activity of nickel has been the subject of much research, chiefly by Sabatier and Senderens and their co-workers,[4] especially in reductions, which are easily effected by passing the vapour of the substance with excess of hydrogen over the catalyst. Thus, by the simple addition of hydrogen, the unsaturated hydrocarbons, including those of the benzene series, are converted into the corresponding saturated compounds, and aldehydes and ketones yield the corresponding alcohols [5] Carbon monoxide and dioxide are reduced to methane and nitro-compounds to amines In general, these reactions proceed at a low temperature, and their rate increases with rise of temperature up to about 180°, where they proceed very rapidly At higher temperatures, the reaction is often reversed, hydrogen being liberated, and at about 350° the higher orgamc compounds are decomposed chiefly into simple hydrocarbons with deposition of carbon [6]

This fact finds an important techmcal application of finely divided nickel as a catalyst for the removal of carbon disulphide from coal-gas, thus reducing its sulphur content considerably

[1] Sabatier, *J Soc Chem Ind* , 1914, 33, 733, Oossley, *ibid* , 1914, 33, 1135-

[2] Moissan and Moureu, *Compt rend*, 1896, **122,** 1240

[3] Sabatier and Senderens, *ibid*, 1897,**124,** 616

[4] *Ibid*, *Ann Chim Phys*, 1905, 4, 319, *ibid*, 1909, **16,** 70, Sabatier, *Ber* 1911, **44,** 1984

[5] See also Brochet, *Compt rend* , 1914,**168,** 1351, Brochet and Bauer, *ibid* , 1914,**159,** 190, Brochet and Cabaret, *ibid* , 1914,**159,** 326, Sandonnim, *Gazz* , 1922, **52,** [i], 394

[6] Sabatier and Gaudion, *Compt rend* , 1919,**168,** 670, Mailhe, *Chem Zentr* , 1921, [1], 717

The catalyst is made by **impregnating** balls of fire-clay with, a nickel salt They are filled into towers and the salt is reduced to metal in a stream of coal-gas The towers are kept at **a** temperature of about 400°, and the gas to be purified is passed through The carbon disulphide is decomposed, the carbon being deposited and the sulphur uniting with the hydrogen of the gas to form hydrogen sulphide, which is then absorbed by ferric oxide in the usual manner (Vol I, p 882) After running for some weeks a tower becomes so filled with carbon that it ceases to work It is then blown out with inert gas (carbon dioxide), and a current of air is passed through This completely burns the carbon, which is swept away as carbon dioxide, and converts the nickel to oxide The tower is then again swept out with carbon dioxide to displace the air, and put into operation again The coal-gas first reduces the oxide to nickel and this is as active as before in the removal of the carbon disulphide

The oxides of nitrogen when passed with hydrogen over finely divided nickel are reduced to nitrogen and ammonia, the relative quantities depending on the composition of the mixture, the rate at which it is circulated over the nickel, the temperature of the reaction, and also the state of the catalyst [1] Sulphur dioxide and hydrogen, when similarly treated, yield hydrogen sulphide,[2] while if hydrogen be passed over a mixture of finely divided nickel and phosphoric oxide, phosphme is obtained [2]

By far the most important application of the catalytic property of nickel is in the hydrogenation or " hardening " of oils for the manufacture of soap and of margarine Very few details have been published of the methods in use, but the process consists in treating the liquid oil with purified hydrogen in the presence of nickel [3] The catalyst is prepared by reducing the oxide as already described, and is introduced into the oil without exposure to air, or, more usually, the oxide itself is added to the oil and reduced in *situ* by the hydrogen The formate or oxalate may be used instead of the oxide, and are said to give a very active metal [4] A new method has been suggested in which nickel oxide is treated in a tube with a mixture of carbon monoxide and hydrogen, and the nickel carbonyl thus formed is swept over into the hot oil and there instantly decomposed,

[1] **Guye and Schneider,** ***Helvetica Chim Acta,*** **1918, 1, 33**
[2] **Neogi and Adhicary,** ***Zeit anorg Chem*** **, 1910, 69, 209**
[3] **See Ellis,** ***J Soc Chem Ind,*** **1912, 31, 1155, Armstrong and Hilditch,** ***Proc Hoy Soc*** **, 1921,** ***[A*** **100, 240**
[4] **Brochet,** ***Bull Soc chim,*** **1920, [4], 27, 897, 899**

yielding the metal in a very finely divided and active condition [1] The mixture of oil and catalyst is kept at a temperature depending on the constitution of the oil and the amount of nickel added, but generally about 150° to 250°, and purified hydrogen is bubbled through with constant stirring In some cases treatment with hydrogen under pressure has been found to be more rapid and satisfactory, and it is claimed that the nickel is then not so sensitive to impurities in the oil and hydrogen [2] After hydrogenation, the oil is filtered in order to remove the nickel, and the metal thus recovered is available for further use

The original oil is an unsaturated compound, and is thus converted into a saturated body of higher melting point For example, oleic acid, in p 14°, is readily transformed into stearic acid, in p 69°, and whale oil (which is worked up in very large quantities) yields a solid of in p about 54°

Some believe that nickel oxide acts as a catalyst,[3] and that when the oxide is added to an oil and hydrogen passed through, it is reduced to a sub-oxide which forms a black, colloidal solution with the oil and is responsible for the catalysis [4] Most authorities, however, hold that all active oxides contain the finely divided metal which alone can act as a catalyst [5]

Colloidal Nickel —Nickel can be obtained in colloidal aqueous solution by coating iron or zinc wires with the metal and then " pulverising " it by Bredig's electrical method [6] It has also been obtained as a colloid in organic solutions by a spark discharge from the granulated metal under the liquid [7]

If nickel be heated in the Bunsen flame and plunged into cold water, a solution is obtained containing the metal and also the hydroxide in colloidal solution [8]

A colloidal solution of pure nickel is obtained by heating a solution of nickel carbonyl in benzene [9] This yields a beautiful

[1] Leasing, *J Soc Chem Ind*, 1913, 32, 917

[2] Ipatiev, *J Buss Phys Chem Soc* , 1914, 46, 302

[3] Bedford and Erdmann, *J pr Chem*, 1913, [2J, 87, 425, Senderens and Aboulenc, *Bull Soc chim* , 1915, [4], 17, 14

[4] Bedford and Erdmann, *he cit*, Willstatter and Waldschmidt Leitz, *Ber* , 1921, 54, *[B],* 113

[5] Meigen and Bartels, *J pr Chem*, 1914, [2], 80, 290, Normann and Pungs, *Chem Zeit*, 1915, 39, 29, 41, Normann, *Chem Zeit*, 1916, 40, 757, Armstrong and Hilditch, *Proc Boy Soc* , 1921, *[A],* 99, 490, Kelber, *Ber* , 1921, 54, [B], 1701, Normann, *ibid* , 1922, 55, [B], 2193

[6] BilUtzer, *Ber*, 1902, 35, 1929

[7] Svedberg, *Ibid*, 1905, 38, 3616, *ibid*, 1906, 39, 1705

[8] Kimura, *Mem Coll Sci Eng Kyoto Imp Umv* , 1913, 5, 211

[9] 0stwald, *Kolloid Zeit*, 1914,15, 204

violet-grey solution, whereas all the other methods of preparation give a brown product f

Reduction of colloidal nickelous hydroxide or of the freshly precipitated hydroxide in the presence of sodium protalbmate as protective colloid, by means of hydrogen with colloidal palladium as catalyst, also yields a colloidal solution of nickel [x]

A colloidal solution is similarly produced by reducing nickel formate, acetate, or freshly precipitated hydroxide, dissolved or suspended in glycerine, with hydrogen at 200° to 210° or with hydroxylamine, hydrazine hydrate, formaldehyde, or hypophosphorous acid Gelatin or gum arable is used as a protective colloid Addition of water precipitates a brown mass containing about 30 per cent of nickel, and this is soluble again in alcohol or glycerine [2]

COMPOUNDS OF NICKEL

NICKEL AND OXYGEN

598 A large number of different oxides of nickel have been described, the most important being the monoxide, NiO, which is the only one yielding a corresponding series of salts In addition, the sesquioxide, Ni_2, has been prepared, and peroxides are obtained by the electrolytic oxidation of the metal Tnnickel tetroxide,[3] Ni_3O_4, has been described together with several other oxides such as Ni_4,[4] Ni_5O_7,[5] and Ni_3O_5,[6] as well as the suboxides Ni_{20},[7] Ni_3O,[8] and Ni_{40},[9] but these are probably mixtures of the monoxide with peroxide in the one case and nickel in the other [10]

Nickel Monoxide or Nickelous Oxide, NiO—This substance occurs as bunsenite at Johanngeorgenstadt in Saxony, in vitreous, translucent, pistachio-green, regular octahedra having a specific gravity of 6 398 It may be obtained by strongly

[1] Paal, *Ber,* 1914, 47, 2202 [2] Kelber, *Ibid,* 1917, 80, 1509

[3] Baubigny, *Compt rend,* 1878, 87, 1082, Dudley, *J Amer Chem Soc ,* 1896, **18,** 901, Bellucci and Bubegm, *Atti R Accad Lmcei,* [5], 1906, **15,** 11, 778

[4] Wioke, *Jahresb ,* 1865, 267

[5] Schroder, *Journ Chem Soc ,* 1890, **68,** 1213

[6] *Chem News,* 1879, **89,** 81

[7] Muller, *Pogg Ann,* 1869, **136,** 59, Tschugaev and Choplin, *Compt rend,* 1914,**159,** 62

[8] Moore, *Chem News,* 1895, 71, 81

[9] Sabatier and Espil, *Compt rend,* 1914,**158,** 668

[10] See Wohler and Balz, *Zeit Elektrochem,* 1921, 27, 406

heating the hydroxide, sesquioxide, carbonate, or nitrate in the form of a green, crystalline powder, which becomes deep-yellow on heating If nickel borate be ignited with lime in a pottery furnace and the mass treated with hydrochloric acid, nickel oxide remains behind in green cubo-octahedra which have a specific gravity of 6 8 (Ebelmen), whilst if the metal be lgnited in a curre are formed When heated in the air, ruckelous oxide at first absorbs oxygen, but loses it again at a higher temperature In the electric furnace, it melts and solidifies in green crystals,[1] which may also be obtained as minute cubo-octahedra of specific gravity 7 45 by heating with excess of potassium chloride at 1000°.[2] It is readily reduced by hydrogen at 220°,[3] by carbon monoxide at 120°, and by solid carbon at 450°, but these temperatures depend on the physical condition of the oxide The dissociation pressures of nickelous oxide have been measured between 800° and 1245°.[1]

Nickelous oxide, like cobaltous oxide, forms compounds when fused with many other metallic oxides With alumina, a well defined blue alumniate, NiO,Al_2O_3 is produced, with stannic oxide a green stannate, and with zinc oxide a green zmcate These compounds dissolve in excess of the oxide to form solid solutions the colour of which varies with the relative proportions of the constituents With magnesium oxide, nickelous oxide forms mixed crystals which are intermediate in colour between the two components, and with manganous oxide mixed crystals of a yellowish-green colour.[5]

Nickel Hydroxide, $Ni(OH)_2$, is thrown down when a solution of a nickel salt is heated with potash or soda, as an apple-green precipitate slightly soluble in water It dissolves in ammonia with a blue colour, and separates out as a green, crystalline powder on boiling the ammoniacal solution Nickel hydroxide has been prepared in colloidal solution by using sodium lysalbate as a protective colloid.[6] It may also be obtained by precipitating nickel chloride with potassium hydroxide and washing free from electrolytes or by dialysmg nickel tartrate solution.[7]

[1] Moissan, *Ann Chim Phys*, 1880, [5], 21, 199, *Compt rend,* 1892, **115,** 1034
[2] Hedvall, *Zeit atoorg Chem*, 1915, 92, 381
[3] patieff, *J pr Chem* , 1908, 77, 513
[4] Foote and Smith, *J Amer Chem Soc* , 1908, **30,** 1344
[6] Hedvall, *Zett anorg Chem* , 1918,**103,** 249
[8] Paal and Brunjes, *Ber,* 1914, 47, 2200
[7] Tower and Cooke *J. Phys Chem* , 1922,**116,** 231

The salts of nickel are derived from the monoxide In the anhydrous condition, and formed from colourless acids, they are usually yellow-coloured, whilst in the hydrated state they possess an apple-green to an emerald-green colour The soluble normal salts have a slightly acid reaction and a sweetish, astringent, metallic taste, and act as emetics.

Nickel Sesquioxide, Ni_2O_3 is a black powder obtained by gentle ignition of the nitrate or carbonate in the air, and is converted at a higher temperature into the monoxide When the sesquioxide is heated in the oxy-coal-gas flame it yields metallic nickel,[1] which on cooling becomes covered with a film of oxide It dissolves in sulphuric and nitric acids with evolution of oxygen, and in hydrochloric acid with evolution of chlorine, with ammonia, nitrogen is evolved

$$3Ni_2O_3 + 2NH_3 + 3H_2O = 6Ni(OH)_2 + N_2$$

When potassium is burnt in the air in nickel vessels, and the product treated with water, black prisms remain having the composition $Ni_2O_3 2HO$, which rapidly oxidise organic substances [2] It appears most probable that the sesquioxide is a compound of the monoxide and dioxide, NiO,NiO_2, and is to be regarded as nickelous mckehte

When chlorine is passed through nickelous hydroxide suspended in water, or when a solution of a nickel salt is warmed with an alkali hypochlorite, a black precipitate is formed which is generally regarded as *nickel tnhydroxide,* $Ni(OH)_3$, corresponding to the sesquioxide According to Bellucci and Clavan,[3] however, this substance is in reality the hydrated dioxide, NiO_2,xH_2O, which rapidly loses oxygen

Nickel Dioxide, NiO_2, has not been prepared in the anhydrous state, but a compound of this oxide and baryta termed *barium nickehte,* $BaO,2NiO_2$, is formed when barium carbonate is strongly heated with nickel sesquioxide in the electric furnace It forms dark coloured crystals of sp gr 4 8, which are rapidly decomposed by hot water and dissolve in hydrochloric acid with evolution of chlorine [4]

[1] Read, *Journ Chem Soc* , 1894, 65, 314

[2] Hofmann and Hiendlmaier, *Ber,* 1906, 39, 3184

[3] *Qazz,* 1905, 14, u, 234, *Atti R Accad Lmcet,* 1907, [5], 16, I, 647, compare Pellini and Meneghini, *Zeit anorg Chem,* 1908, 60, 178, Tanatar, *Ber,* 1909, 42, 1516, Tubandt and Riedel, *ibid,* 1911, 44, 2565, *Zeit anorg Chem,* 1911, 72, 219

[4] Dufau, *Compt rend,* 1896,**128,** 495

A peroxide of nickel, of uncertain composition, is formed by the electrolytic oxidation of the metal, and plays a part in the Jungner-Edison accumulator[1] According to Hollrd,[2] the *tetroxide,* NiO_4, is produced by the electrolysis at 70° of a very dilute solution of a nickel salt containing chromic acid and an alkali pyrophosphate

NICKEL AND THE HALOGENS

599 *Nickel Fluoride,* NiF_2, is obtained by dissolving the hydroxide or carbonate in hydrofluoric acid and evaporating, when blue-green crystals of $NiF_2,3H_{20}$ separate[3] These are decomposed by boiling water with formation of an insoluble pale green oxyfluonde The acid salt, $NiF_2,5HF,6H_2$, is also known[4]

The anhydrous fluoride is obtained by heating the chloride with ammonium fluoride in a current of hydrogen fluoride [5] It forms volatile, green prisms of specific gravity 4 63, which axe not attacked by mineral acids, but are reduced by hydrogen

Nickel fluoride forms double salts with the alkali fluorides

Nickel Chloride, $NiCl_2$—Finely divided nickel burns with a bright light when it is slightly heated in dry chlorine gas, forming yellow scales resembling mosaic gold If a solution of the oxide or carbonate in hydrochloric acid be evaporated to dryness, the anhydrous chloride is obtained as a yellow, earthy mass which dissolves readily in water with evolution of heat On gently heating for some time in the air it evolves chlorine, leaving a residue of the oxide In absence of air, on the other hand, it can be sublimed, and is then obtained in golden scales which, when boiled for some time with caustic potash, are completely converted into the hydroxide They become gradually coloured green on exposure to the air owing to the absorption of moisture, and are then easily soluble in water The salt, $NiCl_2,6H_2$, is obtained in short, six-sided prisms on concentrating the solution, these are easily soluble in water and in alcohol The hexahydrate is stable in contact with its saturated solution up to about 70°.[6] Mono- and di-hydrates are also known

[1] See Zedner, *Zeit Elektrochem,* 1905, **11,** 809, 1906, 12, 463, 1907, **13,** 752, Foerster, *ibid* , 1907,**13,**414, 1908,**14,**17, Riesenfeld, *tbid* , 1906,12, 621

[2] *Compt rend* , 1903,**136,** 229

[3] Compare Costachescu, *Ann Set Untv J assy* , 1911, 7, 5

[4] Edminster and Cooper, *J Amer Chem Soc* , 1920, 42, 2419

[5] Poulenc, *Compt rend,* 1892,**114,** 1426

[6] Etard, *Ann Chtin Phys,* 1894, [7], 2, 539

The anhydrous chloride absorbs ammonia at the ordinary-temperature, swelling up to a white powder possessing a slightly violet tinge, and having the composition $NiCl_2,6NH_3$. The same compound is obtained in blue octahedra by dissolving the chloride in ammonia and allowing the solution to cool This salt readily evolves ammonia when exposed to the air It is easily soluble in water, but less so in strong alcohol A diammoniate and monammoniate have also been prepared[1] Similar compounds are formed by the bromide and iodide

Nickel Bromide, $NiBr_2$—Finely divided nickel absorbs bromine vapour when heated in it, becoming incandescent In absence of air, the bromide sublimes at a red heat in golden scales It is also formed by the addition of bromine to finely divided nickel under ether A yellow compound, $NiBr_2(C_2H_5)_2O$, is obtained, and this, on heating, loses its ether and yields nickel bromide[2] The anhydrous salt deliquesces on exposure to air and is readily soluble in water The solution, which is also obtained by bringing the metal in contact with bromine and water, gives on evaporation deliquescent needles of $NiBr_2,3H_2$ A dihydrate, hexahydrate, and nonahydrate have also been prepared

Nickel Iodide, NiI_2—If nickel powder reduced in hydrogen be heated with iodine, or if the hydroxide be dissolved in hydriodic acid, the solution evaporated to dryness in absence of air, and the solid heated, nickel iodide sublimes in iron-black scales The solution when evaporated to a syrup deposits bluish-green, very deliquescent prisms having the composition $NiI_2,6H_2$

Nickel Chlorate, $Ni(ClO_3)_2$, is obtained by double decomposition of nickel sulphate and barium chlorate solutions, and forms three hydrates containing respectively 6, 4, and 2 molecules of water[8] The *perchlorate* made by dissolving the hydroxide or carbonate in perchloric acid,[4] gives hydrates with 9, 6, 5, and 4 molecules of water, and also forms a hexammoniate[5]

Nickel Iodate, $Ni(IO_3)_2$, forms a tetrahydrate and two isomeric dihydrates The tetrahydrate loses water, iodine, and oxygen below 100° The dihydrate exists in two isomeric forms The a-vanety is made by the action of nickel nitrate and iodic acid

[1] Biltz and Fetkenheuer, *Zeit anorg Chem* , 1913, **88,** 163
[2] Ducelhez and Raynaud, *Compt rend* , 1914,**158,** 2002
[3] Meusser, *Ber* , 1902, 35, 1414
[4] Goldblum and Terhkowski, *Bull Soc chim* , 1912, [4], **11,** 103, 146
[5] Salvador!, *Qazz,* 1912, 48, [1], 458

at 25-30°, and is converted into the -form by warming in the presence of water to 50° The a-form is only slightly soluble in water and the -form still less soluble [1]

NICKEL AND SULPHUR

6oo *Nickel Subsulphide,* Ni_2S, is obtained as a bronze-yellow, non-crystalline mass when the monosulphide is heated in the electric furnace, and on further heating loses the remainder of the sulphur, forming metallic nickel [2]

Nickel Monosulphide, NiS, occurs as millerite, being occasionally found in brass-yellow rhombohedra, but more commonly in capillary ciystals When nickel and sulphur are heated together above the melting point of the latter, this same compound is formed with incandescence as a bronze-yellow, brittle mass which is not soluble in hydrochloric or sulphuric acid, but dissolves in nitric acid or aqua regia It is also obtained by passing hydrogen sulphide over nickel at a red heat The black, hydrated sulphide is precipitated when ammomum sulphide is added to a nickel salt This is difficultly soluble in hydrochloric acid, but slightly soluble with a brownish colour in ammonia, as well as in yellow ammonium sulphide and other alkaline polysulphides, it is precipitated from these solutions on exposure to the air, or on addition of acetic acid In the moist state it oxidises readily on exposure to the air When a solution of a nickel salt is heated with sodium thiosulphate, the monosulphide is obtained in the form of a dense black precipitate which does not undergo alteration on exposure to the air, and which is not acted upon by boiling hydrochloric acid

The sulphide is not precipitated by sulphuretted hydrogen in presence of dilute hydrochloric acid, and yet the precipitated sulphide, when obtained from an alkahne solution, is found to be insoluble in dilute hydrochloric acid It appears probable, therefore, that a rapid change occurs in the freshly precipitated sulphide, and that it thus passes into a form which is insoluble in dilute hydrochloric acid [3] Theie are probably three isomeric forms of the sulphide The a-sulphide is the form chiefly produced when dilute solutions of nickel salts are slowly mixed with

[1] Meusser, *Ber* , 1901, 34, 2432
[2] Mourlot, *Compt rend* , 1897,**124,** 768
[3] See Thiel and Ohl, *Zeit anorg Chem* , 1909, 61, 396

dilute solutions of ajjcah sulphides at the ordinary temperature and in the absence of o*f* It is readily soluble in the cold in mineral acids of concentration as low as 0 012V It is quite stable in absence of air when kept in contact with pure water, but in contact with solutions in which it is slightly soluble it is transformed into the ß- and Ý-vaneties The ß -sulplude is obtained when a solution of nickel acetate acidified with acetic acid is precipitated with hydrogen sulphide It is almost insoluble in 22N-hydrochlonc acid in the cold, but dissolves rapidly on boiling The 7-sulphide is obtained by boiling the y9-form with acetic acid It is practically insoluble in boiling 22V-hydrochlonc acid One form is thus converted into another by treatment with a reagent which has a slight solvent action on it but not on the product The difference between the three forms is supposed to be due to diffeiences in molecular complexity [x]

The freezing-point cfiive foi mixtures of nickel and sulphur [2] shows that the only et pound capable of existence in contact with the melt is Ni_3S_2, "Hing at 787° NiS, Ni_3S_4, and NiS_2 also exist, but dissociate below the melting point

Linnaeite, $(Ni,Co,Fe)_3S_4$, is an important nickel ore occurring at various places in considerable masses

Nickel Sesquisulphide, Ni_2 —A black precipitate having approximately this composition is obtained by acting on nickel carbonyl with sulphur dissolved in carbon disulphide [3]

Nickel Bisulphide, NiS_2, is obtained as an impalpable iron-grey powder by strongly heating a mixture of nickel carbonate, potassium carbonate, and sulphui, the jesidue being lixiviated with water

Nickel Sulphite, $NiSO_3$, is obtained by dissolving the hydroxide in sulphurous acid It crystallises with 4 or 6 molecules of water It dissolves in ammonia to give a hydrated ammoniate, $NiSO_3,3NH_3,3H_2O$, and forms a double salt with ammonium sulphite

Nickel Sulphate, $NiSO_4$—This salt was first obtained in the pure and crystalline condition in 1775 by Beigman In order to prepare it, nickel or its hydroxide or carbonate is dissolved in dilute solution at the ordinary temperature yields green, rhombic prisms of the heptahydrate, $NiSO_4,7H_2O$, isomorphous with

[1] Thiel and Gessner, *Zeit anorg Chem* , **1914,** 86,1, *Chem Zentr* , **1914,1,** 18
[2] Bornemann, *Metallurgy,* 1908, 5, 13, 1901, 7, 667
[3] De war **and** Jones, *Journ Chem. Soc* , **1904, 35, 211**

magnesium sulphate, and with the corresponding iron and cobalt sulphates The heptahydrate is known also as nickel vitriol, or morenosite, occurring in acicular crystals, and as a fibrous efflorescence on certain nickel ores On prolonged exposure to the air, the heptahydrate changes into aggregates of blue tetragonal crystals of the hexahydrate It has long been thought that this change is brought about by the action of sunlight,[1] but it is really simply a case of efflorescence[2] If the crystals are in an atmosphere saturated with water vapour, no change takes place even in the strongest light, but, on the other hand, if the atmosphere be dry the change occurs in the dark This latter compound may be prepared by the slow evaporation at the ordinary temperature of solutions containing 30 per cent sulphuric acid it is stable in contact with its saturated solutions between 32° and 53°[3] If the heptahydrate or the blue hexahydrate ib left in contact with the saturated solution above 54°, it is converted into bright green, monoclmic crystals, which have also the composition $NiSO_4,6H_2O$ The hexahydrate is theiefore dimorphous At a tempeiature about 118° the hexahydrate is transformed into the dihydrate, and if heated above 280°, the salt loses the whole of its water A tetrahydrate is obtained by crystallising the heptahydrate from sulphuric acid of specific gravity 1 4 One hundred parts of satuiated solution contain (Steele and Johnson)

At	0°	15°	%	44 7'	50	00	80	99°	
$NiSO_4$	214	25 5	29 8	32 1	33 4	35 1	38 7	43 4	parts

Vanous basic sulphates have been described[4]

The anhydrous sulphate absorbs ammonia, becoming stongly heated and increasing in bulk, forming a violet-white powde with the composition $NiSO_4,6NH_3$ On dissolving the sulphate in strong ammonia and cooling, or allowing the solution to evaporate over sulphuric acid, transparent, dark blue, tetragonal prisms ciystallise out having the composition $NiSO_4,4NH_3,2H_2$ A compound of the formula $2NiSO_4,10NH_3,7H_{20}$ has also been described

Niclel ^Ammonium Sulphate, $(NH_4)_2SO_4,NiSO_4,6H_{20}$ —This salt is employed in the process of nickel-plating It is obtained by dissolving nickel, free from iron and copper, in dilute

[1] Phillips and Coopei, *Pogg Ann* , 1879, 6, 194
[2] Dobroserdoff, *J Buss Phys Chem Soc* , 1900, 32, 300
[3] Steele and Johnson, *Journ Chem Soc* , 1904, 85, 113
[4] Pickering, *tbid*, 1907, 91, 1985

sulphuric acid, and adding ammonium sulphate to the concentrated acid solution Tha crystalline paste which is deposited is washed with cold water and purified by recrystalhsation It crystallises in short, bluish-green, monochnic prisms One hundred parts of water dissolve (Link)

At	3 5°	16°	20°	30°	40°	50°	68°	85°	
$(NH_4)_2SO_4,NiSO_4$	1 8	5 8	5 9	8 3	11 5	14 4	18 8	28 6	parts

The salt is almost insoluble in an acidified solution of ammonium sulphate (Thomson) Many other double sulphates are known,[1] and also a double salt with mercuric cyanide, $NiSO_4,Hg(CN)_2,10H_{20}$ [2]

Nickel selenate forms double salts with the alkali selenates These are of the same type as the double sulphates and isomorphous with them [3]

NICKEL AND THE ELEMENTS OF THE NITROGEN GROUP, AND BORON

601 *Nickel Nitride* is obtained by the action of excess of ammonia on metallic nickel at 400-600°, and forms a black powder which readily dissolves in dilute sulphuric and hydrochloric acids [4] The composition of the product is intermediate between those corresponding to the formulae Ni_3N and Ni_5N_2 By heating nickelamide at 120° in vacuo, a black, amorphous powder of the mtnde, Ni_3N_2, is obtained [5]

Nickel Azoimide or Aztde, $Ni(N_3)_2$, is obtained together with a basic azoimide, N_3NiOH, on treating a nickel salt with azoimide in aqueous solution [6] It is obtained in the pure state by shaking the dry basic azoimide or finely divided nickel carbonate with azoimide in ethereal solution [7] It is a sandy, green powder which absorbs water and holds it tenaciously It is readily soluble in water, but soon hydrolyses in solution It is extremely explosive and very sensitive even to the slightest rubbing

Nickelamide, $Ni(NH_2)_2$, is obtained by the action of potassamide on nickel thiocyanate in liquid ammonia [8] It is a red, flocculent

[1] See Tutton, *Phil Trans* , 1915, *[A],* **216,** 1
[2] Scaglianni and Bonini, *Gazz* , 1920, 50, [2J, 114
[3] Tutton, *Phil Trans* , 1917, *[A],* **217,** 199
[4] Beilby and Henderson, *Journ Chem Soc* , 1901, 79, 1251
[5] Bohart, *J Physical Chem* , 1915,19, 537
[6] Curtius and Rissom, *J pr Chem* , 1898, [2], 58, 261
[7] Wohler and Martin, *Ber* , 1917, 50, 586, *Zeit angew Chem* , 1917, 30, I, 33
[8] Bohart, *loc cit*

mass which reacts with water, producing nickel hydroxide and ammonia,

$$Ni(NH_2)_2 + 2H_2O = Ni(OH)_2 + 2NH_3$$

Heated at 120° *in vacuo,* it yields the nitride, Ni_3N_2

Nitroniclel, $Ni_2(NO_2)$, is formed as a black mass mixed with oxide when nitrogen peroxide is passed over reduced nickel, and resembles the corresponding cobalt compounds [1]

Nickel Nitrite, $Ni(NO_2)_2$, is obtained in solution by the decomposition of the sulphate with barium nitrite It is a very unstable compound, but forms with potassium nitrite the easily soluble double salt, $4KNO_2,Ni(NO_2)_2$ This is obtained in brownish-red octahedra by mixing a concentrated solution of the mtrite with an excess of potassium nitrite When potassium nitrite is added to a nickel solution containing a calcium salt, a yellow, crystalline precipitate of $2KNO_2,Ca(NO_2)_2,Ni(NO_2)_2$ is formed, which possesses great similarity to potassium cobaltinitiite (p 1343), and if a solution contain a sufficient quantity of calcium together with nickel and cobalt, the whole of the nickel, as well as the cobalt, may be thrown down by potassium nitrite This fact must be remembered in the separation of the two metals The corresponding barium and strontium compounds have been prepared, and also a number of other double and triple nitrites [2]

Nickel Niti ate, $Ni(NO_3)_2,6H_2O$, crystallises in green, monochnic tablets which dissolve in two parts of cold water and in alcohol, and effloresce on exposure to dry air, dehquescmg however, in moist air Hydrates with $3H_2O$ and $9H_2$ have also been obtained[3] Anhydrous nickel nitiate is a pale greenish-yellow powdei, which begins to evolve nitrous fumes at 105-110°[4] The tetrammoniate, $Ni(NO_3)_2 4NH_3, H_2O$, is obtained by adding alcohol to a solution of nickel nitrate and ammonia,[5] and the hexammoniate, $Ni(NO_3)_2,6NH_3$, by the action of ammonia on the anhydrous salt [6] Nickel nitrate forms a number of double nitrates with other nitrates and also a double salt, $Ni(NO_3)_2,Hg(CN)_2,6H_2O$, with mercuric cyanide [7]

[1] Sabatier and Senderens, *Bull Soc chim* , 1893, [3], 9, 669
[2] Cuttica, *Gazz* , 1922, 52, [1], 210
[3] Funk, *Zeit anorg Chem* , 1899, 20, 409
[4] Guntz and Martin, *Bull Sec chim* , 1909, 5, 1004
[5] Erdmann, *J pr Chem,* 1840,19, 445, see W\ckoff, *J Amer Chem Soc* , 1922, 44, 1260
[6] Ephraim, *Ber* , 1913, 48, 3103
[7] Scagliarmi and Bonim, *Gazz* , 1920, 50, 11, 114

Nickel Phosphides —When nickel and phosphorus are heated in the electric furnace the compound Ni_2P is obtained in transparent, grey needles of sp gr 6 3,[1] insoluble in all acids except a mixture of nitric and hydrofluoric acids A phosphide of the same composition is prepared in the wet way as a black precipitate by adding nickel chloride to a boiling solution of potash containing some phosphorus and tartaric acid Compounds of the formulae P_2Ni_5, P_2Ni_3, P_3Ni_2, PNi_3, P_2Ni, P_3Ni have also been described[2]

Nickel Arsenides —These two elements fuse together readily to form brittle alloys, some of which occur as minerals Of these the most important is kupfer-nickel, niccohte, or nickehne, NiAs, which is found massive, and also, although less frequently, crystallised in hexagonal pyramids It has a light copper-red colour, and is an important ore of nickel, being found in various localities in Europe and America Chloanthite, $(Ni,Co,Fe)As_2$, is another nickel arsenide occurring together with the preceding The study of the freezing-point curve for mixtures of nickel and arsenic indicates the existence of the compounds NiAs, Ni_3As_2, and Ni_5As_2[3] The diarsenide, $NiAs_2$, has also been obtained[4]

The Phosphates of Nickel are insoluble in water, and more or less soluble in the mineral acids The *arsenates* possess similar properties, and some of them occur in the mineral kingdom

Nickel Bonde, NiB, is prepared in the electric furnace from its constituents, and forms brilliant prisms of specific gravity 7 39 It is decomposed by fused alkalis and by water vapour at a dull led heat The compounds Ni_2B and NiB_2 have also been described[6] The freezing-point curve of nickel-boron mixtures indicates the formation of the compounds Ni_2B, Ni_3B_2, NiB, and Ni_2B_3[7]

[1] Maronneau, *Compt rend* , 1900,**130,** 656

[2] Sec Granger, *ibid,* 18%, **122,** 1484, 18%, **123,** 176, Konstantinoff, *J Muts Phys Chem Soc,* 1908, **40,** 742, Johbois, *Compt rend,* 1010, **150,** 100

[3] Friednch and Bennigson, *Metallurgie,* 1007, 4, 200 Compare Vigouroux, *Compt rend* , 1908,**147,** 426

[4] Beutell, *Cenlr Min* , 1016, 49

[5] Moiasan, *Compt rend* , 1806,**122,** 424

[6] Bmet du Jassonneix, *ibid,* 1007, **146,** 240, *Eighth Inter Cong App Chem* , 1912, 2, 165

[7] Giebelhausen, *Zeit anorg Chem* , 1915, 91, 251

NICKEL AND THE ELEMENTS OF THE CARBON GROUP

602 *Nickel Carbide,* Ni_3C —Carbon dissolves in molten nickel, and the solubility increases with temperature to a maximum at 2100°, which conesponds to the compound Ni_3C. At lower temperatures this dissociates and the decomposition is very rapid at 1600° Consequently even quenched specimens of the metal contain but little of the carbon in combination and the compound has not been isolated [1]

Nickel Tetracarbonyl, $Ni(CO)_4$—When carbon monoxide is passed over metallic nickel at aboul 350-400°, carbon dioxide is formed and carbon liberated, but at a lower temperature the metal unites with carbon monoxide to form nickel tetracarbonyl This substance is best prepared by reducing nickel oxide in hydrogen at about 400° in a combustion tube, allowing it to cool to 30-80°, and then passing carbon monoxide over the reduced metal When the issuing gas is cooled with salt and ice it deposits the nickel carbonyl, the excess of the gas being repeatedly passed over the nickel until no more of the compound is formed The metal is then again heated in hydrogen at 400°, cooled, and treated with carbon monoxide, the whoJe process being repeated as often as desired, about 10-15 grams are obtained at each operation [2] If caibon monoxide under high pressure is employed, the nickel may be heated much more strongly[3] Thus under 100 atmospheres the nickel carbonyl produced is not decomposed even at 250°

Nickel tetracarbonyl is a colourless liquid having a specific gravity of 13185 at 17°, it boils at 43 2° under 760 mm pressure, and solidifies at —25°, forming needle-shaped crystals It has the normal vapour density of 6 01 at 50°, but explodes at 60°, some carbon dioxide being formed and carbon liberated When diluted with an inert gas the vapour does not explode, and undergoes decomposition less readily,[4] with carbon monoxide as diluent it has nearly the normal vapour density at 100°, and dissociation is not complete at 182° When gas eon-

[1] **Ruff and Martin,** *Metallurgie,* **1912, 9, 143, Ruff,** *Ber,* **1912, 45, 3139, Ruff and Gersten,** *Ber* **, 1913, 46, 400, Ruff and Bormann,** *Zat anorg Chem* **, 1914,88,38b, Briner and Senglet,** *J Chim Phys,* **1915, 13, 351**

[2] **Mond, Langer, and Quincke,** *Journ Chem Soc* **, 1890, 67, 749 See also Tassilly, Penau and Roux,** *Bull Soc chim* **, 1921, [4], 29, 862**

[3] **Dewar,** *Journ Chem Soc* **, 1904, 86,11, 488**

[4] **Dewar and Jones,** *Proc Roy* **Soc , 1903, 71, 427**

taming the vapour is passed through a heated tube, pure metallic nickel is deposited with liberation of carbon monoxide

It is soluble in alcohol, enzene, chloroform, and carbon tetrachloride When the solution in benzene is boiled the carbonyl is decomposed, carbon monoxide being evolved and nickel left as a violet-grey, colloidal solution [1] Nickel carbonyl is not acted on by dilute aqueous acids or alkalis It is not decomposed by water free from air, but dissolves to the extent of 18 mgm per 100 grams of water at 9 8°, dissociation into nickel and carbon monoxide takes place slowly when the solution is preserved In the presence of air it undergoes oxidation, nickel hydroxide being formed together with a white compound of unknown constitution containing carbon,[2] which may possibly be a basic carbonate [3] It is rapidly decomposed by the halogens, yielding carbon monoxide and the nickel halide, concentrated sulphuric acid converts it into nickel sulphate with evolution of hydrogen and carbon monoxide, and it is rapidly oxidised by dry concentrated nitric acid Dry hydrogen chloride and bromide attack it only very slowly, but dry hydrogen iodide yields nickel iodide, hydrogen, and carbon monoxide With sulphur dissolved in carbon disulphide a sulphide having approximately the composition Ni_2S_3 is formed, whilst sulphuretted hydrogen yields nickel monosulphide [4] When nickel carbonyl and thiocarbonyl chloride are allowed to react, carbon monosulphide, or a polymeride of this substance, is produced [5] As already mentioned (p 1358), the formation and subsequent decomposition of nickel carbonyl are made use of on the large scale in the Mond process for extracting nickel from its ores

The vapour of nickel tetracarbonyl has a very poisonous action When inhaled in small quantities it produces toxic symptoms of a very definite type The lethal dose for men is unknown, but for animals (rabbits, dogs, cats, etc) it varies between 0 018 and 0 04 volume per cent of the vapour in air, inhaled for 65 to 90 minutes The substance is decomposed in the lungs into carbon monoxide and a nickel compound, which is possibly the hydrated basic carbonate The carbon monoxide available is not sufficient to produce any symptoms, and the toxic effect is entirely due to the nickel content [6]

[1] Ostwald, *Kolloid Zeit,* **1914, 15, 204**
[2] Berthelot, *Compt rend,* **1891, 112, 1343, 113,** 679
[3] Armit, *Journ Hygiene,* **1907, 7,** 525
[4] Dewar **and** Jones, *Journ Chem Soc ,* **1904, 85, 203**
[5] *Ibid , Proc Boy Soc , [A],* **1910, 83, 408**
[6] Armit, *Journ Hygiene,* **1907,** 7, 525, **1908,** 8, 565

Nickel Carbonate, $NiCO_3$, is obtained in the form of pale green, microscopic rhombohedra, by heating nickel chloride solution with calcium carbonate to 150° When a nickel nitrate solution is mixed with a solution of sodium bicarbonate saturated with carbon dioxide, and this is allowed to stand at a low winter temperature, microscopic, monochnic crystals of $NiCO_3,6H_{20}$ are formed which lose their water readily on warming A tnhydrate, $NiCO_3,3H_{20}$, can also be obtained[1] When a nickel solution is precipitated with an alkali carbonate, basic salts of varying composition are thrown down in the form of pale green precipitates

Nickel Monocyanule, NiCN--When a solution of potassium nickelocyanide, $K_2Ni(CN)_4$, is reduced with potassium amalgam in an atmosphere of hydrogen a red solution is obtained contaming the salt $K_2Ni(CN)_3$, in which the nickel is monovalent, 2KCN,NiCN On acidifying the solution, an orange-yellow precipitate is obtained of nickel monocyanide, NiCN, which rapidly oxidises to ordinary nickel cyanide, $Ni(CN)_2$[2]

The red potassium nickelocyanide, $K_2Ni(CN)_3$, is readily oxidised to the yellow nickelocyanide, $K_2Ni(CN)_4$ This occurs even in absence of air, hydrogen being liberated and metallic nickel deposited

$$4K_2Ni(CN)_3 + 2H_{20} = 3K_2Ni(CN)_4 + Ni + 2KOH + H_2,$$

but in presence of air or of an oxidising agent, such as hydrogen peroxide, nickel hydroxide is precipitated[3]

$$4K_2Ni(CN)_3 + 2H_{202} = 3K_2Ni(CN)_4 + Ni(OH)_2 + 2KOH$$

With ammonium chloride in the hot, oxidation is very rapid owing to neutralisation of the potassium hydroxide by the acid formed by hydrolysis of the ammonium chloride, and the yellow nickelocyanide formed is further attacked with precipitation of nickel cyanide (Bellucci)

$$K_2Ni(CN)_4 + 2NH_4C1 = Ni(CN)_2 + 2KC1 + 2NH_4CN$$

Nickel Cyanide, $Ni(CN)_2$, is an apple-green precipitate easily soluble in an excess of potassium cyanide with formation of the crystalline double salt, $Ni(CN)_2,2KCN$, or $K_2Ni(CN)_4$[4] This is

[1] **Nanty,** ***Ann Chim Phys*** **, 1912, [8], 27, 5, 1913, [8], 28, 77**
[2] **Bellucci and Corelli,** ***Atti R Accad Lincer,*** **1013, [5], 22, 485**
[3] **Bellucci,** ***Gazz*** **, 1919, 49, ll, 70**
[4] **See Rossi,** ***ibid*** **, 1915, 45, I, 6**

again decomposed by ulute acids with separation of nickel cyanide It is also decomposed by alkaline hypochlorites, a hydrated higher oxide of nickel being precipitated The corresponding cobalt salt under similar treatment is oxidised to the cobalticyanide which is not further attacked Advantage is taken of this difference in behaviour for the separation of cobalt and nickel in qualitative analysis No stable salts corresponding to the ferro- and fern-cyanides are formed

Nickel Silicide, Ni_2Si, is obtained by heating an excess of nickel with silicon in the electric furnace until the greater part of the metal has been volatilised, and then treating the residue with dilute nitric acid It is a steel-grey, crystalline powder with a metallic appearance, and has the specific gravity 7 2 It is readily attacked by fluorine, and dissolves in hydrofluoric acid and in aqua regra [1] The method of thermal analysis, controlled by microscopic obsr rvations, indicates the existence of the following compounds of nickel and silicon N13S1, Ni_2Si, Ni_3Si_2, N1S1, and Ni_2Si_3 [2]

The *Nickel Silicates* occur in nature Rewdanskite occurs at Rewdansk in the Urals, and is worked for nickel It is an earthy mineral which consists chiefly of $(Ni,Fe,Mg)_3Si_2,2H_2$, and contains about 18 per cent of nickel Garniente, $2(Ni,Mg)_5Si_4,3H_{20}$, occurs in New Caledonia, and is now largely worked up for nickel in France It contains 24 per cent of nickel (Liversidge)

The *oithosilicate,* Ni_2SiO_4, is formed in greenish-yellow crystals when the oxide and chloride are heated with amorphous silica [3]

DETECTION AND ESTIMATION OF NICKEL

6O3 Nickel compounds behave in a similar manner to those of iron and cobalt when heated with 1 educing agents before the blowpipe An infusible magnetic powder is produced, and when this is dissolved in a drop O1 two of dilute nitric acid and evaporated to complete dryness, a characteristic gieen stain is obtained which becomes yellow on further heating Nickel compounds, moreover, colour the borax bead a brownish-yellow in the oxidising flame, the bead becoming' grey and opaque in the reducing flame owing to the separation of metallic nickel

[1] Vigouroux, *Compt rend* , 1895,**121,** 686, 1906,**142,** 1270
[2] Guertler and Tammann, *Zeit anory Chem* , 1906, 49, 93
[3] Bourgeois, *Compt rem!,* 1889, **108,** 1177

The nickel compounds in general give no flame spectrum, but the acetate when moistened with hydrochloric acid gives first a transient purple, followed by a more permanent deep-red colour, the production of the colour taking place in the inner cone of the flame [1] The chloride yields a characteristic spark spectrum, and the spectrum of the metal also contains many lines, of which a few of the brightest are 5893 in the orange, and 4874, 4866, and 4856 in the green-blue

Nickel is very readily detected with the aid of certain orgamc reagents Thus when a-dimethylglyoxime, $[(CH_3)C\ N\ OH]_2$, is added to a solution of a nickel salt containing excess of ammonia or of sodium acetate, a scarlet precipitate separates, one part of nickel in 400,000 parts of water being capable of detection in this manner [2] Cobalt does not give a precipitate with this reagent, nor does it interfere with the reaction unless present in very large excess This reaction may also be employed for the quantitative estimation of nickel,[3] and, indeed, permits the complete separation of this metal from all other metals belonging to the same analytical group When dicyanodiamide, $C_2N_4H_4$, and then caustic potash are added to a solution of a nickel salt previously acidified with hydrochloric acid, a dense yellow precipitate is produced of nickel dicyanodiamidme, $Ni(C_2H_5ON_4)_2,2H_{20}$, which becomes flesh-coloured when heated In dilute solutions the precipitate forms only on boiling or standing[4] a-Benzyl dioxime may also be employed for the detection and quantitative estimation of nickel It gives a red pi ecipitate with nickel salts [P>]

Nickel is precipitated in alkaline solution by ammonium sulphide along with the other metals of the iron group, from all of which except cobalt it can be separated by treating the pi ecipitate with dilute hydrochloric acid, in which the sulphides of these two metals are almost insoluble A characteristic property of nickel sulphide is that it dissolves slightly in yellow ammonium sulphide to a dark-coloured solution

The best method for the qualitative detection of nickel and cobalt is based on Liebig's method for their estimation (see

[1] Hartog, *British Assoc Reports,* 1001, 613

[2] Tschugaeff, *Ber,* 1005, 38, 2520, *Compt rend,* 1907, **146,** 079, Brunck, *Zeit angew Chem* , 1907, 20, 834, 1835

[3] *Loc cit* See also Armit and Harden, *Proc Boy Soc* , 1006, [J5], 77, 420

[4] Oosgmann and Schuck, *Ber,* 1906, 39, 3356, *Chem Zat,* 1907, 31, 335, 911

[5] Atack, *Analyst,* 1913, 38, 310

below) For this purpose the sulphides are dissolved in concentrated hydrochloric id with the addition of a crystal of potassium chlorate, and the solution is evaporated nearly to dryness and afterwards diluted with water Potassium cyanide is then added until the precipitated cyanides re-dissolve, a drop of acetic acid is added and the liquid boiled for a few minutes The solution then contains potassium cobalticyanide and potassium nickel cyanide The latter is at once decomposed by sodium hypochlorite in alkaline solution, whereas the former is not attacked by this reagent The solution is therefore made alkaline with caustic soda and boiled with sodium hypochlorite, when the nickel is precipitated as the black tnhydroxide, which may be filtered off, washed, and tested by the borax bead, whilst the cobalt can be detected in the filtrate by evaporating and testing the residue by one of the dry reactions

Cobalt is much more leadily precipitated in the form of sesquioxide than nickel, a fact which is made use of in the cominercial separation of the two This reaction can also be used for the qualitative and quantitative separation of nickel and cobalt When bromine water is added to a cold neutral solution of the two metals, the cobalt is rapidly precipitated as the sesquioxide, whilst the nickel remains in solution [1]

Numerous methods, both gravimetric and volumetric, have been proposed for the quantitative separation and estimation of nickel and cobalt In addition to the dimethylglyoxime and dicyanodiamide processes, already referred to, the three following gravimetric methods may be described [2]

Liebig's hydrocyanic acid method[3] may be applied to the quantitative separation of the metals substantially in the form which has been described above The solution containing potassium cobalticyanide and potassium nickel cyanide mav be treated with caustic soda and sodium hypochlorite as there described, or may be boiled with precipitated mercuric oxide, the whole of the nickel being precipitated as a mixture of oxides, which after ignition may be weighed as nickel monoxide The filtrate is acidified with nitric acid, and mercurous nitiate added in excess Mercurous cobalticyanide is precipitated and is converted by ignition into tncobalt tetroxide Both in this and the succeeding methods one of the metals is frequently

[1] Taylor, *Mem Manch Phil Soc* , 1902, 46, No 11
[2] Compare *Zeit anal Chem* , 1891, 30, 227
[3] *Annalen,* 1853, 87, 128

estimated indirectly The two are precipitated together by caustic soda from a known volume of solution, and the mixed oxides weighed, the amount of one of the metals being then found by difference

Another separation of nickel from cobalt depends upon the precipitation of potassium cobaltinitrite (see p 1343) This is dried at 100° and weighed, and the nickel in the filtrate is precipitated by caustic potash, the precipitate boiled, well washed, and converted by ignition into the monoxide

A very accurate method depends on the fact that nitroso-ß-naphthol, $C_{10}H_6(OH)NO$, yields an insoluble compound with cobalt salts, but not with those of nickel[1] The solution is therefore acidified with hydrochloric acid, and a solution of this reagent in acetic acid added A very voluminous precipitate is formed, which is well washed and then lgnited with a little oxalic acid, the cobalt being finally heated in hydrogen and weighed

Nickel may also be estimated by electrolysis of its strongly ammoniacal solution It may also be estimated by precipitating as oxide (with alkaline hypobromite solution), igniting to the monoxide and weighing as such Estimation as sulphide may also be made

The Atomic Weight of nickel has been frequently determined Of the older deteiminations, the most important are those of Russell,[2] Schneider,[3] Dumas,[4] Ziminermann,[5] and Winkler[6] More recent and accurate determinations were made by Richards and Cushman,[7] who deduced the value 58 69 from the amount of silver required to precipitate the bromine in puie nickel bromide, and the value 58 71 from the weight of nickel produced by the reduction of the same compound in hydrogen (Echsner de Coninck and Gerard [8] by reducing the pure oxalate in hydrogen obtained from the ratio nickel oxalate hydrogen a value 58 57 as a mean of five determinations Baxter and Parsons [9] have

[1] Ihnski and Knorre, *Ber*, 1885, **18,** 699, Chapin, *J Amer Chem Soc*, 1907, **20, 1029**

[2] *- Journ Chem Soc* , **1863,16,** 58, *ibid* , 1869, **22,** 294

[3] *Pogg Anh* , 1857,**101, 387**

[4] *Ann Chim Phys*, 1859, [3], **55,** 129 [5] *Annakn*, 1885, **232, 324**

[6] *Zeit anal Chem*, **1867,** 6, ***22,*** *Zeit anorg Chem*, **1893, 4, 10, 462, 1895,** 8, 1, **291**

[7] *Zeit anorg Chem* **,1898,16, 167, 1899,20,352**

[8] *Compt rend* , **1914,158, 1345**

[9] *J Amer Chem Soc* , **1921, 48, 507**

determined the atomic weight of terrestrial and meteoric nickel by reduction of the oxide in hydrogen As a mean of nine determinations they find for terrestrial nickel the value 58 70, and as a mean of three determinations for meteoric nickel the value 58 68 The value now adopted (1922) is 58 68

SUB-GROUP (6) THE RUTHENIUM GROUP.

Ruthenium Rhodium Palladium

604 The three metals of this group all have a silvery lustre, combine with oxygen at high temperatures rather more readily than the members of the platinum group, and melt at a lowei temperatuie The salts of ruthenium and rhodium correspond to the sesquioxide, M_2, whilst palladium forms two series of salts coriespondmg to the monoxide and dioxide, the former being the more stable Ruthenium also yields salts of the acidic oxides RuO_3 and Ru_2, and, unlike the other two, forms a tetroxide, RuO_4

All three metals give rise to series of ammoniacal bases, the properties and composition of which differ, however, in each case The ruthenium bases all contain the nitroso-group, NO, in addition to ammonia, those of rhodium closely resemble the cobalt derivatives, and those of palladium conespond to two of the senes yielded by platinum

RUTHENIUM RU=101 7 At No 44

605 In 1828 Osann[1] stated that he had discovered tlnee new metals in the platinum ores from the Ural To one of these he gave the name of *ruthenium,* from the name of Russia, the country in which it was found In the following year however, he withdrew the statement of the existence of one of the metals, and the existence of the other two remained doubtful until Claus, in 1845, examined the question This chemist proved the existence of a new metal in the platinum ore, and retained for it the name of ruthenium because it was found to be contained in small quantity in the substance termed ruthenium oxide by Osann, which for the most part consisted of silica, zircoma, and the oxides of titanium and iron Claus

[1] ***Pogg Ann*, 1828,14, 329, 1845, 64,197**

investigated the reactions of the metal and a large number of its derivatives [1]

Ruthenium is found both in platinum ore and in osmmdium, whilst it occurs as sulphide in laurite, Ru_2S_3 [2]

Of the various methods of preparing the metal, that of Deville and Debiay [3] is the most interesting, as these chemists obtained it on a large scale, and specially studied its physical properties For this puipose, the alloy of osmmdium (p 1438) containing ruthenium is fused with zinc, the regulus then treated with hydrochloric acid, and one part of the finely-divided residue mixed with three parts of barium peroxide and one part of barium nitrate, the mixture being heated for two hours to a temperature somewhat below the melting point of silver The cold mass is then reduced to an impalpable powder and thrown into dilute hydrochloric acid contained in a stoppered bottle In this operation the liquid niust be kept well cooled in order to prevent the escape of the poisonous vapours of osmium tetroxide, and the operation must be carried on in a good draught As soon as the action is over, one part of nitric acid and two parts of sulphuric acid are added to the liquid, the mixture is well shaken, the barium sulphate allowed to deposit, and the clear liquid poured off The residue is washed by decantation, and the liquid distilled until three-fourths of it has passed over The distillate is woiked up for osmium, whilst the concentrated lesidue, mixed with from two to thiee paits of ammonium chloride and a small quantity of nitnc acid, is dned on the water-bath The residue is then washed with water which is half saturated with ammonium chloride, until the filtrate is colour-less By this treatment ammonium lridichloride, containing some ruthenium, remains behind This is lgnited, and the remaining spongy metallic mass fused for two hours in a silver basm with two parts of mtre and one part of caustic potash The fused mass is then dissolved in water, and the characteristic orange-red solution of potassium ruthenate treated with nitric acid until the yellow colour has disappeared Ruthenium oxide separates out, but still contains silica, with some indium and osmium »It is then lgnited in a graphite crucible and fused in

the oxy-hydrogen furnace

[1] *Annalen*, 1845, 66, 257, 1846, 59, 234, *Pogg Ann*, 1845, 64, 622, 65, 200, *Jahresb*, 1859, 257, 1860,205, 1861,230, 1863,397

[2] Wohler, *Annalen*, 1864,**129,** 116

[3] Deville and Debray, *Compt rend*, 1876, 83, 926, 1879, 89, 587

Another plan for preparing chemically pure ruthenium depends upon the fact hat whilst osmium tetroxide is volatilised in a stream of air, the corresponding volatile tetroxide of ruthenium is only formed by the action of chlorine in alkaline ruthemum solution Hence the metal, as obtained by other processes, must be heated in a current of oxygen until the whole of the osmium tetroxide has been volatilised and then fused a second time with potash and saltpetre, the mass dissolved in water, saturated with chlonne, and distilled in a stream of chlorine on the water-bath, when pure ruthenium tetroxide volatilises This is then dissolved in caustic potash or in water, reduced by alcohol, and the black precipitate converted into metal by ignition in a stream of pure hydrogen [1]

In order to obtain the metal in the crystalline state it may be fused in a carbon crucible with from five to six times its weight of tin, the alloy being treated with boiling hydrochloric acid, which leaves the compound $RuSn_3$ undissolved, this when ignited in a carbon boat in a current of hydrogen chloride leaves a residue of crystallised ruthemum

Fused ruthemum has a specific gravity of 12 063 at 0°, like indium, it is hard and brittle, and next to osmium is the most infusible metal of the group It can, however, be fused in the oxy-hydrogen flame[2] and distilled in the electric furnace[3] With the exception of osmium, it is also the one which combines most readily with oxygen, the fused metal becoming covered with a brown film in the air, on cooling it "spits" like silver and indium When heated in a current of oxygen it yields the dioxide, and at temperatures of about 1000° some tetroxide also is formed, although this substance decomposes when heated by itself at 107°[4] The pure metal is scarcely attacked even by aqua regia, but it combines with chlorine at a red heat *Ruthemum sponge* is made by heating ammonium ruthenichlonde

Colloidal Ruthemum may be prepared by reducing its salts with hydrazine, or other reducing agents, in the presence of a protective colloid such as gum acacia[5]

[1] See Gutbier and Trenkner, *Ze it anorg Chew* , 1905, 45, 166
[2] Myhus and Dietz, *Ber* , 1898, 31, 3187
[3] Moissan, *Compt rend*, 1906,**142,** 189
[4] Debray and Joly, *Ibid*, 1888,**106,** 100
[5] Gutbier and Hofmeier, *J pr Chem*, 1905, [2], 71, 452

RUTHENIUM COMPOUNDS

EUTHENIUM AND OXYGEN

606 Ruthenium forms the oxides Ru_2, RuO_2, and RuO_4, and, in addition, salts corresponding to the acidic oxides RuO_3 and Ru_2 have been prepared Oxides of the formulae RuO, Ru_2, and Ru_4 have also been described, but, according to Gutbier and Ransohor?,[1] these do not exist

Ruthenium Sesquioxide, Ru_2—When finely divided ruthenium is heated in the air it combines with 27 per cent of its weight of oxygen, forming a blue powder which is insoluble in acids This was regarded by Claus as the sesquioxide, but is more piobably a mixture of the dioxide and metal (Gutbier and Ransohofl) The sesquioxide can be obtained, containing a trace of alkali, by heating the tnhydroxide in dry carbon dioxide, and forms a black, scaly mass

Ruthenium Tnhydi oxide, $Ru(OH)_3$, is obtained by precipitating the corresponding chloride with an alkali It forms a blackish-brown precipitate, which even after washing with very dilute hydrochloric acid retains a trace of alkah It dissolves with a yellow colour in acids, but is insoluble in water and alkalis

The chief ruthenium salts are derived from the sesquioxide, and of these only a few of the halogen compounds are well known The chloride and its double salts dissolve in water, forming 1 eddish-yellow solutions, which deposit on standing, slowly in the cold but quickly when warmed, a black, very finely divided precipitate of oxychlonde This reaction is so delicate that one part of the metal imparts a distinct ink-like colour to 100,000 parts of water

Ruthenium Dioxide, RuO_2 —This oxide is obtained by roasting the disulphide or sulphate in contact with air It is likewise formed if the metal is fused in an oxidising atmosphere, when it burns with a sparkling smoky flame, and evolves an ozone-like smell Hence this compound can be easily obtained from the ruthenium contained in the osmiridmm alloy, which may for this purpose be heated in a porcelain tube to the melting point of copper, in a current of pure air, from which all organic substance has previously been carefully separated The ruthenium dioxide is carried forward by the osmium tetroxide

[1] *Zeit anorg Chem* , 1905, 45, 243, where the literature is quoted

formed at the same the, **and deposited in the cold part of** the **tube,** whilst the more **volatile osmium compound is carried** on still further by the current **of air The formation** of dioxide when the finely divided metal is heated in oxygen begins at 600° and the rate of formation increases very rapidly with rise of temperature[1] Euthemum dioxide crystallises in small, very hard, tetragonal pyramids, possessing a green, metallic lustre and a bluish or greenish iridescence These have a specific gravity of 7 2, and are isomorphous with cassitente and rutile (Raminelsberg)

Ruthenium Tetrahydroxide, $Ru(OH)_4,3H_2O$, is obtained, according to Claus, by evaporating ruthenium disulphate with caustic potash, when a dark red precipitate falls down The product always contains alkali, and has not been obtained pure It dries to a leddish-brown mass, giving off water at 300° When more strongly heated it deflagrates with vivid incandescence and evolution of a black, soot-like smoke It is soluble in acids and alkalis, yielding yellow solutions

The oxides RuO_3 and Ru_2 and the corresponding acids have not been prepared, but salts derived from them are known

Potassium Ruthenate, K_2RuO_4,H_2, is obtained by igniting a mixture of ruthenium, caustic potash, and potassium nitrate or carbonate, or by the action of 5O grams of the tetroxide on a solution of 70 grams of caustic potash in 500 c c of water at 60°, it crystallises from water in rhombic crystals having the above composition, which have a green, metallic reflex, and are red in transmitted light They take up moisture and carbon dioxide from the air and lose all their water at 200°

Potassium per-ruthenate, $KRuO_4,H_2$, is prepared by the action of chlorine on a solution of the foregoing salt, or by dissolving 60 grams of caustic potash in 250 c c of water, warming to 60°, and adding 50 grams of ruthenium tetroxide previously fused under water If forms black, lustrous, tetragonal octahedra, When heated in a vacuum at 400° it decomposes with formation of oxygen, ruthenium dioxide, and the ruthenate, or possibly a salt of potassium with a lower oxide[2]

Ruthenium Tetroxide RuO_4—This compound, as already stated, is formed in small quantity when the metal is heated at 1000° in a current of oxygen, although when heated alone it decomposes at 106—107° It is prepared by passing chlorine

[1] **Gutbier and others,** ***Zeit anorg Chem*** **, 1916, 96, 182**
[2] **Debray and Joly,** ***Compt rend,*** **1888,106, 1494, 1891,113, 694**

into a solution of potassium nitrosochlororuthenate, or of potassium ruthenate or sodium ruthenate prepared by fusing the metal with sodium peroxide, the liquid becomes heated and the tetroxide distils over and is deposited in the receiver It is best purified by distillation through anhydrous calcium chloride in a vacuum, the apparatus being carefully freed from orgamc matter It melts at 25 5°, the liquid readily remaining superfused, and solidifying to a vitreous mass When headed it does not boil, but decomposes at 106—107° with a smoky flame but no explosion, the crystalline dioxide being formed. It may, however, be volatilised under reduced pressure, its vapour pressure at 42° and 100 8° being 20 mm and 183 mm The vapour has a yellow colour and an irritating odour resembling that of ozone or nitrous fumes According to Gutbier and Ransohoff, it does not attack the mucous membrane, but cannot long be endured and may produce severe symptoms of poisoning, it blackens orgamc matter rapidly, and is iminediately reduced by alcoholic potash with separation of finely divided metallic ruthenium [1] Serious explosions may occur if the solid tetroxide is treated with alcohol, even in dilute solution [2]

The moist oxide quickly decomposes, in the dry state it is fairly stable, but it decomposes in sunlight with formation of lower oxides It dissolves slowly in water, and the solution when it contains free chlorine or hypochlorous acid may be kept unchanged for some days in the dark, but when pure slowly deposits a black precipitate The aqueous solution has a weak acid reaction Salts are formed with alkali hydroxides but only the ammonium salt, $(NH_4)_2\ RuO_5$, has been isolated [3]

RUTHENIUM AND THE HALOGENS, SULPHUR, AND NITROGEN

607 0nly the tnhalogen derivatives of ruthenium have been prepared in the pure state, but it is probable that dihalogen compounds are also formed, and numerous complex substances derived from the tetrahalogen series are known When chlorine is passed over the metal, combination occurs slowly, but the resulting mass appears to be a mixture

[1] Debray and Joly, *Compt rend*, 1888, **106,** 328, Joly, i*bid*, 1891, **113,** 693

[2] Gutbier and others, *Zett anorg Ghent*, 1916, 95, 177

[3] Krauss, *ibid* , 1921,**119,** 217

***Ruthenium Dichlorice,* $RuCl_2$, has not been isolated, but** is **probably present in the blua liquid obtained by the action of sulphuretted hydrogen on a solution of the trichloride**

Ruthenium Trichloride, **$RuCl_3$, is** said **to be formed** when the finely divided metal is heated in a mixture **of** chlorine and carbonic oxide at 360—440° (Joly) It **is** best prepared by evaporating the tetroxide with hydrochloric acid, chlorine being evolved It then forms a lustrous mass which dissolves readily in water, forming orange-yellow coloured solutions The aqueous solution decomposes when gently warmed, an intensely black precipitate being produced (p 1391)[1] The trichloride unites with ammonia to form a compound, $2RuC]_3,7NH_3$, which forms a deep red solution in water (Joly)

Double salts of the trichloride with alkah chlorides, R_2RuCl_5, known as *i uthemochlorides* or *thlororuthemtes,* can easily be obtained[2] The potassium, rubidium and coesmm compounds are the most characteristic They form dark-coloured crystals containing $1H_{20}$, but the caesium compound may crystallise anhydrous[3] An isomeric series of chlorides also exists termed the *aquocldororuthenates*[4] They are obtained by boiling the solutions of the ruthemochlondes with alcohol *Potassium aquochloro-ruthenate,* $K_2Ru(OH_2)Cl_5$, crystallises in rose-red octahedra Its solution is at once darkened by chlorine

Ruthenium Tetrachloride, $RuCl_4$, is probably formed when the tetrahydroxide is dissolved in hydrochloric acid, but has not been obtained pure Its compound with the alkali chlorides and hydrochlorides of organic bases,[5] R_2RuCl_6, known as *ruthem-chlondes* or *chlororuthenates,* can readily be obtained

Potassium Ruthenichloride, K_2RuCl_6, is prepared by fusing ruthenium with potash and potassium chlorate, dissolving in cold water, and adding dilute hydrochloric acid It forms minute reddish-brown crystals and is sparingly soluble in cold water[6] The salt formed by the action of chlorine on potassium aquochlororuthenate appears to be isomeric with this (Howe)

Ruthenium Oxychloride, RuO_2Cl_2, is not known, but double alkah salts, such as RuO_2Cl_2 2CsCl, have been prepared by the

[1] Gutbier and Trenkner, *Zeit anwg Ghent,* 1905, 45, 166
[2] See Miolati and Tagiuri, *Gazz* , 1900, 30, 11, 511
[3] Gutbier, Falco and Vogt, *Zeit ancrg Che* 1921, **115,** 225
[4] Howe, *J Amer Chem Soc* , 1901, 23, 775 1904, 26, 543
[5] Gutbier and Zwicker, *Ber,* 1907, 40, 690, *J pr Chem* , 1915, [2], 91, 103, Krauss, *Zeit anorg Chem* , 1921,**117,** 111
[6] Antony and Lucchesi, *Gazz* , 1899, 29, 11, 82

action of **hydrochloric** acid on the tetroxide in presence of an alkali chloride (Howe)

Kuthenmm forms also a tnbromide and a tn-iodide, and yields series of rutheniobromides and ruthembromides which closely resemble the chlorine derivatives [1]

A ruthenium trichloride and tetrachloride and double salts of these with alkah chlorides were described by Claus, but later investigation [2] has shown that these all contain nitrogen, and are in i eahty nitroso-denvatives

Ruthenium Sulphide, Ru_2S_3—This compound occurs as the mineral laurite, which is found with platinum ore in Borneo and Oregon, and usually contains a small percentage of osmium It crystallises in small octahedra, generally showing also cube faces Sulphuretted hydrogen gives a precipitate with solutions of ruthenium salts, which consists of a varying mixture of sulphides and oxysulphides of ruthenium with free sulphur

According to Antony and Lucchesi [3] the precipitate produced in a solution of potassium ruthemchlonde, K_2RuCl_6, at 0° is a mixture of the *trisulphide,* RuS_3, and sulphur, whilst at 80° the *disulphide,* RuS_2, is formed These sulphides become incandescent or explode when gently heated in air

Ruthenium Sesquisulphite, $Ru_2(SO_3)_3$—When sulphur dioxide is slowly passed into a solution of rut heme sulphate, $Ru(SO_4)_2$, the colour changes from bright red through green to blue Alcohol added to this blue solution produces a blue precipitate of the colloidal sulphite, which may be dried at 80° It dissolves in water and is precipitated by salts [4]

Crystalline double salts with the alkali sulphites have been prepared [5]

Ruthenium Dithionate, RuS_{206}, is obtained by the continued action of sulphur dioxide on a solution of ruthemc sulphate as a yellow, crystalline, fibrous mass readily soluble in water [6]

Ruthemc Sulphate, $Ru(SO_4)_2$, is obtained by dissolving the precipitated sulphide in nitric acid, or the tetrahydroxide in

sulphuric acid, the reddish-yellow solution leaves on evapora-

[1] Gutbie and Trenkner, *Zed anorg Chem* , 1905, 45, 178, Howe, *J Amer Chem Soc* , 1904, 26, 942

[2] Joly, *Compt rend,* 1888, **107,** 994, Howe, *Amer Chem J,* 1894, 16, 388

[3] *Gazz* , 1900, 30, n, 539

[4] Antony and Lucchesi, *Gazz* , 1900, 30, n, 71

[5] Remy, *Zeit anorg Chem* , 1922, **124,** 248 See also Sailer, *ibid* , 1921, **116,** 209 [6] Antony and Lucchesi, *Gazz* , 1898, 28, n, 139

tion a yellowish-brown, amorphous mass, which yields a deliquescent powder clo^y resembling mosaic gold

Ruthenium and Nitrogen —When brown ruthenium sesquioxide is dissolved in nitric acid it forms a red nitrate, the latter on boiling with successive quantities of hydrochloric acid and evaporation at 120° yields a red, crystalline mass of *ruthenium nitrosochlonde,* $KuCl_3NO,H_{20}$, on recrystalhsation from hot water this forms dichroic trichmc prisms having the composition $RuCl_3NO,5II_{20}$, which rapidly effloresce in dry air. It may also be prepared by the action of aqua regia on the tetroxide * This substance combines with alkali chlorides, forming double salts, identical with the substances formerly supposed to be double salts of ruthenium trichloride and the alkali chlorides[2] The potassium salt has the composition $K_2[RuCl_5(NO)]$, and is a violet-brown, iridescent powder consisting of orange-red, microscopic cubes In aqueous solution, it yields the ions 2K and $[RuCl_5(NO)]^{//}$, and it is dissociated to about the same extent as potassium platinichloride[3] Many other similar double salts have also been prepared

The complex nitroso-denvatives have been investigated by Bnzard [4]

AMMONIACAL DERIVATIVES OF RUTHENIUM

608 Ruthenium forms a number of derivatives, the basic radicle of which contains both ruthenium and ammonia These were first examined by Claus, who described a series of salts derived from the hydroxide, $Ru(NH_3)_4(OH)_2$, and also obtained a hydroxide to which he assigned the composition $Ru(NH_3)_2(OH)_2$ According to Joly,[5] however, the salts containing four molecules of ammonia also contain the nitroso-group, and have the general formula $Ru(NH_3)_4(NO)(OH)X_2$, where X is a halogen or monovalent acid radicle, whilst the hydroxide containing two molecules of ammonia is $Ru(NH_3)NO(OH)_3,H_{20}$ The salts of the first-named series are well crystallised substances usually of a golden-yellow colour, no crystalline salts have been prepared from the second hydroxide This has been confirmed by Werner,[6]

[1] Howe, *J Amer Chem Soc* , 1894,16, 388
[2] Joly, *Compt rend* , 1888,**107,** 994, 1889,**108,** 1300
[3] Luid, *J Amer Chem Soc* , 1903, **25,** 928
[4] *Compt rend* , 1899,**129,** 216, *Ann Chim Phys* , 1900, [7], **21,** 311
[5] *Compt rend,* 1889, **108,** 1300, 1890, **111,** 969, 1893, **115,** 1299, Howe, *J Amer Chem Soc* , 1894,16, 388
[6] *Ber,* 1907, 40, 2614

who regards these compounds as *hydroxynitrosotetrammine-ruthemum salts,* $[Ru(OH)(NO)(NH_3)_4]X_2$, derived from tetravalent ruthenium, and has prepared series of salts in which the hydroxyl group of the complex radicle is replaced by chlorine, bromine, or water, of formula $[Ru(H_{20})(NO)(NH_3)_4]X_3$

RUTHENIUM AND CARBON AND SILICON

609 *Ruthenium Carbonyl,* $Ru(CO)_2$, is obtained as a chocolate-brown powder by the action of carbon monoxide on finely divided ruthenium at 300° under a pressure of 400 atmospheres, and is extracted from the residue by solution in alcohol Unlike all other metallic carbonyls, it is not volatile, is soluble in water and is completely insoluble in benzene It decomposes on heating, metallic ruthenium being formed[1]

A volatile, crystalline compound, soluble in benzene, and insoluble in water or alcohol is produced at the same time as the dicarbonyl Its composition has not yet been determined

Rutheniocyantdes —These compounds correspond to the ferrocyanides The *potassium* salt, $K_4[RuCy_6],3H_2$, is obtained by heating potassium ruthenio-nitrosochlonde with potassium cyanide, and forms colourless crystals isomorphous with those of potassium ferrocyanide Its solution is turned a dark violet colour by feme salts, and yields a pale green precipitate changing to violet with ferrous salts, whilst the salts of mercury, lead, and zinc yield white precipitates of the corresponding ruthemocyanides[2] The free *rutheniocyanic acid,* H_4RuCy_6, prepared from the potassium salt by adding hydrochloric acid and extracting with ether, crystallises in pearly laminae readily soluble in water or alcohol The solution has an acid reaction and an astungent taste, and on exposure to air turns blue (Claus)

Ruthenium Sihcide, RuSi, is formed in small, white crystals when the elements are heated together in the electric furnace It has the specific gravity 5 40, and is very hard It is not attacked by boiling acids, but is decomposed by the halogens; it burns in oxygen, and yields a per-ruthenate when fused with potassium? hydrogen sulphate and potassium nitrate[3]

[1] Mond, *Rep British Assoc* , **1915, 393,** *J Chem Soc*, **1910, 97,** 798, Mond and Walhs, *Journ Chem Soc* , **1921,121, 29**

[2] See Howe, *J Amer Chem Soc*, **1896, 18, 981**, Howe and Campbell, *ifod* , **1898, 20, 29**

[3] **Moissan and** Manchot, *Compt rend* , **1903,**137, **229**

DETECTION AND ESTIMATION OF RUTHENIUM.

610 The ruthenic salts give a dark red precipitate with concentrated solutions of potassium chloride and ammonium chloride, on boiling with water the characteristic ruthenium oxychlonde is formed Ruthenium solutions are first coloured blue by sulphuretted hydrogen, and afterwards the brown sulphide is formed, almost insoluble in ammonium sulphide The production of the volatile tetroxide is also characteristic

Ruthenium, like the other members of this group, is estimated quantitatively as the metal

Atomic Weight of Ruthenium —Claus [1] first determined this constant, but the later investigations of Joly[2] with carefully purified material have shown that the figures of Claus are too high Joly determined the atomic weight (1) by reducing the dioxide in hydrogen, (2) by the reduction of the nitroso-chlonde in hydrogen, (3) by the reduction of ammonium nitroso-chlororuthenate, the numbers obtained being respectively 101 67, 101 74, and 101 62, and the atomic weight is therefore at present (1922) taken as 101 7

RHODIUM Rh=102 9 At No 45

611 When Wollaston [3] in 1804 first acknowledged that he was the discoverer of palladium (p]407), he likewise intimated that he had found another new metal in platinum ore, to which he gave the name of rhodium, because the solutions of its salt possess a rose-red colour *(poSov,* a rose) The metal and its compounds were later investigated by Berzehus and Claus In addition to its occurrence in platinum ore, rhodium had been found, according to Del Rio, alloyed with gold as rhodium-gold

In order to prepare rhodium from the mixed platinum metals, the solution is employed from which ammomum platimchlonde has been precipitated The metals still in solution are then precipitated by metallic iron, and, according to the process of Deville and Debray, the metallic precipitate is fused with one part of lead and two parts of litharge A regulus is thus obtained, from which the lead, copper, and palladium may be

[1] *Petersb Akad Bull,* 3, 353 [2] Joly, *Compt rend,* 1889, **108,** 946
[3] *Phil Trans* , 1904, 94, 419

dissolved out by the action of dilute nitric acid The insoluble metallic powder is then well mixed with five parts of barium peroxide and heated to redness for two hours, the solid mass being lixiviated with water, and the residue boiled with aqua regia in order to volatilise the osmium tetroxide, this latter being condensed The excess of barium is precipitated from the solution by sulphuric acid, the filtrate evaporated at 100° with an excess of ammonium chloride, and the residue washed with a solution of the same salt as long as the wash-water has a rose-red colour The filtrate is then evaporated with an excess of nitric acid in order to decompose the ammonium chloride, and the residual mass heated to redness with from three to four parts of sulphur It is then rapidly boiled out with aqua regia and sulphuric acid, and by this treatment nearly pure rhodium remains behind In order further to purify this, it is fused with from three to four parts of zinc, and the alloy treated with strong hydrochloric acid, when the compound $RhZn_2$ remains behind This is dissolved in aqua regia and evaporated with an excess of ammonia Rhodammomum chloride, $Rh(NH_3)_5Cl_3$, separates out, and this is then purified from traces of indium by recrystalhsation, and lgnited in a carbon crucible with some sulphur, and, lastly, in order to remove from it any traces of silicon and osmium, fused in the oxy-hydrogen or electric furnace

Another method of preparing the pure metal is that described by Bunsen,[1] for the particulars of which his memoir on the subject must be consulted He obtained from one kilogram of the platinum residues from the St Petersburg mint 33 2 grams of pure rhodium sodium sulphate, $Na_3Rh(SO_4)_3$

Cominercial rhodium frequently contains iridium If, however, the metals are converted into the chloropentammine chlorides, the rhodium salt may be obtained quite free from iridium by treating the mixture with nitric acid, filtering off the chloropentamminerhodium nitrate which crystallises out, and reconverting this into the chloride, which then yields ihodium quite free from indium[2]

Rhodium can also be obtained free from indium when the latter is'present as an iridic salt such as $Ir(SO_4)_2$, by precipitating the mixed salts with caustic potash, dissolving the

[1] *Phil Mag* , 1868, [4], 36, 253

[2] Jorgensen, *Zeit anorg Chem*, 1903, 34, 82 See also Mylius and Dietz, *Ber*, 1898, 31, 3187, Leidie, *Compt rend*, 1900, **131,** 888, **Leidie" and** Quennessen, *Bull Soc chim*, **1901, [3], 25, 840**

hydroxides in **dilute sulphuric acid, and adding ewaium** sulphate The sparingly soluble rhodium **caesium alum separates in** the cold, and can readily be purified by recrystallisation and then decomposed electrolytically*

Properties—Rhodium possesses the colour **and** lustre of aluminium, and has a specific gravity of 12 1. It fuses with greater difficulty than platinum, its melting point being 1907° It is less volatile than platinum,[2] and, unlike indium, reduces the volatility of this metal when alloyed with it Such alloys are therefore preferable for the manufacture of crucibles [3] When the metal is heated in air or in oxygen, the sesquioxide is formed, but decomposes again at temperatures above 1150°[4] The molten metal " spits " on cooling, the surface becoming coloured blue from oxidation, it can be distilled in the electric furnace [5]

Pure rhodium, as well as that which contains gold and platinum, is almost insoluble in acids If, however, it be alloyed with bismuth, zinc, lead, or copper, it dissolves in aqua regia Alloys of much platinum and little rhodium also dissolve in aqua regia, but if the rhodium be present in larger quantity much remains undissolved Rhodium can, however be brought into solution by repeated ignition with fused potassium hydrogen sulphate, as well as with phosphoric acid or acid phosphates Of all the platinum metals, rhodium is the most easily attacked by chlorine [6]

Rhodium BlacL —When a solution of one of its salts is heated with sodium formate, the metal is precipitated in the form of a fine black powder It evolves considerable quantities of carbon dioxide, hydrogen, and oxygen, together with other gases and water when heated *%n vacuo* [7] It is an active catalyst, and brings about the umon of hydrogen and oxygen in a similar manner to platinum black[8] It possesses the property of decomposing formic acid, with evolution of heat, into hydrogen and carbon dioxide After a time the action becomes weaker, but the powder then simply requires to be washed with water and dried

[1] Piccim and Marino, *Zeit anorg Chem* , 1901, 27, 62
[2] Crookes, *Proc Boy Soc* , 1912, 86, 461
[3] Burgess and Sale, *J Ind Eng Chem* , 1914, 6, 452, 1915, 7, 516, Burgess and Waltenburg, *tbtd*, 1916, 8, 487
[4] Gutbier, Huttlinger, and Maisch, *Zeit anorg Chem* , 1910, 86, 225
[5] Moissan, *Compt rend*, 1906,**142,** 189
[6] Gutbier and Huttlmger, *Zeit anorg Chem* , 1916, 85, 247
[7] Sieverfcs and Jurisoh, *Ber*, 1912, 45, 221
[8] Quennessen, *Compt rend*, 1904, **138,** 795, *Bull Soc chim*, 1905, *[3]* 33, 101

in the air to be again rendered active [1] At a somewhat higher temperature, and in presence of caustic potash, it also decomposes alcohol, with evolution of hydrogen and formation of potassium acetate, it does not lose this power at a temperature at which "lass begins to soften (Deville and Debray)

Colloidal Rhodium — An unstable, colloidal solution of rhodium can be obtained by Bredig's method,[2] which consists in sparking between electrodes of rhodium under water, or by reducing the pure chloride with hydrazine hydrate In presence of gum arable, the solution can be evaporated over sulphuric acid, and yields a dark brown residue which contains 99 4 per cent of rhodium and is almost completely soluble in warm water[3] Other protective colloids, such as sodium protalbate or lysalbate, may also be employed,[4] and the best method of preparing the colloid consists in reducing sodium rhodochlonde by formaldehyde in the presence of one of these [5] Colloidal rhodium absorbs hydrogen to the extent of more than 2,500 times the volume of rhodium present, and carbon monoxide to the extent of 350 times its volume at ordinary temperatures and 1,800 times at 60° It causes a slight union of nitrogen and hydrogen to form ammonia,[5] and decomposes hydrogen peroxide, the reaction being unimolecular as in the case of platinum [6]

Alloys —Rhodium combines with tin, yielding the alloy $RhSn_3$, which forms small, brilliant crystals [7] It forms also a bismuth compound, $RhBi_4$, which crystallises in needles and is completely soluble in aqua regia, [8] it appears to form a compound with gold, but not with silver The alloy with platinum containing 10 per cent of rhodium is largely used in the form of wire in the construction of thermo-electnc pyrometeis

Crucibles and other forms of chemical apparatus are now made of malleable rhodium, and it is essential to use the perfectly pure metal for their preparation (Matthey)

[1] Blackadder, *Zext physikal Chem* , 1912, **81,** 385
[2] Lancien, *Compt rend,* 1911, **153,** 1088
[3] Outbier and Hofraeier, *J pr Chem* , 1905, [2], **71,** 452
[4] Paal and Amberger, *Ber,* 1904, **37,** 124
[5] Zei^ghelis and Papaconstantinou, *Compt rend,* 1920, **170,** 1058
[6] ***Ibtd,*** **1920,170,1178**
[7] Debray, *tbid,* 1887,**104,** 1470
[8] Rossier, *Chem Zett,* 1900,24 7*3

RHODIUM COMPOUNDS

RHODIUM AND OXYGEN

612 Rhodium forms three oxides, RhO, $Rh_?O_3$, and RhO_2

Rhodium Monoxide, RhO, is obtained by heating the tn-hydroxide, $Rh(OH)_3$, by the cupellation of an alloy of rhodium and lead, or by igniting the finely divided metal in a current of air It is a grey, metallic powder, unatta^ked by acids, when heated in hydrogen it is reduced with evolution of light

Rhodium Sesqmoxide, Rh_{203}, is obtained a.[c] a grey, iridescent, spongy mass by heating the nitrate It is also formed as a crystalline mass when sodium rhodochlonde is heated in oxygen It is insoluble in acids

Rhodium Trihydroxide, $Rh(OH)_3$, is a black, gelatmous precipitate, obtained by heating a solution of odium rhodochlonde with excess of caustic potash On drying it forms a heavy, dark brown mass having a conchoidal fracture and a metallic lustre It is scarcely attacked by acids

If a solution of the sodium double chloride be treated in the cold with potash not in excess, it becomes opaque, and on long standing deposits thin, lemon-yellow crystals of the hydioxide, $Rh(OH)_3,H_{20}$, which dissolve readily in acids, and, when moist, in caustic potash When chlorine is parsed into the solution of the yellow hydroxide in caustic pot<ish, a blue coloration is produced [x] which is probably due to the formation of a per-rhodate, Na_2RhO_4

The rhodium salts are derived from the sesqmoxide They possess either a dark red or a yellow colour, and have a bitter but not astringent taste

Rhodium Dioxide, RhO_2, is obtained by repeated fusion of the metal with caustic potash and saltpetre The sesqmoxide is first formed, and is further oxidised It closely resembles the sesqmoxide, it is not attacked by alkalis O1 acids, and is reduced by hydrogen only at a high temperature

Rhodium Tetrahydroxide, $Rh(OH)_4$- When chlonneois passed into the alkaline solution of the sesquihydroxide for a long time, and caustic potash occasionally added, this compound separates out as a green powder, the liquid becoming blue or violet The green powder dissolves in hydrochloric acid to a

[1] See Alvarez, *Compt rend,* 1905, **140,** 1341,

blue solution, this colour gradually changes to dark red, chlorine beirg evolved. The violet-blue solution probably contains the potassium salt of a rhodous acid, which latter separates out after some time as a blue powder, gas being simultaneously evolved On drying, it is converted into the tetrahydroxide

Insoluble crystalline salts of the composition $K_{20},6RhO_2$, $Na_{20},8RhO_2$, and $BaO,12RhO_2$ aie obtained when the corresponding double nitrites are heated in *vacuo* and the products tr3ated with water These substances may be regarded as *rhodites,* analogous to the manganites, cobaHites, and chromites [x]

613 *Rhodium Trichlomle,* $RhCl_3$, is obtained by the continued lgiition of the finely divided metal in chlorine, and also by heating one of the alkali double salts with sulphuric aud and pouring the cooled mixture into water, a rose-red powder of insoluble rhodium chloride remains behind It may be convienently prepared from the crude double chloride, $RhCl_3,3NaCl$, obtaii ed by the action of chlorine on the metal in presence of sodium chloride, by dissolving it in water, precipitating the sodium chloride by hydrochloric acid, evaporating, and heating the residue in a current of chlorine or hydrogen chloride It then forms a brown powder, insoluble in water or acids, but soluble in ilkahs and in potassium cyanide [2] It is obtained also as a briek-ied powder by heating the rhodium tin alloy, $RhSn_3$, in chlorine at 440°, the tin volatilising as stanmc chloride When the yellow hydroxide is dissolved in hydrochloric acid, a vellow solution is obtained possessing an astringent taste, which on concentration becomes rose red, and then possesses the peculiar bitter taste characteristic of all rhodium salts When this solution is evaporated, a daik red, amorphous mass of the hydrated chloride is obtained, which is deliquescent, and on further heating yields the insoluble anhydrous chloride

The tuchlonde yields a large number of well-crystallised *rhodochlondes* or *ehlororhodites* The *sodium* salt, $Na_3RhCl_6,9H_{20}$, crystallises in deep cherry-red, tnchnic prisms, which are very soluble in water, and effloresce in the air to a peach-blossom coloured powder The *ammonium* salt, $2(NH_4)_3RhCl_6,3H_{20}$, forma four-sided, rhombic prisms

The dark salt formed with potassium chloride has the formula $2KCl,RhCl_3$ or K_2RhCl_5 It crystallises in dark red, acicular prisms which contain $1H_{20}$, according to Berzehus, but accord-

[1] Leidri, *Compt rend,* 1899,**129,** 1249
[2] Joly and Leidie, *ibid,* 1898, 27, 103

mg to Leidie are anhydrous Another hydrate, $K_2RhCl_6,3H_{20}$, crystallising in dark red jgisms has been described by Clans.

Rhodium Monosulphide, RhS—When rhodium is heated in sulphur vapour it takes fire with formation of the sulphide, which is produced also when sulphuretted hydrogen is passed through a solution of a rhodium salt, and the washed precipitate dried by ignition in a current of carbon dioxide Thus obtained, it forms a bluish-white, fused mass of metallic lustre, heated in the air it leaves a residue of spongy rhodium

Rhodium Sesquisulphide, Rh_2S_3, is obtained in the pure state by heating the trichloride in sulphuretted hydrogen at 36O°, and forms blackish, crystalline plates The *hydrosulphide,* $Rh(SH)_3$, is precipitated when sulphuretted hydrogen in large excess is passed into a solution of a rhodium salt at 100°, and forms a brownish-black precipitate which is insoluble in ammonium sulphide [x]

Rhodium Sulphite, $Rh_2(SO_a)_3,6H_{20}$, is obtained by dissolving the yellow hydroxide in sulphurous acid and evaporating It is a pale yellow, indistinctly crystalline mass, and forms crystalline double salts

Rhodium Sulphate, $Rh_2(SO_4)_3,12H_{20}$, is obtained by dissolving the yellow hydroxide in sulphuric acid, evaporating, and washing away the excess of acid bv alcohol It is a yellow, crystalline mass which possesses a sour, astringent taste The anhydrous salt is a brick-red, non-hygroscopic powder (Leidie) According to Claus, it forms crystalline double salts with the alkali sulphates, but Leidie was unable to confirm this statement

A series of *rhodium alums* of the alkali metals, ammomum, and thallium has been prepared by dissolving the yellow hydroxide in excess of dilute sulphuric acid and adding two-thirds of the calculated amount of the alkali sulphate [2] *Rhodium ccesium alum,* $Cs_2SO_4,Rh_2(SO_4)_3,24H_{20}$, forms yellow octahedra, melts at 110—111°, and is sparingly soluble in cold water The potassium compound, on the other hand, is extremely soluble

in water, the rubidium and ammomum salts being intermediate in solubility

Rhodium Nitrite, $Rh(NO_2)_3$, has not been isolated, but forms characteristic double salts *Sodium rhodium nitrite,* $3NaNO_2,Rh(NO_2)_3$, separates in bulky, white crystals, which act on polarised light The *potassium* salt also forms white,

[1] **Leidie,** ***Compt rend,*** **1888,106, 1533**
[2] **Piccini and Marino,** ***Zeit anorg Chem*** **, 1901, 27, 62**

microscopic crystals when pure,[1] but is usually obtained as a heavy, orange-coloured, crystalline powder, which dissolves readily in hydrochloric acid

Rhodium Nitrate, $Rh(NO_3)_3$, does not crystallise, but forms a dark yellow, hygroscopic, gummy mass

Potassium Rhodicyanide, $K_3[RhCy_6]$, is obtained in a similar way to the corresponding indium salt (p 1447), which it closely resembles It may also be prepared by dissolving the yellow hydroxide in caustic potash, diluting, and adding to an excess of hydrocyanic acid[2] It is distinguished from the indium salt, inasmuch as acetic acid produces a pale cnmson-red precipitate of *ihodium cyanide*, $RhCy_3$, soluble in the cyanides of the alkali metals, forming the rhodicyanides (Martins).

AMMONIACAL DERIVATIVES OF RHODIUM

614 The ammoniacal rhodium bases and salts closely lesemble the corresponding cobalt compounds The three chief series have the following general formulae

Hexammine salts (Luteo-salts) $[Rh(NH_3)_6]X_3$
Aquopentaminme salts (Roseo-salts) $[Rh(H_{20})(NH_3)_5]X_3$
Pentammine salts (Purpureo-salts) $[RhX(NH_3)_5]X_2$

in which X is a monovalent negative radicle

Hexammine-Rhodium Trichloride (Luteorhodium Chloride), $[Rh(NH_3)_6]Cl_3$, is obtained in colourless, lustrous crystals by heating the salt next described with ammonia

Chlwopentammine-Rhodium Dichloride (Chloropurpureorhodmm Chloride), $[RhCl(NH_3)_5]Cl_2$, is prepared by dissolving the alloy of rhodium and zinc in aqua regia and adding ammonia It forms small, yellowish, lustrous, rhombic crystals

Aquopentammine-Rhodium Chloride (Roseorhodwm Chloride), $[Rh(H_{20})(NH_3)_5]Cl_3,H_{20}$, is obtained by digesting the foregoing compound with silver oxide for several days, and dissolving the resulting base in hydrochloric acid

Optically Active Rhodium Ammine Salts—There is considerable similarity between rhodium and cobalt salts The trietBylenediamine cobalt salts form optical isomerides, and Werner has succeeded in obtaining the optical isomerides of triethylenediaminerhodium salts[3]

[1] LeidiS, *Compt rend*, 1890, **111,** 106 [2] *Ibid*, 1900,**180,** 87
[3] *Ber*, 1912, 45, 1228

DETECTION AND ESTIMATION OF RHODIUM

615 Solutions of this mftal are precipitated by sulphuretted hydrogen, slowly in the cold, but more quickly when warmed The brown sulphide is insoluble in ammonium sulphide When a rhodium compound is heated in hydrogen the metal is obtained, this is insoluble in aqua regia, but can be obtained in solution when it is fused with acid potassium sulphate The fused mass on treatment with water yields a red solution, from which the metal is precipitated as a black powder on addition of caustic potash and alcohol It is also precipitated from acid solution by zinc and other metals

Rhodium is estimated quantitatively as the metal

Atomic Weight of Rhodium—Jorgensen,[1] from the analysis of chloropentamminerhodium dichloride and of the analogous dibromide, obtained the number 103 1, and Seubert and Hobbe,[2] by the same method, the number 102 94 This figure has been confirmed by the later work of Hutthnger,[3] \\ho found, as a mean of three determinations, the value 102 93, and Dittinar,[4] who, as a mean of seven experiments, obtained the figure 102 91 The value now adopted (1922) is 102 9

PALLADIUM Pd=io67 At No 46

616 In April, 1803, a printed notice came[5] into the hands of Chenevix, to the effect that a new metal, called Palladium, was to be sold at Forstei's, of Gerrard Street, Soho Chenevix,[6] believing that this was simply a fraud, bought the whole stock,

[1] *J pr Chem* , 1883, [2J, 27, 486

[2] *Annalen,* 1891, **260,** 314

[3] *Sitzungsber phys rned Soz Erlangen,* 1907, 39, 1

[4] *Ibid* , 1909, 40, 184

[5] " Palladium, or new silver, has these properties amongst others that show it to be a new noble metal —1 It dissolves in pure spirit of nitre, and makes a dark red solution 2 Green vitriol throws it down in the state of a regulus from this solution, as it always does gold from aqua rcgia 3 If you evaporate the solution you get a red calx that dissolves in spirit of salt or other acids 4 It is thrown down by quicksilver, and by all the metals but go]d, platinum, and silver 5 Its specific gravity by haminermg was only 113, but by flattening as much as 11 8 6 In a common fire the face of it tarnishes a little and turns blue, but comes bright again, like other noble metals, on bemg stronger heated 7 The greatest heat of a blacksmith's fire would hardly melt it 8 But if you touch it while hot with a small bit of sulphur, it runs as easily as zinc "

[6] *Phil Trans* , 1803, 03, 290

and after investigating the question he came to the conclusion that the substance was not a new metal, but that it was a platinum amalgam of peculiar properties. Soon after the communication of Chenevix's paper to the Koyal Society (May 13, 1803), an advertisement appeared in which a handsome reward was offered to any one who should prepare even a grain of this substance, either according to Chenevix's plan, or by any other method No one succeeded in obtaining the reward, although several German chemists endeavoured to prepare the new substance In 1804 Wollaston[1] declared that he was the discoverer of palladium, having taken this name from that of a new planet Pallas, discovered by 0lbers in 1802 At the same time he described the process which he adopted in order to obtam the new metal from platinum ore

Palladium occurs in a tolerably pure state with Brazilian platinum ore, as well as together with gold, at Tilkerode, in the Harz It is contained in most platinum ores, and is found in many places in South America alloyed with gold

Numerous methods of separating palladium from the other platinum metals have been described Among these may be mentioned the precipitation of the dicyanide by the addition of mercuric cyanide to a neutral solution of a palladium salt, and the treatment of the dichloride solution with potassium iodide, or freshly precipitated silver iodide,[2] which yields palladious iodide as a black, insoluble precipitate The cyanide is converted into the metal by ignition, and the iodide by heating in a current of hydrogen Bunsen,[3] by the iodide method, prepared pure palladium from the platinum residues of the St Petersburg mint, which consisted of a mixture of all the platinum metals Other methods of working up the platinum metals on the large scale have been given by Phihpp,[4] Guyard,[6] and Leidie[6] From the palladium-gold alloy it may be obtained by fusing the latter with silver, and treating the granulated metal with moderately dilute nitric acid, which dissolves the silver and palladium, but leaves the gold unattacked The silver is precipitated with sodium chloride, and the palladium from the filtrate by metallic zinc[7]

To prepare pure palladium from the cominercial metal, it is

[1] *Phil Trans* , **1804, 94, 428, 1805, 95, 316**
[2] **0rloff,** *Chem Zeit,* **1906, 30, 714** [3] *Phil Mag* , **1868, [4], 36, 253**
[4] *Dmgl Polyt Journ* , **1876, 220** 95 [5] *Compt rend* , **1863, 56, 1177**
[6] ***Ibid* , 1900,131, 888** [7] **Cock, *Phil Mag*, 1843, [3], 23, 16**

dissolved in aquajegia, and precipitated as the double ammonium chloride together wish platinum and other metals The precipitate is treated with excess of ammonia, when the palladium salt dissolves, and on addition of hydrochloric acid yields, after a time, a precipitate of yellow palladdiammonmm chloride This sometimes contains rhodammonmm chloride, which is separated by retreatment with ammonia and addition of hydrochloric acid The washed precipitate yields spongy palladium on ignition

Palladium has a colour closely resembling that of silver and platinum, a specific gravity of 11 4 at 22 5° (Deville and Debray), or 11 9 (Myhus and Dietz),[1] it melts at 1549°, the lowest melting point of all the platinum metals At the melting point of indium it boils violently, with partial oxidation, and emits green vapours, which condense to a brown sublimate consisting of a mixture of oxide and metal [2]

Palladium is dimorphous The native metal occurs in the Brazils in the form of sand or rounded grains, amongst which small, regular octahedra are sometimes found Native palladium usually contains small quantities of both platinum and iridium, and has a specific gravity varying from 113 to 11 8 The palladium found in the Harz occurs in small, hexagonal tablets, together with gold and lead selenide, and hence this latter body was first considered to be palladium selenide Owing to the difference of crystalline form this variety has been termed by Danna [3] *Allopalladium*

When palladium is heated to dark redness it assumes a violet or blue colour, but at higher temperatures it regains its metallic lustre, and this remains even when the metal is quickly cooled by plunging into water When heated in a current of oxygen till the weight is constant it forms the monoxide, PdO [4] Palladium dissolves readily in nitric acid, especially when this contains nitrous acid, or when the metal is alloyed with either copper or silver It also dissolves in hydrochloric acid if chlorine be passed into the liquid, and is attacked by boiling concentrated sulphuric acid, and by fused potassium bisulphate.

617 *Palladium and Hydrogen.*—Palladium is di&tingjushed for its remarkable power of absorbing or occluding hydrogen

[1] *Ber* , 1898, **31,** 3187
[2] See also Moissan, *Compt rend* , **1906,142, 189,**
[3] *Mineralogy,* 5 th ed p 12
[4] **Wilm, *Ber,* 1892, 25, 220, Wohler, *Zext Elektrochem* , 1905,11, 836**

This property was first discovered by Graham,[1] who observed that absorption of hydrogen occurred when the gas was passed over metallic palladium which had been heated to redness, or when the metal was employed as the negative electrode in the electrolysis of water He found that the metal absorbed about 900 times its own volume of hydrogen, termed the occluded gas *hydrogemum,* and thought it was present in the solid state The absorption or occlusion of hydrogen by palladium has since been the subject of many investigations Sieverts[2] found that the quantity of hydrogen absorbed is independent of the superficial area of the metal and concluded that the phenomenon is a case of simple solution At constant temperature, the amount absorbed is very nearly proportional to the square root of the pressure of the hydrogen With increase of temperature, the amount absorbed decreases rapidly to 600°, then slowly to 800°, and then only very slightly At the melting point, the molten metal absorbs less hydrogen than the solid, consequently there is no " spitting " when molten palladium solidifies in an atmosphere of hydrogen[2] The whole of the occluded gas can be removed by heating in *vacuo* even at 100°[3] The rate of occlusion of hydrogen falls off in proportion to the amount of gas already absorbed, and it is therefore probable that the process of occlusion is first simple adsorption on the surface layer, followed by slow diffusion into the interior of the metal from this layer[4] From the rate of cooling of palladium in hydrogen, Andrew and Holt[5] conclude that the metal exists in two allotropic modifications and the absorption of hydrogen may be regarded as taking place rapidly in the one form and more slowly in the other, thus accounting for the initial rapidity and subsequent slowness of the OCCIUSIOD[6]

The physical properties of palladium undergo considerable change through the absorption of hydrogen The specific gravity of palladium-hydrogen is less than that of the metal, hence expansion must occur in the formation of the compound This expansion can be shown in several ways One of the most striking is to fit two palladium wires honzontally through

[1] *P?ul Mag,* 1866, 32, 516, *Proc Roy Soc,* 1867, 15, 223, 1868, 16, **422,** 1869,17, 212, 500
[2] *Zeit physikal Chem* , 1914, 88, 103, **451**
[3] Mond, Ramsay, and Shields, *Proc Roy Soc* , 1897, 62, 290
[4] Holt, Edgar, and Firth, *Zeit physikal Chem* , **1913,** 82, **513**
[5] *Proc Roy Soc* , 1913, *[A],* 89, **170**
[6] **Holt,** *ibid* , **1914,** *[A*], **90,** 226, **Firth,** *Journ. Chem Soc* , **1920,117, 171.**

the edges of a thin electrolytic trough with parallel glass sides The trough is then fijjpd with acidulated water, and an image of the wires thrown on a screen. An electric current is now passed through the cell, when a singular bending of the palladium wire from which the hydrogen is evolved is noticed. If the current be reversed this wire first returns to its original horizontal position, and then bends to the opposite side, whilst the other wire is deflected in the former direction, the explanation of this double bending being that first one side, and then the other side of the wire becomes saturated with, or loses the hydrogen[x] If one side of a piece of palladium foil be saturated electrolytically with hydrogen, then washed and dried, and afterwards ignited, it becomes so bent that it has almost the appearance of having been rolled up into a coil

The electrical conductivity of palladium decreases with occlusion of hydrogen It first decreases proportionately to the amount of hydrogen absorbed up to 40 volumes, then asymptotically up to 600 volumes and then proportionately again This break in the rate of decrease of conductivity is attributed to the formation of a compound, PdH_2[2] The formation of another hydride, Pd_2H, had been assumed by other investigators[3] from a study of the pressure of the hydrogen evolved from hydrogenated palladium at different temperatures, but the existence of this compound has not been confirmed[4] The magnetic susceptibility of palladium is also decreased by the absorption of hydrogen[5]

The occluded hydrogen is chemically very active The product containing hydrogen often becomes heated on exposure to the air from absorption of oxygen and formation of water, and when palladium black has been employed this action may be sufficiently vigorous to render the powder pyrophonc (Paal and Amberger) Palladium foil charged with hydrogen acts as an excellent reducing agent, reducing ferric and eene salts, ferricyanides, and chromates, and may be employed for this purpose in quantitative analysis[6]

[1] Poggendorff, *Ber* , 1869, 2, 74 See also Dewar, *Phil Mag* , 1887, J4], 47, 334

[2] Wolf, *Zeit physikal Chem* , 1914, 87, 575

[3] Troost and Hautefeuille, *Compt rend* , 1874, 78, 686

[4] Hoitsema, *Zeit physikal Chem* , 1895,17, 1

[5] Biggs, *Phil Mag*, **1916,** [6], 82, **131**, **Oxley,** *Proc Roy Soc* , **1922,** [.4], **101, 264**

[6] **Chapman, *Analyst,* 1904,29, 346.**

The power of palladium to absorb hydrogen is diminished by certain substances, notably hydrogen sulphide and lead salts The question has been studied by Maxted, and the decrease in occlusive power is found to be approximately proportional to the amount of "poison" present[1] The occlusive power of palladium is greatly affected by alloying it with other metals Thus the solubility of hydrogen in palladium is increased by the presence of silver, although hydrogen is insoluble in silver The increase in solubility continues with increase in the amount of silver up to a maximum at 40% of silver, when the solubility at 138° is four times as great as in pure palladium Further increase of the silver content results in a decrease in solubility, and at 70% of silver the solubility is reduced to zero Addition of gold, in the same way, causes "first an increase and then a decrease in the occlusive power, but the effect is not so marked Platinum, on the other hand, decreases the solubility when alloyed with palladium in any proportions Unlike the other cases, the solubility here mcieases with rise of temperature With all the alloys the solubility is proportional to the square root of the pressure of the hydrogen, as in the case of pure palladium[2]

Palladium also occludes other gases, notably carbon dioxide[3]

Hydrogen readily diffuses through palladium, the metal exhibiting this property, also, in a very much more marked degree than platinum or iron The rate of diffusion is approximately proportional to the pressure of the gas[4] The diffusion of hydrogen is selective, for example, pure hydrogen diffuses through the metal from ordinary coal gas[5] Hydrogen which has been ionised by X-rays or radium does not diffuse through palladium[6]

Spongy Palladium—On heating ammomum palladiochlonde decomposes, ammomum chloride being evolved and the palladium left in a spongy form In this condition the metal is more active It dissolves in hydrochloric acid in presence of air and absorbs hydrogen very readily The arrangement shown in Fig 201 is that proposed by Wohler[7] for exhibiting the de-

[1] Maxted, *Journ Chem Soc* , 1919, **115,** 1050, 1920,**117,** 1280,1601, 1921, 119,1881

[2] Sieverts, Jurisch, and Metz, *Zett anorg Chem*, 1915,92, 329, Tammann, *Zett anorg Chem* , 1920, **111,** 90

[3] Harbeok and Lunge, i*bid*, 1898,16, 50

[4] Holt, *Proc Boy Soc* , 1915, *[A],* 91, 148

[5] Graham, *he cit* , Ramsay, *Phil Mag* , 1894,**88,** 206

[6] Sieverts, *Zett physikal Chem*, 1914, **88,** 103

[7] *Annalen,* 1876,**184,**128

composition of palladium-hydrogen by heat and the reabsorption of the hydrogen on cooling The U-tube *(a)* dipping in boiling water contains the spongy palladium, over which a current of hydrogen is passed for half an hour from the cylindrical generator on the right of the figure The water-bath is then removed, and the tube allowed to cool in the current of hydrogen The stop-cock *(d)* is now shut, and the tube *(a)* placed in commumcation with the tube *(b)* This latter dips in the cylinder and is bent up at the lower end into the tube (c) The tube *(a)* is next heated with a flame, when the cylinder soon becomes filled with hydrogen, and on allowing the spongy metal to cool, a rapid absorption of

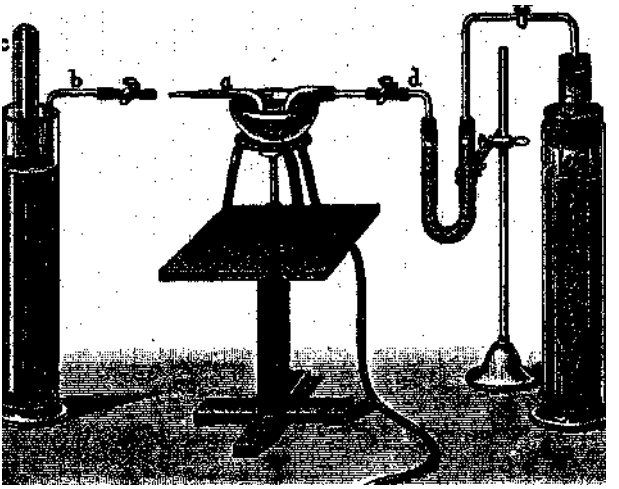

the hydrogen occurs The experiments can be repeated as often as desired

The absorption of hydrogen is a minimum at 20° It increases with rise and also with decrease of temperature,[1] becoming very great at the temperature of liquid air, when it may be used for lemoving the last traces of hydrogen from other gases [2]

Palladium Black is obtained, similarly to platinum black, by reduction of palladium salts with soldium formate Owing to its affinity for oxygen, it contains some palladious oxide [3] It absorbs hydrogen very readily, but on heating the occlusive power is diminished The black is regarded as a mixture of

[1] Gutbier, Gebhardt, and Ottenstein, *Ber* , 1913, 46, 1453
[2] Valenfcmer, *Ber Dent physical Ges*, 1911,13, 1003
[3] Mond, Ramsay, uid Shields, *Proc Roy Soc* , 1897, 62, 50

amorphous and crystalline palladium, and on heating the amorphous is converted into the crystalline variety, in which hydrogen is less soluble All forms of palladium have the same capacity for absorbing hydrogen above 600° The absorption is probably a case of simple adsorption in the amorphous metal, but of true solution in the crystalline variety Palladium black is gradually converted into palladium sponge by heat[1]

Palladium in all its forms acts as a catalyst in many reactions [2] When warm palladium foil is brought into an electrolytic mixture of hydrogen and oxygen, or other explosive gaseous mixture, combination takes place without explosion (CoquiUon),[3] and when the metal is brought into the flame of alcohol or coal gas it becomes covered with a thick film of soot When palladium sponge is placed in a current of ethylene, this gas is decomposed with separation of carbon, this occurs at a temperature at which the gas alone does not undergo any alteration [4]

In the presence of the finely divided metal at moderate temperatures, hydrocarbons mixed with air are completely burnt to carbon dioxide and water Sodium hypophosphite solution is readily oxidised first to the phosphite and then, more slowly, to the phosphate, with evolution of hydrogen [5]

Colloidal Palladium—A colloidal solution of palladium can be prepared by the electrical method,[6] by the action of formaldehyde, hydrazine hydrate,[7] or carbon monoxide [8] on palladious chloride, and by the action of hydrazine hydrate or gaseous hydrogen on a palladium salt in presence of sodium protalbate [9] The last preparation can be obtained by evaporation as a solid hydrosol, which absorbs hydrogen It dissolves readily in water yielding the colloidal solution again

Colloidal palladium is an exceptionally active catalyst Like

[1] Sieverts, *Zeit physikal Ghent*, 1914, **88,** 103, Firth, *Journ Chem Soc* , 1921,119, 1120

[2] Lunge and Akunoff, *Zeit anorg Chem* , 1900,24, 191, Zelinsky, *Ber* , 1898, 31,3203

[3] *Compt rend* , 1876, **88,** 709 See also Tammann, *Zeit anorg Chem* , 1920, **111,** 90

[4] Wohlor, *Annales* 1876,**184,** 128

[5] Sieverts and Peters, *Zeit physikal Chem*, 1916, 91, 199

[6] Bredig and Fortner, *Ber* , 1904,37, 798

[7] Gutbier, *Zeit anorg Chem*, 1902, 32, 347, Gutbier and Hofmeier, *J pr Chem* , 1905, [2], 71. 358

[8] Donau, *MonaUh* , 1906, 27, 71

[9] Paal and Amberger, *Ber*, 1904, 37, 124, 1905, 38, 1398, Amberger, *KolloidZeit* 1913,13,310

platinum, it decomposes hydrogen peroxide and catalyses reductions by hydrogdli,[1] in most cases to a more marked degree. Nitrobenzene is readily reduced to aniline,[2] unsaturated compounds are readily saturated, partially or wholly, and many oils may be " hardened " as when nickel is used as catalyst This activity is doubtless connected with the power of the colloid to absorb hydrogen It also absorbs acetylene to a most remarkable degree, about 5000 volumes of this gas being dissolved, doubtless owing to the formation of condensation and polymerisation compounds [3]

The colloid is readily poisoned by many substances, notably hydrogen sulphide, hydrogen cyanide, hydrogen arsenide, and mercuric salts It readily converts mercury and mercuric oxide into colloidal solution, and thus loses its activity, probably owing to the formation of a colloidal amalgam[4] Mercury, in fact, decomposes palladium-hydrogen hydrosols with evolution of hydrogen[5] The catalytic activity of palladium hydrosols first increases with age, reaches a maximum, and then decreases again [6]

Palladium is now employed in preference to platinum in dentistry for the production of artificial teeth, and also in jewellery, particularly for the setting of stones On account of its unalterabihty in the air, and owing to its bright silver-white colour, it has been employed for the preparation of graduated surfaces for astronomical instruments It is likewise used for coating silver goods, as palladium does not lose its fine white colour on exposure to sulphuretted hydrogen, and hence it has been much employed by dentists as a substitute for gold also Spongy palladium is used in gas analysis to absorb hydrogen

Palladium alloys with gold,[7] silver,[7] copper,[7] and nickel[8] in all proportions no compounds being formed It also alloys with lead, forming a series of compounds [9] The alloys with gold

[1] Kelber and Schwarz, *Ber,* 1912, 45, 1946, Boeseken, van der Weide, and Mom, *Bee trav chim,* 1916, 35, 260, Berti Ceroni, *Gazz,* 1916, 46, 11, 51, Niviere, *Bull Soc chim,* 1921, [4], 29,217, Sandonmni and Quaglia, *Qazz ,* 1922, 52, i, 409

[2] Paal and Amberger, *Ber ,* 1905, 38,1406

[3] Paal and Hohenegger, *Ber,* 1910, 43, 2684, 1915, 48, 275, Paal*and Schwarz, *ibid ,* 1915, 48, 1195

[4] Paal and Hartinann, *Ber,* 1918, 51, 711, 894

[5] Paal and Steyer, *ibid,* 1918, 51, 1743

[6] De Rocasolano, *Compt rend,* 1920,**171,** 301

[7] Ruer, *Zeit anorg Chem,,* 1906, 51, 223, 315

[8] Heinnch, *ibid ,* 1913, 83, 322

[9] Tammann, *ibid ,* 1921,**118,** 93

have a high melting point, and are so resistant to corrosion that they are, for many purposes, employed as a substitute for platinum, and are known as *Rhotamum*[1] Palladium also forms an amalgam which may be made by rubbing the finely divided metal with mercury

PALLADIUM COMPOUNDS

PALLADIUM AND OXYGEN

618 Three oxides of palladium are known the monoxide, PdO, the sesquioxide, which has only been obtained in the hydrated condition, Pd_2, xH_2, and the dioxide, PdO_2 A suboxide, Pd_2, has also been described,[2] but it is probable that this is in reality a mixture of the metal and the monoxide[3]

Palladium Monoxide, PdO, is formed by the long-continued heating of the spongy metal in a current of oxygen at temperatures rising from 700-840°, or by heating a mixture of a palladium salt with potassium carbonate Prepared in the first manner it is a bluish-green, and by the second an amber-coloured mass, which yields a black powder On strong ignition, it yields the metal, the dissociation pressure[4] being 760 mm at 877°, and it is reduced by hydrogen at the ordinary temperature with evolution of light and heat It acts as a powerful oxidising agent to orgamc substances, and is reduced to metal by hydrogen peroxide If a palladious salt be precipitated with sodium carbonate, a dark brown hydroxide, readily soluble in acids, is thrown down, whilst the anhydrous oxide dissolves only after long boiling When precipitated in the cold it is soluble in alkalis, but loses this property when dried or when prepared from a boiling solution The pure hydrated oxide is best prepared by the hydrolysis of the nitrate

The palladious salts, corresponding to this oxide, possess a green, red, or brown colour, and have an astringent, but not metallic, taste

Palladium Sesquioxide is obtained in the hydrated condition by tl\e electrolytic oxidation of palladious nitrate[5] It forms a brown precipitate which dissolves readily in hydrochloric acid,

[1] Fahrenwald, *J Ind Eng Chem* ,1917,9, 590, Gurevich and Wichers, *ibid* , 1919,**11,** 570

[2] Kane, *Phil Trans*, 1842,**132,** 276, Neumann, *Monatsh* , 1892,**13,**40

[3] Wohler and Komg, *Zeit anorg Chem* , 1905, 46, 323

[4] Wohler, *Zeit Elektrochem*, 1905,**11,** 836, 1906,**12,** 781

[5] Wohler and Martin, *Zeit anorg Chem* , 1908, 67, 398

forming an unstable chloride Palladium is thus brought more into line with its neignbojps rhodium and ruthenium

Palladium Dioxide is obtained in an impure hydrated form as a brown precipitate by the addition of caustic soda to potassium palladichloride This is soluble in acids, but becomes less soluble when preserved It can be obtained free from alkali and basic salts by the anodic oxidation of the nitrate, but is not quite free from monoxide The dioxide very readily decomposes into the monoxide and oxygen, and cannot be obtained in the anhydrous state It acts as a vigorous oxidising agent, and decomposes hydrogen peroxide (Wohler and Konig)

PALLADIUM SALTS

619 *Palladious Chloride,* $PdCl_2$, is obtained by heating palladious sulphide, PdS, in dry chlorine, when it is obtained partly as a rose-red sublimate and partly in the form of garnet-red crystals which dissolve slowly but completely in water It is prepared in solution by the simultaneous action of chlorine and hydrochloric acid on the metal On evaporation over caustic lime, brown-red crystals having the composition $PdCl_2,2H_{20}$ are deposited These lose water when gently heated, the anhydrous chloride remaining as a brownish-black mass which melts easily without decomposition, and is reduced by hydrogen in the cold At a red heat it fuses and loses half of its chlorine, forming the *monochloride,* PdCl, which, on cooling, solidifies to a reddish-brown, crystalline mass yielding a light red powder which is very deliquescent The aqueous solution partially decomposes with separation of basic salts, and the solution is reduced by hydrogen, carbon monoxide, and other gases[1] When heated, palladious chloride unites with carbon monoxide,[2] forming the crystalline compounds, $PdCl_2,2CO$, melting at 142°, $2PdCl_2,3CO$, melting at 132°, and $PdCl_2,CO$ These substances are analogous to the corresponding platinum compounds

Palladious chloride forms double chlorides with other chlorides, known as *palladiochlorides* or *chloropalladites*[3] A large number of these salts of organic bases have been prepared[4]

[1] Bottger, *J pr Chem* , 1859, 76, 233
[2] Fink, *Compt rend* , 1898,**126,** 646
[3] See Gutbier and Krell, *Ber* , 1905, 38, 2385
[4] Gutbier, *Ber,* 1905, 38, 2105, *Zeit anorg Chem,* 1905, 47, 23, Gutbier and Krell, *Ber,* 1905, 38, 3869, 1906, 39, 616, 1292, Gutbier and Woernle, *Ber,* 1906, 39, 2716, Gutbier, Fellmer, and others, *Zeit anorg Chem,* 1916, 95, 129

Potassium Palladiochlonde, K_2PdCl_4, is obtained by adding potassium chloride to a solution of palladious chloride It may also be prepared by ignition of potassium palladichloride It is easily soluble in water, less so in alcohol, and crystallises in four-sided prisms, exhibiting a red-green dichroism

Ammonium Palladiochlonde, $(NH_4)_2PdCl_4$, is obtained by evaporating a solution of palladium chloride with ammonium chloride It forms either bronze-yellow prisms exhibiting a play of different colours, or yellowish-green needles, and dissolves in water, forming a dark-red solution

Palladic Chloride, $PdCl_4$, is not known in the free state The brown solution obtained by dissolving the metal in concentrated aqua regia contains *palladichlonc* or *chloropalladic acid,* H_2PdCl_6, corresponding to chloroplatimc acid, this forms salts with the alkali metals and certain aromatic bases [1]

Potassium Palladichloride, K_2PdCl_e, is obtained by adding potassium chloride to a solution of the metal in an excess of aqua regia and gently evaporating It is also prepared by precipitating a solution of palladious chloride, saturated with chlorine, with an excess of potassium chloride, or by warming the palladiochlonde with potassium persulphate and hydrochloric acid [2] It forms cmnabar-red or brownish-red octahedra showing the faces of the cube These dissolve in hot dilute hydrochloric acid without decomposition, but are not soluble in water containing the chlorides of the alkali metals, or in alcohol

Ammonium Palladichloride $(NH_4)_2PdCl_6$, is a bright-red, crystalhne powder consisting of microscopic octahedra It is obtained by precipitating a solution of the chloride, saturated with chlorine, by ammonium chloride On treating the solution with an excess of ammonia a violent evolution of nitrogen takes place, ammonium palladiochlonde being formed

$$3(NH_4)_2PdCl_6 + 2NH_3 = 3(NH_4)_2PdCl_4 + 6HC1 + N_2$$

Palladious Bromide, $PdBr_2$, is obtained by treating the metal with bromine hydrate and nitric acid, and forms a chestnut-brown mass which dissolves in hydrobromic acid but not in water

Potassium palladwbromide, K_2PdBr_4, crystallises in lustrous, reddish-brown needles which are stable in the air Many analogous salts are known (Gutbier and Krell)

Palladic Bromide, $PdBr_4$, is not known, but the *palladi-*

[1] Mohlau, *Ber,* 1906, 39, 861
[2] Scagharini and Berti Ceroni, *Gazz ,* 1916, [2], 46, 51

***bromides* of the alkali metals, R_2PdBr_6, have been prepared by passing** bromine vapour into the solutions **of** the **corresponding** palladiobromides They are sparingly soluble salts which **are** decomposed by hot water and by ammonia (Gutbier and Krell).

PaUadiaus Iodide, PdI_2, is obtained by precipitating the chlonde with potassium iodide as a black, flocculent precipitate which, when dried in the air, forms a deliquescent mass exhibiting a conchoidal fracture It dissolves slowly in hydnodic acid and leadily in a solution of potassium iodide, imparting to this a wine-red colour When heated to 100° it begins to give off iodine, and it decomposes completely at temperatures between 330° and 360° The solution in potassium iodide yields on evaporation blackish-green, deliquescent cubes of *potassium palladioiodide,* K_2PdI_4

Palladium Subsulphide, Pd_2S, is obtained by fusing ammomum palladiochlonde with sodium carbonate, sulphur, and ammomum chlonde A green, molten mass is thus obtamed which crystallises on cooling and exhibits a metallic fracture It is only slowly attacked by aqua regia

Palladium Monosulphide, PdS, is formed with incandescence when the metal is heated in the vapour of sulphur It is a bluish-white, hard mass, which exhibits a laminated fracture and a metallic lustre, and oxidises only slowly in the air A black precipitate is formed by passing sulphuretted hydrogen through a solution of a palladious salt, this is generally supposed to be palladious sulphide, but it always contains more sulphui than is reqmred by the formula PdS^{x}

Palladium Bisulphide PdS_2 —When the foregoing compound is fused with sodium carbonate and sulphur, *sodium thiopalladate,* Na_2PdS_3, is formed This crystallises in reddish-brown needles having a slightly metallic lustre It is decomposed by hydrochloric acid with formation of the disulphide, which is a crystalline, dark brown powder easily soluble in aqua regia When heated in carbon dioxide it is first converted into the monosulphide, and at a higher temperature into the subsulphide

A salt of the formula $(NH_4)_2PdS_u,JH_{20}$ crystallises slowly in slender, yellowish-red needles when solutions of ammonium polysulphide and potassium palladiochlonde are mixed [2]

Sodium Palladiosulphte, $Na_6[Pd(SO_8)_4],2H_{20}$, is" obtained as a white, crystalline precipitate by adding caustic soda to a

[1] **Petrenko Kntschenko, *Zeit anorg Chem* , 1893, 4, 247**
[2] **Hofmann and Hochtlen, *Ber* , 1904, 37, 245**

solution of the chloride which has been saturated with **sulphur** dioxide The simple sulphite is not known

Palladious Sulphate, $PdSO_4,H_{20}$, is obtained by dissolving the hydroxide in sulphuric acid, or by dissolving the metal in the same solvent with the addition of nitric acid It forms indistinct olive-green, deliquescent crystals which are decomposed by water with formation of a basic salt, $PdSO_4,7Pd(OH)_2$, as a brown insoluble powder

Potassium Palladiomtrite, $K_2[Pd(NO_2)_4]$, is obtained on addition of potassium nitrite to a hot solution of potassium palladiochlonde as a pale yellow, crystalline powder, the production ol which serves as a microchemical test for palladium [1] The simple nitrite is not known

Numerous complex nitrites, sulphites, phosphates, and oxalates have also been described [2]

Palladious Nitrate, $Pd(NO_3)_2$, is formed by dissolving the metal or the oxide in nitnc acid It crystalbses in long, brownish-yellow, deliquescent, rhombic prisms which probably contain water of crystallisation A brown powder, $Pd(NO_3)_2,3Pd(OH)_2$, is formed on the addition of water to the solution

Palladious Cyanide, $PdCy_2$, is obtained as a pale yellow precipitate on addition of mercuric cyanide solution to a solution of palladious salt, which must contain no free acid and should not be too dilute On solution in potassium cyanide and evaporation, transparent, thm, rhombic prisms of *potassium palladiocyanide,* $K_2[PdCy_4],3H_{20}$, or small tablets containing $1H_{20}$ are obtained The cyanide is also soluble in acids and in ammonia, and the latter solution yields needles or pearly scales of *palladosammine cyanide,* $[Pd(NH_3)_2Cy_2]$

Palladious Thiocyanate, $Pd(SCy)_2$ is a reddish, flocculent precipitate, and dissolves in potassium thiocyanate solution, forming *potassium palladiothiocyanate,* $K_2[Pd(SCy)_4]$, which crystallises in ruby-red needles [3]

Palladium Silicide—When palladium and silicon are fused together they unite, and the melting-point curve shows the formation of the compounds Pd_2Si and PdSi By dissolving out £he silicon with dilute potash from any alloy containing

[1] Pozzi-Escot and Couquet, *Compt rctid* , 1900,**130,** 1073

[2] Rosenheim and Itzig, *Zeit anorg Chem,* 1900, 28, 28, Vezes, *Butt Soc chim* , 1899, [3], **21,** 172, Loiseleur, *Compt rend,* 1900,**131,** 262, Finck, *ibid* , 1896,**123,** 603

[3] Bellucoi, *Atti R Accad Ltncet,* 1904, [5], **13, 11**, 386.

more than 60% Si, the latter compound is obtained as bluish-grey fragments of speeifis gravity 7 31 [1]

AMMONIACAL PALLADIUM COMPOUNDS

620. These have been investigated chiefly by Hugo Muller,[2] and are formed by the action of ammonia on palladious salts They appear to belong to two series

Palladosammine compounds, $[Pd(NH_3)_2X_2]$,
Palladodiammine compounds, $[Pd(NH_3)_4]X_2$,

and are analogous to the corresponding platinum compounds Unstable hydroxylamine derivatives have also been prepared which probably belong to the same two series [3]

An extended investigation of the palladosammine salts in which ammonia is replaced by orgamc nitrogen bases has been carried out by Gutbier and his colleagues [4]

In addition to these, pyridine derivatives of the type $[Pd(Py)_2Cl_2]Cl_2$ derived from tetravalent palladium, have been described [5]

Palladosammine Hydroxide, $[(OH)_2(NH_3)_2Pd]$, is obtained by the decomposition of the sulphate with baryta water, or of the chloride with silver oxide and water The yellow solution thus obtained, when dried over sulphuric acid, yields a crystalline, ochre-yellow mass The solution has all the properties of a solution of an alkali hydroxide

Dichlorodiammine Palladium or *Palladosammine Chonde*, $[Cl_2(NH_3)_2Pd]$, is obtained by the addition of an excess of ammonia to palladious chloride and either evaporating, or, better, precipitating the salt by means of hydrochloric acid It forms fine, yellow needles, which consist of contiguous octahedra and is almost insoluble in water

Tetramminepalladious Hydroxide or *Palladodiammine Hydroxide*, $[(NH_3)_4Pd](0H)_2$, is obtained by the decomposition of the sulphate with baryta It is a colourless, crystalline mass, its aqueous solution has a strong alkaline reaction, precipitates the salts of copper, iron, cobalt, nickel, and aluminium, but not those of silver, and decomposes ammoniacal salts

[1] Lebeau and Johbois, *Compt rend* , 1908,**146,** 1028
[2] *Annalen,* 1853, 86, 341
[2] Zeisel and Nowack, *Annalen,* 1907, **351,** 439
[4] *Ber,* 1905, 38, 2107, 3869, 1906, 30, 616, 1292, 2716, *Zed anorg Chem* , 1905, 47, 23 See also Hardin, *J Amer Chem Soc* , 1899, 21, 943
[6] Rosenheim and Maas, *Zeit anorg Chem* , 1898,18, 331

Tetramminepalladious Chloride or *Palladodiammine Chloride*, $[(NH_3)_4Pd]Cl_2$, is formed by the repeated evaporation of palladious chloride with ammonia It crystallises in large, colourless, four-sided, monoclinic prisms easily soluble in water

Vauquehn's salt, $[Pd(NH_3)JCl_2,PdCl_2$, is obtained by the action of a slight excess of ammonia on palladious chloride

DETECTION AND ESTIMATION OF PALLADIUM

621 The two most characteristic reactions of palladium are (1) the precipitation of its hydrochloric acid solution by potassium cyanide, the yellowish-white palladium cyanide being thrown down, soluble in both hydrochloric acid and ammonia, and (2) the production of a black precipitate of palladious iodide, insoluble in hydrochloric acid, when potassium iodide or freshly precipitated silver iodide is added to a palladium solution By these reactions it may be separated from all metals, with the exception of copper, and this may be previously removed, according to Wohler, by precipitation as cuprous thiocyanate, after saturation with sulphur dioxide

Palladium is estimated gravimetncally as the metal, obtained by the ignition of the cyanide or by the reduction of the salts with a hydrazine salt[1] in acid solution[2] Palladium may be estimated also by precipitating with acetylene and igniting the precipitate,[3] and by weighing the metal deposited electrolytically with a rotating anode[4] A very convement method of estimating palladium, especially in the presence of nickel, is based on the fact that in acid solution it is quantitatively precipitated by dimethyl glyoxime The yellow-orange precipitate is filtered, washed, and lgnited to the metal On neutralising the filtrate, any nickel present is at once precipitated as the red glyoxime compound[5] Palladium may also be precipitated from acid solution by a-nitroso-/?-naphthol in a similar manner to cobalt The red precipitate is filtered, washed, and lgnited to the metal This method is particularly useful because the other platinum metals are not precipitated by this reagent, moreover, owing to the intense red of the compound it affords

[1] Jannasch and Bettges, *Ber* , 1904, 37, 2210

[2] Jannasch and Rostosky, *Ber*, 1904, 37, 2441, Paal and Amberger, *Ber.* 1905,38, 1388

[3] Erdmann and Makowka, *Ber* , 1904, 37, 2694

[4] Amberg, *Zeit Elektrochem* , 1904,19, 385

[5] Wunder and Thunnger, *Ann Chim* ***anal***, **1912,**17, **201**

a delicate test for palladium, even 0 001 gram per litre being easily diluted *Atomic Weight of PaMdium*—Until the year 1889 the only determination of the atomic weight of palladium was that of Berzehus, who obtained the number 106 by the analysis of potassium palladiochlonde Since 1889 the atomic weight has been redetermined by several investigators, but the results vary considerably Keiser[2] by the determination of the palladium in palladosammine chloride found the number 106 5, and by the same method, using very carefully purified material, Keiser and Breed[3] found the value 106 47 Bailey and Lamb,[4] by the same method, found the number 105 7, and a value closely agreeing with this, 105 8, was obtained by Joly and Leidie[5] by the analysis of potassium palladiochlonde Keller and Smith[6] from the electrolytic determination of the metal in palladosammine chloride obtained the much higher number 1071 A high figure, 106 99, was also obtained by Hardin,[7] who estimated the metal in diphenylpalladodiammonium chloride, $Pd[NH_2(C_6H_5)Cl]_2$, and the corresponding bromide, and in ammonium palladiobromide 0n the other hand, Amberg[8] has obtained a lower number, 106 64, by the analysis of palladosammine chloride, the chlorine and the metal being both estimated Shmn[9] reduced the double chloride of palladium and ammonium with formic acid, and found as the mean of mne experiments the figure 106 71 The most probable value is (1922) taken as 106 7

SUB-GROUP (c). THE PLATINUM GROUP.

Osmium Indium Platinum

622 These metals are distinguished by their high specific gravity and melting pomt Osmium alone forms a tetroxide, thus" resembling ruthenium

The tendency to form complex salts is exceedingly strongly marked, and with the exception of the sulphides and halogen

[1] Schmidt, *Zeit anorg Chem* , 1913, 80, 335
[2] *Amer Chem J* , 1889,**11,** 398
[3] *Ibid,* 1894,**16,** 20 [4] *Journ Chem Soc* , 1892, **61,** 745
[5] *Compt rend,* 1893,**116,** 146 [6] *Amer J Set,* 1892,**44,**423
[7] *J Amer Chem Soc* , 1899, 21, 943 [8] *Annalen,* 1905, **841,** 235
[9] *J Amer Chem Soc* , 1912, **84,** 1448 Compare Gutbier, Hass, and Gebhardt, *J pr Chem* , 1909,79,457

derivatives, very few simple salts are known Such as are known have the general formulae MR_2, MR_3, and MR_4, corresponding to the basic oxides MO, M_{208}, and MO_2, but the series MR_3 is scarcely represented among the platinum compounds The most important of the series of the complex salts are the halogen acids and their derivatives, such as K_2PtCl_4, K_3IrCl_6, and $ILjOsCl_6$, the complex nitrites, such as $K_3Ir(NO_2)_6$ and $K_2Pt(NO_2)_4$, the complex cyanides and thiocyanates, such as $K_2Pt(CN)_4$ and $K_2Pt(SCN)_4$, the sulphites, and above all the ammoniacal derivatives

OSMIUM. Os=i909 At No 76

623 In 18O3 Smithson Tennant investigated the metallic residue which remains when platinum ores are dissolved, and this he believed to contain a new metal At the same time Descotils, as well as Fourcroy and Vauquehn, came to the conclusion that the solution contained a peculiar metal However, in 1804 Tennant[1] proved that the platinum residues contained two new metals, to one of which he gave the name of indium, on account of the varying colour of its salts, and to the other the name osmium *(oijfirj,* a smell), because of the peculiar odour of its volatile oxide, Osmium is found in platinum ores as an alloy with indium, known as osmmdium, which is described under iridium (p 1438) It may be separated from the other members of the platinum group by means of its property of combining directly with oxygen to form a very volatile tetroxide, OsO_4 This compound is obtained, more or less pure, in the course of the preparation of the other platinum metals, and especially of ruthemum (see p 1389) The solution thus obtained may be precipitated with ammonia and ammonium sulphide, and the precipitated sulphide mixed with sodium chlonde, and heated in a slow current of chlorine The mass when lixiviated yields sodium osmichlonde, $Na_{20}sCl_6$, and from this solution ammonium osmichlonde is thrown down by ammonium chloride This is next washed with ammonium chloride solution, and then heated in a covered crucible, when spongy osmium is obtained The sulphide may also be simply heated in a well-covered carbon crucible to the temperature of the melting point of nickel

Pure osmium was obtained by Deville and Debray,[2] by passing the vapour of the pure tetroxide mixed with carbon monoxide

[1] *Phil Trans,* 1804, 94, 411 [2] *Compt rend,* 1876,82,1076

and carbon dioxide through a red hot porcelain tube Thus prepared, the metal asspnes the form of an amorphous powder, which is converted into trfe crystalline variety when fused with from three to four times its weight of tin in a charcoal crucible, the crystalline alloy treated with hydrochloric acid, and the residue heated in a current of hydrogen chloride

The crystalline form of osmium is either that of the cube or of a very obtuse rhombohedron The crystals possess a bluish-white colour with violet lustre, are harder than glass, and possess a specific gravity of 22 477 Hence osmium is the heaviest of known bodies, and is likewise one of the most infusible and least volatile of the metals The melting point of the metal is about 2500°, it may be distilled at the highest temperature of the electric furnace, but the volatilisation takes place much more slowly than that of the other platinum metals [x]

Osmium undergoes oxidation somewhat readily when finely divided, being oxidised and volatilised when heated in air below 212° and in oxygen between 155° and 170° When strongly heated in air, oxidation of the compact metal also takes place, this operation is dangerous owing to the formation of the highly poisonous tetroxide Deville was rendered almost blind for twenty-four hours by having accidentally become exposed to the vapour of the tetroxide This substance produces violent pain and inflammation of the conjunctiva, and vision is permanently injured by reduction to a film of metallic osmium [2]

In the finely divided state osmium possesses great catalytic activity It causes oxygen and hydrogen to unite and is a valuable catalyst in the synthesis of ammonia from its elements [3] Many orgamc compounds can be oxidised by oxygen in the presence of the metal [4]

Crystalhne osmium is not attacked even by aqua regia, and must be brought into solution by fusion with sodium peroxide, caustic soda and potassium nitrate, or barium peroxide and nitrate, the amorphous metal, on the other hand, is readily dissolved by fuming nitric acid, more slowly by aqua regia

On account of its high melting point, osmium has been employed for the preparation of filaments of incandescent electric lamps, but the cost is high and tungsten is now more generally

[1] Moissan, *Compt rend*, 1906,**142,** 189
[2] *Ann Chim Phya* , 1859, [3], 56, 400
[3] Haber and Le Rossignol, *Zat Elektrochem*, 1913, 19, 53
[4] Willstatter and Sonnenfeld, *Ber* , 1913, 46, 2952

employed The alloy osmmdium, or osrid, which is not attacked by acids, is employed for tipping gold fountain pens, and, inasmuch as it is unoxidisable and non-magnetic it has been used for compass- and watch-bearings

Colloidal Osmium —The metal may be obtained in the colloidal condition by reducing potassium osmate with hydrazine hydrate in presence of sodium lysalbate or protalbate [1] or gum arable,[2] and dialysing the product This still contains oxygen, which is removed by heating in hydrogen at 30-40°, the residue being completely soluble in water The colloid may also be obtained by impregnating lanolin with potassium osmate solution and reducing the mass with hydrazine hydrate This is then dissolved in light petroleum and precipitated by alcohol The colloidal osmium dioxide thus obtained is reduced by heating in a current of hydrogen at 50° to 60° The colloidal metal then left is soluble in ether, be much as 21 per cent of osmium may be prepared in this way [3] It effects the catalytic decomposition of hydrogen peroxide more rapidly than any of the other colloidal metals of this group, and actively decomposes formic acid to carbon monoxide and hydrogen[4] Carbon monoxide and oxygen combine to form carbon dioxide when shaken with the sol, even at the ordmaiy temperature [5] The colloid is more active than the finely divided metal in the oxidation of orgamc compounds [6]

COMPOUNDS OF OSMIUM

OSMIUM AND OXYGEN

624 The following oxides are known Osmium monoxide, OsO, osmium sesquioxide, Os_2, osmium dioxide, OsO_2, osmium tetroxide, OsO_4

In addition to these, osmic acid, H_2sO_4, and its salts are known, but the corresponding oxide has not been prepared

The first three of these oxides act as feeble basic oxides, but very few of their salts have as yet been examined, only the sulphate ahd chloride corresponding to the monoxide, and

[1] Paal and Amberger, *Ber* , 1907, 40, 1392, 2201
[2] Gutbier and Hofmeier, *J pr Chetn* , 1905, [2], 71, 452
[3] Amberger, *Kolloid Zeit,* 1915,17,47
[4] Muller and Sponsol, *Zeit Elektrochem* , 1922, 28, 307
[5] Paal, *Ber* , 1916, 49, 548
[6] Willstatter and Sonnenfeld, *Ibid* , 1914,47, 2801

double chlorides of the formula $3M^{1}Cl,OsCl3$, corresponding to the sesquioxide, being known The chloride, $OsCl_4$, has, however, been prepared along with double chlorides corresponding to the derivatives of chloroplatinic acid Osmic acid forms a series of osmates with the alkali metals, whilst the tetroxide yields a neutral solution in water, and forms salts with neither acids nor bases, though it yields compounds with the alkali hydroxides.

Osmium Monoxide, OsO, obtained by igniting the corresponding sulphite mixed with sodium carbonate in a current of carbon dioxide, is a greyish-black powder insoluble in acids

Osmium Sesquioxide, Os_{203}, is a black powder, insoluble in acids, obtained by heating its salts with sodium carbonate in a current of carbon dioxide DeviUe and Debray obtained this oxide in copper-red scales, together with the metal, by the reduction of the tetroxide A brownish-red *hydroxide* is precipitated by alkalis from solutions of the osmochlorides of the alkali metals

Osmium Dioxide, OsO_2, is obtained from its salts in a similar way to the foregoing oxides It is likewise formed when its hydroxide is heated in a current of carbon dioxide It may also be prepared pure by heating osmium in a current of osmium tetroxide and nitrogen at about 650°[x] Obtained in this way, it forms masses having a coppery lustre and specific gravity 7*71 On heating, it begins to decompose at about 500° into osmium and osmium tetroxide, but if it is heated in the vapour of the tetroxide the decomposition temperature is 650° By heating at just below this temperature it is converted into copper-coloured crystals of specific gravity 7 91[x] When mixed with the combustible substances osmium dioxide deflagrates on heating

A hydrated osmium dioxide is obtained by hydrolysis of potassium or ammonium osmichlonde with caustic potash

$$K_{20}sCl_6 + 4H_{20} = OsO_2,2H_{20} + 2KC1 + 4HC1$$

The same substance is produced by the action of alcohol or other reducing agents on a solution of the tetroxide or alkali osmate,

$$K_{20}sO_4 + 2H_{20} \text{-f } C_2H_6\,OH = OsO_2,2H_{20} + 2KOH + CH_3\text{-}CHO,$$

or when potassium osmate is exposed to the sunlight or treated with nitric acid Qaus and Jacoby[2] regarded the black precipi-

[1] **Ruff and Rathaburg, *Ber,* 1917, 60, 484** [2] **pr *Chem,* 1863,90,65**

tate obtained in this way as osmium tetroxide, $Os(OH)_4$, and Moraht and Wischin[1] as osnuc acid, H_2OsO_4, *i e*, OsO_3H_{20} Later investigation[2] shows that the substance is the dihydrate of osmium dioxide, $OsO_2,2H_{20}$, which loses one molecule of water at 100°, and the other at 200°, leaving the dioxide in a very finely divided and active state It combines with hydrogen with almost explosive violence and reacts briskly with oxygen to form the tetroxide When prepared by precipitation with alcohol or from impure ammomum osmichloride, it contains small quantities of organic matter and is then liable to ignite, or, if warm, to detonate on exposure to air

The dioxide obtained in the above reactions is in the colloidal form and gives a solution which is black by reflected and blue by transmitted light It is precipitated by electrolytes, but gives a colloidal solution again when washed free from them or when treated with alkali hydroxides or ammonia[3] A more stable colloid is produced by reducing potassium osmate with hydrazine hydrate in the presence of lanolin as protective colloid

Osmium Trioxide, OsO_3, is unknown, and the corresponding *osmic acid,* $H_{20}sO_4$, believed by Moraht and Wischin to be produced in the manner just described, is also of doubtful individuality The corresponding salts, however, are a well defined class of substances known as the *osmates*

Potassium Osmate, $K_{20}sO_4,2H_{20}$, is obtained by the addition of alcohol or other reducing agents to the solution of the tetroxide in caustic potash The liquid becomes of a fine red colour, and, when sufficiently concentrated, the salt separates out as a crystalline powder When slowly crystallised it forms octahedra which, according to their size, are of a garnet-red or almost black colour They possess a sweet, astringent taste, and do not change on exposure to dry air, but both in solution and in moist air they decompose, especially on addition of an acid, with formation of tetroxide and lower oxides

The *sodium* salt crystallises less easily, and yields an aqueous solution having a rose-red colour, from which barium chloride precipitates $BaOsO_4$ as an amorphous, green, flocculent precipitate slowly changing to lustrous, black, prismatic crystals

Osmium Tetroxide or *Perosmtc Anhydride* (commonly called

[1] ***Zeit anorg Chem*, 1893, 3, 153**

[2] **Ruff and Bornemann, *Zeit anorg Chem*, 1919, 85, 429, Ruff and Rathsburg, *loc cit***

[3] **Ruff and Rathsburg, *loc at***

osmic acid), OsO_4 —Very finely divided metallic osmium oxidises slowly at the ordinary taipperature, and about 400° takes fire with formation of the above oxide The denser the metal the higher is the temperature needed for oxidation Osmium tetroxide may be obtained also by heating the metal in a current of steam, and by dissolving the lower oxides or the metal in nitric acid or aqua regia These reagents, however, do not attack the metal after it has been strongly lgnited Osmium tetroxide sublimes in transparent, glistening needles which become soft and may be moulded in the hand like wax, and melt at 45° [x] They begin to sublime at a very moderate heat, and the fused oxide boils at 100°, yielding a colourless vapour with a density of 8 89, which is slightly greater than the calculated value The crystals dissolve readily in water, forming a colourless liquid which possesses a caustic and burning taste, and does not redden litinus paper Though it does not give salts, its acidic properties are illustrated by the formation with alkalis of compounds such as OsO_4,2KOH, OsO_4,RbOH, OsO_4,CsOH, and $20sO_4$,CsOH These are crystalline bodies, orange or brown in colour They are soluble in water and are strongly hydrolysed in solution [2] Osmium tetroxide has a most powerful penetrating smell, somewhat analogous to that of chloime and iodine A very small quantity of vapour mixed with air attacks the lungs, giving rise to very serious inflammation of the mucous membrane As an antidote to the effects of the tetroxide, Claus recominends the inhalation of sulphuretted hydrogen, which, however, must be cautiously employed Osmium tetroxide also acts violently on the skm, causing a painful eruption which can be removed by the use of sulphur baths The vapour also acts, as has been stated, most violently on the eyes, and may produce most serious consequences [3]

When heated on red hot charcoal it deflagrates like nitre It is easily converted into lower oxides by reducing substances, and its alkaline solution when boiled with a salt of formic acid yields a blue precipitate Sulphur dioxide colours the aqueous solution yellow, then brown, green, and at last indigo-blue

It is used in microscopic work for staining prepara'tions$_o$ and also for taking finger prints,[4] the oxide being reduced to metallic osmium

[1] **Ruff and Tschirch,** ***Ber*** **, 1913, 46, 929**
[2] **Tschugaev,** *Compt rend* **, 1918,187, 162**
[3] **Deville and Debray,** *Ann Chim Phys,* 1859, [3], **66,** 400, *Compt rend* **, 1874, 78,1509**
[4] **Mitchell,** ***Analyst,*** **1920, 46, 125**

Osmium tetroxide acts as a catalyst in many oxidations Thus, in the presence of a very small quantity of this substance, oxygen will oxidise methyl alcohol to formaldehyde and formic acid, and ethyl alcohol to acetaldehyde and acetic acid [1] Potassium chlorate which, alone, acts not at all, or only extremely slowly, in the presence of osmium tetroxide readily oxidises arsenic to arsenic acid, hypophosphorous acid to phosphoric acid, potassium formate to carbon dioxide, hydrazine sulphate quantitatively to nitrogen, and a number of organic substances are similarly oxidized[a] The catalytic action of the tetroxide in these reactions is attributed to the formation of an additive compound with the chlorate Osmium tetroxide also acts as a catalyst in reductions, and may be employed in the same way as nickel (p 1368) for the hydrogenation or hardening of oils The tetroxide is then first reduced to the dioxide [2] and probably the metal [3]

Osmyl Salts —When osmium tetroxide is treated with a suitable reducing agent in the presence of certain salts, compounds containing the group OsO_2 are obtained having the general formula $M^1{}_2(OsO_2)\ X_4$ [4]

Potasstum Osmyl Nitiile, $K_2(OsO_2)\ (NO_2)_4$, is prepared by reducing the tetroxide with nitric oxide in the presence of potassium nitrite

$$2KNO_2 + OsO_4 + NO = K_2(OsO_2)\ (NO_2)_4$$

The salt crystallises in orange-red prisms but is unstable, readily decomposing into the substances from which it was obtained

Potassium Osmyl Chloride, $K_2(OsO_2)Cl_4$, is obtained by treating potassium osmate with excess of hydrochloric acid and warming the solution

$$K_{20}sO_4 + 4HC1 == K_2(OsO_2)Cl_4 + 2F_{20}$$

On rapidly cooling the solution the anhydrous salt crystallises out as red octahedra, but by slowly cooling the solution the dihydrate may be obtained as pale brown, tnclimc crystals The salt is also obtained by the action of hydrochloric acid on osmyl nitrite

Many "other potassium salts have been similarly piepared, and the corresponding barium and silver salts are obtained by double decomposition

[1] Hofmann, *Ber* , 1913, 46, 3329, Hofmann, Ehrhart, and Schneider *fad* , 1913, 46, 1657
[2] Lehmann, *Arch Pharm* , 1913, **251,** 152
[3] Normann and Schick, *ibid* , 1914, **252,** 208
[4] Wmtrebert, *Ann Chim Phys,* 1903, [7], 28, 15

Osmyl Oxy-salts, having the general formula $M^{I}_2(OsO_8)X_2$, have also been obtained[1]

Potassium Osmyl OxynUnte$_t$ $K_2(OsO_3)(NO_2)_2$, is prepared by the action of a concentrated solution of potassium nitrite on osmium tetroxide

$$3KNO_2 + OsO_4 = K_2(OsO_3)(NO_2)_2 + KNO_3$$

or by the action of potassium hydroxide on the osmyl salt

$$K_2(OsO_2)(NO_2)_4 + 2KOH = K_2(OsO_3),(NO_2)_2 + 2KNO_2 + H_{20}$$

The salt crystallises in nearly black, monoclmic needles

Ammonmm Osmyl Oxychloride, $(NH_4)_2(OsO_3)Cl_2$, is made by the action of hydrochloric acid on the osmyl oxynitrite

$$(NH_4)_2(OsO_8)(NO_2)_2 + 2HC1 = (NH_4)_2(OsO_3)Cl_2 + 2HNO_2$$

It is a crystalline, yellow powder and with alkaline hydroxides yields the corresponding osmate and ammonia

$$(NH_4)_2(OsO_3)Cl_2 + 4KOH = K_{20}sO_4 + 2KC1 + 3H_{20} + 2NH_3$$

OSMIUM AND THE HALOGENS

625 *Osmium Tetrafluoride*, OsF_4.—By the action of fluorine on finely divided osmium at 25O°, the three fluorides are produced At lower temperatures, or by using a less active specimen of the metal, the product is mainly the tetrafluoride It has not been isolated in the pure state but its solution in water has been obtained[2]

Osmium Hexafluoride, OsF_6, is obtained with the two other fluorides by treating the metal with fluorine The octafluonde is removed (see below) and the hexafluonde obtained by heating at 50° under diminished pressure, when it sublimes and condenses as a light green, crystalline mass Its boiling point is about 205° It is decomposed by water, giving osmium oxides and hydrofluoric acid.[8]

Osmium Octafluonde, OsF_8, is obtained as already stated and is formed in greatest amount with an active metal preparation and with a rapid stream of fluorine It is isolated by evacuating the tube and collecting in a receiver cooled with liquid air. It is a lemon-yellow, crystalline substance, melting at 34-5° to a

[1] Wintrebert, *loc at* [2] Ruff and Tschireh, *Ber*, 1913, 46, 929
[3] *Ibid*, loo cit

yellowish-red liquid. The vapour is colourless, has a peculiar odour, and vigorously attacks the mucous membrane of the nose and eyes It begins to decompose at 225°, the decomposition being appreciable at 400° Osmium octafluonde violently attacks orgamc substances It dissolves in water, and is hydrolysed, the solution having the odour of the tetroxide and not of the octafluonde [x]

Osmium Dichloride, $OsCl_2$, is obtained in very small amount by heating osmium in chlorine It is better prepared by heating the trichloride to 500° under Teduced pressure and cooling the vapour[2] It is a brownish-black powder which forms a dark, violet-coloured, unstable solution in water

Osmium Trichloride, $OsCl_3$, is obtained admixed with the tetrachloride by heating finely divided osmium in chlorine at 1050° and rapidly cooling the vapour It is prepared in the pure state by heating ammonium osmichlonde in chlorine at 350°, when a dark, crystalline sublimate of the trichloride is obtained[3] It is readily soluble in water

When osmic acid is boiled for a long time with concentrated hydrochloric acid and a little alcohol, a solution is obtained which on evaporation yields red crystals of the composition $Os_2Cl_7,7H_{20}$, which become olive-green in moist air[4] This appears to be a mixture of the tn- and tetra-chlorides, since, on addition of potassium chloride to the alcoholic solution, potassium osmichlonde, $K_{20}sCl_6$, separates, and the filtrate on evaporation yields crystals of the trichloride, $OsCl_3,3H_{20}$

Potassium Osmochlonde or *Chlorosmite*$_y$ $K_3OsCl_6,3H_{20}$, is obtained by adding ammonia to a solution of osmium tetroxide in caustic potash, and saturating the liquid, as soon as it has become yellow, with hydrochloric acid On evaporation, the above salt separates out together with potassium and ammonium chlorides The latter can be readily separated mechanically. It forms dark red crystals which effloresce in the air and become pink It dissolves in water, yielding a cherry-red coloured solution, possessing first a strong astringent and then a sickly sweetish taste

Aryrnvmum Osmochlonde, $2(NH_4)_3OsCl_6,3H_{20}$—In order to prepare this salt, sulphuretted hydrogen is passed into a hydrochloric acid solution of the tetroxide until it has become red

[1] **Ruff and Tschirch,** ***loc cit***
[2] **Ruff and Bornemann,** ***Zett anorg Chem*** **, 1910, 66, 429**
[3] ***ibid*** **, loo cit**
[4] **Moraht and Wwchw,** ***Zeit anorg Chem,*** **1893, 3, 153**

The **liquid is** then evaporated with sal-ammoniac, when fine, red crystals are deposited resembling the potassium salt

Osmium Tetrachloride,$OsCl_4$, is obtained by heating the metal in dry chlorine It forms a red sublimate which dissolves in water, yielding a yellow solution, and this on dilution with more water attains a green tint On standing, the solution becomes colourless with separation of the lower oxides, whilst hydrochloric acid and osijnum tetroxide remain in solution A solution of osmium tetrachloride is obtained by dissolving the tetroxide in concentrated hydrochloric acid, though with more dilute acids it is reduced to the monoxide or dioxide [1]

Potassium Osmichlonde or *Chlorosmate*, $K_{20}sCl_6$, is obtained by gently heating a mixture of the finely divided metal with potassium chloride in a current of chlorine, and also by evaporating the hydrochloric acid solution of the tetroxide with potassium chloride It crystallises in dark brown, glistening octahedra, which yield a cinnabar-red powder, and dissolve in water with a yellow colour Alcohol precipitates the compound from this solution in the form of a red, crystalline powder

Sodium Osmichlonde, $Na_{20}sCl_6,?H_{20}$, is obtained in a similar way, and crystallises in long, orange-coloured prisms which are easily soluble in water and alcohol

Ammonium Osmichlonde, $(NH_4)_{20}sCl_6$, is obtained by the addition of powdered ammomum chloride to a solution of the sodium salt It is then deposited as a red, crystalline powder, crystallising from dilute solution in brown octahedra

Another sodium osmium chloride has also been prepared It has the composition Na_6OsCl_{12}, *i e*, 6NaCl,$OsCl_c$, and has therefore been called *sodium osmium heaachlonde* It is made by warming sodium sulphonosmate (p 1434), in a current of hydrochloric acid gas It forms lustrous, copper-coloured leaflets which cannot be crystallised without decomposition The *potassium* salt is formed in a similar mannei [2]

Osmium and Bwmine—When osmic acid is boiled with hydrobromic acid and a little alcohol, and the solution evaporated, dark, brown, prismatic crystals of the composition $Os_2Br_9,6H_{20}$ are obtained, which are possibly a mixture of $OsBr_3$ and $OsBr_G$ *Osmibromides* have also been prepared

Osmium and Iodine—By the action of boiling hydnodic

[1] Itemy, *J pr Chem*, 1920, [2], **101,** 341, Milbauer, *ibid*, 1917, [2], 96, 187, Ruff and Mugdan, *ibid* , 1918, [2], 98, 143

[2] Rosenheim and Sasserath, *Zeit anorg Chem* , 1899, 21, 122,

acid on osmic acid, violet-black crystals are formed having a metallic lustre, the composition of which appears to be OsI_4 (Moraht and Wischin) When a solution of potassium iodide, strongly acidified with hydrochloric or phosphoric acid, is added to one of osmium tetroxide, a green substance of the composition $OsI_2,2HI$ is formed On addition of ether, the latter assumes a green colour even when only traces of osmium are present,[1] and this may be used as a test for the metal *Osmi-iodides* have also been prepared

OSMIUM AND SULPHUR

626 Metallic osmium burns when heated in sulphur vapour, and sulphuretted hydrogen throws down a dark yellow sulphide of osmium from the hydrochloric acid solution of the oxide This is slightly soluble in water, giving rise to a dark yellow solution, and easily dissolves in nitric acid

Osmium Tetrasulphide, OsS_4, is thrown down as a brown precipitate when sulphuretted hydrogen is passed through an aqueous solution of osmium tetroxide lt is insoluble in alkalis and the sulphides of the alkali metals

Osmium Oxtjsulplude, Os_2S_2,H_{20} —By the action of hydrogen sulphide on the dry dihydrate of osmium dioxide (p 1427), which they regarded as osmic acid, Moraht and Wischin[2] obtained this compound The reaction is very violent, much heat bemg evolved The oxysulphide is a brown powder which is readily soluble in acids with evolution of hydrogen sulphide Tt is possible that water is not present as such in the molecule, and that the formula of the substance is more correctly represented by $Os_2(SH)_2$

Osmium Sulphite, $OsSO_3$ —In O1 der to pieparethis salt, sulphur dioxide is led into an aqueous solution of the peroxide, and sodium sulphate added to the blue liquid The dark blue gelatmous precipitate, after washing, is dried and yields a powder which is unalterable in the air, and which on trituration exhibits a metallic, silveiy lustre If the blue solution be treated with caustic potash a blackish-blue precipitate of hydroxide is obtained, which on exposure to air absorbs oxygen as rapidly as ferrous hydroxide

Osmium forms a large number of complex sulphites, which crystallise well and are stable substances *Sodium osmisidphite,*

[1] Alvarez, *Chem News,* 1905, 91, 172 [2] *Zed anorg Chem,* 1893, 3, 153

$Na_8[Os(SO_3)_c],8H_{20}$,, is obtained by boiling a solution of sodium osmichlonde with^cmcentrated sodium hydrogen sulphite, and crystallises in brownish-white prisms Crystalline compounds have been obtained in which one or more of the SO_3 groups are replaced by the groups CI or H_{20} The compound $Na_6[Os_4(SO_3)_7],24H_{20}$ is obtained as a dull-violet precipitate by the action of sodium hyposulphite on sodium osmichlonde[1]

Complex sulphites of a r different series, known as the *sulphonosmates,* are obtained by passing sulphur dioxide through a solution of osmium tetroxide, and then adding an alkali hydrogen sulphite The *sodium* salt has the composition $3Na_{20},OsO_3,4SO_2,5H_{20}$, its constitution being probably $(ONa)_{20}s(SO_3Na)_4,5H_{20}$ It crystallises in bright brown needles, and is readily soluble in water at 5O° to a reddish-brown solution, which soon decomposes to give a black oxide [2]

OSMIUM AND NITROGEN

627 Like the other metals of this sub-group, osmium forms complex derivatives with ammonia, but these have not as yet been fully investigated It also forms complex nitrates, a peculiar acid termed osmiamic acid, $OsNO_3H$, and derivatives containing nitrogen but free from hydrogen and oxygen termed the nitnlo-compounds, which are obtained by the action of acids on the osmiamates [3]

Osmosammine Hydroxide, $Os[(NH_3)_2(OH)_2]$, is obtained by dissolving the tetroxide in an excess of concentrated ammonia, and heating the reddish-yellow solution in a closed vessel to 5O°, when a black precipitate is formed The flask is then opened and the solution evaporated at a low temperature until the excess of ammonia has been driven off The base is thus obtained in the form of a blackish-brown powder, which when heated decomposes with rapid evolution of gas With acids it forms amorphous salts

Osmyldiammine Chloride, $OsO_2(NH_3)_4Cl_2$, is obtained by the addition of ammonium chloride to a solution of potassium osmate, and forms a yellow, crystalline precipitate easily soluble in water, the solution soon undergoing decomposition [4] "

[1] Sailer, *Zeit anorg Chem* , 1921,116, 209
[2] Rosenheim and Sasserath, *Zeit anorg Chem* , 1899, 21, 122, 1900, 24, 420
[3] See Werner and Dmklage, *Ber*, 1900, 39, 499, Brizard, *Ann Chim Phys*, 1900, [7], 21, 311
[4] See also Wolcott Gibbs, *Amer J Sci*, 1873, & 233

Ostmamic Acid, $OsN0_8H$—Osmiamates are formed by the action of ammonia on the tetroxide, especially in the presence of potash, the potassium salt being more stable than the ammonium compound It was at first supposed [1] that this substance had the formula $K_2N_20s_20_5$, but Joly [2] has shown that the true formula is $KNOs0_3$, its formation being represented by the equation

$$Os0_4 + KOH + NH_3 = KNOs0_3 + 2H_20$$

The acid has the constit  , he salts being derived from the tautomeric form 

The free acid is obtained by decomposing the barium salt with dilute sulphuric acid, or the silver salt with hydrochloric acid The light yellow solution remains in the dilute state without change for some time In the concentrated condition, however, it decomposes to give a gas and a brown powder

Potassium Osmiamate, $KNOs0_3$, forms orange-yellow tetragonal pyramids, which dissolve slowly in cold, and more readily in hot water, and on crystallisation become dark-coloured, owing to partial decomposition It decomposes when heated, with loss of introgen Crystalline salts of sodium, barium, and silver are also known

Osmium Nitrite, $Os(N0_2)_3$, is prepared from barium osmmitrite by precipitating the barium exactly with sulphuric acid, and evaporating the resulting solution of osmmitrous acid It forms a deep brown powder

The double intrites with the alkali metals and those of the alkaline earths, and of magnesium and zinc, crystallise well, and are soluble in water [4] *Sodium osminitrite,* $Na_20s(N0_2)_5,2H_20$, crystallises in orange-yellow parallelopipeds, and the remaimng osmimtntes form similar crystals, the colour of which varies from pale to full orange-yellow

[1] Fritzsche and Struve, *Petersb Acad Bull,* 1863, 6, 81
[2] *Compt rend,* 1891,**112,** 1442
[3] Werner and Dinklage, *Ber ,* 1906, 39, 499
[4] Wintrebert, *Compt rend,* 1905,**140,** 585

OSMIUM AND CARBON

628 Osmium forms a series of osmocyanides, derived from divalent osmium, which correspond closely in composition and in their properties to the ferrocyanides The most important of these compounds are the following

Osmocyanic Acid, $H_4[OsCy_6]$, is deposited in the form of white scales on the addition of fuming hydrochloric acid to a solution of the potassium salt These are easily soluble in alcohol, and crystallise out from the alcoholic solution on the addition of ether in colourless, glistening, transparent, hexagonal prisms Its aqueous solution has an acid reaction, and from it a substance of the empirical formula $OsCy_2$ separates out as a dark violet precipitate, which, is however, probably a complex osmium osmocyanide

Potassium Osmocyanide, $K_4[OsCy_6],3H_{20}$, is obtained by adding potassium cyanide to an alkaline solution of osmium tetroxide, evaporating the filtered solution, and heating the residue It crystallises from hot water, in which it is easily soluble, in yellow, tetragonal tablets, these when heated give off water and become colouiless Its solution yields a light blue precipitate with ferrous salts, which becomes darkei coloured on exposure to air, when tieated with nitric acid, it is converted into a fine, violet-colouied powder, which is also obtained by precipitating the potassium salt with ferric chlonde After diying, this forms a fragile mass ha\ing a copper-red colour, and when boiled with caustic potash it yields feme hydroxide and potassium osmocyanide

Barium Osmocyanide, $Ba_2[OsCy_6],3H_{20}$, is formed when the iron precipitate is boiled with baryta It crystallises in small, yellowish-red, transparent, rhombic prisms, which are readily soluble in water and alcohol

Potassium Barium Osmocyanide, $K_2Ba[OsCy_c],3H_{20}$, is obtained by mixing hot solutions of the potassium and barium salts On cooling, small, yellow, oblique rhombohedra are deposited, which are sparingly soluble in cold water

DETECTION AND ESTIMATION OF OSMIUM

629 The presence of this metal may be most easily detected by the formation of the volatile strongly-smelling tetroxide Solutions containing osmium as tetroxide or osmichlonde, when

warmed with excess of thiocarbamide and a few drops of hydrochloric acid, give a deep red or rose coloration, and one part in a hundred thousand may be thus detected[1] Sulphuretted hydrogen throws down a precipitate of the sulphide insoluble in ammomum sulphide If a solution contain a mixture of the platinum metals, and other metals precipitable by sulphuretted hydrogen, this gas is passed into the hot solution so long as a precipitate is formed This is then washed and warmed with yellow ammonium sulphide, when platinum, indium, gold, etc , dissolve The filtrate is then acidified with hydrochloric acid, the precipitate fused with sodium caibonate and sodium nitrate, and the fused mass lixiviated with water, the residue being treated according to the method described under platinum In this way the iridium is obtained together with platinum and gold, and these may be readily separated The portion insoluble in ammomum sulphide is then fused with caustic potash and potassium chlorate, and treated with water in order to dissolve the potassium salts of ruthenic and osmic acids The solution is carefully neutralised with nitric acid in order to separate the black oxide of ruthenium, and the filtrate distilled with nitric acid, when the volatile osmium tetroxide passes over The residue insoluble in water is gently ignited in a current of hydrogen, and treated with dilute nitric acid, when palladium and rhodium remain behind, and these are separated by aqua regia, in which the latter metal is insoluble

Osmium is usually estimated *quantitatively* as the metal It is separated from other metals as the volatile tetroxide, the vapours of which, in order to avoid lobs, are passed into caustic potash, alcohol is added to the distillate in order to form potassium osmate, and the solution then treated with ammomum chloride and the precipitated osmyldiammine chloride lgnited in hydrogen, when the metal is obtained

Osmium tetroxide may also be estimated by adding dilute sulphuric acid and potassium iodide to its aqueous solution, and titrating the liberated iodine One molecule of osmium tetroxide liberates four atoms of iodine [2]

The Atomic Weight of osmium was determined by Beizehus in 1828. in a similar way to that of platinum, and he obtained the number 198 9, whilst Fr&ny,[3] in 1844, by converting the

[1] **Tsohugaev, *Compt rend* , 1918,167, 235**
[2] **Klobbie, *Journ Chem Soc* , 1899, 76, n, 184**
[3] ***Ann Chim Phys* , 1844, [3], 12, 514**

metal into the tetroxide, obtained the number 199 6 According to these determinations, the atomic weight of osmium appeared to be greater than that of indium, whereas the analogies of the metal with ruthenium seemed to indicate that it should precede indium in the periodic system, just as ruthenium precedes rhodium In 1888 Seubert[1] redetermined the atomic weight by analysing pure potassium and ammonium osmichlondes and obtained the number 191 4, whilst in 1891, from a later[2] and more concordant series of expenments, he obtained the still lower number 190 6 The value now (1922) adopted is 190 9

IRIDIUM Ir = 1931 At No 77

630 The history of the discovery of this metal has already been described under osmium

Iridium is found in the platinum ores in considerable quantity in the form of the alloys platinindium and osmindium The first of these occurs in grains, and often in small cubes with rounded edges, the second usually in flat, irregular grains, and occasionally in hexagonal prisms The composition of these minerals is shown in the following analyses

	PLATINIRIDIUM		OSMRIDIUM			
	Urals	Brazil	Urals	*New* Granada	Call fornia	Austra ha
Iridium	76 85	27 79	55 24	57 80	53 50	58 13
Osmium	—	—	27 23	3510	43 40	33 46
Platinum	19 64	55 44	10 08	—.	:—	—
Rhodium	—	6 86	151	0 63	2 60	3 04
Ruthenium	—	—	5 85	6 37	0 50 '	522
Palladium	0 89	0 49	trace	—		
Iron		4 14	trace			
Copper	178	3 10	trace	0 06		0 15
	9916	97 82	99 91	100 06	100 00	10000

adium is usually prepared from the alloys described above tfhieh are left behind when platinum ores are treated with

1 *Ber* , 1888, 21, 1839

2 *Annalen,* 1891, 261, 257,

aqua regia One of the most efficacious of the many methods[1] which have been proposed for the extraction of the metal is that employed by Deville and Debray[2] in the production of the pure indium required for the standard metre bars of platinum-lridium prepared for the International Commission on the Metric System The osmiridium is fused with zinc, and heated until all the zinc evaporates, the porous residue being then powdered and lgnited with barium nitrate, which converts the indium into oxide and the osmium into barium osmate The residue after extraction with water is boiled with nitric acid, which brings the iridium into solution, whilst the osmium is volatilised in the form of tetroxide The indium oxide is precipitated from the residual solution by baryta, dissolved in aqua regia, and then thrown down as the double chloride of indium and ammonium This, on ignition, yields spongy iridium, containing small quantities of platinum, ruthemum, and a little rhodium The metal is then lgnited with potass-ium nitrate, and the mass treated with water, when potassium ruthenate dissolves It is lastly fused with lead, the regulus obtained leaving, after treatment with nitric acid and aqua regia, a residue of pure indium

Another method frequently employed is to mix the " osnd " with sodium chloride and heat to redness in an atmosphere of chlorine The metals are then converted into chlorides, and the osmium chloride, being volatile, is expelled The mixed chlorides are then dissolved in water, the solution treated with chlorine and hydrochloric acid and excess of potassium chloride added A precipitate of the double chlorides of potassium and platinum, indium, and ruthemum is produced, which is filtered off and boiled with water Hydrogen is then passed through the solution when platinum and ruthemum are precipitated and the solution becomes green The solution is decanted from the precipitate and hydrogen again passed through, when the iridium slowly separates out as bright lustrous, thin laminae

After osmium, indium is the most difficultly fusible and least volatile of the platinum metals, but it may be fused and volatilised in the electric furnace, the melting point is 2300° The molten metardissolves carbon, which separates out on cooling as graphite It possesses a white lustre, resembling that of polished steel In

[1] Wohler, *Pogg Ann* , 1833, **31,** 161, Claus, *Annalen,* 1858,**107,** 134, Gibbs, *Amer J Sci,* 1861, [2], **31,** 70, Matthey, *Proc Roy Soc,* 1879, 28, **463**

[2] *Compt rend,* **1874, 78, 1502**

the cold it is very brittle, but at a white heat it is somewhat malleable The specific gravity of the fused metal is 21 15, whilst that of the crystallised metal is 22 4

If the alcoholic solution of the sulphate be exposed to sunlight the metal is deposited as an impalpable, black powder, which, when washed with hot water and dried, acts even more energetically in bringing about the combination of combustible gases than does platinum black The smallest trace brought on to paper saturated with alcohol produces ignition, the metal at the same time being converted into a grey sponge

Spongy indium is prepared by igniting the double chloride of indium and ammonium It absorbs hydrogen, the absorption being a minimum at 0° with falling temperature and a maximum at 20° with rising temperature The hydrogen is easily expelled by a slight increase in temperature, but the last traces are removed only by strong heating[x] The spongy metal oxidises when heated in the air, and when ignited becomes dense and lustrous, and then absorbs oxygen only slowly, whilst the coherent metal does not do so at all

A very active metal is produced when indium foil is subjected to long-continued cathodic pulverisation in a vacuum, the surface becoming dull and brittle It absorbs 800 times its own volume of hydrogen at the ordinary temperature It explodes electrolytic gas and forms an amalgam with mercury which is completely soluble in aqua regia [2]

Indium black, as well as the coherent metal when alloyed with much platinum, dissolves in aqua regia Pure massive indium is, however, not attacked When it is heated with acid potassium sulphate, or in presence of fused alkalis, it is oxidised, and it unites directly with chlorine at a dull red heat When the metal is held in the middle of a flame of alcohol it becomes covered with a black, moss-like deposit, which has the composition IrC_4, and easily takes fire on exposure to the air The metal is in this case penetrated throughout its mass with carbon, and becomes of a dark grey colour The oxides also are converted into the carbide of iridium, with evolution of light and heat, when they are heated in gases or vapours containing carbon

Owing to its bnttleness it is very difficult to roll it into foil or draw it out into wire These difficulties, however, have been overcome, and the metal is employed for the manufacture of scientific apparatus

[1] **Gutbier, Ottenstein, and Weise, *Ber* , 1919, 52, [B], 1366**
[2] **Rother, *Ber K Sachs Ges Wiss Math -Phys Kl,* 1912, 64, 5**

Iridium is sometimes used for pointing gold pens, and is first heated with phosphorus, which renders it more fusible and easy to work The phosphorus is afterwards removed by heating the mass in a hme crucible

It forms an alloy with 9 parts of platinum, which is extremely hard, as elastic as steel, perfectly unalterable in the air, and capable of taking an exceedingly fine polish This alloy has been employed in the production of ^standard metre bars and for electrodes to be used in corrosive liquids A similar alloy is used for the wires of high temperature pyrometers

Colloidal Indium may be prepared by sparking between iridium electrodes under cold water (Bredig's method) It is also obtained by the reduction of indium salts with hydrazine hydrate in presence of sodium protalbate or lysalbate [1] or gum arable [2] as protective colloids, or by reducing colloidal solutions of the tetrahydroxide with hydrogen, sodium formate, or formaldehyde [3] The colour of the solution varies from red to black It possesses considerable catalytic activity Carbon monoxide and oxygen combine when shaken with the solution at the ordinary temperature [4] The decomposition of hydrogen peroxide is catalytically accelerated, but not so greatly as by colloidal platinum The catalyst is " poisoned " by hydrogen sulphide, mercuric chloride, and potassium cyanide [5]

COMPOUNDS OF IRIDIUM.

631 Indium forms two basic oxides, the sesquioxide, Ir_2O_3 and the dioxide, IrO_2, and two corresponding series of salts, the sesqui-salts, of the general formula IrR^1_3 and the iridic salts IrE^T_4 The halogen compounds form double salts with the corresponding alkali compounds, which must be looked upon as alkali salts of complex acids Compounds in which the metal is divalent are also known, but have only been slightly investigated Like the other members of this group, iridium forms numerous complex derivatives, the chief of which are the halogen derivatives just mentioned, the double cyanides, and the ammonincal derivatives.

[1] **Paal and Amberger, *Ber* , 1905, 38, 1398, 1907, 40, 1392, 2201**
[2] **Gutbier and Hofmeier, *J pr Chem* , 1905, O], 71,358**
[3] **Paal, Biehler, and Steyer, *Ber,* 1917, 60, 722**
[4] **Paal, *Ber,* 1916, 49, 548**
[5] **Brossa, *Zett physikal Chem,* 1909, 66, 162**

IRIDIUM AND OXYGEN

632 *Iridium Sesquiosxide,* Ir_2O_3 is formed when potassium iridichloride, K_2IrCl_6, is mixed with sodium carbonate and heated to dull redness

$$2K_2IrCl_6 + 4Na_2CO_3 = Ir_2O_3 + 8NaCl + 4KCl + 4CO_2 + O$$

The fused mass is washed with water containing ammonium chloride, and the residue, after ignition to expel the ammomum chloride, is treated with dilute acid in order to remove the small quantity of alkali It is also obtained impure by mixing air-free solutions of potassium hydroxide and sodium lridioehlonde, Na_3IrCl_6, evaporating to dryness, and heating the residue to redness in a current of carbon dioxide [1]

Iridium sesquioxide is a bluish-black powder which is decomposed by heat At 400°, it is converted into a mixture of the metal and the dioxide, a little oxygen also being lost at this temperature[1] It evolves oxygen rapidly at 1139°, leaving metallic iridium[2]

Indium sesquioxide is readily reduced by hydrogen In the pure state it imparts to porcelain after firing a fine black colour, and with zinc oxide it yields a grey tint

Indium Tnhydroxide, $Ir(OH)_3$, is obtained by a process similar to that employed for the preparation of the corresponding rhodium compound (p 1402), which it closely resembles It forms a yellowish-green precipitate which readily dissolves in

alkalis and oxidises quickly in the air

Indium Dioxide, IrO_2, is a black powder obtained by heating the hydroxide in a current of carbon dioxide It is also formed when the metal is heated to bright redness in the air,[3] or in oxygen, the best temperature for its formation being 1070° On heating, it decomposes into the metal and oxygen[4] It is insoluble in acids

Indium Tetrahydroxide, $Ir(OH)_4$, is formed by the oxidation of the tnhydroxide in the air, or by precipitating the tetrachloride with an alkali, as well as by boiling potassium mdate with ammomum chloride It is a heavy, indigo-blue powder which is almost insoluble in dilute sulphuric and nitric acids,

[1] **Wohler and Witzmann,** *Zeit anorg Chem,* **1908, 57, 323**
[2] **Deville and Debray,** *Compt rend* **, 1878, 87, 441**
[3] **Geisenheimer,** *Ibid,* **1890,110, 855**
[4] **Wohler and Witzmann,** *Zeit Elektrochem* **, 1908,14, 97**

but dissolves completely, though slowly, in hydrochloric acid Its solubility, however, appears to depend on the method of preparation[1] On heating the indigo-blue solution it becomes green and then brown

Indium tetrahydroxide has also been obtained in the colloidal form On the addition of potassium hydroxide to potassium lndichloride in the cold, a violet, colloidal solution of the tetra-hydroxide is obtained which turns blue on heating[2] If indium chloride is added to sodium protalbate or lysalbate, an olive-green or rust brown precipitate of the protalbate or lysalbate is obtained, the colour depending on the acidity of the solution, and on dissolving this precipitate in sodium hydroxide or carbonate, blood-red hydrosols of iridium trihydrate are obtained, which, in the presence of excess of sodium hydroxide, are oxidised, giving blue hydrosols of the tetrahydroxide[3]

Potassium Iridate is obtained as a partially soluble bluish mass when indium is lgnited with potassium nitrate Its composition is not definitely known

SALTS OF IRIDIUM

633 *Indium Monochloride,* IrCl, is obtained by heating the dichloride in chlorine between 773° and 798° It forms copper-red crystals of specific gravity 10 18 It is insoluble in bases and acids, including even concentrated sulphuric acid[4]

Indium Bichloride or *Indious Chloride,* $IrCl_2$, is formed as a brown, crystalline substance by heating the trichloride in chlorine between 763° and 773° Above this temperature, it further decomposes into the monochloride[5] It has been stated to be formed as a green mass when chlorine is passed over spongy iridium at a red heat Like the monochloride, it is insoluble in bases and acids

Indium Trichloride, $IrCl_3$, is best prepared by heating the reduced metal in chlorine at 600°[6] It is stable in chlorine from below 100° to 763°, when]t decomposes into the dichloride, which, in turn, is stable up to 773°, when the monochloride is formed The trichionde is also obtained by heating one of its double salts with sulphuric acid If the mass be then thrown into water,

[1] See also Joly and Leidi6, *Compt rend* , 1895,**120,**1341
[2] Wokler and Witzmann, *Zeit Elektrochem* , 1908, 57, 323
[3] Paal, Biehler, and Steyer, *Ber,* 1917, 50, 722
[4] Wohler and Streicher, *Ber,* 1913, 46,1577
[5] *Ibid ,loc cit* [6] *Ibid* , loc *cit*

the chloride separates out as a light olive-green precipitate containing water and hydrochloric acid, and may be obtained almost anhydrous by heating at 200° to 500° in a current of hydrochloric acid [1] It may also be prepared by heating ammomum lndichloride in chlorine at 440° [2] A solution of the trichloride is obtained by treating the hydrochloric acid solution of the tetrahydroxlde with sulphur dioxide until it has become green Indium trichloride is an olive-green, crystalline substance which is insoluble in acids and bases It forms complex derivatives with the chlorides of phosphorus and arsenic [3]

Potassium Indiochloride or *Chloriridite,* $K_3IrCl_6,3H_{20}$, is best obtained from the corresponding lndichloride by heating it with sulphuretted hydrogen, and adding potassium chloride to the olive-green solution It forms very soluble, green, rhombic prisms which effloresce readily The monohydrate, isomorphous with the corresponding rhodium compound, is obtained by the action of hydrochloric acid on potassium indium oxalate as greenish-brown crystals[4] The sodium and ammonium salts are similar compounds of the formulae $Na_3IrCl_6,12H_{20}$ and $(NH_4)_3IrCl_6,H_{20}$

Indium Tetrachloride or *Iridic Chloride,* $IrCl_4$, is obtained by dissolving the finely divided metal in aqua regia, or by the solution of indium tetrahydroxide in hydrochloric acid When the solution is evaporated at a temperature not above 40°, a black mass is obtained which appears red in thin films, and contains a small quantity of trichloride The tetrachloride is stable only below 100°, and is formed by the action of chlorine on the metal below this temperature, but the reaction is extremely slow, even with liquid chlorine [5] The hydrochloric acid solution probably contains *iridichloric acid,* H_2IrCl_6, corresponding to the following compounds

Potassium lndichloride or *Chlonridate,* K_2IrCl_6, is obtained by the addition of potassium chloride to the above hydrochloric acid solution On evaporation, small, blackish-red, regular octahedra, isomorphous with the corresponding platinum compounds, are deposited These are slightly soluble in cold, and more readily

in hot wate

alkali chloride or in alcohol

[1] Detepine, *Compt rend* , 1914,**158,** 264
[2] Antony, *Qazz,* 1893, 23, I, 184
[3] Geisenheimer, *Compt rend,* 1890, **110,** 1004, 1336
[4] Duffour, *Ibid* , 1912,**155,** 222
[5] Wohler and Streioher, *Ber,* 1913, 46, 1577

Sodium Iridichlortde, $Na_2IrCl_6,6H_{20}$, is readily soluble in water and crystallises in almost black tablets or prisms, which are ISOmorphous with the corresponding platinum compound

Ammonium Indichloride, $(NH_4)_2IrCl_6$, is obtained by precipitating the acid solution of the chloride by ammonium chloride It is a dark cherry-red powder, consisting of small, blackish-red octahedra, isomorphous with the corresponding platinum compound It is considerably more soluble than the platinum salt One hundred parts of water dissolve O 566 part of the salt at 0°, and 4 381 parts at 100° [1]

Indichlorides of metal-complex bases have also been prepared, e,g.,$[Co(NH_8)_8]_2$, $[IrCl_6]_32$

Indium Tnbromide, $IrBr_3,4H_{20}$—When the blue hydroxide is dissolved in hydrobromic acid, a blue liquid is obtained which loses bromine on evaporation and deposits small, light olive-green, six-sided crystals, having the above composition They dissolve readily in water, but are not soluble in alcohol, and lose their water of crystallisation at 100° From the mother-liquor of this salt steel-grey needles of lndiobromic acid, $H_3IrBr_6,3H_{20}$, are deposited, having a metallic lustre by reflected light These lose water at 100° and are converted into a brownish-red mass easily soluble in water or alcohol The solution decomposes carbonates with formation of lndiobromides

Potassium Indwbromide, $K_3IrBr_6,3H_{20}$, forms long, olive-green, lustrous, efflorescent, four-sided needles, becoming light green and opaque They dissolve readily in water

Ammonium Indwbromide, $2(NH_4)_3IrBr_6,3H_{20}$, is obtained by reducing the corresponding indibromide with sulphur dioxide and neutralising with ammomum carbonate It crystallises in dark olive-green prisms, and is isomorphous with the corresponding rhodium salt, with which it crystallises in all proportions

Iridium Tetrabromide, or *Iridic Bromide,* $IrBr_4$—The blue hydroxide dissolves in hydrobromic acid, giving rise probably to *iridibromic acid,* H_2IrBr_6 This on evaporation with nitric acid leaves a blue, deliquescent, crystalline mass It forms, with other bromides, well crystallised *tridibromides,* such as KoJrBrJJ, which crystallises in opaque, lustrous, blackish-blue, regular octahedra

Indium Tetriodide, or *Iridic Iodide,* Irl_4, is obtained by boiling

[1] Archibald and Kern, *Trans Roy Soc Canada,* 1917-18, [3], **11,** 7 See also Rimbach and Korten, *Zed anorg Chem ,* **1907, 52, 406**

[2] **Benrath, Buoher,** and Eckstein, *Zett anorg Chem ,* **1922,121, 347**

the hydrochloric acid solution of the chloride with potassium iodide. **It** forms **a** black powder, **which** yields, with the iodides of the alkali metals, well crystallised double **compounds** possessing a ruby-red colour

Indium Monosulphide, IrS—-The metal burns when ignited in sulphur galena in its appearance

Indium Sesquisulphide, Ir_2S_3, is precipitated when sulphuretted hydrogen is passed into a solution of a salt of indium sesquioxide It is a brown powder, somewhat soluble in water, and slightly so in potassium sulphide and nitric acid

Indium Ammonium Pentadecasulphide, $(NH_1)_3IrS_{15}$, crystallises in large, brown, tetragonal octahedra [1]

Indium Bisulphide, IrS_2, is formed when the powdered metal is heated with sulphur and sodium carbonate, and is formed by the action of sulphuretted hydrogen on lithium lndichloride at 4° It is a brown powder, insoluble in nitric acid, and decomposes at 300° into its elements [2]

Indians Sulphite has not been prepared, but several double salts with sodium sulphite, such as $IrSO_3,3Na_2SO_3,10H_{20}$ and $IrH_2(SO_3)_2,3Na_2SO_3,4H_{20}$, have been described by Seubert,[3] who obtained them during the separation of iridium from rhodium according to Bunsen's method

Indium Sesquisulphite, $Ir_2(SO_3)_3,6H_{20}$, is obtained when the hydroxide suspended in water is treated for some time with sulphur dioxide This compound is found in solution whilst a brown, basic salt remains undissolved The solution is then evaporated, when the normal sulphite separates out in the form of a yellow, crystalline precipitate which is scarcely soluble in water but dissolves readily in dilute acids It also forms a number of double salts

Indium Sesquisulphate, $Ir_2(SO_4)_3,xH_{20}$, crystallises out when a solution of the tnhydroxide in sulphuric acid is evaporated in absence of air It combines with the sulphates of the alkali metals, ammonium and thallium, forming a series of alums having the general formula $M^I{}_2SO_4,Ir_2(SO_4)_3,24H_2$ which all crystallise in yellow octahedra[4]

A double salt of the composition $Ir_2(SO_4)_3,3K_2SO_4,2H_{20}$ has

[1] **Hofmann and Hochtlen,** ***Ber*** **, 1904, 37, 245**
[2] **Antony,** ***Gazz*****, 1893, 23, i, 184**
[3] ***Ber*** **, 1878,11, 1761 See also Sailer,** ***Zeit anorg Chem*** **, 1921,116, 209**
[4] **Marino,** ***Zeit anorg Chem*** **, 1904, 42, 213**

also been obtained, which separates from boiling aqueous solution, on cooling, in rectangular or hexagonal crystals[1]

Iridic sulphate, $Ir(SO_4)_2$, was obtained by Berzehus as a yellowish-brown, amorphous mass by oxidation of the sulphide with nitric acid When warmed with sulphuric acid, it undergoes reduction to a green solution of the sesquisulphate [2]

Iridionitrites —The simple nitrite of iridium has not been prepared as it readily forms complex nitrites

Hydrogen Iridionitrite, $H_3[Ir(NO_2)_6],H_{20}$, forms light-yellow, readily soluble needles [3]

Potassium Iridionitrite, $K_3[Ir(NO_2)_6]$, is best prepared by adding potassium mtrite to a solution of indium sesquisulphate at 70-80° It is a white powder, readily soluble in boiling water, but almost insoluble in the cold liquid, and in potassium chloride solution The coirespondmg *sodium* salt crystallises with $2\,H_2$ [4]

A series of salts in which some of the mtrite groups are replaced by chlorine is also known They are intermediate between the mdichlorides and lridinitntes and are known as the *chlor-nitntes*

Cyanogen Derivatives of Iridium—The chief of these are the lridicyanides, which resemble the ferricyanides, and have been investigated by Martius [5]

Potassium Iridiocyanide, $K_4[Ir^nCy_6]$, is obtained in colourless prisms when potassium ferrocyanide is gently ignited with indium

Indicyanic Acid, $H_3[Ir^{in}Cy_6]$, is obtained by decomposing the barium salt with dilute sulphuric acid It is very soluble in water or alcohol, less so in ether, and is deposited from solution in crystalline crusts It possesses an acid reaction and has an unpleasant taste, and from its solutions hydrochloric acid precipitates a green substance which is probably a complex indium mdicyanide

Potassium Indicyanide, $K_3[IrCy_6]$, is obtained by fusing ammomum lridichloride with potassium cyanide, and also by the decomposition of the barium salt with potassium sulphate It crystallises in colourless, tetragonal prisms, which are easily

[1] Del6pine, *Compt rend,* 1906, **142,** 1525
[2] Rimbach and Korten, *Zeit anorg Ckem ,* 1907, **52,** 406
[3] Gibbs, *Ber ,* 1871, 4, 280
[4] Leidi6, *Bull Soc chim ,* 1902, [3], 87,936 See also Miolati, *Atti R Accad Lincei,* 1902, [5], 11, 11, 151
[5] *Annahn,'1861,* **117,** 357

soluble in water, but insoluble in alcohol It is a very stable body, unattacked byohlorme or hydrogen chloride.

Barium Indicyanide, $Ba_3[IrCy_6]_2,18H_{20}$—In order to prepare this compound the crude potassium salt is precipitated with copper sulphate, and the precipitate decomposed with baryta water It forms hard, transparent, probably tetragonal crystals, which effloresce on exposure, are easily soluble in water, and are attacked with difficulty by acids

AMMONIACAL DERIVATIVES OF IRIDIUM

634 Iridium forms ammoniacal derivatives corresponding to mdious chloride, $IrCl_2$, and iridic chloride, $IrCl_4$, which are analogous to the corresponding platinum compounds It forms also an extended series[1] of compounds corresponding to the trichloride, $IrCl_3$, which are similar to the cobaltic, chromic, and rhodic compounds, and are most probably strictly analogous to these in constitution

1 *Indious Compounds —Dichloro-diammine-iridium (Iridioammomum Chloride),* $[Cl_2(NH_3)_2Ir]$, is obtained by heating a solution of lridious chloride with an excess of ammonium carbonate and neutralising the solution with dilute hydrochloric acid It is a yellow, granular body, insoluble in water The corresponding hydroxide is not known, and of the other salts only the *sulphato~compound,* $[SO_4(NH_3)_2Ir]$, has been prepaied This is obtained by heating the chloride with sulphuric acid, when easily soluble orange-coloured crystals are formed

Tetrammine-indium Bichloride (Iridiodiammonium Chloride), $[(NH_3)_4Ir]Cl_2$, is obtained by prolonged boiling of the preceding chloride with excess of ammonia. On cooling, a whitish precipitate separates, and this is decomposed by boiling water with evolution of ammonia The hydroxide has not been prepared The *sulphate* crystallises in rhombic prisms, which are easily soluble in hot water and deflagrate on heating

2 *Iridic Compounds —Dichloro-tetrammine-mdium Dinitrate (Indidiammonium Chloronitrate),* $[Cl_2(NH_3)_4Ir](NO_3)_2$, is formed when concentrated nitric acid is gradually added *to* dichloro-diammine-mdium It dissolves in hot water, and crystallises in lustrous laminae If an excess of hydrochloric acid be added to a solution of this compound, the *chloride* is precipitated, crys-

[1] Palmaer, *Ber,* 1889, 22, 15, 1890, 23, 3810, 1891, 24, 2090, *Zeit anorg Chem* , 1895,10, 320, 1896,13, 211

tallising from boiling water in violet octahedra Silver nitrate precipitates only the half of the chlorine which it contains Sulphuric acid converts the nitrate into the *sulphate,* $[Cl_2(NH_8)_4Ir]SO_4$, which crystallises in fine, greenish needles

3 *Indium Sesqui-compounds —Hexammine-iridium trichloride,* $[(NH_3)_6Ir]Cl_3$, prepared by heating the following compound with ammonia at 140°, forms colourless prisms

Chloro-pentammine-mdium dichlorifte (Purpureo-iridium chloride), $[Cl(NH_3)_5Ir]Cl_2$, is produced,by the action of ammonia on ammonium lndiochlonde, and forms yellowish-brown, octahedral crystals, or a flesh-coloured, crystalline powder Silver nitrate precipitates only two-thirds of its chlorine

A large number of other pentammine-mdmm derivatives have been described, as well as aquo-pentammine, tetrammine, and triammine compounds

DETECTION AND ESTIMATION OF IRIDIUM

635 Ammomum chloride produces, in a tolerably concentrated solution of indium, a dark-red, crystalline precipitate, and the dark colour sometimes observed in the corresponding platinum precipitate indicates the presence of indium in this metal Indium is also distinguished from platinum by the formation of a colourless solution of potassium mdichloride when caustic potash is added to the chloride of the metal, on exposure to the air, this solution first becomes red-coloured, and afterwards blue Sulphuretted hydrogen decolorises the solution of an iridic salt with separation of sulphur, whilst the brown sulphide, soluble in ammomum sulphide, is precipitated

Indium is always estimated quantitatively as the metal

The Atomic Weight of indium was determined by Berzehus by igniting potassium mdichloride in hydrogen, the result of a single experiment being 196 5 Seubert,[1] in 1878, working with carefully purified material, obtained the number 192 O5 by the analysis of the same salt, whilst the ignition of the ammomum salt gave the higher number 193 39 Joly,[2] in 1890, by the analysis of the potassium and ammomum iridichlorides, obtained the number 193 18 Archibald,[3] in 1909, by reduction of potassium iridichloride in hydrogen, obtained the value 192 90, but no details of the work have yet been published Hoyermann,[4]

[1] ***Ber*, 1878,11, 1770** [2] ***Compt rend*, 1890, 110, 1131**
[3] ***Chem News*, 1909,100,150**
[4] ***Sitzungsber phys med Soz Erlangcn*, 1911, 42, 278**

in 1911, by reducing ammonium iridichloride in hydrogen, obtained, as a mean of five determinations, the value 192 61, and Holamann,[1] in 1912,4dopting the same method, found as a result of four determinations the value 193 42

The number now (1922) adopted is 193 1

PLATINUM., Pt=1952 At No 78

636 This metal appears to have been first observed in the sixteenth century, for Scaliger, who died in 1558, in his work *Exercitationes Exotencce de Subtilitate,* combated the views of Cardanus that all metals are fusible, for, he adds, in the mines of Mexico and Carian a metallic substance is found " quod nullo lgni, nullis Hispanicis artibus, hactenus hquescere potuit " As platinum occurs in the above districts, it appears very probable that this was the metal here referred to Indeed the metal seems to have been used long before this date, for an alloy containing platinum together with gold and indium has been found composing some of the hieroglyphs on an Egyptian box discovered at Thebes, dating from the seventh century B C [2]

It was not, however, until the eighteenth century that platinum attracted general attention, and this time many chemists occupied themselves diligently with the subject The first of these was Don Antonio de Ulloa, who took part in the French Expedition of 1735 which had for its object the measurement of an arc of the meridian on the equator In 1748 he published his *Eelacion Historica del Viage a la America Meridional,* in which he describes an unworkable metallic mineral which even makes gold ore useless if it occur mixed with it in large quantities William Brownngg[3] was the first to describe native platinum as a compact metal He had obtained it mne years previously from Charles Wood, who had brought some samples of it from Carthagena in Granada to Jamaica, and thence to England Brownngg termed it a semi-metal It was afterwards more exactly examined by Scheffer, who descnbed it in the Memoirs of the Stockholm Academy in 1752 with the title " On White gold, or the seventh Metal, termed in Spamsh ' plating del Pinto/ " that is, small silver of Pinto, *platina* being the diminutive

[1] *Sitzungsber phys med Soz Erlangen,* 1912, **44,** 84
[2] Berthelot, *Compt rend,* 1901, 132, 729, *Ann Chim Phys,* 1901, [7], 23, 5
[3] *Phi Trans ,'l* 750, 46, 584

of *plata,* the Spanish for silver The name of del Pinto was added because it was first found in the auriferous sand of that river Scheffer describes the insolubility of platinum in nitric acid, and was acquainted with the facts that aqua regia dissolves it and that it is precipitated from the solution by mercury He also states that it is infusible at the strongest heat of a furnace, but that it can be alloyed with other metals, and that it may be fused by the help of arsenic He declares the new body to be a true metal, and, on account of its unalterabikty, believes it to be a noble one, and suggests that it may be used for the specula of telescopes In 1754 Lewis [x] published a series of researches on platinum, and in 1757 the investigations of Marggraf were communicated to the Berlin Academy Amongst the most important of his observations was that which has since proved of such service to analytical chemistry, that platinum solution produces with the salts of the alkalis an orange-yellow precipitate, with the exception of that of the mineral alkali soda, with which it produces none Next came Macquer and Beaume's researches on platinum, which were published in the Memoirs of the Pans Academy of 1758 The most important new fact observed by these chemists was that platinum can be fused in the focus of a powerful burning-glass Besides this, the paper in question contains the information that platinum had hitherto been so rare a substance, because the Spanish Government had forbidden its exportation, inasmuch as gold could be alloyed with a considerable quantity of the new metal without its colour being sensibly changed, thus giving rise to the possibility of fraud Further investigations were made by Cronstedt in 1764, and by Bergman in 1777, the latter chemist explaining the nature of the changes which occur when a platinum solution is treated with the alkalis Count von Sickingen, at that time the representative of the Palatinate at the Court of Paris, worked diligently on the subject of platinum, and was the first, in 1772, to prepare platinum foil and platinum wire, and to show that this metal when alloyed with silver dissolves in nitric acid His experiments were commumcated to the Academy in 1778, and in 1782 the same researches were described in a pamphlet which appeared in German with the title *Experiments an Platinum* All the preceding researches, as well as many later ones, were made with South American platinum

In 1819 grains of a white metal were discovered in the aun-

[1] ***Phil Trans*, 1764, 48, 638**

ferous sands of the Urals, but it was not till 1823 that platinum was detected in this substance This discovery gave rise to the Scientific Expedition to the Urals undertaken by Humboldt, G Rose, and Ehrenburg, in 1829

With the exception of *Sferrylite*, $PtAs_2$, found in small quantities in the nickel-copper ores of Ontario,[1] platinum occurs in the native state, but native platinum is very seldom pure, the purest specimens having been found in Brazil together with grains of palladium The usual platinum " ore," as it is termed, contains all the metals of this group together with iron, copper, titamc iron ore, etc It is sometimes, though seldom, found crystallised in cubes and octahedra, but more usually occurs in rounded or flattened grains, or sand having a metallic lustre, and occasionally in large, rounded nuggets, both forms occurring in river sand or detritus Some of the more important localities from which platinum is obtained are Choco near Popayan, the gold-washmgs of the Pinto in the province of Antioquia in Columbia, and Minas Geraes in Brazil In the Urals it is found in alluvial deposits at Nischnetagilsk and Goroblagodat Platinum likewise occurs in the Natoos Mountains in Borneo, and in Haiti, Peru, California, India, and Australia, especially in New South Wales It is also found in small quantities in the sands of various rivers, occurring in the Rhine, and in streams in Wicklow, North Carolina, and Canada East The largest mass which has yet been obtained is that in the Demidoff Cabinet in St Petersburg, weighing 7 837 kilos In the Urals platinum is found together with chrome iron ore in serpentine, whilst in the Brazils it occurs with gold in syenite Many common minerals, such as dolomite, heavy spar, and fahl ore, contain traces of platinum, and this explains the occurrence of the metal in the sands of so many rivers It is found in small quantities also in most of the ores of lead and silver, and it is usually contained with palladium in small quantities in all silver, and it has been observed in meteoric iron[2] Some American copper ores contain platinum, and it is recovered in the electrolytic refining of copper In the United States mints the gold is refined electrolytically, and sometimes the anode sludge contains small quantities of platinum Thus, in the San Francisco mint, 112 ounces of platinum and indium were

[1] Walker, *Zeit Kryst Min*, 1896, 25, 561, *Amer J Sci*, 1896, [4], 1, 110, Wells and Penfield, *ibid*, 1902, [4], 13, 95, Dickson, *ibid*, 1903, [4], 15, 137

[2] Davison, *Amer J Sci*, 1899, [4], 7, 4

recovered from the refining of 1,073,000 standard ounces of gold.

The following table contains a series of analyses of various platinum ores by Deville and Debray [1]

Locality	Choco (S America)	California	Australia	Urals
Platinum	86 20	85 50	61 40	76 40
Gold	100	0 80	120	0 40
Iron	7 80	6 75	4 55	1170
Indium	0 85	105	110	4 30
Rhodium	140	100	185	0 30
Palladium	0 50	0 60	180	140
Copper	0 60	140	1 10	410
Osmindium	0 95	110	26 00	0 50
Sand	0 95	2 95	120	140
	100 25	101 15	100 20	100 50

The body termed osmindium is an alloy of osmium and indium which is not attacked by aqua regia, the sand contains quartz, chrome iron ore, hyacinth, spinel, and llmenite

637 *The Metallurgy of Platinum* —The mfusibihty of platinum, as well as its power of withstanding the action of many of the most powerful reagents, rendered it desirable that this metal should be employed for the manufacture of vessels for chemical use In 1784 Achard mentioned that the substance obtained by fusing arsenic and platinum together leaves, on ignition, a residue of malleable platinum, in this way he prepared what was probably the first platinum crucible From the year 1787 this method was employed in Pans, where Janetty was celebrated for his platinum work Platinum vessels were, however, so expensive and difficult to obtain, that in the year 1801 G Rose and Karsten, for want of a platinum crucible, were unable to exanyne the statement of Guyton de Morveau and Desormes that potash consists of lime and hydrogen, and soda of magnesia and hydrogen.

[1] *Ann Chim Phys*, 1859, [3], 66, 449 See also Martin, 16ft *Ann Rept U S Geol Survey for* 1894-5, Pt I I I , 1895, 628, Koifman, *Arch Sci phys nai*, 1915, [4], 40, 22

In the year 1800 Richard Knight[1] published a method for preparing malleable platinum This consisted in dissolving the crude platinum, precipitating the solution with ammomum chloride, stamping the dried precipitate of the double chloride of platinum and ammomum into a corneal mould made of fire clay, and igniting the whole In this way platinum is obtained as a coherent metallic mass, which can then be worked up In 1822 a similar method was described by Barrual, but for many years before this, in fact from 1800 to 1809, a relative of a member of the well-known firm of Messrs Johnson, Matthey and Co was employed in working on platinum, and had discovered (whether independently of Knight is uncertain) a method for consolidating the sponge, which was afterwards elaborated by Wollaston and described by him in the Bakenan Lecture[2] for 1828 This, although identical in the mam features with Knight's process, is distinguished from it in several important particulars, and is the method by which platinum was manufactured up to the year 1859, when Deville's process came into use[3] Wollaston in the first place pointed out the necessity of heating the double chloride very gently at a temperature just sufficient to expel the whole of the ammomum chloride and to occasion the particles of platinum to cohere as little as possible, for on this depends the ultimate ductility of the product The metallic powder thus obtained must be rubbed between the hands of the operator so fine as to pass through a fine lawn sieve After having been well levigated, the uniform mud or pulp is pressed whilst cold into a brass barrel and strongly compressed by a powerful lever The cake of platinum can be easily removed, owing to the corneal form of the barrel, and is so hard that it can be handled without danger of breaking It is then placed on a charcoal fire and heated to redness to drive off moisture and to give it a greater degree of cohesion After this it is heated in a wmd furnace to the most intense heat that can be obtained After ignition for about twenty minutes, the cake is removed from the furnace and placed upright on an anvil, and struck when hot with a heavy haminer The ingot of platinum thus obtained may be drawn into wire or'submitted to any of the processes of which the most ductile metafs are capable

The easy method thus proposed for working up platinum has

[1] *Tilloch's Phil Mag*, 1803, 16, 1 [2] *Phil Trans*, 1829, 119, 1
[3] *Ann Chim Phys*, 1859, [3], 58, 484

had **a** great influence on the progress of chemistry. The present generation of chemists can scarcely understand the difficulties with which their predecessors had to contend, unable, as they were, to use platinum crucibles, basins, retorts, foil, or wire In his *Letters on Chemistry* Liebig says

" Without platinum it would be impossible, in many cases, to make the analysis of a mineral The mineral must be dissolved and it must be first rendered soluble, or prepared for solution Now, vessels of glass, of porcelain, and of all non-metallic substances are destroyed by the means we employ for that purpose Crucibles of gold and silver would melt at high temperatures But platinum is cheaper than gold, harder and more durable than silver, infusible at all temperatures of our furnaces, and is left intact by acids and alkali carbonates Platinum unites all the valuable properties of gold and of porcelain, resisting the action of heat, and of almost all chemical agents Without platinum the composition of most minerals would have yet remained unknown "

Platinum apparatus is also employed on a large scale and with great advantage in the chemical industries, thus, for example, in the manufacture of sulphuric acid, and in the parting of the noble metals The first platinum apparatus for concentrating sulphuric acid, weighing 423 ounces, was made in London in 1809 by Messrs Johnson, Matthey and Co , who since that time have furnished platinum vessels for all parts of the world The price charged for this first platinum still was at the rate of 16s per ounce, the present price is about £20

The application of the oxy-hydrogen blowpipe for fusing large masses of platinum, proposed first by Hare,[1] has exerted a great influence on the progress of the platinum industry Hare succeeded in fusing 971 grams of platinum, as well as large quantities of indium and osmium This method was improved upon by Deville and Debray,[2] whose investigations on the platinum metals have been of great service to the general progress of chemical industry The means employed by these chemists for fusing platinum, and now employed on the large scale by most of the platinum manufacturers, consists in the use of two well-fitting lumps of quick lime The upper one has a hole drilled through the middle for the introduction of the blowpipe, whilst a side opening permits the escape of the products

[1] *Phil Mag*, 1847, [3], 31, 356
[2] *Ann Chim Phys*, 1859, [3], 66, 385

of combustion and serves as an outlet for the molten metal Instead of hydrogen common coal-gas is usually employed This is allowed to enter through the tube H, Fig 202, whilst the oxygen enters at o The upper portion of the blowpipe consists of copper and the lower of platinum Lime is used for the crucible, because it stands a high temperatuie well, and at the same time it absorbs the slags of the oxides of iron and silicon and other materials which are formed during the operation The introduction of this process induced chemists to seek for a cheap method of preparing oxygen on the large scale, whilst by means of the oxy-hydrogen blowpipe Messrs Johnson, Matthey and Co have succeeded in effecting a provement in the metallurgy of platinum, viz, that of soldering platinum by itself (autogenous soldering), instead, as was formerly the case, of soldering with gold The electric furnace is now frequently employed for fusing platinum

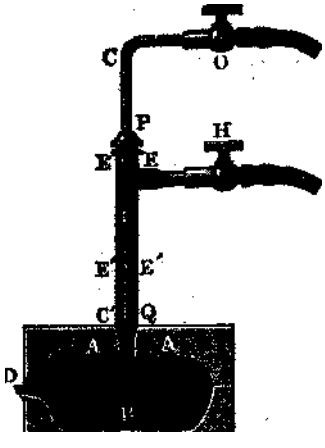

Most of the platinum of commerce has been obtained from the Urals by a process of concentration by washing, similar to the manner in which alluvial gold is extracted The crude platinum thus obtained is in the form of fine particles, grains, and scales, nuggets are also occasionally met with, and a little gold is also generally present This gold is extracted from the crude platinum by amalgamation, the material being rubbed with mercury in a dish made of wood, iron, or porcelain

Deville and Debray elaborated two methods [1] for treating in the dry way the crude platinum remaining According to the first of these, the ore is repeatedly melted in a vessel made of lime In this way an alloy of platinum with indium and rhodium is obtained This method is especially applicable to the fusion of old platinum vessels, inasmuch as all the impurities, such as sulphur, phosphorus, iron, gold, lead, etc , which occur in the scrap platinum, are either volatilised or absorbed by the

[1] *Ann Chim Phys*, 1859, [3], 66, 385, 1861, 61, 5

lime The second method depends on the fact that lead can be alloyed with the platinum metals but not with osmiridium These processes have, however, not met with much success in practice, as the platinum thus prepared may contain, besides the harmless indium and rhodium, other admixtures, and may not be homogeneous

Hence wet methods are more generally used The following process is adopted in the German works of Heraus in Hanau [1] The raw ore is treated in glass retorts under a pressure of twelve inches of water with a mixture of 1 part of aqua regia and 2 parts of water The solution is evaporated to dryness, and the dried mass heated to 125°, at which temperature the palladium and rhodium salts are reduced to lower chlorides The clear aqueous extract acidified by hydrochloric acid is then precipitated with ammomum chloride, the double chloride of platinum and ammonium being thrown down, whilst the corresponding iridium salt is obtained on evaporating the mother-liquor The solution remaining after precipitating the platinum is treated with scrap iron, when the other metals are thrown down, and the precipitate, from which the excess of iron has been dissolved by hydrochloric acid, is again treated with aqua regia, and from this solution a new portion of platinum and indium thrown down The mother-liquors, as well as the residue left on dissolving the oie in aqua regia, contain palladium, rhodium, ruthemum, osmium, and indium The spongy platinum obtained by igniting the double chloride of platinum and ammomum is then pressed, broken up, and fused with excess of oxygen in a lime crucible

In the wet process of G Matthey the platinum is first melted with six times its weight of lead, and then granulated by pouring into water

The process employed in Russia is very similar to the foregoing The crude platinum is dissolved in aqua regia in porcelain basins set on a sand-bath The solution is repeatedly evaporated with hydrochloric acid until all nitric acid has been removed, the aqueous solution then filtered, and the filtrate treated as described above [2]

Most of the platinum which occurs In commerce is not pure, but contains, like Russian platinum com, 2 per cent of iridium. This alloy is valuable for the preparation of chemical vessels, as it is less readily attacked by acids than pure platinum

[1] **Phihpp,** ***Ber Entw Chem Ind,*** **1, 999**
[2] ***Mineral Industry,*** **1897, 6, 561**

638 *Preparation of Pure Platinum*—Deville and Debray[1] have prepared pure platinum on a large scale by the following process The metal, which contains iridium and rhodium, is fused with six to ten times its weight of lead, the mass after cooling treated with nitric acid, and the residue treated with dilute aqua regia, when a crystalline alloy of indium, ruthenium, and iron remains behind, whilst lead, platinum, and some rhodium go into solution , This latter is treated with ammonium chloride, the double chloride, $(NH_4)_2PtCl_6$, being thrown down in a finely divided, amorphous state and almost white, whilst the rhodium is kept in solution The precipitate is washed with water containing hydrochloric acid, ignited, and the residue of platinum fused in a lime crucible When fused, the supply of gas is suddenly stopped, so that the metal solidifies from the outside, in this way the formation of bubbles in the metal is avoided

According to O Matthey,[2] the preparation of pure platinum is a matter of great difficulty His process is, to begin with, similar to that already described, but he evaporates down the aqua regia solution, and then adds pure sulphuric acid to the residue in order to convert any lead which may remain in solution into the insoluble sulphate The platinichloric acid is then dissolved out with water and precipitated by a mixture of ammonium chloride and common salt, the latter being added because the ammomum platinichloride is less soluble in a solution of common salt than in water The liquid is then heated to 8O° and allowed to stand for some days in order that the precipitate may become denser This is then repeatedly washed with a solution of ammomum chloride, and at last with distilled water acidified with hydrochloric acid The washed precipitate is then dried and mixed with potasium bisulphate and a small quantity of ammomum bisulphate The mixture is then heated to dark redness in a platinum basin On boiling the mass with water, potassium sulphate and potassium rhodo-sulphate dissolve, leaving pure platinum behind

The production of platinum from the Ural mines has been subject to great variations In 1825, when the mines werp first opened, only 361 pounds were produced In 1827 the experiment of coming with platinum was tried at the St Petersburg mint pieces of 3, 6, and 12 roubles being produced The coinage of platinum was, however, soon abandoned (in 1844), and the coins

[1] *Compt rend*, 1875, 81, 893 [2] *Proc Boy Soc*, 1879, 28, 463

in circulation were withdrawn, owing to the very considerable variations which the price of the metal underwent from year to year and the impossibility therefore of fixing a permanent monetary value upon the coin The total value coined amounted to 4,146,5O4 roubles, and the annual amount produced towards the close of the period in which the metal was coined reached 7,716 4 pounds It afterwards declined, but subsequently increased owing to the large demand for the metal occasioned by the widespread introduction of electric lighting, the metal being employed in the construction of incandescent lamps In 1893 the production reached the amount of 11,196 pounds

Later the supply of platinum has not been equal to the increase in demand, Russia is still the chief source of the metal, and the scarcity is partly due to the local difficulty of securing the necessary mining labour, and also to the diminution of yield in the richer mines The average output of the Russian mines was, for the years 1893 to 1898, 12,050 lb per annum, for the years 1899 to 1904, 12,600 lb , whilst during the year 1905, 14,050 lb were produced There is, however, a small production of platinum in the United States, between 100 and 200 troy ounces being produced per annum, Columbia also produced 800 lb during 1904, and since that time the output has considerably increased

639 *Properties*—Pure platinum has a tin-white colour, is soft like copper, has a specific gravity of 21 4136-21 4317 (Kahlbaum),[1] and is the most malleable of metals after gold and silver The specific heat of platinum is 0 03159, and this increases with temperature even at very high temperatures[2] Its coefficient of expansion is very nearly the same as that of glass, so that a platinum-glass join may be made without the latter cracking Like iron, it can be readily welded at a white heat It melts at 1710° as determined by a resistance -thermometer,[3] whereas higher temperatures, 1753-1889°, are indicated by the optical pyrometer method[4] An extremely fine wire can be melted in the flame of a Bunsen burner, platinum in large masses is infusible even at the highest temperature of a blast-furnace, although a small piece of the metal may be melted

[1] *J Chim Phys*, 1904, 2, 537

[2] Magnus, *Ann Phys*, 1916, [4], 48, 983, Fabaro, *Nuovo Chim*, 1915, [6], 9, 1, 123

[3] Harker, *Proc Boy Soc*, 19O6, 76, [-4], 235

[4] Waidner and Burgess, *Bull U S Bureau Standards*, 1907, 3, 163, Holborn and Valentiner, *Ann Physik*, 1907, 22, 1

in such a furnace[1] It can, however, be fused in the oxy-hydrogen flame When large masses of the molten metal are quickly cooled they exhibit the phenomenon of " spitting " so characteristic of silver

Platinum is sensibly volatile below its melting point, even at 13000,[2] and cubic or octahedral crystals of the metal have been found in the neighbourhood of the platinum electrodes in electric furnaces[3] According to Hulett and Berger[4] it begins to volatilise at 800° in air, whilst it is unchanged at this temperature in the absence of oxygen, this phenomenon has been attributed to the formation at high temperatures of a volatile oxide which undergoes decomposition at lower temperatures Roberts[5] found that platinum does not volatilise in hydrogen, nitrogen, or in vacuo, but begins to do so in oxygen even at 500°, the extent of the volatilisation being nearly proportional to the pressure of the oxygen, and he concludes that the volatilisation is due to the formation of the oxide PtO_2 which decomposes at lower temperatures

The loss of weight of platinum by heating is increased by the presence of indium and decreased by rhodium, these effects being particularly noticeable above 900° Iridium is frequently alloyed with platinum in order to stiffen it for the manufacture of crucibles, but rhodium would be preferable for this purpose The presence of iron reduces the loss of weight on heating, and below 900° there may even be a gam in weight owing to the iron diffusing to the surface and oxidising[6] Platinum can be distilled in the electric furnace[7]

Hydrogen diffuses through platinum,[8] and tubes made from fused and haminered platinum allow hydrogen to pass through them at a strong red heat in larger quantity than is the case with caoutchouc membranes at the ordinary temperature. This property depends upon the fact that the red-hot metal has the power of absorbing hydrogen (Vol I, p 159) It dissolves 3 8 volumes of the gas, which it gives off on heating in a vacuum, the surface of the platinum becoming covered

[1] Meyer, *Ber*, 1896, 29, 850
[2] Crookes, *Proc Roy Soc*, 1912, 86, 464
[3] Guntz and Bassett, *Bull Soc chtin*, 1905, [3], 38, 1306
[4] *J Amer CJiem Soc*, 1904, 26, 1512
[5] *Phil Mag*, 1913,25, 270
[6] Burgess and Sale, *J Ind Eng Chem* , 1914, 6, 452, 1915, 7, 516, Burgess and Waltenberg, *ibid*, 1916, 8, 487
[7] Moissan, *Compt rend*, 1906, **142,** 189
[8] See Schmidt and Lucke, *Zeit physikal Chem* , 1921, 8, 152

with bubbles [1] The solubility is proportional to the square root of the pressure of the hydrogen and is less than in the case of iron and nickel.[2] The power of platinum to absorb hydrogen is diminished by the presence of mercury, sulphur, arsenic, and zinc, and the extent of the " poisoning " is proportional to the amount of poison present[3] Such substances also cause a diminution in the catalytic activity of the metal, the extent of the poisoning being different for different reactions[4] The absorption of hydrogen is also noticed when platinum foil is employed as the negative pole in the electrolysis of water, the hydrogen being given off again when it is converted into the positive pole Platinum does not dissolve carbon dioxide or sulphur dioxide [2]

In January, 1817, Sir Humphry Davy communicated the fact to the Royal Society that mixtures of oxygen or air with hydrogen, carbon monoxide, ethylene, vapour of alcohol, vapour of ether, and other easily inflammable gases or vapours, are capable of bringing about the incandescence of a warmed platinum wire,[5] and that then these mixtures either combine slowly or in some cases quickly, and even with explosion This now well-known phenomenon is thus described by Davy " A temperature much below ignition only was necessary for producing the curious phenomenon, and the wire was repeatedly taken out and cooled in the atmosphere till it ceased to be visibly red, and yet when admitted again it instantly became red hot" In the following year Erman observed that it was only necessary to warm the platinum wire to 5O° to enable it to bring about this combination

In 182O Edmund Davy showed that the black powder deposited when a platinum solution is precipitated by sulphuretted hydrogen, the precipitate dissolved in mtric acid, and the liquid thus obtained mixed with its own volume of alcohol, possesses the property, when moistened with spirits of wme, of becoming lgnited in the air Two years later, Doberemer observed that spongy platinum, obtained by the ignition of the double phlonde of platinum and ammonium, exhibits the same

[1] See also Winkelmann, *Ann Phystk,* 19O1, [4], 6, 1O4, 19O2, [4], 8, 388, 19O6, [4], **19,** 1O45, Langmuir, *J Amer Chem Soc,* 1918, 4O, 1361

[2] Sieverts and Jurisch, *Ber,* 1912, 46, 221

[3] Maxted, *Journ Chem Soc* , 1921, **119,** 225 Compare Paal and Windisch, *Ber* , 1913, 46, 4010

[4] See Vavon and Husson, *Compt rend* , 1922,**175,** 277

[5] *Phil Trans,* 1817, **1O7,** 77

phenomenon when gently warmed with alcohol In 1823 the same chemist noticed that when hydrogen is allowed to pass over spongy platinum in presence of air the hydrogen gas is lgnited, and upon this was founded the well-known Doberemer's Hydrogen Lamp [1] Faraday afterwards showed that chemically clean platinum acts in a similar way. The circumstances in which platinum and certain other metals exhibit this action were investigated by Thenard and Dulong in the same year

In order to exhibit this action, Davy's glow-lamp is used (Fig 2O3) It is fed with a mixture of alcohol and ether, or with methyl alcohol, this is ignited in order to heat the spiral of platinum wire to redness The flame is then blown out, and the mixed vapours of alcohol and ether rising from the moist wick are oxidised, and thus the spiral is kept brightly incan-

FIG. 2O3.

FIG. 204.

descent The same phenomenon can be observed if a spiral of platinum wire be hung in a small test-glass (Fig 204) into which a little ether has been poured Another mode of showing the same experiment is to heat a small piece of platinum foil in the flame of a Bunsen burner, and then quickly to extinguish the flame, allowing the gas to escape The foil soon begins to glow, and if it be placed near the burner it becomes hot enough to re-ignite the gas, if further removed, the foil continues to glow, but the gas is not ignited

The catalytic action of platinum in the oxidation of hydrogen and of carbon monoxide has been studied by Langmuir [2]

Spongy Platinum, first prepared by E Davy, is very finely divided metallic platinum, which possesses a very large surface compared with its mass, and is able to condense large quantities of oxygen This substance is frequently employed as an oxidising

[1] *Schweigger's J* , 42, 6O, *Tilloch's Phil Mag* , 1825, 65, 15O
[2] *Trans Faraday Soc* , 1922,17, 6O7

agent, and may be readily prepared by gently heating the double chloride of platinum and ammonium By the action of sodium hydroxide solution on chloroplatimc acid mixed with formaldehyde, a more active product is obtained which becomes incandescent on exposure to air owing to the absorption of oxygen [1] Spongy platinum forms a porous mass which, when heated strongly, becomes denser, and assumes a metallic lustre under the burnisher

Platinum Black —This form of platinum was also discovered by E Davy, who, however, misled by certain accidental impurities, considered it to be a platinous nitrite It is to Liebig[2] that we owe the discovery of this error, and also a description of a good method for the preparation of the substance This consists in warming a solution of platinum dichloride in potash with alcohol Thus obtained, it is a soft, black, dull powder, which soils any surface on which it is rubbed When thoroughly freed from alcohol by boiling with water, and dried in a vacuum over sulphuric acid, it absorbs oxygen from the air so rapidly that the mass becomes red hot Platinum black is obtained also by dissolving alloys of platinum with other metals, such as copper and zinc, in nitric acid, when the platinum remains in the form of a black powder This latter preparation, heated in open vessels to a temperature considerably below redness, deflagrates with a hissing noise, sometimes detonating like gunpowder Platinum black is obtained also when platinum is precipitated by other metals from a dilute solution, or when such a solution is treated with reducing agents Thus, for instance, if a solution of platimc chloride be allowed to drop into a boiling mixture of three volumes of glycerol and two of caustic potash of specific gravity 1 O8, the black obtained possesses extremely active properties,[3] as does that prepared by the reduction of platimc chloride by means of formaldehyde [4] A very active platinum black is also produced by adding a boiling solution of chloroplatimc acid neutralised with sodium carbonate to a boiling solution of sodium formate By the action of dilute hydrochloric acid or boiling neutral liquids, it is converted into , a greyish-black modification which is an intermediate stage between platinum black and spongy platinum and this is

[1] Feulgen, *Ber*, 1921, 64, [B], 36O
[2] *Pogg Ann* , 1829, 17, 1O2
[3] Zdrawkowitch, *Bull Soc chim*, 1876, [2], 26, 198
[4] Loew, *Ber*, 189O, 23, 289

reconverted into the black variety by treatment with sodium formate in slightly aikalme solution [1]

According to Liebig, platinum black absorbs more than 800 times its volume of oxygen, whereas the black prepared by Mond, Ramsay, and Shields was found to absorb 100 volumes of oxygen When brought into hydrogen 310 volumes were taken up, 200 of which united with the oxygen present to form water, whilst the remaining 110 were absorbed[2] A certain amount of occluded oxygen can, however, coexist with occluded hydrogen in platinum black It appears probable that platinous hydroxide is formed by the absorption of oxygen, since the heat of occlusion of oxygen by the black is almost identical with the heat of formation of platinous hydroxide [8] Platinum black after absorbing oxygen dissolves partially in hydroch between the loss of weight of the black and the amount of platinum in solution also corresponds to the formation of this hydroxide [4] Moreover, the black containing oxygen is able to bring about oxidising actions similar to those produced by platinous oxide, such as the liberation of iodine from potassium iodide, and the oxidation of arsenious to arsenic acid [5] After frequent ignition in a mixture of combustible gas and air, the black becomes denser, approaching spongy platinum in its properties Heat alone also affects its behaviour[6] Platinum black is frequently used in organic chemistry as an oxidising agent, and it has been successfully applied in place of oxide of copper in organic analysis [7]

Platinum black also absorbs hydrogen It dissolves about 16O volumes, whereas platinum sponge does not absorb more than 1 volume The maximum solubility is at O°, there being a decrease on either side of this temperature, the solubility of hydrogen in platinum sponge, on the other hand, increases with temperature.[8] Owing to its power of absorbing hydrogen,

[1] **Gutbier and Maisch,** ***Ber,*** **1919, 52, [23], 1368**

[2] ***Proc Roy Soc,*** **1895, 58, 242**

[3] **Mond, Ramsay, and Shields,** ***Proc Roy Soc,*** **1897, 62, 6O**

[4] **Engler and Wohler,** ***Zeit anorg Chem,*** **19O1, 29, 1, WohlerJ** ***Ber,*** **19O3, 36, 3475**

[5] **See also Rasehig,** ***Zeit angew Chem,*** **19O6, 19, 1748, 2O83, Bredig,** ***ibid,*** **1985, Luther,** ***ibid,*** **2049**

[6] **See Wright and Smith,** ***Journ Chem Soc*** **, 1921,119, 1683**

[7] **Kopfer,** ***Journ Chem Soc*** **, 1876, 29, 66O, 1877, 31, 228, Dennstedt,** ***Ber*** **, 19O6, 39, 1623**

[8] **Gutbier and Maisch,** ***loc cit***

platinum black brings about a number of reductions also,[1] Especially the hydrogenation of unsaturated organic compounds Its activity is reduced by previous heating, and it is thus possible, by first using mactive specimens prepared in this way, to reduce an unsaturated body in stages[2] Platinum black is also an active catalyst in the decomposition of many organic bodies[3]

Platinum black also absorbs 60 volumes of carbon monoxide, at the ordinary temperature, and this is liberated on heating[4]

Colloidal Platinum may be obtained as a dark brown solution by passing an electric arc between platinum wires immersed in water It may also be prepared in a similar manner to colloidal gold and silver by reducing platinic chloride with hydrazine hydrate in the presence of sodium lysalbate as protective colloid, and on evaporating the solution and drying at 100° black, glistening scales of colloidal platinum are obtained which are soluble in water[5] Similar solutions are obtained by reducing solutions of platinum salts with other reducing agents, and in the presence of other protective colloids[6]

Colloidal platinum is a very active catalyst It is capable of causing the union of oxygen and hydrogen[7] It rapidly decomposes hydrogen peroxide and even minute quantities have a marked effect[8] By measurement of the rate of decomposition in the presence of different colloids, their protective action on colloidal platinum has been determined and gelatine found to have the most effect[9]

The colloidal solution absorbs hydrogen and is therefore very active in effecting reduction Ferric salts may be reduced to the ferrous state and tetravalent titanium salts and molybdic

[1] See Loew and Aso, *Bull Coll Agr Tokyo Imp Univ*, 1906, 7, 1

[2] Vavon, *Compt rend*, 1914, **158,** 409, 1921,**173,** 360

[3] See Oliven Mandaia, *Gazz* , 1920, **50,** n, 81

[4] Hemptinne, *Zeit physikal Chem*, 1898, 27> 429

[5] Paal and Amberger, *Ber*, 1904, 37, 124

[6] Gutbier, *Zeit anorg Chem*, 1902, 32, 347, *J pr Chem*, 1905, [2], **71,** 358, Hennch, *Ber* , 1903, 36, 309, Garbowski, *ibid* , 1215, Gutbier and others, *Kolloid Zeit*, 1916,**18,** 1, *ibid* , 1916,**19,** 298, Amberger, *ibid* , 1913,13, 310

[7] Ernst, *Zeit physikal Chem*, 1901, 37, 448, Paal and Hartinann, *J pr Chem*, 1909, [2], **80,** 337, Paal and Schwarz, *ibid*, 1916, [2], 93, 106

[8] Bredig, *Zeit angew Chem*, 1898, 951, *Zeit physikal Chem*, 1901, 38, 122, Bredig and von Berneck, *ibid*, 1899, 31, 353, Bredig and Ikeda, *ibid*, 1901, 37, 1, Raudnitz, *ibid*, 1901, 37, 551, Rocasolano, *Compt rend*, 1920, **170,** 1502, *Anal Fis Quim* , 1920, **18,361,** Maclnnes, *J Amer Chem Soc*, 1914, 36, 878

[9] Groh, *Zeit physikal Chem*, 1914, **88,** 414, Iredale, *Journ Chem Soc*, 1921, **119,** 109

acid are similarly reduced [1] The solution is useful in the hydrogenation of unsaturated organic compounds, thus acetylene may be reduced to ethylero, and this, in turn, to ethane [2] Many oils may likewise be hardened in much the same way as when nickel is used as catalyst The colloid is incapable of bringing about hydrogenation even of the most reactive compounds if it is completely freed from oxygen, and such deoxygenated platinum may be revivified by shaking with oxygen The catalytic activity has therefore been ascribed to the presence of an oxide, , which is assumed to form a compound with the hydrogen, and this compound readily gives it up to the reducible substance, and is again re-formed [3] The oxides formed by fusing chloroplatinic acid with sodium nitrate are very active in the catalytic reduction of organic compounds[4] The role of the oxide m catalysis has, however, been demed [5]

Colloidal platinum is "poisoned" by many substances, notably hydrogen sulphide, hydrogen cyanide, carbon monoxide and dioxide, and acetylene[6] The catalytic activity is also gradually lost by exposure to ultra-violet light[7]

The colloidal particles of platinum are spherical in shape [8] and are negatively charged The solution is precipitated by electrolytes [9] and by many metals The efficiency of the metal as a precipitant increases with its electropositive character, and the action is due to the absorption of metallic ions by the colloid particles the charges on which are thereby neutralised[10] The sol is also coagulated by exposure to sunlight[11] or ultra-violet light[12]

[1] *Eggert,Zeit Elektrochem,* 1914,20,370, 1915, 21, 349, Paal and Buttner, *Ber* , 1915, 48, 220, Loew and Aso, *Bull Coll agr Tokyo Imp Umv* , 1906, 7, 1

[2] Paal and Schwarz, *Ber,* 1915, 48, 994, 1195

[3] Willstatter and Jaquet, *Ber,* 1918, 51, 767, Willstatter and Wald schmidt Leitz, *Ber* , 1921, 54, *B,* 113 See Rocasolano, *Compt raid* , 1921, **173,** 41, 234

[4] Voorhees and Adams, *J Amer Chem Soc* , 1922, 44, 1397

[5] Skita, *Ber* , 1922, 55 [B], 139

[6] Bredig and Ikeda, *Zeit physikal Chem,* 1901, **37,** 1, Paal anu Schwarz, *Ber,* 1915, 49, 1195, Kruger and Taege, *Zeit Elektrochem,* 1915, 21, 562

[7] Farmer and Parker, *J Amer Chem Soc* , 1913, 35, 1524

[8] Gans and Calatroni, *Ann Physik,* 1920, [4], 61, 465

[9] Pappada, *Zeit Chem Ind Kolloide,* 1911, 9, 270

[10] Spear and Kahn, *J Amer Chem Soc,* 1918, 40, 181

[11] Ganguly and Dhar, *Kollotd Zeit,* 1922, **31,** 16

[12] Spear, Jones, Neave, and Schlager, *J Amer Chem Soc* , 1921, 43, 1385

Platinum is scarcely oxidised at any temperature by oxygen, Water, or nitric acid. If very thin platinum foil be heated in .oxygen for some weeks at 420-450° it becomes covered with a small quantity of platinous oxide, whilst platinum sponge is more quickly converted into this oxide in the same manner[1]

It is appreciably attacked by sulphuric acid [2] at 250°, although very slightly so below 200°, and dissolves to a small extent when used for the electrodes in the electrolysis of sulphuric acid, especially when alternating currents are employed[3] The dissolving of platinum by sulphuric acid is accounted for by the presence of oxygen formed by dissociation of the acid, and is prevented by the presence of reducing agents, such as sulphur dioxide or arsenious or antimonious oxides [4] It is not attacked by sulphur alone, although action takes place if alkalis are present These latter, as well as nitre, oxidise the metal, and for this reason fusion with alkalis or mtre ought not to be performed in platinum vessels [5] It dissolves in potassium cyanide solution in the absence of oxygen with evolution of hydrogen, the amount dissolved being very small in the cold but increasing on heating[6] Alkali cyanides should not be fused in contact with platinum, as these likewise attack the metal It is also inadvisable to expose platinum vessels to direct contact with burning charcoal, as the silicon reduced from the charcoal-ash "unites with the metal, making it brittle and liable to crack Especially to be avoided is contact at a high temperature with compounds of the easily reducible metals, as these readily form fusible alloys with the platinum Phosphorus and arsenic also combine with heated platinum When platinum vessels are heated over a smoky flame, or in one in which the supply of air is insufficient to bring about complete combustion, such as the internal zone of a Bunsen burner, the surface of the platinum becomes disintegrated, possibly owing to the successive formation and decomposition of compounds of the metal with carbon from the flame, or, more probably, owing to the

[1] Wohler, *Ber*, 1903, 36, 3475

[2] Conroy, *J Soc Chem Ind*, 1903, 22, 465

[3] Margueles, *Ann Phys Chem*, 1898, [2], 65, 629, 66, 540, Ruer, *Zeit Elektrochem*, 1903, 9, 235, 1905, 11, 10, Brochet and Petit, *Compt rend*, 1905, **140,** 655, *Zett Elektrochem*, 1905, 11, 441, Senter, *Trans Faraday Soc*, **1907,** 2, 1

[4] McCay, *Eighth Inter Cong App Chem* , 1912, 1, 351

[5] See Nicolardot and Chatelot, *Bull Soc chim*, 1919, [4], 25, 4

[6] Glaser, *Zett Elektrochem*, **1903, 9, 11**, Wohler, *Ber*, **1903, 86, 3475**

action of the carbon disulphide present in the gas, for platinum takes up sulphur from* this compound even at 100° [1]

The best method of cleaning a platinum crucible is to fuse in it some potassium bisulphate (Gmelin), and in order to test whether a new platinum crucible be of proper quality it is first boiled with hydrochloric acid and afterwards with pure nitric acid. If none of the metal be dissolved the platinum is good The surface of a platinum crucible is best cleaned by being rubbed with moist animal charcoal

Platinum forms alloys with a number of other metals and also an amalgam with mercury

Platinum is largely used in dentistry, and also in jewellery, principally for the setting of stones For both these purposes, however, it is now being displaced by palladium It is also employed largely in the electrical industry, and its salts are applied in photography for the preparation of printing papers which yield exceptionally permanent and beautiful prints It is also employed as a catalyst in many reactions, notably in the manufacture of oleum (Vol I, p 433) It is used for protecting other metals, and a pure white deposit is obtained by using a boiling solution of 4 grams of chloroplatinic acid, 20 grams of ammonium phosphate, 90 grams of sodium phosphate, and 5 grams of sodium chloride per litre [2] The electro-deposition of platinum is known as " platinising " The process is used to obtain a velvety-black coating on the electrodes of conductivity cells by employing the following solution 3 grams of platinic chloride, O O2-O O3 gram of lead acetate, and 100 c c of water.

COMPOUNDS OF PLATINUM

PLATINUM AND OXYGEN

640 Three oxidesof this metal are definitely known platinum monoxide or platinous oxide, PtO, giving rise to the platinous salts, platinum dioxide or platinic oxide, PtO_2, giving rise to the platinic salts, and the trioxide, PtO_3 In addition, a sesquioxide, Pt_2O_3, and an oxide, Pt_{304}, have been described, but doubt has been thrown on their existence

Platinum Monoxide, PtO, is obtained as a grey powder by the careful ignition of the hydroxide, or as a violet powder by

[1] **Myhus and Huttner,** ***Zeit anorg Chem*** **, 1916, 95, 257**
[2] **Nikolaus,** ***Zeit Elecktrochem,*** **1914, 21, 193**

igniting the compound of platinic oxide and lime *{vide inf)*, and treating the residue with nitric acid It is also probably formed to some extent as already mentioned when platinum is heated for some time in oxygen (Wohler) When strongly heated it passes into the metal, deflagrating when heated with charcoal It is reduced to platinum black when heated with aqueous formic acid, CH_{202}, with violent evolution of carbon dioxide

Platmous Hydroxide, $Pt(OH)_2$, is obtained by decomposing the dichloride with hot caustic potash The whole of the chlorine cannot, however, be removed in this way, and if caustic soda be employed, a product is obtained from which the soda cannot be completely washed out (Liebig) It is prepared in the pure state by mixing one part of potassium platinochloride, K_2PtCl_4, with twelve parts of water, adding the exact quantity of dilute caustic soda necessary for decomposition, and heating the mixture to boiling until the alkaline solution has become neutral The hydroxide retains its water in a remarkable manner, one sample contained 6 6 per cent of water after heating for several days at 405° (Wohler)[1] It dissolves in hydrochloric, hydrobromic, and sulphurous acids, but not in other oxy-acids Boiling caustic potash decomposes it into metal and the dioxide It is an oxidising agent and acts as a weak base, of which the halogen salts, as well as a few double salts of the oxy-acids, have been prepared.

Platinum Dioxide, PtO_2, is obtained as a black powder by gently heating the corresponding hydroxide

Platinum Hydroxide or *Platinic Hydroxide* is prepared by boiling a solution of platinic chloride with caustic potash, when a basic double salt is precipitated, and this is treated with acetic acid in order to dissolve out the alkali In this way it is obtained as an almost white precipitate, which on drying becomes yellow This is termed *platinic acid* and probably has the composition[2] $H_2Pt(OH)_6 = PtO_2,4H_{20}$, analogous to platinichlonc acid, H_2PtCl_6 Platinic hydroxide acts both as a weak base and as an acid-formmg oxide It dissolves in alkalis and the solutions deposit crystalline *platinates* such as $K_2Pt(OH)_6$ isomorphous with the stannates[8], they do not lose water at 100-110°, and their solutions give with silver acetate a precipitate of

[1] ***Zat anorg Chem*, 1904, 40, 423**

[2] **Beliuoci, *Atti B Accad Lincei*, 1903, [5], 12, n , 635, Wohler, *Zeit anorg Chem*, 1904, 40, 423, compare Blondel, *Ann Chim Phya*, 1905, [8], 6, 81.**

[3] **Bellucci and Parravano, *Atti R Accad Lincei*, 1905, [5], 14, I , 459**

$Ag_2Pt(OH)_6$ A reddish-yellow, partially crystalline powder of the composition $Na_{20},3Ert;O_{2l}6H_{20}$ is obtained when a clear aqueous mixture of platinichloric acid and sodium carbonate is exposed to sunshine, or when the mixture is heated for some time at 100° The aqueous solution of the two salts may also be evaporated to dryness, and the residue boiled out with water, when a denser precipitate of the same compound is obtained having an ochre-yellow colour A compound of the composition $Na_{20},5PtO_2,9H_{20}$ has also been obtained (Blondel) When an excess of lime water is added to a solution of platinic chloride and the mixture exposed to sunlight, a white or yellowish pulverulent precipitate falls down, to which the name of calcium platinate has been given,[1] its composition corresponding approximately to the formula $CaPt_{205},CaCl_{2j}7H_{20}$ If the hydroxide is boiled with a solution of a polymolybdate, or a polytungstate, salts are formed of the complex acids, platinmolybdic acid $H_8PtMo_{10}O_{36}$, and platintungstic acid, $H_8PtMo_{10}O_{36}$ These acids and their salts form yellow or greemsh crystals[2]

Platino-platinic Oxide, Pt_3O_4, is obtained as a black, insoluble powder by heating sodium platinichlonde with sodium carbonate and extracting with water,[3] whilst *platinum sesquioxide*, Pt_2O_3, is obtained as a dark brown powder[4] by heating spongy platinum with sodium dioxide, neutralising the alkali, washmg, and drying at 450° According to Wohler, however, these substances are not definite oxides, only two oxides of platinum exist, and these readily form colloidal solutions and retain foreign matter on precipitation

Platinum Trioxide, PtO_3, is obtained by the electrolysis of a solution of platimc hydroxide in 22V-potassmm hydroxide A compound of the composition $K_{20},3PtO_3$ is thus obtained, which, when treated with cold acetic acid, yields the trioxide as a brown powder It readily loses oxygen and slowly evolves chlorine from dilute hydrochloric acid[5]

PLATINUM AND THE HALOGENS.

641 *Platinum Tefrafluonde*, PtF_4, is formed when platinum wire is heated to dull redness in a current of fluorine It is thus

[1] Herschel, *Phil Mag*, 1832, [2], 1, 58
[2] Gibbs, *Ber*, 1877, 10, 1384
[3] Jorgensen, *J pr Chem*, 1877, [2], 16, 344
[4] Dudley, *Amer Chem J*, 1902, 28, 59
[5] Wohler and Martin, *Ber*, 1909, 42, 3326

obtained as a deep red-coloured, fused mass, which yields chamois-yellow crystals It is extremely hygroscopic, and when added to water it first gives a tawny coloration, then heat is rapidly developed and decomposition occurs with formation of hydrogen fluoride and hydrated platinum dioxide Very dilute solutions are more stable, but the same reaction takes place iminediately if they are heated When the anhydrous substance is heated it yields fluorine and leaves crystalline platinum [1]

In the preparation of the tetrafluonde the *difluoride,* PtF_2, is also formed in small quantities as a greenish-yellow, insoluble substance

Phosphorus pentafluonde acts on spongy platinum at a red heat to form volatile crystals of the formula PF_3,PtF_2 [2]

Platinum Monochloride, PtCl —When a solution of potassium platinichlonde in 10,000 parts of water is heated for some days, a yellow, non-crystallme precipitate is formed which probably consists of hydrated platinum monochlonde,[3] PtCl

Platinous Chloride or *Platinum Dichlonde,* $PtCl_2$, is formed when platinichloric acid, H_2PtCl_6, obtained by dissolving the metal in aqua regia and crystallising, is heated to 300°, or when spongy platinum is heated in a current of dry chlorine to between 240° and 250° [4] It is a greenish-grey powder, having a specific gravity of 5 87 It is not readily moistened with water, and is insoluble in this liquid On heating it decomposes into platinum and chlorine [5]

Platinum dichloride unites with phosphorus trichloride to form the compound $PtCl_2,PCl_3$, which is obtained by heating spongy platinum with pentachlonde of phosphorus to 250° The product is easily soluble in benzene or chloroform, and crystallises therefrom in fine brown needles When these are dissolved in water and the solution is evaporated in a vacuum, orange-yellow, deliquescent prisms of *chloroplatinophosphorous acid,* $PtCl_2,P(OH)_3$, are obtained This has an acid metallic taste, and yields a white precipitate with silver nitrate and a yellow one with lead acetate Corresponding salts of the alkali metals have not been prepared, since hydroxides and carbonates decompose the acid

[1] Moissan, *Compt rend,* 1889, **109,** 807, *Ann Chim Phys,* 1891, [6], 24, 287

[2] Moissan, *Bull Soc chim,* 1891, [3], 5, 464

[3] Sonstadt, *Proc Chem Soc* , 1898, 25 See also Wohler and Streicher, *Ber,* 1913, 46, 1591

[4] Schtitzenberger, *Ann Chim Phys,* 1870, [4], 21, 351

[5] See Shenstone, *Journ Chem, Soc,* 1892, 61, 450

The foregoing compound readily takes up another molecule of phosphorus trichloride, forming $PtQ_2,2PCl_3$, which may likewise be crystallised from chloroform or benzene in large, deliquescent prisms, these melt at 160°, and when strongly heated give off phosphorus trichloride. If they are allowed to remain in contact with water at a winter temperature, or if their solution be evaporated at a low temperature in a vacuum, very deliquescent, yellow needles are obtained of *chloroplalmodiphosphorous avid,* $PtCl_2,2P(OH)_8$, and this readily undergoes decomposition at 12°, with evolution of hydrogen chloride, into the compound $PtC10P_2(OH)_5$ This latter forms white crystals, is less deliquescent than the former compounds, and when heated to 150° is converted into a light yellow, non-deliquescent powder having the composition $PtC10_2P_2(OH)3$ The solution of this compound, like the preceding, is precipitated by silver nitrate [1]

Carbonyl Platinochlondes or *Chloroplatinites*—When platinous chloride is heated to a temperature of 250° in a current of carbon monoxide there are formed $PtCl_2,2COCl_2$, $PtCl_2,CO$, $PtCl_2,2CO$, $2PtCl_2,3CO$. The last named is produced in largest quantity and is obtained pure by boding the crude product with carbon tetrachloride In this way fine orange-yellow needles melting at 130° are obtained, these when heated to from 250° to 260° in dry carbon dioxide yield the compound $PtCl_2,CO$ in fine needles which melt at 194° and may be partially sublimed in a current of dry carbon dioxide at 240° At 300° they decompose mto carbonyl chloride, $COCl_2$, and platinum When this compound, or the crude product, is heated to 150° in carbon monoxide, the compound $PtCl_2,2CO$ sublimes in white needles which melt at 1420 [2] All these compounds are decomposed by water to give the metal, carbon dioxide, and hydrochloric acid

642 *The Plattriochlondes* or *Chloroplatinites* —The solution of platinous chloride in hydrochloric acid may be regarded as *platinochlonc* or *chloroplatinous acid,* $H_2[PtCl_4]$ The potassium salt is the usual starting point for the preparation of this compound and its salts [3]

Potassium Platinochloride, K_2PtCl_4—This salt, wLch was

[1] Schutzenberger, *Bull Soc chim,* 1872, [2], **17,** 482, **18,** 153, Rosenheim and Lowenstamm, *Zeit anorg Chem,* 1903, **37,** 394

[2] Schutzenberger, *Ann Chim Phys,* 1868, [4], **15,** 100, and 1870, 21, 325, Pulhnger, *Journ Chem Soc* , 1891, **59, 598.**

[3] Thomsen, *J pr Chem,* **1877,** [2], **15, 294.**

first prepared by Magnus,[1] is easily obtained by adding moist cuprous chloride to a thick paste of potassium platinichlonde, KgPtClg, and water, in such quantity that a small portion remains unreduced On cooling the filtered liquid, the greater portion of the platinochlonde separates out, the mother-liquor yielding a second crop on concentration, whilst the remainder of the salt is precipitated from the last portion of the liquor with alcohol These various crops are £hen washed with alcohol, and the pure salt is obtained by recrystallisation from hot water It forms soft, rose-coloured, crystalline fibres It may also be prepared by reducing a hot solution of platinichloric acid with sulphur dioxide until a sample gives no precipitate with ammomum chloride, and then adding a hot solution of potassium chloride On cooling, potassium platinochlonde separates out and is washed with alcohol and dried in absence of light[2] When the requisite quantity of platinichloric acid is added to the hot saturated solution of this salt potassium platinichlonde is precipitated and an almost pure solution of platinochloric acid, H_2PtCl_4, is obtained The same acid is produced by treating the barium salt with dilute sulphuric acid On evaporation in a vacuum over sulphuric acid or caustic potash, a solid compound separates out which dries with loss of hydrogen chloride, forming a brown, amorphous mass of $H_2Pt(OH)Cl_3,H_{20}$[3] By dissolving oxides, hydroxides, carbonates, or chlorides in the acid a series of compounds is obtained (Nilson)

Ammonium Platinochlonde, $(NH_4)_2PtCl_4$, described first by Vauquelin and afterwards by Peyronne, crystallises from solution in hot water in large, red, four-sided prisms or in thin tablets

Most of the other platinochlondes crystallise with water in fine red or brown crystals which are often deliquescent, some, such as the silver salt, Ag_2PtCl_4, and the lead salt, $PbPtCl_4$, are flesh-coloured precipitates

Platinum Trichloride, $PtCl_3$ is obtained by heating platinic chloride in dry chlorine at 390°. It is a dark green, nearly black powder, which dissolves very slowly in cold water but more readily on boiling to give a reddish-brown solution. Hot concentrated hydrochloric acid decomposes it into a mixture of the dichloride and tetrachloride.[4]

[1] *Pogg Ann,* 1828,**14, 241**
[2] Klason, *Ber,* 1904, 87, 1360
[3] Nilson, *J pr Chem,* 1877, [2], 16, 260
[4] Wohler **and** Martin, *Ber ,* 1909, 48, 3958

Platinic Chloride or *Platinum Tetrachloride*, $PtCl_4$.—When metallic platinum is heated in a current of chlorine it is attacked and this compound is slowly formed The action diminishes when the temperature is raised, as the tetrachloride decomposes into metal and chlorine at 370° d* If, however, the temperature be raised to 1300°, the formation of tetrachloride recommences, and if an excess of chlorine be employed and the temperature raised to 1700°, the action becomes rapid and a yellow sublimate of tetrachloride is deposited[2] The same reaction occurs if a spiral platinum wire be heated by an electric current nearly to its melting point in a stream of chlorine At the thick end of the wire crystals of metallic platinum are deposited These are not formed owing to any volatility of the metal, but are produced by the alternate production and decomposition of the tetrachloride[3] The anhydrous chloride is formed also when crystalline platimchlonc acid is dried over sulphuric acid and then heated to 369° in a current of chlorine,[4] or at 165° in a current of hydrogen chloride [5]

By mixing solutions of aqueous platimchlonc acid and silver nitrate in the proportion of one molecule of the former to two of silver nitrate, a precipitate of silver platimchlonde is thrown down, which is decomposed by hot water into silver chloride and platinic chloride The yellowish-red solution yields on evaporation over sulphuric acid fine, red, apparently monocknic, crystals of the composition $PtCl_4,5H_{20}$ They are not deliques-cent, and their concentrated solution is only slowly precipitated by ammonium chloride on standing[6] The crystals are con-verted by ammonia into the acid $PtQ(OH)_3$ [7] According to Miolati, platinum tetrachloride in aqueous solution is present as the dibasic acid, $H_2PtCl_4(OH)_2$, and salts have been prepared corresponding to this acid which are amorphous powders [8]

Hydrates containing one, four, and seven molecules of water have also been prepared

Platinichlonc Acid or *Chloroplatimc Acid*, $H_2[PtCl_6]$ —This

[1] Wohler and Streicher, *Ber*, 1913, 46, 1591

[2] Troost and Hautefeuille, *Compt rend*, 1887, 84, 946, Langer and Meyer, *Pyrochem Untersuchungen*, p 57

[3] Hodgkmson and Lowndes, *Nature*, 1888, 38, 6

[4] Pigeon, *Compt rend*, 1890, **110,** 77, 1891, **112,** 1218, *Ann Chim Phys* , 1894, [7], 2, 433, Gutbier and Heinnch, *Zeit anorg Chem* , 1913, 81, 278

[5] Pulknger, *Journ Chem Soc* , 1892, 61, 422

[6] Norton, *ibid* , 1872, **25,** 680

[7] Jorgensen, *J pr Chem*, 1877, [2], 16, 345

[8] *Zeit anorg Chem*, **1900, 22, 445** See also Kohlrausch, *Zeit physikal Chem* , **1900,** 83, **257**

compound, which is often erroneously called platinum chloride, is obtained by dissolving the metal in aqua regia and evaporating with hydrochloric acid until all nitric acid is removed[1] It crystallises in brownish-red, very deliquescent prisms having the composition $H_2PtCl_6,6H_{20}$ If the solution be repeatedly evaporated with aqua regia, nitrosoplatinic chloride, $(NO)_2PtCl_6$, is formed This crystallises in small, orange-coloured cubes and is very deliquescent, dissolving in water with evolution of nitric oxide Chloroplatinic acid made by the action of aqua regia on platinum may therefore be contaminated with this compound if the evaporation with hydrochloric acid be not carried far enough Pure chloroplatinic acid may be obtained by treating platinum black, which has not been lgnited, with hydrochloric acid at 50° to 60°, and slowly adding hydrogen peroxide when chlorine is evolved and the platinum passes into solution[2] Platinum sponge may also be dissolved in hydrochloric acid saturated with chlorine[3] Platinum in any form is readily attacked by a mixture of chloric and hydrochloric acids[4] The acid may also be prepared by electrolysing a suspension of finely divided platinum in concentrated hydrochloric acid between platinum electrodes, when the chlorine evolved at the anode attacks the finely divided metal, forming platinic qhlonde, which dissolves in the hydrochloric acid to form chloroplatinic acid[5]

The hydrogen in platinichloric acid can be readily replaced by metals, giving a series of crystalline salts termed the *platinichlorides* or *chloroplatinates*, of which the most important are those of the alkali metals, their widely differing solubilities rendering them very valuable in analytical chemistry

Potassium Platinichloride or *Potassium Chloroplatinate*, K_2PtCl_6, is thrown down, on the addition of potash or a potassium salt to the acid, in the form of a yellow, crystalline precipitate which is deposited from solution in hot water in the form of small, reddish-yellow octahedra, having a specific gravity of 3 586 It undergoes hydrolysis, very rapidly even in the dark with concentrated solutions, but only on exposure to hght in dilute solution[6]

[1] See Tingle and Tingle, *J Soc Chem Ind*, 1916, 86, 77
[2] Rudnick and Cooke, *J Amer Chem Soc* , 1917, 39, 633
[3] Dittinar and MaoArthur, *Trans Hoy Soc Edxn* , 1888, **33,** [2], 561
[4] Zappi, *Anal Fts Quim Argentina*, 1915, 8, 68
[5] **Weber, *J. Amer. Chem. Sec*, 1908, 30, 29**
[6] **Archibald, *J. Chem, Soc.*, 1920,117,1104.**

It is insoluble in a saturated solution of potassium chloride as well as in alcohol. It disolves in caustic potash and is precipitated from the solution on the addition of acids

Sodium Platinichloride, $Na_2PtCl_6,6H_{20}$, is obtained by evaporating the acid with common salt, when light red, tnchnic prisms or tablets are deposited which have a specific gravity of 2 499 These become anhydrous at 100°, falling to a yellowish-red powder, readily soluble in water and alcohol.

Lithium Platinichloride, $Li_2PtCl_6,6H_{20}$, crystallises in large, efflorescent, orange-yellow plates, easily soluble in water and in a mixture of alcohol and ether, but not in pure ether

Rubidium and Cæsium Platinichlondes, Kb_2PtCl_6 and Cs_2PtCl_6, closely resemble the potassium salt, but are less soluble One hundred parts of water dissolve the following amounts of the three salts

At	20°	40°	60°	80°	**100°**	
K_2PtCl_6		112	176	2 61	3 79	518 parts
Rb_2PtCl_6		O 141	O 166	O 258	O 417	O 634 „
Cs_2PtCl_6		O O70	O142	O 213	O 291	O 377 „

Ammonium Platinichloride, $(NH_4)_2PtCl_6$, is obtained by precipitating the acid with an ammonium salt as a lemon-yellow, crystalline powder which crystallises from hot water in orange-yellow octahedra, these have a specific gravity of 3 O, and are indistinguishable in appearance from the potassium salt One hundred grams of water dissolve O 365 gram of the salt at O° and 3 25 grams at 100° [x] It is not soluble either in alcohol or ether, and scarcely soluble in a solution of ammomum chloride On heating, it decomposes without fusion, leaving pure platinum sponge behind [2]

Other acids and their corresponding salts have been prepared which may be regarded [3] as being intermediate between platimc acid, $H_2[Pt(OH)_e]$, and platinichloric acid, $H_2[PtCl_6]$, and to these compounds mav be ascribed formulae such as $H_2[Pt(OH)_5Cl]$ and $H_2[PtCl_6(OH);f$

Platinous Bromide, $PtBr_2$, is obtained by heating platini-bromic acid to 280°, and forms a brown mass which' dissolves with a brownish-red colour If boiling saturated solution of potassium platinichloride and potassium bromide are mixed,

[1] Archibald and Kern, *Trans Roy Soc Canada,* **1917-18,** [3], **11, 7**

[2] **See Wichers,** / *Amer Chem Soc* , **1921,43, 1268**

[3] **Miolati and Bellucci, *Atti B Accad Lincet,* 1900, [5], O, 11, 140, 1903, [5], 11, 11 , 241, 271, Ruff and Jeroch, *Ber,* 1913, 46, 920.**

double decomposition occurs, and the potassium chloride may be separated from the *potassium platinobromide,* K_2PtBr_4, by crystallisation The latter forms large, nearly black pyramids or brownish-red needles (Thomsen) It unites with carbon monoxide, forming a compound, $PtBr_2$,CO (Pulhnger).

Platinic Bromide, $PtBr_4$—Bromine acts upon platinum at different temperatures in the same way as chlorine The tetra-bromide is best obtained by heating spongy platinum witb bromine and hydrobromic acid to 180°, evaporating the solution, and drying the residue at 180° It is a brownish-black, deliquescent powder, nearly insoluble in water, but readily soluble in alcohol and ether, yielding a brown solution [x] When platinum is dissolved in a mixture of nitric and hydrobromic acids, and the concentrated solution allowed to evaporate over quick lime, dark red, monoclmic prisms of *platinibromic acid,* $H_2PtBr_6,9H_{20}$, are deposited, which are very deliquescent The compound is also made in the pure state by evaporating pure platinic chloride several times with concentrated hydrobromic acid on the water-bath[2] This acid gives rise to a series of platini-bromides corresponding to the platinichlorides, most of which possess a red colour

Platinous Iodide, PtI_2, is formed by warming the chloride with a solution of potassium iodide, or, with liberation of iodine, when excess of potassium iodide is added to a solution of potassium platinichlonde This reaction has been used as a method of estimating platinum[3] It is a black powder closely resembling lamp-black in appearance It forms a carbonyl, PtI_2,CO

Platinic Iodide, PtI_4, is a black or brownish-black, amorphous powder obtained by the action of hydnodic acid on a soluble platinichlonde *Platiniodic acid,* $H_2PtI_6,9H_{20}$, easily decomposes into water, hydnodic acid, and platimc iodide The *platiniodides* are brown, and possess a metallic lustre, they are soluble in water, and are very unstable, giving off lodme at a temperature below 100°

PLATINUM AND THE ELEMENTS OF THE SULPHUR GROUP

643 *Platinum Monosulphide,* PtS, is formed when platinum sponge is heated with sulphur in a vacuous glass tube, or when

[1] **V Meyer and Zublm, *Ber*, 1880, 13, 404, Halberstadt, *tbtd*, 1884, 17, 2962**

[2] **Gutbier, Krauss, and von fuller, *Chem Zentr*, 1914, [1], 1162**

[3] **Peterson, *Zett anorg Chem*, 1898,19, 59**

platinous chloride is fusea with sodium carbonate and sulphur, and the mass extracted with water It forms a green powder or a mass of glistening needles [1] When heated in the air it decomposes, leaving a residue of platinum, and when lgnited in

hydrogen it yields sulphuretted hydrogen and spongy platinum The carbonyl, PtS,CO, is precipitated by the action of hydrogen sulphide on a solution of $PtCl_2$,CO

« *Platinum Disulphide,* PtS_2, is formed as a steel-grey powder by heating ammomum platinichlonde with sulphur to a dark red heat When sulphuretted hydrogen is passed through a solution of a platinic salt a black precipitate of sulphide is first formed, but this by further action of the gas becomes light brown, from formation of hydrogen platinum sulphide, a compound which on exposure to the air again gives off sulphuretted hydrogen The disulphide may be obtained pure by precipitating a solution of potassium platinichlonde at 90° with sulphuretted hydrogen, and drying at 70-80° in an atmosphere of nitrogen [2] The precipitation of platinum by hydrogen sulphide is not quantitative owing to the formation of a stable colloidal solution of the sulphide The hydrosol is, however, converted into an insoluble hydrogel in the presence of magnesium chloride [3]

Platinum disulphide combines with basic sulphides and therefore dissolves in the sulphides of the alkali metals

Potassium Platinoihioplatinate, $K_2Pt_4S_6 = K_2S,3PtS,PtS_2$, is obtained by fusing together platinum sponge, potash, and sulphur, and lixiviating the mass with water It then separates in the form of hard, six-sided tablets, which on heating in the air burn like tinder Dilute sulphuric acid converts it into $H_2Pt_4S_6$, and this on exposure to air oxidises to *platinum sesqiasulphide,* Pt_2S_3, forming a steel-grey, crystalline powder

Di-sodium Platinothioplatinate, $Na_4Pt_3S_6 = 2Na_2S,2PtS,PtS_2$, is obtained in a similar way to the preceding compound, and forms pale copper-red, thin, crystalline needles which are converted by hydrochloric acid, without alteration of form, into a reddish-brown compound, $H_4Pt_3S_6$, which oxidises extremely quickly in the air to give the sesquisulphide [4]

A compound of the formula $PtS_{15}(NH_4)_2,2H_{20}$ has been

[1] **Debray and Deville,** ***Compt rend*** **, 1879, 89, 587**

[2] **Antony and Lucohesi,** ***Gazz,*** **1896, 26, i, 211**

[3] **Ivanov,** ***J Puss Phys Ghent Soc,*** **1916, 48, 527 See also Gaze,** ***Chem Zentr*** **, 1913, [1], 464**

[4] **Schneider,** ***Pogg Ann,*** **1866,188, 604.**

prepared by the action of ammonium polysulphide on platinichloric acid,[1] and forms large, red, rhombic crystals

Potassium Platinosulphite, $K_6Pt(SO_3)_4,2H_{20}$—A solution of potassium platinochlonde becomes decolorised when warmed with acid potassium sulphite, the above salt separating out from the solution in yellowish or colourless needles Sodium salts precipitate *sodium platinosulphite,* $Na_6Pt(SO_3)_4,7H_{20}$, from this solution in microscopic needles *Ammonium platinosulphite,* $(NH_4)_6Pt(SO_3)_4$, is obtained by similar means

These compounds must be regarded as salts of complex acids, since they do not show the ordinary reactions for either platinum or sulphurous acid

Sodium platinothiosulphate, $Na_6Pt(S_{20}3)_4,10H_{20}$ —Reduction of sodium platinichlonde with excess of sodium hyposulphite gives a reddish-brown solution which on evaporation yields first a reddish-brown precipitate of complex sodium platinosulphites with sodium platinothioplatinate, $Na_2Pt_4S_6$, then reddish-brown crystals of $Na_4Pt(SO_3)_3(OH)_2,H_{20}$ and, finally, bright yellow crystals of sodium platinothiosulphate [2]

Platinic Sulphate, $Pt(SO_4)_2$, is obtained as a brown mass by acting on the hydroxide or chloride with sulphuric acid and evaporating the solution

Platinum Selenide—Spongy platinum when heated unites with selemum with incandescence, forming a grey, infusible powder, this, when heated before the blowpipe, loses the whole of its selenium Platinum also unites with tellurium[3] to form the tellundes, Pt_2Te, PtTe, and $PtTe_2$

PLATINUM AND THE ELEMENTS OF THE NITROGEN GROUP

644 *The Platinonitntes* or *Nitnto-platinites*—These compounds are probably analogous in composition to the ammoniacal derivatives corresponding to the platinous salts (p 1481) and behave, not as double salts, but as salts of a complex acid, since they do not show the usual reactions either of platinum salts or nitrites They were first described by Lang,[4] and afterwards investigated more completely by Nilson [5]

Potassium Platinonitnte, $K_2Pt(NO_2)_4$, is obtained when solu-

[1] **Hofmann and Hochtlen, *Ber*, 1903, 36, 3090**
[2] **Sailer, *Zeit anorg Chem* , 1921,116, 209**
[3] **Roessler, *Zeit anorg Chem*, 1897, 26, 405**
[4] ***J pr Chem*, 1861, 88, 415**
[5] ***Ber*, 1876, 9,1722, 1877,10, 934.**

tions of potassium nitrite and potassium platinochloride are warmed together It is twposited in the form of small, glistening, six-sided prisms, which dissolve in 27 parts of water at 15°, and at a higher temperature in a smaller quantity Alkalis do not precipitate platinum oxide, and sulphuretted hydrogen does not precipitate sulphide of platinum from its solution. When the solution is allowed to evaporate spontaneously, rhombic tablets having the composition $K_2Pt(NO_2)_4,2H_{20}$ separate out, which effloresce rapidly It readily combines with a molecule of chlorine or bromine,[1] and forms with dry liquid nitrogen peroxide the compound $K_2Pt(NO_2)_4,N_{204}$, and with cold concentrated hydrochloric acid the compound $K_2Pt(NO_2)_4,HCl$[2]

Stiver Platinonitrite, $Ag_2Pt(NO_2)_4$, is obtained when solutions of the potassium salt and silver nitrate are mixed On recrystalhsing the precipitated salt from hot water, large, yellow, glistening, monochnic prisms are obtained, which on heating decompose with incandescence and detonation

Barium, Platinonitrite, $,BaPt(NO_2)_4,3H_{20}$, is obtained by decomposing the silver salt with barium chloride It crystallises from solution in hot water in colourless octahedra If this salt be decomposed by dilute sulphuric acid, and the solution evaporated in a vacuum over caustic potash, microscopic crystals having the colour of chromium trioxide separate out, these possess, according to Lang, the composition $H_2Pt(NO_2)_4$ Nilson however, was unable to obtain this compound The solution yielded, on evaporation, a gummy mass and a green, glistening residue having the composition $H_4Pt_{30}(NO_2)_8,2H_{20}$, and this on neutralisation with potash and evaporation, yielded the potassium salt, $K_4Pt_{30}(NO_2)_8,2H_{20}$, in oblique, four-sided, glistening, light-yellow tablets

Fulminating Platinum — E v Meyer has examined a series of explosive compounds obtained by acting upon ammomum platinichlonde with potash, the existence of some of which was pointed out long ago by Proust and Doberemer Their constitution is as yet unknown, the yellow precipitate obtained on heating ammomum platinichlonde with potash has the composition $PtClNH_6O_2$[3]

[1] Blomstrand, *J pr Chem,* 1871, [2], 3, 207, Vezes, *Compt rend,* 1891, 112,616, 113,696

[2] Miolati, *Atti R Accad Lincei,* 1896, [5], 5, n , 355

[3] *J pr Chem,* 1878, [2], 18, 305

AMMONIACAL PLATINUM COMPOUNDS.

645 As already stated (p 1423), the various platinum salts are capable of forming complex compounds with ammonia The first of these compounds was obtained in 1828 by Magnus[1] by the action of ammonia on platinous chloride as a green, insoluble salt having the empirical composition $PtCl_2(NH_3)_2$ which is usually known as Magnus' green salt Gros[2] then obtained a series of light yellow or colourless salts by the action of nitric acid upon the green salt of Magnus Reiset[8] and Peyronne[4] independently found that by the action of ammonia on Magnus' green salt, or on platinous chloride, two other series of compounds could be obtained These were distinguished as the chlorides of Reiset's first and second bases. Peyronne showed that Magnus' salt is a platinichlonde of the second base Further investigations of these compounds, and theoretical speculations concerning their constitution, have been made by various other chemists[5]

These derivatives exist in two series, in which the platinum is divalent and tetravalent respectively

In the platinous series, the metal is capable of combining with or co-ordinating only 4 molecules or radicles to form the characteristic complex radicle, and the maximum number of external acid radicles is 2, since the platinum is divalent

In the platinic series, on the other hand, the metal, like chromium, is capable of forming a complex radicle with 6 molecules or radicles, but, platinum being in these salts tetravalent, the maximum number of external acid radicles is 4, instead of 3 as in the derivatives of trivalent chromium

It is characteristic of the platinum series that the free hydroxides from which the salts are derived are in many cases stable substances, whereas this is rarely the case in the chromium and cobalt series

[1] *Pogg Ann*, 1828, 14, 204
[3] *Ann Chim Phys*, 1838, [2], 69, 204
[3] *ibid, 1844*, [3], 11, 417, *Compt rend*, 1840, 10, 870, 1844,18, 1103
[4] *ibid*, 1844, [3], 12, 193, 1846,, [3], 16 462
[5] foaewsky, *Ann Chim Phys*, 1844, [3], 12, 278, Gerhardt, *Compt rend*, 1850, 31, 244, Buckton, *Annalen*, 1852, 84, 220, Thomsen, *Ber*, 1870, 3, 42, Odlng, *Ber*, 1870, 3, 42, Blomstrand, *Ber*, 1871, 4, 673, Cleve, *Bull Soc. chim*, 1867, [2], 7, 12, 1871, 15, 161, 16, 203, 1872, 17, 289, Cossa, *Journ Chem Soc*, 1887, 52, 642, 1896, 70, 11, 251, *Ber*, 1890, 23, 2503, *Zett anorg Chem*, 1891, 1, 65, Werner, ibid, 1893, 3, 267, 1895, 8, 153, 1896, 12, 46 see also references given under chromium (p 1088)

The following are the chief series of these derivatives which have been described, X and R being monovalent acid and basic radicles respectively,

PLATINOUS COMPOUNDS

1 Tetrammine-platinous compounds, $[(NH_3)_2Pt]X_4$
(Plato-diammine)
2 Triammine-platinous compounds, $[X(NH_3)_3Pt]X$
3 Diamrmne-platinous compounds, $[X_2(NH_3)_2Pt]$
(Platosammine and platosemidiammine)
4 Monammine-platinous compounds, $[X_3(NH_3)Pt]R$
(Platosemiammine)

PLATINIC COMPOUNDS

1 Hexammine-platinic compounds, $[(NH_3)_6Pt]X_4$
(Drechsers base)
2 Pentammine-platinic compounds, unknown
3 Tetrammine-platinic compounds, $[X_2(NH_3)_4Pt]X_2$
(Platin-diammine)
4 Triammine-platinic compounds, $[X_3(NH_3)_3Pt]X$
(Platinmonodiammine)
5 Diammine-platinic compounds, $[X_4(NH_3)_2Pt]$
(Platinammine and platinsemidiammine)
6 Monammine-platinic compounds, $[X_5(NH_3)Pt]R$
(Platimsemiammine)

Magnus' Green Salt, $[(NH_3)_4Pt][PtCl_4]$, which is the starting-point for the preparation of these derivatives, is made by tke action of ammonia on platinous chloride, and when boiled with ammonia passes into *tetrammine-platinoas chloride,* $[(NH_3)_4Pt]Cl_2$

The tetrammine salts lose ammonia when heated, thus yielding the syminetrical diammine compounds (platosammine salts), whilst the isomeric asyminetrical compounds (platosemidiammine salts) are formed by the moderate action of ammonia on the platinous salts The platinic salts are formed by the axidation of the corresponding platinous derivatives The diamrvme compounds of both the platinous and platinic series can exist in two geometrically isomeric forms (p 1092)

In addition to the classes of compounds already mentioned, several others have been described containing organic substituted ammonias in the complex radicle, and also compounds

the members **of** which contain more than one atom of platinum. Little is known of these latter compounds, for a detailed description reference must be made to the original papers

PLATINUM AND PHOSPHORUS AND ARSENIC

646 *Platinum and Phosphorus*—These two elements fuse together readily If finely divided platinum be heated in the vapour of phosphorus it burns witL evolution of light to form *platinum diphosphide,* PtP_2, which is a bright mass with a metallic lustre, not attacked by hydrochloric acid, but easily dissolved by ammonia (Schrotter) According to Granger,[1] the phosphide, Pt_3P_5, is formed at the same time, and this compound is also obtained if platinum be heated at about 600° in

phosphorus vapour

Spongy platinum and arsenic unite with incandescence The brittle alloy, $PtAs_2$, loses all its arsenic on ignition Platinum forms brittle alloys also with antimony, bismuth, and vanadium

PLATINUM AND CARBON

647 *Platinous Cyanide,* $Pt(CN)_2$, is obtained as a pale yellow precipitate on the addition of mercuric cyanide to an alkali platinochlonde solution It is insoluble in acids and alkalis, and on heating it burns, leaving platinum

Platinocyanic Acid, $H_2[PtCy_4]$, is obtained by decomposing the copper or mercury salt with sulphuretted hydrogen,[2] or by decomposing the barium salt with dilute sulphuric acid[3] After evaporating to dryness, the residue is treated with a mixture of alcohol and ether, and the ethereal solution allowed to evaporate spontaneously, when fine cinnabar-red prisms, exhibiting a splendid blue colour by reflected light, are obtained These have the composition $H_2PtCy_4,5H_2O$ Sometimes yellowish-green crystals, having a copper-red or golden lustre, are obtained which contain more water When heated to 100° they become yellow, and they decompose at temperatures above 140° They are deliquescent, yielding a colourless solution in alcohol, the aqueous solution decomposes carbonates

Potassium Platinocyanide, $K_2PtCy_4,12H_2O$, is formed when a mixture of equal parts of spongy platinum and potassium

[1] *Compt rend,* **1896,123, 1284**
[2] **Quadrat, *Annalen,* 1847, 63 164, 1858, 65, 249, 1849, 70, 300**
[3] **Weselsky, *J pr Chem* 1856, 69, 276**

ferrocyanide is heated nearly to redness in a crucible, the mass dissolved in water, and the ^ltrate evaporated (Gmelin), or when platinous chloride is dissolved in potassium cyanide[1] It is also obtained by dissolving ammonium platinichlonde together with caustic potash in a boding concentrated solution of potassium cyanide The liquid is boiled until no further evolution of ammonia takes place, when the salt crystallises out[2] This is also formed when spongy platinum is boiled with a solution of potassium cyanide, or when a mixture of these two substances is heated at 500° to 600° in steam (Deville and Debray)

$$4KCy + Pt + 2H_{20} = K_2PtCy_4 + 2KOH + H_2$$

It forms long, yellow, rhombic prisms, exhibiting a blue, metallic lustre by reflected light, and it is very readily soluble in water If the hot solution be saturated with chlorine, or boiled with aqua regia, colourless prisms of *potassium chloropfahnicyanidc,* $K_2PtCy_4Cl_2,2H_{20}$, are obtained on evaporation If this solution be mixed in the right proportion with potassium platinocyanide a double salt of the composition $5K_2PtCy_4,K_2PtCy_4Cl_2,21H_{20}$ is obtained crystallising in magnificent green prisms which exhibit a copper-red lustre by reflected light and are soluble in water This salt is formed also when potassum platinocyanide is treated with a moderate quantity of chlorine[3] In alkaline solution it acts as an oxidising agent, potassium hypochlorite being formed

$$5K_2PtCy_4,K_2PtCy_4Cl_2\ 4\ 2KOH = 6K_2PtCy_4 + KOC1 + KC1 + H_{20}$$

Barium Platinocyanide, $BaPtCy_4,4H_{20}$, was first obtained by passing hydrocyanic acid into water containing platinous chloride and barium carbonate in suspension[4] It can also be readily obtained by decomposing the copper salt by baryta water, or by adding the calculated quantity of barium hydroxide and hydrocyanic acid to a solution of platinichloric acid, and treating the warm mixture with sulphur dioxide until colourless The barium sulphate formed is filtered off and the solution cooled, when barium platinocyanide separates out and may be purified by recrystallisation from water This method of preparation serves as a means of separating platinum from

[1] Knop, *Annalen,* 1842, 43, i l l
[2] Martius, *Annalen,* 1861,**117,** 357
[3] Hadow, *Journ Chem Soc,* **1861, 18, 106**
[4] **Woaelsky,** ***J pr*** *Chem,* 1856V 00, **276.**

iridium, the compound of the latter metal remaining in solution[1] Barium platinocyanide forms large, rhombic crystals which exhibit a green and sulphur-yellow dichroism. By crystallising the salt from solution in the presence of a small quantity of barium cyanide or barium hydroxide Levy[2] obtained apple-green crystals, whilst in the presence of a small amount of hydrogen cyanide or other acids golden-yellow crystals were produced The crystals also differed in their fluorescent properties and slightly in density, but their crystalline form was identical Levy regards the two forms as isomers differing in the manner in which the water molecules are grouped, but it is possible that the differences in properties may be accounted for by the presence of traces of other salts Barium platinocyanide has also been obtained as the dihydrate and as the anhydrous salt

Calcium Platinocyanide, $CaPtCy_4,5H_{20}$, is prepared in the same way as the barium salt Two isomers have been similarly obtained,[2] yellow and green in colour but of nidentical crystalline form The anhydrous salt is white

Magnesium Platinocyanide, $2MgPtCy_4,7H_{20}$, is obtained by decomposmg the barium salt with magnesium sulphate, and is one of the most beautiful salts of this group It forms large, square-based, red prisms, the sides of which viewed by reflected light have a beetle-green lustre, whilst the end faces reflect blue or purple light It crystallises from alcohol with six molecules of water in four-sided, lemon-yellow tablets, having a blue reflection, and often exhibiting all shades of colour of red, blue, and green Other hydrates are also known

Many other platinocyanides besides these are known, of which several are remarkable for their splendid play of colours Some, such as the green copper salt, are insoluble powders obtained as precipitates by double decomposition. A very characteristic reaction for the platinocyanides is that on addition of a mercurous or a mercuric salt to their solution a white precipitate is first thrown down, but on addition of more mercurous salt this becomes of a smalt-blue colour

These salts become luminous when exposed to the Rontgen rays, and are employed for making screens by means of which the absorption of these rays may be observed

Platinum Tncyanide, $PtCy_3$ is obtained as a light yellow

[1] Bergsoe, *Zeit anorg Chem,* 1899,**19,** 318

[2] *J Chem Soc,* **1908, 98, 1446, ibid, 1912,101, 1081; Levy and Sisson, ibid.**, **1906, 89, 126.**

powder on heating platinicyanic acid to 120° It is insoluble in water but dissolves" in ^boiling solution of potassium cyanide [x]

Platinicyanic Acid, $HPtCy_4$, is obtained by evaporating a fairly concentrated solution of platinocyanic acid with hydrogen peroxide on the water-bath *

$$2H_2PtCy_4 + H_{202} = 2HPtCy_4 + 2H_{20}$$

As evaporation proceed^ the white substance at first formed turns pink, brown, and finally dull olive-green This is platinicyanic acid, $HPtCy_4,2H_{20}$ The colour changes are due to differences in the degree of hydration and take place in the reverse order when water is added to the acid

The acid is reduced to platinocyanic acid on boiling with sulphur dioxide, and liberates iodine from potassium iodide solution quantitatively according to the equation

$$2HPtCy_4 + 2KI = 2KHPtCy_4 + I_2$$

Silver Platinicyanide, $AgPtCy_4$, is obtained as a brown, flocculent precipitate on the addition of silver nitrate to a solution of platinicyanic acid When dry it is a buff-coloured powder which on ignition leaves a residue of silver and platinum

Oxidation of the platinocyanides with hydrogen peroxide in sulphuric acid solution yields the corresponding platinicyanides With strong solutions, the pure *sodium* and *lithium* salts have been obtained More usually, however, compounds of the platuncyanides with the platinocyanides are produced, as, for example, $LiPtCy_4,2Li_2PtCy_4$, and $KPtCy_4,3K_4PtCy_4$ [1]

Potassium Platinoihiocyanate, $K_2Pt(SCN)_4$, is obtained by dissolving platinum dichloride in a solution of potassium thiocyanate, or, better, by dissolving equal parts of potassium platinochlonde and potassium thiocyanate in the smallest quantity of water, when the mixture becomes warm, and, on cooling, the salt separates out in red, microscopic prisms When the barium salt is decomposed by dilute sulphuric acid, the free acid is obtained in solution, but undergoes rapid decomposition [2]

Platinithiocyanic Acid, $H_2[Pt(SCN)_6]$ —On decomposing the lead salt with dilute sulphuric acid, a thick, dark red, very acid liquid is obtained, which decomposes carbonates, and dissolves zinc with evolution of hydrogen On evaporation in a vacuum, an indistinct, crystalline mass remains behind

[1] Levy, *Journ Chem Soc*, 1912, 101 1081
[2] Buckton, *Journ Chem Soc* , 1855, 22

Potassium Platintthiocyanate, $K_2Pt(SCN)_6$, is obtained by adding potassium thiocyanate solution, not in excess, to a solution of potassium platinichlonde and heating to boiling. The filtered solution on cooling deposits large, six-sided prisms or tablets having a carmine-red colour and possessing a very disagreeable taste They dissolve in water, forming such a deep red solution that one drop of the concentrated liquid imparts a distinct colour to 100,O00 parts of .water When the concentrated solution is boiled with ammonium sulphate a very similar ammomum platinithiocyanate is formed The platinithiocyanates of the alkali metals are soluble in water and crystallisable, those of the heavy metals are insoluble, and have a yellowish- or blackish-red colour (Buckton)

DETECTION AND ESTIMATION OF PLATINUM

648 If a platinum compound be heated on a carbomsed match in the gas-flame, a grey, spongy mass is obtained soluble only in aqua regia The concentrated solution yields with potassium chloride and ammomum chloride the well-known and characteristic precipitates Sulphuretted hydrogen throws down from solutions of a platinum salt, slowly in the cold but more quickly on heating, the brown disulphide which is soluble in an excess of yellow ammomum sulphide A solution of stannous chloride colours platinic chloride solutions dark brown, inasmuch as platinous chloride is formed A solution of benzidine in acetic acid forms a delicate reagent for the detection of platinum, a blue, flocculent precipitate being obtained Iron and gold also give blue colorations with this solution [1]

In the general separation of the metals, platinum and gold are obtained together with arsenic, antimony, and tin Their presence is indicated by the brown colour of the precipitate produced by hydrochloric acid in the solution in ammomum sulphide In this case the precipitate is fused with sodium carbonate and nitre, the fused mass lixiviated with water, and the residue, which may contain the gold and platinum together with tin "dioxide and sodium antimonate, is treated with zinc and "hydrochloric acid when the latter two compounds are reduced to metals The mass is first boiled with hydrochloric acid to remove the tin, and next with nitric acid and a little tartaric acid to dissolve the antimony; the residue is then

[1] **Malatesta and Di Noia,** ***Soil Chim Farm,*** **1913, 62, 461**

treated with aqua regia, the solution concentrated and evaporated to dryness on the water-both with an excess of ammonium chloride, and alcohol added to dissolve the gold chloride From the alcoholic solution the gold may be readily precipitated with ferrous sulphate The portion insoluble in alcohol may contain ammonium platinichlonde, and this on ignition will leave a residue of spongy platinum The qualitative separation *pi* the platinum metals by means of their sulphides has already been described (p 1437)

An alternative method for the rapid qualitative analysis of a mixture containing these metals has been devised by Mylius and Dietz[1] A solution of the chlorides is boded in a retort with dilute nitric acid and the vapours passed into a solution of caustic soda If osmium be present it is thus converted into the volatile tetroxide which forms a yellow solution in the soda and may be detected in the usual manner The residual liquor, after extraction with ether to remove gold chloride, is then heated with ammomum acetate and formic acid for several hours in a reflux apparatus, whereby the salts of the platinum metals are reduced to the metals, and the black precipitate, after washing and drying, is heated to redness in a stream of hydrogen to remove mercury The residue is then extracted with hydrochloric acid, mixed with sodium chloride, heated in chlorine, and the product dissolved in a little water, filtered, and ammomum chloride added so long as any precipitate forms In this way the platinum, indium, and ruthenium are precipitated, whilst the palladium and rhodium remain in solution, but the separation is not quantitative The precipitate is dissolved in warm water, treated with hydroxylamine, and again precipitated with ammonium chloride, whereby the tetrachlorides of ruthenium and iridium first formed are converted into the trichlorides which remain in solution, whilst the platinum is precipitated as ammomum platinichlonde Kuthenium and indium are separated in the filtrate from this precipitate by evaporating to dryness, reducing to the metals in a current of hydrogen, fusing with potash and nitre, extracting with water, and distilling off the volatile ruthenium tetroxide in a current of chlonne into dilute acidified alcohol The indium is detected in the insoluble residue by treatment with chlorine and sodium chloride and precipitation with ammomum chlonde The original filtrate containing rhodium and palladium is evaporated

[1] *Ber*, 1808,31, 3191

to dryness With excess of ammonia, the residue dissolved in the least possible quantity of ammonia and cooled, when the less soluble ammoniacal rhodium chloride separates out, and the palladium may be precipitated from the filtrate by hydrochloric acid as palladosammine chloride

The *quantitative estimation* of platinum always takes place as metal, obtained by ignitiorr of ammonium platinichlonde, or by heating potassium platinichlonde in a current of hydrogen and lixiviating the residue with water, or sometimes also by ignition of the sulphide

The Atomic Weight of platinum was determined by Berzelius [1] by analysis of the potassium double chloride, the mean number obtained by him was 197 1, Andrews,[2] who employed the same method, found the atomic weight to be 197 9, but Seubert[3] obtained 195 14, and Halberstadt,[4] confirming this result, found 195 07 More recent work by Archibald,[5] who analysed the carefully purified potassium and ammonium salts of chloro- and bromo-platinic acids, has given as a mean of twenty-eight determinations the figure 195 23 The value now (1922) adopted is 195 2

[1] *Lehrbuch, 5te Aufl* 3, 1212
[2] *Chem Gaz,* **1852,** 379
[3] *Annalen,* **1881, 207, 1**
[4] ***Ber,* 1884, 17,** 2963
[5] *Proc Roy Soc Edin,* **1909, 29, 721**

*

THE RADIOACTIVE ELEMENTS

649 Becquerel's discovery of the radioactivity of uranium in i896 has led to the development of an entirely new branch of scientific thought Special methods of investigation, mainly physical in character, have been invented, and the results are of extraordinary interest and importance Much, however, yet remains to be done before many of the conclusions hitherto drawn can be considered as established, and discoveries are constantly being made In these circumstances only a very brief outline of the subject is here attempted [x]

650 The phenomena of the electrical discharge in an ordinary vacuum tube containing gas at a few millimetres pressure are quite familiar If the tube contain air or nitrogen, the negative pole, or cathode, is clothed with a violet glow, quite distinct from the brick-red positive column, which occupies most of the tube The narrow portion of the tube may be bent into any curved form—a spiral, for example—and the discharge follows all the curves But the phenomena are quite different if the vacuum in the tube be greatly increased, the dark space separating the cathode from the violet glow becomes much greater, and the discharge from the cathode refuses to follow the curves of the tube, but pursues a straight course, normal to the surface of the cathode, until it strikes the glass, where it produces phosphorescence The phenomena of such high vacua were investigated by Crookes [2] in 1870 He found these electric streams from the cathode produced brilliant phosphorescence in diamonds, rubies, etc, and threw well-defined shadows of objects placed in their path upon the opposite wall of the tube, which phosphoresces all round the shadow Further, this electric stream can put lightly poised vanes into motion, and it is deflected by a magnet brought near the tube Such an electric stream is now Spoken of as consisting of " cathode rays " It was shown by Hertz that

[1] A full account of the subject is given in *Radioactive Substances and their Radiations,* by Rutherford (Cambridge The University Press, 1913) The chemical behaviour of radioactive bodies is dealt with by Soddy in *The Chemistry of the Radio Elements* (Longmans)

[1] *Phil Trans* , 1874,**164,** 601, 1875,**165,** 519, 1876,**166,** 325

the cathode rays, though they **will** not pass through glass or mica, will penetrate thin metal foil, and Lenard, by constructing vacuum tubes with aluminium " windows," observed the cathode rays to pass out through the metal into the air, there to produce phosphorescence, although the rays cannot be produced at all in air at ordinary pressure Crookes aptly spoke of these phenomena as belonging to a " fourth state " of matter, quite different from matter in either the solid, liquid, or gaseous state The cathode rays are now recognised as streams of electrons carrying negative charges

J J Thomson showed,[1] in 1897, that the cathode rays are not only deflected in a magnetic field, but also by an electric field, and this is what should occur if the rays are streams of negatively electrified particles He employed a vacuum tube so arranged that the cathode stream passed midway between two parallel insulated plates of metal, respectively charged positively and negatively When the plates were uncharged the cathode stream produced a luminous spot on the end of the tube, but when the plates were charged the displacement of this spot showed that the stream had been deflected towards the positively charged plate, thus proving that the particles of the stream carried a negative charge By means of an electro-magnet the stream could be deflected in the opposite direction so as to bring the spot back to its original position By measuring the strengths of the electric and magnetic fields, data were obtained for calculating the velocity of the particles, and also the ratio of the electric charge to the apparent mass of a particle The strength X of the electric field is V/d, where V is the difference of potential between the plates and d their distance apart If H be the strength of the magnetic field, the force acting on a particle with charge e and moving with velocity u is Hai, and at equilibiium,

$$Heu=Xe \qquad (1)$$

If the magnetic field be acting alone, a particle of mass in and charge e describes a circular orbit of radius p, such that

From equations (1) and (2) the values of u and e/m can be determined By measurements made in this way it has been found that the velocity of the particles varies between about 10^9

[1] *Phil Mag* 1807, [5], 44, 203.

and 10^{10} cm per second (The velocity of light is 3 X 10^{10}, and the velocity of the molecules of hydrogen in the gas at N T P 1 844 x 10^5 cm per sec) These experiments do not, however, give us the mass of a particle, but only the ratio of the charge to the mass It follows from Faraday's laws of electrolysis that all monovalent ions in electrolysis carry the same charge, and experiment has shown that it requires 9 6 x 10^3 electromagnetic units of electricity to set free one gram of hydrogen If N be the number of atoms in one gram of hydrogen, then Ne = 9 6 x 10^3, and if in be the mass of a hydrogen atom, then Nm = 1 Hence e/m = 9 6 X 10^3 for the hydrogen ion Simon[1] obtained an average value of 1 86 x 10^7 (with an average velocity of 7 X 10^9) for the ratio e/m for the cathode rays, and if we assume that the charge of the particles (or electrons) is the same as that of an atom of hydrogen, so that e has the same value in the two equations e/m = 1 86 X 10^7 and e/m' = 9 6 X 10^3 (where m' is the mass of the hydrogen atom), then $m!$ = 1943m The mass of the particle in the cathode rays is thus about the one two-thousandth part bf the mass of a hydrogen atom According to the work of Millikan the value is 1/1830 of the mass of a hydrogen atom (see p 40)

It has been mentioned that the cathode rays excite phosphorescence in the glass of the tube at the place where they impinge, or in other substances placed in the path of the stream of electric particles In 1895 Rontgen discovered that in these circumstances the phosphorescent glass emitted rays of a most remarkable character—the so called X-rays—capable of penetrating such opaque substances as paper, wood, aluminium, flesh, etc , but stopped by lead, platinum, glass, or bone These rays have the power of exciting fluorescence in such substances as barium platinocyanide, and of affecting a photographic plate, so that it is possible to photograph, or by the use of a fluorescent screen to see, the shadow of the bones of the hand, or a com concealed between the pages of a book The X-rays are incapable of refraction or reflection from isotropic media, recently, however, reflections have been obtained from crystalline substances such as mica, but this phenomenon is more analogous to interference in optics than to true reflection[2] (p 216) The rays are'not sensibly acted on by a magnet They have been found to have the power of discharging an electroscope

[1] ***Ann Physik*, 1899, 69, 589**

[2] **Laue, Friedrichs, and Knipping, *Sitzungsber Bayr Akad. Wiss*, 1912, 303**

There is another type of ray which is observed when an electric discharge passes through a rarefied gas It was shown by Goldstein[1] that under certain conditions of pressure streams of rays pass through the holes in a perforated cathode These streams are known as canal rays, and have been shown by Wien to consist of positively charged particles moving with high velocities From measurements of their deflection in electric and magnetic fields, it appears that the .carriers of the electricity are of atomic size and thus differ in this respect from the cathode particles, as well as in carrying electricity of opposite sign This distinction between the sizes of the carriers of positive and negative electricity is general and of great importance, and will

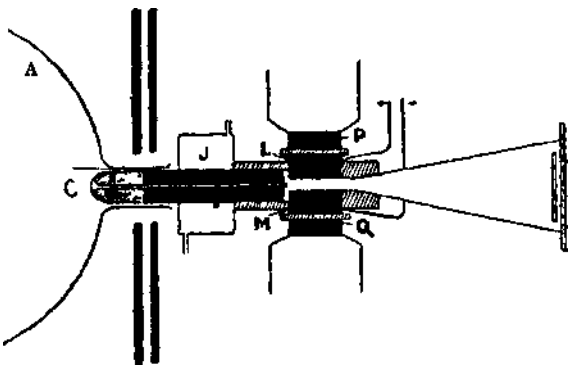

FIG **205**

be seen later to exist in the positively and negatively charged radiations emitted by radioactive bodies

651 Some experiments by J J Thomson[2] are of particular interest as a delicate means of chemical analysis The method consists in subjecting the positive rays simultaneously to an electric and a magnetic field and noting the deflection suffered by the rays The electric and magnetic fields are arranged to be in the same direction so as to deflect the rays in two directions at right angles to each other, with the result that the particles move along different paths determined by the masses and velocities of the particles The experimental arrangement will be understood from Fig 205 An electric discharge is passed through the rarefied gas contained in the vessel, A, provided with a cathode, C, with a small hole at its

[1] ***Berlin Sitzungsber,* 1886, 39, 691.**
[2] ***J,* J. Thomsorfi *Baty of Positive Electrictiy***

centre The positively electrified particles which move with great velocity towards the athode pass through this hole and emerge as a fine pencil of electrified particles passing between the plates, L and M, connected to the positive and negative poles of a battery, and between the pole-pieces, P and Q, of an electro-magnet The heterogeneous pencil of particles, all of which follow the same course before entering the electric and magnetic fields, is split up into a number of groups of rays branching off in different directions No two particles move along the same

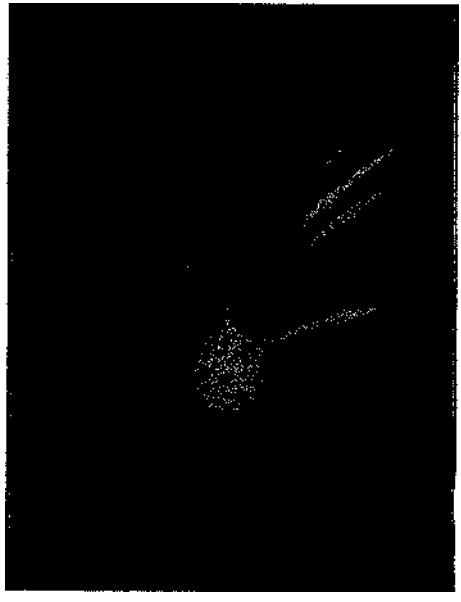

path unless they have the same masses and also the same velocities It can be shown that all particles with the same masses but with different velocities move along the surface of a cone which is peculiar to the particular particle, so that if this cone is determined, the nature of the particle carrying the positive charge is also known, in this way, from a study of the path traversed by a particle, it is possible to deduce its mass and therefore the chemical nature of the atom or molecule constituting the positive radiation The cones are determined by observing their parabolic sections on a photographic plate placed in the path of the rays A typical photograph obtained in this way is, shown in Fig 206, The photograph was obtained with the

residues from liquid air containing the lighter gases, there aie present lines corresponding to helium, neon, argon, and also a line of special interest corresponding to an atomic weight 22, which could not be identified with the line of any known gas, for the possibility of its being due to molecules of CO_2 carrying a double charge of electricity is precluded by the fact that on passing the gases through tubes immersed in liquid air the line persisted, whereas the line at 44, due to carbon dioxide, disappeared There seems to be no doubt that the line is due to a new gas of atomic weight 22 contained in the atmosphere and closely associated in properties with neon, for it is found in all the specimens of neon which have been examined

The nature of the positive rays is very complicated, since the

FIG 207

particles constituting them may consist either of atoms or molecules, with single or multiple changes The method of examination described above is hardly capable of disentangling their complexities, but a modification and refinement devised by Aston[1] has given results of striking importance The improvement consists in so arranging the apparatus that after deflection by an electric and a magnetic field, rays having the same value of $\frac{e}{m}$ are brought approximately to a focus on a phonographic plate, and in this way a " positive ray spectrum " or " mass spectrum " of the radiation is obtained The general arrangement adopted is shown in Fig 207 The rays after

[1] Aston, *Phil Mag*, 1919, [6], 88, 707, 1920, [6], 89, 449, 611, 1920, [6], 40, 628, 1921, [6], 42,140, 436, Aston and Fowler, *ibid, 1922* [6], 43, 514.

reaching the cathode pass through two narrow parallel slits, S_1, S_2, and the resulting bear passes between the parallel plates, P_1, P_2, maintained at different electric potentials The rays deflected by the electric field may be considered to diverge approximately from a point, Z, at the middle of the field A group of these rays passes through the diaphragm, D, and into a magnetic field maintained by an electro-magnet with circular pole-pieces The magnetic, field is arranged to deflect the beam in a direction opposite to that produced by the electric field It can be shown that with this method rays having various values of will all be brought to a focus on a photographic plate, GF

Typical photographs taken with the positive ray spectrograph are shown in Fig 208 The various spectrographs shown are indicated as belonging to different elements Ne, CI, A, Kr, Xe, etc , but it must be realised that with this delicate method of analysis it is impossible to exclude impurities arising from gases occluded in the walls of the tube and from hydrocarbons emitted by the tap grease unavoidably used in the apparatus A very careful study of each spectrograph is therefore necessary before the disturbances arising from impurities can be eliminated

Lines due to elements will appear for values of - corresponding with the atomic weights of the elements, and with single, double, and treble charges Following a nomenclature, analogous to that of optics, lines due to singly-charged atoms are known as first order spectra, those due to doubly-charged atoms as second order spectra, and so on The complication arising from charged molecules is fortunately rendered less serious by the fact that in most cases molecular spectra appear only in the first order The large number of lines in the spectrographs (Fig 208) arising from hydrocarbons and other carbon compounds can thus be identified and left out of consideration For measurement, it is necessary to establish certain standard lines, oxygen gives a useful set of lines for this purpose, showing, as it does, lines at 32,16, and 8, due, respectively, to the singly-charged molecule and to the singly- and doubly-charged atoms Other useful lines of reference are found at C^{++}(6), C^{+}(12), CO^{+}(28) and CO_2^{+}(44) By comparison with these and other lines, the masses corresponding with any particular lines can be accurately determined

It is not proposed to enter into a full discussion of the com-

plicated results shown in Fig 208, for a single example, that of chlorine, will suffice to indicate the manner in which the results have been interpreted

Spectrum 1 shows two lines at 20 and 22 due to neon found by

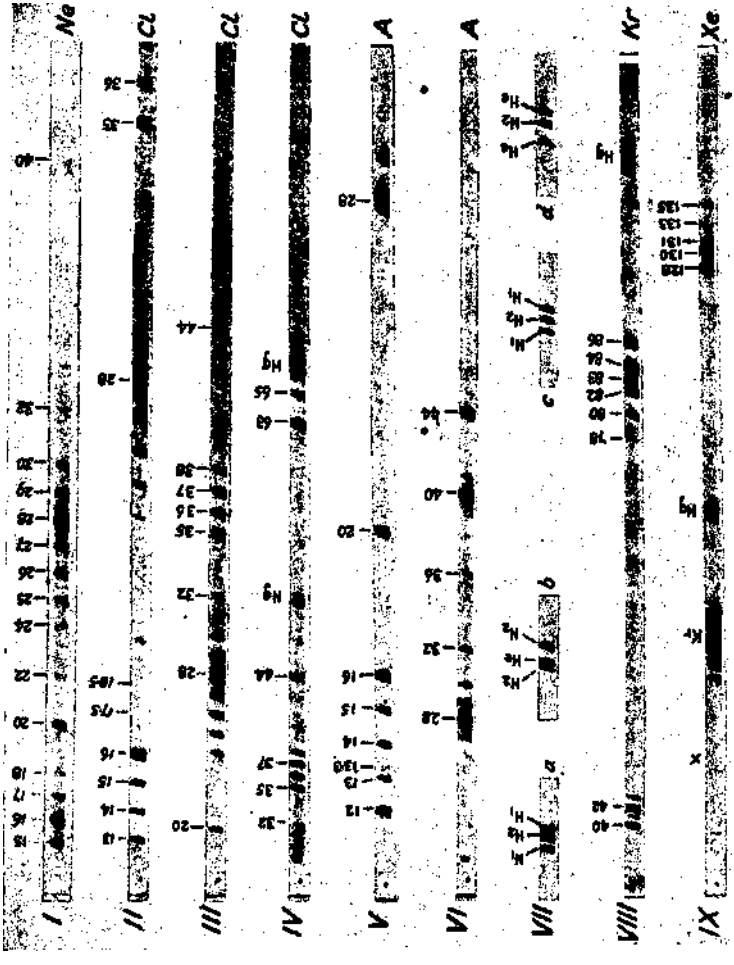

J J Thomson as mentioned above On introducing phosgene (COCI5) into the tube the spectra shown in I I , I I I , and IV were obtained It will be seen that the introduction of chlorine has proceed a series of lines at 35, 36, 37, and 38, but no line appears in the position corresponding with the accepted atomic weight, 35 46 On spectrum II may be seen lines at 17 5 and 18 5 when free chlorine was introduced and lines corresponding with 35

and 37 The lines at 36 and 38 are ascribed by Aston to hydrochloric acid formed from chlorine of atomic weights 35 and 37, respectively

We thus have two examples of elements, neon and chlorine, each appearing to have two distinct atomic weights represented by whole numbers, 20 and 22 in the case of neon, and for chlorine 35 and 37 Similar results have been found with other elements, and it is impossible to escape from the conclusion that we can no longer regard the elements as made up of exactly similar atoms, but, on the other hand, that they consist of a mixture of atoms having integral atomic weights mixed in different proportions These atoms, however, are inseparable by any chemical process, being in every way identical in chemical

Element	Atomic number	Atomic weight	Minimum number of isotopes	Masses **of isotopes in order of intensity**
i H	1	1008	1	1008
He	2	3 99	1	4
Li	3	O 94	2	7,6
B	5	10 9	2	11, 10
C	6	12 00	1	12
N	7	14 O1		14
O	8	10 00	\	16
F	9	19 00	1	19
Ne	10	20 20	2	20,22(21)
Na	11	23 O	1	23
Al	13	27 O	1	27
Si	14	28 3	2	28, 29, (30)
P	15	3104	1	31
S	lb	32 Ob	1	32
CI	17	35 4b	2	35, 37
A	18	39 88	(2)	40 (36)
K	19	39 1	2	39, 41
Fe	26	55 84	1	55 94 ± O O5 (54)
As	33	74 96	1	75
Se	34	79 2	b	80, 78, 76, 82, 77, 74
Br	35	79 92	2	79, 81
Kr	3(>	82 92	6	84, 86, 82, 83, 80, 78
Rb	37	85 45	2	85, 87
Sn	51	118 7	8	120, 118, 116, 124, 119, 117, 122, 121
Sb	52	120 2	2	121, 123
I	53	126 92	1	127
Xe	54	130 2	7	129, 132, 131, 134, 136, 128, 130
Cs	*55*	132 81	1	133
Hg	80	200 b	(6)	(197-200),202,204

photographic plate with the Becquerel rays, whereas with the X-rays a photograph can be taken in less than a minute

Becquerel's discovery was followed in 1898 by the observation made independently by Schmidt[1] and Mine Curie,[2] that the compounds of thorium and minerals containing this element also emit radiations of a similar charactei to the Becquerel rays These discoveries have led to the recognition of an entirely new class of substances which possess the remarkable property of radioactivity

Eadioactive substances spontaneously emit rays possessing in varying degrees the properties of canal, cathode, and X-rays The "phenomena available for the study of the radiations from such substances are

(a) The action on a photographic plate

(6) The phosphorescence produced in certain substances *e g* ,

[1] ***Ann+Phynk*, 1898, 65, 141** [2] ***Compt rend*, 1898,186,1101**

the platinocyanides, willemite (znic silicate), kunzite, and Sidot's blende (crystalline znic sulfide)

(c) The lonisation of gases produced by the rays

The last of these lends itself most readily to quantitative measurements, and is generally employed for measuring the degree of radioactivity possessed by a substance

According to the theory of the lonisation of gases of J J Thomson and Rutherford,[1] this effect is due to the production of ions or positively and negatively charged earners in the gas, the rate of production being proportional to the intensity of the radiation These ions move with uniform velocity through a uniform electric field, the positively charged towards the negative plate, and vice *versa,* and their velocity is proportional



FIG **209**

to the strength of the held The separated ions gradually recombine, the rate of recombination being proportional to the square of the number present An lomsed gas preserves its conducting power for some time after removal of the ionising agent, and may be carried in a current of air so as to discharge an electroscope some distance away

The arrangement for measuring the rate of lonisation produced by X-rays or cathode rays or by the presence of radioactive material is shown diagrammatically in Fig 209

The active material is placed at R on the lower of twq insulated plates, A and B, charged respectively negatively and positively by means of a battery connected to B and with the other pole earthed at E The plate A is connected to one pair of quadrants of an electrometer, EM, of which the other pair is earthed The gas between the plates A and B being ionised at a constant rate

[1] ***Phil Mag.,* 1896, [5], 42, 392.**

if no electric field be present, the number of ions soon reaches a maximum, when the rate of production of fresh ions is balanced by the rate of recombination If, however, B be kept charged to a constant potential V, the rate at which the plate A gains charge may be measured by the quadrant electrometer, EM Positive ions travel to the negative plate A, and negative ions to the positive plate B, there is thus a current through the gas which is measured by the rate at which A rises in potential

When V is small the current is small, but as V increases the current rapidly rises to a limit and then remains constant even when the value of V is largely increased This condition is not always attainable in practice, a slight increase of current generally

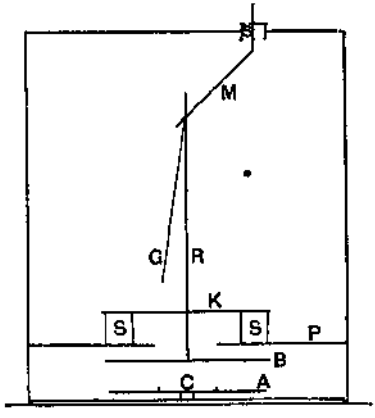

FIG 210

occurring with increase of V This limiting *saturation current* through the gas thus measures the charge carried by the ions produced per second by the radiation, that is, it is a measure of the radioactivity of the substance under examination For uranium, and for substances not more than a thousand times as active as uranium, a potential difference of 300 volts is usually sufficient, but for radium, and for very active substances, the plates are placed close together, and a higher voltage may be necessarji.

Frequently, some form of gold-leaf electroscope is used to measure the saturation current. Such an electroscope is shown in Fig 210 A strip of gold-leaf, 6, is attached to a vertical Tod, R, which is supported by the horizontal rod K, resting on sulphur, SS, by which the system is insulated The rod K passes through an opening in the metal plate P, and terminates in a horizontal

plate, B, which is opposed to the removable plate A, on which the radioactive material, is placed The whole is enclosed in a metal case and the motion of the gold-leaf is observed through an opening in the metal case by means of a microscope of low power provided with a micrometer eyepiece M is a bent wire passing through an insulating plug of sulphur, S, in the top of the case, by means of this wire the electroscope can be charged During an observation the metal case and the lower plate A are connected to earth, and the time taken for the gold-leaf to pass over a fixed part of the scale is determined, this observation being corrected for the " natural leak" of the instrument, measured when no radioactive material is present The measurements are generally comparative, uranium oxide being often used as a standard of comparison The instrument described above is typical of an electroscope used for such measurements The details of construction will depend upon the particular measurement to be made [1]

In the examination of radioactive substances, and in the search for new radioactive material, the electroscope has proved an invaluable guide Bunsen showed that 0 0000003 milligram of sodium could be detected by spectrum analysis, but for the detection of substances like radium the electroscope is many thousand times as sensitive as the method of spectrum analysis, for by its means a substance having only the ten-thousandth of the activity of uranium can be detected, the activity of radium is about 2,000,O00 times that of uranium

PHENOMENA OF RADIOACTIVITY

653 The radiations from radium and most of the radioactive substances are found to be complex The different kinds of radiation are distinguished by their different behaviours in a magnetic field and by their different powers of penetrating metal screens, etc By these methods it has been found that radium emits three different kinds of rays, which have been called by Rutherford a-, B-, and 7-rays respectively

The a-rays are analogous to canal rays and are easily absorbed by thin metal foil and by a short column of air Their deflection in a magnetic field is slight compared with that of the B-rays, but is in the opposite direction, proving that they are

[1] **See Makower and Geiger, *Practical Measurements in Radioactivity* (Longmans, 1912)**

positively charged The magnitude of their deflection shows that they are moving with a velocity approximately one-tenth of that of light.

The B-rays are identical with the cathode rays produced in a highly exhausted vacuum tube they are deflected by a magnetic field in such a direction as to show that they are carriers of negative electricity They are completely absorbed by one millimetre of lead Their velocity, is, however, much greater than that of the cathode rays in a vacuum tube, the $-rays from radium varying in velocity between about 10^{10} and nearly 3×10^{10} cm per second Their penetrating power increases rapidly with the velocity, and some of those expelled from radium penetrate a thickness of a millimetre of lead

Besides the *a*- and B-rays, uranium, thorium, and radium compounds emit very penetrating rays known as 7-rays, the penetrating power of which is 100 times that of the B-rays, so that the rays can be detected after passing through several centimetres of lead These rays are not deflected[1] in a magnetic field They can easily be detected from a few milligrams of radium bromide enclosed in a lead vessel of 1 cm thickness (which completely absorbs the a- and B-rays) by the luminosity they produce in a fluorescent screen of barium platinocyanide or of willemite, when observed in a dark room The 7-rays, which are similar in nature to -X-rays, are usually associated with j8-rays, and are probably produced in some way from the /3-particles as they escape from the atom It has, however, been shown by Chadwick[2] that y-rays may be produced in small quantity from a-rays

The different behaviours of the three kinds of rays in a magnetic field is diagrammatically illustrated[3] in Fig 211

E, represents the radium compound placed at {he bottom of a small cylindrical lead vessel, standing on a photographic plate, AC By a strong magnetic field applied at right angles to the plane of the paper and directed towards the paper, the three types of radiation are separated the 7-rays take a straight course without Jbemg deflected by the field, the B-rays are deflected to thought, describing circular paths, and affect the photographic plate on the right of R, while the a-rays are slightly deflected to the left, but are quickly absorbed by the air

[1] Villard, *Ccmpt rend* , 1900,**130,** 1010, 1178, Becquerel, *thtd* , 1164
[2] *Phil Mag,* 1913, [6], 25, 193
[3] Rutherford, *Radioactive Substances* p 116

The phosphorescence, produced in a zinc sulphide screen by radium is chiefly due to the a-rays This phenomenon was discovered by Crookes,[1] and is well exhibited by his apparatus, known as the *spinthariscope* In this a fine metallic point, which has been dipped in a solution of a radium salt, is fixed a millimetre or two above a zinc sulphide screen, which is examined with a magnifying glass in darkness The surface of the screen is then seen to be dotted with flashes of light, which follow each other rapidly, and this action is kept up without any apparent diminution for years It has been shown that

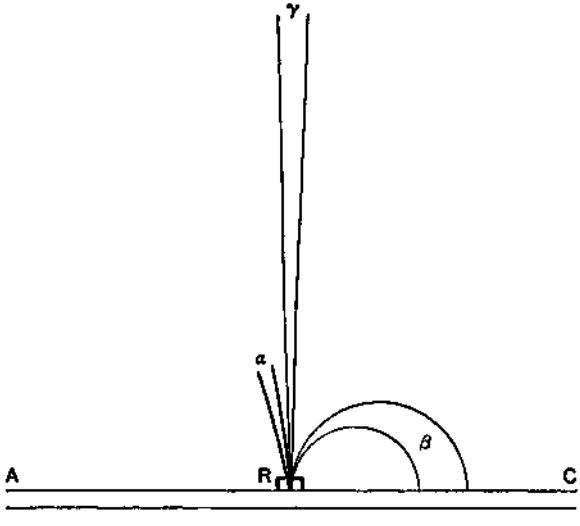

FIG 211

nearly every a-particle striking the screen produces a flash of light, and this property has been employed to count the number of a-particles emitted by a source of radiation [2]

The velocity of the a-ray is not easy to determine exactly, because of the smallness of the deflection of the a-particles in an electric or a magnetic field Eutherford and Robinson[3] have found it to be 1 92 x 10^9 cm per second, whilst the ratyo e/m = 4 82 x 10^3 E M units This value of e/m is almost exactly°,half that of the hydrogen ion in electrolysis.

[1] *Proc Roy Soc* , 1903, *[A]*, 71, 405
[2] Rutherford and Gteiger, *ibid*, 1908, *[A]*, 81, **141,** and Regener, *Verh deut physikal Ges* , 1908,**19,** 78, 351
[3] *Phil Mag* , **1914,** [6], **552**

The velocity of the a-particle emitted from different substances vanes, and the foregoing figure applies to that given off by the substance known as radium-C (p. 1525) On the other hand, the ratio *e/m* is constant When the velocity of the a-particle falls below a certain limit, which is about 40 per cent of the velocity given above, the particle ceases to produce the effects characteristic of radioactivity, and passes beyond the reach of our present experimental methods When the velocity of an a-particle has thus been reduced, the particle seems to be brought to rest within a very short distance, so that it appears to be suddenly stopped after traversing a certain thickness of matter The maximum distance which an a-particle can penetrate through air at normal temperature and pressure has been called by Bragg the *range* of the a-particle The lonisation produced by an a-particle near the end of its range increases very rapidly and then suddenly vamshes The range of different a-particles varies from 2 53 cm to 8 17 cm [1] and is characteristic of the particular product from which the a-particle is emitted [2] A relation has been obtained by Geiger and Nuttall [3] between the range and the rate of decay of radioactive products The nature of an a-particle has been the subject of much speculation, and many considerations point to its identity with an atom of helium The' value of *e/m* for a helium atom of atomic weight 4 carrying the same lonic charge as a hydrogen ion in electrolysis should be 2 5 X 10^3, and we have seen that the value of *e/m* for an a-particle is almost exactly twice that number Now Rutherford and Geiger [4] have shown that an a-particle is associated with twice the atomic charge, whence it follows that the atomic weight of the a-particle is 4, i *e*, that the a-particle is a charged atom of helium This has been confirmed by direct experiment by Rutherford and Royds (p 1520)

Associated with the expulsion of a-particles is the phenomenon of radioactive recoil. When an a-particle of mass in is emitted by an atom of mass *M* the residual atom, the mass of which must be $M—m_1$ will be projected in a direction opposite to that

in which the a-particle is travelling with a velocity *V* given by

[1] Geiger, *Zeit f Physik,* 1921, 8, 1, 45.

[2] *it* has recently been established by Rutherford and A B Wood *(Phil Mag,* 1921, [6], 41, 570 and 673) that in the disintegration of thorium active deposit a small number of a particles (about one in ten thousand) is emitted with a range of 11 3 om

[3] *Phil* ***Mag,*** **1911,22, 613** [4] ***Proc Hoy*** *Soc,* **1908,** $[A]_9$ **81,162**

the equation $(M—m)V = mv$, where v is the velocity of the a-particle Now since the velocity of an a-particle is about 2×10^9 cm /sec, and since its atomic weight is 4 and that of a radioactive atom about 200, it follows, from the above equation, that the velocity with which the residual atom recoils must be 4×10^7 cm per second This atom which constitutes the next product (p 1511) in the disintegration series to the product from which the a-particle is emitted, will travel a considerable distance if free to move through a vacuum, as has been shown by Russ and Makower [1] The recoiling atom is positively charged and can be deflected in electric and magnetic fields, and this property can be used, as in the case of a-rays, to determine the velocity of projection and the value of — for the recoiling atoms The employment of this method affords a means of determining the atomic weights of several radioactive substances When projected into air at atmospheric pressure, a recoil stream does not penetrate more than about a tenth of a millimetre, but the recoiling atoms after being stopped still retain their positive charges and can thus be collected on the negative electrode in an electric field By this process many radioactive products have been separated [2] Although an atom when it recoils possesses only $^1/_{50}$ the energy of the a-particle, it is able to produce lonisation in gases, as has been shown by Wertenstem [3]

654 If, as we have seen, the heavy radioactive atom recoils from the particle when it is expelled, it might be expected that an a-particle in its path through a substance of low atomic weight such as hydrogen would, under suitable conditions of impact, cause the light hydrogen atoms to recoil with considerable velocity This was first observed to be the case by Marsden [4] He observed that when a-particles passed through hydrogen, feeble scintillations could be detected at distances far beyond the range of the a-particle The range of the recoil stream of hydrogen was found to be about four times that of the a-particles producing it, a value which agrees well with that calculated by Darwin [5] on Bohr's [6] theory of the absorption of a-particles by matter Eutherford [7] has confirmed and extended these observations, akd has

[1] ***Proc Roy Soc*** **, 1909, *[A]*, 82, 205**
[2] **Hahn, *Verh deut physikal Ges*, 1909,11, 55**
[2] ***Le Radium*, 1912, 9, 6**
[4] **Marsden, *Phil Mag*** **, 1914, [6], 27, 824**
[5] **Darwin, *ibid*** **,499** [6] **Bphr, *ibid*, 1913, [6], 25, 10**
[7] **Rutherford, *ibid*, 1919, [6], 37, 537, 562, 571, 581**

obtained results of far-reaching importance from the point of view of atomic structure Whereas the results obtained with a-particles of short range (less than 4 cm of air) are consistent with the simple theory of collisions between point atomic nuclei, the results for a-particles of long range such as those from radium-C (range 7 cm) are entirely inconsistent with this view In this case it can be calculated that when such collisions take place the nuclei of the two colliding atoms may come within a distance of about 3 X 10^{-13} cm , a distance which is less than the diametef of an electron It was found that the number and distribution of the hydrogen atoms giving rise to scintillations are quite different from those to be expected if the nuclei were point charges repelling each other according to the inverse square law The hydrogen atoms produced by such swift a-particles are shot forward mainly in the direc are nearly uniform in velocity Rutherford explains these results by supposing that the helium nucleus behaves as a charged disc of radius 3 X 10^{-13} with its plane perpendicular to its direction of motion, and that in these very close collisions with hydrogen atoms such intense electric forces are involved that both the structure of the helium atom and possibly the electron itself may be deformed In this way, the forces between the nuclei at very close distances might be greatly modified, although at greater distances the law of the inverse square would hold, as is known to be the case

It can be calculated that, for all atoms carrying unit electric charge and of atomic weight less than 16, scintillations should appear beyond the range of the a-particles, and evidence has been obtained that this is the case with oxygen and nitrogen, but not with any heavier element

The case of nitrogen is particularly remarkable, for besides the scintillations due to nitrogen atoms having a range slightly greater than the a-particles producing them, a few scintillations of much greater range are detectable The evidence goes to show that these are caused by charged atoms of hydrogen produced by the disruption of the nitrogen nucleus, thus showing that the nitrogen nucleus contains hydrogen nuclei as a constituent It seems probable that the nitrogen nucleus consists of three helium nuplei each of mass four and two hydrogen nuclei, giving to nitrogen the known atomic weight 14 This observation opens a new field of inquiry into the structure of atomic nuclei, for with **a-particles of greater enejgy *it* should be possible to disintegrate**

other nucler besides that of nitrogen Analogous effects have, in fact, been observed with boron, fluorine, sodium, aluminium, and phosphorus [1] It thus appears that some, if not all, of the elements are built up from helium and hydrogen nuclei For the latter fundamental constituent of matter Rutherford has suggested the name *proton*

655 When the B-particles are expelled from radium they carry with them negative electricity and must leave the radium positively charged This is clearly shown by the contrivance called the *Radium clock* [2] This consists of a small tube containing some radium compound, which is attached at its upper end by an

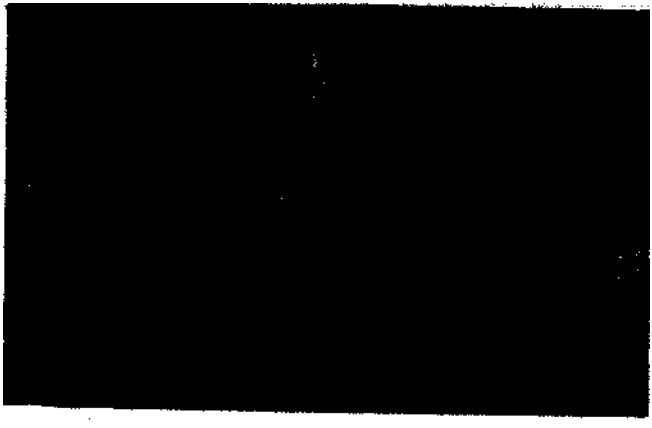

FIG. 212.—α-Rays from radium. Some of the α-particles have traversed the air before the expansion, others after the expansion.

insulating rod of quartz to the top of a wider tube within which it hangs At the lower end of the small tube two thin gold leaves are attached, the outer surface of the tube having been coated with phosphoric acid to render it conducting The larger tube is coated on the inside with tinfoil, connected to earth, and is exhausted as completely as possible to reduce the loss of charge consequent on lonisation of its gaseous contents With 30 mgrms of pure radium bromide the leaves are observed to diverge, until they touch a piece of metal connected to earth, when they collapse, and then gradually diverge again, this

[1] Rutherford, *Proc Phys Soc Lond* , 1921, 33, 389 See also Rutherford, "Artificial Disintegration of the Elements," *Journ Chem 80c* , 1922,121, 400, and Rutherford and Chadwick, *Phil Mag* ,1921, 42, 809

[2] Strutt, *Phil Mag* , 1903, [6], 6, 588

periodic movement of the leaves occupying about a minute The effect is due to the stoppage of the a-particles with their positive charge by the thin glass of the inner tube, which, however, allows the yS-particles to pass through The rhythmic motion continues with regularity for years, and it is estimated that it would take more than two thousand years for the emission of /3-particles to fall to half its present rate, when the movement of the gold leaves would take place in two minutes instead of one

The emission of B-rays from radioactive atoms is far more complicated than the emission of a-rays, for although, as in the case of a-rays, it seems possible that only one /3-particle is emitted for each atom disintegrating,[1] the particles are emitted with very different velocities By subjecting the radiation to a magnetic field the rays can be separated into definite groups known as a *magnetic spectrum* It has been shown that in and its di products there are a great number of groups of rays [2] It seems probable that the B-particles from any particular product are all projected with the same initial velocity, but that they are retarded to different extents while escaping from the atom [3]

FIG 213—Acorn plete *a* ray from radium emanation

The phenomena involved in the passage of a-, B-, and y-rays through air have been very strikingly demonstrated by C T E Wilson[4] When an *a*- or B-particle passes through air, very intense lonisation is produced in the track of the particle If the air is saturated with water vapour, and if, by sudden expansion, the air is cooled iminediately after the passage of the particle, a cloud is formed along its track By a suitable timing device, an instantaneous photograph is obtained of the cloud, which thus renders visible the track of the particle In the case of the a-particle the track is almost straight, showing only an occasional and sudden deflection or " scattering " from its course At the

[1] Moseloy, *Proc Boy Soc* , 1912, *[A],* 87, 230
[2] Danysz, *Le Radium*, 1913,10, 5
[3] Rutherford, *Phil Mag* , 1912, [6], 24, 453
[4] *Proc Roy Soc,* W12, *[A},* 87, 277

end of its range, the scattering of the a-particle is more marked (Fig 212) The photograph exhibit also, on careful inspection, the lonisation produced by an atom recoiling from the a-particle when struck by it (Fig 213) In the case of the y-particle, the path is much more tortuous, showing the greater part played by scattering in the case of these particles (Fig 214) With y-rays the photographs are much more complicated and consist of innumerable ramifications along the path of the rays The photographs are such as to indicate that the lonisation is not

FIG 214 —lonisation by B rays

produced by the y-rays themselves, but by secondary B-rays produced in their path—a suggestion first put forward by Bragg (Fig 215) i

A remarkable property of the compounds of radium, first observed by Curie and Laborde,[2] is that of maintaining themselves constantly at a higher temperature than the surrounding atmosphere, the difference observed being from 3° to 5° The continuous emission of heat which this shows was found by Curie and Dewar to be unaffected at the temperature of liquid air or liquid hydrogen They found that O 7 grm of pipe radium bromide, surrounded by liquid hydrogen, caused the vola-

[1] *Phil Mag* , **1910, 20,** 385, *Proc Boy Soc* , **1911,** ***[Al*** **85, 349**
[2] ***Compt rend,*** **1903,136, 673**

tilisation of 73 c c of hydrogen per minute From data thus obtained it appears that one gram of radium emits nearly as much energy as would decompose one gram of water every day, or, otherwise expressed, that one pound of radium emits energy at the rate of about 1 1 ^ horse-power

It does not seem possible that radium derives its enormous store of energy from external sources The more probable supposition is that the a-particles are originally in rapid motion in the atom and that an a-particle when released from the atomic system flies off with the velocity it had in the atom

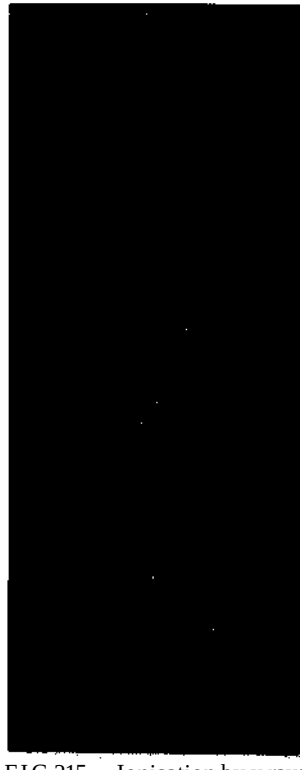

FIG 215 —Ionisation by y rays

The view that the energy emitted by radioactive bodies is derived from a store in the atoms is supported by the fact that the energy is given off at a rate which is quite unaffected by variations in physical and chemical conditions such as temperature, pressure, or mode of combination of the element, for it is difficult to account for these facts on any other supposition

THE PRODUCTS OF RADIOACTIVE CHANGE

656 A most remarkable property possessed by radium, actinium, and thorium, but not by uranium, is the power of giving off continuously a radioactive gas which can be condensed by extreme cold The radioactivity of thorium was observed to vary capriciously, and this inconstancy was traced by Owens[1] to currents of air which removed the gas Rutherford[2] gave the name of *emanation* to this remarkable gas, which discharges an electroscope, affects a photographic plate, diffuses through porous substances, and can be washed through water without loss of activity, it is condensed at the temperature of liquid air,[3]

[1] *Phil Mag*, 1899, [5], 48, 360 [2] *Ibid*, 1900, [5], 49, 1
[3] Rutherford and Soddy, *Phil Meg*, **1903, 3.[6], 5, 561.**

but not at that of solid carbon dioxide It thus behaves differently from the ionised gas produced by X-rays, since the conductivity of such ionised gas is completely removed by passing through cotton wool, or by bubbling through water The emanation from thorium rapidly loses its activity with time, falling to half value in about one minute[1] Dorn[2] showed that radium compounds also gave off an active emanation, the amount obtained being much increased by heating the compound or by dissolving it in water

These discoveries have led to the recognition of a hitherto unsuspected phenomenon, the spontaneous disintegration of the atoms of an element in a series of stages, each being marked by the emission of certain definite particles and in the case of a-ray transformations the production of a substance of lower atomic weight, characterised by definite physical and chemical properties. According to this *theory of the spontaneous disintegration of matter,* put forward by Rutherford and Soddy, in each second a proportion of the atoms of a radioactive material becomes unstable, these atoms break up with explosive violence, the change being accompanied by the expulsion of an *a*- or a B-particle Thus the atom is to be regarded as a complex aggregate, which breaks up spontaneously with an evolution of energy enormous compared with that released in ordinary chemical action These aggregates behave like atoms in that they cannot be split up by ordinary chemical or physical agencies

The rate of change of any single product at any time is found to be proportional to the number of atoms present at that time, so that the change follows the same law as a monomol^cular chemical reaction. Hence if N_0 represents the number of atoms of a radioactive substance present at any time, and N the number present after the lapse of time t, then

where X is known as the *disintegration constant* of the substance, and *e* is the base of the natural logarithms By differentiating this equation it is seen that

[1] Le Rossignol and Gimingham *(Phil Mag* , 1904, [6], 8,107) found that the activity fell to half value in fifty one seconds, Bronson *{Amer J Set,* 1905,**19,** 185) found fifty-four seconds

[2] *Naturforsch Ges* ***Halle*** **(1900)**

from which it follows that X represents the fraction of the total number of atoms undergoing disintegration at any instant. The rate of disintegration of a substance is expressed by the constant X, but it is more usual to define the rate of decay by the time *T* taken for half the number of atoms present to disintegrate The value of *T* is connected with X thus .

$$T = \frac{1}{\lambda}\log_e 2 = \frac{0\ 693}{\lambda}.$$

The quantity *T* is known as the *period of half-change* of the substance, $\frac{1}{\lambda}$ being the *period of average life* of the atom

When an active product is removed from a radioactive substance, *e g*, the emanation from a thorium compound, the activity of the isolated product gradually falls, according to the foregoing law, whilst that of the parent substance rises, also according to that law, owing to the accumulation of a fresh quantity of the active product After the expiration of any period it is found that the isolated product has lost a certain fraction of its original activity whilst the parent substance has regained the same fraction of the activity which it had lost

The determination of the exact series of changes undergone by a radioactive substance is a matter of considerable difficulty, and the solution of the problem is due largely to the brilliant researches of Rutherford and his colleagues For this purpose it is necessary to measure separately the radioactivity due to the a-, the B-, and the y-rays, and to construct curves showing the variation of each of these with time The differentiation of the action of the three types of ray is effected by taking advantage of their different penetrating powers, sheets of metal of sufficient thickness to absorb the a-rays, or both the a- and B-rays, being interposed between the material and the electroscope The B- and y-rays are also often separated by deflecting the B-rays by a magnetic field

From a comparison of the curves thus produced the number of change which occur, the nature of the radiation, and the rate of the change can be deduced The matter is much simplified when the products can be separated either physically or chemically from the parent substance and subjected to examination, as is the case with the emanation of radium, etc

In most cases of radioactive changes, the products are formed **from** each **other in a direct series of transformations. Thus**

any particular type of radioactive matter breaks up at a perfectly definite rate always giving we to the same substance—the next member in the radioactive series Some very interesting cases have, however, come to light in which it appears that certain types of atom can break up in two different ways, thus giving rise to two distinct products This has been found to be the case with radium-C[1] (p 1525), thormm-C,[2] and actinium-C (p 1531-2) Thus radium-C usually disintegrates with the 'production of radium-D through the very short-lived product RaC, but occasionally an atom of radium-C gives rise to another product, radium-C", instead of radium-C [3] In the case of thorium-C the proportion of atoms giving rise to a branch product is much greater, for one-third of the atoms of thorium-C break up with the emission of a-rays and produce thorium-C", whereas two-thirds emit £-rays and give rise to the product thorium-C [4] Both the C and C" products seem to give rise to the D products (p 1531) Another important case of a branch product is that of uranium-Y,[5] which forms the starting point of the actinium series (p 1527)

Recently great interest has centred in the question of the position of the radioactive elements in Mendeleev's periodic system It has been pointed out by Fajans [6] that when a transformation takes place with the emission of a B-particle the resulting product is more electronegative than the parent substance Exactly the reverse is the case when a transformation takes place with the emission of an a-particle It has been shown by Soddy[7] that during an a-ray transformation the atom passes from a family of even number in the periodic table to the next lower even family, the families of the odd numbers being always missed This rule has been generalised and extended to include the case of B-ray transformations by Russell,[8] and by Fajans,[9] who has shown that in all cases in which the chemical nature of the radioactive products is sufficiently well known to test its correctness, the following rule holds In an a-ray transformation the product generated falls into a group *two* places lower than that

[1] Hahn and Meitner, *Physikal Zeit,* 1909,**10,** 697
[2] Hahn and Meitner, *Verh dent physikal Ges,* 1909,**11,** 55
[3] Fajans, *Physikal Zeit,* 19^1,**12,** 369
[4] Marsden and Darwin, *Proc Boy Soc* , 1912, *[A],* 87, 17
[5] Antonoff, *Phil Mag,* 1911, [6], **22,** 419
[6] *Physikal Zeit,* 1913,**14,** 131
[7] *Chemistry of the Radio-Elements,* p 30
[8] *Chem News,* 1913,**107, 49**
[8] ***Ber*, 1913, 46,422, and** *Physikal.* ***Zeit*, 1913,14,136.**

to which the parent substance belongs On the other hand, in a B-ray transformation the product generated falls into a group *one* place higher than that of the parent substance These laws are exemplified in the table (p 1517). It will be seen that a single space in the periodic table is in each case occupied by several different products which are inseparable by any chemical process and can be distinguished only by their radioactive properties Thus for instance Actimum-X, Thonum-X, Kadmjn, and Mesothorium are inseparable by any chemical process Here we have another example of *isotopic* elements *(cf* pp 74, 1498, 1517)

RADIUM. Ra==226 At No 88

657 The mineral pitchblende—an impure oxide of uranium (p 1149)—is the richest source of radioactive substances Whilst investigating this material Mine Curie found that some specimens of pitchblende had four times the activity of the metal uranium, and by chemical methods M and Mine Currie succeeded in separating two new substances, characterised by intense radioactivity, which they named polonium and radium

The history of Mine Curie's successful search for a radioactive substance in the residues of the pitchblende of Joachimsthal is of great interest[1]

For the extraction of uranium the crushed ore is roasted with sodium carbonate, and washed with warm water and dilute sulphuric acid, the solution contains the uranium, and the insoluble residues are rejected The Austrian Government presented Mine Curie with a ton of these residues, the activity of which was found to be about four and a half times that of uranium The residues consist chiefly of the sulphates of lead, barium, and calcium, silica, alumina, and oxide of iron, and contain also small amounts of copper, bismuth, zinc, cobalt, manganese, nickel, vanadium, antimony, thallium, the rare earths, columbium, tantalum, arsenic, etc The search for the radioactive substances which cause the high activity of pitchblende was made in the early stages by the ordinary methods of chemical analysis The residues were first treated with boiling soda, and tie sodium sulphate formed removed by washing, together with lead, strontium, and aluminium The insoluble portion was

[1] **See translation of thesis presented to the Faculty des Sciences of Paris, *Chem News*, 1903, 88, 86.**

attacked by hydrochloric acid, which dissolves most of it The residue from this operation was found to contain a radioactive substance which received the name *radium* The solution also was found to contain radioactive substances, one of which is precipitated by sulphuretted hydrogen together with bismuth, and received the name *polonium.* A second, discovered by Debierne,[1] and named *actinium,* is contained in the hydroxide precipitated by ammonia in the filtrate from the precipitated sulphides

658 *Purification and Properties of Radium Salts* —The radium is extracted from the insoluble portion mentioned above by boiling with a strong solution of sodium carbonate, which transforms the barium and radium into carbonates These are washed and dissolved in hydrochloric acid, and sulphuric acid is added, which precipitates the sulphates of barium and radium, with calcium, lead, iron, and a trace of actinium

One ton of the Joachimsthal residues yielded from 10 to 20 kilos of the crude sulphates, of an activity about 60 times that of uranium. The crude sulphate is next transformed into chloride, treated with sulphuretted hydrogen, the filtrate oxidised with chlorine, and precipitated with ammonia The filtrate is then precipitated with sodium carbonate, and the carbonates are converted into chlorides, and washed with pure strong hydrochloric acid, which dissolves calcium sulphate, leaving barium and radium chlorides These chlorides are then separated by repeated fractional crystallisation from water When only a small quantity of crystals is allowed to separate, it is found that five times as much radium separates with the crystals as is left in solution. By repeating this process a great number of times a fraction of a gram of radium chloride was obtained of an activity a million times that of uranium

Giesel[2] employs the bromides instead of chlorides in the fractional separation of radium and barium the radium separates with the least soluble portion, and about eight fractionations effect the removal of most of the barium

The compounds of radium resemble those of barium in properties The crystals of the chloride are isomorphous with th^se of barium chloride, when pure they are colourless, but those containing both barium and radium become coloured yellow, orange, or pink. The solution in water evolves hvdrogen and

[1] *Compt rend*, 1899, **129,** 593, 1900, **180,** 906, 1903, **186,** 446, 767
[2] *Ann. Phys Chem.*, 1899, [2], **69,** 91, Ber., 1902, **86,** 3608.

Group in Periodic System
Element of Highest Atomic Weight
VIIA
VIA
VA
IVA
IIIA
IIA
IA
O
VIIB
VB
IVB
IIIB
IIB
IB
Uranium Series
U
Ur 1
Ur 2
Ta
UrX2
UrX1
Th
Io
UrY
Protactinium
La
Actinium
Ra
RaEm
ActX
ActEm
RaA
RaB
RaC
RaC'
RaD
RaE
RaF
RaG (Lead)
ActA
ActB
ActC
(ActC')
ActD (Lead)
Ac
RadioAct
Th
MesoTh 1
MesoTh 2
RadioTh
ThX
ThEm
ThA
ThB
ThC
ThC'
ThC''
ThD (Lead)
Thorium Series
Ce
I
Te
Bi
Pb
Tl
Hg
Au

oxygen continuously The *nitrate, carbonate, sulphate, bromide,* and *platinocyanide* resemble the corresponding salts of barium very closely When freshly prepared the anhydrous bromide exhibits a splendid blue phosphorescence, which gradually disappears, but is more permanent in the presence of barium salts

Radium has been prepared in the metallic state by Curie and Pebierne [1]

659 *Spectrum of Radium* —Radium is found to have its own characteristic spectrum and this affords one of the strongest proofs of its elementary character Radium bromide colours the Bunsen flame a pure carmine-red, and the flame shows four bands or lines in the red and a strong line in the blue

The spectrum [2] of radium has been investigated by Demar§ay,[3] Runge,[4] Exner, and Haschek,[5] Runge and Precht,[6] and Crookes [7]

The most intense lines in the spark spectrum are 4683, 4436, 4341, 3814, 3650, 2814, and 2709

660 *Atomic Weight of Radium*—The atomic weight was determined by estimating the percentage of chlorine in the anhydrous chloride As only about one decigram of substance was available, Mine Curie [8] made preliminary determinations of the atomic weight of barium with about the same weight of pure barium chloride, and found that good results could be obtained With barium chloride of an activity 600 times that of uranium the number 137 was obtained, with that of 7,500, the result was 143 8, and with chloride of increasing activity the atomic weight increased, giving about 225 with a specimen which only showed very faint traces of the brightest barium lines in the spectroscope This sample was repurified, and gave the following results

Radium chloride taken	Silver chloride obtained	Atomic weight (H = 1)
O O9192	O O8890	225 7
O O8936	O O8627	226 2
O O8839	O O8589	224 5

The activity of this chloride was about two minion times that of uranium A later determination made by Mine 'Purie

[1] *Compt rend* , 1910,**151,** 523, *Le Radium* 1910, 7, 309
[2] See Watts, *Index of Spectra,* Appendix O, p 40
[3] *Compt rend,* 1898,**127,** 1218
[4] *Ann Physik,* 1903,12, 407
[5] *Wien Ber* , 1901, July 4
[6] *Ann Physik,* 1904, 14, 418
[7] *Proc Boy Soc* , 1904, **72,** 295
[8] *Compt rend,* 1899, **229,** 760, 1900, **Isi, 382,** 1902,**185, 161.**

in 1907 gave the value 226 4,[1] and Thorpe[2] found the value 226·7 Ramsay and Gray[3] give the value 226 45 A determination with a large quantity of radium, which therefore probably gives the most trustworthy result, has been made by Honigschmid,[4] who finds the atomic weight to be 225 95 This number is in harmony with the chemical behaviour of radium, which then finds its place in the periodic table in Group II, Series 12

Runge and Precht[5] have made calculations of the atomic weight of radium from the spectrum, and have deduced the value 256 3 This assumes that radium really belongs to the group of alkaline earths, and is based upon the observation that radium, like Mg, Ca, Sr, and Ba, has in its spectrum pairs of lines, repeated several times, with a constant difference of oscillation frequency, and that the distance apart of these pairs for the different elements increases in a regular manner with the atomic weight (p 165)

It must be remembered that this calculation amounts to an extrapolation passing over the unknown element below barium in the perio for a considerable distance It has been pointed out[6] that the result of the calculation is probably too high, for the reason that a similar calculation of the atomic weight of mercury from those of zinc and cadmium gives the atomic weight too high by about 22 units it seems probable that this method has a tendency to give results too high for the higher atomic weights A similar criticism has been made by Rudorf[7] Furthermore, in the case of radium the atomic weight obtained by the spectroscopic method disagrees with strong evidence derived from a consideration of the disintegration theory (p 1512), for there is reason to believe that radium is formed from uranium with the emission of three a-particles Taking the atomic weight of uranium as 238 the atomic weight of radium should be 226, agreeing with the values found by chemical methods.

The question of establishing a standard quantity of radium was discussed at the International Congress of Radiology (Brussels, 1910) As a result 21 99 milligrams of the radium chloside used by Mine Curie in the determination of the atomic

[1] *Compt rend*, 1907, **146,** 422
[2] *Proc Roy Soc*, 1908, *[A]*, 80, 298
[3] *Proc Roy Soc*, 1912, [4], 86, 270
[4] *Sitzunfsber K Akad Wtss Wien,* **1911, Ha, 120, 1617**
[5] *Phil Mag*, **1903,** [6], **5, 476** [6] Watts, *ibid*, 6, 64
[7] *Zett physikal Chem* **1904, 60, 100**

weight of radium have been sealed in a small glass tube and deposited at Pans in the Bureau International des Poids et Mesures A similar reserve standard has been deposited in Vienna With the aid of these standards the quantity of radium in any sample can be estimated by comparing the 7-radiation it emits with that emitted by the standard

'PRODUCTS FORMED FROM RADIUM BY RADIOACTIVE CHANGF

661 *Production of Helium by the Spontaneous Change of Radium* —In 1903 Ramsay and Soddy [1] made the remarkable discovery that helium is given off by radium They found that 30 milligrams of pure radium bromide (which had been prepared three months) when dissolved in water liberated gases amongst which were hydrogen and oxygen These were removed by passing the gas over a red-hot spiral of partially oxidised copper wire, and then over phosphoric anhydride into a vacuum tube joined on to a small U-tube

By placing the U-tube in liquid air most of the emanation present was condensed The spectrum of the gas left in the vacuum tube, including the carbon dioxide present in the original gas, was then observed and showed the characteristic hehum line D_3 In a repetition of the experiment the helium lines at 6677, 5876, 5016, 4922, 4713, and 4472 were observed as well as three unknown lines at 6180, 5695, and 5455 They also found that the emanation alone yielded helium in about three days

These observations have been repeated and confirmed by Dewar and Curie [2] and by Himstedt and Meyer [8] The latter observers sealed up 30 milligrams of radium bromide in an exhausted vacuum tube The tube showed the lines of hydrogen and an oxide of carbon at first, but after four months the helium lines appeared

Before the discovery of the production of helium in radioactive processes it was suggested by Rutherford and Soddy [4] that this gas might be a disintegration product of the radioelements This has since been proved by Rutherford and Royds [5] by sealing up some radium emanations in a glass tube, the thickness of the walls of which was only O·O1 millimetre The a-particles which passed through the walls of this tube

[1] ***Proc Boy Soc*, 1903, 72, 206, 1904, 78, 346**
[2] ***Compt rend*, 1904, J£8, 190** [3] ***Ann Physik*, 1904,15, 184**
[4] ***Phil Mag*, 1902, 4, 569, 1903,5, 57C** [5] ***Ibid*, 1909,17,281**

were collected in a vessel which surrounded it, after some days the spectrum of helium could be detected in the outer vessel, proving that the a-rays consisted of charged atoms of helium

The rate of production of helium from radium has been measured by Dewar,[1] and by Boltwood and Rutherford[2] From one gram of radium (metallic) in equilibrium with the emanation, radium-A, and radium-C, the latter find that 156 cubic millimetres of helium are produced per year. Dewar found the value 169 cubic millimetres per year, which must, however, be slightly corrected to be comparable with the number found by Boltwood and Rutherford on account of the difference in the values of the radium standards used in the two sets of experiments When thus corrected the value found by Dewar becomes 164 cubic millimetres The volume of helium to be expected from theoretical considerations is 158 cubic millimetres per gram of radium per year

662 *Radium Emanation* —The emanation is continuously produced from radium compounds and is itself strongly radioactive A portion of it escapes, but the remainder is occluded in the compound To this is due the phenomenon, observed by Curie, that the activity and emission of heat of radium compounds vary with their age, the activity increasing for about a month after preparation, when it becomes steady This state of radioactive equilibrium is reached when the rate of production of fresh emanation balances the rate of change of that already formed

The emanation is formed from radium by the expulsion of an a-particle and itself passes into the next lower product by a similar change. The period of half-change for radium is about 2,O00 years, and for the emanation 3 85 days By measuring the emanation from O O6 gram of radium bromide, Ramsay and Soddy conclude that the maximum amount of emanation obtainable from one gram of radium is one cubic millimetre This quantity is known as one *curie* Later determinations by Rutherford,[3] Debierne,[4] and Gray and Ramsay[5] give the value O 6 eubic millimetre

The emanation is most readily obtamed by dissolving the radium compound in water and removing the gases produced,

[1] *Proc Roy 89c*, 1908, *[Al* 81, 280, 1910, 83, 404
[2] *Phil Mag* , 1911,28,586 [2] *Ibid*, 1908, 16, 300
[4] *Compt, rend.,* 1909,**148,** 1264. [5] *Journ. Chem, Soc.,* 19QO, 96,1073.

This is best done by causing the solution to boil under reduced pressure If air be passed through a radium solution large quantities of a mixture of air with the emanation may be obtained, and this may be stored in a gas-holder, and the electrical and photographic action examined for days after its production The emanation can also be removed by heating the salt When mixed with a large volume of air it condenses at —154°, but it must be remembered that in these circumstances the partial pressure of the emanation is exceedingly minute When purified and at atmospheric pressure the emanation boils at — 65°[1] When at very low partial pressures, the condensation pomt of the emanation seems to depend upon the nature of the surface upon which it condenses[2] If the emanation obtained from a few milligrams of radium bromide by heating a solution be condensed in a small U-tube surrounded by liquid air, the U-tube being connected with a larger tube containing a small phosphorescent screen of zinc sulphide, and the whole apparatus connected with an air pump, the behaviour of the emanation can be watched by means of the phosphorescence of the screen The apparatus being partially exhausted, and the U-tube iminersed in liquid air, no luminosity of the screen is observed, but if the liquid air be removed, in a few minutes the emanation diffuses into the wider tube, and the screen becomes brightly phosphorescent If the U-tube be re-iminersed in liquid air the emanation re-condenses, but the phosphorescence of the screen dies away only slowly, being maintained for some time by the production of an active deposit on the glass

In another experiment a quantity of the emanation was collected in a small glass tube, which was seen to phosphoresce brightly under the rays from the emanation, and in a dark room the passage of the emanation from point to point of the tube could be traced On opening the tap which connected the tube with the pump the slow flow of the emanation through the capillary portion of the tube and its more rapid passage through the wider portions was well seen

The emanation obeys Boyle's law Attempts to determine its density by measuring its rate of diffusion show that it is a heavy gas, of a density about 100, the method of diffusion is, however, for a variety of reasons unsuitable for determining the

[1] **Rutherford,** ***Phil Mag,*** **1909,17, 723**
[2] **Laborde,** ***Le Radium,*** **1909, 6, 289; 1910, 7, 294, Boyle,** ***Phil Mag*** **1910, 20, 955.**

atomic weight of the emanation From a consideration of the disintegration theory of radioactive changes, the atomic weight of radium emanation should be 222 Assuming the emanation to be monatomic, Gray and Ramsay[1] find the value 223, by a direct determination of its density with a specially constructed sensitive balance The emanation belongs to the helium-argon group of gases, and like them resists attack by all chemical agents that have been tried It is not affected when led in tubes over platinum black, copper oxide, zinc dust, etc, at a high temperature, and is unaffected by prolonged sparking with oxygen over caustic potash

The spectrum of the emanation was first examined by Ramsay and Collie,[2] and later by Rutherford and Royds,[3] Cameron and Ramsay,[4] Watson,[5] and Royds[6] The brightest lines are those of wave-lengths 4681-1, 4644 7, 4460 O, 4350 3, 4308 3, 4203 7, 4166 6, 4018 O, 3982 O, 3753 6, 3664 6

Rutherford and Barnes[7] have made experiments on the heat emission by radium bromide and by the emanation obtained from it The heat emission per gram of radium bromide was found to be 65 gram-calories per hour (which corresponds to 110 gram-calories per hour per gram of radium itself) The emanation was then driven off, and condensed by means of liquid air After removal of the emanation the heat emission of the radium bromide fell off in three hours to about one-quarter (27%), and then slowly increased, reaching its original rate in about a month The heat emission from the separated emanation rose to a maximum in three hours, and then slowly decayed, falling to a half value in about 3 7 days The rate of decay of the emanation and the rate of recovery of the radium compound are both expressed by the exponential formula

where Q is the heat emission at first, and Q_t that after a time t_9 X being the constant of change The radioactivity itself also follows a similar law, but the variation in the heat emission both of radium and of the emanation correspond approximately to the activity as measured by the a-rays and not to that of the B- or y-rays The heat emission of radium thus corresponds approximately with the expulsion of a-particles

[1] *Proc Roy Soc* , 1911, *[Al* 84, 536
[2] *Ibid,* **1904,** 73, 470 [3] *Phil Mag,* 1908,**16,** 313
[4] *Proc Roy Soc,* 1908, *[A],* 81, 210 [5] *Ibid,* [A] 1909, **83,** 60
[6] *Phil Mag,* **1909,17, 262** [7] ***Ibid,*** **1904 [6] 7. 202.**

The most recent and accurate determinations of the heating effect of radium are by Meyor and Hess,[1] and by Rutherford and Robinson[2] The former give, for the heat emitted by one gram of radium in equilibrium with its disintegration products the value 132 3 and the latter the value 135 gram-calories per hour Rutherford and Robinson have also determined the heat emitted by each of the disintegration products separately, and also estimate that the B-rays contribute 3 5 per cent and the 7-rays *4* 8 per cent of the total heating effect of radium The observed heat emission is in good agreement with the calculated kinetic energy of the radiations The heat emitted by radium and its products of disintegration is shown in the following table

	Heating effect in gram-calones per hour, corresponding to one gram of radium			
	a-Rays	B Rays	y-Kays	Total
Radium	25 1			25 1
Emanation	28 6			28 6
Radium A	30 5			30 5
Radium-B				
Radium C	39 4	47	64	50 5
Totals	123 6	47	64	134 7

When the emanation is left in contact with water, the latter is decomposed, a mixture of hydrogen and oxygen containing an excess of hydrogen being evolved. About 003 c mm of emanation yielded 2—4 c c of gas in different experiments, containing 3—14 per cent of hydrogen in excess The origin of this excess is not at present understood,[3] but it is probably in some way connected with the formation of ozone The emanation is also capable of bringing about the slow combination of gaseous hydrogen and oxygen

As already mentioned, the emanation on preservation yields helium, the volume of the latter being about three times as great as that of the emanation[4]

663 *Radium-A,* -J3, -C, -D, and -*E* —The radium emanation induces radioactivity on the glass in which it is contained, on

[1] *Wien Ber* , 1912, **121,** 603 [2] *Phil Mag* , 1915, **25,** 312
[3] See Ramsay, *Journ Chem Soc* , 1907, 91, 931
[4] Cameron and Ramsay, *Journ Chem Soc,,* **1907,91,1266**

removing the emanation the excited activity at once cominences to decay This excited activity is due to the deposit on the surface of bodies of active matter, which can be removed by solution in acid, and recovered on evaporation of the solvent It has the property of concentrating itself on a negatively charged wire Such a wire placed in the presence of the radium emanation becomes strongly active, and if drawn across a screen of zinc sulphide, some of the active matter is rubbed off, leaving a luminous trail

It has been ascertained that the deposited active matter from the radium emanation breaks up rapidly in successive and well-marked stages, yielding three ephemeral substances which have been named radium-A, radium-B, and radium-C, the first of these emits a-rays only, the last emits rays of all three kinds, and radium-B emits B- and 7-rays The emanation is half transformed in 3 85 days radium-A is half transformed in three minutes, radium-B takes 26 7 minutes, and radium-C 19 5 minutes for half transformation into a comparatively permanent product, radium-D This requires 16 5 years for half transformation into radium-E, half of which is transformed in 5 days into radium-F The complex nature of radium-C has already been discussed (p 1514)

,664 *Radium-F, Polonium, Radio-tellurium*—During the investigation of the pitchblende residues from which radium was isolated, Mine Curie obtained a second radioactive element to which the name of polonium was given This substance was found by Mine Curie to separate out with bismuth She employed three methods of separation

(a) Sublimation of the sulphides *%n vacuo* the active sulphide is the more volatile

(6) Precipitation of the nitrate by water the precipitate is the more active

(c) Precipitation of a strongly acid solution of the chlorides by sulphuretted hydrogen the precipitate is the more active

Marckwald[1] obtained a radioactive substance with tellurium as an impurity, which he called radio-tellurium It is undoubtedly the same as polonium Marckwald found that if a plate of bismuth be immersed in a solution containing polonium the active "matter is deposited on the plate, and the solution

[1] *Ber* ,100C, 35, 2285,4239, 1903,86,2662

remains inactive The active matter is also precipitated by treating the solution with stannous chloride From fifteen tons of pitchblende MarcKwald obtained sixteen grams of mixed selenium, tellurium, and polonium, from which, by treatment of the oxides with ammonia, an insoluble residue weighing three milligrams and containing all the active matter was obtained

The radiation is extremely active, consisting entirely of a-rays One-hundredth of a milligram produces intense phosphorescence in a screen of zinc sulphide The period of half change is 136 days, and in this respect and in the nature of its radiation polonium agrees exactly with radium-F, with which it is doubtless to be identified

Marckwald[1] considered that radio-tellurium or polonium would prove to be the missing element of the sulphur-selenmm-tellurium family, a supposition which has since been confirmed Since polonium (RaF), is produced from radium by changes involving the expulsion of four a-particles, it follows that the atomic weight of polonium should be 226 — 4 x 4 = 210 The product radmm-G formed from polonium has therefore an atomic weight 206, and has been identified as an isotopic form of lead Another isotope of lead has been separated from thorium minerals (p 940)

The lead salts separated from pitchblende are also radioactive, but it has been shown that they owe their activity to the presence of the transformation products of radium known as radium-D, -E, and -F

An interesting method of separating polonium from lead and radium-D by dialysis has been devised by Paneth,[2] who finds that polonium in solution behaves like a colloid and cannot diffuse through a membrane made of bladder or parchment Making use of this property it is possible to separate polonium from lead salts and other impurities

The properties of the various transformation products of radium are summarised in tabular form on p 1531

ACTINIUM Ac==226 At No 89

665 Actinium, discovered by Debierne,[3] is, no doubt, the same substance as that described by Giesel[4] under the name of

[1] *Ber* , 1905, **88,** 591 [2] *Monatsh* , **191$,** 34, 401
[3] *Compt rend,* 1899, **129,** 593, 1900, **130,** 206, 1903, **186,** 446, 767
[4] *Ber*, 1902, 35, 3608, 1903, **36,** 342, 1904,«7, 1696, 3963.

emanium It was discovered in the precipitate of rare earths separated from pitchblende, the bulk of which consisted of thoria, and was finally obtained mixed with lanthana It gives a characteristic emanation, and imparts activity to neighbouring objects

Debierne has shown that actinium, like radium, gives rise to helium proportionate in quantity to the activity of the preparation

The present state of knowledge regarding actinium is summarised in the table on p 1531

Boltwood [1] has shown that the amount of actinium present in uranium minerals is approximately proportional to the uranium content of the mineral This fact suggests a genetic connection between actinium and uranium, but actinium is not in the direct series of disintegration products of uranium The connection between uranium and actinium has been established by Hahn and Meitner,[2] who showed that actinium is derived from uranium 2 through the branch product uranium-Y (p 1532), and a new product of very long life which they called *protacttinum*

THORIUM Th = 232 4. At No 90

666 As already mentioned, the radioactivity of thorium was discovered by Schmidt and by Mine Curie, and the existence of an emanation by Rutherford

Rutherford and Soddy,[3] by adding ammonia to a solution of a thorium salt, so as to precipitate the thorium as hydroxide, found that the filtrate contained a substance many times more active than the thorium itself This active constituent they named thorium-X in a month's time it had completely lost its activity while the thorium had completely recovered its original activity The decay of activity of the thorium-X, and the recovery of the activity of the thorium, are found to be represented by exactly similar curves, the time required for decay to half value, or for the recovery of half the lost activity, being in each case 3 7 days

thorium-X appears not to bg formed directly from thorium, but through three intermediate products, mesothorium 1,

[1] ***Amer J Set*, 1908, 25, 269**

[2] **Hahn andJMeitner, *Phys Zeit*, 1918, 19, 208, 1919,20, 127, 529, also Hahn, *Phys Zeit*, 1920, 21, 591**

[3] ***Phil Mag*, 1906, [6], 4, 370, 509**

mesothorium 2, and radiothorium [1] Radiothorium cannot be separated from thorium b^any known chemical process, nor can mesothorium 1 be separated from thorium-X, but the first two substances can be separated from the second two by adding excess of ammonia to a solution of thorium nitrate The further changes undergone by this substance are summarised on p 1521

The final product of disintegration of thorium has been shown to' be an isotopic form of lead, the atomic weight of which should from theoretical considerations be 208 Estimations of the atomic weight of lead separated from Ceylon-thorite give the values 207 74 [2] and 207 77,[3] the difference between these numbers and the theoretical number (208) being no doubt due to a slight admixture of lead derived from radium with atomic weight 206 This demonstration of the existence of two forms of lead with atomic weights 206 and 208 respectively affords one of the most direct and striking proofs of the theory of isotopes

Thorium, radium, and actinium exhibit many points of similarity, each gives an emanation whose life is short, these emanations have no definite combining properties, and belong to the helium-argon group of inert gases, in each case the emanation gives rise to a non-volatile substance (thorium-A, radium-A, actinium-A) which deposits on the surface of bodies, and is concentrated on the negative electrode in an electric field The emanations and the subsequent disintegration products show very striking analogies both with regard to the radiations emitted by each product and other properties This can be seen from the table given on p 1531

URANIUM U = 2382 At No 92

667 The discovery of the radioactivity of uranium by H Becquerel, in 1896 was, as already mentioned (p 1490), the starting point of the series of brilliant investigations by which the science of radioactivity has been established There is strong evidence derived from the radioactive properties of uranium that this body really consists of two distinct elements which, however, are so similar to each other as to be inseparable

1 Hahn, *Proc Boy Soc*, 1905,*[Al*76, 115, *Ber*, 1907, 40, 1462, *Physikal zeit*, 1907, 8,277, *ibid*, 1908,9, 246

2 Soddy, *Science Aba* , 1916, 502

3 Homgschmid, *Zeit Elektrochem.*, 1917, g3, 161, *Phys, Zett*,, 1917,18, 114.

by chemical methods The evidence rests on the fact, first noticed by Boltwood and subsequently confirmed by Gerger and Rutherford,[1] that an atom of uranium appears to give out two a-particles during the disintegration instead of one, as is the case with most radioactive atoms emitting a-rays This fact can only be explained either by supposing uranium to consist of two successive disintegration products, or by assuming that an atom of uranium gives out two a-particles simultaneously The latter hypothesis has been disproved by Marsden and Barratt,[2] and Geiger and Nuttall[3] have shown that the a-particles are not homogeneous The two types of uranium are known as uranium 1 and uranium 2, the half change period of one of which is 5×10^9 years

Von Hevesy[4] has shown that the valencies of the radio-elements can be found by observations on their rates of diffusion and mobilities in solution It is shown that at any rate in many cases the expulsion of an a-particle by a parent substance gives rise to a change of valency of two units in the resulting product It has been shown by von Hevesy and von Putrioky[5] that uranium 1 and uranium 2 cannot be separated by diffusion, and that uranium 2 is not only very similar to uranium 1, but has also the same valency as that element In fact they are isotopes

Crookes showed[6] that by a single chemical operation, viz , by precipitating a uranium salt with ammonium carbonate in excess, the whole of the photographic activity of uranium was concentrated in the precipitate, and the uranium left in solution was photographically inactive The precipitate containing a substance which he called Uranium-X was, photographically, many hundred times as active as the uranium from which it had been separated Becquerel[7] found that on adding barium chloride to a solution of uranium salt and precipitating as barium sulphate, the precipitate was strongly active, photographically, and the uranium had lost its activity A year later it was found that the barium had become inactive, whilst the urarjium had completely regained its activity

The uranium deprived of uranium-X, although photographically inactive, is electrically active, this being due to the fact

[1] *Phil Mag*, 1910, 20, 691 [2] *Proc Phya Soc* , 1911, 28, 367
[3] *Phil Mag*, 1912, 82, 439 [4] *Ibid*, 1913, 25, 390
[5] *Ibid*, 26, 415 [6] *Proc Soy Soc* , 1900, $6, 409
[7] *compt rend*,, 1900,181, 137, 1901,188, 977

that the a-particle which it emits is incapable of producing much photographic action Uraruum-X can also be separated from uranium salts by boiling with lampblack, which retains this product [1] Uranium-X emits only B- and y-rays and has been shown to consist of two products, uranium-X_1 and uranmm-X_2, having half change periods of 24 6 days and 117 minutes respectively.[2] They are intermediate between uranium 1 and uranium 2, which parses into *ionium,* the parent of radium

668 *Relation of Uranium and Radium*—The further history of the transformation of uranium is interesting, for many facts point to the conclusion that radium is one of its transformation products This was first surmised from the fact that the radio-activity of the uranium minerals is proportional to the quantity of uranium present[3] (in the absence of thorium) The ratio of uranium to radium in such minerals is almost constant,[4] and these facts are most readily explained by the supposition that the radium is actually formed from the uranium. The production of radium from "uranium has been measured by Soddy,[5] and by Boltwood,[6] who carefully freed uranium from radium and measured by the emanation test the amount of radium present after the lapse of a year or two It was found that the rate of production of radium was far less than was to be expected if radium were formed directly from uranium This seemed to indicate the existence of an intermediate product of slow rate of decay This product has since been separated from carnotite by Boltwood,[7] who gave it the name *imium* This element is the direct predecessor of radium in the disintegra-tion series From measurements on the rate of growth of radium from uranium Soddy [8] suggested that the half-change period of ionium is of the order 100,O00 years This value is confirmed by Geiger and Nuttall, who, having determined the range of the a-particle from ionium, deduced its half-change period to be 200,000 years (p 1505)

[1] **Beoquerel,** ***Compt rend,*** **1905,141, 485**
[2] **Fajans and Gohnng,** ***Die Naturwissenschaften,*** **1913, 14, 339**
[3] **McCoy,** ***Ber*** **, 1904, 37, 2641**
[4] **Strutt,** ***Proc Boy Soc,*** **1905,** ***76, [A],*** **88, 312, Boltwood,** ***Phil Mag,*** **1905, [6], 9, 599**
[5] ***PhiI Mag,*** **1905, [6], 9, 768, 1908, 16, 632, 1909, 18, 846, 1910, 20, 340**
[6] ***Amer J Set,*** **1905, 20,339**
[7] ***Ibid,*** **1906, 22, 537, 1907, 24, 370, 1908, 25, 365.**
[8] ***Phil Mag,*** **1909,18, 858**

669 The following tables summarise our present knowledge of the active products of disintegration of the radio-elements The column headed *half-change period* gives the time of falling to half activity, or the time required for half the substance to be transformed into the next product

URANIUM-RADIUM SERIES

Product	Half-change Period	Bays emitted and Ranges of a-particles in cm at 0°	Atomic Weight	Group in Periodic Table to which Product belongs
Uranium 1	5×10^9 years	a (2 53)	238	VIA
Uranium X_1	24 6 days	fry	234	IVA
Uranium-X_2	117 minutes	B, y	234	VA
Uranium 2	2×10^6 years	a (2'91)	234	*VIA*
(Uranium-*Y*)	25 5 hours		230	IVA
Ionium	2×10^5 years	a (3 O3)	230	IVA
Radium	2000 years	a, B (3 21)	226	IIA
Radium emanation	3 85 days	a (3 91)	222	O
Radium-A	3 O minutes	a (4 48)	218	; *VIB*
Radium-B	26 7 minutes	B, y	214	*IVB*
Radium-*C*	19 5 minutes	B, y	214	*VB*
Radium-*C*	10^{-6} seconds	a (6 61)	214	*VIB*
(Radium-C")	1 4 minutes	P	210	*IIIB*
Radium-D	16 5 years	fry	210	*IVB*
Radium *E*	5 days	B Y	210	*VB*
Radium *F* (Polonium)	136 days	a (3 72)	210	*VIB*
Radium-*G* (Lead)		—	206	*IVB*

THORIUM SERIES

Product	Half-change Period	Rays emitted and Ranges in cm of a-particles in air at 0°	Atomic Weight	Group in Periodic Table to which Product belongs
Thorium	1.3×10^{10} years	a (2 75)	232	
Mesothorium 1	6 7 years		228	IIA
Mesothorium 2	6 2 hours	B. y	228	IIIA
Radio thorium	1 9 years	a (3 31)	228	IVA
Thorium-X	3 7 days	a, p (4 13)	224	IIA
Thorium emanation	54 5 seoonds	a (4 80)	220	O
Thorium-A	O 14 second	a (5 39)	216	VIB
Thorium-*B*	10 6 hours	B, Y	212	*IVB*
Thorium *C*	60 8 minutes	a, B (4 54)	212	*VB*
Thorium-C")	(?) 10^{-11} sec	a (8 17)	212	*VIB*
Thorium-C"	3 1 minuted	B, Y	208	IIIB
Thorium *D* (Lead)			208	*IVB*

ACTINIUM SERIES

Product	Half-change Period	Bays emitted and Ranges of a-particles in cm at 0°	Atomic Weight	Group in Periodic Table to which Product belongs
Protactinium	**12,O00 years**	**a (3 48)**	**230**	***VA***
Actinium	**20 years**	—	**226**	**IIIA**
Radio-actinium	**19 5 days**	**a (4 43)**	**226**	**IVA**
Actinium-X	**116 days**	**a (4 14)**	**222**	**IIA**
Actinium emanation	**3 9 seconds**	**a (5 49)**	**218**	**0**
Actinium-A	**O 002 second**	**a (6 24)**	**214**	***VIB***
Actinium-B	**36 3 minutes**	B, y	**210**	***IVB***
Actinium-C	**2 15 minutes**	a, B (5 22)	**210**	***VB***
(Actinium-C)	**very short**	**a (6 10)**	**210**	**VIB**
Actinium-C″	**4 71 minutes**	B, y	**206**	**I I I B**

Products in brackets are branch products

670 The discovery that the atoms of certain heavy elements undergo continuous spontaneous disintegration with the formation of new substances necessitates a profound modification of our conceptions of chemical atoms Much information regarding atomic structures has been obtained of recent years on this subject from other sources, and it becomes important to co-ordinate the knowledge thus obtained with radioactive phenomena

From a consideration of the absorption of cathode rays of high velocity, Lenard [1] expressed the view that these rays would penetrate atoms and that only a very small part of the atom was impervious to them The same conclusion has been reached and elaborated by Rutherford as a result of his investigations of the two kinds of scattering of a-particles on passing through thin metal foil The first type, a small angle scattering proceeding according to the ordinary laws of probability, need not be considered here, but the second type, consisting of a very occasional scattering through large angles, is of fundamental importance The nature and distribution of this scattering have been studied in great detail by Gerger and Marsden,[2] and an explanation of their results has been given by Rutherford [3] on the supposition that the atom is the seat of intense electric forces whereby the a-particle can under suitable conditions be deflected through angles greater than a right angle by a single encounter with an atom. To produce these intense fields, the

[1] *Ann Physik,* **1903, 12, 714**
[2] ***Proc Boy. Soc.*, 1909, *[A],* 88, 495.** [3] ***Phil Mag.*, 1911, 21,** 669.

atom is supposed to consist of a small positively charged " nucleus " surrounded by a number of rotating electrons which neutralise the charge on the nucleus In its passage through the atom, the a-particle is attracted by the electrons producing small angle scattering and repelled by the nucleus, and it is by passing sufficiently closely to the nucleus that the large angle scattering mentioned above takes place The dimensions of the nucleus have been estimated by Darwin to be of the order 10^{-13} cm[1] Since the atom is electrically neutral, it follows that the charge on the nucleus is equal to the number of electrons in the atom scattering, to be approximately equal to half the atomic weight of the atom in question Since half the atomic weight of an element is in most cases nearly equal to the " atomic number " or position of an element in the periodic table, the above considerations suggest that for any element the nuclear charge, and therefore the number of electrons in an atom, is equal to the atomic number of the element, an idea which, as we shall see later, is substantiated by other evidence According to this view each element in the periodic table contains one electron more than the preceding element, and an atom must be regarded as analogous to a planetary system consisting of a positively charged nucleus surrounded by electrons, equal in number to the atomic number of the element and rotating round the nucleus to produce stability The a-particle on entering the planetary system behaves like a comet, passing in general almost straight through the atom, but being deflected along a hyperbolic path if it happens to pass sufficiently near to the nucleus

This conception of atomic structure has been elaborated by Bohr,[2] and later by Sominerfeld, from a consideration of spectroscopic evidence, particularly for the cases of hydrogen and helium, which are relatively simple The hydrogen atom is the simplest possible, for which the atomic number is 1. It consists of a singly-charged positive nucleus, about which rotates a single electron In general, the orbits of the electrons in any atpm will be elliptical, but the general atomic properties may be described by considering them as circular. According to the ordinary principles of dynamics, the electron could be considered to be rotating in an orbit of any radius provided that it is given

[1] C G Darwm, *Phi Mag*, 1914, 27, 606
[2] *Phil Mag.*, 1013, 26, 476, 857; 1915, **29** 332; **1915** 80, **394,**

a velocity of rotation which will balance the attraction of the nucleus Such a system wou*ld* radiate energy, and it is to Bohr that we owe the conception that there are certain non-radiating orbits of specified radius representing special stable states of the system Radiation is supposed to take place only when the electron passes from one position of stability to another. The possible stable orbits are determined by certain relations demanded by Planck's quantum theory, and while the view is in conflict with the classical laws of dynamics, it is demanded both by the existence of distinct and sharp spectral lines and by the permanence of the atom The hydrogen ion consists of the isolated nucleus the dimensions of which is minute compared with atomic magnitudes The case of the helium atom is much more complicated, since it consists of a doubly-charged nucleus surrounded by two rotating electrons It is not proposed to discuss here in detail the constitution of the helium or more complicated atoms, but this conception of the helium atom is of importance from our point of view, in that it gives definite information regarding the nature of the a-particle By the loss of two electrons we arrive at a doubly-charged nucleus of sub-atomic dimensions—the a-particle The properties of the a-particle discussed above then become clear—its power of penetrating matter, and *its* occasional large angle scattering on passmg through an atom in the neighbourhood of the nucleus, the absence of any emission of light by a-particles (for there are no electrons to emit any), and its ultimate transformation into helium by attracting two electrons

The importance of the atomic number as compared with the atomic weight of an element has been substantiated by other evidence besides that derived from the scattering of a-particles mentioned above—notably from a study of X-ray spectra Here, too, the idea of the atomic number brings order into phenomena where confusion reigns in terms of atomic weights.

When white light falls upon an ordinary diffraction grating the transmitted or reflected light is found to be broken up into well-defined spectra of different orders according to well-known laws Laue was the first to recogmse that a crystal afforded an example of a space grating in which the distances between the component atoms forming the crystal are so small that the crystal should behave towards rays of very short wave-length much as a diffraction grating behaves towards ordinary light. If, as seemed probable, X-rays Consisted of ether vibrations

having wave-lengths of the order 10^{-8} cm , the crystalline space grating would be of the right dimensions to produce X-ray spectra Laue's idea has been brilliantly justified by the experiments of Laue, Friedrich, and Knipping,[1] in which it was shown that X-rays can be diffracted by passing through crystals, thus establishing beyond doubt that the X-rays consist of ether waves of extremely short wave-length This phenomenon supplied at once the means of investigating the structure of crystals, and of measuring the wave-lengths of the X-radiations emitted from anticathodes of different materials when used in a discharge tube The question of crystal structure is beyond the scope of this section (but see p 213), but the investigation of X-ray spectra from different elements has contributed much to our knowledge of atomic structure, and the results obtained will be briefly reviewed

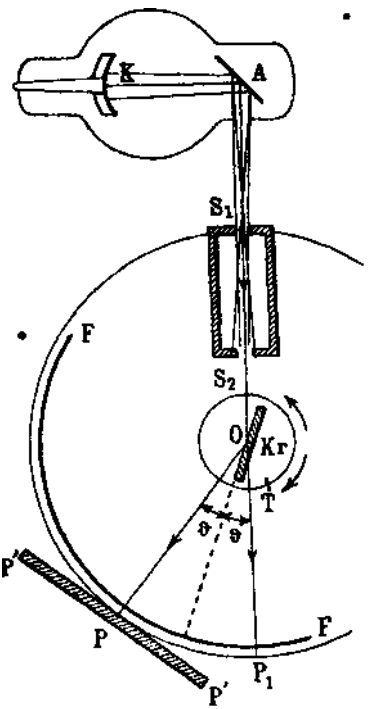

Fig 216

The general theory of the space grating is not altogether simple, but fortunately the diffraction effects produced by crystals on X-rays can be treated in a simple manner by considering certain planes of syminetry in the crystal as equivalent to reflecting surfaces selectively reflecting special wave-lengths It can be shown that if X-rays impinge on such a plane of a crystal at an angle O, then maxima of intensity will occur if

$$2d \sin 9 = \text{ny},$$

where d is the grating constant, X the wave-length of the radiation, and n·an integer

In Fig 216 is shown a typical piece of apparatus for obtaining spectra The Vays from the anticathode, A, after **passing througk**

[1] Ioc *cit*

suitably situated slits, S_1 S_2, placed to confine the beam fall upon a crystal at O and, if of ware-length such, as to conform with the equation just given, are reflected on to a photographic plate ox lonisation chamber placed at P By rotating the crystal rays of different wave-lengths can be brought into action

Prior to the discovery of the diffraction of X-rays by crystals Barkla[1] had shown that when cathode or X-rays impinge on different elements, certain characteristic secondary radiations are emitted by each eleihent The phenomenon was studied by observations on the penetrating power, or hardness, of the secondary rays emitted, and it was shown that the hardness of the secondary rays increases with the atomic weight of the element upon which the primary radiation falls The characteristic radiation emitted by an element was thus seen to be an atomic property depending on its atomic weight Barkla showed that the characteristic radiation fell into two series which he called *K*- and i-radiations (a third type, the *M*-radiation, has since been discovered by Siegbahn) On account of the fact that the characteristic rays were always softer than the exciting primary rays, Barkla described the secondary radiation as fluorescence radiations by analogy with fluorescence as observed in optics

The detailed study of these phenomena and their explanation according to modern views on atomic structure has become possible by the application of the method of spectrum analysis. Moseley[2] was the first to make a systematic study of the elements by this method, and to bring out the importance of the atomic number of an element in this connection The method of spectrum analysis and the introduction of the idea of atomic numbers as opposed to atomic weights renders the results at once definite and simple to interpret

In Moseley's experiments cathode rays were allowed to fall on anticathodes of different metals which could be changed at will, and the Z-radiation thus produced was examined by means of a crystal as described above The ^-radiation from elements ranging from Ca (atomic number, Z, = 20) to Cu (atomif number, Z, = 29) were examined and the results shown in Fig 217 were obtained From an exammatioh of the figure it appears that the pair of lines emitted by each element and known as the -K-and K-line respectively move regularly to positions of smaller wave-

[1] *Phil Mag*, 1909,17, 739, 1911, 21, 270.
[2] *Ibid*, 1913, 26, 1024, **1914, 27, 703.**

lengths with increasing atomic numbers and in such a way that the more intense and softer K_a-line can be represented in a manner similar to that given by Balmer for the hydrogen series in optics represented by the formula

$$v = IN(Z - 1)^2$$

where v is the frequency of the vibration, Z the atomic number of the element, and N the well-known Balmer constant The results obtained by Moseley for the K series have been extended by Siegbahn to the L series, and a newly-discovered M series [1]

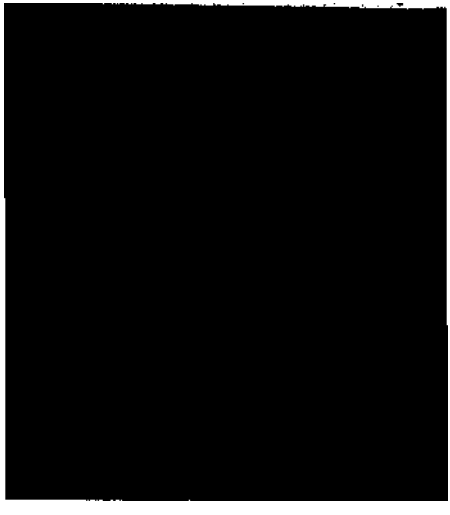

FIG. **217**

The general results obtained by him are shown in Fig 218, in which the atomic numbers as ordinates are plotted against wave-lengths as abscissae It is at once evident that the frequencies of the characteristic vibrations progress regularly with increase of atomic number as previously shown by Moseley

These important results receive a simple explanation on the theory of atomic constitution propounded by Rutherford to account for the scattering of a-particles, and elaborated by Bonr from spectroscopic evidence As we have seen, the atom is regarded as consisting of a positively charged nucleus surrounded by rings of elections rotating in approximately circular

[1] Siegbahn, *Verh d Deutuch Phys Ges* , 1916, 18, 278, and Sternstrom, *Ann Physik*, 1918, 57, 347

orbits From evidence deduced from the periodicity of atomic volumes and other phenonmina, it may be supposed that as we proceed through the periodic system of elements adding one new electron as we pass from one element to the next of higher atomic number, a new ring of electrons is added successively as we reach each univalent alkali element Proceeding from the nucleus outwards the successive rings are known as the K-, Z-, *M-*, *N-*, etc, rings respectively Without going into any detail as

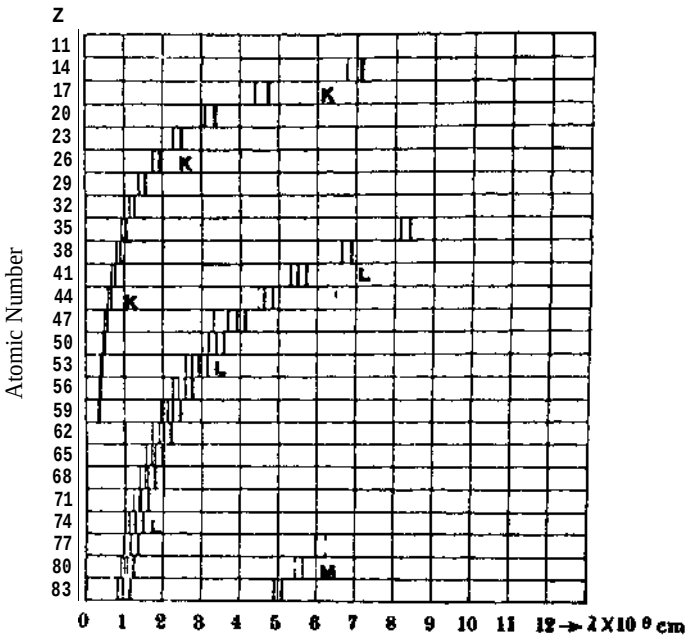

FIG 218

to the exact nature and orientation in space of these successive rings, it is supposed that, to produce Z-radiation by cathode or X-rays, it is necessary to remove an electron from the innermost or *K-ring,* and similarly for the Z- and If-radiations to remove an electron from one of these rings respectively Suppose now, for example, that* an electron has been removed by a primary radiation from the if-ring of any atom, the atom will then be in a position to emit characteristic Z-radiation, and this may take place by electrons from the Z-, *M-*, N-rings, etc , falling back into tfie Z-ring with the production of radiation known as K_a-, K_B- K_y-radiation, etc. The same thing will **happen with the *L* series,**

and radiation will be emitted by the atom by the transference of electrons to the L-ring from the outer M-, N-rings, etc Thus we see in general that Z-radiations are produced when an electron falls from an outer ring into the Z-ring, and so on The series of K-lines discovered by Moseley and shown in Fig 218 are produced by electrons falling respectively from the *L*- and *M*-rings into the K-ring and the reason that only two lines were observed in these ex employed was insufficient to detect lines due to electrons coming from the outer rings With higher resolution the characteristic X-ray spectra can be shown to be more complicated, the K_a-line being broken up into a doublet

We now obtain an explanation of Moseley's formula (p 1537) on Bohr's theory, in which the energy of the L-ring is given by

where *h* is the fundamental constant in Planck's quantum theory Similarly for the K-ring,

Then the energy emitted when the electron falls from the L-ring into the if-ring, giving rise to the K-radiation, is given by the relation

$$W. - W_b = vh = Nh(Z - 1)i(I - I)$$

whence $$v = \tfrac{3}{4}N(Z — 1)^2$$

It is not possible to consider here any of the finer points regarding X-ray and other spectra, and the reader is referred to special treatises on the subject[1]

[1] **Cf Sominerfeld, *Atombau und Spektrallinien* (Vieweg, 1919)**

INDEX

A

Absolute atomic distances, 222
Absorption spectra, 173
Acid bronze, 739
Acid forming oxides, 114
Acid salts, 117
Acids and alkalis, 100
Acids, bases, and salts, 99
Acids, nature of, 107
Actinium, 1516, 1526, 1532
iEschynite, 975
Aich's metal, 671
Aikinite, 1032
Alabandite, 1172, 1196
Albite, 731
Alembroth, 711
Algaroth, powder of, 1016
Algodonite, 454
Alkali manufacture, 296
Alkali metals, 240
Alkali waste, 302, 311, 314
Alkaline earth metals, 545
Alkalis, 240
Alkalis and acids, 100
Alkermes mineral, 1019
Allemontite, 988, 1026
Allopalladium, 1408
Alloys, 83, 86, conductivity of, 96, constitution of, 92, mioroscopical study of, 90, solubility of, 96, thermal classification of, 86
Almandine, 731
a particles, 1502, lomsation by, 1509, range of, 1505, velocity of, 1504
Alstonite, 620, 631
Alum, 730
Alum cake, 750
Alumina, 739, oolloidal 743
Aluminates, 744
Aluminite, 750
Aluminium, 730, alloys of, 738, annual output of, 734, atomio weight of, 770, compounds of, 739, detection of, 769, electrolytic pro duction of, 732, estimation of, 770, preparation of, 731, properties of, 734, uses of, 737
Aluminium ajnalgam, 739
Aluminium brass, 739
Aluminium bromide, 748
Aluminium bronze, 738
Aluminium carbide, 758
Aluminium chloride, 746, vapour density of, 33
Aluminium chlorosulphate, 750
Aluminium fluoride, 745
Aluminium group, 729
Aluminium hydroxides, 741
Aluminium iodide, 748
Aluminium nitrate, 757
Aluminium nitride, 757
Aluminium oxide, 739
Aluminium peroxide, 744
Aluminium phosphates, 757
Aluminium phosphides, 757
Aluminium selenide, 749
Aluminium silicates, 758
Aluminium sulphate, 749
Aluminium sulphide, 748
Aluminium tellunde, 749
Alum stone, 751
Alums, 750
Alunite, 751
Amalgams, 83, 97, 698
Amidochromic acid, 1072
Ammiohte, 1011
Ammonal, 737
Ammoma alum, 755
Ammonia-soda process, 317
Ammomacal derivatives of chromium, 1087, of cobalt, 1345, of copper, 457, of indium, 1448, of mercury, 720, of palladium, 1420, of platinum, 1481, of rhodium, 1405, of ruthenium, 1396, of zinc, 681
Ammomacal liquor, 394
Ammonium amalgam, 391, 699
Ammonium antimonate, 1013
Ammonium aurichlonde, 532
Ammonium auncyanide, 541
Ammonium aurooyanide, 540
Ammonium azoimide, 402
Ammonium bromide, 397
Ammonium carbonates, 405
Ammonium chlorate, 397
Ammonium chloride, 394
Ammonium chromate, 1065
Ammonium chromic sulphate, 1081
Ammonium compounds, 389
Ammonium cyanate, 407

Ammonium cyanide, 407
Ammonium dichromate, 1066
Ammonium ferricyanide, 1313
Ammonium ferrocyanide, 1309
Ammonium fluoride, 393
Ammonium fluorosulphonate, 394
Ammonium hexavanadate, 955
Ammonium hydrosulphide, 398
Ammonium iodide, 397
Ammonium indichloride, 1445
Ammonium indiobromide, 1445
Ammonium iron alum, 1292
Ammonium metavanadate, 954
Ammonium molybdates, 1106
Ammonium nitrate, 403
Ammonium nitrite, 403
Ammonium osmichlonde, 1432
Ammonium osmochlonde, 1431
Ammonium osmyl oxychlonde, 1430
Ammonium palladiehloride, 1417
Ammonium palladioehlonde, 1417
Ammonium perchlorate, 397
Ammonium permanganate, 1191
Ammonium peroxide, 393
Ammonium persulphate, 402
Ammonium perthiomolybdate, 1119
Ammonium phosphates, 404
Ammonium phosphomolybdate, 1110
Ammonium platinichlonde, 1476
Ammonium platinochlonde, 1473
Ammonium plumbichlonde, 924
Ammonium polysulphides, 399
Ammonium rhodochlonde, 1403
Ammonium selenate, 402
Ammonium stannichlonde, 895
Ammonium sulphate, 399
Ammonium sulphide, 398
Ammonium tetravanadate, 954
Ammonium throantimonate, 1023
Ammonium throcyanate, 408
Ammonium thromolybdate, 1119
Ammonium throvanadate, 966
Ammonium titanofluonde, 841
Ammonium tungstates, 1134
Ammonium uranate, 1155
Ammonium vanadite, 960
Ammonium vanadium alum, 968
Amphoteric hydroxides, 116
Analysis, crystallochemical, 212
Anatase, 833, 836
Andradite, 731
Anglesite, 903, 927
Anhydrite, 546, 568
Annabergite, 1355
Anomalies of periodic system, 71, 74
Anorthic system, 196
Antifriction metal, 1005
Antimonates, 1012
Antimomal copper, 998
Antimomal nickel, 999
Antimomal saffron, 1024
Antimomal silver, 999
Antimonic acids, 1011
Antimomous acid, 1010
Antimonite, 997
Antimony, 997, alloys of, 1004, atomic weight of, 1030, detection of, 1027, estimation of, 1028, medicinal uses of, 1026, modifications of, 1003, preparation of, 999, properties of, 1001, uses of, 1004
Antimony arsenide, 1026
Antimony black, 1004
Antimony blende, 1024
Antimony chlorosulphides, 1024
Antimony cinnabar, 1021
Antimony hydride, 1006
Antimony lodosulphides, 1024
Antimony ochre, 999
Antimony oxides, 1008
Antimony oxychlondes, 1016
Antimony oxysulphide, 1024
Antimony pentachlonde, 1017
Antimony pentafluonde, 1014
Antimony pentasulphide, 1023
Antimony pentoxide, 1011
Antimony phosphide, 1026
Antimony poisoning, 1027
Antimony selenides, 1025
Antimony sulphate, 1024
Antimony telluride, 1025
Antimony tetrachloride, 1017
Antimony tetrasulphide, 1022
Antimony tetroxide, 1010
Antimony thiophosphate, 1026
Antimony thiosulphate, 1025
Antimony tribromide, 1018
Antimony trichloride, 1015
Antimony trifluonde, 1014
Antimony triiodide, 1018
Antimony trioxide, 1008
Antimony trisulphide, 1018
Apatite, 546, 553, 575
Apjohnite, 1198
Apophyllite, 582
Aquamarine, 636
Aquochlororuthenates, 1394
Aragonite, 198, 546, 579
Arc spectra, 154
Argentan, 739
Argentiferous copper, 471
Argentite, 460,
Argentum metal, 1005
Argon, atomic weight of, 69
Argyrodite, 868, 869
Arsenical pyrites, 1212, 1223, 1298
Arsenomolybdic acids, 1111
Arsenovanadic acid, 970
Asbestos, 644
Ashbury metal, 1005
Assaying, 506
Astracanite, 128
Asyminetric system, 196
Atom, constitution of the, 39
Atom and molecule, 27
Atomic collisions, 1507
Atomic distances, calculation of, 222

Atomic heat, 15, 67
Atomic numbers, 72, 1533, 1536
Atomio structure, 39, 77, 1532
Atomic volume, 59
Atomic weights, basis of, 9, correc tion of doubtful, 68, determination of, 6, revision of, 13, selection of, 13
Augite, 644
Aunbromic acid, 533
Auric bromide, 533
Auric chloride, 530
Auric cyanide, 540
Auric hydroxide, 528
Auric iodide, 534
Auric oxide, 528
Auric sulphide, 535
Auric thiocyanate, 541
Aunchalcite, 664
Aunchlonc acid, 531
Auncyanic acid, 540
Auroaunc oxide, 529
Auroaunc sulphide, 535
Aurodiamine, 537
Aurous acetyhde, 539
Aurous bromide, 532
Aurous carbide, 539
Aurous chloride, 529
Aurous cyanide 539
Aurous hydroxide, 527
Aurous iodide, 533
Aurous oxide, 527
Aurous sulphide, 534
Auious thiocyanate, 541
Auryl hydroxide, 528
Austenite, 1263
Autocatalysis, 1191
Autunite, 1149
Avanturme glass, 609
Axes of symine try, 192
Axial ratios, 188
Azure blue, 1333
Azunte, 414, 456

B

Balanced reactions, 137
Baldwin's phosphorus, 573
Barium, 619, atomic weight of, 633, compounds of, 622, detection of, 632, estimation of, 633, occurrence of, 620, preparation of, 620, pro perties of, 621
Barium amide, 630
Barium azoimide, 630
Barium brSmide, 626
Bajium oarbide, 631
Barium oarbonate, 631
Barium chlorate, 626
Barium chloride, 624
Barium chromate, 1067
Barium cobaltite, 1337
Barium dioxide, 623
Barium disulphate, 629
Barium dithionate, 629
Barium ferrate, 1274
Barium ferrocyanide, 1310
Barium fluoride, 626
Barium hydride, 624
Barium hydrosulphide, 627
Barium hydroxide, 623
Barium lodate, 626
Barium iodide, 626
Barium indicyanide, 1448
Barium manganate, 1187
Barium molybdates, 1108
Barium monoxide, 622
Barium nickehte, 1372
Barium nitrate, 630
Barium nitnde, 630
Barium nitrite, 630
Barium osmocyanide, 1436
Barium percarbonate, 632
Barium permanganate, 1192
Barium persulphate, 630
Barium platinocyanide, 1484
Barium platinonitrite, 1480
Barium silicates, 632
Barium subchlonde, 626
Barium suboxide, 622
Barium sulphate, 232, 628
Barium sulphide, 627
Barium tetrasulphide, 627
Barium thioantimonate, 1024
Baryta, 622
Baryta water, 623
Baryto calcite, 620, 631
Baryto celestinc, 612, 620
Bases, acids, and salts, 99
Basic oxides, 112
Basic salts, 117
Basset i te, 1149
Bauxite, 730, 741 742
Becquerelite, 1150
Becquerel rays, 1498
Bell metal, 880
Benedict metal, 1365
Beraunite, 1297
Berthiente, 998
Beryl, 201, 636
Beryllium, 636
Bessemer steel 1250
B particles, 1502, 1508, lonisation by, 1509
Biotite, 731
Biscuit *v* are, 764
Bismuth, 1031, alloys of, 1035, atomic weight of, 1048, detection of, 1047, estimation of, 1048, metallurgy of, 1032, properties of, 1034
Bismuth arsenate, 1046
Bismuth-aunte, 507
Bismuth carbonate, 1047
Bismuth chlorosulphide, 1043
Bismuth chromate, 1069
Bismuth dichloride, 1&40
Bismuth hexoxide, 1039

Bismuth hydride, 1036
Bismuth nitrate, 1044
Bismuth nitride, 1044
Bismuth ochre, 1032,1038
Bismuth oxybromide, 1041
Bismuth oxychlonde, 1040
Bismuth oxyfluonde, 1040
Bismuth oxyiodide, 1039, 1041
Bismuth oxysulphides, 1043
Bismuth pentoxide, 1039
Bismuth phosphate, 1046
Bismuth selenide, 1043
Bismuth silicate, 1047
Bismuth subiodide, 1039
Bismuth suboxide, 1037
Bismuth subsulphide, 1042
Bismuth sulphate, 1043
Bismuth tellunde, 1044
Bismuth tetroxide, 1039
Bismuth thiosulphate, 1043
Bismuth tribromide, 1041
Bismuth trichlonde, 1040
Bismuth trifluonde, 1039
Bismuth trihydroxide, 1038
Bismuth triodide, 1041
Bismuth trioxide, 1038
Bismuth trisulphide, 1042
Bismuthite, 1032, 1042
Bismuthosmaltite, 1032
Bismutite, 1047
Bitter-spar, 646
Black-ash process, 307
Black band iron-stone, 1225
Black-jack, 663
Blanc fixe, 629
Blast furnace, 1228, chemical changes in, 1233, gases of the, 1235
Bleaching powder, 555, 558
Bleaching processes, 565
Bleimente, 1014
Blende, 677
Bleu celeste, 1334
Blister copper, 417
Blister steel, 1249
Blood, spectrum reaction of, 176J
Blue John, 553
Blue vitriol, 449
Boiling points of the elements, 63
Bone-phosphate, 575
Bones, constituents of, 575
Bononian phosphorus, 628
Boracite, 344
Borax, 286
Borax glass, 287
Boronatrocalcite, 287
Boulangente, 999
Bournonite, 903, 999
Brannente, 1150
Brass, 671
Braunite, 1172, 1178
Breithauptite, 999, 1355
Brewstente, 612, 620
Brine, electrolysis of, 325, evaporation of, 266
Brine wells, 265
Britannia metal, 1005
Bromargynte, 487
Bronze, 880
Brookite, 833, 836
Brown-spar, 546
Bruoite, 649
Brunswick green, 448
Bunsenite, 1370
Butter of antimony, 1015
Butter of tin, 893
Buttercup yellow, 1067

C

Cadmium, 684, alloys, 685, atomic weight of, 690, colloidal, 685, detection of, 690, estimation of, 690, preparation of, 684, properties of, 685, uses of, 685
Cadmium amide, 689
Cadmium carbonates, 689
Cadmium chloride, 687
Cadmium hydroxide, 687
Cadmium iodide, 688
Cadmium nitrate, 689
Cadmium nitride, 689
Cadmium nitrite, 689
Cadmium oxides, 686
Cadmium sulphate, 688
Cadmium sulphide, 688
Cadmous hydroxide, 686
Cadmous oxide, 686
Caesium, 386, atomic weight of, 389, detection of, 389, discovery of, 171, properties of, 387, occurrence of, 386, separation of, 381
Caesium alum, 755
Caesium carbonate, 389
Caesium chloride, 388
Caesium compounds, 387
Caesium hydride, 389
Caesium hydroxide, 388
Caesium monoxide, 387
Caesium nitrate, 389
Caesium peroxides, 388
Caesium platinichlonde, 1476
Caesium selenate, 388
Caesium sulphate, 237, 388
Caesium sulphides, 388
Calaite, 758
Calamine, 662, 664, 681
Calavente, 507
Calcium, 545, atomic weight of, 611, detection of, 610, estimation of, 611, preparation of, 5\6, properties *of*, 548, occurrence of, 540
Calcium arsenate, 576
Calcium arsenide, 576
Calcium bisulphite, 568
Calcium bonde, 577
Calcium borosihcates,9582
Calcium bromide, 555
Calcium carbide, 577

Calcium carbonate, 578, dissociation of, 138
Calcium ohlorate, 566
Calcium chloride, 553
Calcium cyanamide, 581
Calcium dioxide, 551
Calcium disulphide, 567
Calcium ferrite, 1272
Calcium ferrocyanide, 1310
Calcium fluoride, 552
Calcium hydride, 552
Calcium hydrosulphide, 567
Calcium hydroxide, 551
Calcium hydroxyhydrosulphide, 567
Calcium hypophosphite, 676
Calcium hyposulphite, 568
Calcium iodide, 555
Calcium manganite, 1181
Calcium metaplumbate, 921
Calcium molybdates, 1108
Calcium monosulphide, 566
Calcium monoxide, 549
Calcium nitrate, 573
Calcium nitride, 573
Calcium nitrite, 573
Calcium pentasulphide, 567
Caltium perplumbate, 921
Calcium phosphates, 574
Calcium phosphide, 574
Calcium platinocyanide, 1485
Calcium pyrovanadate, 955
Calcium silicates, 582
Calcium sihcide, 581
Calcium subchlonde, 555
Calcium sulphate, 568
Calcium sulphite, 568
Calcium thiosulphate, 572
Calcium titanate, 839
Calcium titanosihcate, 83^
Calcium tungstate, 1134
Calcspar, 546, 678
Caliche, 278
Calomel, 704, 724
Campyhte, 930
Canal rays, 1493
Canfieldite, 868
Canton's phosphorus, 567
Carbides, 136
Carbonates, 136
Carbonylferrooyanio aoid, 1320
Carbonylplatinoohiondes, 1472
Carnallite, 128, 334, 344, 379,644,
Carnotite, 944,1149
Case hardening, 1260
Cassel yellow, 924
Cassitente, 205, 232, 873, 884
Cast iron, 1222,1226,1237,1241
Castner's process, 254
Catalytio action, 142
Cathode rays, 1490
Caustio potash, 339
Caustic soda, 2$O, 313, 331
Celestine, 612, 616
Celtium, 829
Cementation process, 1248
Cements, 582
Centre of syminetry, 193
Ceno fluoride, 819
Ceno nitrate, 820
Ceno oxyohlonde, 819
Ceno selenite, 821
Ceno sulphate, 820
Cente, 795, 797
Cenum, 813, atomic weight of, 821, detection of, 821, estimation of, 821, properties of, 813
Cenum carbide, 821
Cenum oxides, 814
Cenum sihcide, 821
Cerous bromide, 816
Cerous carbonate, 819
Cerous chlonde, 816
Cerous hydnde, 816
Cerous hydroxide, 814
Cerous iodide, 817
Cerous nitrate, 818
Cerous nitnde, 818
Cerous phosphate, 818
Cerous sulphate, 817
Cerous sulphide, 817
Cerussite, 903, 930
Cervantite, 999
Chalcocite, 414
Chalcopynte, 414
Chalk, 546, 579
Chalybite, 546
Chance process, 315
Characteristic radiations, 1536
Chemical analysis by positive rays, 75, 1493
Chemical crystallography, 227
Chih saltpetre, 278
Chillagite, 1097, 1124
Chloanthite, 1380
Chlorargynte, 461, 484
Chlorates, 133
Chlonde of lime, 555
Chlondes, 132
Chlonte, 731
Chloroauno acid, 531
Chlorochromio acid, 1071, 1072
Chloropalladates, 1417
Chloropalladites, 1416
Chloroplatinic aoid, 1474
Chloroplatinites, 1472
Chloroplatinophosphorous acids, 1471
Chlororhodites, 1403
Chlororuthenates, 1394
Chlororuthenites, 1394
Chlortitamo acid, 843
Chromammines, 1089
Chrome alum, 1080
Chrome iron stone, 1052,1059
Chrome ochre, 1055
Chrome orange, 1068
Chrome red, 1068
Chrome yellow, 1068
Chromic acids, 1061

Chromic anhydride, 1060
Chromio azide, 1084
Chromic bromide, 1079
Chromio chloride, 1077
Chromic chromate, 1069
Chromic **fluoride, 1077**
Chromic hydroxides, 1056
Chromic hypophosphite, 1084
Chromic iodide, 1080
Chromic nitrate, 1084
Chromic oxide, 1055
Chromic phosphates, 1084
Chromic sulphate, 1080, action *6i* heat on, 1081
Chromic sulphide, 1080
Chromic thiocyanate, 1086
Chromic tungstates, 1086
Chromite, 1052
Chromites, 1058
Chromitite, 1052
Chromium, 1051, alloys of, 1054, ammoniacal compounds of, 1087, asyminetric compounds of, 1092, atomic weight of, 1095, detection of, 1093, estimation of, 1094, isomerism of complex compounds of, 1091, preparation of, 1052, pro perties of, 1053
Chromium amalgams, 1054
Chromium arsenides, 1085
Chromium borides, 1085
Chromium carbides, 1085
Chromium carbonate, 1085
Chromium dioxide, 1069
Chromium group, 1050
Chromium monoxide, 1055
Chromium nitride, 1083
Chromium phosphide, 1084
Chromium sesquioxide, 1055
Chromium sihcides, 1086
Chromium trioxide, 1059
Chromium tungstates, 1134
Chromosulphochromic acid, 1083
Chromosulphunc acids, 1083
Chromous acetate, 1076
Chromous bromide, 1075
Chromous carbonate, 1076
Chromous chloride, 1074
Chromous cyanide, 1085
Chromous fluoride, 1074
Chromous hydroxide, 1055
Chromous iodide, 1075
Chromous sulphate, 1076
Chromous sulphide, 1075
Chromyldichloride, 1070
Chromyl difluoride, 1070
Chrysoberyl, 636, 745
Chrysocolla, **456**
Cinnabar, 692, 713
Classification of the elements, 43
Claus **kiln,** 316
Clay iron-stone, 1225, 1227
CIRys, 760
Clinoclasite, 455
Cobalt, 1329, atomic weight of, 69, 1354, detection of, 1353; estimation of, 1354, preparation of, 1331, properties of, **1331**
Cobalt and nickel, separation of, 1386, 1387
Cobalt antimonides, **1349**
Cobalt arsenates, 1349
Cobalt arsenides, 1348
Cobalt azoimide, 1343
Cobalt bloom, 1329, 1349
Cobalt blue, 1333
Cobalt bromide, 1339
Cobalt carbonates, 1349
Cobalt carbonyls, 1350
Cobalt chlorate, 1340
Cobalt chloride, 1338
Cobalt dioxide, 1336
Cobalt glance, 1329, 1348
Cobalt green, 1334
Cobalt lodate, 1340
Cobalt iodide, 1340
Cobalt nitrate, 1344
Cobalt nitride, 1342
Cobalt nitrite, 1343
Cobalt nitrosotncarbonyl, 1350
Cobalt perchlorate, 1340
Cobalt phosphates, 1349
Cobalt phosphides, 1348
Cobalt pyrites, 1341
Cobalt red, 1334
Cobalt silicates, 1352
Cobalt sihcides, 1352
Cobalt sulphide, 1340
Cobalt tetraoarbonyl, 1350
Cobalt tncarbonyl, 1350
Cobalt ultramarine, 1333
Cobaltammine salts, 1345
Cobaltic ammonium alum, 1342
Cobaltic fluoride, 1337
Cobaltic hydroxide, 1335
Cobaltic oxide, 1335
Cobaltic sulphate, 1342
Cobaltic sulphite, 1341
Cobalticyanic acid, 1352
Cobaltite, 1329, 1348
Cobaltites, 1337
Cobalto-cobaltic oxide, 1335
Cobaltous cobalticyanide, 1352
Cobaltous cobaltite, 1337
Cobaltous cyanide, 1351
Cobaltous fluoride, 1337
Cobaltous hydroxide, 1334
Cobaltous oxide, **1333**
Cobaltous sulphate, **1341**
Cobaltous sulphite, 1341
Cæline, **1334**
Cœruhum, **1334**
Coinage, gold, 526
Coinage, nickel, 1360
Coinage, **silver, 479**
Coloothar, 1269
Collargol, 476
Colloidal solutions of metals, 81

Cologne yellow, 1068
Columbates, 981
Columbio acid, 980
Columbite, 973, 975
Columbium, 973, atomic weight of, 989, detection of, 987, estimation of, 988, hahde bases of, 985, preparation of, 979, properties of, 979
Columbium compounds, extraction of, 976
Columbmm nitride, 986
Columbium oxides, 980
Columbium oxybromide, 985
Columbium oxychlonde, 985
Columbium oxyfluonde, 985
Columbium pentabromide, 985
Columbium pentachlonde, 984
Columbium pentafluoride, 982
Columbium sulphide, 986
Columbium trichloride, 984
Common salt, 265
Complex salts, 118
Compressible atoms, theory of, 63
Conductivity of alloys, 96, metals, 66
Corfdy's fluid, 1189
Constantan, 1365
Constitution of the atom, 39, 77
Co-ordination compounds, 38
Copiapite, 1291
Copper, 412, alloys of, 433, amnion lacal compounds, 457, annual pro duction of, 432, atomic weight of, 459, colloidal, 434, detection of, 458, electrolytic refining of, 430, estimation of, 459, ores of, 413, properties of, 433, sources of, 413, uses of, 435, wet extraction of, 426
Copper amalgam, 699
Copper arsenates, 455
Copper arsenides, 454
Copper carbonates, 455
Copper chromates, 1066
Copper dioxide, 441
Copper ferrocyanide, 1310
Copper glance, 414
Copper oxides 435
Copper oxychlonde, 448
Copper peroxide, 440
Copper phosphides, 446
Copper polysulphides, 449
Copper pyrites, 414, 1212, 1285
Copper quadrantoxide, 440
Copper sihoates, 456
Copper smelting, 414, 421
Copper sulphate, 449
Copper tnentoxide, 440
Copper vanadates, 966
Coprohtes, 675
Coral, 546
Correction of doubtful atomic weights, 68
Corrosive sublimate, 709, 724
Corpuscular theory of atomic constitution, 39
Corundum, 730, 740
Cotunnite, 923
Covellite, 414
Crocoisite, 903, 1052, 1067
Crocus, 1269
Crocus anhmonit, 1024
Crookesite, 781
Crucible steel, 1250
Crucibles, 766
Cryolite, 731, 746
Cryolite soda process, 316
Crystal carbonate, 290, 330
Crystalline form of metals, 80
Crystallochemical analysis, 212
Crystallographic axes, 188, systems, 195
Crystallography, 183, chemical, 227
Crystal structures, theories of, 213, *X* ray analysis of, 216
Crystals, characteristics of, 184, classes of, 193, 209, distortion of, 185, measurements of, 185, optical properties of, 206, pyroelectnc behaviour of, 208, structure of, 213, symmetry of, 190, thermal properties of, 206
Cubic system, 202
Cupellation, 461, 506
Cupric arsenite, 455
Cupric bromide, 448
Cupric chloride, 447
Cupric fluonde, 447
Cupric hydride, 447
Cupric hydroxide, 438
Cupric nitrate, 453
Cupric nitrite, 453
Cupric oxide, 438
Cupric perchlorate, 448
Cupric phosphate, 454
Cupno phosphide, 454
Cupric selenate, 452
Cupric sulphate, 449
Cupric sulphide, 448
Cuprite, 413
Cupro-nickel, 1365
Cuproscheehte, 1124
Cuprotungstite, 1124
Cuprous acetyhde, 443
Cuprous bromide, 443
Cuprous chlonde, 441, molecular formula of, 32, 35
Cuprous cyanide, 446
Cuprous fluonde, 441
Cuprous hydnde, 441
Cuprous hydroxide, 437
Cuprous lmide, 445
Cuprous iodide, 443
Cuprous nitride, 445
Cuprous oxide, 436
Cuprous phosphide, 446
Cuprous*sulpnate, 444

Cuprous sulphide, 444
Cuprous sulphite, 444
Cuprous thiocyanate, 446
Curie, 1621
Cyanides, 132
Cyanides, complex, 1251

D

Daguerreotype process, 499
Damascening, 1260
Danbunte, 582
Datohte, 582
Dechenite, 944
Descloizite, 944
Desilverisation of lead, 909
Dialogite, 1203
Dianium, 975
Diaspore, 730, 741
Diffusion of metals, 95
Dilute solutions of salts, acids and bases, 109
Dioptase, 456
Disintegration constant, 1512
Disintegration theory, 1512
Dissociation, 138, 146, electrolytic, 109
Divanadyl hydroxide, 960
Dolomite, 546, 644, 659
Domeykite, 454
Double salts, 118, 127
Duahstic theory, 103
Dufrenite, 1297
Dulong and Petit's law, 16
Dung substitute, 285
Duralumin, 739
Dutch brass, 671
Dutch white, 934
Dyscrasite, 461, 999
Dysprosium, 828

E

Earthenware, 760, 765
Eau de Javelle, 269
Eau de Labarraque, 269
Ekaboron, 70
Ekaluminium, 70
Ekasihcon, 70
Electrochemical theory of valency, 39
Electrolysis of alkali salts, 106
Electrolysis of brine, 327
Electrolytic dissociation, 109
Electrolytic soda process, 325
Electrons, 40
Electro-nickel plating, 1361
Electrotyping process, 431
Elements, classification of, 43
Elements in sun's atmosphere, 178
Emanation, 1511, 1521
Embokte, 488
Emerald, 636, 740
Emerald copper, 456
Emery, 740
Emission spectra, 154
Emplectite, 1032
Enamel, 606
Enantiomorphism, 203, 227
Epsom salts, 652
Epsomite, 644, 652
Equilibrium, 139, 142
Equilibrium constant, 143, 146
Equivalent, determination of the, 9
Erbium, 828
Erdmann's salt, 1347
Erubesoite, 414
Erythnte, 1329, 1349
Estramadunte, 575
Ethyl ferrocyanide, 1307
Euolase, 636
Eulytite, 1032, 1047
Europium, 826
Eutectic mixtures of metals, 87, 93
Euxenite, 796, 803, 859, 976
Eventt's salt 1312
Explosive antimony, 1003

F

Faience, 765
Felspars, 731, 759
Ferbente, 1124
Fergusonite, 796, 975
Ferric acid, 1273
Ferric ammonium sulphate, 1292
Ferric arsenates, 1298
Feme arsenite, 1298
Ferric bromide, 1280
Ferric chloride, 1276, hydrates of, 126, vapour density of, 33
Ferric ferricyanides, 1319
Ferric ferrocyanides, 1312
Feme fluoride, 1275
Ferric hydroxide, 1269
Feme nitrate, 1293
Ferric nitride 1293
Feme oxide, 1268
Feme oxychlondes, 1280
Ferric phosphates, 1297
Feme potassium sulphate, 1291
Feme sulphate, 1290
Feme sulphide, 1283
Feme thiocyanate, 1324
Fenicyanic acid, 1311
Ferricyanogen compounds, 1311
Ferrite, 1263
Ferrites, 1272
Ferrocyanic acid, 1307
Ferrocyanogen oompounds,%1305
Ferrocyanogen radicle, 1303
Ferroheptanitrososulphydnc acid 1295
Ferromanganese, 1239
Ferropentacarbonyl, 1300
Ferrosihcon, 1325
Ferroso-fernc chloride, 1276
Ferroso-ferno fluoride, 1275
Ferroso-femo oxide, 1266

Ferroso feme sulphates, 1291
Ferrotetracarbonyl, 1301
ferrous ammonium sulphate, 1290
Ferrous bicarbonate, 1300
Ferrous bromide, 1280
Ferrous carbonate, 1300
Ferrous chloride, 1275
Ferrous chromite, 1059
Ferrous cobalticyanide, 1352
Ferrous cyanide, 1302
Ferrous disulphate, 1290
Ferrous ferrocvanides, 1311
Ferrous fluoride, 1275
Ferrous hydroxide, 1265
Ferrous iodide, 1281
Ferrous nitride, 1293
Ferrous nitrate, 1293
Ferrous oxide, 1265
Ferrous perchlorate, 1281
Ferrous phosphate, 1296
Ferrous sulphate, 1287
Ferrous sulphide, 1282
Ferrous sulphite, 1286
Ferrous thiocyanate 1323
Ferrous tungstate, 1134
Fibro-fenite, 1291
Fiscfter's salt, 1343
Flame spectra, 154
Fluorides, 131
Fluorochromates, 1070
Fluorspar, 202, 206, 552
Fowler's solution, 368
Fracture of metals, 81
Frankhnite, 664, 1224
Fraunhofer's lines, 174, 178
Freezing point curves for alloys, 86
Fulminating gold, 537
Fulminating platinum, 1480
Fulminating silver, 481, 494
Fusible metal, 1035
Fusible white precipitate, 723
Fusibility of salts, 131

G

Gadolinite, 795, 797, 860
Gadolinium, 827
Gahnite, 664, 745
Galena, 902, 926
Gallium, 70, 771, atomic weight of, 776, discovery of, 172, preparation of, 772, properties of, 773
Gallium, chlorides, 774
Gallium nitrate, 774
Gallium oxide, 773
Gallium selenate, 774
Gallium sulphate, 774
y-rays, 1502, lomsation by, 1510
Garnet 202, 731, 759
Garhiente, 1356, 1384
Gerkiehte, 839
Germanium, 70, 868, atomic weight of, 871, deteotion of, 871; estimation of, 871, **properties** of, **868**
Germanium chloroform, 870
Germanium dichloride,871
Germanium fluoride, 870
Germanium hydride, 870
Germanium oxides, 869
Germanium oxychloride, 870
Germanium sulphides, 871
Germanium tetrachloride, 870
German silver, 1363
Gibbsite, 741
Gilding, 525
Gilpinite, 1150
Glass, 584, annealing of, 602, coloured, 606, composition of, 589, decomposition of, 604, devitrification of, 605, history of, 585, manufacture of, 593, thermal expansion of, 591, varieties of, 589, 606
Glass of antimony, 1024
Glaubente, 274, 572
Glauber's salt, 274
Glucina, 637
Glucinum, 635, atomic weight of, 68, 642, compounds of, 637, detection of, 642, estimation of, 642, preparation of, 636, properties of, 637
Glucinum borocarbide, 641
Glucinum bromide, 640
Glucinum carbide, 641
Glucnium carbonates, 641
Glucnium chloride, 640
Glucnium fluoride, 640
Glucinum hydroxide, 640
Glucinum iodide, 640
Glucnium nitrate, 641
Glucnium oxide, 637
Glucnium phosphates, 641
Glucnium sulphates, 640
Gothite, 1269
Gold, 507, alloys of, 526, atomic weight of, 68, 543, colloidal, 523, compounds of, 527, detection of, 541, estimation of, 541, electrodeposition of, 526, extraction of, 511, fulminating, 537, native, 511, occurrence of, 507, preparation of pure, 520, properties of, 520, refining and parting of, 517, world's production of, 510
Gold amalgam, 527
Gold bronze, 739
Gold bullion, assay of, 542
Gold coinage, 526
Gold cyanides, 539
Gold halides, 529
Gold oxides, 527
Gold ores, assay of, 542
Gold phosphides, 539
Gold sulphides, 534
Gold telluride, 537
Goniometer, 185
Goslante, 664
Greenookite, 684, 688

Green vitriol, 1287
Grossman's alloy, 739
Grossular, 731
Guannite, 839
Guignet's green, 1057
Gun metal, 880
Gunpowder, 362
Gypsum, 646, 568

H

Haematite, brown, 1212, 1225, 1227, red, 1212, 1224, 1227
Hafnium, 858
Haidingente, 576
Hamburg white, 933
Hardening of oils, 1368
Hardenite, 1263
Harmotome, 620
Hatchett's brown, 1310
Hauente, 1172, 1197
Hauyne, 769
Hausmannite, 1172, 1177
Heavy spar, 620, 628
Heavy stone, 1124
Helium, discovery of, 172
Helium from radium, 1520
Hemihedral forms, 203
Hemimorphite, 664
Hexagonal system, 201
Hexavanadic acid, 952
Holmium, 828
Horn quicksilver, 704
Horn silver, 461, 484
Hubnente, 1124, 1134
Hyacinth, 849, 857
Hyalophane, 620
Hydrargillite, 741
Hydrates and solubility, 119, 122
Hydraulic cement, 583
Hydraulic lime, 550
Hydraulic mortar, 582
Hydrazine, salts of, 409
Hydrogenium, 1409
Hydrohæmatite, 1269
Hydrolysis of salts, 111
Hydromagnesite, 659
Hydroxides, 112
Hydroxylamine, salts of, 408
Hydroznicite, 664
Hypochlorites, 133, 558
Hypovanadates, 960
Hypovanadic hydrate, 960
Hypovanadic sulphates, 968
Hypovanadic sulphite, 966

Illium, 1365
Ilmenite, 832, 833, 839
Ilmenium, 975
Im&ochromic acid, 1072
Incandescent mantles, 815, 800
Indicators, 110
Indices, crystal, 189
Indigo copper, 448
Indium, 775, atomic weight of, 69, 780, detection of, 780, discovery of, 172
Indium ammonium alum, 779
Indium bromide, 778
Indium chlorides, 778
Indium compounds, 777
Indium fluoride, 778
Indium hydroxide, 777
Indium iodide, 778
Indium nitrate, 779
Indium oxide, 777
Indium selenate, 779
Indium sulphate, 779
Indium sulphide, 779
Indium sulphite, 779
Infusible white precipitate, 722
Intercepts, law of rational, 188
Intermetallic compounds, 94
Iodargynte, 489
Iodme, atomic weight of, 69
Iodostannic acid, 891
Ionisation of gases, 1500, 1509
Ionium, 1530, 1531
Indibromides, 1445
Indichlorides, 1444
Indicyanic acid, 1447
Indicyanides, 1447
Indiochlondes, 1444
Indionitrites, 1447
Indium, 1423, 1438, alloys, 1441, ammoniacal derivatives of, 14^8, atomic weight of, 66, 1449, colloidal, 1441, detection and estimation of, 1449, preparation of, 1439, properties of, 1439, spongy, 1440
Indium black, 1440
Indium bromides, 1445
Indium chlorides, 1443
Indium hydroxides, 1442
Indium iodide, 1445
Indium oxides, 1442, 1444
Indium sulphates, 144b, 1447
Indium sulphides, 1446
Indium sulphites, 1446
Iron, 1210, atomic weight of, 1328, compounds of, 1264, detection of, 1326, estimation of, 1327, grey, 1237, isotopes of, 1329, metallurgy of, 1221, meteoric, 1211, mottled, 1237, ores of, 1212, 1223, passive, 1216, preparation of pure, 1213, properties of, 1214, reduced 12J8, rusting of, 1218, spongy, 1218, vanetiesof, 1222, white, 1237
Iron alum, 1291, 1292
Iron amalgam, 1220
Iron arsenides, 1298
Iron borides, 1298
Iron carbides, 1299

Iron oarbonyls, 1300, 1301
Iron cyanogen compounds, 1302
Iron disulphide, 12854
Iron femoyanides, 1313
Iron ferrooyanide, 1313
Iron, magnetic oxide of, 115, 1266
Iron nitrides, 1292
Iron, nitroso compounds of, 1293
Iron pentaoyano compounds, 1320
Iron phosphides, 1264, 1295
Iron pyrites, 1212, 1223, 1285
Iron silicates, 1325
Iron suicides, 1325
Iron subsulphide, 1282
Iron tree, 1325
Isobares, 1498
Isodimorphism, 238
Isomorphism, 24, 230, and chemical constitution, 231,
Isomorphous mixtures, 234, 235
Isomorphous series, 26
Isotopes, 74,1498, 1499, 1515, separa tion of, 76, spectra of, 163

J

Janesonite, 999
Jargon, 857
Johannite, 1164

K

K radiation, 1536
Kamite, 344, 355, 644
Kaolin, 731, 759
Keifun, 705
Keilliauite, 795, 833
Keramohalite, 749
Kermesite, 1024
Kiesento, 344, 644, 652
Kleinite, 711
Kupfernickel, 1355, 1380

L

L radiation, 1536
Labile systems, 124, 234
Labradonte, 731
Lanarkite, 903
Lanthanite, 812
Lanthanum, 808, atomic weight of, 813, detection of, 812, estimation of, 812, properties of, 809
Lanthanum bromate, 811
Lanthanum carbide, 812
Lanthanum carbonate, 812
Lanthanum chloride, 810
Lanthanum hydride, 810
Lanthanum hydroxide, 810
Lanthanum nitrate, 811
Lanthanum nitride, 811
Lanthanum oxide, 810
Lanthanum peroxide, 810
Lanthanum sulphate, 811
Lanthanum sulphide, 810
Lapis lazuli, 766
Launonite, 923
Launte, 1389, 1395
Law of Dulong and Petit, 16
Law of geometrical crystallography, 187
Law of mass action, 137, 140
Law of octaves, 48
Law of rational intercepts, 188
Lazurite, 766
Loadstone, 1224
Lorandite, 781
Lead, 902, action of water on, 935; atomic weight of, 939, colloidal 915, compounds of, 915, detection of, 937, desilverisation of, 909, electro refining of, 912, estimation of, 939, isotopes of, 940, 1526, 1528, poisonous action of, 935, preparation of chemically pure, 913, properties of, 914, smelting of, 903, world's production of, 913
Lead antimonate, 1014
Lead borates, 930
Lead bromide, 925
Lead carbonates, 930
Lead chloride, 922
Lead chromates, 1067
Lead cyanate, 934
Lead cyanide, 934
Lead ferricyanide, 1313
Lead fluorides, 922
Leadhillite, 903
Lead hydride, 922
Lead hydroxide, 917
Lead lmide, 928
Lead iodide, 925
Lead metavanadate, 955
Lead molybdate, 1108
Lead monoxide, 916
Lead nitrate, 929
Lead nitrite, 928
Lead orthovanadate, 955
Lead oxybromide, 925
Lead oxychlondes, 923
Lead peroxide, 919
Lead persulphate, 928
Lead peruranate, 1157
Lead phosphates, 930
Lead pyrovanadate, 955
Lead sesquioxide, 918
Lead sdioates, 934
Lead suboxide, 917
Lead sulphate, 927
Lead sulphide, 926
Lead tetrachloride, 924
Lead tetravanadate, 956
Lead tungstate, 1134
Lead vitriol, 927
Leblanc soda process, 298
Leipsig yellow, 1068
Lemon chrome, 1067

Lepidolite, 242, 379
Leucophane, 636
Libethenite, 464
Liohtenberg's metal, 1035
Liebigite, 1150, 1167
Light, action of, on silver salts, 504
Lime, 549, superphosphate of, 576, felspar, 731
Lime burning, 549
Limestone, 546, 549, 579
Limonite, 1225, 1269
Lmnaeite, 1329, 1341, 1355, 1376
Lipowitz metal, 1035
Liquation in alloys, 94
Litharge, 916
Lithium, 241, atomic weight of, 252, detection of, 251, estimation of, 252, occurrence of, 170, prepara* tion of, 244, properties of, 245, salts of, 247, sources of, 242, spectroscopic detection of, 170, 251
Lithium amide, 248,
Lithium azounide, 249
Lithium carbide, 249
Lithium carbonate, 250
Lithium chloride, 247
Lithium cyanide, 250
Lithium fluoride, 247
Lithium hydride, 246
Lithium hydroxide, 246
Lithium imide, 248
Lithium lodotetrachlonde, 248
Lithium nitrate, 249
Lithium nitride, 248
Lithium nitrite, 249
Lithium oxide, 246
Lithium perchlorate, 248
Lithium peroxide, 247
Lithium phosphate, 249
Lithium platiniohlonde, 1476
Lithium silicates, 251
Lithium sihcide, 251
Lithium sulphate, 248
Lithium ultramarine, 768
Liver of sulphur, 353
Livers of antimony, 1021
Lollingite, 1298
Lorandite, 781
Lunar caustic, 495
Lutecium, 829

M

M radiation, 1536
Macles, 205
Magistery of bismuth, 1045
Magnalium, 646
Magnesia, 643, 648
Magnesia alba, 643, 658
Magnesite, 644, 657
Magnesium, 643, atomic weight of, 661, compounds of, 648, detection of, 660, estimation of, 660; preparation of, 644, properties of, 646
Magnesium alummate, 744
Magnesium amalgam, 699
Magnesium arsenates, 657
Magnesium bromide, 651
Magnesium carbides, 657
Magnesium carbonates, 657
Magnesium chloride, 650
Magnesium cobaltite, 1337
Magnesium ferrite, 1273
Magnesium ferrocyanide, 1310
Magnesium fluoride, 650
Magnesium hydroxide, 649
Magnesium iodide, 652
Magnesium molybdate, 1107
Magnesium nitrate, 655
Magnesium nitride, 655
Magnesium oxide, 648
Magnesium oxychlorides, 651
Magnesium peroxide, 649
Magnesium phosphates, 655
Magnesium phosphide, 655
Magnesium platinocyanide, 1485
Magnesium silicates, 660
Magnesium sihcide, 659
Magnesium sulphate, 203, 652
Magnesium sulphide, 652
Magnetio iron ore, 1212, 1224, 1^27
Magnetic oxide of iron, 115, 1266
Magnetic pyrites, 1212, 1285
Magnetic spectrum, 1509
Magnetite, 1224
Magnoferrite, 648
Magnus Green Salt, 1482
Malachite, 413, 455
Malleable iron, 1222, 1239, 1246
Manganates, 1185
Manganese, 1171, alloys of, 1175, atomic weight of, 1207, detection of, 1204, estimation of, 1205, preparation of, 1172, properties of, 1174
Manganese alums, 1199
Manganese amalgam, 1175
Manganese antimonide, 1202
Manganese arsenides, 1201
Manganese borate, 1202
Manganese bondes 1202
Manganese bronze, 1175
Manganese carbide, 1202
Manganese carbonate, 1203
Manganese ohromite, 1059
Manganese dioxide, 1179, regeneration of, 1181
Manganese disulphide, 1197
Manganese heptoxide, 1187
Manganese nitrate, 1200
Manganese nitride, 1200
Manganese ores, valuation of, 1206
Manganese peroxide, 1179
Manganese persulphate, 1199
Manganese phosphides, 1200
Manganese sihcides, 1203
Manganese spar, 1172, 1203
Manganese steel, 1261

Manganese sulphide, 1196, 1264
Manganese tetrachloride, 1194
Manganese thiooyanate, 1203
Manganese trichloride, 1194
Manganese trioxide, 1184
Manganese tungstate, 1134
Manganic bromide, 1196
Manganic fluoride, 1192
Manganio hydroxide, 1178
Manganic oxide, 1178
Manganic phosphates, 1201
Manganic sulphate, 1198
Manganm, 1175, 1365
Manganite, 1172, 1178
Manganites, 1181
Mangano calcite, 546
Mangano manganic oxide, 1177
Mangano tantahte, 975
Manganous aluminium sulphate, 1198
Manganous arsenate, 1201
Manganous bromide, 119b
Manganous chloride, 1193
Manganous dithionate, 1200
Manganous fluoride, 1192
Manganous hydroxide, 1176
Manganous iodide, 1196
Manganous oxide, 1176
Manganous phosphates, 1201
Manganous silicates, 1204, 1265
Manganous sulphate, 1197
Manganous tetriodate, 1196
Mapping spectra, 157
Marble, 546, 579
Marcasite, 1031, 1285
Martensite, 1263
Mass action, law of, 137, 140
Massicot, 916
Mass spectra, 1495, 1547
Matlockite, 903, 923
Matt glass, 610
Meerschaum, 644
Melaconite, 413
Melting pomts of the elements, 63
Menachanite, 832
Mendeleev's system, 50
Mendipite, 903, 923
Mercurial ointment, 698
Mercurial poisoning, 725
Mercuric aoetylide, 719
Mercuric arsenide, 719
Mercuric bromide, 712
Mercuric bromofluonde, 708
Mercuric oarbonates, 719
Mercuric chloride, 708
Mercuric oblorofluonde, 708
Mercuric compounds, 700
Mercuric oyanate, 720
Mercuric cyanide, 719
Mercuric fluoride, 708
Mercuric hyponitrite, 718
Mercuric iodide, 712, 724
Mercuric nitrate, 717
Mercuric nitrite, 718
Mercuric oxide, 702
Mercuric oxychlorides, 711
Mercuric oxycyanide, 720
Mercuric perchlorate, 713
Mercuric phosphide, 718
Mercuric sulphate, 717
Mercuric sulphide, 713
Mercuric thiocyante, 720
Mercurous bromide, 706
Mercurous carbonate, 708
Mercurous chloride, 704
Mercurous compounds, 700
Mercurous fluoride, 704
Mercurous iodide, 706
Mercurous nitrate, 707
Mercurous nitrite, 707
Mercurous oxide, 702
Mercurous sulphate, 706
Mercurous sulphide, 706
Mercury, 691, alloys of, 698, ammonlacal compounds of, 720, atomic weights of, 727, colloidal, 698, compounds of, 700, detection of, 725, estimation of, 726, isotopes of, 727, manufacture of, 693, pro perties of, 696, purification of, 696, uses of, 698, world's production of, 695
Mercury and its compounds, therapeutic uses, of, 724
Mercury nitride, 717
Mercury penodide, 713
Mercury peroxide, 703
Mesothorium, 1527, 1531
Metabisulphites, 135
Metalloids, 4
Metals, boiling pomts of, 63, conductivity of, 65, crystalline form of, 80, diffusion of, 95, melting points of, 63, molecular weights of, 26, specific heat of, 15, vapour density of, 26
Metals and non metals, 4, 6
Metals, colloidal solutions of, 81
Metastable systems, 124, 234
Metastannic acid, 885, 887
Metavanadic acid, 951
Meteoric iron, 1211, 1356
Mica, 731
Microcosmio salt, 404]
Microlite, 975
Microscopical study of alloys, 90
Millenan indices, 189
Millente, 1355, 1375
Millon's base, 721
Milk glass, 606
Milk of lime, 551
Mimetesite, 903, 930
Minium, 918
Mispiokel, 1298
Mote's Salt, 1290
Molecular heat of compounds, 22
Molecular weights of metallic com pounds, **14**
Molecular **weights** of **the metals, 26**

Molecule and atom, 27
Molybdates, 1104
Molybdenite, 1097, 1118
Molybdenum, 1096, atomio weight of, 68, 1123, detection of, 1121, estimation of, 1122, hahde bases of, 1113, metallurgy of, 1097, properties of 1098
Molybdenum bonde, 1120
Molybdenum carbides, 1120
Molybdenum cyanides, 1120
Molybdenum dibromide, 1113
Molybdenum dichloride, 1112
Molybdenum di iodide, 1113
Molybdenum dioxide, 1100
Molybdenum dioxydifluonde, 1116
Molybdenum disulphide, 1118
Molybdenum hexafluonde, 1115
Molybdenum molybdates, 1108
Molybdenum nitride, 1120
Molybdenum oxyhahdes, 1116
Molybdenum pentachloride, 1115
Molybdenum pentasulphide, 1118
Molybdenum pentoxide, 1101
Molybdenum phosphate, 1120
Molybdenum phosphide, 1120
Molybdenum sesquioxide, 1099
Molybdenum sesquisulphide, 1118
Molybdenum silicide, 1121
Molybdenum tetrabromide, 1114
Molybdenum tetrachloride, 1114
Molybdenum tetrahydroxide, 1100
Molybdenum tetrasulphide, 1119
Molybdenum tetriodide, 1115
Molybdenum thiocyanates, 1120
Molybdenum tnbromide, 1114
Molybdenum trichloride, 1114
Molybdenum trioxide, 1101
Molybdenum trisulphide, 1118
Molybdenyl tetrachloride, 1116
Molybdenyl tetrafluonde, 1116
Molybdio acid, 1102
Molybdio ochre, 1097
Molybdio tetrahydroxide, 1100
Monazite, 796, 859, 860
Mond nickel process, 1358
Monei metal, 1365
Monoclinic system, 197
Monosyminetrio system, 197
Monthier's blue, 1317
Morenosite, 1377
Mortar, 550, 682, hydraulic, 582
Mosaic gold, 896
Mottramite, 944
Muntz metal, 671

N

Nagyagite, 507
Natron, 290
Natural arrangement of the elenic 46
Neodymium, 824, compounds **824;** detection of, 825
Neoytterbium, 829
Neptunium, 975
Nessler's solution, 702
New blue, 1334,
Newton's metal, 1035
Nicoolite, 1355, 1380
Niohrome, 1365
Nickel, 1355, alloys of, 1363, as catalyst, 1366, atomic weight of, 69,1387, colloidal, 1369, detection of, 1384, estimation of, 1386; metallurgy of, 1356, properties of, 1359
Nickel amide, 1378
Nickel ammonium sulphate, 1377
Nickel and cobalt, separation'of, 1386, 1387
Nickel arsenates, 1380
Nickel arsenides, 1380
Nickel azoimide, 1378
Nickel blende, 1355
Nickel bonde, 1380
Nickel bromide, 1374
Nickel carbide, 1381
Nickel carbonate, 1383
Nickel chlorate, 1374
Nickel chloride, 1373
Nidkel coinage, 1360
Nickel cyanide, 1383
Nickel dioxide, 1372
Nickel disulphide, 1376
Nickel fluoride, 1373
Nickel glance, 1355
Nickel hydroxide, 1371
Nickel lodate, 1374
Nickel iodide, 1374
Nickel monocyanide, 1383
Nickel monosulphide, 1375
Nickel monoxide, 1370
Nickel nitrate, 1379
Nickel nitride, 1378
Nickel nitrite, 1379
Nickel ochre, 1355
Nickel oxides, 1370
Niokel phosphates, 1380
Nickel phosphides, 1380
Nickel plating, 1361
Nickel selenate, 1378
Nickel sesquioxide, 1372
Nickel sesquisulphide, 1376
Nickel silicates, 1384
Nickel silicide, 1384
Nickel silver, 1363, 1364
Nickel-steel, 1365
Nickel subsulphide, 1375,
Nickel sulphate, 1376
Nickel sulphite, 1376
Nickel tetracarbonyl, 1381
Nickel tetroxide, 1373
Nickel tnhydroxide, 1372
Nickel vitriol, 1377
Nickeline, 1355, 1380
E, Niobium, 974
Nitrates, 136

Nitre, 358
Nitrides, 135
Nitrites, 135
Nitritoplatinites, 1479
Nitrocobalt, 1343
Nitrocopper, 445
Nitronickel, 1379
Nitroprussic acid, 1321
Nitrosoferricyanic acid, 1321
Nixferrum, 1010
Non metals, 4
Normal salts, 116

O

Odontolith 758
Okenite, 582
Olivenite, 455
Olivine, 644
Open hearth process, 1256
Optical activity, 204
Orangite, 859, 862
Oriental amethyst, 740
Oriental topaz, 740
Ornithite, 575
Orthoclase, 334, 731, 759
Orthorhombic system, 198
Osmates, 1427
Osmiamic acid, 1435
Osmic acid, 1427, 1428
Osmichlorides, 1432
Osminitrites, 1435
Osmindium, 1389, 1423, 1425, 1438
Osmisulphites, 1433
Osmnim, 1423, atomic weight of, 68, 1437, colloidal, 1425, detection of, 1436, estimation of, 1437, preparation of, 1433, properties of, 1424
Osmium bromides, 1432
Osmium chlorides, 1431, 1432
Osmium fluorides, 1430
Osmium iodides, 1433
Osmium nitrite, 1435
Osmium oxides, 1425
Osmium oxysulphide, 1433
Osmium sulphite, 1433
Osmium tetrasulphide, 1433
Osmium tetroxide, 1427
Osmochlondes, 1431
Osmocyanic acid, 1436
Osmosammine hydroxide, 1434
Osmyldiammine chloride, 1434
Osmyl salts, 1429
Osnd, 1439
Osteolite, 546, 574
Oxides, 112
Oxymunate of tin, 894
Ozomolybdio acid, 1111

P

Packfong, 1364
Palladichloridea, 1417
Palladiochlondes, 1416
Palladium, 1406, alloys, 1414, ammoniacal compounds of, 1420, atomic weight of, 1422, colloidal, 1413, detection and estimation of, 1421, occlusion of gases by, 1408, preparation of, 1407, properties of, 1408, spongy, 1411, uses of, 1414
Palladium black, 1412
Palladium bromides, 1417
Palladium chlorides, 1416, 1417
, Palladium cyanide, 1419
Palladium hydrogen, 1408
Palladium iodide, 1418
Palladium nitrate, 1419
Palladium oxides, 1415
Palladium sihcide, 1419
Palladium sulphate, 1419
Palladium sulphides, 1418
Palladium tinocyanate, 1419
Parallel growths, 234
Parametral plane, 188
Parametral ratios, 188
Paris blue, 1319
Pans yellow, 1068
Partinium, 739
Paste, 609
Patent yellow, 924
Patronite, 944
Pearl ash, 369
Pearlite, 1263
Pectolite, 582
Pelopium, 974
Pentlandite, 1355
Perchlorates, 133
Perchromates, 1072
Perchromic acid, 1072
Percolumbic acid, 982
Period of average life, 1513
Period of half-change, 1513
Periodic system, 50, anomalies of, 71,74
Permanent white, 625, 629
Permanganic acid, 1187
Permanganic oxychloride, 1195
Permolybdic acid, 1111
Pertantahc acid, 993
Pervanadates, 956
Pervanadic acid, 956
Perofskite, 833, 839
Perosmio anhydride, 1427
Peroxides, 114
Perstannic acid, 889
Pertantahc acid, 993
Perthiomolybdates, 1112, 1119
Pertungstic aoid, 1138
Peruranates, 1156
Pervanadates, 956
Pervanadic acid, 956
Petalite, 242
Pewter, 1005
Pharaoh's serpent, 720
Pharmaoosidente, 1298
Phase rule, **124**

Phenacite, 636
Phosgenite, 903
Phosphides, 136
Phosphochalcite, 454
Phosphomolybdio acid, 1109
Phosphor-bronze, 882
Phosphorescence spectra, 157
Phosphorite, 575
Phosphotungstic acids, 1135
PhosphovanadiC acid, 970
Photography, 499
Pig iron, 1222, 1226, 1237, 1241
Pink salt, 895
Pitchblende, 1149, 1150, 1515
Plane of syminetry, 191
Plaster of Pans, 571
Platinates, 1469
Plating, 477
Platinibromic acid, 1470
Platinic acid, 1469
Platinic bromide, 1477
Platinic chloride, 1474
Platinic hydroxide, 1469
Platinic iodide, 1477
Platinic sulphate, 1479
Platinibromic acid, 1477
Platinichlonc acid, 1474
Platinichlondes, 1475
Platinicyanic acid, 1486
Platiniodic acid, 1477
Platiniridium, 1438
Platinising, 1468
Platinite, 1366
Platinithiocyanic acid, I486
Platinochlondes, 1472
Platinocyanic acid, 1483
Platinoid, 1365
Platinonitrites, 1479
Platino-platinic oxide, 1470
Platinosulphites, 1479
Platinotinoplatinates, 1478
Platinous bromide, 1476
Platinous chloride, 1471
Platinous cyanide, 1483
Platinous hydroxide, 1469
Platinous iodide, 1477
Platinum, 1451, action of various reagents on, 1467, ammoniacal compounds of, 1481, atomic weight of, 68,1489, colloidal, 1465, detection of, 1487, estimation of, 1489, fulminating, 1480, metallurgy of, 1453, preparation of pure, 1458, properties of, 1458, spongy, 1462, uses of, 1468, world's production of, 1458
Platinum arsenide, 1483
Platinum black, 1463
Platinum dioxide, 1469
Platinum fluorides, 1470
Platinum monochlonde, 1471
Platinum monoxide, 1468
Platinum ore, 1388, 1398, 1407, 1423, 1438, 1450, 1452, 1453
Platinum oxides, 1468
Platinum phosphides, 1483
Platinum selenide, 1479
Platinum sesquioxide, 1470
Platinum sulphides, 1477
Platinum telfundes, 1479
Platinum trichlonde, 1473
Platinum trioxide, 1470
Plumbates, 921
Plumbocaloite, 546
Pneumatogen, 338
Pollux, 386
Polonium, 1516
Polybasite, 461
Polycrase, 976
Polyhalite, 344
Polymorphism, 210
Polysphaente, 930
Porcelain, 760, 762
Portland cement, 583
Positive ray analysis, 75, 1493
Potash, 240
Potash alum, 754
Potashes, 369
Potash felspar, 334, 731, 759
Potash lye, 341
Potassamide, 357
Potassammonium, 392
Potassium, 332, atomic weight of, 69, 377, detection of, 375, dis covery of, 332, estimation of, 376, preparation of, 334, properties of, 337, sources of, 333
Potassium aluminate, 744
Potassium amalgam, 99, 699
Potassium ammonostannate, 898
Potassium antimonate, 1012
Potassium antimonyl tartrate, 1009
Potassium arsenate, 368
Potassium arsenide, 367
Potassium arsenite, 367
Potassium aurate, 529
Potassium aunbromide, 533
Potassium aunchlonde, 532
Potassium auncyanide, 541
Potassium auric sulphite, 536
Potassium aurochlonde, 530
Potassium aurocyanide, 540
Potassium azoimide, 356
Potassium borates, 368
Potassium bromate, 350
Potassium bromide, 346
Potassium carbide, 368
Potassium carbonate, 369
Potassium chlorate, 347
Potassium chlonde, 334, 344
Potassium chloroohromate, 1072
Potassium chloroplatinicyanide, 1484
Potassium chromate, 1062
Potassium chromic sulphate, 1080
Potassium chromicyanide, 1085
Potassium chromithiooypnate, 1086
Potassium chromocyanide, 1085
Potassium chromosulphate, **1083**

Potassium cobalticyanide, 1351
Potassium cobaltinitrite, 1343
Potassium oobaltooyanide, 1351
Potassium columbifluoride, 983
Potassium cyanate, 373
Potassium cyanide, 372
Potassium dichromate, 187, 1062
Potassium cusulphate, 356
Potassium di-uranate, 1155
Potassium ferricyanide, 1311
Potassium ferrocyanide, 1308,
Potassium fercodinitrososulphide,1294
Potassium ferrodinitrosothiosulphate, 1295
Potassium ferroheptanitrososulphide, 1295
Potassium fluorochromate, 1070
Potassium fluoride, 344
Potassium hexatantalate, 992
Potassium hydride, 343
Potassium hydrogen carbonate, 371
Potassium hydrogen sulphate, 355
Potassium hydrogen sulphite, 354
Potassium hydrosulphide, 352
Potassium hydroxide, 339
Potassium hypoantimonate, 1011
Potassium hypochlorite, 347
Potassium lodate, 350
Potassium iodide, 346
Potassium lodotetrachlonde, 347
Potassium indate, 1443
Potassium indibromide, 1445
Potassium indichloride, 1444
Potassium indicyanide, 1447
Potassium indiobromide, 1445
Potassium indiochloride, 1444
Potassium indiocyanide, 1447
Potassium indionitrite, 1447
Potassium manganate, 1186
Potassium manganichlonde, 1195
Potassium manganicyanide, 1203
Potassium manganifluonde, 1192
Potassium manganite, 1181
Potassium manganocyanide, 1203
Potassium metabisulphite, 354
Potassium metaphosphate, 367
Potassium metaplumbate, 921
Potassium metavanadate, 953
Potassium molybdates, 1106
Potassium monoxide, 339
Potassium nitrate, 358
Potassium nitrite, 357
Potassium nitroprusside, 1322
Potassium orthophosphate, 366
Potassium osmate, 1428
Potassium osmiamate, 1435
Potassium osmichlonde, 1432
Potassium osmoohlonde, 1431
Potassium osmooyanide, 1436
Potassium osmyl chloride, 1429
Potassium osmyl nitrite, 1429
Potassium palladichloride, 1417
Potassium palladiobromide, 1417
Potassium palladioeWoride, 1117
Potassium palladiocyanide, 1419
Potassium palladioiodide, 1418
Potassium palladionitrite, 1419
Potassium palladiothiocyanate, 1419
Potassium pentathiomolybdate, 1119
Potassium perborate, 368
Potassium percarbonate, 372
Potassium perchlorate, 232, 350
Potassium periodate, 192, 351
Potassium permanganate, 1189
Potassium peroxide, 342
Potassium per-ruthenate, 1392
Potassium persulphate, 356
Potassium pertantalate, 993
Potassium platinichlonde, 1475
Potassium platinithiocyanate, 1487
Potassium platinothioplatinate, 1478
Potassium platinobromide, 1477
potassium platinochlonde, 1472
Potassium platinocyanide, 1483
Potassium platinonitrite, 1479
Potassium platinosulphite, 1479
Potassium platinothiocyanate, 1486
Potassium polysulphides, 353
Potassium pyroantimonate, 1013
Potassium pyrophosphate, 367
Potassium rhodicyanide, 1405
Potassium ruthenate, 1392
Potassium ruthenichlonde, 1394
Potassium ruthenio-oyanide, 1397
Potassium selenate, 356
Potassium silicates, 374
Potassium silicofluonde, 375
Potassium silicotungstates, 1137
Potassium stannate, 887
Potassium stannifluoride, 893
Potassium sulphate, 198, 232, 237, 354
Potassium sulphide, 351
Potassium sulphite, 353
Potassium sulpho-carbonate, 372
Potassium tantalofluonde, 993
Potassium tetrachromate, 1065
Potassium tetrathiophosphate, 367
Potassium tetravanadate, 953
Potassium thioantimonate, 1023
Potassium thiomolybdate, 1119
Potassium thiocyanate, 374
Potassium thiostannate, 897
Potassium thiosulphate, 356
Potassium thorofluonde, 863
Potassium titanates, 838
Potassium titanofluonde, 841
Potassium triantimonite, 1010
Potassium trichromate, 1064
Potassium tri-iodide, 347
Potassium tungstates, 1132
Potassium ultramarine, 768
Potassium uranates, 1155
Potassium vanadio thiocyanate, 971
Potassium vanadite, 960
Potassium zirconofluonde, 853
Pottery, 760, 765
Powder of Algarotf, 1016
Powetyte, 1097

Praseodymium, 822, Compounds of, 823, detection of, 824
Prediction of undiscovered elements, 69
Preparing salts, 887
Principal valency, 37
Protactinium, 1527, 1532
Proton, 1508
Proustite, 461
Prout's hypothesis, 44
Prussian blue, 1302, 1314, 1315, 1316, 1318, 1319
Prusfian green, 1320
Prussiate of potash, red, 1311, yellow, 1308
Pseudomalachite, 454
Pseudoracemic compounds, 206
Psilomelane, 620, 1172
Psittacinite, 944
Puchente, 944, 1032
Puddling process, 1242
Purple of Cassius, 524
Puzzuolana, 582
Pyrargynte, 461, 999
Pyntic smelting, 424
Pyrochlor, 859
Pyrolusite, 1172, 1179
Pyromorphite, 903, 930
Pyrovanadic acid, 952
Pyrrhotite, 1285

Q

Quadratic system, 199
Quartation, 96
Quartz, 205
Quartz glass, 610
Quicksilver, 691

R

Racemic substances, 229
lladioactive change, products of, 1511, rate of, 1512
Radioactive elements, 1490, 1531
Radioactive elements and the periodic system, 1514, 1517
Radioactive recoil, 1505
Radioactive substances, discovery of, 1490
Radioactivity, measurement of, 1500, phenomena of, 1502
Radiotellunum, 1525
Radiothorium, 1528, 1531
Radium, 1515, atomic weight of, 1518, emanation, 1521, 1531, extraction of, 1515, 1516, heat emission by, 1510, 1523, spectrum of, 1518, spontaneous change of, 1520, transformation products of, 1520
Radium A, -B, -C, -D, -E, 1524, -F, 1525, G, 1526, C, C, 1514
Radium and uranium, 1530
Radium clock, 1508
Radium salts, preparation and properties of, 1516
Rare earths, 793, metals of the, 71, 74, separation of, 798
Reaction velocity, 140
Reaction velooity and temperature, 142, 146
Recalescenoe of iron, 1215, of steel, 1261
Red copper ore, 413, 436
Red lead, 115, 918
Red precipitate, 702
Red prussiate of potash, 1311
Red silver ore, 999
Regular system, 202
Regulus of Venus, 1005
Reversible reactions, 137
Rewdanskite, 1355, 1384
Rheostan, 1365
Rhodites, 1403
Rhodium, 1398, alloys, 1401, ammoniacal derivatives of, 1405, atomic weight of, 1406, colloidal, 1401, detection and estimation of, 1406, preparation of, 1398, properties of, 1400
Rhodium alums, 1404
Rhoblium black, 1400
Rhodium chloride, 1403
Rhodium hydroxides, 1402
Rhodium nitrate, 1405
Rhodium nitrite, 1404
Rhodium oxides, 1402
Rhodium sulphate, 1404
Rhodium sulphides, 1404
Rhodium sulphite, 1404
Rhodochlondes, 1403
Rhodocrosite, 1172, 1203
Rhodonite, 1204
Rhombic system, 198
Rhombohedral system, 200
Rinmann's green, 1334
Ripidolite, 731
Rock salt, 265, structure of, 220
Romente, 1291
Roman cement, 583
Romeite, 1011
Roscoelite, 944
Rose's metal, 1035
Rosin blende, 663
Rotatory polarisation, 204
Rubidamide, 384
Rubidium, 377_1 atomic weight of, 385, detection of, 385, discovery of, 171, estimation of, 3°5, occurrence of, 172, 379, preparation of, 382, properties of, 382, separation of, 381
Rubidium alum, 755
Rubidium carbonate, 385
Rubidium chlorate, 384
Rubidium chloride, 383
Rubidium hydride, 383
Rubidium hydroxide, 383

Rubidium nitrate, 384
Rubidium oxides, 383
Rubidium perohlorate, 384
Rubidium platinichlonde, 1476
Rubidium selenate, 384
Rubidium sulphate, 237, 384
Rubidium sulphides, 384
Ruby, 730, 740, synthetic, 741
Ruby glass, 606
Rupert's drops, 603
Rusting of iron, 1218
Rustless steel, 1054, 1220
Ruthctuochlorides, 1394
Ruthemocyanio acid, 1397
Ruthenium, 1388, ammoniaoal derivatives of, 1396, atomio weight of, 1398, detection and estimation of, 1398, preparation of, 1389, properties of, 1390
Ruthenium bromide, 1395
Ruthenium carbonyl, 1397
Ruthenium chlorides, 1394
Ruthenium dithionate, 1395
Ruthenium hydroxides, 1391, 1392
Ruthenium iodide, 1395
Ruthenium nitrosochlonde, 1396
Ruthenium oxides, 1391, 1392
Ruthenium oxychloride, 1394
Ruthenium silicide, 1397
Ruthenium sulphate, 1395
Ruthenium sulphides, 1395
Ruthenium sulphite, 1395
Rutile, 832, 833, 836

S

Sal-ammoniac, 394
Salt-cake process, 303
Saltpetre, 358
Saltpetre, Chih, 278
Salts, acid, 117, basic, 117, complex, 118, double, 118, 127, fusibility and volatility of, 131, generic properties of, 131, normal, 116, solubility of, 119
Salts, acids, and bases, 94
Sal volatile, 405
Samarium, 825, compounds of, 826
Samarskite, 795, 797, 976, 1150
Sapphire, 730, 739, synthetic, 741
Saxifragin, 631
Scandium, 70, 803, compounds of, 803
Scheele's green, 455
Scheelite, 1124, 1133
Schhppe's salt, 1023
Schonite, 355
Schorlomite, 833
Schweizer's reagent, 439
Selenite, 546, 568
Sellaite, 650
Semi porcelain, 765
Senarmontite, 238
Serpentine, 644
Setting of cements, 584
Sidente, 1225
Silicotungstic acids, 1136
Silver, 460, alloys of, 478, atomic weight of, 506, colloidal, 475, detection of, 505, electrolytic refining of, 471, electro-deposition of, 477, estimation of, 505, metallurgy of, 461, molecular, i 473, ores of, 460, preparation of pure, 472, properties of, *473, wet extraction of, 468, world's production of, 471
Silver acetj lide, 497
Silver alum, 756
Silver amalgam, 700
Silver amide, 494
Silver arsenate, 497
Silver arsenite, 497
Silver azoimide, 494
Silver bromide, 487
Silver carbide, 497
Sliver carbonate, 498
Silver chlorate, 491
Silver chloride, 484
Silver chlorite, 491
Silver chromate, 1066
Silver coinage, 479
Silver cyanamide, 498
Silver cyanate, 498
Silver cyanide, 498
Silver dichromate, 1067
Silver disulphide, 492
Silver fluoride, 483
Silver glance, 461
Silver hyponitrite, 49i
Silver iodide, 489
Silver nitrate, 495
Silver nitride, 494
Silver nitrite, 495
Silver oxide, 480
Silver permanganate, 1192
Silver peroxide, 481
Silver phosphates, 497
Silver phosphide, 497
Silver platinicyanido, 1486
Silver platinonitrite, 1480
Silver sodium thiosulphate, 498
Silver subfluonde, 483
Silver sulphate, 492
Silver sulphide, 491
Silver sulphite, 492
Silver thiocyanate, 493
Silver thiosulphate, 498
Silver ultramarine, 768
Silver vanadates, 956
Silvering, 476
Skutterudite, 1329, 1348
Slaked lime, 551
Smalt, 1352
Smaltite, 1329, 1348
Smithstote, 664

Soda, 240, 296, manufacture of, 296, 297, 298, 316, 317, 326, natural, 296
Soda ash, 290, 313
Soda by electrolytic processes, 325
Soda crystals, 290, 330
Soda from cryolite, 316
Soda glass, soluble, 293
Sodamide, 277
Sodammonium, 392
Soddite, 1150
Sodium, 253, atomic weight of, 295, compounds of, 259, detection of, 294, estimation of, 295, manufacture of, 254, occurrence of, 253 properties of, 257 spectroscopic detection of, 168, uses of, 258
Sodium alum, 756
Sodium alummate, 744
Sodium aluminium chloride, 747
Sodium amalgam, 99, 690
Sodium antimonate, 1013
Sodium antimonite, 1010
Sodium arsenates, 285
Sodium arsenide, 285
Sodium aurichloride, 532
Sodium aurosulphide, 534
Sodium aurothiosulphate, 536
Sodium aurous sulphite, 535
Sodium azoimide, 277
Sodium bicarbonate, 291, 331
Sodium borates, 286
Sodium bromide, 268
Sodium carbide, 289
Sodium carbonate, 290
Sodium chlorate, 270
Sodium chloride, 265
Sodium chromate, 1065
Sodium cyanide, 292
Sodium diohromate, 1065
Sodium dioxide, 262
Sodium disulphate, 275
Sodium disulphite, 273
Sodium di uranate, 1155
Sodium ferricyanide, 1313
Sodium ferrocyanide, 1309
Sodium fluoride, 265
Sodium hydrogen fluoride, 265
Sodium hexatantalate, 992
Sodium hexavanadate, 952
Sodium hydrate, 260
Sodium hydride, 264
Sodium hydrogen carbonate, 291
Sodium hydrogen peroxide, 263
Sodium hydrogen sulphate, 275
Sodium hydrogen sulphite, 272
Sodium hydroxide, 260
Sodium hypochlorite, 268
Sodium hypophosphite, 279
Sodium hyposulphite, 272
Sodium iodide, 968
Sodium indichloride, 1445
Sodium manganate, **1187**
Sodium metabisulphite, 273
Sodium metaborate, 288
Sodium metaphosphates, 283
Sodium metastannate, 888
Sodium metavanadate, 952, 954
Sodium molybdates, 1105
Sodium monoxide, 259
Sodium nitrate, 200, 278
Sodium nitrite, 277
Sodium nitroprusside, 1322
Sodium orthophosphates, 280
Sodium orthovanadate, 963
Sodium osmate, 1427
Sodium osmichlonde, 1432
Sodium osminitrite, 1435
Sodium osmisulphite, 1433
Sodium pailadiosulphite, 1418
Sodium porborate, 288
Sodium percarbonate, 292
Sodium perchlorate, 271
Sodium permanganate, 1189
Sodium peruranate, 1157
Sodium phosphide, 279
Sodium platinichlonde, 147b
Sodium platinosulphite, 1479
Sodium platinothiosulphate, 1479
Sodium polyphosphate, 282
Sodium pyroantimonate, 1013
Sodium pyroborate, 286
Sodium pyrophosphates, 282
Sodium pyrovanadate, 952, 954
Sodium rhodochlonde, 1403
Sodium seleno antimonate, 1025
Sodium sesquicarbonate, 331
Sodium silicates, 293
Sodium sihcofluonde, 294
Sodium stannate, 887
Sodium suboxide, 259
Sodium sulphate, 273, solubihty of, 125
Sodium sulphides, 271
Sodium sulphite, 272
Sodium sulphonosmate, 1434
Sodium tantalofluoride, 993
Sodium tetravanadate, 952, 954
Sodium thioantimonate, 1023
Sodium thiopalladate, 1418
Sodium thiostannate, 897
Sodium thiosulphate, 275
Sodium titanate, 839
Sodium titanofluonde, 841
Sodium trioxide, 264
Sodium trithiophosphite, 280
Sodium tungstates, 1131
Sodium vanadite, 960
Sodium zirconate, 852
Soft soap, 342
Sohncke systems, 216
Solar atmosphere, 178
Solar spectrum, 178
Solder, 880
Solubility of alloys, 91, of salts, 119
Soluble soda glass, 293

Solvay's apparatus, 320
Sombrerite, 575
iSorawallahs, 358
Sorbite, 1263
Space lattice, 214
Spark spectra, 154
Spathic iron ore, 1212, 1222, 1225, 1300
Speoific gravity of the elements, 59
Specific heat of metals, 15
Spectra, flame, 154, arc 154, spark, 154, X ray, 157, 163, mapping and measuring, 157, , variations in, 161, of the elements, 162, of isotopes, 163, 178, of compounds, 164, absorption, 173
Spectral lines, relations befrwocn, 165
Spectroscope, 152
Spectroscope and chemical analysis, 168
Spectrum analysis, 148
Specular iron, 1239
Specular iron ore, 1212, 1224
Speculum metal, 880
Speiss cobalt, 1239
Sper ylite, 1452
Sphene, 833, 839
Spiegel iron, 1239
Spinel, 644, 745
Spinthariscope, 1504
Spodumene, 242
Stainless steel, 1054, 1220
Stannates, 886
Stannibromides, 896
Stannichlondes, 895
Stannifluondes, 893
Stannic acids, 885
Stannic bromide, 895
Stannic chloride, 893
Stannic fluoride, 892
Stannic hydroxides, 885
Stannic iodide, 896
Stannic nitrate, 898
Stannic oxide, 884
Stannic oxysulphide, 898
Stannic pyrophosphate, 899
Stannic sulphate, 898
Stannic sulphide, 896
Stannous bromide, 890
Stannous chloride, 890
Stannous fluoride, 889
Stannous iodide, 891
Stannous nitrate, 892
Stannous oxide, 883
Stannous sulphate, 892
Stannous sulphide, 891
Stassfurt minerals, 128
Stassfurt salts, 344
Steel, 1222, 1246, 1259, 1261, 1262
Steel bronze, 739
Stellar spectra, $81
Stephanite, 461
Stibine, 1006
Stibio-tantalite, 975
Stiblite, 999
Stibnite, 997,1018
Stolzite, 903, 1124, 1133
Stoneware, 764
Stream tin, 873, 884
Stromeyente, 461
Strontia, 614
Strontianite, 612, 617
Strontium, 612, atomic weight of, 618, compounds of, 614, detection of, 618, estimation of, 618, preparation of, 613, properties of, 614
Strontium arsenide, 617
Strontium boride, 617
Strontium carbonate, 617
Strontium chloride, 615
Strontium ferrocyanide, 1310
Strontium hydride, 615
Strontium hydroxide, 614
Strontium nitrate, 617
Strontium nitride, 617
Strontium oxides, 614
Strontium phosphide, 617
Strontium sulphate, 616
Strontium sulphide, 610
Suboxides, 115
Sunt, 334
Sulphates, 135
Sulphides, 133
Sulphites, 134
Sulphomolybdic acid, 1119
Sulphonosmates, 1434
Sulphur, 211
Sulvanite, 944
Superphosphate of lime, 576
Supersaturated solutions, 129
Supersaturation, relief of, 234
Supersolubihty curve, 130
Supplementary valency, 37
Syepoorite, 1340
Sylvanite, 507
Sylvine, 334, 344, structure of, 220
Syminetry of crystals, 190
Sympathetic inks, 1339
Syngenite, 572

T

Tachhydnte, 344, 553, 651
Tachyol, 483
Talc, 644
Tantalates, 992
Tantalio acid, 992
Tantalite, 973, 975, 977
Tantalum, 990, atomic weight of, 996, detection of, 987, halide bases of, 995, preparation of, 990, properties of, 990
Tantalum carbide, 996#
Tantalum compounds, extraction of, 976

Tantalum nitrides, 996
Tantalum oxides, 991
Tantalum pentabromide, 994
Tantalum pentaohlonde, 994
Tantalum pentafluonde, 993
Tantalum pentaiodide, 995
Tantalum sulphide, 996
Tap cnider, 1245
Tartar emetio, 1009, 1027
Telluric bismuth, 1032
Tellurium, atomic weight of, 69
Tenonte, 413
Tephxoite, 1204
Terbium, 827
Tesseral system, 202
Tetartohedral form, 204
Tetradymite, 1032, 1044
Tetragonal system, 199
Thallic bromide, 790
Thallic chloride, 789
Thallic hydroxide, 789
Thallic nitrate, 791
Thallic sulphate, 790
Thallic sulphide, 790
Thallium, 781, atomic weight of, 792, compounds of, 783, detec tion of, 791, discovery of, 172, estimation of, 792, preparation of, 781, properties of, 782
Thallium alum, 786
Thallium monoxide, 783
Thallium phosphates, 787
Thallium silicate, 788
Thallium trioxide, 788
Thallous borate, 788
Thallous bromide, 784
Thallous carbonate, 787
Thallous chlorate, 785
Thallous chloride, 784
Thallous cyanide, 787
Thallous fluoride, 784
Thallous hydroxide, 783
Thallous iodide, 785
Thallous nitrate, 786
Thallous perchlorate, 785
Thallous sulphate, 786
Thallous sulphide, 785
Thenard's blue, 1333
Thermal classification of alloys, 87
Thermite, 737, 1053
Thermonatrite, 290
Thioantinomites, 1021
Thiostannic acid, 897
Thiotungstates, 1145
Thona, 862
Thonanite, 796, 859, 860
Thorite, 859, 860, 862
Thorium, 859, atomic weight of, 867, compounds of, 862, detec tion of, 867, estimation of, 867, preparation of, 861, properties of, 862, radio-ac£ivity of, 1527
Thorium bondes, 866
Thorium carbide, 866
Thorium carbonates, 866
Thorium chloride, 864
Thorium emanation, 1528, 1531
Thorium fluoride, 864
Thorium hydride, 863
Thorium nitrate, 866
Thorium nitride, 866
Thorium oxides, 862, 863
Thorium phosphate, 866
Thorium silicide, 866
Thorium sulphate, 865
Thorium sulphide, 865
Thorium-X, 1527, 1531
Thulium, 828
Tiers Argent, 739
Tin, 872, alloys of, 880, atomic weight of, 901, compounds of, 883, detection of, 900, estimation, of, 900, metallurgy of, 873, properties of, 877, uses of, 879
Tin amalgam, 882
Tin hydride, 892
Tin peroxide, 889
Tin phosphides, 899
Tin pyrites, 873
Tin salt, 890
Tincal, 286
Tinstone, 873, 884
Titanamide, 843
Titanic acids, 837
Titanic iron ore, 839
Titanite, 833, 839
Titanium, 832, atomic weight of, 849, compounds of, 835, detec tion of, 848, estimation of, 848, preparation of, 833, properties of, 834
Titanium bromides, 844
Titanium carbide, 847
Titanium chlorides, 841
Titanium cyanonitride, 847
Titanium dichloride, 841
Titanium fluorides, 840
Titanium iodides, 844
Titanium nitrides, 846
Titanium oxides, 835
Titanium oxychlonde, 844
Titanium sulphates, 845
Titanium sulphides, 845
Titanium tetrachloride, 842
Titanium trichloride, 841
Titanium trioxide, 839
Tiza, 287
Tombac, 671
Topaz, 759, oriental, 740
Topic axes, 236
Torbernite, 1150
Tourmaline, 644
Transition interval, 128
Transition temperature, 122
Trichromyl chloride, 1071
Triclinio system, 196
Trigonal system, 200
Trunanganese tetroxide, 1177

Triphane, 242
Teiphylite, 242, 379
Trogente, 1166
Troilite, 1282
Trona, 292
Troostite, 1263
Tungstates, 1129
Tungsten, 1124, alloys of, 1127* atomic weight of, 1148, detection of, 1147, estimation of, 1148, preparation of, 1124, properties of, 1125
Tungsten arsenide, 1146
Tungsten boride, 1147
Tungsten bronzes, 1134
Tungsten carbides, 1146
Tungsten chlorosulphide, 1145
Tungsten dibromide, 1143
Tungsten dichloride, 1140
Tungsten di iodide, 1144
Tungsten dioxide, 1127
Tungsten disuiphide, 1145
Tungsten hexabromide, 1144
Tungsten hexachlonde, 1141
Tungsten hexafluonde, 1138
Tungsten nitride, 1146
Tungsten oxybromides, 1144
Tungsten oxychlondes, 1143
Tungsten oxyfluondes, 1139
Tungsten pentabromide, 1144
Tungsten pentachloride, 1141
Tungsten phosphides, 1146
Tungsten sesquioxide, 1127
Tungsten silicide, 1147
Tungsten tetrachloride, 1140
Tungsten tetra iodide, 1144
Tungsten trichloride, 1140
Tungsten trioxide, 1128
Tungsten trisulphide, 1145
Tungsten tungstates, 1134
Tungstenite, 1124
Tungstio acid, 1129
Tung8tosihcic acid, 1136
Turnbull's blue, 1319
Turner's yellow, 924
Turquoise, 758
Twin crystals, 205
Type metal, 1004

Ullmannite, 999,
Ultramarine, 7[illegible]
Uranates 115[illegible]6, yellow, 1067
Uranio hydrox[illegible]
Uranio oxide, [illegible]ide, 1154
Uranmite, 11[illegible]1154
Uranium, 11[illegible]49
60, 1160, [illegible]49, atomic weight of, estimation of, 1151, detection of, 1167, of, 1168, preparation of, 1151, radioactiv[illegible] properties of, 1151, Uranium an[illegible]ity of, 1528
[illegible]d radium, 1530

Uranium arsenide, 1165
Uranium bonde, 1166
Uranium carbide, 1166
Uranium difluonde, 1157
Uranium dioxide, 1153
Uranium hexafluonde, 1158
Uranium mica, 1150
Uranium nitride, 1164
Uranium oxybromide, 1161
Uranium oxyohlonde, 1169, 1160
Uranium pentachloride, 1159
Uranium pentoxide, 1156
Uranium peroxide, 1156
Uranium phosphide, 1165
Uranium radium series, 1531
Uranium red, 1162
Uranium selenides, 1163
Uranium sesquisulphide, 1161
Uranium silicide, 1167
Uranium tellunde, 1163
Uranium tetrabromide, 1161
Uranium tetrachloride, 1158
Uranium tetrafluonde, 1157
Uranium tetraiodide, 1161
Uranium tribromide, 1161
Uranium trichloride, 1158
Uranium X, 1529, 1531
Uranium yellow, 1155
Uranoso uranic oxide 1156

Uranospathite, 1149
Uranospinite, 1166

Uranothallite, 1150
Uranous chloride, 1168
Uranous fluoride, 1157
Uranous hydroxide, 1153
Uranous oxyfluonde, 1158
Uranous phosphates, 1165
Uranous sulphate, 1163
Uranous sulphide, 1161
Uranyl arsenates, 1166
Uranyl bromide, 1161
Uranyl carbonates, 1166
Uranyl chloride, 1160
Uranyl oyanides, 1167
Uranyl fluoride, 1168
Uranyl hypophosphite, 1165
Uranyl iodide, 1161
Uranyl nitrate, 1164
Uranyl oxide, 1154
Uranyl phosphates, 1165
Uranyl selenide, 1163
Uranyl sulphate, 1164
Uranyl sulphide, 1162
Uranyl sulphite, 1163
Urao, 292
Uvarovite, 1052

Valency, 28, 36, 39.57
Valentinite, 999, 1008
Vanars, 952

Vanadio acids, 951
Vanadio anhydride, 960
Vanadinite, 944
Vanadious sulphate, 966
Vanadites, 960
Vanadium, 943, alloys of, 949, atomic weight of, 972, detection of, 971, estimation of, 972, preparation of, 945, properties of, 948
Vanadium alums, 967
Vanadium bronze, 951
Vanadium carbide, 970
Vanadium chlorides, 961
Vanadium cyanides, 970
Vanadium dichloride, 963
Vanadium dioxide, 959
Vanadium fluorides, 961
Vanadium group, 942
Vanadium monoxide, 957
Vanadium nitrides, 969
Vanadium oxides, 949
Vanadium oxychlondes, 962
Vanadium sesquioxide, 959
Vanadium sesquisulphate, 967
Vanadium silicides, 971
Vanadmm suboxide, 957
Vanadium Sulphates, 966
Vanadium tetrachides 965
Vanadium thiocyanatede 962
Vanadium tribromide, 965 970
Vanadium trichloride, 962
Vanadyl bromides, 965
Vanadyl chlorides, 964
Vanadyl sulphates, 968
Vanadyl sulphite, 966
Vanadyl trichloride, 963
Vapour density of metallic compounds, 14, 32
Vauquelinite, 1066
Vauquelin's salt, 1421
Velocity coefficient, 140
Velocity of reaction, 140
Venetian white, 933
Verdigris, 456
Vermilion, 716
Vitriol, blue, 449
Vitriol, green, 1287
Vitriol, white, 677
Vitriol ochre, 1291
Vivianite, 1296
Voglite, 1150
Volatility of salts, 131
Volborthite, 944
Vrbaite, 781

W

Wad, 1329
Walpurgite, 1166
Washing soda, 290
Wavellite, 758
Wefrstente, 750
Weldon process, 1181
Werners theory of valency, 36
White lead, 931
White metal, 1005
White precipitate, 722
White vitriol, 677
Whitneyite, 454
Wukite, 803
Williamson's violet, 1317
Withente, 620, 631
Wolfram, 1124, 1133
Wolframochre, 1124
Wolfsbergite, 998
Wollastonite, 582
Wood tin, 884
Wood's metal, 1035
Wrought iron, 1222, 1239, 1246
Wulfenite, 903, 1097
Wurtzite, 677

X

Xenotime, 796
Xonalite, 582
X rays, 1492
X ray spectra, 157, 163, 1534
X ray spectrometer, 219
X ray analysis of crystal structure, 21b, powder method of, 223, results of, 223

Yellow prussiate of potash, 1308, of soda, 1309
yellow ultramarine, 1067
cotrium, 805, atomic weight of, 808, deterpounds of, 806, 807, 808,
atalite, 973, 976

Zaffre, 1329, 1..
Zinc, 661, alloy [illegible] **49**
derivatives of, [illegible] **s of, 671, ammoniacal**
of, 683, compo [illegible] **681, atomic weight**
tion of, 682, [illegible] **unds of, 672, detec-**
properties of, [illegible] **estimation of, 683,**
664. uses of, 67[illegible] **68, smelting of,**
Zinc amide, 680
Zinc blende, 663, 67
Zinc bromide, 676
Zinc carbonates, 681
Zinc chloride, 675
Zinc chromates, 1067
Zinc chromite, 1058
Zinc cyanide, 681
Zinc dust, 670
Zinc ferrite, 1273
Zinc ferrocyanide, 1310

Zinc hydrazide, 680
Zinc hydroxide, 673
Zinc iodide, 676
Zinc nitrate, 680
Zinc nitride, 679
Zinc oxide, 672
Zinc oxyohlondes, 676
Zinc peroxide, 674
Zinc phosphates, 680
Zinc phosphide, 680
Zinc spar, 664, 681
Zinc spinel, 664, 745
Zinc sulphate, 677
Zinc sulphide, 677
Zinc thiosulphate, 679
Zinc white, 672
Zinc yellow, 1067
Zinckenite, 903
Zircon, 199, 232, 849, 851, 857
Zirconia, 851
Zirconium, 849, atomic weight of, 858, detection of, 857, estimation of, 858, preparation of, 850, properties of, 851
Zirconium bonde, 856
Zirconium bromide, 854
Zirconium carbides, 856
Zirconium chloride, 854
Zirconium fluoride, 853
Zirconium hydride, 853
Zirconium iodide, 855
Zirconium nitrate, 856
Zirconium nitrides, 856
Zirconium oxide, 851
Zirconium peroxide, 853
Zirconium seaquioxide, 853
Zirconium silicates, 857
Zirconium silicide, 857
Zirconium sulphate, 855
Zirconium sulphide, 855